

## 300 °C GaN/AlGa<sub>N</sub> Heterojunction Bipolar Transistor

Fan Ren<sup>1</sup>, Cammy R. Abernathy<sup>2</sup>, J. M. Van Hove<sup>3</sup>, P. P. Chow<sup>3</sup>, R. Hickman<sup>3</sup>, JJ Klaasen<sup>3</sup>, R. F. Kopf<sup>4</sup>, Hyun Cho<sup>2</sup>, K. B. Jung<sup>2</sup>, J. R. La Roche<sup>1</sup>, R. G. Wilson<sup>5</sup>, J. Han<sup>6</sup>, R. J. Shul<sup>6</sup>, A. G. Baca<sup>6</sup> and S.J. Pearton<sup>2</sup>

<sup>1</sup>Department of Chemical Engineering, University of Florida,

<sup>2</sup>Department of Materials Science and Engineering, University of Florida,

<sup>3</sup>Blue Lotus Micro Devices, an SVT Associates company,

<sup>4</sup>Bell Laboratories, Lucent Technologies,

<sup>5</sup>Charles Evans and Associates,

<sup>6</sup>Sandia National Laboratories/New Mexico,

(Received Tuesday, September 8, 1998; accepted Wednesday, October 21, 1998)

A GaN/AlGa<sub>N</sub> heterojunction bipolar transistor has been fabricated using Cl<sub>2</sub>/Ar dry etching for mesa formation. As the hole concentration increases due to more efficient ionization of the Mg acceptors at elevated temperatures (> 250°C), the device shows improved gain. Future efforts should focus on methods for reducing base resistance, which are briefly summarized.

### 1 Introduction

There is a strong interest in developing wide bandgap semiconductor heterojunction bipolar transistor (HBTs) for applications in wide bandwidth (initially 1-5GHz, eventually 5-25GHz) amplifiers employed in radar and communication systems. The GaN/AlGa<sub>N</sub> heterostructure system is an attractive one for these devices, [1] [2] [3] [4] based on the remarkable success of the existing laser and light-emitting diode technology. [5] The wide bandgaps of the nitrides allow for higher temperature device operation (e.g. an  $n_i$  of  $10^{15}\text{cm}^{-3}$  would be reached at 300°C in Si, 500°C in GaAs, but in excess of 1000°C in GaN), reducing the thermal management issues. Pankove et.al. [6] reported a GaN/SiC HBT operable to 535°C with gain of 100 and current density  $1.84 \times 10^3 \text{A}\cdot\text{cm}^{-2}$ . The barrier to hole injection from the p-SiC base to the GaN was measured to be 0.43eV, in good agreement with the band-offsets.

In this paper we report the fabrication and high temperature operation of a GaN/AlGa<sub>N</sub> HBT grown by a hybrid method. The active regions are grown by Molecular Beam Epitaxy (MBE) on a thick GaN buffer grown by Metal Organic Chemical Vapor Deposition (MOCVD). The device shows improved gain above 250°C as the hole density in the base increases and leads to lower base resistance. The device performance is still limited by the base doping, but there are various

approaches that appear promising for improving this aspect.

### 2 Experimental

A highly resistive undoped buffer of  $\sim 2\mu\text{m}$  thick GaN, grown on c-plane (0001) sapphire, was used as the substrate for subsequent growth of the active device by RF-MBE. This structure formed a template for subsequent growth of the active regions by rf atomic nitrogen MBE at a rate of  $\sim 0.5\mu\text{m}\cdot\text{hr}^{-1}$ . [7] The Si-doped ( $\sim 10^{18}\text{cm}^{-3}$ ) GaN sub-collector ( $0.8\mu\text{m}$  thick) was followed by a  $0.5\mu\text{m}$ , Si-doped ( $10^{17}\text{cm}^{-3}$ ) GaN collector. Then a  $0.15\mu\text{m}$  Mg-doped GaN base was deposited under process conditions calibrated for  $1 \times 10^{18}\text{cm}^{-3}$  p-type carrier concentration as determined by Hall effect measurement. The epitaxy was completed with a  $0.1\mu\text{m}$  thick, Si-doped ( $5 \times 10^{17}\text{cm}^{-3}$ ) Al<sub>0.15</sub>Ga<sub>0.85</sub>N emitter, a  $0.05\mu\text{m}$  graded Al<sub>x</sub>Ga<sub>1-x</sub>N ( $x = 0.15-0$ ,  $8 \times 10^{18}\text{cm}^{-3}$ ) region to a  $0.2\mu\text{m}$  thick, Si-doped ( $8 \times 10^{18}\text{cm}^{-3}$ ) GaN contact layer.

Large area ( $\sim 90\mu\text{m}$  diameter) devices were fabricated using a Cl<sub>2</sub>/Ar Inductively Coupled Plasma (ICP) etch process to expose both the base and sub-collector regions. [8] AZ5209E photoresist was used as an etch mask, and etching was performed in a Plasma Therm 790 system. The operating pressure was 2mTorr, and the source and rf chuck power were kept relatively lightly doped (300W and 40W, respectively) to minimize ion

damage to the GaN. It is generally found that dry etch processes tend to produce N<sub>2</sub>-deficient surfaces on GaN that are strongly n-type. [9] This is an advantage when stopping at an existing n-type layer, because ohmic contact resistance will be improved. However to avoid this problem at the emitter-base junction, we terminated the etching ~100Å above the junction, then oxidized the surface using ozone, and stripped this in an acid solution. Ti/Al/Pt/Au n-type metallization and Ni/Pt/Au p-type metallization were deposited by e-beam evaporation to contact the emitter, base and sub-collector. A schematic of the completed structure is shown in Figure 1. Device characterization was performed with a HP 4145 parameter analyzer.

### 3 Results and Discussion

Figure 2 shows the forward current voltage (I-V) characteristics of the emitter-base junction at both 25 and 300°C. The relatively low hole concentration in the base at room temperature (a few 10<sup>17</sup>cm<sup>-3</sup> based on the Mg ionization level of ~0.17eV), leads to a strong influence of the series resistance on the I-V characteristic. The low bias current at 300°C is about an order of magnitude higher than at 25°C due to the increase of thermionic current. The improvement in base contact I-V characteristic with increasing temperature is shown in Figure 3. As is fairly typical of p-contacts on GaN, the behavior is really that of a leaky Schottky-barrier at room temperature. [10] [11] The best characteristics were obtained after annealing the Ni/Au at 700°C for 20secs, consistent with past reports. At higher annealing temperatures the I-V characteristics degraded and in some cases shorting of the devices was observed. We ascribe these observations to punch-through of the base metallization.

The base-collector junction forward I-V characteristics are shown in Figure 4. Similar comments apply as for the e-b junction, with the high base resistance having a strong influence. For this reason it was not possible to obtain a meaningful ideality factor.

A Gummel plot for the HBT at 300°C is shown in Figure 5. The dc current gain is around 10 at this temperature because of the improvement in base resistance.

There are several approaches possible for improving the HBT performance. One would be to induce a higher hole concentration in the base through piezoelectric stress. A number of recent studies have demonstrated and analyzed the influence of the piezoelectric effort on III-nitride devices, [12] [13] [14] [15] [16] particularly heterostructure field effect transistors. In these structures piezo-induced electrons increase the conductivity in the channel of an AlGaIn/GaN epitaxial structure. To induce more holes in the base of an HBT, one could consider placing an appropriate stress layer between the base and collector. A second alternative is to decrease

base resistance by employing a lower gap material such as InGaIn or SiC. There are still problems with these choices because of the difficulty in achieving high p-type doping in both materials- in In<sub>x</sub>Ga<sub>1-x</sub>N there is a strong tendency for high n-type backgrounds, but p-type conductivity has been achieved for In compositions up to ~x=0.15, while the Al Acceptor in SiC has a large ionization level (~0.2eV).

The third alternative and probably the most attractive, is selective regrowth of the extrinsic base region. [17] [18] The base doping typically represents a trade-off between base contact resistance and gain. By employing a separate regrowth step, it is possible to optimize both parameters. The intrinsic base material under the emitter can be relatively low in order to increase the minority carrier lifetime and hence the gain and base thickness reduced to decrease base transit time and hence speed. By selectively regrowing a heavily doped extrinsic base contact layer, the parasitic losses associated with the base contact resistance can be significantly reduced. Potential candidates for the regrown p<sup>+</sup> material include GaAs (C) and GaP (C) which can attain hole concentrations in excess of 10<sup>21</sup>cm<sup>-3</sup>. [17] The main issue would then be hole transport across the heterointerface, and compositional grading of the base material might also be necessary.

### 4 Summary and Conclusions

A GaN/AlGaIn HBT operating at 300°C has been demonstrated, using an MBE-grown structure. Mesa formation has achieved with ICP Cl<sub>2</sub>/Ar dry etching, combined with a wet etch clean-up step at the emitter-base junction. Base resistance limits the performance in this initial device design, but several options exist for future development in this area.

### ACKNOWLEDGMENTS

**The work at UF is partially supported by ONR grant N00014-98-1-0204 (J.C. Zolper) and a DARPA/EPRI grant MDA-972-98-1-0006 (E.R. Brown/J. Melcher). Sandia is a multiprogram laboratory operated by Sandia Corporation, a Lockheed-Martin company, for the US Department of Energy under contract DEAC04-95-AC85000.**

### REFERENCES

- [1] M. S. Shur, *Mater. Res. Soc. Symp. Proc.* **483**, 15 (1998).
- [2] M.S. Shur and M.A. Khan, "GaN Based Electronics and Photonics", in *High Temperature Electronics*, ed. M. Willander and H.L. Hartnagel (Chapman and Hall, London 1996), pp. 297-321
- [3] M. N. Yoder, *IEEE Trans. Electr. Dev.* **43**, 1633 (1996).

- [4] T. P. Chow, N. Ramungul, M. Ghezzi, *Mater. Res. Soc. Symp. Proc.* **483**, 89 (1998).
- [5] S. Nakamura, M. Senoh, S. Nagahama, N. Iwasa, T. Yamada, T. Matsushita, H. Kiyoku, Y. Sugimoto, T. Kozaki, H. Umemoto, M. Sano, K. Chocho, *Jpn. J. Appl. Phys.* **36**, L1568 (1997).
- [6] J. I. Pankove, M. Leksono, S. S. Chang, C. Walker, B. Van Zeghbroeck, *MRS Internet J. Nitride Semicond. Res.* **1**, 39 (1996).
- [7] J.M. Van Hove, P.P. Chow, J.J. Klaassen, R. Hickman, A.M. Wowchak, D.R. Croswell, C. Polley, *Mater. Res. Soc. Symp. Proc.* **468**, 51 (1997).
- [8] R.J. Shul, G.B. McClellan, S.A. Casalnuovo, D.J. Rieger, S.J. Pearton, C. Constantine, C. Barratt, R.F. Karlicek, C. Tran, M. Schurman, *Appl. Phys. Lett.* **69**, 1119-1121 (1996).
- [9] S.J. Pearton and R.J. Shul, "Wet and Dry Etching of GaN", in GaN I. ed. J.I. Pankove and T.D. Moustakas (Academic Press, NY 1998)
- [10] L. F. Lester, D. J. King, L. Zhang, J. C. Ramer, S. D. Hersee, J. C. Zolper, *Electrochem. Soc. Proc.* **97-1**, 171 (1997).
- [11] D.J. King, L. Zhang, J.C. Ramer, S.D. Hersee, L.F. Lester, *Mater. Res. Soc. Symp. Proc.* **468**, 421 (1997).
- [12] Alexei Bykhovski, Boris Gelmont, Michael Shur, *J. Appl. Phys.* **74**, 6734-6739 (1993).
- [13] E. T. Yu, P. M. Asbeck, S. S. Lau, G. J. Sullivan, *Electrochem. Soc. Proc.* **98-2**, 468 (1998).
- [14] R. Gaska, J. W. Yang, A. D. Bykhovski, M. S. Shur, V. V. Kaminskii, S. Soloviov, *Appl. Phys. Lett.* **72**, 64-66 (1998).
- [15] P.M. Asbeck, E.T. Yu, S.S. Lau, G.J. Sullivan, J. Van Hove, J. Redwing, *Electron. Lett.* **33**, 1230-1231 (1997).
- [16] E. T. Yu, G. J. Sullivan, P. M. Asbeck, C. D. Wang, D. Qiao, S. S. Lau, *Appl. Phys. Lett.* **71**, 2794 (1997).
- [17] See "Topics in Growth and Device Processing of III-V Semiconductors", S.J. Pearton, C.R. Abernathy and F. Ren (World Scientific, Singapore, 1997) Chapter 2
- [18] H. Simawaki, *Inst. Phys. Conf. Ser.* **129**, 271 (1993).

## FIGURES

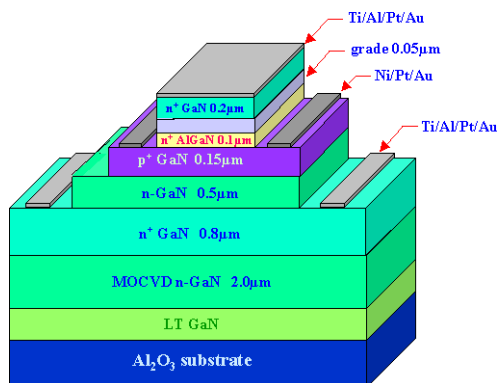


Figure 1. Schematic of GaN/AlGaN HBT

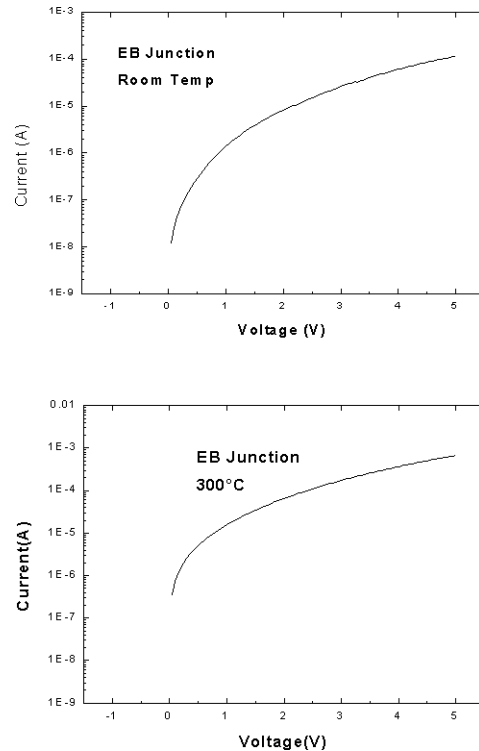


Figure 2. HBT emitter-base junction forward I-V characteristics at 25°C (top) and 300°C (bottom).

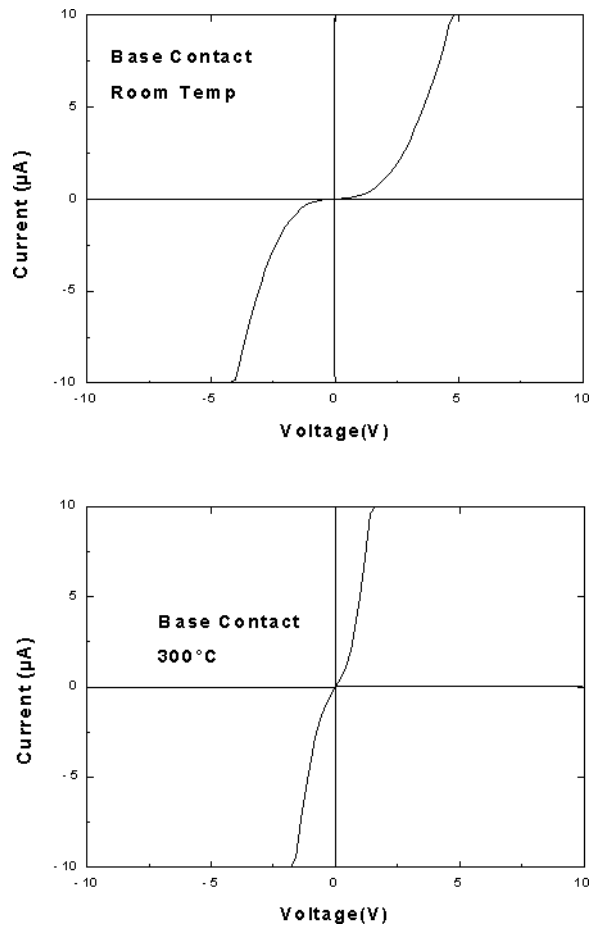


Figure 3. Ni/Pt/Au base contact I-V characteristics at 25°C (top) and 300°C (bottom).

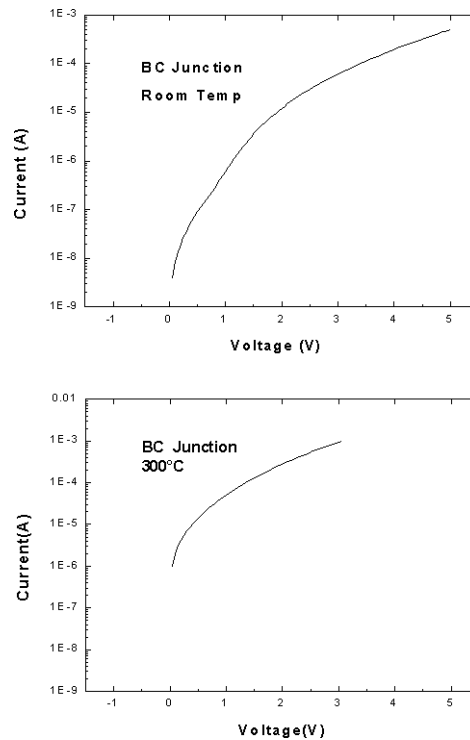


Figure 4. HBT base-collector junction forward I-V characteristics at 25°C (top) and 300°C (bottom).

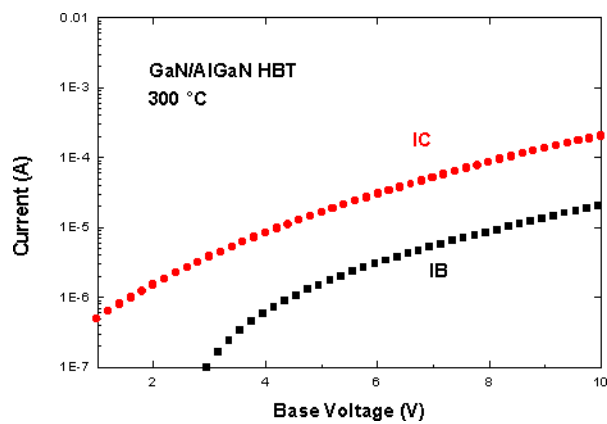


Figure 5. Gummel plot for a 90µm diameter GaN/AlGaIn HBT at 300°C.