

A Class of Organopolysulfides as Liquid Cathode Materials for High Energy Density Lithium Batteries

Amruth Bhargav[†], Michaela Elaine Bell[†], Jonathan Karty[§], Yi Cui^{†#}, and Yongzhu Fu^{†‡*}

[†] Department of Mechanical Engineering, Indiana University-Purdue University Indianapolis, Indianapolis, IN 46202, United States

[‡] College of Chemistry and Molecular Engineering, Zhengzhou University, Zhengzhou 450001, China

[§] Department of Chemistry, Indiana University, Bloomington, IN 47405, United States

[#] School of Mechanical Engineering, Purdue University, West Lafayette, IN 47907, United States

*Corresponding author: yfu@zzu.edu.cn (Y. Fu)

KEYWORDS - organopolysulfide, phenyl polysulfide, lithium battery, specific energy, energy density

Abstract

Sulfur-based cathodes are promising to enable high energy density lithium-sulfur batteries; however, elemental sulfur as active material faces several challenges including undesirable volume change (~80%) when completely reduced and high dependence on liquid electrolyte wherein an electrolyte/sulfur ratio $>10 \mu\text{L mg}^{-1}$ is required for high material utilization. These limit the attainable energy densities of these batteries. Herein, we introduce a new class of phenyl polysulfides $\text{C}_6\text{H}_5\text{S}_x\text{C}_6\text{H}_5$ ($4 \leq x \leq 6$) as liquid cathode materials synthesized in a facile and scalable route to mitigate these setbacks. These polysulfides possess sufficiently

1
2
3 high theoretical specific capacities, specific energies, and energy densities. Spectroscopic
4
5 techniques verify their chemical composition and computation shows that the volume change
6
7 when reduced is about 37%. Lithium half-cell testing shows that phenyl hexasulfide
8
9 ($\text{C}_6\text{H}_5\text{S}_6\text{C}_6\text{H}_5$) can provide a specific capacity of 650 mAh g^{-1} and capacity retention of 80%
10
11 through 500 cycles at 1C rate along with superlative performance up to 10C. Furthermore, 1,302
12
13 Wh kg^{-1} and $1,720 \text{ Wh L}^{-1}$ are achievable at a low electrolyte/active material ratio, *i.e.*, $3 \mu\text{L mg}^{-1}$
14
15 ¹. This work adds new members to the cathode family for Li-S batteries, reduces the gap between
16
17 the theoretical and practical energy densities of batteries, and provides a new direction for the
18
19 development of alternative high-capacity cathode materials.
20
21
22
23
24
25

26 From waking up to alarms on a cellphone to getting around in electric cars, our everyday
27
28 lives are progressively relying on rechargeable batteries. The dramatic advances in these systems
29
30 have been the major driving force for scientists to explore new materials that enable batteries
31
32 with higher specific energy and energy density. Society has been so far reliant on solid metal
33
34 oxide cathodes for lithium-ion (Li-ion) batteries.¹⁻² However, the inherently low specific
35
36 capacities of these materials limit the achievable specific energy.³⁻⁴ This roadblock led to the
37
38 investigations into solid conversion cathodes such as elemental sulfur which offers an order of
39
40 magnitude higher specific capacity thus improving the specific energy.⁵⁻⁶ Despite being a
41
42 promising cathode material, an intrinsic volume change (~80%) occurring during conversion of
43
44 sulfur to lithium sulfide necessitates cathode substrates that possess structural stability
45
46 throughout the cycle life of the cell.⁵ In addition, complete conversion in ether electrolyte
47
48 requires a high electrolyte/sulfur ratio, *e.g.*, $\geq 10 \mu\text{L mg}^{-1}$, which significantly limits the specific
49
50 energy of lithium-sulfur (Li-S) batteries.⁷⁻¹¹
51
52
53
54
55
56
57
58
59
60

1
2
3 Research efforts aimed at accommodating this volume change have focused on designing
4 cathode to physically flex during battery operation by employing sulfur wrapped cathodes¹²⁻¹³,
5 confinement in core-shell structures¹⁴⁻¹⁵, flexible polymers and the like.¹⁶⁻¹⁷ Unfortunately,
6 during long term cycling, these solutions result in microstructural changes in the cathode which
7 negatively affect the performance.¹⁸ Furthermore, this effect is further exacerbated at higher
8 sulfur loadings.¹⁹ An alternative strategy to cathode stabilization relies upon liquid sulfur-
9 containing compounds, where the volume change between the lithiated and delithiated materials
10 is greatly reduced. Herein, we utilize a facile and scalable process to synthesize phenyl
11 polysulfides namely phenyl tetrasulfide (PTS, C₆H₅S₄C₆H₅, PhS₄Ph), phenyl pentasulfide (PPS,
12 PhS₅Ph), and phenyl hexasulfide (PHS, PhS₆Ph) in pure forms. In these compounds, a linear
13 sulfur chain is bonded with two phenyl groups on the ends. Each polysulfide molecule can take
14 several Li⁺ and e⁻ when reduced; therefore, possess a high specific capacity and energy. The
15 volume change when utilizing these materials is about 37% (see supporting for computation),
16 which is less than half that of the sulfur cathode in Li-S batteries thus significantly reducing
17 internal electrode stresses. This enables the cathode to accommodate the chemical transitions
18 over a few hundred cycles while still maintaining mechanical integrity and ensuring electrical
19 contact with the active material. In addition, this class of liquid cathode materials allows for high
20 material utilization at low electrolyte/active material ratios (*i.e.*, 3 μL mg⁻¹) thus reducing the
21 fraction of inactive cell components. These unique properties can be leveraged for developing
22 lithium batteries with long cycle life and high energy density for practical applications.
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48

49 In this letter, these new polysulfides were synthesized in a facile and scalable route and
50 their chemical composition was verified using different spectroscopic techniques. Their
51 electrochemical, material and physical transformations occurring on the cathode in lithium half-
52
53
54
55
56
57
58
59
60

1
2
3 cells were probed to understand their reduction processes in batteries. Furthermore,
4
5 performances under high rate and also low electrolyte to active material ratios were evaluated,
6
7 which shows their potential to overcome the intrinsic issues of sulfur cathodes.
8
9
10

11 12 **Results and Discussion**

13
14 Bis(aryl) polysulfides such as phenyl polysulfides and benzyl polysulfides have been
15 synthesized commonly through the reaction of the corresponding thiols with sulfur
16
17 monochloride,²⁰⁻²² reaction of corresponding aryl halides with alkali polysulfides,²³⁻²⁴ and also
18
19 the base-catalyzed reaction of thiols with elemental sulfur²⁵ among others.²⁶ These techniques
20
21 rely on a variety of solvents, catalysts and non-ambient conditions and result in a mixture of
22
23 reaction products thus requiring further extraction/purification steps before obtaining the final
24
25 products in pure form. Herein, we introduce a solvent-free and catalyst-free technique to
26
27 synthesize phenyl polysulfides that yields the required product in a single step. The reaction
28
29 involves the simple mixing and stirring of the starting thiol, *i.e.*, benzenethiol (PhSH) with
30
31 elemental sulfur in the appropriate stoichiometric ratio as visualized along with the equation in
32
33 Figure 1a. The high acidity of the thiol group facilitates the ring-opening of the cyclo-octasulfur
34
35 leading to the formation of phenyl polysulfanes (PhS_xH).²⁵ The instability of these high order
36
37 polysulfanes results in intermolecular condensation and elimination of H₂S gas leading to the
38
39 formation of the required order of phenyl polysulfide.²⁵⁻²⁶ The presence of H₂S can be detected
40
41 through the blackening on exposure of lead acetate test strips (shown in Figure 1a) and can also
42
43 be observed in the bubbling of the reaction mixture (supporting Figure S1). The H₂S evolution
44
45 greatly subsides in 1 hour and ceases at about 5 hours. Continuous agitation until 6 hours
46
47 removes almost all the dissolved gas leaving behind the oily polysulfide liquid. Furthermore,
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 upon scaling, the H₂S released can be collected from the reaction vessel and the sulfur can be
4
5 recovered from it using the Claus process thus regenerating the starting material and mitigating
6
7 the toxic impact of H₂S.
8
9

10 Two equivalents of PhSH react with 3 equivalents of sulfur to yield phenyl tetrasulfide
11
12 (PTS, PhS₄Ph). Similarly, 4 equivalents of sulfur give phenyl pentasulfide (PPS, PhS₅Ph) and 5
13
14 equivalents result in phenyl hexasulfide (PHS, PhS₆Ph) which are shown in Figure 1b. As
15
16 expected, the density of these liquids almost linearly increases with polysulfide order. This
17
18 results in the gravimetric specific capacity and volumetric capacity density increase with the
19
20 order of phenyl polysulfide as summarized in Figure 1c. PHS has a specific capacity of 774.5
21
22 mAh g⁻¹ and a capacity density of 1,022.4 mAh mL⁻¹ which are, respectively, nearly 4 times and
23
24 twice that of state-of-the-art cathode materials used in Li-ion batteries.²⁷ On collating the energy
25
26 increase with polysulfide order as described by Figure 1d, we see that all the three polysulfides
27
28 have a higher specific energy than metal oxide cathode materials, while PPS and PHS are able to
29
30 surpass them in terms of energy density. This comparison of theoretical capacity and energy
31
32 values clearly establishes the great promise this class of materials hold in surpassing the current
33
34 cathode materials used in Li-ion batteries.
35
36
37
38
39

40 Upon their synthesis, different spectroscopic techniques were used to corroborate the
41
42 composition of the polysulfides. Firstly, Fourier Transform Infrared (FTIR) spectroscopy was
43
44 conducted to confirm the conversion of thiol to polysulfide. The S-H bond stretch, ν(SH), is
45
46 typically present in the 2500-2600 cm⁻¹ range as shown in the IR spectrum in Figure 2a.²⁸ This is
47
48 evident in the spectrum of PhSH whereas this peak is absent in the spectra of PTS, PPS, and PHS
49
50 marking the conversion of the thiol into corresponding polysulfides. Characteristic peaks of the
51
52 phenyl polysulfide bonds are visible in the 400-550 cm⁻¹ region (supporting Figure S2). Here,
53
54
55
56
57
58
59
60

1
2
3 weak peaks attributed to S-S bond stretching mode can be seen in 480-500 cm^{-1} band along with
4
5 the stronger peak at about 470 cm^{-1} owing to the out-of-plane deformation of the phenyl rings
6
7 due to the presence of polysulfide linkages.²⁹⁻³⁰ Next, on establishing the conversion to
8
9 polysulfides, we ascertain their order through Ultraviolet-Visible (UV-Vis) spectroscopy. The
10
11 spectra for equimolar solutions in chloroform of the synthesized polysulfides along with that of
12
13 the commercially available phenyl disulfide (PDS) as a reference were collected as shown in
14
15 Figure 2b. The peak wavelength (λ , in nm) increases as we move from PDS to PHS.³¹ The plot
16
17 of peak wavelength as a function of square root of polysulfide order (n , *i.e.* number of sulfur
18
19 atoms) shown in inset Figure 2b follows a linear trend as expected of phenyl polysulfide thus
20
21 validating the order of the synthesized polysulfides.³²
22
23
24
25

26 In addition, in order to confirm the purity of the synthesized polysulfides, electron impact
27
28 mass spectrometry (EI-MS) was performed. The mass spectrum in Figure 2c has the parent ion
29
30 peak at a m/z of 281.96 corresponding to the molar mass for PTS. Other daughter fragmentation
31
32 peaks corresponding to that of PhS_3Ph (phenyl trisulfide, $m/z = 250$), PhS_2Ph (phenyl disulfide,
33
34 $m/z = 218$), $\text{PhSS}\cdot$ (phenyl perthiolate radical, $m/z = 141$) and $\text{PhS}\cdot$ (phenyl thiolate radical, m/z
35
36 $= 109$) are also evident.²⁰ The absence of peaks beyond m/z of 288 (supporting Figure S3)
37
38 supports the clean formation of PTS. The mass spectrum in Figure 2d confirms the presence of
39
40 PPS ($m/z = 313.98$) along with its fragments which include PTS. Trace amounts of PHS ($m/z =$
41
42 345.95) is also formed as evidenced by supporting Figure S4. The peak for a m/z of 345.92 in
43
44 Figure 2e asserts the formation of PHS along with trace amounts of PhS_7Ph (phenyl heptasulfide,
45
46 $m/z = 377.89$) indicated by supporting Figure S5. The spectroscopic data above substantiates the
47
48 synthesis of the polysulfides as mainly governed by the equation in Figure 1a.
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 The synthesized polysulfides were subject to electrochemical testing using CR-2032 coin
4 cells. The cathode consisted of commercially available carbon nanotube (CNT) paper discs that
5 function as the polysulfide reservoir, conductive substrate as well as the current collector as used
6 in several studies.³³⁻³⁴ The cyclic voltammogram in Figure 3a shows three distinct reduction
7 peaks in the cathodic scan which are present for all three polysulfides. The first peak at 2.4 V
8 corresponds to the breakage of the central S-S bonds which increases with the polysulfide order
9 owing to the lowering of their bond energy.³⁵ The following reduction of the lithium polysulfides
10 which occurs at 2.2 V is mediated by the formed phenyl persulfide and phenyl sulfide radicals.^{34,}
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

³⁶⁻³⁸ This is followed by conversion of lithium polysulfides (Li_2S_x , $2 \leq x \leq 4$) to lithium sulfide (Li_2S) and the formation of lithium thiophenolate (PhSLi) at 2 V.³⁹ The anodic scan illustrates that the charging reaction occurs in two steps. Majority of the conversion occurs at 2.3 V followed by the reversal to phenyl polysulfides at 2.43 V.

Alongside this, the examination of the voltage profiles of the three polysulfides upon galvanostatic cycling at $C/2$ (Figure 3b) reveals the first discharge plateau occurs at 2.35 V for PHS and PPS whereas it is a sloping region until 2.25 V for PTS. This is followed by a sloping second plateau at 2.15 V for PTS and 2.2 V for PPS and PHS. The lower order lithium polysulfides formed at this stage (Li_2S_x , $2 \leq x \leq 4$) transition to Li_2S at the 2 V plateau. We can see that, the higher voltage characteristic organopolysulfide transitions that occur above 2 V contribute to nearly 320 mAh g^{-1} . This equates to 62%, 52%, and 45% of the total capacity for PTS, PPS, and PHS, respectively, which is markedly different from the 25% obtained through the 2.4 V higher order polysulfide transition in Li-S batteries.⁴⁰ The two electron-withdrawing phenyl rings attached to the sulfur chains elevate the electrochemical potential of sulfur; therefore it is beneficial for improving specific energy of lithium batteries. Additionally, the

1
2
3 resonance in thiophenolate ion stabilizes it thus forming stable discharge products. This
4
5 fundamentally changes the reaction mechanism compared to other organosulfur compounds.
6
7

8 Following this, the physical and chemical transitions occurring at the cathode were
9
10 probed using X-ray diffraction (XRD), X-ray photoelectron spectroscopy (XPS), and scanning
11
12 electron microscopy (SEM). XRD pattern of the discharged cathodes in supporting Figure S6
13
14 exhibits the broadened (220) and (311) peaks for Li_2S and no characteristic peaks for PhSLi for
15
16 all three polysulfides. This signals the formation of a near amorphous form of Li_2S and non-
17
18 crystalline form of PhSLi on cell discharge, indicating a uniform mixing of Li_2S and PhSLi in
19
20 the discharged electrode. On recharge, only the peaks for the bare CNT paper can be seen
21
22 (supporting Figure S7) signaling the conversion of the solid discharge components to liquid
23
24 phenyl polysulfides. To confirm the presence of PhSLi owing to its absence in XRD, we turned
25
26 to XPS of the discharged cathode of PHS (Figure 3c). The presence of the doublet with S $2p_{3/2}$
27
28 peak at 161.6 eV asserts the presence of PhSLi while the doublet with S $2p_{3/2}$ at 160.2 eV
29
30 corroborates the Li_2S observed through XRD. Additionally, to capture the morphological
31
32 transitions, SEM was performed. The micrograph of the discharged cathodes of PHS (Figure 3d),
33
34 PPS (supporting Figure S8), and PTS (supporting Figure S9) all show the discharged products
35
36 uniformly coated in what appears like a sheath over the CNT core. The lithium thiophenolate
37
38 mediated discharge mechanism seems to assist in the spatially homogeneous distribution of
39
40 discharge products. This uniform distribution of the discharge products in the CNT matrix as
41
42 detected by the inset energy dispersive X-ray (EDX) ensures adequate electron transfer pathways
43
44 and maximizes electrolyte penetration. It also enables excellent polysulfides confinement which
45
46 results in high Coulombic efficiency (CE) and material utilization.⁴¹⁻⁴² The complete reversal to
47
48 liquid polysulfides upon charge is revealed by the pristine nature of the CNT seen after washing
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 the charged electrode (supporting Figure S10). In addition, the similar discharge voltage profiles
4
5 observed in several cycles (1st, 250th, and 500th) further confirm that the recharged product is
6
7 electrochemically identical to the original phenyl polysulfide (supporting Figure S11).
8
9

10 Subsequently, these polysulfides were tested at 1C rate to capture the long-term cycling
11
12 behavior of these materials (Figure 3e). PTS delivers 514 mAh g⁻¹ which corresponds to 90%
13
14 material utilization. It is able to retain 65% of its initial capacity after 300 cycles. Meanwhile,
15
16 PPS delivers 612 mAh g⁻¹ which corresponds to 89.6% material utilization in the first cycle and
17
18 also retains 75% this capacity post 300 cycles. The most stable of the polysulfides however, is
19
20 PHS with an initial capacity of 650 mAh g⁻¹ (84% utilization) and a retention of 80% through
21
22 500 cycles. This increased cycling stability from PTS to PHS could be due to the increase in
23
24 molecular size thus preventing its shuttle. Despite starting out with a low initial CE of ~98%, all
25
26 polysulfides stabilize quickly and have an average CE of over 99.5%. In addition to confinement
27
28 of the phenyl polysulfides in the CNT pores as stated above, limiting the formation of long chain
29
30 lithium polysulfides, and the sulfur concatenation mediated by the thiophenolate ion could all
31
32 contribute to minimized shuttle effect and thus the high CE. Furthermore, excellent reversibility
33
34 and sustenance of the same reaction pathway throughout the cycling of the phenyl polysulfides
35
36 can be confirmed through the consistency observed in the voltage profile for PHS over 500
37
38 cycles (supporting Figure S11). This exemplary performance serves to cement the advantage of
39
40 limiting the overall volume change at the cathode.
41
42
43
44
45
46

47 In addition to cycle life, high rate performance was also evaluated. PHS cathode was
48
49 tested at various rates ranging from C/2 to 10C as in Figure 4a. PHS can deliver about 700 mAh
50
51 g⁻¹ at low rates like C/2 and also manage to deliver 448 mAh g⁻¹ and 409 mAh g⁻¹ at high rates
52
53 like 6C and 10C, respectively. This demonstrates a material utilization of over 50% even at such
54
55
56
57
58
59
60

1
2
3 high rates. The cell is able to cycle in <12 minutes at 6C and a little over 6 minutes at 10C.
4
5 Moreover, the increase in overpotential, *i.e.*, 0.35 V from C/2 to 10C is modest (supporting
6
7 Figure S12), showing the excellent power performance of this material. To put this in a practical
8
9 perspective we turn to Ragone plots wherein the interplay between energy and power is
10
11 appropriately highlighted. The gravimetric Ragone plot in supporting Figure S13 shows that, at a
12
13 material level, over 1500 Wh kg⁻¹ can be obtained under low demands such as 800 W kg⁻¹.
14
15 However, even under pressing demand scenarios (13 kW kg⁻¹), a high specific energy of 725 Wh
16
17 kg⁻¹ can be obtained. Even on a volumetric basis (supporting Figure S14) 800Wh L⁻¹ can be
18
19 achieved at a power demand corresponding to 13 kW L⁻¹.
20
21
22
23

24 Many recent works have rightly shown that low electrolyte to active material ratios are a
25
26 critical aspect of materials design for true high energy density sulfur-based batteries.⁷⁻¹⁰ Keeping
27
28 in mind that a high loading cathode with minimal electrolyte is essential for achieving high cell
29
30 level specific energy, we tested a high loading (9 μL or 11.9 mg) of PHS which comprised 68%
31
32 of the cathode's mass with a 3 μL mg⁻¹ electrolyte ratio at C/10 rate. As seen in Figure 3d, this
33
34 cathode can yield 7.6 mAh cm⁻² of areal capacity which is much higher than that of commercial
35
36 Li-ion cells.⁴³ Stable cycling is achieved for 50 cycles with 82% capacity retention. The observed
37
38 fading is attributed to aggressive electrolyte consumption and failure of lithium anode
39
40 (supporting Figure S15). At an active material level, PHS can offer an impressive specific energy
41
42 of 1,302 Wh kg⁻¹ and an energy density of 1,720Wh L⁻¹ based on the first cycle. To highlight the
43
44 improved performance of PHS over sulfur cathodes when operating under low-electrolyte, *i.e.*,
45
46 lean conditions, PHS cells were compared to solid lithium polysulfide-based cells with the same
47
48 substrate and theoretical cathode capacity were tested at three electrolyte-to-sulfur ratios namely
49
50 3, 5, and 10 μL mg⁻¹. Inspection of the first cycle voltage profile (supporting Figure S16) of 3 μL
51
52
53
54
55
56
57
58
59
60

1
2
3 mg^{-1} based cell shows failure to operate normally while the cell with $5 \mu\text{L mg}^{-1}$ exhibits high
4
5 overpotentials. Only at $10 \mu\text{L mg}^{-1}$ did sulfur cells achieve first cycle performance comparable to
6
7 the PHS, but penalties to overpotential and capacity remained. Assessment of cycling behavior
8
9 (supporting Figure S17) of these cells clearly shows failure at $3 \mu\text{L mg}^{-1}$ and rapid degradation at
10
11 $5 \mu\text{L mg}^{-1}$. Even at $10 \mu\text{L mg}^{-1}$ only 69% of sulfur can be utilized. For reference, 80% of PHS
12
13 can be utilized even at $3 \mu\text{L mg}^{-1}$ cycling conditions. Moreover, the CE of the operating sulfur
14
15 cells (supporting Figure S18) is 89% compared to that of PHS at 99%. This superior cycling
16
17 performance of PHS coupled with a reduced inactive electrolyte fraction translates to nearly 100
18
19 Wh kg^{-1} higher specific energy than the sulfur system at a cell level as conveyed in supporting
20
21 Figure S19. While this work only serves to demonstrate the potential of this class of materials,
22
23 further engineering and optimization could certainly enable much higher specific energies from
24
25 these batteries.
26
27
28
29
30
31
32

33 **Conclusion**

34
35 In summary, we demonstrate that high purity phenyl polysulfides can be synthesized in a
36
37 facile, low cost, one-pot route that is scalable. These polysulfides are high-sulfur-content
38
39 compounds with high theoretical capacities in the order of $\text{PHS} > \text{PPS} > \text{PTS}$ and high energy
40
41 densities. They exhibit long high discharge voltage plateaus due to the electron-withdrawing
42
43 phenyl rings attached to the sulfur chains and each polysulfide has its own characteristic voltage
44
45 profile. In Li half cells, they show excellent cyclability up to 500 cycles due to reduced volume
46
47 expansion in the cathode along with superior rate performance. Importantly, high-order PHS
48
49 shows respectable performance under lean electrolyte operation, which outperforms lithium
50
51 polysulfide cathode in terms of material utilization, Coulombic efficiency, and specific energy.
52
53
54
55
56
57
58
59
60

1
2
3 These multifaceted advantages provide the motivation for further exploration of this class of
4 materials towards a truly high energy density sulfur-based battery system.
5
6
7
8
9

10 **Supporting Information**

11
12 Supporting Information Available: experimental details, volume change calculations along with
13 additional materials characterization and electrochemical data. This material is available free of
14 charge via the Internet at <http://pubs.acs.org>
15
16
17
18
19
20
21

22 **Acknowledgements**

23
24 YF acknowledges the Release Time for Research grant from Office of the Vice Chancellor for
25 Research at Indiana University-Purdue University Indianapolis and the support from Thousand
26 Youth Talents Program of China. We would like to acknowledge the Integrated Nanosystems
27 Development Institute (INDI) for use of their Bruker D8 Discover XRD Instrument, which was
28 awarded through the NSF grant MRI-1429241 and for use of their JEOL7800F Field Emission
29 SEM, which was awarded through NSF grant MRI-1229514. We thank the Department of
30 Chemistry and Chemical Biology at IUPUI for the use of their FTIR facility. We also thank Dr.
31 Yaroslav Losovyj at the Nanoscale Characterization Facility at Indiana University for XPS
32 measurements.
33
34
35
36
37
38
39
40
41
42
43
44
45

46 **Author contributions**

47
48 A.B. proposed the concept of the battery and did the main measurements and analysis under the
49 Y.F.'s supervision. M.E.B. assisted in acquiring FTIR data. Y.C. performed the SEM. J.K.
50 collected and assisted in the analysis of EI-MS data. A.B. and Y.F. prepared the manuscript. All
51 the authors discussed the results and commented on the manuscript.
52
53
54
55
56
57

Competing interests

The authors declare no competing financial interests.

Corresponding Author

yfu@zzu.edu.cn(Y. Fu)

References

1. Goodenough, J. B.; Park, K.-S., The Li-ion rechargeable battery: a perspective. *J. Am. Chem. Soc.* **2013**, *135*, 1167-1176.
2. Armand, M.; Tarascon, J. M., Building better batteries. *Nature* **2008**, *451*, 652-657.
3. Manthiram, A., Materials Challenges and Opportunities of Lithium Ion Batteries. *J. Phys. Chem. Lett.* **2011**, *2*, 176-184.
4. Goodenough, J. B.; Kim, Y., Challenges for Rechargeable Li Batteries. *Chem. Mater.* **2010**, *22*, 587-603.
5. Manthiram, A.; Fu, Y.; Su, Y.-S., Challenges and prospects of lithium–sulfur batteries. *Acc. Chem. Res.* **2012**, *46*, 1125-1134.
6. Manthiram, A.; Fu, Y.; Chung, S.-H.; Zu, C.; Su, Y.-S., Rechargeable lithium–sulfur batteries. *Chem. Rev.* **2014**, *114*, 11751-11787.
7. Hagen, M.; Hanselmann, D.; Ahlbrecht, K.; Maça, R.; Gerber, D.; Tübke, J., Lithium–Sulfur Cells: The Gap between the State-of-the-Art and the Requirements for High Energy Battery Cells. *Adv. Energy Mater.* **2015**, *5*, 1401986.
8. McCloskey, B. D., Attainable Gravimetric and Volumetric Energy Density of Li–S and Li Ion Battery Cells with Solid Separator-Protected Li Metal Anodes. *J. Phys. Chem. Lett.* **2015**, *6*, 4581-4588.
9. Fu, C.; Guo, J., Challenges and current development of sulfur cathode in lithium–sulfur battery. *Curr. Opin. Chem. Eng.* **2016**, *13*, 53-62.
10. Peng, H. J.; Huang, J. Q.; Cheng, X. B.; Zhang, Q., Review on High-Loading and High-Energy Lithium–Sulfur Batteries. *Adv. Energy Mater.* **2017**, *7*, 1700260.
11. Guo, W.; Fu, Y., A Perspective on Energy Densities of Rechargeable Li-S Batteries and Alternative Sulfur-Based Cathode Materials. *Energy Environ. Mater.* **2018**, *1*, 20-27.
12. Wang, H.; Yang, Y.; Liang, Y.; Robinson, J. T.; Li, Y.; Jackson, A.; Cui, Y.; Dai, H., Graphene-Wrapped Sulfur Particles as a Rechargeable Lithium–Sulfur Battery Cathode Material with High Capacity and Cycling Stability. *Nano Lett.* **2011**, *11*, 2644-2647.
13. Evers, S.; Nazar, L. F., Graphene-enveloped sulfur in a one pot reaction: a cathode with good coulombic efficiency and high practical sulfur content. *Chem. Commun.* **2012**, *48*, 1233-1235.
14. Seh, Z. W.; Li, W.; Cha, J. J.; Zheng, G.; Yang, Y.; McDowell, M. T.; Hsu, P.-C.; Cui, Y., Sulphur–TiO₂ yolk–shell nanoarchitecture with internal void space for long-cycle lithium–sulphur batteries. *Nat. Commun.* **2013**, *4*, 1331.

15. Fu, Y.; Manthiram, A., Core-shell structured sulfur-polypyrrole composite cathodes for lithium-sulfur batteries. *RSC Adv.* **2012**, *2*, 5927-5929.
16. Wu, F.; Chen, J.; Chen, R.; Wu, S.; Li, L.; Chen, S.; Zhao, T., Sulfur/Polythiophene with a Core/Shell Structure: Synthesis and Electrochemical Properties of the Cathode for Rechargeable Lithium Batteries. *J. Phys. Chem. C* **2011**, *115*, 6057-6063.
17. Yang, Y.; Yu, G.; Cha, J. J.; Wu, H.; Vosgueritchian, M.; Yao, Y.; Bao, Z.; Cui, Y., Improving the Performance of Lithium–Sulfur Batteries by Conductive Polymer Coating. *ACS Nano* **2011**, *5*, 9187-9193.
18. Barai, P.; Mistry, A.; Mukherjee, P. P., Poromechanical effect in the lithium–sulfur battery cathode. *Extreme Mechanics Letters* **2016**, *9*, 359-370.
19. Waluś, S.; Offer, G.; Hunt, I.; Patel, Y.; Stockley, T.; Williams, J.; Purkayastha, R., Volumetric expansion of Lithium-Sulfur cell during operation – Fundamental insight into applicable characteristics. *Energy Storage Materials* **2018**, *10*, 233-245.
20. Cerda, M. M.; Hammers, M. D.; Earp, M. S.; Zakharov, L. N.; Pluth, M. D., Applications of Synthetic Organic Tetrasulfides as H₂S Donors. *Org. Lett.* **2017**, *19*, 2314-2317.
21. Derbesy, G.; Harpp, D. N., A simple method to prepare unsymmetrical di- tri- and tetrasulfides. *Tetrahedron Lett.* **1994**, *35*, 5381-5384.
22. Chakravarti, G. C., CX.-Action of sulphur monochloride on mercaptans. *J. Chem. Soc., Trans.* **1923**, *123*, 964-968.
23. Kawase, A.; Shirai, S.; Yamoto, Y.; Arakawa, R.; Takata, T., Electrochemical reactions of lithium-sulfur batteries: an analytical study using the organic conversion technique. *Phys. Chem. Chem. Phys.* **2014**, *16*, 9344-9350.
24. Nobuo, Y.; Mutsuhisa, F.; Masayuki, N.; Toshikazu, T., Direct Preparation of Anhydrous Sodium Oligosulfides from Metal Sodium and Elemental Sulfur in Aprotic Organic Media Directed toward Synthesis of Silane Coupling Agent. *Chem. Lett.* **2002**, *31*, 454-455.
25. Vineyard, B. D., Versatility and the mechanism of the n-butyl-amine-catalyzed reaction of thiols with sulfur. *J. Org. Chem.* **1967**, *32*, 3833-3836.
26. Steudel, R., The Chemistry of Organic Polysulfanes R–Sn–R (n > 2). *Chem. Rev.* **2002**, *102*, 3905-3946.
27. Myung, S.-T.; Maglia, F.; Park, K.-J.; Yoon, C. S.; Lamp, P.; Kim, S.-J.; Sun, Y.-K., Nickel-Rich Layered Cathode Materials for Automotive Lithium-Ion Batteries: Achievements and Perspectives. *ACS Energy Lett.* **2017**, *2*, 196-223.
28. Das, P.; Ray, S.; Bhaumik, A.; Banerjee, B.; Mukhopadhyay, C., Cubic Ag₂O nanoparticle incorporated mesoporous silica with large bottle-neck like mesopores for the aerobic oxidative synthesis of disulfide. *RSC Adv.* **2015**, *5*, 6323-6331.
29. Minoura, Y.; Moriyoshi, T., Infra-red spectra of dibenzyl polysulphides. *Trans. Faraday Soc.* **1963**, *59*, 1504-1509.
30. Tsurugi, J.; Nakabayashi, T., Organic Polysulfides. II.1 Polymorphism in Dibenzhydryl Tetrasulfide. *J. Org. Chem.* **1960**, *25*, 1744-1747.
31. Tsurugi, J.; Nakabayashi, T., Synthesis of Dibenzhydryl and Dibenzyl Penta- and Hexasulfides. *J. Org. Chem.* **1959**, *24*, 807-810.
32. Minoura, Y.; Moriyoshi, T., Ultra-violet absorption spectra and molecular refractions of dibenzyl mono-, di-, tri-, tetra-, penta-, hexa-, hepta-, octa-sulphides. *Trans. Faraday Soc.* **1963**, *59*, 1019-1025.

- 1
2
3 33. Fu, Y.; Su, Y.-S.; Manthiram, A., Highly Reversible Lithium/Dissolved Polysulfide
4 Batteries with Carbon Nanotube Electrodes. *Angew. Chem. Int. Ed.* **2013**, *52*, 6930-6935.
5
6 34. Wu, M.; Cui, Y.; Bhargav, A.; Losovyj, Y.; Siegel, A.; Agarwal, M.; Ma, Y.; Fu, Y.,
7 Organotrissulfide: A High Capacity Cathode Material for Rechargeable Lithium Batteries.
8 *Angew. Chem. Int. Ed.* **2016**, *55*, 10027-10031.
9
10 35. Denk, M. K., The Variable Strength of the Sulfur–Sulfur Bond: 78 to 41 kcal – G3, CBS-
11 Q, and DFT Bond Energies of Sulfur (S₈) and Disulfanes XSSX (X = H, F, Cl, CH₃, CN,
12 NH₂, OH, SH). *Eur. J. Inorg. Chem.* **2009**, *2009*, 1358-1368.
13
14 36. Chen, S.; Dai, F.; Gordin, M. L.; Yu, Z.; Gao, Y.; Song, J.; Wang, D., Functional
15 Organosulfide Electrolyte Promotes an Alternate Reaction Pathway to Achieve High
16 Performance in Lithium–Sulfur Batteries. *Angew. Chem. Int. Ed.* **2016**, *55*, 4231-4235.
17
18 37. Bhargav, A.; Patil, S. V.; Fu, Y., A phenyl disulfide@CNT composite cathode for
19 rechargeable lithium batteries. *Sustainable Energy Fuels* **2017**, *1*, 1007-1012.
20
21 38. Shuru, C.; Daiwei, W.; Yuming, Z.; Donghai, W., Superior Performance of a Lithium–
22 Sulfur Battery Enabled by a Dimethyl Trisulfide Containing Electrolyte. *Small Methods*
23 **2018**, *2*, 1800038.
24
25 39. Guo, W.; Wawrzyniakowski, Z.; Cerda, M.; Bhargav, A.; Pluth, M.; Ma, Y.; Fu, Y.,
26 Bis(aryl) Tetrasulfides as Cathode Materials for Rechargeable Lithium Batteries. *Chem.*
27 *Eur. J.* **2017**, *23*, 16941-16947.
28
29 40. Su, Y.-S.; Fu, Y.; Cochell, T.; Manthiram, A., A strategic approach to recharging lithium-
30 sulphur batteries for long cycle life. *Nat. Commun.* **2013**, *4*, 2985.
31
32 41. Hua, W.; Yang, Z.; Nie, H.; Li, Z.; Yang, J.; Guo, Z.; Ruan, C.; Chen, X. a.; Huang, S.,
33 Polysulfide-Scission Reagents for the Suppression of the Shuttle Effect in Lithium–Sulfur
34 Batteries. *ACS Nano* **2017**, *11*, 2209-2218.
35
36 42. Preefer, M. B.; Oschmann, B.; Hawker, C. J.; Seshadri, R.; Wudl, F., High Sulfur
37 Content Material with Stable Cycling in Lithium-Sulfur Batteries. *Angew. Chem. Int. Ed.*
38 **2017**, *56*, 15118-15122.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

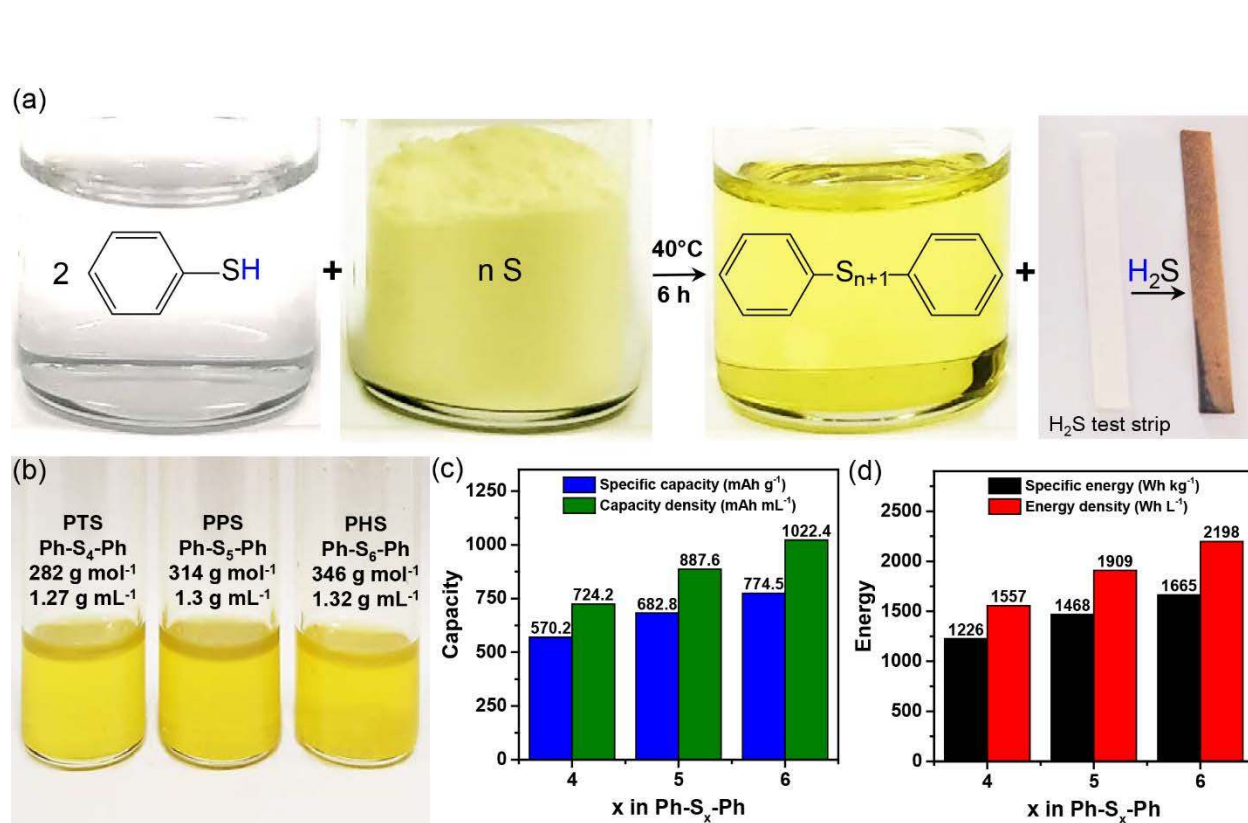


Figure 1. (a) Equation along a visual representation of the phenyl polysulfide synthesis process.

Lead acetate based test strip was used to confirm the H₂S evolution. (b) Optical image of the liquid polysulfides along with their properties. (c) Theoretical specific capacities (mAh g⁻¹) and capacity densities (mAh mL⁻¹) of the different polysulfides and their (d) theoretical specific energies (Wh kg⁻¹) and energy densities (Wh L⁻¹).

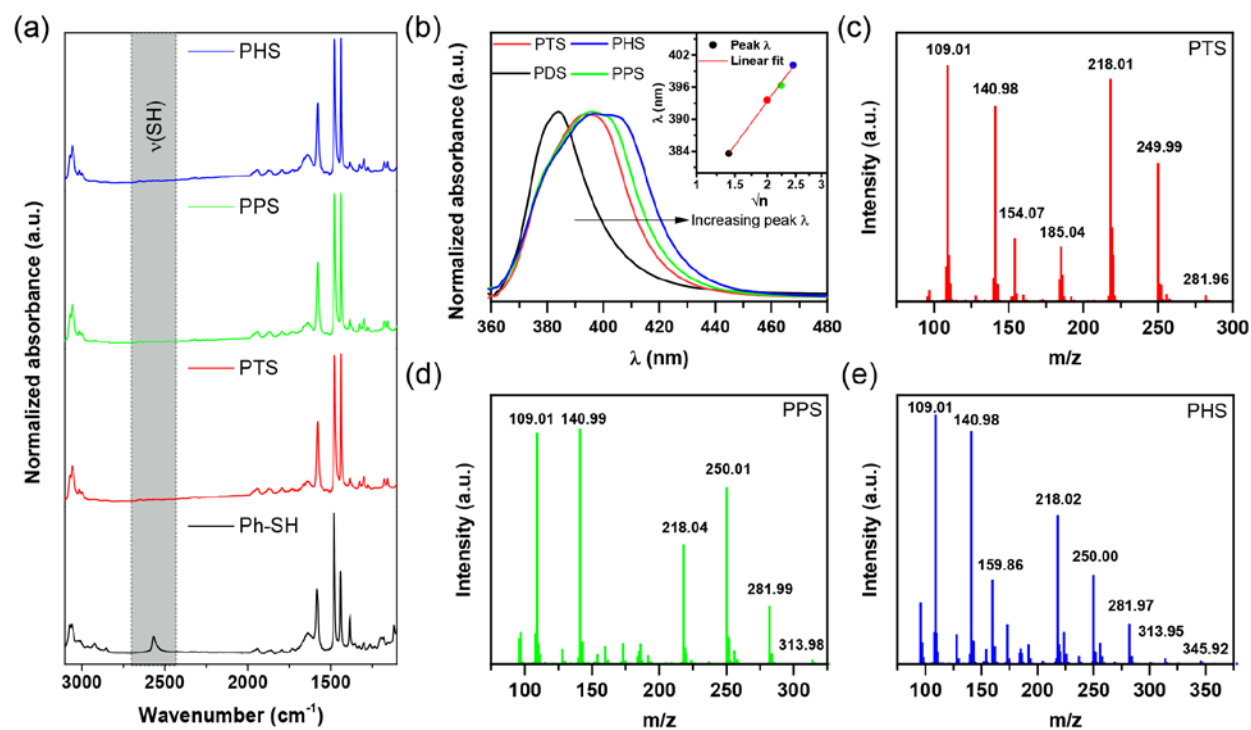


Figure 2. (a) FTIR spectrum of benzenethiol (Ph-SH) and the synthesized phenyl polysulfides. (b) UV-Vis spectra of equimolar solutions of different phenyl polysulfides along with that of phenyl disulfide (PDS) as reference. Inset of (b) shows the linear increase in peak λ as a function of number of sulfur atoms. EI-MS spectrum of (c) phenyl tetrasulfide (PTS), (d) phenyl pentasulfide (PTS), and (e) phenyl hexasulfide (PHS).

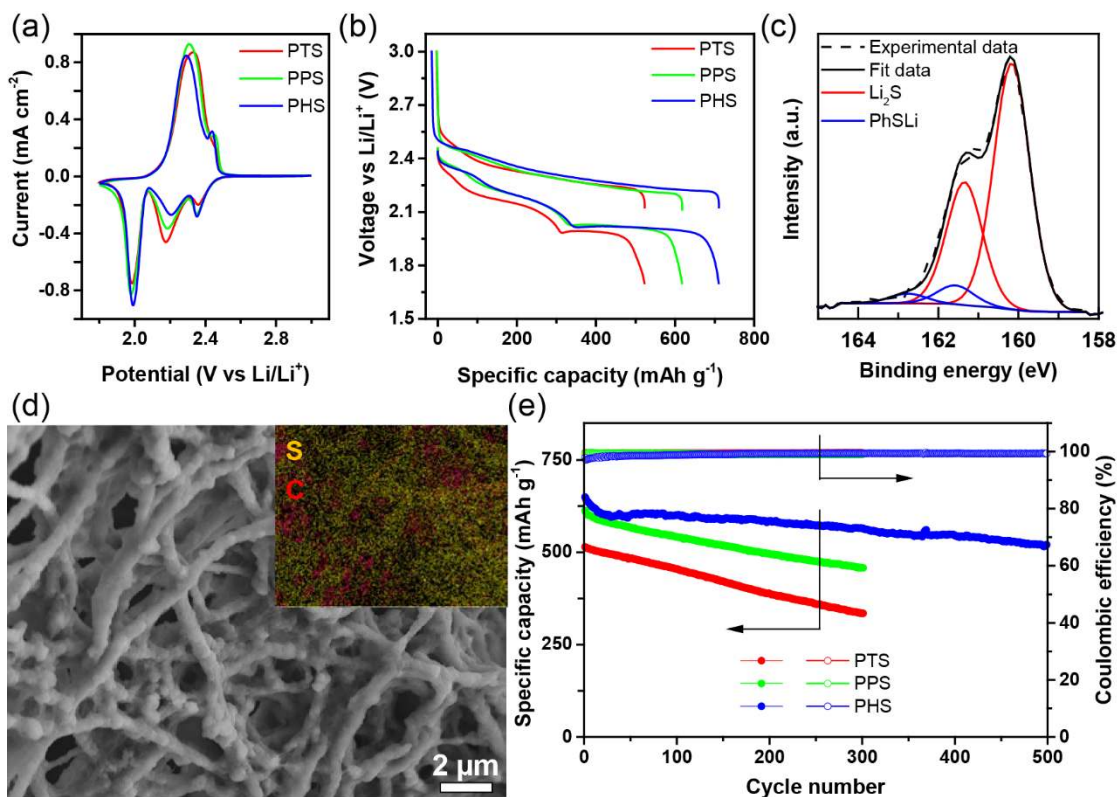


Figure 3. (a) Cyclic voltammety (CV) of the phenyl polysulfide cathodes performed at 0.05 mV s^{-1} . (b) Voltage profile of the polysulfide cathodes cycled at $C/2$. (c) Sulfur 2p XPS spectrum of the PHS cathode in the discharged state. (d) SEM of the PHS cathode in the discharged state along with its inset EDX mapping and (e) long term cycling performance of the polysulfides at $1C$. The cycling rate was based on active material mass in the cathode with $1C_{\text{PTS}} = 570 \text{ mA g}^{-1}$, $1C_{\text{PPS}} = 683 \text{ mA g}^{-1}$, and $1C_{\text{PHS}} = 775 \text{ mA g}^{-1}$.

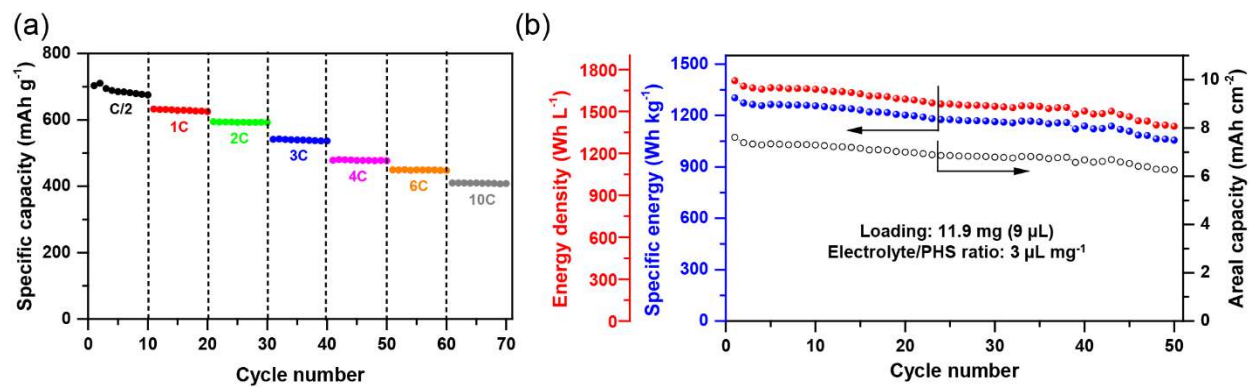


Figure 4. (a) Rate performance of PHS cathode and (b) performance of high loading, low electrolyte/PHS ratio cell cycled at C/10. The cycling rate was based on active material mass in the cathode with $1C_{PTS} = 570 \text{ mA g}^{-1}$, $1C_{PPS} = 683 \text{ mA g}^{-1}$, and $1C_{PHS} = 775 \text{ mA g}^{-1}$.

1
2
3 **Table of Contents Figure**
4
5
6
7
8
9

