


MM FILE COPY

④

Mechanics and Materials Center
TEXAS A&M UNIVERSITY
College Station, Texas

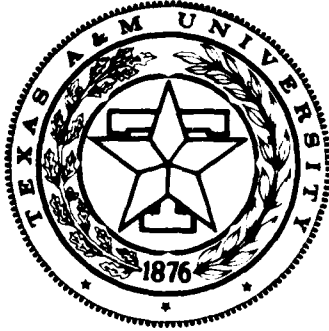

AD-A202 588

A CONTINUUM DIFFUSION MODEL FOR VISCOELASTIC MATERIALS

Y. WEITSMAN

DTIC
SELECTED
NOV 20 1988
S D
CD

OFFICE OF NAVAL RESEARCH
MECHANICS DIVISION
ENGINEERING SCIENCES DIRECTORATE
CONTRACT N00014-82-K-0562

NOV 20 1988

MM 4762-88-17

NOVEMBER 1988

88 11 28 050

unclassified

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION unclassified		1b. RESTRICTIVE MARKINGS									
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT									
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE		unlimited									
4. PERFORMING ORGANIZATION REPORT NUMBER(S) MM-4762-88-17		5. MONITORING ORGANIZATION REPORT NUMBER(S)									
6a. NAME OF PERFORMING ORGANIZATION Mechanics & Materials Center Texas A&M University		7a. NAME OF MONITORING ORGANIZATION CNR									
6b. OFFICE SYMBOL (If applicable)		7b. ADDRESS (City, State and ZIP Code) Mechanics Division Office of Naval Research; Code 432 800 Quincy Ave. Arlington, VA 22217									
6c. ADDRESS (City, State and ZIP Code) College Station, Texas 77843		8. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract CNR N00014-82-K-0562									
8a. NAME OF FUNDING/SPONSORING ORGANIZATION CNR		8b. OFFICE SYMBOL (If applicable)									
8c. ADDRESS (City, State and ZIP Code)		9. SOURCE OF FUNDING NOS.									
		<table border="1"> <thead> <tr> <th>PROGRAM ELEMENT NO.</th> <th>PROJECT NO.</th> <th>TASK NO.</th> <th>WORK UNIT NO.</th> </tr> </thead> <tbody> <tr> <td></td> <td></td> <td></td> <td></td> </tr> </tbody> </table>		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.				
PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.								
11. TITLE (Include Security Classification) A Continuum Diffusion Model for Viscoelastic Materials											
12. PERSONAL AUTHOR(S) Y. Weitsman											
13a. TYPE OF REPORT Technical		13b. TIME COVERED FROM _____ TO _____									
		14. DATE OF REPORT (Yr., Mo., Day) November 1988									
		15. PAGE COUNT 33									
16. SUPPLEMENTARY NOTATION											
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)									
FIELD	GROUP	SUB. GR.	Diffusion, Viscoelasticity, Moisture. (mgm)								
19. ABSTRACT (Continue on reverse if necessary and identify by block number)											
<p>A model for diffusion in polymers is established from basic principles of irreversible thermodynamics, employing the methodology of continuum mechanics. The polymeric materials are considered to respond viscoelastically, with ageing.</p> <p>It is shown that effects of stress on diffusion and certain anomalies in the moisture sorption process can be explained by the present model.</p>											
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS <input type="checkbox"/>		21. ABSTRACT SECURITY CLASSIFICATION unclassified									
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. Y. Rajapakse		22b. TELEPHONE NUMBER (Include Area Code) (202) 696-4305									
		22c. OFFICE SYMBOL									

1. Introduction

The processes of moisture transport and sorption in polymers have been studied by numerous investigators for more than fifty years. Most of these studies, which involved experimental, analytical, and materials science aspects, were conducted by researchers in the fields of physical and polymer chemistry. These investigations were mostly focused towards applications in membrane technology and therefore concerned aspects of permeability and seepage. It is far beyond the scope of the present article to list the many significant contributions made to this field. References [1] - [9] list some of the many outstanding review articles on the subject.

During the past fifteen years the transport of moisture in polymers raised concern and interest in composite materials technology. Moisture plays a significant role in affecting the mechanical response of fiber-reinforced polymeric composites and in influencing the behavior of adhesive joints which are increasingly employed in composite structures. These concerns, which focus mainly on mechanical effects, produced more than 500 publications on the subject. A review and summary of some of these works is given in references [10] and [11].

In spite of many overlaps the investigations in the two foregoing categories reveal distinctions that reflect the disparate scientific disciplines from which they derive - polymer science in one case and applied mechanics in the other. It may thus be worthwhile to present an approach to theory of diffusion that employs the methodology of continuum mechanics and its well developed constitutive formalism. This approach is especially useful in the modelling of coupling effects, such as between stress and diffusion, as detailed in a recent work^[12].

It should be noted that the most crucial issue associated with diffusing

substances in polymeric composites is their detrimental effects on structural strength, integrity and durability. In certain circumstances, diffusing substances were noted to damage the composites by debonding the fiber/matrix interfaces. This issue is a topic of current research and its modelling is hampered by uncertainties regarding the damage mechanisms. Several investigations concerning moisture induced damage in composites were reviewed in ref. [11] and an attempt at a continuum-level modelling of the phenomenon is provided in ref. [13]. The issue of damage will not be discussed in the present paper.

2. Basic Equations

Consider a solid body B occupying a material volume V bounded by a surface A. Let the solid, of mass density ρ_s , absorb vapor through its boundary and let m denote the vapor-mass per unit volume of the solid. Also, let \underline{x} be the position of a solid mass particle in the deformed configuration that corresponds to the place \underline{X} in the undeformed state, and let \underline{f} , \underline{g} and \underline{v} denote fluxes of vapor-mass and of heat, and the velocity of the solid particles, respectively.

In addition, let u and s be the internal energy and entropy densities of the solid/vapor mixture per unit solid mass, and let σ_{ij} and T denote the components of the Cauchy stress due to mechanically applied loads, and temperature, respectively.

A proper accounting of the state of the solid/vapor mixture, which is a thermodynamically open system, is obtained by considering each element in thermodynamic equilibrium with a reservoir containing vapor at pressure \tilde{p} , density $\tilde{\rho}$, and internal energy and entropy densities \tilde{u} and \tilde{s} respectively [14], [15], [16].

Conservation of the solid and vapor masses gives

$$\dot{\rho}_s + \rho_s \nabla \cdot \underline{v} = 0 \quad (1)$$

$$\dot{m} = -\nabla \cdot \underline{f} \quad (2)$$

Conservation of energy over B reads

$$\begin{aligned} \frac{d}{dt} \int_V \rho_s u \, dV &= \int_A \sigma_{ij} n_j v_i \, dA - \int_A q_i n_i \, dA \\ &\quad - \int_A \tilde{p} \frac{f_i}{\tilde{\rho}} n_i \, dA - \int_A \tilde{u} f_i n_i \, dA \end{aligned} \quad (3)$$

The third integral on the right side of (3) expresses the mechanical power due to vapor flux, observing that $f_i/\tilde{\rho}$ corresponds to vapor velocity. The last integral in (3) expresses the rate of vapor-borne energy.

The entropy inequality reads

$$\frac{d}{dt} \int_V \rho_s s \, dV \geq \int_A -(q_i/T) n_i \, dA - \int_A \tilde{s} f_i n_i \, dA \quad (4)$$

Where the last integral in (4) expresses the rate of vapor-borne entropy.

Application of Green's theorem to (3) and (4), and employment of (2), yields^[12]

$$\rho_s \dot{u} = \sigma_{ij} v_{i,j} - q_{i,i} - \tilde{h}_{,i} f_i + \tilde{h} \dot{m} \quad (5)$$

and

$$\rho_s T \dot{s} \geq -q_{i,i} + (q_i/T) g_i - T \tilde{s}_{,i} f_i + T \tilde{s} \dot{m} \quad (6)$$

where $\tilde{h} = (\tilde{p}/\tilde{\rho}) + \tilde{u}$ is the enthalpy of the vapor in the hypothetical reservoir and $g_i = T_{,i}$.

Elimination of $q_{i,j}$ between (5) and (6) yields the following expression for the "reduced entropy inequality"^[12]

$$-\rho_{SO} \dot{\phi} - \rho_{SO} S \dot{T} - \dot{\sigma}_{ij} \epsilon_{ij} - (q_i/T) g_i + \dot{m} - f_{ij} \dot{u}_{,j} - \dot{s} g_i f_i \geq 0 \quad (7)$$

In (7) $\phi = u - Ts - \frac{1}{\rho_{SO}} \sigma_{ij} \epsilon_{ij}$ is the Gibbs free energy and $\tilde{\mu} = \tilde{h} - T\tilde{s}$ is the chemical potential of the vapor in the hypothetical reservoir. In eqn. (7) ρ_{SO} denotes the initial mass density of the solid and infinitesimal deformation has been assumed, whereby $\epsilon_{ij} \ll 1$.

3. Ageing Viscoelastic Response With Moisture.

The viscoelastic behavior of high polymers has been associated with the various degrees of freedom afforded by the motions of the long chain molecules [17], [18], [19]. The normal modes of these motions can be represented by N scalar-valued internal state variables γ_r ($r = 1, \dots, N$). This representation motivated subsequent researchers [20]-[24] to derive a theory of viscoelasticity from fundamental concepts of irreversible thermodynamics, with irreversibility stemming from the foregoing variables γ_r through "growth laws" that correspond to viscous resistance.

The physical ageing of polymers is generally ascribed [24] to the introduction of a "free volume" into those materials upon their cooling across the glass transition temperature T_g . The free volume is a non-equilibrium thermodynamic internal state variable, which decays spontaneously with the passage of time and influences the rate of all time-dependent processes within the polymer.

Consider therefore

$$\phi = \phi(\sigma_{ij}, m, T, \gamma_r, v_f) \quad (8)$$

where v_f denotes the non-dimensional free-volume fraction.

Since eqn. (7) cannot be violated by any process, the methodology of continuum mechanics [26] yields the following constitutive equations

$$\begin{aligned} \epsilon_{ij} &= -\rho_{so} \frac{\partial \phi}{\partial \sigma_{ij}} \\ s &= -\frac{\partial \phi}{\partial T} \\ \mu &= \rho_{so} \frac{\partial \phi}{\partial m} \end{aligned} \quad (9)$$

and

$$-R_r \dot{\gamma}_r - R \dot{v}_f - (q_i/T)g_i - \tilde{s} g_i f_i \geq 0 \quad (10)$$

In eqn. (10), the affinities R_r and R are defined by

$$R_r = \rho_{so} \frac{\partial \phi}{\partial \gamma_r} \quad \text{and} \quad R = \rho_{so} \frac{\partial \phi}{\partial v_f}.$$

The aging process is associated with the spontaneous collapse of the free volume v_f [25],[27] from an initial value v_{f0} , which is created by the cooling of a polymer across its glass transition temperature T_g down to a temperature T_0 . In addition, the subjection of a polymer externally to σ_{ij} , m , or $\Delta T = T - T_0$, will trigger an irreversible process which will cause the internal variables γ_r to drift spontaneously toward their equilibrium values γ_r^e . The two abovementioned processes are assumed independent of each other [25],[27]. Consequently, while both $\dot{\gamma}_r$ and \dot{v}_f in eqn. (10) denote derivatives with respect to time, the time-lapse t for γ_r is not necessarily equal to the time-span τ for v_f .

Assume $\gamma_r, v_f \ll 1$. A Taylor expansion about the initial state ($\gamma_r = 0, v_f = v_{f0}$) then reads

$$\begin{aligned} \rho_{so} \phi &= \rho_{so} [\phi_0 + \phi_r \gamma_r + \phi_v (v_f - v_{f0}) + \frac{1}{2} \phi_{rq} \gamma_r \gamma_q + \frac{1}{2} \phi_{vv} (v_f - v_{f0})^2 \\ &\quad + \text{H.O.T.}] \end{aligned} \quad (12)$$

In eqn. (12) $\phi_0 = \phi_0(\sigma_{ij}, m, T, 0, v_{f0})$ and $\phi_r, \phi_v, \phi_{rq}, \phi_{vv}$ denote partial

derivatives at $\gamma_r = 0$, $v_f = v_{f0}$, all of which depend on σ_{ij} , m , and T .

According to the extremum principles of thermodynamics^[28] ϕ attains its minimum at the equilibrium values $\gamma_r = \gamma_r^e$ and $v_f = v_f^e$. Therefore, at equilibrium we have

$$\frac{\partial \phi}{\partial \gamma_r} = 0, \quad \frac{\partial \phi}{\partial v_f} = 0, \quad \text{and}$$

$$\frac{1}{2} \frac{\partial^2 \phi}{\partial \gamma_r \partial \gamma_s} \delta \gamma_r \delta \gamma_s + \frac{1}{2} \frac{\partial^2 \phi}{\partial v_f^2} (\delta v_f)^2 > 0 \quad \text{for all } \delta \gamma_r \text{ and } \delta v_f.$$

Expanding ϕ about γ_r^e and $v_f^e = 0$ we have

$$\rho_{SO} \phi = \rho_{SO} [\phi_e + \frac{1}{2} \phi_{rq}^e (\gamma_r - \gamma_r^e) (\gamma_q - \gamma_q^e) + \frac{1}{2} \phi_{vv}^e v_f^2 + \text{H.O.T.}] \quad (13)$$

In view of the assumption that $\gamma_r, \gamma_r^e, v_f, v_{f0} \ll 1$, expansions (12) and (13) are equal, implying in particular that

$$\phi_{vv} = \phi_{vv}^e, \quad \phi_{rq} = \phi_{rq}^e.$$

Therefore, $\phi_{vv} > 0$ and ϕ_{rq} are components of a symmetric, positive definite matrix.

Employing the familiar assumption of viscous-like resistance^{[17]-[23]} let

$$R = -b(m, T, v_f) \frac{dv_f}{d\tau} \quad (14)$$

and

$$R_r = -b_{rq}(m, T, v_f) \frac{d\gamma_q}{dt} \quad (15)$$

By Onsager's principle $b_{rq} = b_{qr}$ and, in view of the dissipation inequality (10), $b > 0$ and b_{rq} are components of a semi positive definite, symmetric matrix. As noted earlier, the time τ and t in eqns. (14) and (15) are distinct because the quench-time τ usually occurs earlier than the exposure-time t , namely $t = \tau - t_e$.

Equations (11), (13) and (14) give

$$\rho_{so} \ddot{v}_f + b \frac{dv_f}{d\tau} = 0 \quad (16)$$

whereby

$$v_f = v_{f0} e^{-\xi/\tau_v} \quad (17)$$

with $d\xi = d\tau/b$ and $\tau_v^{-1} = \rho_{so} \ddot{v}_f$

Equations (11), (12) and (15) yield

$$\rho_{so} \ddot{\gamma}_{rq} + b_{rq} \dot{\gamma}_{rq} = -\rho_{so} \ddot{\gamma}_r \quad (18)$$

Since $\ddot{\gamma}_{rq}$ and b_{rq} are symmetric, positive definite matrices* they can be diagonalized simultaneously [29] and eqn. (18) is expressible in the form

$$\rho_{so} \ddot{\gamma}_p + B_p \dot{\gamma}_p = -\rho_{so} \ddot{\gamma}_p \quad (p = 1, \dots, N. \text{ no sum on } p) \quad (19)$$

Note that b_{rq} , and therefore also B_p , depend on the quency-time τ as well as on the exposure-time t through their dependence on m , T and v_f in eqn. (15).

Following Schapery [22]-[24] assume that all $\ddot{\gamma}_{rq}$ have a common dependence on σ_{ij} , m , and T namely $\ddot{\gamma}_{rq} = a_G(\sigma_{ij}, m, T) \phi_{rq}^0$ with constant ϕ_{rq}^0 and, similarly, $b_{rq} = a(m, T, v_f) b_{rq}^0$. These common "shift-factors" a_G and a carry over to eqn. (19) whose solution, subject to the conditions $\gamma_r(0) = 0$, $\gamma_r(\infty) = \gamma_r^e$, reads

$$\hat{\gamma}_p = -K_p (1 - e^{-\xi/\tau_p}) \quad (20)$$

*The case of a semi-positive definite b_{rq} is omitted here for the sake of brevity. This case corresponds to a viscoelastic fluid, as modelled by a free dash pot attached to Kelvin or Maxwell elements.

where

$$\kappa_p = \frac{\phi_p}{a_G \phi_p}, \quad \tau_p = \frac{B_p}{\rho_{SO} \phi_p} \quad (\text{no sum on } p, p = 1, 2, \dots, N) \quad (21)$$

and

$$d\xi = \left(\frac{a_G}{a}\right) dt. \quad (22)$$

Aiming at linear stress-strain behavior, consider $\sigma_{ij}/E \ll 1$ where E denotes a characteristic modulus. To retain linearity assume that all retardation times do not depend on σ_{ij} . Hence, in eqns. (17) and (20),

$\tau_v = \tau_v(m, T, v_f)$ and $\tau_p = \tau_p(m, T, v_f)$ $p = 1, \dots, N$. Furthermore, to establish the linear stress-strain relations, consider the expansion in eqn. (12) truncated after three-terms, which, resorting to the diagonalized form, reads

$$\rho_{SO} \phi = \rho_{SO} [\phi_0 + \phi_r \hat{\gamma}_r + \phi_v (v_f - v_{f0})] \quad (23)$$

Eqn. (9)₁ gives

$$\epsilon_{ij} = -\rho_{SO} \left[\frac{\partial \phi_0}{\partial \sigma_{ij}} + \frac{\partial \phi_r}{\partial \sigma_{ij}} \hat{\gamma}_r + \frac{\partial \phi_v}{\partial \sigma_{ij}} (v_f - v_{f0}) \right] \quad (24)$$

The specific forms which follow from eqn. (24) depend on the material symmetry at hand. Considering isotropy we have

$$\phi(\sigma_{ij}, m, T, \hat{\gamma}_r, v_f) = \phi(\sigma_{kk}, \sigma_{ij} \sigma_{ij}, m, T, \hat{\gamma}_r, v_f)^*$$

which, for linear behavior gives the well known forms

$$\begin{aligned} \rho_{SO} \phi_0 &= A_0(m, T) - L_0(m, T) \sigma_{kk} - M_0(m, T) \sigma_{kk} \sigma_{\ell\ell} - N_0(m, T) \sigma_{k\ell} \sigma_{\ell k} \\ \rho_{SO} \phi_r &= A_r(m, T) + L_r(m, T) \sigma_{kk} + M_r(m, T) \sigma_{kk} \sigma_{\ell\ell} + N_r(m, T) \sigma_{k\ell} \sigma_{\ell k} \\ \rho_{SO} \phi_v &= A_v(m, T) + L_v(m, T) \sigma_{kk} + M_v(m, T) \sigma_{kk} \sigma_{\ell\ell} + N_v(m, T) \sigma_{k\ell} \sigma_{\ell k} \end{aligned} \quad (25)$$

It is advantageous to express L_0 , L_r and L_v in terms of expansional coefficients α and β , namely

*The stress invariant $|\sigma_{ij}|$ is inadmissible for linear behavior.

$$L(m, T) = \alpha(m, T)\Delta T + \beta(m, T)m \quad (26)$$

Equations (24) and (25) then yield

$$\begin{aligned} \epsilon_{ij} = & [\hat{\alpha}_0 - \hat{\alpha}_r \hat{\gamma}_r - \hat{\alpha}_v (v_f - v_{f0})] \Delta T \delta_{ij} + [\hat{\beta}_0 - \hat{\beta}_r \hat{\gamma}_r - \hat{\beta}_v (v_f - v_{f0})] m \delta_{ij} \\ & + 2[M_0 - M_r \hat{\gamma}_r - M_v (v_f - v_{f0})] \sigma_{kk} \delta_{ij} + 2[N_0 - N_r \hat{\gamma}_r - N_v (v_f - v_{f0})] \sigma_{ij} \quad (27) \end{aligned}$$

It can be noted from eqns. (20) and (21) that γ_p depends on σ_{ij} through the presence of ϵ_p in K_p . However, for sufficiently small stresses K_p themselves can be expanded according to (25), whereby upon collecting like-powers in σ_{ij} , the form of the strain-stress relationship given in eqn. (27) remains valid with stress-independent $\hat{\gamma}_r$.

The stress strain relations (27) are of the familiar form employed in linear viscoelasticity, except that the retardation spectra incorporate now ageing effects and all instantaneous compliances age with time. Recalling eqn (20), for a discrete spectrum of retardation-times τ_r expressions (27) read

$$\begin{aligned} \epsilon_{ij} = & [\alpha_0 + \alpha_1 (1 - e^{-\zeta/\tau_v}) + \sum_r \alpha_r (1 - e^{-\xi/\tau_r})] \Delta T \\ & + [\beta_0 + \beta_1 (1 - e^{-\zeta/\tau_v}) + \sum_r \beta_r (1 - e^{-\xi/\tau_r})] m \\ & + [B_0 + B_1 (1 - e^{-\zeta/\tau_v}) + \sum_r B_r (1 - e^{-\xi/\tau_r})] \sigma_{kk} \delta_{ij} \\ & + [J_0 + J_1 (1 - e^{-\zeta/\tau_v}) + \sum_r J_r (1 - e^{-\xi/\tau_r})] \sigma_{ij} \quad (28) \end{aligned}$$

In eqn. (28), the quantities α , β , B and J depend on m and T , the "reduced times" ξ and ζ both depend on m , T and the ageing time τ . However, in contrast to ζ , the reduced time ξ is measured from the time of application of σ_{ij} , m , and T . For fluctuating environments and stresses, expression (28) takes the form of convolution integrals. The case of a continuous spectrum of retardation times τ_r can be represented in the familiar manner by means of retardation integrals.

4. Stress Assisted Diffusion in Ageing Viscoelastic Media

Employing eqns. (9)₃, (23), (25) and (26) we obtain

$$\begin{aligned}
 \mu = & \frac{\partial A_0}{\partial m} + \frac{\partial A_r(m,T)}{\partial m} \gamma_r + \frac{\partial A_v(m,T)}{\partial m} (v_f - v_{f0}) \\
 & + \left\{ \left[-\frac{\partial \alpha_0}{\partial m} + \frac{\partial \alpha_r}{\partial m} \gamma_r + \frac{\partial \alpha_v}{\partial m} (v_f - v_{f0}) \right] \Delta T \right. \\
 & \quad \left. - \frac{\partial (m\beta_0)}{\partial m} + \frac{\partial (m\beta_r)}{\partial m} \gamma_r + \frac{\partial (m\beta_v)}{\partial m} (v_f - v_{f0}) \right\} \sigma_{kk} \\
 & + \left[-\frac{\partial M_0}{\partial m} + \frac{\partial M_r}{\partial m} \gamma_r + \frac{\partial M_v}{\partial m} (v_f - v_{f0}) \right] \sigma_{kk} \sigma_{\ell\ell} \\
 & + \left[-\frac{\partial N_0}{\partial m} + \frac{\partial N_r}{\partial m} \gamma_r + \frac{\partial N_v}{\partial m} (v_f - v_{f0}) \right] \sigma_{k\ell} \sigma_{\ell k} \quad (29)
 \end{aligned}$$

The boundary conditions for moisture transport are

$$\mu(x,t) = \mu_A(x,t) \quad \underline{x} \text{ on boundary} \quad (30)$$

where μ_A represents the chemical potential of the ambient vapor.

Assume for simplicity that the expansional coefficients α and β do not vary with m . In this case eqns. (29) and (30), together with eqn. (20), yield

$$\begin{aligned}
 \frac{\partial A_0}{\partial m} = & \mu_A + \sum_r W_r(m,T) (1 - e^{-\xi/\tau_r}) + W(m,T) (1 - e^{-\xi/\tau_v}) \\
 & + \left[-\beta_0 + \sum_r \beta_r (1 - e^{-\xi/\tau_r}) + \beta_v (1 - e^{-\xi/\tau_v}) \right] \sigma_{kk} \\
 & + \left[-Y(m,T) + \sum_r Y_r(m,T) (1 - e^{-\xi/\tau_r}) + Y_v (1 - e^{-\xi/\tau_v}) \right] \sigma_{kk} \sigma_{\ell\ell} \\
 & + \left[-Z(m,T) + \sum_r Z_r(m,T) (1 - e^{-\xi/\tau_r}) + Z_v (1 - e^{-\xi/\tau_v}) \right] \sigma_{k\ell} \sigma_{\ell k} \quad (31)
 \end{aligned}$$

Eqn. (31) illuminates the effects of viscoelastic retardation and ageing, as well as of stress, on the diffusion process. In the absence of those effects the boundary condition, which reads $\partial A_0/\partial m = \mu_A$, translates into the familiar statement $m(\underline{x},t) = m_0(t)$, \underline{x} on boundary and m_0 prescribed. In contrast, eqn. (31) states that the equilibrium boundary value is approached

gradually with time (even for exposure to constant ambient vapor pressure), it is affected by age, and depends quadratically on the applied stress.

Consider now the diffusion coefficient D . Since this coefficient reflects micro-level phenomena, its form cannot be derived from a continuum model*. Molecular-level considerations of diffusion in solids^[30] and fluids^[31] suggest that

$D \sim$ Vacancy in host material \cdot Agitation energy of diffusing substance

In the present case it is reasonable to expect that the vacancy would depend mostly on v_f and secondarily on m, T and σ_{ij} (through their influence on swelling strains). On the other hand, the agitation energy would depend mostly on T .

Accordingly

$$D \sim D_0 [m, T, v_f(\xi(\tau)), \int_0^t F(\xi(t) - \xi(\tau)) \frac{d\sigma_{kk}}{d\tau} d\tau] \cdot (\exp(-E/RT)) \quad (32)$$

In the absence of a satisfactory molecular theory for the glassy state at the present time it appears expedient to base the form of D on empirical evidence.

In isotropic materials, the flux of moisture at fixed σ_{ij} and T is taken to be**

$$f_i = -D \frac{\partial \mu}{\partial x_i} \quad (33)$$

Consequently, eqn. (2) yields the field equation

*The principle of equi-presence suggests that $D = D(\sigma_{ij}, m, T, \gamma_r, v_f)$ but provides no further insight.

**When m, T and σ_{ij} vary in space couplings occur between the fluxes of moisture and of temperature and both depend on the gradients of μ, T ^[32] and of the invariants of stress ^[12].

$$\frac{\partial m}{\partial t} = \frac{\partial}{\partial x_i} \left(D \frac{\partial \mu}{\partial x_i} \right) \quad (34)$$

In view of eqns. (29) and (32), relations (33) and (34) are extremely complicated even at $T = T_0$ and $\sigma_{ij} = \sigma_{ij}^0$. The complexity is due to the presence of m in D and v_f (through $\xi(\tau)$, and $z(\tau)$ in the compliances listed in eq. (29)). However, in spite of the cumbersome details and the paucity in information several features of the form of equation (34) emerge. Accordingly, the diffusion equation:

- (1) Contains non-linear terms in the moisture gradient $\partial m / \partial x_i$.
- (2) Follows a time-retardation process akin to mechanical viscoelastic response.
- (3) Varies non-linearly with external stresses σ_{ij} .
- (4) Exhibits an ageing behavior characteristic of glassy polymers.

5. Two-Phase Diffusion

The non-Fickian weight uptake of water vapor by epoxy resins can be described by a two-phase diffusion model. This model assumes that the vapor within the polymer divides into two portions - a bound phase m_c and a mobile phase m_a . Details are given in refs. [33], [34], where the resin's viscoelasticity has been discarded.

It is interesting to note that the above model can be derived in the context of the thermodynamic theory developed in this work. In this case, let

$$\rho_{SO} \phi = \rho_{SO} \phi (\sigma_{ij}, m_a, m_c, T, \gamma_r, v_f) \quad (35)$$

In analogy with sections 2-4 we now have

$$\mu_a = \rho_{SO} \frac{\partial \phi}{\partial m_a}, \quad \mu_c = \rho_{SO} \frac{\partial \phi}{\partial m_c}$$

Equation (29) and the boundary condition (31) pertain now to the chemical

potential of the mobile phase μ_a , so that all partial derivatives in those equations should be taken with respect to m_a instead of m .

Similarly, the flux-gradient relation now involves the mobile phase only, so that eqn. (33) is replaced by

$$f_i = -D \frac{\partial \mu_a}{\partial x_i} \quad (36)$$

Since the balance equation (2) remains valid, equation (34) is replaced now by

$$\frac{\partial (m_a + m_c)}{\partial t} = \frac{\partial}{\partial x_i} \left(D \frac{\partial \mu_a}{\partial x_i} \right) \quad (37)$$

The system of equations is supplemented by the phase interaction relation [33],[34]

$$\frac{\partial m_c}{\partial t} = P m_c - Q m_a \quad (38)$$

where P and Q are empirical factors.

The dependence of field equations and boundary conditions on retardation-times, physical ageing and stress is retained for the case of two-phase diffusion and is expressible in the same forms as presented in section 4.

6. Experimental Observations.

The present constitutive model can be employed to explain certain experimental observations on diffusion in polymers, as shown in Figs. 1-9 below.

Fig. 1 exhibits the uptake of water vapor, from an ambient environment maintained at a fixed level of 97% R.H., by unidirectionally reinforced graphite/epoxy coupons. The per-cent weight gain is plotted vs. $\sqrt{\text{time}}$. Note the discrepancy between data and predictions based upon the linear Fickian model.

On the other hand, when the retardation process of the epoxy is taken in consideration by means of a boundary condition of the form

$$m(\text{boundary}) = m_a + m_b (1 - e^{-t/\tau_1}) \quad (39)$$

it is possible to obtain an excellent fit between data and theory. In eqn. (39) m_a corresponds to the instantaneous response and m_b is the contribution of polymeric retardation processes. The corresponding prediction, with $m_a = 1.2\%$, $m_b = 0.467\%$, and $\tau_1 = 2.63 \times 10^6$ min., is drawn with a solid line in Fig. 1.* It is worth noting that the above value of τ_1 falls roughly in the middle of the spectrum of mechanical retardation-times for epoxy.

Another form of history-dependence of moisture sorption in epoxy is suggested in Fig. 2^[36]. According to those data there exists a distinct difference in the moisture up-take of "as prepared" samples and the re-absorption by saturated-and-dried samples. This behavior can be attributed to the possibility that re-absorption may have occurred before the complete recovery of the retardation processes caused by the earlier exposure.

It is possible to match data of the type shown in Figure 2 with the boundary condition expressed in eqn. (39). The incomplete viscoelastic recovery at the onset of the second exposure to moisture can be introduced by an enhanced value of m_a , compensated by a reduced value of m_b , maintaining $m_a + m_b = m_\infty = \text{constant}$. Alternately, the incomplete viscoelastic recovery may be expressed by an increased value of τ_1 . The trends are exhibited in Figs. 3 and 4 respectively.

Effects of stress on diffusion are shown in Figs. 5-8^{[37]-[39]}. Fig. 5 shows the per-cent weight gain of water vapor, maintained at 97% R.H., by

*An analytic solution for boundary condition (39) is available in Ref. [35].

epoxy coupons that were subjected to various levels of uniaxial tensile stress. The weight-gain is plotted vs. $\sqrt{\text{time}}$ and data are compared against predictions of the linear Fickian law, showing discrepancies that increase with stress. The maximal level of moisture up-take reached during the tests (which lasted about seven weeks) are plotted vs. stress in Fig. 6. Although the above maximal levels of moisture uptake are not the equilibrium saturation levels, Fig. 6 shows a trend which suggests a quadratic relation between saturation levels and stress, as suggested in section 4.

In Figs. 5 and 6 the ultimate tensile stress was $\sigma_{ult.} = 5.17 \text{ MPa}$.

The dependence of water absorption by polymers on compressive stress levels was reported in ref. [38]. In particular, the sorption of distilled water by epoxy coupons subjected to uniaxial compression is shown in Fig. 7. In spite of the relatively short duration of these tests, which were terminated much below saturation, they indicate a non-linear relationship between stress and saturation levels.

A similar, though less direct, non-linear relation between stress and saturation levels is inferred from Fig. 8.^[39] This figure shows the reduced permeability associated with the flow of oxygen gas across a membrane made of extruded PET, when the membrane is subjected to various levels of uniaxial and biaxial tensile stresses.

A more intricate kind of sorption behavior is shown in Fig. 9^[36]. Since earlier experiments have shown that equilibrium solubility decrease with temperature^[36], one might expect to observe water desorption when a specimen equilibrated at 75°C is transferred to a water bath at 23°C. However, Fig. 9 shows that the opposite takes place. A similar phenomenon was also observed in graphite/epoxy composites^[40].

One possible explanation of this behavior, in addition to those suggested

in [36], is that the slow, decelerating collapse of the free volume (initiated when the sample was created) is reactivated in the saturated epoxy when it is cooled from 75°C down to 23°C. Indeed, it was indicated in [36], that for saturated epoxy T_g is lowered to 108°C. According to eqns. (29) and (30) the rejuvenation of the process of free volume collapse would indeed be reflected in an increased saturation level.

6. Concluding Remarks

In this article it was shown that the constitutive formalism of continuum mechanics can be employed to model several aspects of the process of diffusion in polymers. Certain micro-level characteristics of the polymer structure, such as free volume and motion degrees-of-freedom, were incorporated as internal state variables. The constitutive formalism led to a linear viscoelastic model with ageing and resulted in diffusion relations that were coupled with stress and with the time-dependent material response.

On the other hand, it was shown that the continuum mechanics formalism provides only scant information about material parameters such as the diffusion coefficient. This shortcoming is attributable to the fact that continuum mechanics, which aims at the modelling of macro-level phenomena, is unsuitable for describing inherently micro-level aspects. This conclusion indicates that an interdisciplinary effort, combining continuum mechanics and polymer science, is required for a comprehensive formulation of the diffusion process.

Acknowledgements

This work was performed under Contract N00014-82-K-0562 from the Office of Naval Research. The author is indebted to Dr. Y. Rajapakse of the Mechanics Division, Engineering Science Directorate, ONR, for his support and encouragement.

The author thanks Butterworth Publishers, The Society of Plastics Engineers and Ryder Associates for their kind permissions to incorporate figures 2 and 9, figure 7, and figure 8, respectively, in this work.

References

- [1] C.E. Rogers: "Solubility and Diffusivity". In "The Physics and Chemistry of the Organic Solid State" (D. Fox, M.M. Labes and A. Weissberger - Editors). Interscience, pp. 509-635. (1965).
- [2] V. Stannett and H.B. Hopfenberg: "Diffusion in Polymers": In MTP International Review of Sciences. Vol. 8: Macromolecular Science. (C.E. H. Bawn - Editor). Butterworth, pp. 329-369. (1972).
- [3] H.B. Hopfenberg and V. Stannett: "The Diffusion and Sorption of Gases and Vapours in Glassy Polymers". In "The Physics of Glassy Polymers" (R.N. Howard - Editor). Applied Science Pub. pp. 504-547. (1973).
- [4] W.R. Vieth, J.M. Howell and J.H. Hsieh: "Dual Sorption Theory" J. Membrane Science, Vol. 1, pp. 177-220 (1976).
- [5] V.T. Stannett, W.J. Koros, D.R. Paul, H.K. Lonsdale, and R.W. Baker: "Recent Advances in Membrane Science and Technology". Adv. Poly. Sci. Vol. 32, pp. 69-121. (1979).
- [6] H.L. Frisch: "Sorption and Transport in Glassy Polymers - A Review". Polymer Eng. Sci. Vol. 20 pp. 2-13. (1980).
- [7] H.L. Frisch and S.A. Stern: "Diffusion of Small Molecules in Polymers". CRC Critical Reviews in Solid State and Materials Science. Vol. 11, No. 2, pp. 123-187. (1983).
- [8] C.E. Rogers: "Permeation of Gases and Vapours in Polymers". In "Polymer Permeability" (J. Comyn - Editor). Elsevier Applied Science Pub. pp. 11-73. (1985).
- [9] A.H. Windle: "Case II Sorption". *ibid*, pp. 75-118.
- [10] J.P. Komorowski, "Hygrothermal effects in Continuous Fiber Reinforced Composites", Aeronautical Notes NAE-AN-4, 10, 11, and 12. National Research Council Canada, (1983).

- [11] Y. Weitsman: "Moisture in Composites: Sorption and Damage". In "Fatigue of Composite Materials" (K.L. Reifsnider - Editor) Elsevier - Forthcoming.
- [12] Y. Weitsman: "Stress Assisted Diffusion in Elastic and Viscoelastic Materials", Journal of the Mechanics and Physics of Solids Vol. 35, No. 1, pp. 73-97. (1987).
- [13] Y. Weitsman: "Coupled Damage and Moisture-Transport in Fiber-Reinforced Polymeric Composites", International Journal of Solids and Structures, Vol. 23, No. 7, pp. 1003-1025. (1987).
- [14] I. Prigogine, "Thermodynamics of Irreversible Processes," 3rd Edition, Interscience. Chapters I-IV. (1967).
- [15] J. Kestin, "A Course in Thermodynamics", Vol. I, McGraw Hill (Especially pp. 582-585). (1979).
- [16] J.R. Rice, and M.D. Cleary, "Some Basic Stress Diffusion Solutions for Fluid-Saturated Elastic Porous Media with Compressible Constituents", Rev. Geophysics and Space Physics, Vol. 14, No. 2, pp. 227-241. (1976).
- [17] P.E. Rouse: "A Theory of the Linear Viscoelastic Properties of Dilute Solutions of Coiling Polymers", Journal of Chemical Physics, Vol. 21, No. 7, pp. 1272-1280. (1953).
- [18] F. Bueche: "The Viscoelastic Properties of Plastics". Journal of Chemical Physics Vol. 22, No. 4, pp. 603-609. (1954).
- [19] B.H. Zimm: "Dynamics of Polymer Molecules in Dilute Solution: Viscoelasticity, Flow Birefringence and Dielectric Loss". Journal of Chemical Physics, Vol. 24, No. 2, pp. 269-278. (1956).
- [20] M.A. Biot: "Theory of Stress-Strain Relations in Anisotropic Viscoelasticity and Relaxation Phenomena ", Journal of Applied Physics, Vol. 25, pp. 1385-1391. (1954).

- [21] M.A. Biot: "Variational Principles in Irreversible Thermodynamics with Application to Viscoelasticity", Physical Review Vol. 97 No. 6, pp. 1463-1469. (1955).
- [22] R.A. Schapery: "Application of Thermodynamics to Thermomechanical, Fracture and Birefringent Phenomena in Viscoelastic Media", Journal of Applied Physics, Vol. 35 No. 5, pp. 1451-1465. (1964).
- [23] R.A. Schapery: "A Theory of Non-Linear Viscoelasticity Based on Irreversible Thermodynamics". Proc. 5th U.S. National Congress of Applied Mechanics, pp. 511-530. (1966).
- [24] R.A. Schapery: "Further Development of a Thermodynamic Constitutive Theory: Stress Formulation", Purdue Univ., Report AA&ES 69-2. (AFML Contract F 33615-67-C-1412). (1969).
- [25] L.C.E. Struik: "Physical Aging in Amorphous Polymers and Other Materials". Elsevier. (1978).
- [26] W. Jaunzemis: "Continuum Mechanics". McMillan (1967).
- [27] J.D. Ferry: "Viscoelastic Properties of Polymers", J. Wiley (1961) (pp. 411-414).
- [28] H.B. Callen: "Thermodynamics". J. Wiley (1960). (p. 106).
- [29] L. Meirovitch: "Analytical Methods in Vibrations". MacMillan (1967). (Section 4-3).
- [30] P.G. Shewmon: "Diffusion in Solids". J. Williams Book Co. (1983).
- [31] P.J. Flory: "Principles of Polymer Chemistry". Cornell University Press (1953). (Chapter XII).
- [32] S.R. deGroot and P. Mazur: "Non Equilibrium Thermodynamics". North-Holland (1962). (pp. 273-284).

- [33] H.G. Carter and K.G. Kibler: "Longmuir - Type Model for Anomalous Moisture Diffusion in Composite Resins". J. Comp. Mat. Vol. 12, pp. 118-131. (1978).
- [34] M.E. Gurtin and C. Yatomi: "On a Model for Two-Phase Diffusion in Composite Materials". J. Comp. Mat. Vol. 13, pp. 126- (1979).
- [35] J. Crank: "The Mathematics of Diffusion". Oxford Science Pub. 2nd Edition (1975). (page 53).
- [36] A. Apicella, L. Nicolais, G. Astarita, and E. Drioli: "Effect of Thermal History on Water Sorption, Elastic Properties and the Glass Transition of Epoxy Resins". Polymer, Vol. 20, pp. 1143-1148 (1979).
- [37] M.C. Henson, and Y. Weitsman: "Stress Effects on Moisture Transport in an Epoxy Resin and Its Composite". In "Composites' 86: Recent Advances in Japan and the United States", Proc. Third Japan - U.S. Conference on Composite Materials, Kawata, Ukema, Kobayashi - Editors, pp. 775-784 (1987).
- [38] G. Yaniv and O. Ishai: "Coupling Between Stress and Moisture Diffusion in Polymeric Adhesives". Polymer Eng. and Sci. Vol. 27, No. 10 pp. 731-739. (1987).
- [39] R.W. Seymour and S. Weinhold: "High Barrier Polyester Container". Proceedings of Ryder Conference '85, Ninth International Conference on Oriented Plastics Containers, pp. 281- (1985).
- [40] F.W. Crossman and W.J. Warren: "The Influence of Environment on Matrix Dominated Composite Fracture". Lockheed Palo Alto Research Laboratory. Final Report, Contract N60921-81-C-0157. (Dec. 1985).

Figure Titles

- Fig. 1: Moisture weight gain (%) in a 12-ply unidirectional AS4/3502 graphite/epoxy laminate under exposure to constant ambient relative humidity of 97%, Vs. $\sqrt{\text{time}}$. Temperature = 73°C. Data (dots), predictions of Fick's law (dashed line), and of eqn. (39) (solid line). Values of m_a , m_b and τ_1 given in text.
- Fig. 2: Solubility S (in %) Vs. non-dimensional $\sqrt{\text{time}}$ of epoxy samples immersed in water at 23°C. Open circles - samples as prepared, solid circles - samples previously swollen and dried. After Apicella et. al., reference [36].
- Fig. 3: Moisture weight gain (%) Vs. $\sqrt{\text{time}}$ for test conditions as in Fig. 1 and predictions according to eqn. (39). m_a and m_b as in text (dashed line) and $\bar{m}_a = 1.25 m_a$, $\bar{m}_b = m_b - 0.25 m_a$ (solid line). In both cases τ_1 is same as in text.
- Fig. 4: Moisture weight gain (%) Vs. $\sqrt{\text{time}}$ for test conditions as in Fig. 1 and predictions according to eqn. (39). τ_1 as in text (solid line) and $\bar{\tau}_1 = \tau_1/2$ (dashed line). In both cases m_a and m_b are same as in text.
- Fig. 5: Average values of moisture weight gains (%) Vs. $\sqrt{\text{time}}$ of 3502 epoxy coupons subjected to various stress levels under constant relative humidity of 97% and at temperature of 40°C. Predictions of Fick's law are drawn by dashed lines. After Henson and Weitsman, reference [37].
- Fig. 6: Maximal levels of moisture weight gain (%) attained in 3502 epoxy samples after five weeks of exposure to humidity under various stress levels. Conditions same as in Fig. 5. After Henson and Weitsman, reference [37].

- Fig. 7: Relative moisture absorption (%) in epoxy coupons Vs. time. Samples immersed in distilled water at 5°C under various levels of compressive stress. After Yaniv and Ishai, reference [38].
- Fig. 8: Reduced O_2 permeability in extruded PET films Vs. stress. After Seymour and Weinhold, reference [39].
- Fig. 9: Solubility S (in %) Vs. non-dimensional $\sqrt{\text{time}}$ of epoxy samples immersed in water. Regime "A" - sorption behavior at 75°C. Regime "B" - increased sorption in a sample equilibrated at 75°C, then cooled to 23°C. After Apicella et. al., reference [36].

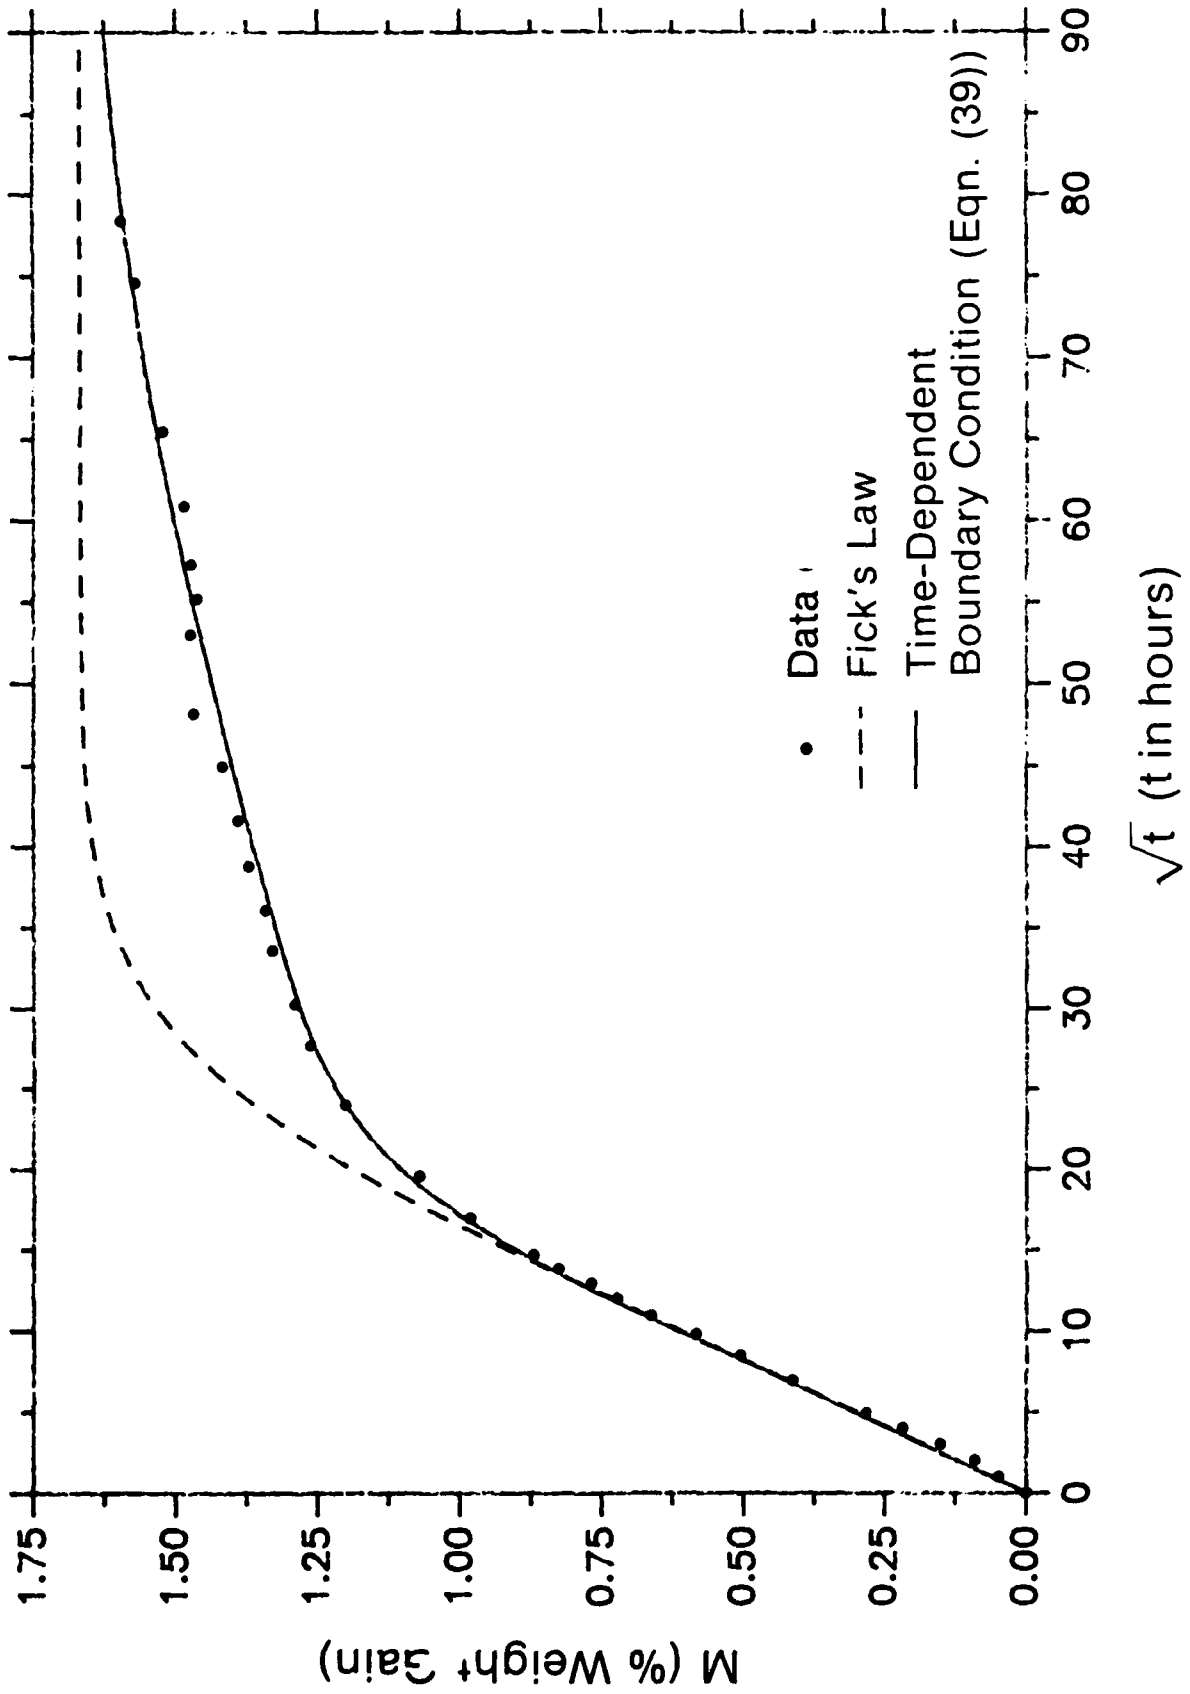


Fig. 1

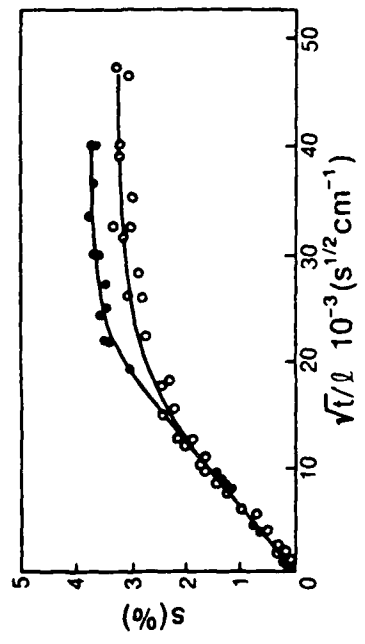


Fig. 2

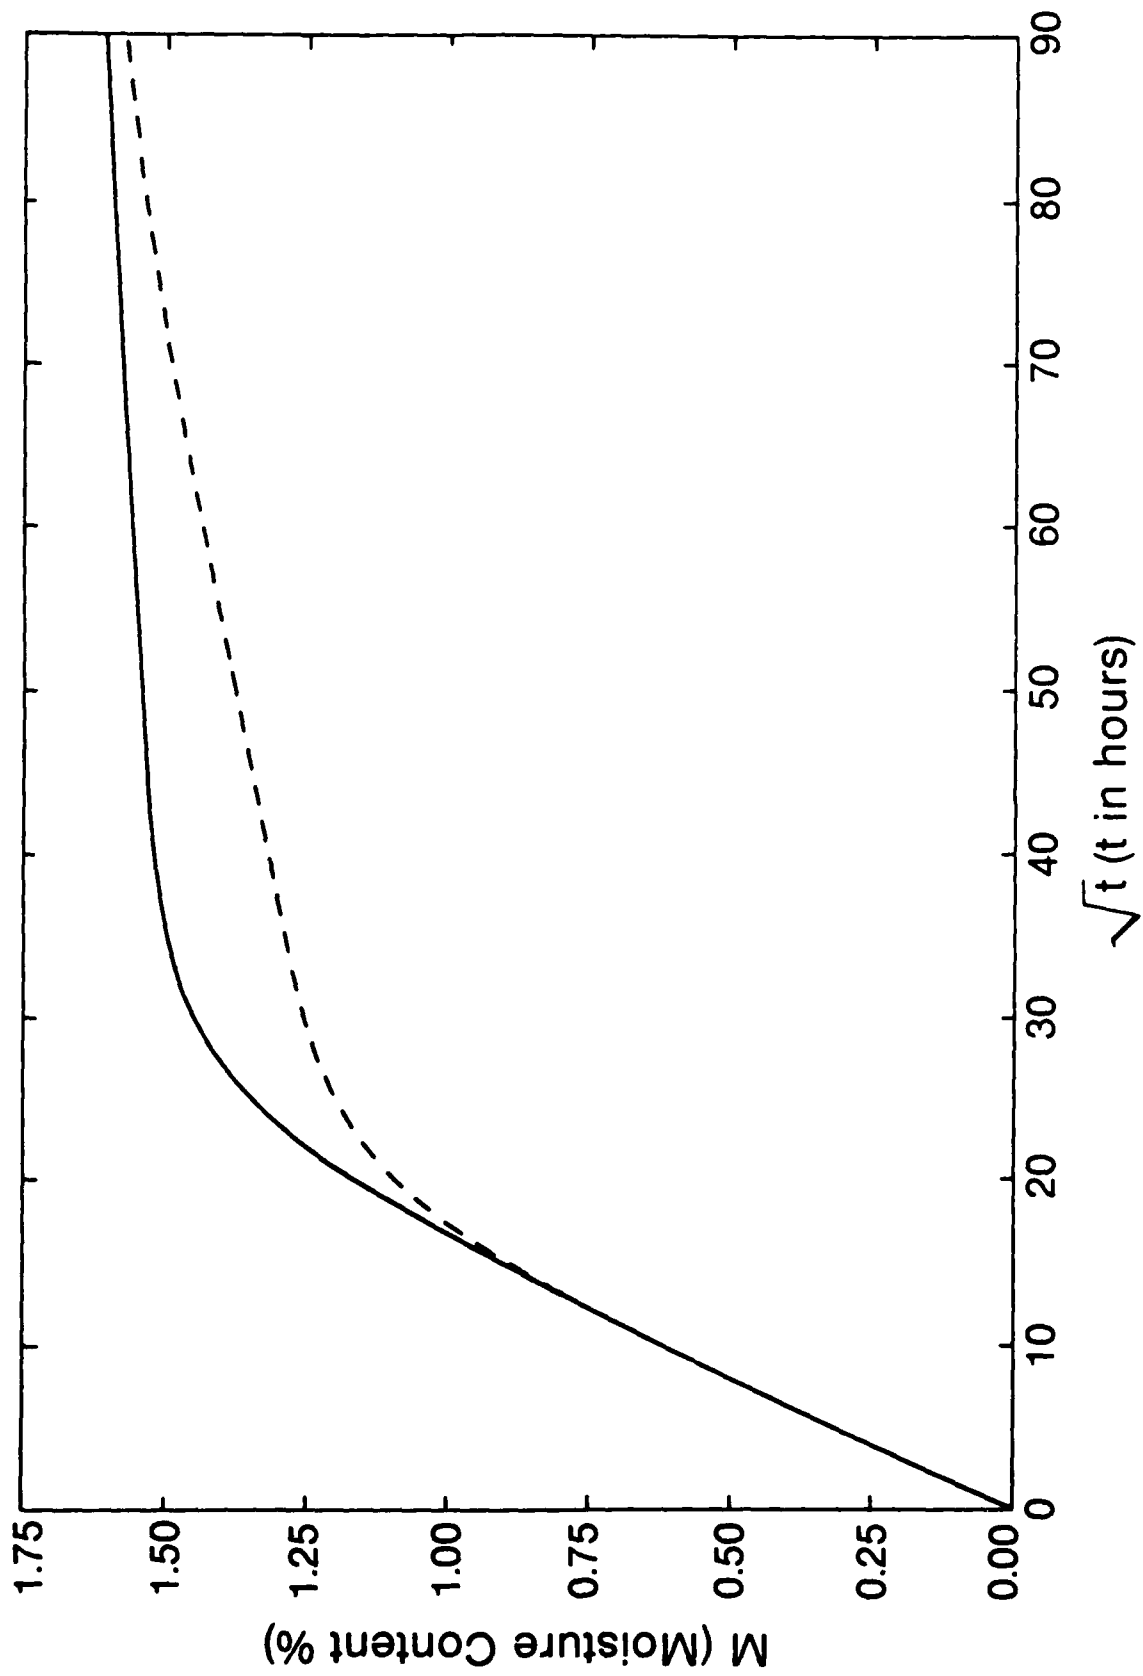


Fig. 3

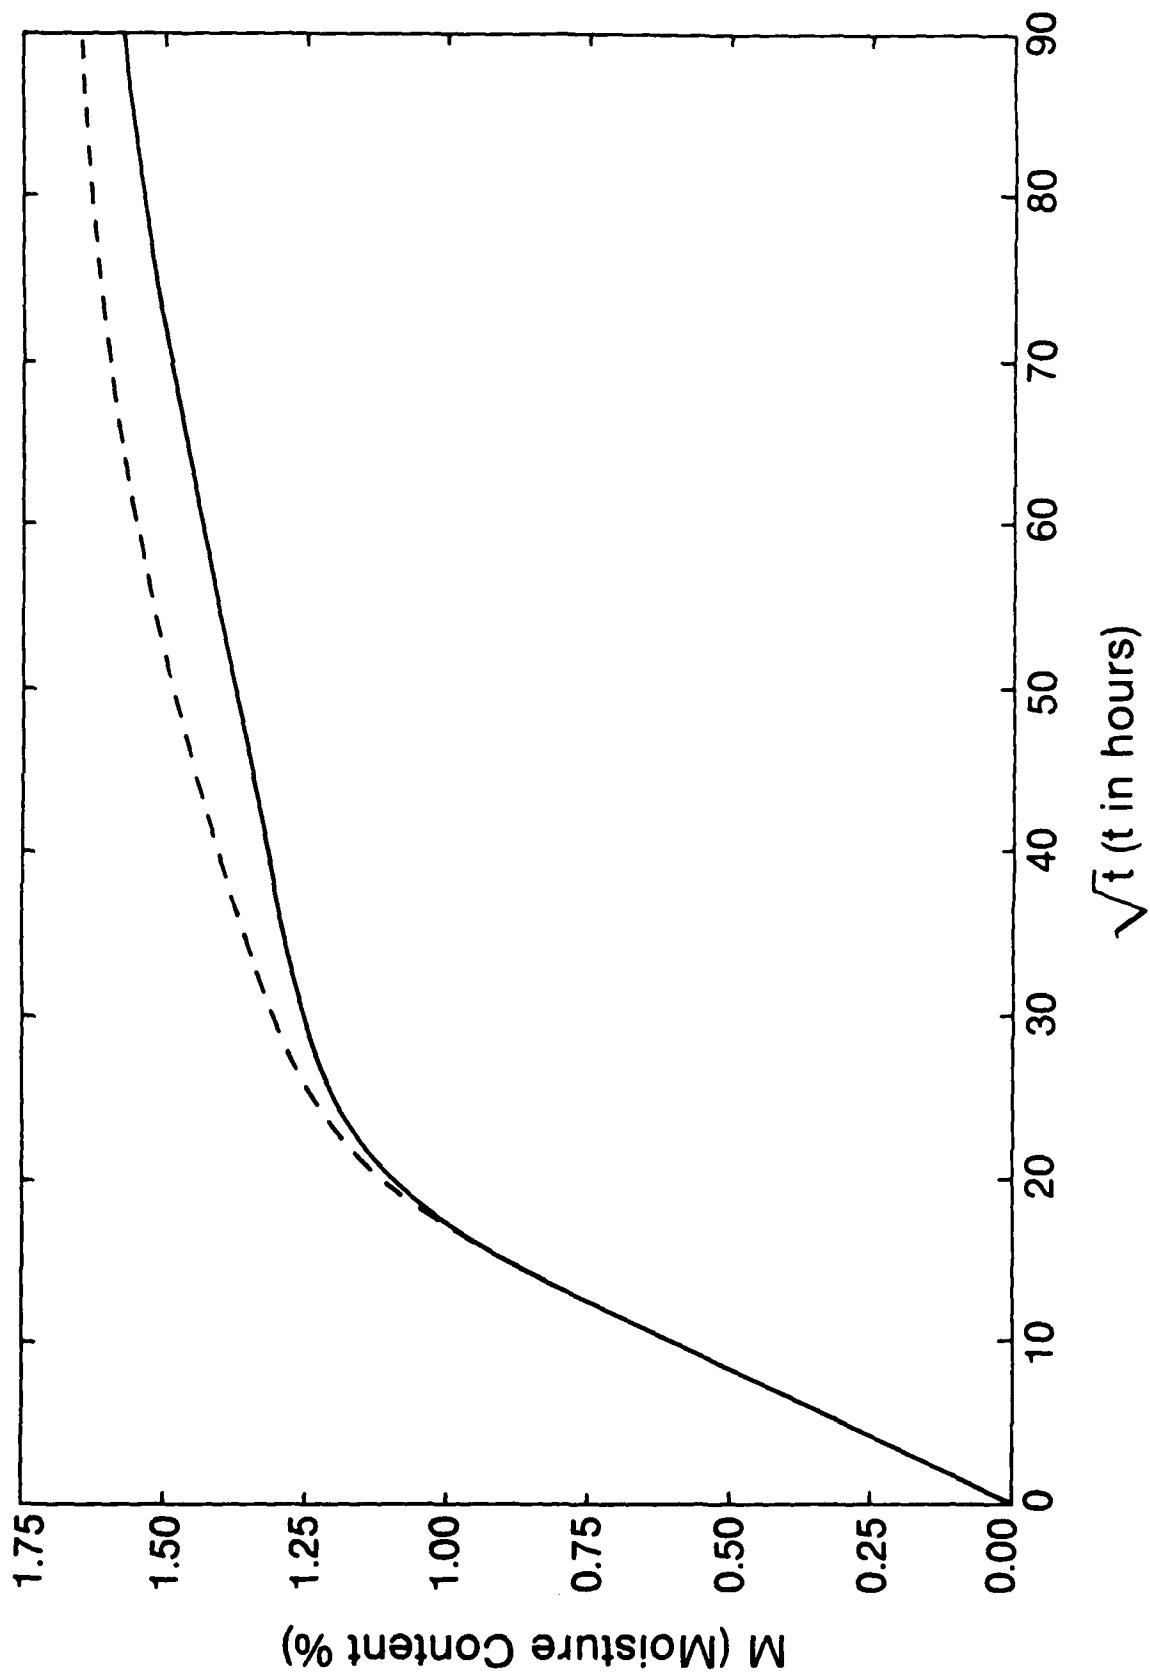


Fig. 4

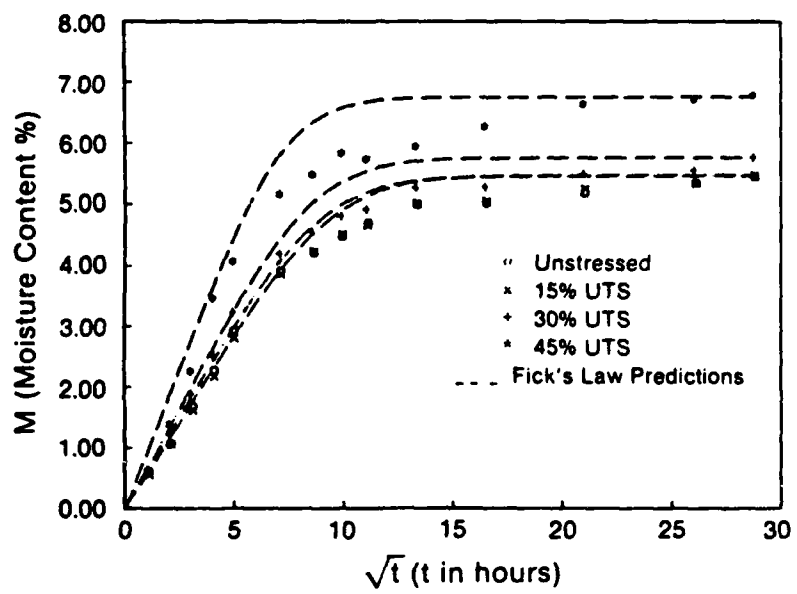


Fig. 5

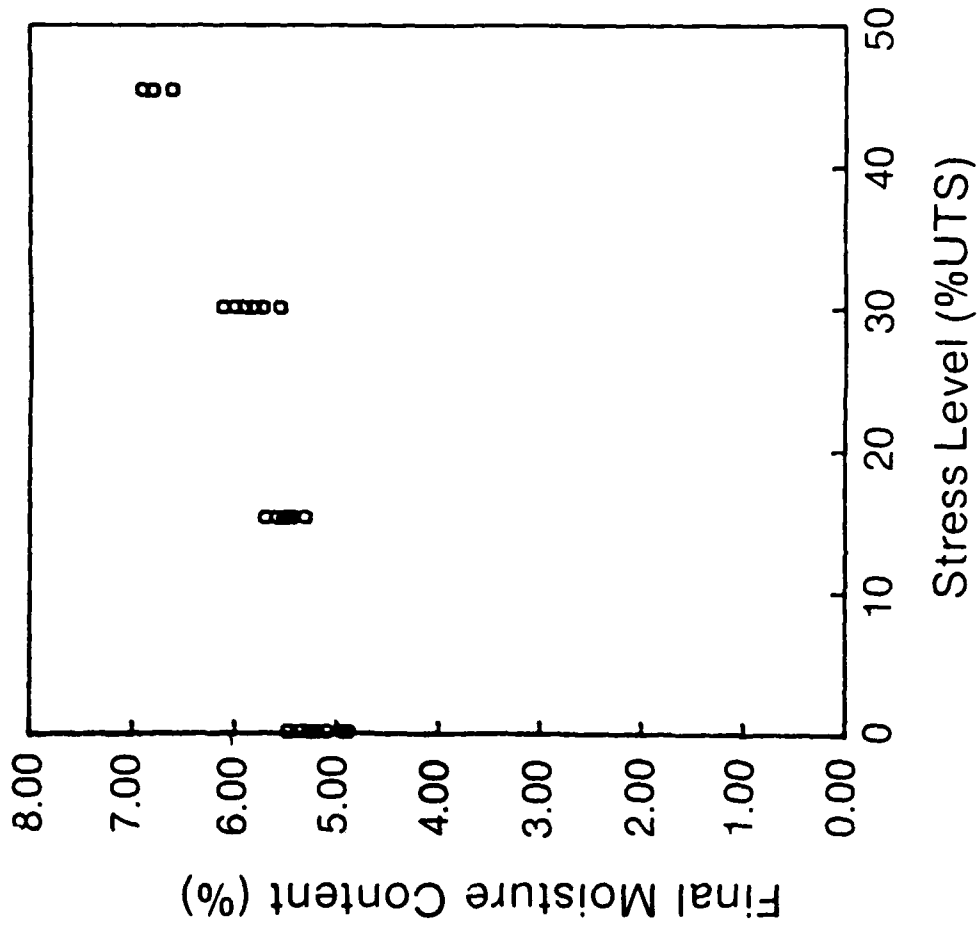


Fig. 6

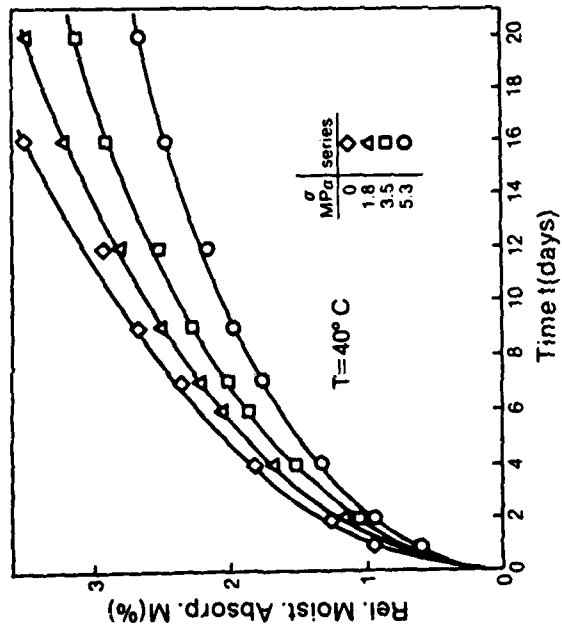


Fig. 7

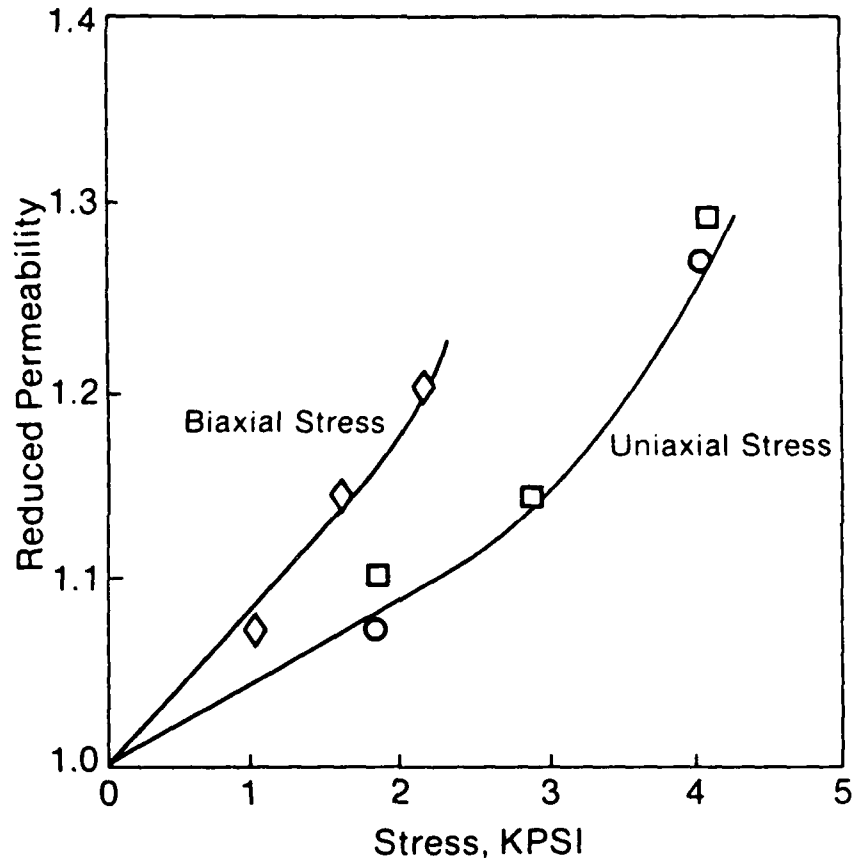


Fig. 8

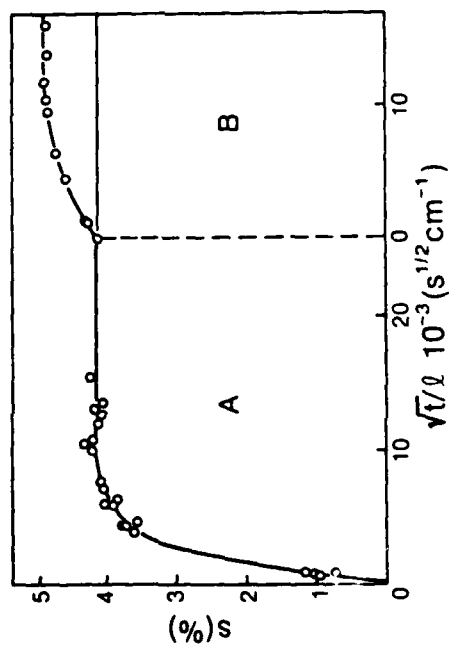


Fig. 9