

A liquid crystal derived from ruthenium(II,III) and a long-chain carboxylate

Andrés Zelcer,^a Zulema D. Chaia,^{a*} Fabio D. Cukiernik,^{a,b} Eduardo E. Castellano^c and Oscar E. Piro^d

^aINQUIMAE, Departamento de Química Inorgánica, Analítica y Química Física, Facultad de Ciencias Exactas y Naturales, Universidad de Buenos Aires, Ciudad Universitaria, Pabellón II, 1428 Buenos Aires, Argentina, ^bInstituto de Ciencias, Universidad Nacional de General Sarmiento, Roca 850, 1663 San Miguel, Buenos Aires, Argentina, ^cInstituto de Física de São Carlos, Universidad de São Paulo, CP 369, 13560 São Carlos (SP), Brazil, and ^dDepartamento de Física, Facultad de Ciencias Exactas, Universidad Nacional de La Plata and IFLP (CONICET), CC 67, 1900 La Plata, Argentina

Correspondence e-mail: zchaia@qi.fcen.uba.ar

Received 21 September 2001

Accepted 17 December 2001

Online 13 February 2002


The title compound, *catena*-poly[[tetrakis(μ -decanoato- κ^2 O:O')-diruthenium(II,III)(Ru—Ru)]- μ -octanesulfonato- κ^2 O:O'], [Ru₂(C₁₀H₁₉O₂)₄(C₈H₁₇O₃S)], is an octanesulfonate derivative of the mixed-valence complex diruthenium tetradeconoate. The equatorial carboxylate ligands are bidentate, bridging two Ru atoms to form a dinuclear structure. Each of the two independent dinuclear metal complexes in the asymmetric unit is located at an inversion centre. The octanesulfonate anion bridges the two dinuclear units through axial coordination. The alkyl chains of the carboxylate and sulfonate ligands are arranged in a parallel manner. The global structure can be seen as infinite chains of polar moieties separated by a double layer of non-polar alkyl groups, without interdigitation of the alkyl chains.

Comment

Mixed-valence diruthenium(II,III) tetracarboxylates, [Ru₂-(O₂CR)₄X] (X⁻ is an anion), have been extensively studied in recent years because they exhibit interesting electronic structures, spectroscopic features, magnetic behaviour and liquid crystalline (LC) properties (Aquino, 1998). In particular, LC phases (mesophases) have been obtained with long-chain carboxylates, provided that an appropriate combination of the equatorial carboxylate (RCO₂⁻) and axial anion (X⁻) is used (Cukiernik, Ibn-Elhaj *et al.*, 1998; Chaia *et al.*, 1999; Caplan *et al.*, 1999). For example, aliphatic equatorial carboxylates combined with long-chain axial anions, such as dodecylsulfate or an aliphatic carboxylate, induce mesomorphic behaviour (Cukiernik, Ibn-Elhaj *et al.*, 1998). In some of these cases, a model describing the structural changes taking place through the phase transition has been proposed.

As is usual in LC work, these models were based on the structural parameters of the LC phase (obtained from powder X-ray diffraction experiments), on information provided by local spectroscopic probes and on the crystalline structure of short-chain (non-mesogenic) analogues.

Of the more than 30 structures of mixed-valence diruthenium carboxylates that are known, the great majority deal with short-chain analogues (Bennett *et al.*, 1969; Bino *et al.*, 1979; Togano *et al.*, 1980; Cotton *et al.*, 1988; Barral *et al.*, 1997). The longest chain [Ru₂(O₂CR)₄X] compound for which the molecular structure is known is the non-mesogenic pentanoate derivative [Ru₂{O₂C(CH₂)₃CH₃]₄Cl] (Cukiernik, Luneau *et al.*, 1998). We have now determined the structure of the title ruthenium decanoate derivative with octanesulfonate as the axial anion, [Ru₂{O₂C(CH₂)₈CH₃]₄{O₃S(CH₂)₇CH₃}], (I). This compound is particularly interesting, as it undergoes a transition to a thermotropic hexagonal columnar LC phase at 458 K. We are confident that the crystal structure information we report here will be useful when interpreting the structure of the mesophase of the whole [Ru₂{O₂C(CH₂)_{*n*}-CH₃]₄{O₃S(CH₂)₇CH₃}] series of compounds, with *n* = 8–16.

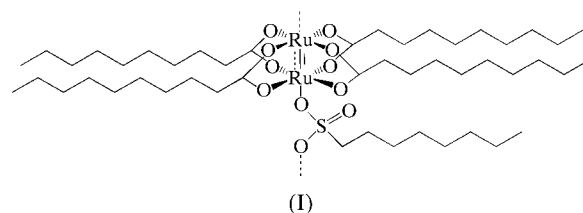


In compound (I), an {Ru₂}⁵⁺ metallic centre is bridged by four carboxylate equatorial ligands; the axial positions are occupied by the octanesulfonate anion. The unit cell contains two independent dinuclear complexes, each located at a crystallographic inversion centre. The Ru atoms are in an environment of approximately C_{4v} symmetry, while the dinuclear structure exhibits approximate D_{4h} symmetry.

The Ru—O equatorial bond distances are in the range 2.019 (3)–2.034 (3) Å. The average O—C—O bond angle of the carboxylate ligands is 123.1 (3)°, and the O_{*i*}—Ru_{*j*}—Ru'_{*j*} angles (*i* = 11, 12, 13, 14, 21, 22, 23 or 24, and *j* = 1 or 2) are nearly 90°. Thus, the pseudo-octahedral environment of the Ru atoms is not significantly distorted, indicating that the dinuclear structure is achieved with little stress around the metal centres.

The Ru—Ru' distance is 2.271 (3) Å (averaged for the two independent dinuclear units), a typical value for mixed-valence diruthenium carboxylates axially coordinated by O atoms (Aquino, 1998). Four alkyl chains from carboxylate ligands are oriented towards the periphery of the polar centre in a zigzag conformation; two are completely extended, while the others rotate around the β -C atom (C12 and C32) in order to align with the former chains. The alkyl chain of the sulfonate ligand also aligns in an extended conformation parallel to the carboxylic acid alkyl chains.

The alkylsulfonate moiety acts as a bidentate ligand bridging two independent dinuclear units (Fig. 1). The three S—O distances are consistent with double bonds, although the S—

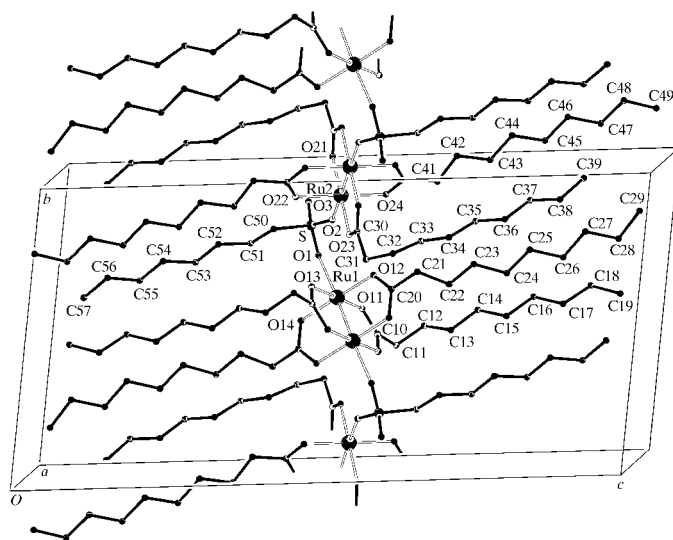
Figure 1

The crystal packing of (I) viewed down the *a* axis, showing the non-H atom labelling. Only the most populated (61% occupancy) of the two conformations of the C1*n* chain is shown for clarity.

O3 bond is significantly shorter than the other two. This can be ascribed to a slight softening of the S—O bonds involved in coordination to the Ru centres (S—O1 and S—O2), arising from π back-donation.

Due to the bridging nature of the octanesulfonate axial anion, the bimetallic centres polymerize in an infinite chain nearly parallel to the *b* axis. An intermolecular distance along the polymeric structure of 6.76 (1) Å can be calculated, being the distance between two neighbouring dinuclear centres. The corresponding Ru—Ru axes are nearly perpendicular to each other [91.94 (4)°]. However, all the aliphatic chains (both carboxylic and sulfonic) of each such polymeric structure are parallel, without interdigitation.

In the global structure, polar chains composed of dinuclear centres and sulfonate axial ligands are separated by non-polar double layers of alkyl chains. An interlayer separation of 26.623 (3) Å can be inferred from the distance between adjacent *ab* faces. There is no interdigitation between adjacent layers.

Experimental

[Ru₂(O₂C(CH₂)₈CH₃)₄Cl] was synthesized following a method already reported for other homologues of this series (Cukiernik, Ibn-Elhaj *et al.*, 1998). Compound (I) was obtained by a metathesis reaction. A methanol suspension of [Ag{O₃S(CH₂)₇CH₃}] (150 mg) was added slowly to [Ru₂(O₂C(CH₂)₈CH₃)₄Cl] (418 mg) dissolved in methanol. The reaction was protected from light and refluxed for 3 h under nitrogen. The AgCl by-product was filtered off while still hot and the solvent was evaporated under vacuum. The pale-brown solid obtained was dissolved in CH₂Cl₂, the solution was filtered on a 0.2 µm porous membrane and, after addition of heptane, the CH₂Cl₂ was evaporated under vacuum. After a couple of hours, a pale-brown solid was filtered off, and then washed by suspension in ethyl ether and distilled water. Brown crystals of (I) were obtained by slow

evaporation of a methanolic solution. Characterization was performed by IR spectroscopy (KBr pellets) on an FT-IR Nicolet 510P and by elemental analysis on a Carlo Erba EA1108 analyzer. IR spectroscopic analysis (ν , cm⁻¹): 1249 (*m*) (ν_{S-O} SO₃), 1115 (*s*) (ν_{S-O} SO₃); analysis calculated for C₄₈H₉₃O₁₁Ru₂S: C 53.36, S 2.97, H 8.68%; found: C 53.50, S 2.26, H 8.63%; calculated for C₄₀H₇₆ClO₈Ru₂: C 52.07, H 8.30%; found: C 51.31, H 8.39%.

Crystal data

[Ru₂(C₁₀H₁₉O₂)₄(C₈H₁₇O₃S)]
M_r = 1080.43
 Triclinic, *P* $\bar{1}$
a = 8.0020 (1) Å
b = 13.3040 (4) Å
c = 26.7230 (6) Å
 α = 83.427 (2)°
 β = 85.045 (1)°
 γ = 74.051 (1)°
V = 2712.9 (1) Å³

Z = 2
D_x = 1.321 Mg m⁻³
 Mo K α radiation
 Cell parameters from 8725 reflections
 θ = 1.0–27.5°
 μ = 0.65 mm⁻¹
T = 120 (2) K
 Thin plate, red
 0.40 × 0.18 × 0.06 mm

Table 1

Selected geometric parameters (Å, °).

Ru1—O12	2.023 (3)	Ru2—O23	2.035 (3)
Ru1—O14	2.028 (3)	Ru2—O22	2.034 (3)
Ru1—O13	2.020 (3)	Ru2—O2	2.233 (3)
Ru1—O11	2.029 (3)	Ru2—Ru2 ⁱⁱ	2.2732 (6)
Ru1—O1	2.228 (3)	O21—C30 ⁱⁱ	1.278 (5)
Ru1—Ru1 ⁱ	2.2680 (6)	O22—C40 ⁱⁱ	1.275 (5)
O11—C10	1.284 (5)	O23—C30	1.282 (5)
C10—O13 ⁱ	1.265 (5)	C30—O21 ⁱⁱ	1.278 (5)
C10—C11	1.504 (8)	C30—C31	1.491 (6)
C10—C11 ⁱ	1.505 (9)	C40—O22 ⁱⁱ	1.275 (5)
O12—C20	1.262 (5)	C40—C41	1.486 (5)
C20—O14 ⁱ	1.275 (5)	S—O3	1.430 (4)
C20—C21	1.502 (5)	S—O1	1.467 (3)
O13—C10 ⁱ	1.265 (5)	S—O2	1.471 (3)
O14—C20 ⁱ	1.275 (5)	S—C50	1.785 (5)
Ru2—O24	2.019 (3)	C50—C51	1.507 (6)
Ru2—O21	2.021 (3)	C51—C52	1.519 (6)
O12—Ru1—O14	178.8 (1)	O24—Ru2—O22	178.6 (1)
O12—Ru1—O13	90.8 (1)	O21—Ru2—O22	88.7 (1)
O14—Ru1—O13	89.9 (1)	O23—Ru2—O22	91.4 (1)
O12—Ru1—O11	89.8 (1)	O24—Ru2—O2	89.3 (1)
O14—Ru1—O11	89.5 (1)	O21—Ru2—O2	85.5 (1)
O13—Ru1—O11	179.0 (1)	O23—Ru2—O2	95.2 (1)
O12—Ru1—O1	93.1 (1)	O22—Ru2—O2	91.9 (1)
O14—Ru1—O1	87.8 (1)	O24—Ru2—Ru2 ⁱⁱ	89.59 (8)
O13—Ru1—O1	87.7 (1)	O21—Ru2—Ru2 ⁱⁱ	89.01 (8)
O11—Ru1—O1	93.1 (1)	O23—Ru2—Ru2 ⁱⁱ	90.28 (8)
O12—Ru1—Ru1 ⁱ	89.10 (8)	O22—Ru2—Ru2 ⁱⁱ	89.36 (8)
O14—Ru1—Ru1 ⁱ	90.00 (8)	O2—Ru2—Ru2 ⁱⁱ	174.33 (9)
O13—Ru1—Ru1 ⁱ	89.38 (9)	C30 ⁱⁱ —O21—Ru2	119.9 (3)
O11—Ru1—Ru1 ⁱ	89.83 (9)	C40 ⁱⁱ —O22—Ru2	118.7 (3)
O1—Ru1—Ru1 ⁱ	176.36 (7)	C30—O23—Ru2	117.9 (2)
C10—O11—Ru1	118.2 (2)	O21 ⁱⁱ —C30—O23	122.9 (4)
O13 ⁱ —C10—O11	123.0 (3)	O21 ⁱⁱ —C30—C31	117.7 (4)
O13 ⁱ —C10—C11	114.4 (8)	C40—O24—Ru2	119.3 (3)
O11—C10—C11	122.5 (8)	O22 ⁱⁱ —C40—O24	123.0 (4)
O13 ⁱ —C10—C11 ⁱ	127 (1)	O22 ⁱⁱ —C40—C41	119.0 (4)
O11—C10—C11 ⁱ	110 (1)	O24—C40—C41	117.9 (4)
C20—O12—Ru1	119.3 (2)	O3—S—O1	112.5 (2)
O12—C20—O14 ⁱ	123.6 (4)	O3—S—O2	116.4 (2)
O12—C20—C21	118.6 (4)	O1—S—O2	108.32 (18)
O14 ⁱ —C20—C21	117.8 (4)	O3—S—C50	105.8 (3)
C10 ⁱ —O13—Ru1	119.5 (3)	O1—S—C50	106.7 (2)
C20 ⁱ —O14—Ru1	117.9 (3)	O2—S—C50	106.5 (2)
O24—Ru2—O21	92.3 (1)	S—O1—Ru1	129.6 (2)
O24—Ru2—O23	87.6 (1)	S—O2—Ru2	147.4 (2)
O21—Ru2—O23	179.3 (1)	C51—C50—S	113.8 (4)

Symmetry codes: (i) 1 - *x*, 1 - *y*, 1 - *z*; (ii) -*x*, 2 - *y*, 1 - *z*.

Data collection

Nonius KappaCCD area-detector diffractometer	11 539 independent reflections
CCD scans	8728 reflections with $I > 2\sigma(I)$
Absorption correction: numerical (Spek, 1990)	$R_{\text{int}} = 0.084$
$T_{\text{min}} = 0.782$, $T_{\text{max}} = 0.965$	$\theta_{\text{max}} = 27.5^\circ$
31 736 measured reflections	$h = -10 \rightarrow 10$
	$k = -17 \rightarrow 17$
	$l = -34 \rightarrow 30$

Refinement

Refinement on F^2	$w = 1/[\sigma^2(F_o^2) + (0.0748P)^2 + 2.5168P]$
$R[F^2 > 2\sigma(F^2)] = 0.049$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.155$	$(\Delta/\sigma)_{\text{max}} = 0.124$
$S = 1.11$	$\Delta\rho_{\text{max}} = 1.04 \text{ e } \text{\AA}^{-3}$
11 539 reflections	$\Delta\rho_{\text{min}} = -1.67 \text{ e } \text{\AA}^{-3}$
647 parameters	
H-atom parameters constrained	

The C11–C19 carboxylate chain is disordered. During the refinement, the corresponding occupancies were allowed to vary so as to sum to 1.0 and the C–C bond distances were restrained to a target value of 1.51 (1) Å. Several H atoms were located in a Fourier difference map. However, they were positioned stereochemically and refined with a riding model. The methyl H atoms were treated in the refinement as rigid bodies and allowed to rotate around the corresponding C–C bond so as to maximize the sum of the observed electron density at the three calculated H-atom positions. As expected, all methyl groups converged to staggered conformations.

Data collection: *KappaCCD Software* (Nonius, 1997); cell refinement: *SCALEPACK* (Otwinowski & Minor, 1997); data reduction: *DENZO* and *SCALEPACK*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 1997); program(s) used to refine structure: *SHELXL97* (Sheldrick, 1997); molecular graphics: *PLATON* (Spek, 1998); software used to prepare material for publication: *WinGX* (Farrugia, 1999).

This work was supported by CONICET and the University of Buenos Aires (grant AX27), Argentina, and by FAPESP and the Vitae Foundation, Brazil. FDC and OEP are members of the Scientific Staff of CONICET. We thank the Cambridge Structural Database and AZ thanks the University of Buenos Aires for a student fellowship.

Supplementary data for this paper are available from the IUCr electronic archives (Reference: DA1217). Services for accessing these data are described at the back of the journal.

References

- Aquino, M. A. S. (1998). *Coord. Chem. Rev.* **170**, 141–202.
- Barral, M. C., Jiménez-Aparicio, R., Priego, J. L., Royer, E. C., Urbanos, F. A. & Amador, U. (1997). *J. Chem. Soc. Dalton Trans.* pp. 863–868.
- Bennett, M. J., Caulton, K. G. & Cotton, F. A. (1969). *Inorg. Chem.* **8**, 1–6.
- Bino, A., Cotton, F. A. & Felthouse, T. R. (1979). *Inorg. Chem.* **18**, 9, 2599–2604.
- Caplan, J. F., Murphy, C. A., Swansburg, S., Lemieux, R. P., Cameron, S. & Aquino, M. A. S. (1999). *Can. J. Chem.* **76**, 1520–1523.
- Chaia, Z., Heinrich, B., Cukiernik, F. D. & Guillon, D. (1999). *Mol. Cryst. Liq. Cryst.* **330**, 213–220.
- Cotton, F. A., Matusz, M. & Zhong, B. (1988). *Inorg. Chem.* **27**, 4368–4372.
- Cukiernik, F. D., Ibn-Elhaj, M., Chaia, Z. D., Marchon, J. C., Giroud-Godquin, A. M., Guillon, D., Skoulios, A. & Maldivi, P. (1998). *Chem. Mater.* **10**, 83–91.
- Cukiernik, F. D., Luneau, D., Marchon, J. C. & Maldivi, P. (1998). *Inorg. Chem.* **37**, 3698–3704.
- Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
- Nonius (1997). *KappaCCD Software*. Nonius BV, Delft, The Netherlands.
- Otwinowski, Z. & Minor, W. (1997). *Methods in Enzymology*, Vol. 276, *Macromolecular Crystallography*, Part A, edited by C. W. Carter & R. M. Sweet, pp. 307–326. London: Academic Press.
- Sheldrick, G. M. (1997). *SHELXS97* and *SHELXL97*. University of Göttingen, Germany.
- Spek, A. L. (1990). *Acta Cryst.* **A46**, C-34.
- Spek, A. L. (1998). *PLATON*. University of Utrecht, The Netherlands.
- Togano, T., Mukaida, M. & Nomura, T. (1980). *Bull. Chem. Soc. Jpn.* **53**, 2085–2086.