

An improved method for preparing glutaraldehyde cross-linked chitosan–poly(vinyl alcohol) microparticles

Elisa Campos · Patrícia Coimbra · M. H. Gil

Received: 28 March 2012/Revised: 13 July 2012/Accepted: 12 September 2012/
Published online: 19 September 2012
© Springer-Verlag Berlin Heidelberg 2012

Abstract The features of microparticles, as size, surface structure, and morphology, depend, mainly, on the methodology used for their preparation. Emulsion polymerization techniques are undoubtedly among the most widespread. However, the use of toxic, volatile organic solvents represents a major disadvantage, namely, because of environmental issues. In this study, we prepared glutaraldehyde cross-linked chitosan–poly(vinyl alcohol) microparticles by an improved water-in-oil emulsion technique using corn oil as organic phase. The application of this polymeric blend as microparticle is scarcely investigated. As resulting of the procedure here presented, spherical and smooth surface microparticles were obtained, with mean diameter of 16 μm . The cross-linking reaction between the aldehyde and the amino or the hydroxyl groups formed either an imine (Schiff's base) or an acetal bond, respectively, as analyzed by infrared spectroscopy. The microparticles here described did not present cytotoxic potential. Accordingly, this study can find promising and successful application in biotechnology.

Keywords Microparticle · Chitosan · Poly(vinyl alcohol) · Glutaraldehyde · Water-in-oil emulsion · Cytotoxicity

E. Campos (✉) · P. Coimbra · M. H. Gil
Chemical Process Engineering and Forest Products Research Centre (CIEPQPF), Department of
Chemical Engineering, Faculty of Sciences and Technology, University of Coimbra,
Rua Sílvio Lima, 3030-790 Coimbra, Portugal
e-mail: elisajcampos@gmail.com

Present Address:

E. Campos
Instituto de Tecnologia Química e Biológica, Universidade Nova de Lisboa, Av. da República,
2780-157 Oeiras, Portugal

Introduction

The development and/or improvement of polymeric matrices represents an interesting and promising challenge in Material Sciences. Strategies as chemical modification or combination of polymers can be straightforwardly followed towards new materials with potential applications in several fields. In the case of biomaterials, improvements in their characteristics have been achieved by the combination of synthetic polymers and biological polymers. Whereas synthetic polymers are characterized by their good physicochemical and mechanical properties but not sufficient biocompatibility, biological polymers have good biocompatibility but their mechanical properties are often limited [1]. An example of a successful combination has been blending chitosan and poly(vinyl alcohol) (PVA) [2].

Chitosan is a natural cationic polysaccharide, which is a copolymer formed by units of 2-deoxy-*N*-acetyl-D-glucosamine and 2-deoxy-D-glucosamine linked by β -1,4 glycosidic bonds. It occurs rarely in nature being generally obtained by alkaline and by enzymatic deacetylation of chitin, the second most abundant natural polymer found in nature, obtained from the exoskeleton of shrimps, fungi, insects, annelids, and mollusks. Chitosan has been preferred over chitin because it is readily soluble in dilute acids and, therefore, easily processed. Moreover, chitosan is biocompatible, biodegradable, nontoxic, mucoadhesive, hemostatic, hypocholesterolemic, hypolipidemic, antimicrobial, immunoadjuvant, antiviral, and antitumoral [3], which make it very attractive for applications in Medicine and Pharmacy. This biopolymer has been also tested in other scientific and industrial fields as soil remediation [4], wastewater treatment [5], food packaging [6] and cosmetics [7], among others.

PVA is produced by the polymerization of vinyl acetate to poly(vinyl acetate) (PVAc), followed by hydrolysis of PVAc to PVA. The hydrolysis reaction is not complete resulting in polymers with a certain degree of hydrolysis that depends on the extent of reaction [8]. As it is nontoxic, water-soluble, biocompatible, and biodegradable, this synthetic polymer is widely used namely for biochemical and biomedical applications [9].

There are several chitosan cross-linking agents already described such as genipin [10], glyoxal [11], epichlorohydrin [12], and ascorbic acid [13]. In this study, glutaraldehyde was chosen as cross-linking agent. Glutaraldehyde has been used more frequently as a cross-linking agent than any other reagent, as it is less expensive, readily available, and highly soluble in aqueous solution [14]. The high reactivity of the aldehyde groups, which readily form imine bonds (Schiff's base) with amino groups and acetal bonds with hydroxyl groups [15], provides the efficiency of glutaraldehyde on the cross-linking of chitosan and PVA.

The polymeric matrix resultant from the cross-linking of chitosan and PVA by glutaraldehyde has shown promising attributes for practical applications, because of its high swelling and shrinking ratio, high pH sensitivity and biodegradability [16]. Membranes [17], hydrogels [16], and films [2] based on this polymeric matrix were reported. From our knowledge, our research group prepared, for the first time, microparticles based on a similar polymeric matrix [18].

Microparticles constitute a technology used by several industries as agricultural, food, graphics, cosmetics, and pharmaceutical. For the preparation of these systems, there is a large number of starting materials and techniques [19]. In this study, microparticles were prepared by solvent extraction/evaporation, specifically water-in-oil emulsion. Basically, this technique consists of four major steps: (i) dissolution of the polymer in an appropriate solvent; (ii) emulsification of this polymeric phase in a second continuous phase immiscible with the first one; (iii) extraction of the solvent from the dispersed (polymeric) phase, transforming the droplets into solid microparticles; (iv) recovery of the microparticles. In water-in-oil emulsion, neither elevated temperatures nor phase separation-inducing agents are required [20], which make it valuable for industrial applications and suitable for the encapsulation of thermolabile compounds. However, the use of toxic, volatile organic solvents as the continuous phase such as cyclohexane [21], toluene, and chloroform [22] constitutes a major drawback regarding the safe production and usage of the microparticles. To overcome this issue, we developed a nonvolatile organic solvent water-in-oil emulsion method using vegetable oil (corn oil) as organic phase.


In this study, we improved a previous procedure [18] aiming the design of a water-in-oil emulsion technique protocol volatile organic solvent-free to prepare glutaraldehyde cross-linked chitosan–PVA microparticles (CCPMs). Moreover, we also improved the procedure to obtain smooth surface microparticles. Particle size analysis, morphological and topographical studies were made, as well as chemical studies by attenuated total reflectance-Fourier transform infrared (ATR-FTIR) spectroscopy. As we were mainly focused on an application in the field of biotechnology and biomedicine, cell toxicity of CCPMs was also evaluated.

Experimental section

Materials

Chitosan (medium molecular weight, degree of deacetylation 75–85 %), glutaraldehyde (25 % (v/v)) aqueous solution and PVA (M_w 9,000–10,000, 80 % hydrolyzed) were obtained from Aldrich (St. Louis, MO). Acetic acid (96 %, p.a.) and methanol (p.a.) were purchased from Merck (Darmstadt, Germany) and Panreac (Barcelona, Spain), respectively. Corn oil and petroleum ether were received from Sovena (Algés, Portugal) and JM Vaz Pereira (Sintra, Portugal), respectively. Complete RPMI 1640 was used as culture medium and was prepared with RPMI 1640 (Invitrogen, Carlsbad, CA), penicillin–streptomycin solution (1 %), L-glutamine (1 %), and 10 % (v/v) fetal bovine serum were purchased from Aldrich (St. Louis, MO). 3-(4,5-Dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) was supplied by Aldrich (St. Louis, MO). Isopropanol and chloridric acid were bought from Merck (Darmstadt, Germany). All chemicals were used without further purification. The distilled water used was prepared in the laboratory. Sterile 96-well flat-bottomed culture plates were supplied by Corning Inc, Costar[®] (Lowell, MA).

Scheme 1 Representative steps followed for the preparation of CCPMs by water-in-oil emulsion method

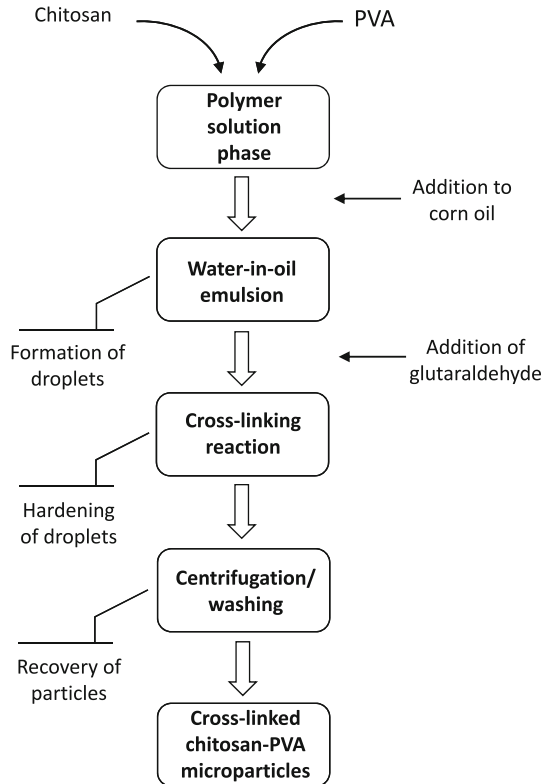

Preparation of CCPMs by water-in-oil emulsion

The main steps of the preparation of CCPMs by water-in-oil emulsion are depicted in Scheme 1. The dispersed/polymeric phase was composed by 2 % (w/v) chitosan solution in 2 % acetic acid:methanol (2:1, v/v) and 2 % (w/v) PVA in water:methanol (1:2, v/v). This aqueous polymeric solution was added, dropwise, to corn oil as organic continuous phase (1:50, v/v). A stable water-in-oil emulsion was obtained after 2 h at 38 °C, under continuous mechanical stirring (RZR-1, Heidolph, Germany) at 1,370 rpm. The cross-linking agent, 25 % (v/v) glutaraldehyde as solution saturated in toluene [23–25] was dropped in the emulsion. The cross-linking reaction was carried out for during 2 h at 38 °C. The CCPMs obtained were recovered from the continuous phase by centrifugation at 3,500 rpm for 10 min. Then, the CCPMs were washed with petroleum ether twice and copiously with distilled water. Finally, CCPMs were dried in the oven at 37 °C and kept in sealed containers prior to their use.

Morphology

All CCPMs were preliminarily observed for size and shape by optical microscopy using a BH2 (Olympus, Japan) microscope. Shape and surface characteristics of

CCPMs were investigated by scanning electron microscopy (SEM). The CCPMs were dispersed in water, dropped in a cover glass, and air-dried at room temperature. The cover glass was fixed onto a metal stub with a double-sided adhesive tape. The sample was then sputter coated, under vacuum and in argon atmosphere, with copper and examined in a JSM-5310 (Jeol, Japan) scanning microscope operating at 25 kV, at room temperature.

Particle size study

The particle size and particle size distribution were analyzed by laser light scattering using a LS 130 (Beckman Coulter, USA) particle analyzer. Small amounts of CCPMs were suspended in water. To destroy possible aggregates, CCPMs were sonicated for 1–2 min before analysis. Particle size and particle size distribution values were determined according to the Theory of Fraunhofer, using the Coulter software.

FTIR analysis

Chemical composition of CCPMs polymeric matrix was analyzed by infrared spectroscopy using a Magna IR System 750 (Nicolet, USA) IR spectrometer with an ATR accessory (golden gate Mk II with diamond top-plate and ZnSe lenses, Specac, UK). Chitosan, PVA, and CCPMs FTIR spectra were recorded at room temperature, in the frequency range 4,000–400 cm^{-1} , at 4 cm^{-1} resolution and scanned 32 times.

Cell toxicity

The cytotoxicity of CCPMs was investigated by MTT assay [26] using peritoneal macrophages harvested from Wistar mice. Wistar mice (aprox. 300 g) were obtained from the Animal Facility of Faculty of Medicine, University of Coimbra, Portugal. All animals were maintained in accordance with to the national and international regulations on animal welfare. Macrophages were cultured in complete RPMI 1640 medium, at 37 °C in a humidified atmosphere containing 5 % CO_2 , for 4 h, until form a confluent monolayer [27]. Afterward, culture medium was replaced by CCPMs suspensions in complete RPMI medium at 0.2, 2.0, and 10 % (v/v) (final concentration). As negative control, the cells were incubated in complete culture medium without CCPMs. The cells were incubated in the same conditions. After 20-h incubation, the supernatant of each well was replaced by 0.5 mg mL^{-1} MTT in culture medium, and the cells were incubated for 2 h, in the same conditions. The MTT solution was then replaced by hydrogen chloride-2-propanol solution 4 %, to lyse cells and to solubilize the formazan crystals. After 5 min at room temperature, the absorbance was read on a microplate reader (Spectra SLT, Tecan, Switzerland) at 540 nm. Cell viability was calculated by comparing the sample absorbance (A_{sample}) to the negative control absorbance (A_{control}), which was by definition 100 %, according to the equation $(A_{\text{sample}}/A_{\text{control}}) \times 100$ [28]. Data were expressed as mean \pm standard deviation (SD) of three wells ($n = 3$). Statistical significance of CCPMs concentration changes in cell viability relatively to the negative control

were evaluated by one-way ANOVA (Microsoft Office Excel 2007). Tukey's HSD (honestly significant differences) test was used as a post hoc method to identify the significantly different means among CCPMs concentrations samples. Moreover, the toxic effect of CCPMs on cells viability was qualitatively observed by optical microscopy (Eclipse TE-300, Nikon, Japan). All the samples submitted to the cytotoxicity experiment were previously sterilized by exposure to UV light.

Results and discussion

Evaluation of CCPMs preparation procedure

In this study, CCPMs were prepared by an improved water-in-oil emulsion technique. Recently, other works were published where microparticles based on a similar polymeric matrix were prepared but using different preparation protocols [29–31], therefore, leading to microparticles with different characteristics. The improvements now presented aimed to prepare microsized particles of spherical and with smooth surface.

In our first attempts to produce glutaraldehyde cross-linked chitosan–PVA microparticles by water-in-oil emulsion, we used dichloromethane as organic phase [18]. However, we aspired to reduce toxic solvents in preparing microparticles. In this way, we decided to use vegetable oils as organic phase. Moreover, as the organic phase viscosity is one of the parameters which influence the size of microparticles produced by emulsion technique [32], it would be advantageous to use more viscous continuous phase to control microparticles size. Commercially, several vegetable oils are available with different viscosities [33]. This work was mainly focused in the use of corn oil as organic phase. However, sunflower and soya bean oils were also tested leading to similar results (data not shown).

In order to form spherical polymer droplets, water was removed from polymeric phase, diffusing into the vegetable oil phase and then evaporating at the oil/air interface [34]. By adding methanol to the polymeric solution, water removal was improved and, thus, the formation of spherical polymer droplets in vegetable oil [25, 35]. Although the use of a suitable stabilizer is pointed out in most preparation procedures of microparticles by emulsion, when using a vegetable oil that step can be avoided [32].

In this water-in-oil emulsion technique, two steps could be distinguished: (i) production of two-phase systems involving the dispersion of a chitosan and PVA solution in vegetable oil, leading to the formation of small droplets of polymeric solution in immiscible liquid; (ii) conversion of initially formed polymer droplets into the corresponding microparticles, as a result of gradual hardening of the droplets by cross-linking, due to the addition of glutaraldehyde. Water-soluble polymers with hydroxyl groups, as PVA, as well as amine-containing groups, like chitosan, can be cross-linked with glutaraldehyde. Glutaraldehyde in the organic phase induced the reaction between aldehyde groups and amino or hydroxyl groups at the surface of the polymer goblets. Consequently, there should be a high cross-linking density near the surface of the CCPMs, possibly, accompanied by

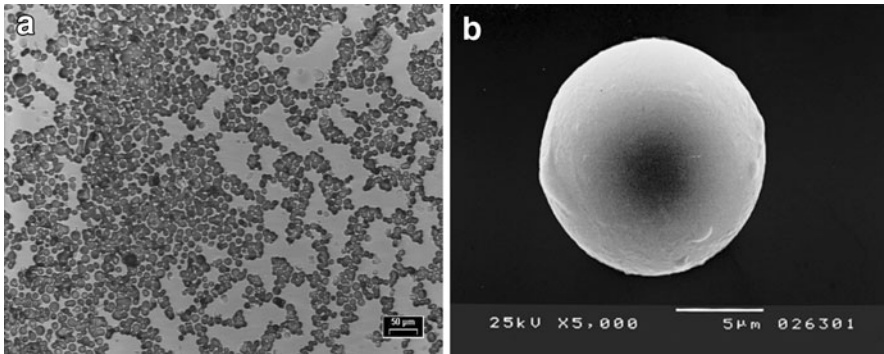


Fig. 1 Photographs of CCPMs acquired by **a** optical microscopy ($\times 10$) and **b** SEM ($\times 5,000$)

monoreacted dialdehyde at the surface. The resulting of monofunctional glutaraldehyde capping of chitosan and PVA at the CCPMs surface could, later on, facilitate a variety of chemical modifications including enzyme, antibody, or other protein ligand or even the tissue immobilization [23]. In this study, glutaraldehyde was added to the organic phase as solution saturated in toluene, improving its solubility in that phase and, therefore, enhancing cross-linking reaction.

Morphological characterization

The morphology of the CCPMs produced was investigated by optical microscopy and SEM. Examination of the CCPMs by optical microscopy revealed the formation of spherical particles, with regular shape, well-formed, without aggregation and, apparently, homogeneously distributed (Fig. 1a). Figure 1b shows a representative SEM photograph of the CCPMs surface. These CCPMs have smooth and uniform surface indicating the optimization of solvent evaporation rate during polymer droplets formation process, as described above. Besides, as the hardening of chitosan and PVA matrix was performed, with constant stirring at high speed, friction of vegetable oil with the CCPMs might have resulted in spherical geometry of these same particles, turning it smooth and with compact surface. The SEM observation also showed the nonexistence of pores on the surface of the CCPMs neither evidence of collapsed particles.

Particle size and particle size distribution

Particle size is a key property in certain processes related with the surface area, as degradation time [36]. While improving this procedure, speed of stirring was taken into account because it strongly determines particle size [37]. In fact, increasing speed of stirring led to smaller particles as a more efficient dispersion of polymeric phase in the organic one was achieved (data not shown). Moreover, it is known that the smaller the radius of a sphere, the larger is its surface area/volume ratio. By producing smaller microparticles, a more efficient release or adsorption system would be achieved, for instance.

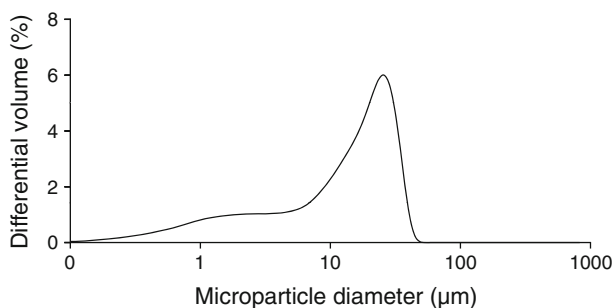


Fig. 2 Particle size distribution of CCPMs

The particle size distribution of CCPMs is shown in Fig. 2. CCPMs had particle size inferior to 49 μm in diameter and mean particle size was $16 \pm 11 \mu\text{m}$. Statistical analysis of CCPMs showed that 10 % of CCPMs sample population was above 32 μm diameter, 50 % was above 16 μm and 90 % was above 1 μm . Concerning skewness, which is a measure of the asymmetry of the frequency distribution, the value obtained was positive (0.289), meaning that the distribution was deviated to smaller size particles.

Chemical analysis of CCPMs polymeric matrix

FTIR spectroscopy was used to verify the structural modifications upon cross-linked reaction during preparation of CCPMs. Figure 3 shows the FTIR spectra of chitosan, PVA, and CCPMs. The FTIR spectrum of chitosan (spectrum a) showed a broad band at $3,285 \text{ cm}^{-1}$ due to O–H and amine N–H stretching. The peak at $2,867 \text{ cm}^{-1}$ was assigned to C–H stretch vibration. In addition to the peak at $1,586 \text{ cm}^{-1}$, assigned to amide II, there were also peaks at $1,639$ and $1,320 \text{ cm}^{-1}$, characteristic of chitin and chitosan, which have been reported as amide I and III bands, respectively. The peak at $1,373 \text{ cm}^{-1}$ was assigned to CH_3 deformation, whereas the peak at $1,420 \text{ cm}^{-1}$ was assigned O–H and C–H deformation. A significant peak around $1,027 \text{ cm}^{-1}$ is corresponding to C–O bending, typical of saccharide structure [38]. Regarding the spectrum of PVA (spectrum b), the characteristic absorption band at $3,212 \text{ cm}^{-1}$ was attributed to stretching of O–H group; bands at $2,914 \text{ cm}^{-1}$ and at $1,238$ and 844 cm^{-1} were assigned to C–H stretching and bending, respectively, whereas the band at $1,090 \text{ cm}^{-1}$ was due to C–O stretching. The band observed at $1,732 \text{ cm}^{-1}$ was characteristic of carbonyl group of PVAc. In fact, as PVA is prepared from PVAc, a certain amount of PVAc may still exist in PVA batch [39]. Oxidation of PVA occurred during the manufacturing and processing [40] can also explain the presence of PVAc. In the spectrum of CCPMs (spectrum c), a new peak was found at $1,644 \text{ cm}^{-1}$, which can be assigned to the C=N stretching vibration from the imine bond [13] formed by the reaction between amino groups of chitosan and aldehyde groups of glutaraldehyde. At $1,063 \text{ cm}^{-1}$, another new peak was observed, which was assigned to the acetal bond [41], due to the reaction of glutaraldehyde with the hydroxyl group of PVA.

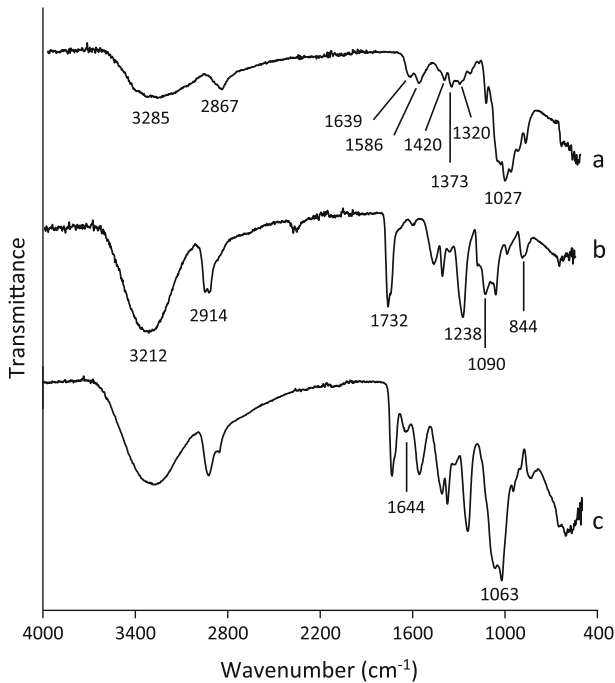


Fig. 3 Representative FTIR spectra of (a) chitosan, (b) PVA, and (c) CCPMs

CCPMs cytotoxicity

Cytotoxicity evaluation is on the first lane for screening biocompatibility or biological safety of materials. In general, accepted cytotoxic effects of materials are: cell death, loss of membrane integrity, reduced cell adhesion, altered cell morphology, reduced cell proliferation, and reduced biosynthetic activity [42]. There are several rapid, standardized, sensitive, and inexpensive tests to determine if a material contains significant quantities of biologically toxic extractables. The MTT cytotoxicity test is widely used for this purpose. Yellow water-soluble MTT is reduced by mitochondrial succinate dehydrogenase in viable cells to a blue–violet insoluble formazan. The number of viable cells is correlated to the color intensity, which is quantified using a spectrophotometer, after dissolving the formazan in acidic alcohol [43]. In this study, Wistar mouse peritoneal macrophages viability was measured after 20 h of incubation with 0.2, 2.0, and 10.0 % (v/v) CCPMs in culture medium (Fig. 4). According to one-way ANOVA, the cell viability of the negative control was significantly different from the one of the CCPMs concentrations of 2.0 and 10.0 % (v/v) samples ($p < 0.01$). Differences between cell viability of CCPMs concentration of 0.2 % (v/v) and of 2.0 % (v/v) ($p < 0.05$) and 10.0 % (v/v) ($p < 0.01$) were also identified as statistically significant. As cell viability was >70 % of the negative control in all tested CCPMs concentrations, according to the guidelines of ISO 10993-5 for biological evaluation of medical

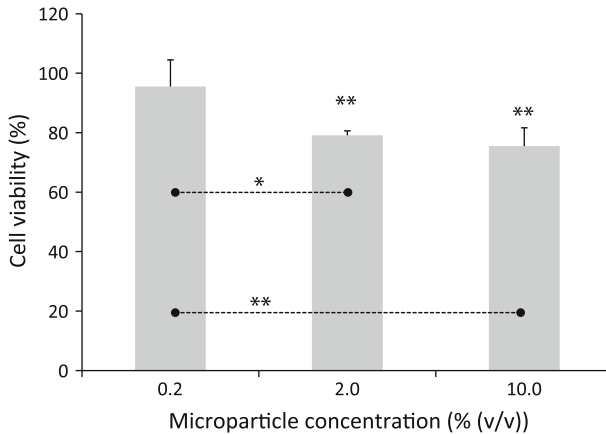


Fig. 4 CCPMs cell toxicity assessment performed by MTT assay on Wistar mouse peritoneal macrophages. Percentage of viable cells relative to the negative control after 20-h incubation with CCPMs at different concentrations. Data are represented as the mean \pm SD ($n = 3$). * $p < 0.05$; ** $p < 0.01$ (one-way ANOVA and Tukey's HSD test)

materials, we assumed that CCPMs matrices were able to preserve viability of cells, having, thus, no cytotoxic potential. Figure 5 shows optical micrographs of negative control and 2.0 % (v/v) CCPMs 20-h incubation, before and after the addition of MTT. The purple color due to formazan crystals inside cells (Fig. 5b, d) suggested that incubation with CCPMs did not affect cell viability.

The use of glutaraldehyde as cross-linking agent in the preparation of materials, in particular biomaterials, has been cause of concern as it is related to inflammatory reactions, cytotoxicity, calcification, and lack of endothelialization. However, reports of cytotoxic effects of glutaraldehyde were, in general, due to the use of a high glutaraldehyde concentration [14]. In this study, despite the use of toxic glutaraldehyde, results revealed no adverse effect on cells viability suggesting that its toxicity was likely minimized by the cross-linking reaction underwent in the preparation of CCPMs by the present procedure [44].

Conclusion

CCPMs were prepared by an improved and more environmentally friendly water-in-oil emulsion method. Results showed the formation of particles with good spherical shape, nonagglomerated, with smooth surface, and mean diameter of 16 μm . FTIR analysis suggested cross-linking reaction so that both imine and acetal groups were likely to occur during CCPMs preparation. Despite the use of glutaraldehyde as cross-linking agent, CCPMs proved to be noncytotoxic. We believe that this procedure can be followed straightforwardly in the preparation of CCPMs for a broad range of biotechnological applications.

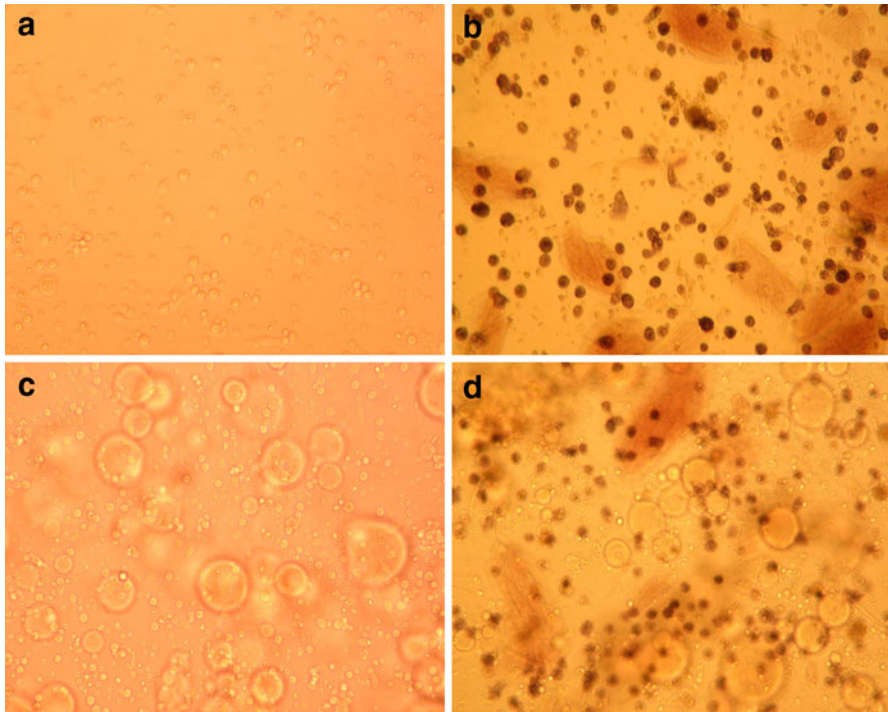


Fig. 5 Representative optical microphotographs of Wistar mouse peritoneal macrophages 20-h incubated in **a** culture medium (negative control), before addition of MTT, **b** culture medium (negative control), after addition of MTT, **c** CCPMs 2.0 % (v/v) in culture medium, before addition of MTT, and **d** CCPMs 2 % (v/v) in culture medium, after addition of MTT

Acknowledgments The authors thank to Vítor Redondo (Institute Pedro Nunes, Coimbra, Portugal) for providing the optical microscopy facility and for the particle size analysis. Authors also thank Prof. Ana Cristina Santos (Faculty of Medicine, University of Coimbra, Portugal) for conducting MTT assay.

References

1. Cascone MG, Sim B, Dowries S (1995) Blends of synthetic and natural polymers as drug delivery systems for growth hormone. *Biomaterials* 16:569–574
2. Parida UK, Nayak AK, Binhani BK, Nayak PL (2011) Synthesis and characterization of chitosan–polyvinyl alcohol blended with cloisite 30B for controlled release of the anticancer drug curcumin. *J Biomater Nanobiotechnol* 2:414–425
3. Peniche C, Argüelles-Monal W, Peniche H, Acosta N (2003) Chitosan: an attractive biocompatible polymer for microencapsulation. *Macromol Biosci* 3:511–520
4. Kamari A, Pulford ID, Hargreaves JSJ (2011) Chitosan as a potential amendment to remediate metal contaminated soil—a characterisation study. *Colloids Surf B* 82:71–80
5. Kumar M, Tripathi BP, Shahi VK (2009) Crosslinked chitosan/polyvinyl alcohol blend beads for removal and recovery of Cd(II) from wastewater. *J Hazard Mater* 172:1041–1048
6. Portes E, Gardrat C, Castellan A, Coma V (2009) Environmentally friendly films based on chitosan and tetrahydrocurcuminoid derivatives exhibiting antibacterial and antioxidative properties. *Carbohydr Polym* 76:578–584
7. Anchisi C, Meloni MC, Maccioni AM (2006) Chitosan beads loaded with essential oils in cosmetic formulations. *J Cosmet Sci* 57:205–214

8. Hassan CM, Peppas NA (2000) Structure and applications of poly(vinyl alcohol) hydrogels produced by conventional crosslinking of by freezing/thawing methods. *Adv Polym Sci* 153:37–65
9. Zheng H, Du Y, Yu J, Huang R, Zhang L (2001) Preparation and characterization of chitosan/poly(vinyl alcohol) blend fibers. *J Appl Polym Sci* 80:2558–2565
10. Sinha VR, Singla AK, Wadhawan S, Kaushik R, Kumria R, Bansal K, Dhawan S (2004) Chitosan microspheres as a potential carrier for drugs. *Int J Pharm* 274:1–33
11. Yang Q, Dou F, Liang B, Shen Q (2005) Studies of cross-linking reaction on chitosan fiber with glyoxal. *Carbohydr Polym* 59:205–210
12. Wan Ngah WS, Endud CS, Mayanar R (2002) Removal of copper (II) ions from aqueous solution onto chitosan and cross-linked chitosan beads. *React Funct Polym* 50:181–190
13. Varshosaz J, Sadrai H, Alinagari R (2004) Nasal delivery of insulin using chitosan microspheres. *J Microencapsul* 21:761–774
14. Jayakrishnan A, Jameela SR (1996) Glutaraldehyde as a fixative in bioprostheses and drug delivery matrices. *Biomaterials* 17:471–484
15. Wang T, Turhan M, Gunasekaran S (2004) Selected properties of pH-sensitive, biodegradable chitosan–poly(vinyl alcohol) hydrogel. *Polym Int* 53:911–918
16. Gunasekaran S, Wang T, Chai C (2006) Swelling of pH-sensitive chitosan–poly(vinyl alcohol) hydrogels. *J Appl Polym Sci* 102:4665–4671
17. Svang-Ariyaskul A, Huang RYM, Douglas PL, Pal R, Feng X, Chen P, Liu L (2006) Blended chitosan and polyvinyl alcohol membranes for the pervaporation dehydration of isopropanol. *J Membr Sci* 280:815–823
18. Campos E (2006) Preparação e caracterização de sistemas de libertação controlada para aplicação oftalmológica. MSc Dissertation, University of Coimbra
19. Burgess DJ, Hickey AJ (2002) Microsphere technology and applications. In: Swarbrick J, Boylan JC (eds) *Encyclopedia of pharmaceutical technology*. Marcel Dekker Inc, New York, pp 1783–1794
20. Freitas S, Merkle HP, Gander B (2005) Microencapsulation by solvent extraction/evaporation: reviewing the state of art of microspheres preparation process technology. *J Control Release* 102:313–332
21. Hamdi G, Ponchel G, Duchêne D (1998) An original method for studying in vitro the enzymatic degradation of cross-linked starch microspheres. *J Control Release* 55:193–201
22. Stertman L, Lundgren E, Sjöholm I (2006) Starch microparticles as a vaccine adjuvant: only uptake in Peyer’s patches decides the profile of the immune response. *Vaccine* 24:3661–3668
23. Longo WE, Iwata H, Lindheimer TA, Goldberg EP (1982) Preparation of hydrophilic albumin microspheres using polymeric dispersing agents. *J Pharm Sci* 71:1323–1328
24. Jameela SR, Jayakrishnan A (1995) Glutaraldehyde cross-linked chitosan microspheres as long acting biodegradable drug delivery vehicle: studies on the in vivo degradation of microspheres in rat muscle. *Biomaterials* 16:769–775
25. Genta I, Costantini M, Asti A, Conti B, Montanari L (1998) Influence of glutaraldehyde on drug release and mucoadhesive properties of chitosan microspheres. *Carbohydr Polym* 36:81–88
26. Mosmann T (1983) Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays. *J Immunol Methods* 65:55–63
27. Santos A (2002) Água trocável do pulmão: Contribuição para o desenvolvimento de uma metodologia para a sua avaliação. PhD Dissertation, University of Coimbra
28. Campos E, Cordeiro R, Santos AC, Matos C, Gil MH (2011) Design and characterization of bi-soft segmented polyurethane microparticles for biomedical application. *Colloids Surf B* 88:477–482
29. Şanlı O, Karaca İ, Işıklan N (2009) Preparation, characterization, and salicylic acid release behavior of chitosan/poly(vinyl alcohol) blend microspheres. *J Appl Polym Sci* 111:2731–2740
30. Udrea LE, Hritcu D, Popa MI, Rotariu O (2011) Preparation and characterization of polyvinyl alcohol–chitosan biocompatible magnetic microparticles. *J Magn Magn Mater* 323:7–13
31. Ramakrishna P, Mallikarjuna B, Babu AC, Sudhakar P, Rao KC, Subha MCS (2011) Interpenetrating polymer network of crosslinked blend microspheres for controlled release of acebutolol HCl. *J Appl Pharm Sci* 01:212–219
32. Arshady R (1990) Albumin microspheres and microcapsules: methodology of manufacturing techniques. *J Control Release* 14:111–131
33. Demirbas A (2005) Biodiesel production from vegetable oils via catalytic and non-catalytic supercritical methanol transesterification methods. *Prog Energy Combust Sci* 31:466–487
34. Chang C-M, Bodmeier R (1996) Organic solvent-free polymeric microspheres prepared aqueous colloidal polymer dispersions by a w/o-emulsion technique. *Int J Pharm* 130:187–194

35. Genta I, Perugini P, Conti B, Pavanetto F (1997) A multiple emulsion method to entrap a lipophilic compound into chitosan microspheres. *Int J Pharm* 152:237–246
36. Albertsson A-C, Carlfors J, Struresson C (1996) Preparation and characterization of poly(adipic anhydride) microspheres for ocular drug delivery. *J Appl Polym Sci* 62:695–705
37. Campos E, Cordeiro R, Alves P, Rasteiro MG, Gil MH (2008) Polyurethane-based microparticles: formulation and influence of processes variables on its characteristics. *J Microencapsul* 25:154–169
38. Costa-Júnior ES, Barbosa-Stancioli EF, Mansur AAP, Vasconcelos WL, Mansur HS (2009) Preparation and characterization of chitosan/poly(vinyl alcohol) chemically crosslinked blends for biomedical applications. *Carbohydr Polym* 76:472–481
39. Kim OH, Lee K, Kim K, Lee BH, Choe S (2006) Optimum conditions for preparing micron-sized PMMA beads in the dispersion polymerization using PVA. *Colloid Polym Sci* 284:909–915
40. Jayasekara R, Harding I, Bowater I, Christie GBY, Lonergan GT (2004) Preparation, surface modification and characterisation of solution cast starch PVA blend films. *Polym Test* 23:17–27
41. Jegal J, Lee K-H (1999) Nanofiltration membranes based on poly(vinyl alcohol) and ionic polymers. *J Appl Polym Sci* 72:1755–1762
42. Dekker A, Panfil C, Valdor M, Pennartz G, Richter H, Mittermayer CH, Kirkpatrick CJ (1994) Quantitative methods for in vitro cytotoxicity testing of biomaterials. *Cell Mater* 4:01–112
43. Scudiero DA, Shoemaker RH, Pauli KD, Monks A, Tierney S, Nofziger TH, Currens MJ, Seniff D, Boyd MR (1988) Evaluation of a soluble tetrazolium/formazan assay for cell growth and drug sensitivity in culture using human and other tumor cell lines. *Cancer Res* 48:4827–4833
44. Ramires PA, Milella E (2002) Biocompatibility of poly(vinyl alcohol)-hyaluronic acid and poly(vinyl alcohol)-gellan membranes crosslinked by glutaraldehyde vapors. *J Mater Sci Mater Med* 13: 119–123