

APPLICATIONS OF SAMPLE CONTROLLED THERMAL ANALYSIS (SCTA) TO KINETIC ANALYSIS AND SYNTHESIS OF MATERIALS

L.A. PÉREZ-MAQUEDA, J.M. CRIADO, P.E. SÁNCHEZ-JIMÉNEZ, M.J. DIÁNEZ

Instituto de Ciencia de Materiales de Sevilla, Centro Mixto Universidad de Sevilla-C.S.I.C., Américo Vespucio 49, 41092 Sevilla (Spain)

ABSTRACT: The advantages of the Sample Controlled Thermal Analysis (SCTA) for both the kinetic analysis of solid state reactions and the synthesis of materials are reviewed. This method implies an intelligent control of the temperature by the solid state reaction under study in such a way that the reaction rate as a function of the time fits a profile previously defined by the user. It has been shown that SCTA has important advantages for discriminating the kinetic model of solid state reactions as compared with conventional rising temperature methods. Moreover, the advantages of SCTA methods for synthesizing materials with controlled texture and structure are analyzed.

INTRODUCTION

Smart temperature methods for studying chemical reactions imply controlling the temperature in such a way that the reaction itself follows a trend predefined by the user. The most widely used smart temperature control method is the Sample Controlled Thermal Analysis (SCTA), independently developed by Rouquerol [1-2] and the Paulik brothers [3], although the last authors named the method Quasi-isothermal Quasi-isobaric Thermal Analysis as shown in the review of J. Simon [4]. This method involves controlling the temperature in such a way that the reaction rate is maintained constant all over the process. SCTA has been used by several authors for the synthesis of different materials, such as catalysts and sorbents with controlled porosity [5-23], structural ceramics [24-27] or electroceramics [28-31] and for binder burnout [32-34]. Besides it has many applications in analytical chemistry [35-38]. CRTA has been also extensively applied to the kinetic analysis of solid state reactions [39-62]. The scope of this work is to summarize the advantages of SCTA methods for performing the kinetic analysis of solid state reactions and for the synthesis of materials.

THE SCTA METHOD

The graphic representation proposed by Reading [63, 64], shown in Fig. 1, is very useful for remarking the advantages of SCTA with regards to conventional methods from the point of view of the experimental condition control. Fig. 1 represents the evolution of the temperature, mass change and partial pressure of the evolved gases as a function of the time for different experimental conditions. In general, the lower the

reaction rate, the lower is the chance of appreciable temperature or pressure gradients within the sample bed. Therefore, Constant Rate Thermal Analysis (CRTA) provides an advantage in terms of maintaining constant the product gas pressure and the reaction rate at a strictly constant value. Thus, SCTA method reduces the pressure and temperature gradients within the sample and, therefore, minimizes the influence of heat and mass transfer phenomena on the forward reaction, leading to meaningful kinetic parameters necessary for an adequate kinetic analysis. On the other hand, the isothermal and conventional rising temperature methods would lead to significant changes in the reaction rate and in the product gas pressure, which generally cannot be controlled by the user and could modify the shape of the α -T plots leading to a meaningless interpretation of the reaction mechanism. The proper control that SCTA methods exert on both the atmosphere surrounding the sample and the real temperature of the sample bed explains that it has been frequently observed that the activation energies calculated by this method, for either reversible [45, 65-78] or irreversible [79] thermal decomposition of solids, are independent of the sample size in a wide range of starting sample mass, while a similar behaviour was not observed when rising temperature experiments were concerned.

Fig. 2 illustrates, by way of example, a simple and universal SCTA device developed by us [80, 81] that could be used with any thermoanalytical instrument (TAI). It is constituted by a conventional PID temperature programmer, which has the thermocouple connected to the input socket, for setting preselected isothermal or rising temperature conditions. A second programmer is used for controlling the profile of the TAI output signal as a function of the time. The control of the reaction rate is achieved by connecting the control relay of the TAI programmer to the digital input of the temperature programmer. SCTA control is performed by selecting from the menu of the digital input that allows one to move the temperature program from a preset heating rate when the TAI control relay is closed to a preset cooling rate when the TAI control relay is open. In other words, the temperature increases if the output signal supplied by the TAI is higher than the programmed setpoint and decreases if it is lower than the setpoint. This device has been successfully attached to different analytical devices for SCTA control. Fig. 3 shows, by way of example [80], the change of weight and temperature as a function of the time obtained for the thermal decomposition of PVC under SCTA control at a previously selected constant decomposition rate rate $C = 1.2 \cdot 10^{-3} \% \cdot s^{-1}$. In this case the output corresponding to the total change of weight supplied by the electrobalance was used as input of the TAI signal programmer on the device outlined in Fig. 2. It can be observed that the plot of the reacted fraction as a function of the time fits a straight line with a slope equal to the previously selected constant decomposition rate.

ADVANTAGES OF SCTA

Discrimination of the kinetic model

The reaction rate of a solid state reaction can be represented by the following equation:

$$\frac{d\alpha}{dt} = A \exp\left(-\frac{E}{RT}\right)f(\alpha) \quad (1),$$

where α is the reacted fraction, t is the time, da/dt is the reaction rate, T is the temperature, A is the preexponential factor of Arrhenius, E is the activation energy, R is the gas constant and $f(\alpha)$ is a function representing the kinetic model.

Eq. (1) must be accomplished for whatever thermal pathway is followed for achieving a particular point of the triplet $(d\alpha/dt)$ - α - T . If the α - T (or t) plot is obtained at a constant decomposition rate ($C = da/dt$), Eq. (1) can be rearranged, after taking logarithms, in the form:

$$-\ln f(\alpha) = \ln \frac{A}{C} - \frac{E}{RT} \quad (2).$$

The plot of the left hand side of Eq. (2) as a function of $1/T$ leads to a straight line, where the slope leads to the activation energy and the intercept to the pre-exponential factor of the Arrhenius expression of the process. It was previously shown from a theoretical analysis [62] that only the $f(\alpha)$ function that really describes the kinetic model obeyed by the reaction fulfil Eqn. (2), contrarily to what occurs in rising temperature experiments[82-93]. In this latter case, a number of different kinetic models can fit simultaneously a given α - T plots, making impossible to discriminate the kinetic model from a single experiment recorded under a linear heating program. In order to illustrate this behaviour it has been shown in Fig. 4 that a unique TG curve can be calculated by assuming different kinetic models: F1, A2 and A3, while these models can be unambiguously discriminated by CRTA as shown on the right side of Fig. 4 that represents the curves calculated from Eq. 1 for the models F1, A2 and A3 by assuming the same kinetic parameters used in Fig. 4.6 and a constant reaction rate, $C = 5.10^{-6} \text{ s}^{-1}$. This analysis leads to the conclusion that SCTA method is a more reliable approach than conventional non-isothermal methods both for discriminating the real kinetic model obeyed by solid state reactions and for obtaining correct values of their activation energies.

The experimental results included in Fig. 5 for the thermal dehydrochlorination of PVC supports the above conclusion. Thus, the SCTA α - T plot obtained from Fig. 3 is compared with a conventional thermogravimetric curve (TG) obtained for the thermal decomposition of PVC under a heating rate of $3,3.10^{-2} \text{ K.s}^{-1}$. It is observed that the SCTA experiment allows discriminating the two steps evolved in the dehydrochlorination of PVC, while conventional TG cannot. Moreover, the shape of the α - T plot clearly shows that the first step of the dehydrochlorination takes place through an Avrami-Erofeev kinetic model. It has been shown [62,94] that in such a case the α - T plot starts with a rise of temperature until reaching the preset value of the reaction rate that is immediately followed by a decreasing of the temperature until reaching a given

value, α_m , of the reacted fraction (that depends on the value of the coefficient n of the Avrami-Erofeev equation), and the temperature rises again once the corresponding α_m value is attained. Thus, a glance to the shape of the SCTA curve would be enough for envisioning the kinetic model of a solid state reaction contrarily what occurs with the TG curves have always led to sigmoidal shaped α -T plot, independently of the reaction mechanism obeyed by the reaction.

Synthesis of materials with controlled texture and structure

The SCTA methods allow a precise control of the reaction rate, what implies a direct or indirect control of the partial pressure of the gases generated or consumed in the reaction and the associated heat evolution rate. This temperature control allows both minimizing the heat and mass transfer phenomena and performing a very precise control of the atmosphere surrounding the samples. These features have been exploited for developing materials with controlled porosity and structure for being used either as adsorbents or catalysts [5,9,21-23, 95-100].

The universal SCTA control device outlined in Fig. 2 has been used for controlling both the reaction rate and the partial pressure during the thermal decomposition under vacuum of precursors of catalysts and ferroelectric materials. The output signal of the pirani or penning was used as TAI input control signal at the time that the decomposition rate was monitored through a proper control of the pumping rate of the vacuum system. Thus, both the partial pressure of the gases generated in the reaction and the thermal decomposition rate were simultaneously controlled. The results obtained by using the described SCTA vacuum system for the synthesis of α -Fe₂O₃ (hematite) from the thermal decomposition under vacuum of α -FeO(OH) (goethite) samples with acicular shaped particles [19,20] are reported as way of example. Slit pore channels oriented along the c -lattice axis (the long axis of the particle) were formed at very low water vapour pressures as shown in Fig. 6. Isolated round pores were progressively formed as far as the water vapour pressure was increased at the time that its size was increasing as a function of the pressure as Fig. 6 shows. A diminution of the water vapour pressure during the thermal decomposition of goethite strongly promoted the increase of the specific surface of the hematite obtained as final product. A similar behaviour was reported for the textural properties of the γ -Fe₂O₃ (maghemite) obtained by controlling both the rate and the water vapour pressure during the thermal decomposition of the γ -FeOOH (lepidocrocite) precursor by means of the SCRT method [18]. Very recently, SCTA has been used for enhancing the long-term CO₂ capture of CaO at Ca-looping conditions. Thus it has been shown that CaO regenerability at conditions close to the Calcium-looping (CaL) process is improved by means of a relatively short-timed preheating treatment and carried out at a relatively low temperature, which is based on SCTA in an air/CO₂ atmosphere [100]

References

- 1 Ganteaume M, Rouquerol J. Etude cinétique d'une décomposition thermique par couplage de la calorimétrie et de l'analyse thermique. *J Therm Anal.* 1971; 3:413- 420
2. Rouquerol J. Méthode d'analyse thermique sous faible pression et à vitesse de décomposition constante. *Bull Soc Chim Fr.* 1964:31-32.

3. Paulik, J.; Paulik F. Quasi-isothermal thermogravimetry. *Anal Chim Acta*. 1971; 56:328-331.
4. Simon J. Novel multiple methods and results in thermal analysis. *J Thermal Anal*. 1976; 10: 451-460
5. Rouquerol J, Rouquerol F, Ganteaume M. Thermal decomposition of gibbsite under low pressure. I. Formation of boehmitic phase. *J Catal*. 1975; 36:99-110.
6. Rouquerol J, Rouquerol F, Ganteaume M. Thermal decomposition of gibbsite under low pressure. 2. Formation of microporous alumina. *J Catal*. 1979;57:222-30.
7. Paulik F, Paulik J, Naumann R, Kohnke K, Petzold D. Mechanism and kinetics of the dehydration of hydrargillites. Part I. *Thermochim Acta*. 1983; 64:1-14.
8. Dufau N, Luciani L, Rouquerol F, Llewellyn P. Use of sample controlled thermal analysis to liberate the micropores of aluminophosphate AlPO₄-11: evidence of template evaporation. *J Mater Chem*. 2001;11:1300-1304.
9. Sicard, L, Llewellyn PL, Patarin J, Kolenda F. Investigation of the mechanism of the surfactant removal from a mesoporous alumina prepared in the presence of sodium dodecyl sulfate. *Microporous Mesoporous Mater*. 2001; 44:195-201.
10. Keene MTJ, Gougeon RDM, Denoyel R, Harris RK, Rouquerol J, Llewellyn P. Calcination of the MCM-41 mesophase: mechanism of surfactant thermal degradation and evolution of the porosity. *J Mater Chem*. 1999; 9:2843-50.
11. Rouquerol F, Rouquerol J, Thevand G, Triaca M. Surf Sci. Desorption of chemisorbed species: its study by Controlled Rate Thermal Analysis. 1985; 162: 239-44.
12. Torralvo MJ, Grillet, Y, Rouquerol F, Rouquerol J. Application of CRTA to the study of microporosity by thermodesorption of preadsorbed water. *J Therm Anal*. 1994;41: 1529-34.
13. Barnes PA, Parkes GMB, Brown DR, Charsley EL. Applications of new high resolution evolved gas analysis systems for the characterisation of catalysts using rate-controlled thermal analysis. *Thermochim Acta*. 1995;269:665-76.
14. Dawson EA, Parkes GMB, Barnes PA, Chinn MJ, Norman PR. A study of the activation of carbon using sample controlled thermal analysis. *J Therm Anal Calorim*. 1999;56:267-73.
15. Charsley EL, Rooney JJ, Hill JO, Parkes GMB, Barnes PA, Dawson EA. Development and applications of a preparative scale sample controlled thermogravimetric system. *J Therm Anal Calorim*. 2003;72:1091-.
16. Fesenko EA, Barnes PA, Parkes GMB, Dawson EA, Tiernan MJ. Catalyst characterisation and preparation using sample controlled thermal techniques - high resolution studies and the determination of the energetics of surface and bulk processes. *Top Catal*. 2002;19(3-4):283-301.
17. Dawson EA, Parkes GMB, Barnes PA, Chinn MJ. An investigation of the porosity of carbons prepared by constant rate activation in air. *Carbon*. 2003;41(3):571-578.
18. Chopra GS, Real C, Alcalá MD, Perez-Maqueda LA, Subrt J, Criado JM. Factors influencing the texture and stability of maghemite obtained from the thermal decomposition of lepidocrocite. *Chem Mater*. 1999;11(4):1128-1137.
19. Perez-Maqueda LA, Criado JM, Real C, Subrt J, Bohacek J. The use of constant rate thermal analysis (CRTA) for controlling the texture of hematite obtained from the thermal decomposition of goethite. *J Mater Chem*. 1999;9:1839-1846.
20. Perez-Maqueda LA, Criado JM, Subrt J, Real C. Synthesis of acicular hematite catalysts with tailored porosity. *Catal Lett*. 1999;60(3):151-156.

21. Perez-Maqueda LA, Sanchez-Jimenez PE, Criado JM. Sample controlled temperature (SCT): A new method for the synthesis and characterization of catalysts. *Current Topics in Catalysis*. 2007;6:1-17.
22. Fesenko EA, Barnes PA, Parkes GMB. SCTA and catalysis. In: Sørensen OT, Rouquerol J, editors. *Sample controlled thermal analysis: Origin, goals, multiple form and future*: Kluwer Academic; 2003. p. 174-225.
23. Llewellyn P, Rouquerol F, Rouquerol J. SCTA and adsorbents. In: Sørensen OT, Rouquerol J, editors. *Sample controlled thermal analysis: Origin, goals, multiple form and future*. Dordrecht: Kluwer Academic; 2003. p. 135-173.
24. Alcalá MD, Criado JM, Gotor FJ, Real C. Beta-sialon obtained from carbothermal reduction of kaolinite employing sample controlled reaction temperature (SCRT). *J Mater Sci*. 2006;41:1933-1938.
25. Alcalá MD, Criado JM, Real C. Sample controlled reaction temperature (SCRT): Controlling the phase composition of silicon nitride obtained by carbothermal reduction. *Advanced Engineering Materials*. 2002;4:478-482.
26. Alcalá MD, Gotor FJ, Perez-Maqueda LA, Real C, Dianez MJ, Criado JM. Constant rate thermal analysis (CRTA) as a tool for the synthesis of materials with controlled texture and structure. *J Therm Anal Calorim*. 1999;56:1447-1452.
27. Real C, Alcalá D, Criado JM. Synthesis of silicon carbide whiskers from carbothermal reduction of silica gel by means of the Constant Rate Thermal Analysis (CRTA) method. *Solid State Ionics*. 1997;95:29-32.
28. Monnereau O, Tortet L, Llewellyn P, Rouquerol F, Vacquier G. Synthesis of Bi_2O_3 by controlled transformation rate thermal analysis: A new route for this oxide?. *Solid State Ionics*. 2003;157:163-169.
29. Criado JM, Gotor FJ, Real C, Jimenez F, Ramos S, Delcerro J. Application of the constant rate thermal-analysis technique to the microstructure control of BaTiO_3 yielded from coprecipitated oxalate. *Ferroelectrics*. 1991;115:43-8.
30. Gotor FJ, Perez-Maqueda LA, Criado JM. Synthesis of BaTiO_3 by applying the sample controlled reaction temperature (SCRT) method to the thermal decomposition of barium titanyl oxalate. *J Eur Ceram Soc*. 2003;23:505-13.
31. Perez-Maqueda LA, Dianez MJ, Gotor FJ, Sayagues MJ, Real C, Criado JM. Synthesis of needle-like BaTiO_3 particles from the thermal decomposition of a citrate precursor under sample controlled reaction temperature conditions. *J Mater Chem*. 2003;13:2234-2241.
32. Arii T, Terayama K, Fujii N. Controlled-rate thermal analysis - study of the process of super hard material debinding. *J Therm Anal*. 1996;47:1649-1661.
33. Dwivedi A, Speyer RF. Rate-controlled organic burnout of multilayer green ceramics. *Thermochim Acta*. 1994 ;247:431-8.
34. Nishimoto MY, Speyer RF, Hackenberger WS. Thermal processing of multilayer PLZT actuators. *J Mater Sci*. 2001;36:2271-6.
35. Paulik J, Paulik F. Simultaneous thermoanalytical examinations by means of derivatograph. *Wilson's, comprehensive analytical chemistry*. XII. Amsterdam: Elsevier; 1981.
36. Paulik F. *Special trends in thermal analysis*. New York: John Wiley; 1995.
37. Parkes GMB, Barnes PA, Charsley EL. New concepts in sample controlled thermal analysis: Resolution in the time and temperature domains. *Anal Chem*. 1999;71:2482-2487.

38. Sanchez-Jimenez PE, Perez-Maqueda LA, Crespo-Amoros JE, Lopez J, Perejon A, Criado JM. Quantitative characterization of multicomponent polymers by sample-controlled thermal analysis. *Anal Chem.* 2010;82:8875-80.
39. Arai T, Kishi A. The effect of humidity on thermal process of zinc acetate. *Thermochim Acta.* 2003;400:175-85.
40. Bordere S, Floreancig A, Rouquerol F, Rouquerol J. Obtaining a divided uranium oxide from the thermolysis of $\text{UO}_2(\text{NO}_3) \cdot 2.6\text{H}_2\text{O}$ - outstanding role of the residual pressure. *Solid State Ionics.* 1993;63:229-235.
41. Bordere S, Rouquerol F, Llewellyn PL, Rouquerol J. Unexpected effect of pressure on the dehydration kinetics of uranyl nitrate trihydrate: An example of a smith-topley effect. *Thermochim Acta.* 1996 ;283:1-11.
42. Criado JM, Perez-Maqueda LA, Gotor FJ, Malek J, Koga N. A unified theory for the kinetic analysis of solid state reactions under any thermal pathway. *J Therm Anal Calorim.* 2003;72:901-6.
43. Koga N, Criado JM, Tanaka H. Kinetic analysis of the thermal decomposition of synthetic malachite by crta. *J Therm Anal Calorim.* 2000;60:943-54.
44. Koga N, Criado JM, Tanaka H. A kinetic aspect of the thermal dehydration of dilithium tetraborate trihydrate. *J Therm Anal Calorim.* 2002;67:153-61.
45. Laureiro Y, Jerez A, Rouquerol F, Rouquerol J. Dehydration kinetics of wyoming montmorillonite studied by controlled transformation rate thermal analysis. *Thermochim Acta.* 1996 ;278:165-73.
46. Ortega A, Roldan MA, Real C. Carbothermal synthesis of vanadium nitride: Kinetics and mechanism. *Int J Chem Kinet.* 2006 ;38:369-75.
47. Parkes GMB, Barnes PA, Charsley EL, Reading M, Abrahams I. Real-time analysis of peak shape: A theoretical approach to sample controlled thermal analysis. *Thermochim Acta.* 2000;354:39-43.
48. Tatsuoka T, Koga N. Effect of atmospheric water vapor on the thermally induced crystallization in zirconia gel. *J Am Ceram Soc.* 2012;95:557-64.
49. Tiernan MJ, Barnes PA, Parkes GMB. Use of solid insertion probe mass spectrometry and constant rate thermal analysis in the study of materials: Determination of apparent activation energies and mechanisms of solid-state decomposition reactions. *J Phys Chem B.* 1999;103:6944-6949.
50. Tiernan MJ, Barnes PA, Parkes GMB. New approach to the investigation of mechanisms and apparent activation energies for the reduction of metal oxides using constant reaction rate temperature-programmed reduction. *J Phys Chem B.* 1999 ;103:338-45.
51. Yamada S, Tsukumo E, Koga N. Influences of evolved gases on the thermal decomposition of zinc carbonate hydroxide evaluated by controlled rate evolved gas analysis coupled with TG. *J Therm Anal Calorim.* 2009;95:489-93.
52. Criado JM, Perez-Maqueda LA. Sample controlled thermal analysis and kinetics. *J Therm Anal Calorim.* 2005;80:27-33.
53. Sanchez-Jimenez PE, Criado JM, Perez-Maqueda LA. Kissinger kinetic analysis of data obtained under different heating schedules. *J Therm Anal Calorim.* 2008;94:427-32.
54. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado JM. Combined kinetic analysis of thermal degradation of polymeric materials under any thermal pathway. *Polym Degrad Stab.* 2009;94:2079-85.
55. Sanchez-Jimenez PE, Perejon A, Criado JM, Diane MJ, Perez-Maqueda LA. Kinetic model for thermal dehydrochlorination of poly(vinyl chloride). *Polymer.* 2010;51:3998-4007.

56. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado JM. A new model for the kinetic analysis of thermal degradation of polymers driven by random scission. *Polym Degrad Stab.* 2010;95:733-739.
57. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado JM. Generalized kinetic master plots for the thermal degradation of polymers following a random scission mechanism. *J Phys Chem A.* 2010;114:7868-7876.
58. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado JM. Constant rate thermal analysis for thermal stability studies of polymers. *Polym Degrad Stab.* 2011;96:974-981.
59. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado JM. Nanoclay nucleation effect in the thermal stabilization of a polymer nanocomposite: A kinetic mechanism change. *J Phys Chem C.* 2012;116:11797-11807.
60. Criado JM, Perez-Maqueda LA. SCTA and kinetics. In: Sørensen OT, Rouquerol J, editors. *Sample controlled thermal analysis: Origin, goals, multiple form and future.* Dordrecht Kluwer Academic; 2003. p 62-101
61. Criado JM. Kinetic-analysis of thermoanalytical diagrams obtained with the quasi-isothermal heating technique. *Thermochim Acta.* 1979;28:307-312.
62. Criado JM, Ortega A, Gotor F. Correlation between the shape of controlled-rate thermal-analysis curves and the kinetics of solid-state reactions. *Thermochim Acta.* 1990;157:171-179.
63. Reading M. "Controlled Rate Thermal Analysis and Beyond" in "Thermal Analysis Techniques and applications (Charsley EL and Warrington SB, Eds.), Royal Society of Chemistry, Cambridge 1992, p. 126-155
64. Reading M. "Controlled Rate Thermal Analysis and Related Techniques" in "Handbook of Thermal Analysis and Calorimetry" (Gallagher PK, General Ed.). Vol 1: "Principles and Practice" (M.E. Brown, Ed. Vol. 1), Elsevier, Amsterdam 1998, vol. 1, p. 423-443
65. Criado JM, Rouquerol F, Rouquerol J. Thermal decomposition reactions in solids - comparison of the Constant Decomposition Rate Thermal Analysis with the conventional TG method. *Thermochim Acta.* 1980; 38:109-115
66. Criado JM. Study of the thermal decomposition of double strontium and barium carbonates using a new technique: Constant Rate Thermal Analysis (CRTA) *Mater Sci Monogr.* 1980; 6: 1096-1105
67. Criado JM. Determination of the mechanism of thermal decomposition of $MnCO_3$, $CdCO_3$ and $PbCO_3$ by using both TG and the Cyclic and constant Decomposition Rate of Thermal Analysis. *Thermal Analysis (Miller Ed.). Proc. 7th International Conference on Thermal Analysis, Wiley (London) 1982, Vol. 1, p.99-103*
68. Reading M, Dollimore D, Rouquerol J, Rouquerol F. The measurement of meaningful activation energies using thermoanalytical methods - a tentative proposal. *J Therm Anal.* 1984; 37:775-785
69. Criado JM, Ortega A, Rouquerol J, Rouquerol F. Un nuevo método de de Análisis Térmico: El Análisis Térmico a Velocidad de Reacción Controlada. I. Desarrollo histórico y consideraciones generales. *Bol Soc Espan Ceram Vidr.* 1987; 25: 407- 414
70. Ortega, A, Akahouari S, Rouquerol F, Rouquerol J. On the suitability of Controlled Transformation Rate Thermal Analysis (CRTA) for kinetic-studies .1. Determination of the activation-energy by the rate-jump method *Thermochim Acta.* 1990; 163: 25-32

71. Criado JM, Diánez MJ, Macías M, Paradas MC. Crystalline structure and thermal stability of double strontium and barium carbonates. *Thermochim Acta*. 1990; 171: 229-238
72. Criado J.M., Ortega A.. Kinetic study of thermal decomposition of dolomite by controlled transformation Rate Thermal analysis. *J Therm Anal* 1991; 37:2369-2375
73. Reading M, Dollimore D, Whittehead. The measurement of meaningful kinetic-parameters for solid-state decomposition reactions. *J Therm Anal*. 1991;37:2165-2188
74. Koga N., Criado JM and Tanaka H. Kinetic Analysis of Inorganic Solid State Reactions by Controlled Rate Thermal Analysis. *NetsuSokutei*. 2000; 27:128-140 (in japoneese)
75. Málek J, Sesták J, Rouquerol F, Rouquerol J, Criado JM, Ortega A. Possibilities of two non-isothermal procedures (Temperature or Rate Controlled) for kinetical studies. *J Therm Anal*. 1992;38:71-87
76. Ortega A, Akahouari S, Rouquerol F, Rouquerol J. On the suitability of Controlled Transformation Rate Thermal Analysis (CRTA) for kinetic-studies .2. comparison with conventional tg for the thermolysis of dolomite with different particle sizes *Thermochim Acta*. 1994; 235:197-204
77. Koga N, Criado JM. The influence of mass transfer phenomena on the kinetic analysis for the thermal decomposition of calcium carbonate by Constant Rate Thermal Analysis (CRTA) under vacuum. *Int J Chem Kinet*. 1998; 30:737-744
78. Hatakeyamka T, Zhenay L, *Handbook of Thermal Analysis*, Wiley, Chichester, 1998
79. Finary A, Salageanu I, Segal J. Non-isothermal kinetic study of the heterogeneous thermal decomposition of a Mannich compound. *J Therm Anal Calorim*. 2000; 61:239-242
80. Diánez MJ, Pérez-Maqueda LA, Criado JM. Direct use of the mass output of a thermobalance for controlling the reaction rate of solid-state reactions. *Rev Sci Instrum*. 2004; 75:2620-2624
81. Criado JM, Pérez-Maqueda LA, Diánez MJ, Sánchez-Jiménez PE. Development of a universal Constant Rate Thermal Analysis system for being used with any thermoanalytical instrument. *J Therm Anal Calorim*. 2007;87:297-300
82. Criado JM, Morales J. Defects of thermogravimetric analysis for discerning between 1st order reactions and those taking place through Avrami-Erofeevs mechanism. *Thermochim Acta*. 1976;16:382-387
83. Criado JM, Morales J. On the evaluation of kinetic-parameters from thermogravimetric curves. *Thermochim Acta*. 1980;41:125-127
84. Criado JM, Dollimore D, Heal G R. A critical-study of the suitability of the Freeman and Carroll method for the kinetic-analysis of reactions of thermal-decomposition of solids. *Thermochim Acta*. 1982;54: 159-165
85. Flynn JH. Thermal-analysis kinetics-problems, pitfalls and how to deal with them. *J Therm Anal*. 1988;34: 367-381
86. Agrawal RK. Analysis of irreversible complex chemical-reactions and some observations on their overall activation-energy. *Thermochim Acta*. 1988;128: 185-208

87. Vyazovkin SV, Lesnikovich AI. On the methods of solving the inverse problem of solid-phase reaction-kinetics .1. methods based on discrimination. *J Therm Anal.* 1989;35: 2169-2188
88. Criado JM, Ortega A, Gotor F. Correlation between the shape of Controlled Rate Thermal Analysis curves and the kinetics of solid state reactions. *Thermochim Acta.* 1990;157:171-179
89. Koga N, Sesták J, Málek J. Distortion of the Arrhenius parameters by the Inappropriate kinetic-model function. *Thermochim Acta.* 188 (1991) 333-336
90. Málek J. The kinetic analysis of nonisothermal data. *Thermochim Acta.* 1992;200:257-269
91. Vyazovkin S, Wight CA. Isothermal and non-isothermal kinetics of thermally stimulated reactions of solids. *Int Rev Phys Chem.* 1998;17: 407-433
92. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A, Criado J M. Limitations of model-fitting methods for kinetic analysis: Polystyrene thermal degradation. *Resources Conservation and Recycling* 2013; 74: 75-81.
93. Sanchez-Jimenez PE, Perez-Maqueda LA, Perejon A., Criado JM. Clarifications regarding the use of model-fitting methods of kinetic analysis for determining the activation energy from a single non-isothermal curve. *Chemistry Central Journal* 2013; 7.
94. Tiernan M J, Barnes PA, Parkes GMB. Reduction of iron oxide catalysts: The investigation of kinetic parameters using rate perturbation and linear heating thermoanalytical techniques. *J Phys Chem B.* 2001; 105: 220-228
95. Rouquerol J, Ganteaume M. Thermolysis under vacuum: essential influence of residual pressure on thermoanalytical curves and reaction-products. *J Therm Anal.* 1977; 11: 201-210
96. Stacey MH. Evolution of porosity during conversion of eta-alumina to a novel porous alpha-alumina fiber. *Stud Surf Sci Catal.* 1991;62:615-624
97. Stacey MH. Kinetics of decomposition of gibbsite and boehmite and the characterization of the porous products. *Langmuir.* 1987;3: 681-686
98. Salles F, Douillard J.M, Denoyel R, Bildstein O, Jullien M, Beurroies I, Van Damme H. Hydration sequence of swelling clays: Evolutions of specific surface area and hydration energy. *J. Colloid Interf. Sci.* 2009;333: 510-522
99. Belgacem K, Llewellyn P, N Nahdi K, Trabelsi-Ayadi M. Thermal behaviour study of the talc. *Optoelectron Adv Mat Rapid Comm.* 2008;2: 332-336
100. Valverde J. M., Sanchez-Jimenez P. E., Perejon A., and Perez-Maqueda L. A., Constant rate thermal analysis for enhancing the long-term CO₂ capture of CaO at Ca-looping conditions, *Applied Energy.* 2013; 108: 108-120

Figure 1.

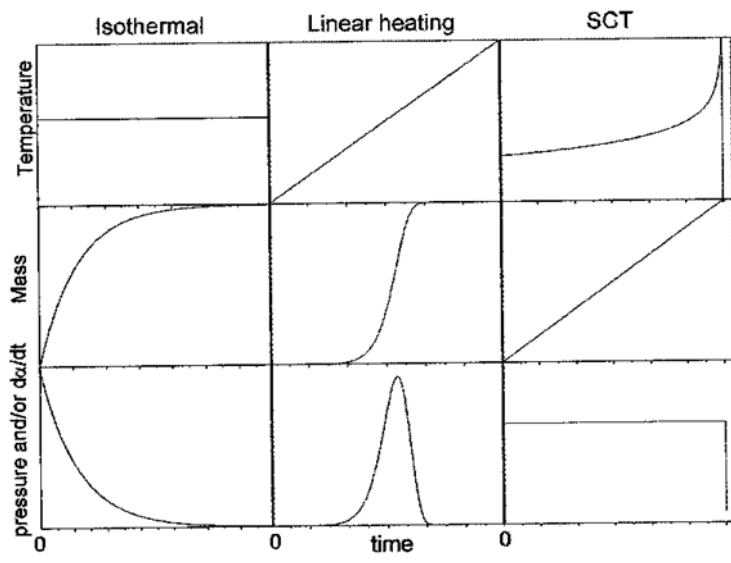


Figure 2.

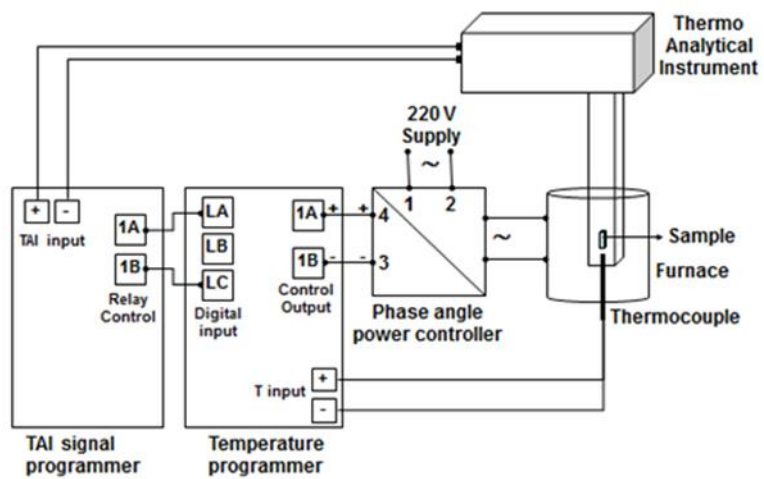


Figure 3.

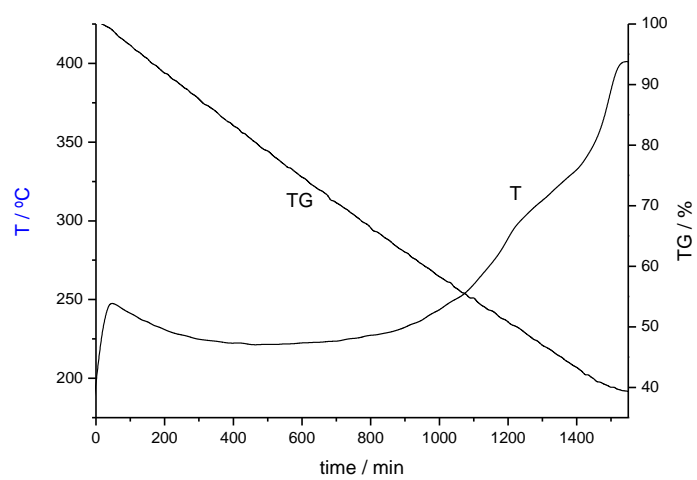


Figure 4.

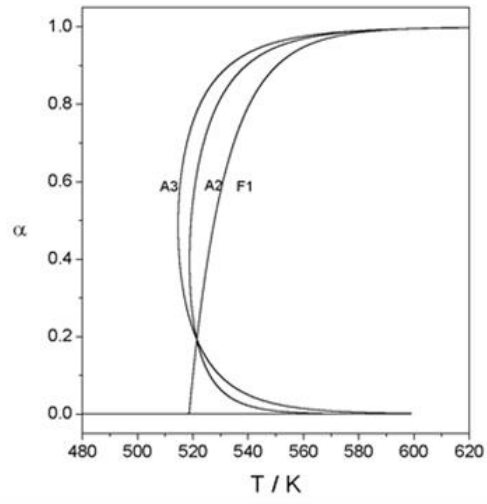
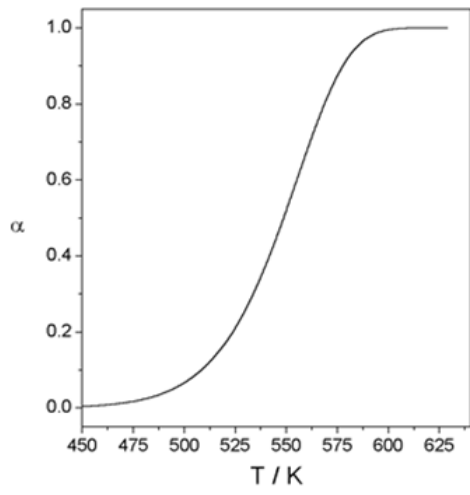


Figure 5.

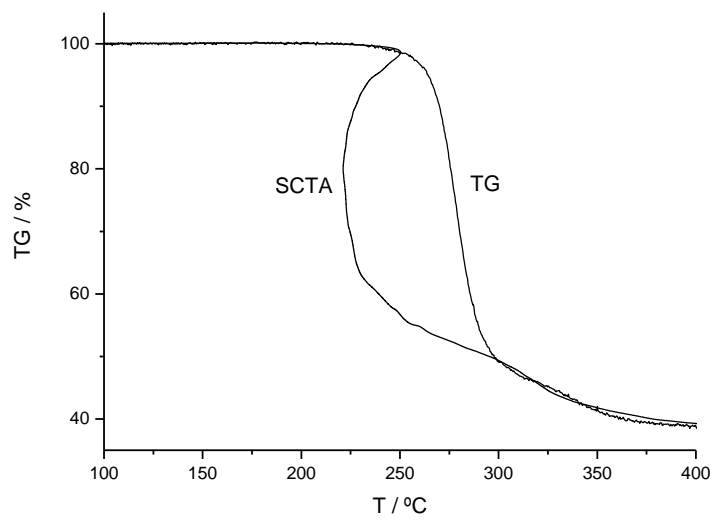


Figure 6.



S: 44 m2 g-1



S=102 m2 g-1

Captions of figures.

Figure 1. Trend of temperature, mass and pressure (and/or $d\alpha/dt$) during a thermal decomposition reaction for different methods.

Figure 2. Scheme of the universal SCTA device to be used for controlling the reaction temperature of any thermoanalytical device.

Figure 3. SCTA plot obtained for the dehydrochlorination of PVC at a constant decomposition rate $C = 5.10^{-4} \text{ s}^{-1}$ ($5.0.10^{-4} \text{ mg.s}^{-1}$)

Figure 4. A single TG curve at a heating rate of $1 \text{ }^\circ\text{C}/\text{min}$ for three different models: F1: $E_a = 172.3 \text{ kJ mol}^{-1}$ and $A = 2.30 \cdot 10^{13} \text{ s}^{-1}$; A2: $E_a = 118.1 \text{ kJ mol}^{-1}$ and $A = 1.24 \cdot 10^8 \text{ s}^{-1}$; A3: $E_a = 100.0 \text{ kJ mol}^{-1}$ and $A = 1.66 \cdot 10^6 \text{ s}^{-1}$ (left). Discrimination between the three kinetic models (F1, A2, A3) of Fig. 4.6 by means of the SCTA method (right).

Figure 5. A comparison of the α -T plot obtained from the SCTA experimental data included in Figure 3 with a TG recorded for the dehydrochlorination of PVC at a heating rate $\beta = 3,3.10^{-2} \text{ K.s}^{-1}$

Figure 6. TEM micrographs corresponding to hematite sample prepared by thermal decomposition of goethite under SCTA conditions: $P = 5.5 \cdot 10^{-5} \text{ mbar}$ and $C = 1,6.10^{-5} \text{ s}^{-1}$ (left) and $P = 8.3 \text{ mbar}$ and $C = 1,2.10^{-5} \text{ s}^{-1}$.