

Muhammad Saeed<sup>1,\*</sup>, Majid Muneer<sup>1</sup>, Muhammad Kaleem Khan Khosa<sup>1</sup>, Nadia Akram<sup>1</sup>, Sheeba Khalid<sup>1</sup>, Muhammad Adeel<sup>1</sup>, Asif Nisar<sup>1</sup> and Sonia Sherazi<sup>2</sup>

# *Azadirachta indica* leaves extract assisted green synthesis of Ag-TiO<sub>2</sub> for degradation of Methylene blue and Rhodamine B dyes in aqueous medium

<https://doi.org/10.1515/gps-2019-0036>

Received December 18, 2018; accepted May 04, 2019.

**Abstract:** Aqueous pollution due to textile industry is an important issue. Photocatalysis is one of the methods used for eradication of dyes from textile industrial effluents. In this study, the synthesis, characterization and evaluation of photo catalytic activity of Ag-TiO<sub>2</sub> is reported. TiO<sub>2</sub> catalysts with 2, 4, 6 and 8% loading of Ag were prepared by green methods using *Azadirachta indica* leaves extract as reducing agent with titanium dioxide and silver nitrate as precursor materials. Prepared catalyst was characterized by advanced techniques and was used as catalyst for degradation of Methylene blue and Rhodamine B dyes. Deposition of Ag greatly enhanced the catalytic efficiency of TiO<sub>2</sub> towards degradation of dyes. Irradiation of catalyst excites electrons from conduction band of catalyst to valence band yielding an electron-hole pair. This electron-hole pair undergoes secondary reactions and produce OH<sup>•</sup> radicals. These active radicals take part in degradation of dyes. More than 90% dyes were degraded in 120 min. Photo catalytic degradation of Methylene blue and Rhodamine B followed Eley-Rideal mechanism which states that dye react in fluid phase with adsorbed oxygen.

**Keywords:** TiO<sub>2</sub>; Ag-TiO<sub>2</sub>; Methylene blue; Rhodamine B; photo degradation; Eley-Rideal mechanism

## 1 Introduction

Dyes and pigments are predominantly used in different industries and a reasonable amount of these compounds go to environment through industrial effluents. As these compounds are toxic and carcinogenic in nature, therefore, their impact on the environment is a major concern. Furthermore, these dyes impart color to aqueous body blocking the penetration of sunlight and dissolution of oxygen [1-3]. Thus, a number of physical and chemical techniques such as filtration, precipitation, coagulation, adsorption and oxidation have been pursued for elimination of these toxic compounds. Photocatalytic oxidation, which is one of the viable and developing methods utilized for destruction of toxic pollutants and dyes, has increased much research enthusiasm for late years. The photocatalytic oxidation technique has a number of preferences over traditional techniques, viz less energy requirement, no requirement for sludge disposal and complete degradation of pollutants [4-9]. TiO<sub>2</sub> has been broadly utilized as catalyst for photocatalytic oxidation of a wide scope of pollutants because of its low cost and high stability. However, the photocatalytic activity of TiO<sub>2</sub> has been restrained due two reasons; firstly, the rate of electron-hole pair recombination formed by irradiation is relatively high and secondly, it has wide band gap (about 3.2 eV) [10-14]. These restrictions can be overcome by modification in electronic band structure of TiO<sub>2</sub>. This modification has been accomplished by addition of a substance like Ag that decreases the rate of recombination of electron-hole pair [15,16]. Although silver (Ag) is highly effective, however, it cannot be employed as photocatalyst because the recovery of Ag nanoparticles from reaction mixture is difficult. Immobilization of Ag nanoparticles on other substances like TiO<sub>2</sub> is technique to produce an efficient photocatalyst for aqueous phase degradation of pollutants. Immobilization of Ag nanoparticles on TiO<sub>2</sub> prevents the electron-hole pair recombination, thus

\* Corresponding author: Muhammad Saeed, Department of Chemistry, Government College University Faisalabad, Faisalabad Pakistan, e-mail: msaeed@gcuf.edu.pk; Tel.: +92 346 9010903

Majid Muneer, Muhammad Kaleem Khan Khosa, Nadia Akram, Sheeba Khalid, Muhammad Adeel and Asif Nisar, Department of Chemistry, Government College University Faisalabad, Faisalabad Pakistan

Sonia Sherazi, Department of Chemistry, University of Gujrat, Gujrat Pakistan

enhancing the photocatalytic activity of TiO<sub>2</sub> [17-19]. Different strategies have been utilized for fabrication of Ag-TiO<sub>2</sub>, however, green synthesis has received high consideration in which extract of plants is utilized as stabilizing and reducing agent. A number of plants have been used for green synthesis of nanoparticles [20-27].

In present study, Ag-TiO<sub>2</sub> is fabricated utilizing the aqueous extract of *Azadirachta indica* L, locally called as neem. The prepared Ag-TiO<sub>2</sub> was employed as photocatalyst for degradation of Methylene blue and Rhodamine B dyes.

## 2 Experimental

### 2.1 Materials

TiO<sub>2</sub> (Merck), AgNO<sub>3</sub> (Alfa Aesar), Methylene blue (Merck), Rhodamine B (commercial grade), *Azadirachta indica* leaves (Botanical garden, University of Agriculture Faisalabad, Pakistan) and distilled water were used in this study.

### 2.2 Synthesis of Ag-TiO<sub>2</sub>

First, the dried leaves (20 g) of *Azadirachta indica* were boiled in distilled water for 2 h. Then, after cooling the mixture, the aqueous extract was separated by filtration and was used for synthesis of Ag-TiO<sub>2</sub>. For synthesis of Ag-TiO<sub>2</sub>, a 50 mL plant extract was added dropwise to a mixture containing a known amount of AgNO<sub>3</sub> and TiO<sub>2</sub> under continuous stirring. Afterward, the synthesized Ag-TiO<sub>2</sub> was filtered, washed and dried at 80°C for 12 h. Ag-TiO<sub>2</sub> catalysts with 2, 4, 6 and 8% Ag loading were prepared. The leaves of referred plant contain a variety of phytochemicals including flavonoids and phenolic components which are considered as reducing agent for reduction of Ag<sup>1+</sup> to Ag [28-32].

### 2.3 Photocatalytic degradation experiment

The photocatalytic activity of Ag-TiO<sub>2</sub> was demonstrated with two different solutions of Methylene blue ( $\lambda_{\text{max}} = 660 \text{ nm}$ ) and Rhodamine B ( $\lambda_{\text{max}} = 554 \text{ nm}$ ) in a batch reactor. A 50 mL dye solution was taken in a reactor vessel. Then, a pre-weighed amount of photocatalyst was suspended in dye solution for 30 min in dark. Finally, the reaction mixture was irradiated with UV

light. Reaction samples were withdrawn from the reactor after regular time intervals and were analysed using UV-visible spectrophotometer (U-2800, HITACHI, Japan). Equation 1 was used to calculate the degradation efficiency.

$$\text{Degradation (\%)} = \frac{A_0 - A}{A_0} \times 100 \quad (1)$$

where  $A_0$  is the initial and  $A$  is the final absorbance at  $\lambda_{\text{max}}$  of each dye. Effect of Ag loading, temperature and concentration on degradation of dyes was also investigated.

### 2.4 Reaction kinetics

The kinetics of present degradation study can be described by pseudo first order kinetics model in terms of Eley-Rideal (E-R) mechanism. This mechanism is described by Eq. 2 which transforms to Eq. 3 and Eq. 4 by considering constant pressure of oxygen and integration respectively.

$$\text{Rate} = -\frac{dC}{dt} = k_r O_2 (ads) C \quad (2)$$

$$-\frac{dC}{dt} = kC \quad (3)$$

$$\ln \frac{C}{C_t} = kt \quad (4)$$

## 3 Results and discussion

### 3.1 Characterization

Phase investigation and crystallinity of synthesized Ag-TiO<sub>2</sub> was performed by XRD measurement with JDX-3532 Japan X-Ray Diffractometer and the results are given in Figure 1. The XRD pattern of TiO<sub>2</sub> is dominated with sharp and well-resolved peaks at 25°, 36°, 48° and 55° which correspond to (1-0-1), (0-0-4), (2-0-0) and (1-0-5) diffraction planes, respectively, of anatase structural phase (JCPDS# 21-1272). In spectrum of Ag-TiO<sub>2</sub>, additional peaks at 2θ 38° and 44° can be observed corresponding to face centered cubic unit cell of Ag [33-37].

Figure 2 shows the scanning electron micrographs of TiO<sub>2</sub> and Ag-TiO<sub>2</sub> recorded with JSM-5910 Japan Microscope. Micrographs show that particles of TiO<sub>2</sub> are spherical, uniform and homogeneous in morphology. Furthermore, it can also be noted that the particles are well dispersed and non-agglomerated. The Ag particles deposited on TiO<sub>2</sub> are also well dispersed. Uniformity and smoothness in shape and homogeneous nature of

catalyst particles play an important role in reproducible catalytic activities.

The particle size distribution of prepared catalysts measured with Analysette 22 Compact, Germany is given in Figure 3. The particle sizes ranges from 0.001 to 20  $\mu\text{m}$ , however, 85% of the particles have particles size equal to or less than 2  $\mu\text{m}$ . The surface area measured with Quanta Chrome, Nova 2200e instrument was found as 58 m<sup>2</sup>g<sup>-1</sup> and 51 m<sup>2</sup>g<sup>-1</sup> for TiO<sub>2</sub> and Ag-TiO<sub>2</sub> respectively. The decrease in surface area by deposition of Ag on TiO<sub>2</sub> might be due to blockage of micropores by Ag nanoparticles.

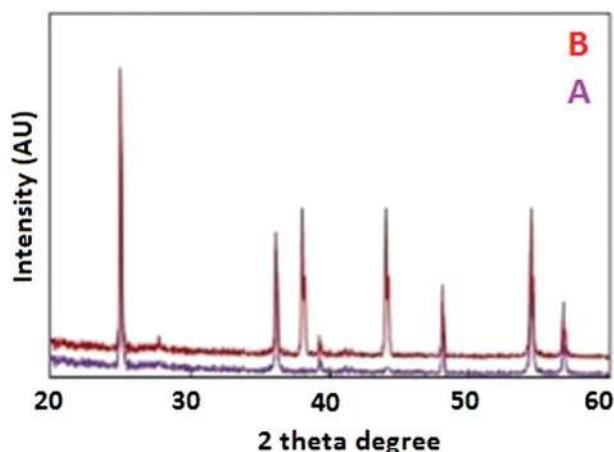


Figure 1: XRD pattern of TiO<sub>2</sub> (A) and Ag-TiO<sub>2</sub> (B).

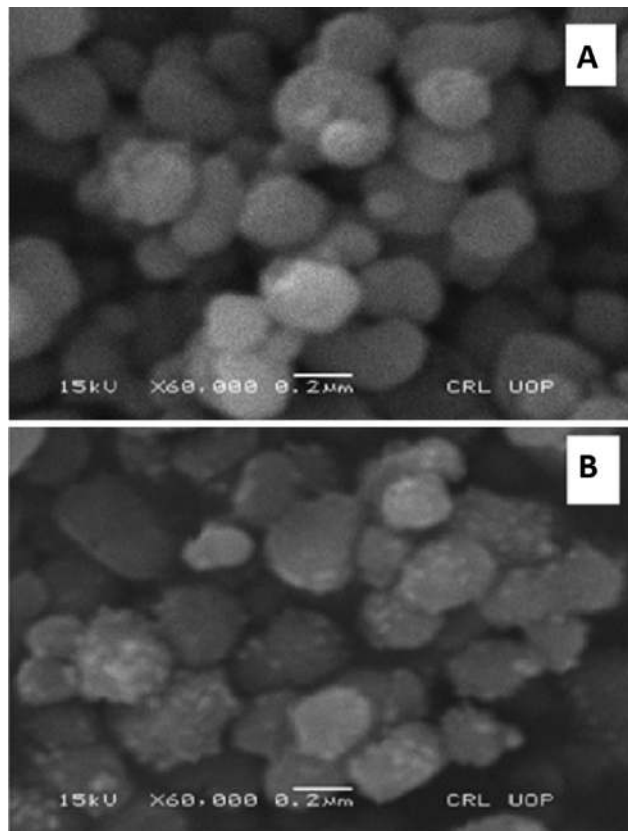


Figure 2: Scanning electron micrographs: (a) TiO<sub>2</sub>, (b) Ag-TiO<sub>2</sub>.

### 3.2 Photocatalytic activity

Separate degradation experiments were performed with solutions of Methylene blue and Rhodamine B dye for evaluation of catalytic activity of biosynthesized Ag-TiO<sub>2</sub>. This investigation was performed by suspending a 0.1 g 6% Ag-TiO<sub>2</sub> catalyst in 50 mL of 100 mg/L dye solution at 40°C and the resulting data in terms of  $C_t/C_0$  ( $C_0$  and  $C_t$  represents initial concentration of dye and concentration of dye at different time interval respectively) is given in Figure 4. This data is derived from measurement of absorbance at different time interval at  $\lambda_{\text{max}}$  of each dye. The data presented in Figure 4 indicates that fabrication of Ag enhanced the photocatalytic activity of TiO<sub>2</sub> for degradation of dyes. Similarly, the effect of Ag loading on photocatalytic activity of TiO<sub>2</sub> was also investigated. For this purpose, degradation of Methylene blue dye was studied with 2, 4, 6 and 8% loading of Ag under identical experimental



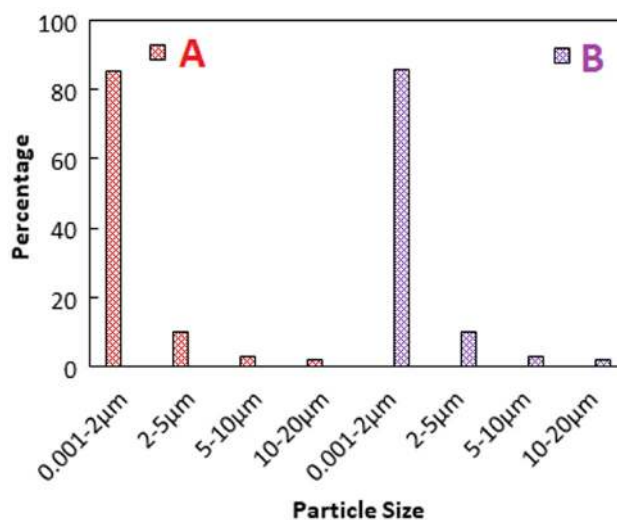



Figure 3: Particle size distribution of the catalysts particles: (A) TiO<sub>2</sub>, (B) Ag-TiO<sub>2</sub>.

conditions. It was found that 65, 84, 97 and 78% of dye degraded after 120 min of reaction with 2, 4, 6 and 8% Ag-TiO<sub>2</sub> as catalyst respectively. Higher concentration of Ag block the active center of TiO<sub>2</sub>, therefore, the photocatalytic activity decreased at higher Ag loading. Hence, 6% loading of Ag was considered as optimum loading [38,39]. It is proposed that heterogeneous photocatalytic degradation reaction takes place through the creation of positive hole ( $h_{VB}^+$ ) in valence band and photo excited electron ( $e_{CB}^-$ ) in the conduction band of catalyst by irradiation. These positive holes and photo excited electrons produce OH<sup>•</sup> radicals by a series of secondary reactions. These OH<sup>•</sup> radicals are highly reactive species which attack on dye molecules and produce degradation products. The positive hole reacts with water molecule and produces OH<sup>•</sup> radical and H<sup>+</sup>. Similarly, superoxide anion is formed by reaction of electron with oxygen which produces OH<sup>•</sup> radical by a


series of further reaction. The proposed mechanism was confirmed by performing the degradation experiments with Methylene blue dye in absence of irradiation. The results showed that degradation efficiency [30] in absence of light was much lower in comparison to degradation efficiency under irradiation (97%). In another experiment, the degradation efficiency was observed as 48% in the presence of isopropyl alcohol, OH<sup>•</sup> radical scavenger [40]. These results support the proposed mechanism. The proposed mechanism can be summarized as follows:



The deposition of Ag reinforces the catalytic activities of TiO<sub>2</sub> because the Ag nanoparticles prevent the recombination of positive holes and photo excited electrons [36,37,41,42].

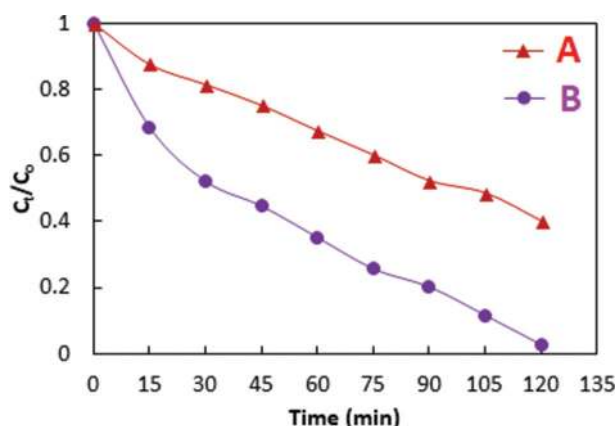


**Figure 4a:** Photo degradation of Methylene blue dye catalyzed by TiO<sub>2</sub> (A) and Ag-TiO<sub>2</sub> (B) in aqueous medium.

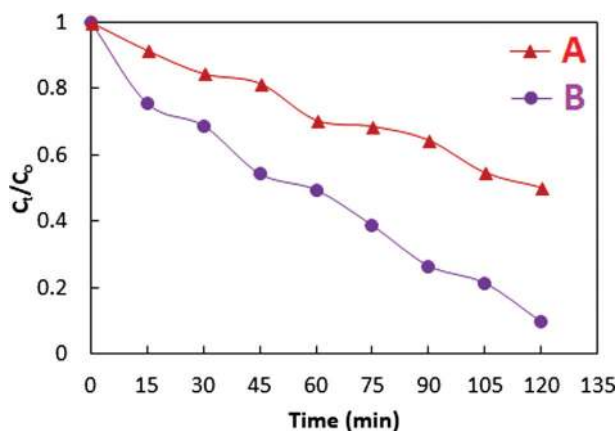

**Figure 4b:** Photo degradation of Rhodamine B dye catalyzed by TiO<sub>2</sub> (A) and Ag-TiO<sub>2</sub> (B) in aqueous medium.

### 3.3 Effect of temperature

Generally, temperature affects the rate of reactions, therefore, we explored the temperature dependence of present catalytic system. For this purpose, separate catalytic experiments were performed with 50 mL of 100 mg/L dye solution over 0.1 g of 6% Ag-TiO<sub>2</sub> at 30, 40 and 50°C. The results are given in Figure 5. It can be noted that temperature does not affect significantly the rate of reaction in present study. It is due the fact that photochemical reactions are generally less temperature dependent [4,5]. The experimental data at different temperatures was analysed according to pseudo first order kinetics equation (Eq. 4) and results are given in Figure 6. The slop of straight lines gives the rate constants which are given in Table 1. The activation energy determined

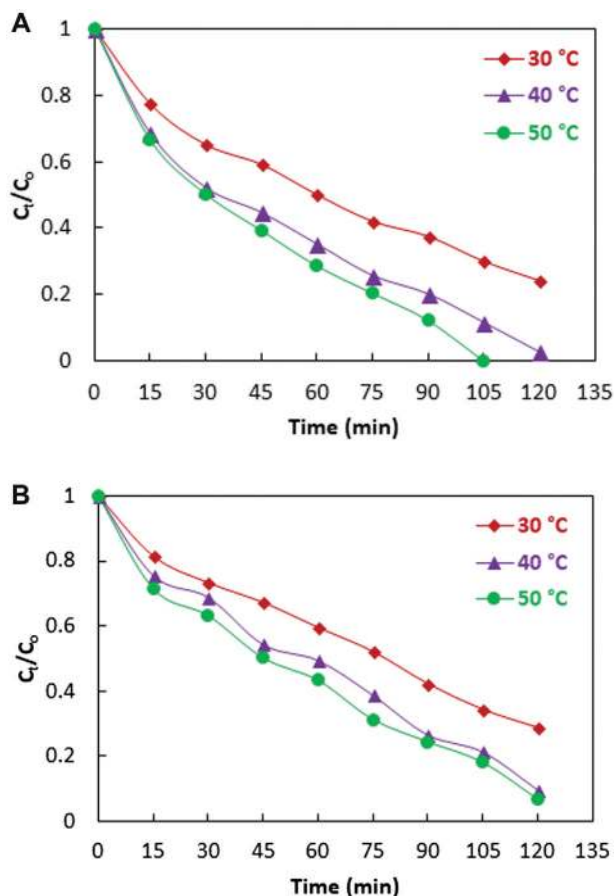


**Figure 5:** Ag-TiO<sub>2</sub> catalyzed photo degradation of (a) Methylene blue dye and (b) Rhodamine B dye, both at various temperatures.

by application of Arrhenius equation to rate constants at various temperature was found to be 27.1 and 20.4 kJ/mol for photo degradation of Methylene blue and Rhodamine B dye respectively.

### 3.4 Effect of initial concentration of dye

To investigate the effect of initial concentration of dye on rate of reaction, separate experiments were performed with 100, 200 and 300 mg/L as initial concentration of dyes. Photocatalytic degradation experiments for Methylene blue and Rhodamine B dye were performed at 40°C with 6% Ag-TiO<sub>2</sub> catalyst. It was found that 97, 79 and 60% of Methylene blue dye degraded with 100, 200 and 300 mg/L as initial concentration after 120 min of reaction respectively. Similarly, 90, 74 and 58% Rhodamine B dye degraded after 120 min of reaction with 100, 200 and 300 mg/L as initial concentration respectively. The experimental data with various initial concentration of dyes was analysed according to first order kinetic

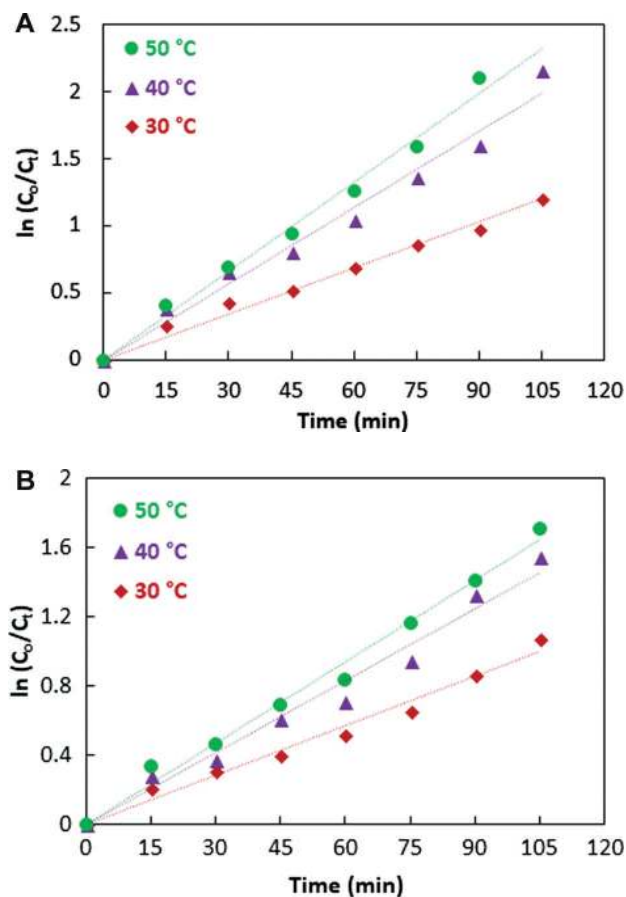

**Figure 6:** Kinetics of Ag-TiO<sub>2</sub> catalyzed photo degradation of (a) Methylene blue dye and (b) Rhodamine B dye, both at various temperatures.

**Table 1:** Rate constants of Ag-TiO<sub>2</sub> catalyzed photo degradation of Methylene blue and Rhodamine B dye at various temperatures.

T (°C)	Methylene blue		Rhodamine B	
	k (per min)	R <sup>2</sup>	k (per min)	R <sup>2</sup>
30	0.0141	0.984	0.0095	0.0981
40	0.0189	0.979	0.0139	0.976
50	0.0221	0.991	0.0157	0.991

equation (Eq. 4) and the results are given in Figure 7. The rate constants determined from the slopes of straight lines in Figure 7 are given in Table 2. The data listed in Table 2 shows that rate constants decreases with increase in initial concentration of dye.

It can be noted that increase in concentration causes a decrease in degradation efficiency, which is due to two reasons. First, the concentrated solution becomes more intense in colour which results in hindrance to penetration of radiations to the catalyst surface. Secondly, as other experimental conditions are same, so the ratio of number



of OH<sup>•</sup> radicals to number of molecules of dye decreases with increase in concentration, hence, the rate of reaction decreases with increase in initial concentration of dye [4,5,36,37,43,44].

### 3.5 Effect of pH


pH of reaction mixture is also an experimental parameter that affects the photo degradation efficiency of dyes. The

surface charge of titania changes with variation of solution pH and changes the catalytic activity of TiO<sub>2</sub> particles. The surface of TiO<sub>2</sub> becomes positive and negative in acidic and alkaline condition respectively. As both Methylene blue and Rhodamine B dyes are cationic dyes therefore, the alkaline condition favors the adsorption of these dyes on TiO<sub>2</sub> surface. Furthermore, the OH<sup>•</sup> radicals are easier to be generated in alkaline solution due to oxidation of OH ions, thus, the degradation efficiency increases with pH [2,45-50]. Therefore, both Methylene blue and Rhodamine B dyes have shown to degrade more at pH 10. Other researchers have also reported similar trends [36,37,51,52].

## 4 Conclusions

Ag-TiO<sub>2</sub> was successfully fabricated by environmentally friendly and low cost green method using *Azadirachta indica* leaves extract as reducing agent and titanium dioxide and silver nitrate as precursor materials. The photocatalytic activities of prepared particles were evaluated by degrading Methylene blue and Rhodamine B dyes under UV irradiation. The 6% Ag-TiO<sub>2</sub> exhibited the best catalytic activity for degradation of Methylene blue and Rhodamine B dyes. More than 90% dyes were degraded in 120 min. It was found that there was no loss in catalytic efficiency of prepared Ag-TiO<sub>2</sub> catalyst after recycling it for two times. Photocatalytic degradation of Methylene blue and Rhodamine B followed Eley-Rideal mechanism which states that dye react in fluid phase with adsorbed oxygen.

**Acknowledgment:** Project No. 65-CHM-5 of GCUF-RSP is appreciated.

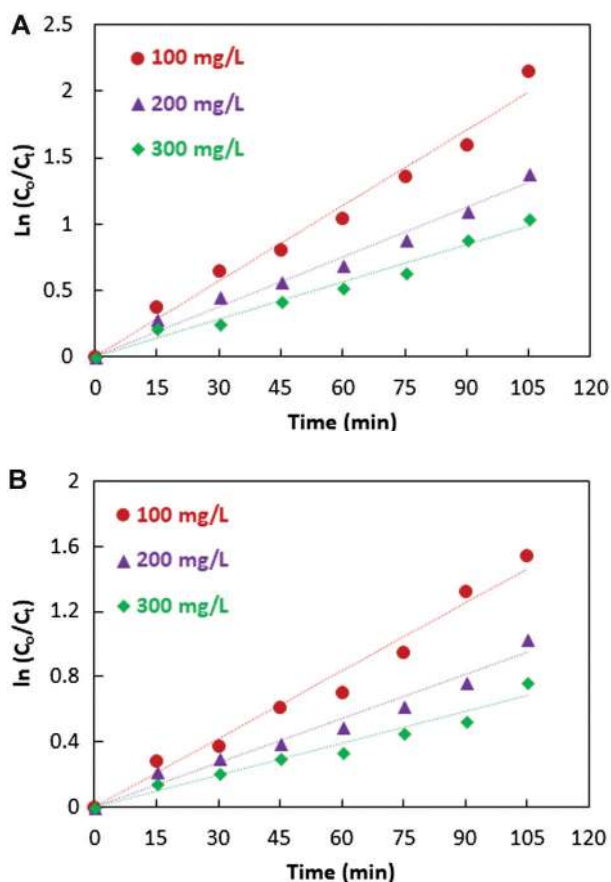

**Figure 7:** Kinetics of Ag-TiO<sub>2</sub> catalyzed photo degradation of (a) Methylene blue dye and (b) Rhodamine B dye, both with various initial concentrations.

**Table 2:** Rate constants of Ag-TiO<sub>2</sub> catalyzed photo degradation of Methylene blue and Rhodamine B dye with various initial concentrations of dyes.

Conc. (mg/L)	Methylene blue		Rhodamine B	
	k (per min)	R <sup>2</sup>	k (per min)	R <sup>2</sup>
100	0.0189	0.979	0.0139	0.976
200	0.0125	0.979	0.0091	0.969
300	0.0095	0.981	0.0068	0.959

## References

- [1] Muthirulan P., Devi C.N., Sundaram M.M., Synchronous role of coupled adsorption and photocatalytic degradation on CAC-TiO<sub>2</sub> composite generating excellent mineralization of alizarin cyanine green dye in aqueous solution. *Arab. J. Chem.*, 2017, 10, S1477-S1483.
- [2] Rauf M.A., Meetani M.A., Hisaindee S., An overview on the photocatalytic degradation of azo dyes in the presence of TiO<sub>2</sub> doped with selective transition metals. *Desalination*, 2011, 276, 13-27.
- [3] Sood S., Kumar S., Umar A., Kaur A., Mehta S.K., Kansal S.K., TiO<sub>2</sub> quantum dots for the photocatalytic degradation of indigo carmine dye. *J. Alloy. Compd.*, 2015, 650, 193-198.

- [4] Gupta V.K., Jain R., Agarwal S., Nayak A., Shrivastava M., Photodegradation of hazardous dye quinoline yellow catalyzed by TiO<sub>2</sub>. J. Colloid Interf. Sci., 2012, 366, 135-140.
- [5] Gupta V.K., Jain R.J., Mittal A., Saleh T.A., Nayak A., Agarwal S., et al., Photo-catalytic degradation of toxic dye amaranth on TiO<sub>2</sub>/UV in aqueous suspensions. Mater. Sci. Eng., 2012, 332, 12-17.
- [6] Ata S., Shaheen I., Ayne Q., Ghafoor S., Sultan M., Majid F., et al., Graphene and silver decorated ZnO composite synthesis, characterization and photocatalytic activity evaluation. Diam. Relat. Mater., 2018, 90, 26-31.
- [7] Arshad M., Qayyum A., Abbas G., Haider R., Iqbal M., Nazir A., Influence of different solvents on portrayal and photocatalytic activity of tin-doped zinc oxide nanoparticles. J. Mol. Liq., 2018, 260, 272-278.
- [8] Arshad M., Qayyum A., Abbas G., Soomro G.A., Nazir A., Munir B., et al., Zn-doped SiO<sub>2</sub> nanoparticles preparation and characterization under the effect of various solvents: Antibacterial, antifungal and photocatalytic performance evaluation. J. Photoch. Photobio. B, 2018, 185, 176-183.
- [9] Arshad M., Abbas M., Haque S.E., Farrukh M.A., Ali A., Rizvi H., et al., Synthesis and characterization of SiO<sub>2</sub> doped Fe<sub>2</sub>O<sub>3</sub> nanoparticles: Photocatalytic and antimicrobial activity evaluation. J. Mol. Struct., 2019, 1180, 244-250.
- [10] Silva C.G., Faria J.L., Photochemical and photocatalytic degradation of an azo dye in aqueous solution by UV irradiation. J. Photoch. Photobio. A, 2003, 155, 133-143.
- [11] Wu Y., Zhou Y., Liu Y., Wang Y., Yang L., Li C., Photocatalytic performances and characterizations of sea urchin-like N, Ce codoped TiO<sub>2</sub> photocatalyst. Mater. Res. Innov., 2017, 21, 33-39.
- [12] Nada A.A., Tantawy H.R., Elsayed M.A., Bechelany M., Elmowafy M.E., Elaboration of nano titania-magnetic reduced graphene oxide for degradation of tartrazine dye in aqueous solution. Solid State Sci., 2018, 78, 116-125.
- [13] Ghasemi S., Hashemian S., Alamolhoda A., Gocheva I., Setayesh S.R., Plasmon enhanced photocatalytic activity of Au@ TiO<sub>2</sub>-graphene nanocomposite under visible light for degradation of pollutants. Mater. Res. Bull., 2017, 87, 40-47.
- [14] El-Maghrabi H.H., Barhoum A., Nada A.A., Moustafa Y.M., Seliman S.M., Youssef A.M., et al., Synthesis of mesoporous core-shell CdS@TiO<sub>2</sub> (0D and 1D) photocatalysts for solar-driven hydrogen fuel production. J. Photochem. Photobiol. Chem., 2018, 351, 261-270.
- [15] Nasr M., Balme S., Eid C., Habchi R., Miele P., Bechelany M., Enhanced visible-light photocatalytic performance of electrospun rGO/TiO<sub>2</sub> composite nanofibers. J. Phys. Chem. C, 2016, 121, 261-269.
- [16] Bhanvase B., Shende T., Sonawane S., A review on graphene-TiO<sub>2</sub> and doped graphene-TiO<sub>2</sub> nanocomposite photocatalyst for water and wastewater treatment. Environ. Technol. Rev., 2017, 6, 1-14.
- [17] Ziyu L., Zhigang J., Wenwen L., Jianhong L., Shan J., Shengbiao L., et al., Synthesis of Ag/AgCl nanoparticles immobilized on CoFe<sub>2</sub>O<sub>4</sub> fibers and their photocatalytic degradation for methylene orange. Rare Metal Mater. Eng., 2017, 46, 3669-3674.
- [18] Li W., Ma Z., Bai G., Hu J., Guo X., Dai B., et al., Dopamine-assisted one-step fabrication of Ag@AgCl nanophotocatalyst with tunable morphology, composition and improved photocatalytic performance. Appl. Catal. B-Environ., 2015, 174, 43-48.
- [19] Lu L., Li J., Yu J., Song P., Ng D.H., A hierarchically porous MgFe<sub>2</sub>O<sub>4</sub>/γ-Fe<sub>2</sub>O<sub>3</sub> magnetic microspheres for efficient removals of dye and pharmaceutical from water. Chem. Eng. J., 2016, 283, 524-534.
- [20] Kamran U., Bhatti H.N., Iqbal M., Jamil S., Zahid M., Biogenic synthesis, characterization and investigation of photocatalytic and antimicrobial activity of manganese nanoparticles synthesized from *Cinnamomum verum* bark extract. J. Mol. Struct., 2019, 1179, 532-539.
- [21] Bibi I., Kamal S., Ahmad A., Iqbal M., Nouren S., Jilani K., et al., Nickel nanoparticle synthesis using *Camellia Sinensis* as reducing and capping agent: Growth mechanism and photocatalytic activity evaluation. Int. J. Bio. Macromol., 2017, 103, 783-790.
- [22] Bibi I., Nazar N., Iqbal M., Kamal S., Nawaz H., Nouren S., et al., Green and eco-friendly synthesis of cobalt-oxide nanoparticle: Characterization and photo-catalytic activity. Adv. Powder Technol., 2017, 28, 2035-2043.
- [23] Nazar N., Bibi I., Kamal S., Iqbal M., Nouren S., Jilani K., et al., Cu nanoparticles synthesis using biological molecule of *P. granatum* seeds extract as reducing and capping agent: Growth mechanism and photo-catalytic activity. Int. J. Bio. Macromol., 2018, 106, 1203-1210.
- [24] Alzohairy M.A., Therapeutics role of *Azadirachta indica* (Neem) and their active constituents in diseases prevention and treatment. Evid. Based Compl. Alter. Med., 2016, 7382506.
- [25] Fan X., Lin P., Lu X., Zi J., A new spiro-type limonoid from *Azadirachta indica* A. Juss. Tetrahedron Lett., 2019, 60, 1158-1160.
- [26] Rajendran K., Muthuramalingam R., Ayyadurai S., Green synthesis of Ag-Mo/CuO nanoparticles using *Azadirachta indica* leaf extracts to study its solar photocatalytic and antimicrobial activities. Mat. Sci. Semicon. Proc., 2019, 91, 230-238.
- [27] Babatunde D.E., Otusemade G.O., Efeovbokhan V.E., Ojewumi M.E., Bolade O.P., Owolaye T.F., Chemical composition of steam and solvent crude oil extracts from *Azadirachta indica* leaves. Chem. Data Collec., 2019, 20, 100208.
- [28] Hossain M.A., Al-Toubi W.A.S., Al-Riyami Q.A., Al-Sabahi J.N., Identification and characterization of chemical compounds in different crude extracts from leaves of *Omani neem*. J. Taibah Uni. Sci., 2013, 7, 181-188.

- [29] Dash S.P., Dixit S., Sahoo S., Phytochemical and biochemical characterizations from leaf extracts from *Azadirachta indica*: An important medicinal plant. *Anal. Biochem.*, 2017, 6, 1000323.
- [30] Ayodhya D., Veerabhadram G., One-pot green synthesis, characterization, photocatalytic, sensing and antimicrobial studies of *Calotropis gigantea* leaf extract capped CdS NPs. *Mater. Sci. Eng. B*, 2017, 225, 33-44.
- [31] Ahluwalia V., Elumalai S., Kumar V., Kumar S., Sangwan R.S., Nano silver particle synthesis using *Swertia paniculata* herbal extract and its antimicrobial activity. *Microb. Pathogenesis*, 2018, 114, 402-408.
- [32] Bordbar M., Negahdar N., Nasrollahzadeh M., *Melissa officinalis* L. leaf extract assisted green synthesis of CuO/ZnO nanocomposite for the reduction of 4-nitrophenol and Rhodamine B. *Sep. Purif. Technol.*, 2018, 191, 295-300.
- [33] Deshmane V.G., Owen S.L., Abrokwhah R.Y., Kuila D., Mesoporous nanocrystalline TiO<sub>2</sub> supported metal (Cu, Co, Ni, Pd, Zn, and Sn) catalysts: Effect of metal-support interactions on steam reforming of methanol. *J. Mol. Catal. A-Chem.*, 2015, 408, 202-213.
- [34] Atarod M., Nasrollahzadeh M., Sajadi S.M., *Euphorbia heterophylla* leaf extract mediated green synthesis of Ag/TiO<sub>2</sub> nanocomposite and investigation of its excellent catalytic activity for reduction of variety of dyes in water. *J. Colloid Interf. Sci.*, 2016, 462, 272-279.
- [35] Xu M., Wang Y., Geng J., Jing D., Photodecomposition of NO<sub>x</sub> on Ag/TiO<sub>2</sub> composite catalysts in a gas phase reactor. *Chem. Eng. J.*, 2017, 307, 181-188.
- [36] Saeed M., Ahmad A., Boddula R., Din I., Haq A., Azhar A., Ag@M<sub>n</sub>xO<sub>y</sub>: An effective catalyst for photo-degradation of rhodamine B dye. *Environ. Chem. Lett.*, 2018, 16, 287-294.
- [37] Saeed M., Muneer M., Mumtaz N., Siddique M., Akran N., Humayun M., Ag-Co<sub>3</sub>O<sub>4</sub>: Synthesis, characterization and evaluation of its photo-catalytic activity towards degradation of rhodamine B dye in aqueous medium. *Chin. J. Chem. Eng.*, 2018, 26, 1264-1269.
- [38] Chen G., Si X., Yu J., Bai H., Zhang X., Doping nano-Co<sub>3</sub>O<sub>4</sub> surface with bigger nanosized Ag and its photocatalytic properties for visible light photo degradation of organic dyes. *Appl. Surf. Sci.*, 2015, 330, 191-199.
- [39] Jermwongratanchai T., Jacobs G., Ma W.P., Shafer W.D., Gnanamani M.K., Gao P., et al., Fischer-Tropsch synthesis: comparisons between Pt and Ag promoted Co/Al<sub>2</sub>O<sub>3</sub> catalysts for reducibility, local atomic structure, catalytic activity, and oxidation-reduction (OR) cycles. *Appl. Catal. A-Gen.*, 2013, 464, 165-180.
- [40] Yue B., Zhou Y., Xu J., Wu Z., Zhang X., Zou Y., et al., Photocatalytic degradation of aqueous 4-chlorophenol by silica-immobilized polyoxometalates. *Environ. Sci. Technol.*, 2002, 36, 1325-1329.
- [41] Vidyasagar D., Ghugal S.G., Kulkarni A., Mishra P., Shende A.G., Umare J.S.S., et al., Silver/Silver(II) oxide (Ag/AgO) loaded graphitic carbon nitride microspheres: An effective visible light active photocatalyst for degradation of acidic dyes and bacterial inactivation. *Appl. Catal. B-Environ.*, 2018, 221, 339-348.
- [42] Vartooni A.R., Nasrollahzadeh M., Niasari M.S., Atarod M., Photocatalytic degradation of azo dyes by titanium dioxide supported silver nanoparticles prepared by a green method using *Carpobrotus acinaciformis* extract. *J. Alloy. Compd.*, 2016, 689, 15-20.
- [43] Davis R.J., Gainer J.L., Neal G., Wenwu I., Photocatalytic decolourisation of wastewater dyes. *Water Environ. Res.*, 1994, 66, 50-53.
- [44] Pare B., Jonnalagadda S.B., Tomar H., Singh P., Bhagwat V.W., ZnO assisted photocatalytic degradation of acridine orange in aqueous solution using visible irradiation. *Desalination*, 2008, 232, 80-90.
- [45] Konstantinou I.K., Albanis T.A., TiO<sub>2</sub>-assisted photocatalytic degradation of azo dyes in aqueous solution: kinetic and mechanistic investigations: a review. *Appl. Catal. B-Environ.*, 2004, 49, 1-14.
- [46] Lachheb H., Puzenat E., Houas A., Ksibi M., Elaloui E., Guillard C., et al., Photocatalytic degradation of various types of dyes (Alizarin S, Crocein Orange G, Methyl Red, Congo Red, Methylene Blue) in water by UV-irradiated titania. *Appl. Catal. B-Environ.*, 2002, 39, 75-90.
- [47] Baran W., Makowski A., Wardas W., The effect of UV radiation absorption of cationic and anionic dye solutions on their photocatalytic degradation in the presence TiO<sub>2</sub>. *Dyes Pigments*, 2008, 76, 226-230.
- [48] Augugliaro V, Baiocchi C, Prevot A.B., López E.G., Loddo V., Malato S., et al., Azo-dyes photocatalytic degradation in aqueous suspension of TiO<sub>2</sub> under solar irradiation. *Chemosphere*, 2002, 49, 1223-1230.
- [49] Soutsas K., Karayannis V., Poullos I., Riga A., Ntampegiotis K., Spiliotis X., et al., Decolorization and degradation of reactive azo dyes via heterogeneous photocatalytic processes. *Desalination*, 2010, 250, 345-350.
- [50] Behnajady M.A., Modirshahla N., Shokri M., Photodestruction of Acid Orange 7 (AO7) in aqueous solutions by UV/H<sub>2</sub>O<sub>2</sub>: influence of operational parameters. *Chemosphere*, 2004, 55, 129-134.
- [51] Zielinska B., Grzechulska J., Grzmil B., Morawski A.W., Photocatalytic degradation of Reactive Black 5: a comparison between TiO<sub>2</sub>-Tytanpol A11 and TiO<sub>2</sub>-Degussa P25 photocatalysts. *Appl. Catal. B-Environ.*, 2001, 35, L1-L7.
- [52] Guillard C., Lachheb H., Houas A., Ksibi M., Elaloui E., Herrmann J.M., Influence of chemical structure of dyes, of pH and of inorganic salts on their photocatalytic degradation by TiO<sub>2</sub> comparison of the efficiency of powder and supported TiO<sub>2</sub>. *J. Photoch. Photobio. A*, 2003, 158, 27-36.