

2008

Bond of high strength concrete with high strength reinforcing steel

Muhammad N. S Hadi
University of Wollongong, mhadi@uow.edu.au

Follow this and additional works at: <https://ro.uow.edu.au/engpapers>



Part of the [Engineering Commons](#)

<https://ro.uow.edu.au/engpapers/3663>

Recommended Citation

Hadi, Muhammad N. S: Bond of high strength concrete with high strength reinforcing steel 2008, 143-147.
<https://ro.uow.edu.au/engpapers/3663>

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library: research-pubs@uow.edu.au

Bond of High Strength Concrete with High Strength Reinforcing Steel

Muhammad N.S. Hadi*

Faculty of Engineering, University of Wollongong, Wollongong 2522, Australia

Abstract: This paper presents a study about the bond of high strength concrete with high strength steel. Fourteen pull out tests were carried out to determine the bond. The concrete strength was about 70 MPa and the steel was a 500 MPa grade. Bar diameters used were 12, 16, 20, 25, 28, 32 and 36 mm. In order to investigate the effect of cover, each test was done twice, once in a 240 mm diameter concrete cylinder and the second in a 300 mm diameter cylinder. Based on the test results a new equation representing the bond is proposed.

Key Words: Reinforced concrete, Bond, High strength concrete, High strength steel.

RESEARCH SIGNIFICANCE

High strength concrete is being more widely used in the last few years. More recently, new 500 MPa reinforcing steel has been introduced. Most design guides are limited to concrete up to 50 MPa or so compressive strength and reinforcing steel of 400 MPa tensile strength. This paper is a step in understanding the behaviour of one aspect of high strength concrete reinforced with high strength steel.

INTRODUCTION

In many countries, high strength concrete has become popular in recent years. High strength concrete is undergoing widespread use in civil engineering and construction processes today. The strength of concrete up to 130 MPa has been used popularly for overseas projects while concrete up to 100 MPa has been used in some Australian projects. The benefits of increased strength, smaller dimensions and lower volumes would see its immediate application into design. In the last few years, a draft standard incorporating the use of high strength 500 MPa steel to the construction industry was introduced. The use of high strength steel provides smaller cross sections and a solution to congestion problems. The benefit of the increase in steel strength, includes providing stronger structural members and decreasing the dead load of members. The scope of the Australian Standards for Concrete Structures, AS 3600 [1] is limited to concrete with strength less than 50 MPa and reinforcing steel of 400 MPa strength. Hence, there is a need to investigate many aspects of the behaviour and interaction of high strength concrete and high strength steel and propose design rules and limitations for their use. This paper is a step in this direction.

In order to investigate the bond strength of high strength steel bars with high strength concrete, pullout tests were conducted. These tests were conducted on 14 specimens with concrete compressive strength of about 70 MPa while the tensile steel was greater than 500 MPa.

BEHAVIOUR OF BOND

The transfer of axial force from a reinforcing bar to the surrounding concrete results in the development of tangential stress components along the contact surface. The stress acting parallel to the bar along the interface is called bond stress [2]. For reinforced concrete to function effectively as a composite material it is necessary for the reinforcing steel to be bonded to the surrounding concrete. Bond ensures that there is little or no slip of the steel relative to the concrete and the means by which stress is transferred across the steel-concrete [3].

Bond resistance is made up of chemical adhesion, friction and mechanical interlock between the bar and surrounding concrete. In the plain bars, only the first two of these components contribute to the bond strength. In the deformed bars, the surface protrusions or ribs interlocking with and bearing against the concrete key formed between the ribs contribute more positively to bond strength, and is the major reason for their superior bond effectiveness [2].

Fig. (1) illustrates the equilibrium conditions for portion of a reinforcing bar of length dx . The bond stress u can be expressed as the change in the stress in the reinforcement over the length dx as follows [4]:

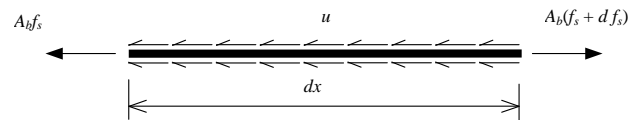


Fig. (1). Bond stress acting on a reinforcing bar.

$$u(\pi d_b dx) = A_b (f_s + d f_s) - A_b f_s \quad (1)$$

and hence

$$u = \frac{A_b d f_s}{\pi d_b dx} = \frac{d_b d f_s}{4 dx} \quad (2)$$

where A_b is the area of bar, d_b is the bar diameter, and f_s is the stress in the bar.

For uniform bond, the bond stress can be expressed as:

$$u = \frac{P_{\max}}{\pi d_b L_d} \quad (3)$$

*Address correspondence to this author at the Faculty of Engineering, University of Wollongong, Wollongong 2522, Australia; Tel: +61 2 4221 4762; Fax: +61 2 4221 3238; E-mail: mhadi@uow.edu.au

where P_{max} = maximum pullout load, d_b = diameter of the bar and L_d is the embedded bar length.

Several researchers have attempted to formulate equations that represent the bond between the reinforcing bars and the concrete. Below is a brief description of a few:

Orangun *et al.* [5] proposed the following formula:

$$u = 0.083045 \sqrt{f'_c} \left[1.2 + 3 \frac{c}{d_b} + 50 \frac{d_b}{L_d} \right] \quad (4)$$

where c = minimum concrete cover, mm and f'_c is the concrete compressive strength, MPa.

Darwin *et al.* [6] proposed a modified expression (in SI) for bond strength as follows:

$$u = 0.083045 \sqrt{f'_c} \left[\left(1.06 + 2.12 \frac{c}{d_b} \right) \left(0.92 + 0.08 \frac{C_{max}^*}{C_{min}} \right) + 75 \frac{d_b}{L_d} \right] \quad (5)$$

where $C = \min(C_x, C_y, C_s/2)$ and, $C_{max}^* = \max \left[\min(C_x, \frac{C_s}{2}), C_y \right]$ in which C_x is the side cover, C_y is the bottom cover and C_s is the spacing between the bars.

Australian Standard 3600 [1] recommends the following equation:

$$u = 0.265 \sqrt{f'_c} \left(\frac{c}{d_b} + 0.5 \right) \quad (6)$$

Esfahani and Rangan [7] proposed the following formula for high strength concrete with compressive equal to or greater than 50 MPa:

$$u = 8.6 \frac{C/d_b + 0.5}{C/d_b + 5.5} f_{ct} \quad (7)$$

where C is the minimum cover and f_{ct} is the tensile strength of concrete taken as $0.55 \sqrt{f'_c}$, in MPa.

PULLOUT SPECIMEN FABRICATION

In order to test the viability of the above formulas and their applicability for high strength concrete and high strength steel, fourteen pullout test specimens were produced to determine the bond between high strength concrete and high strength steel bar. All of the pullout specimens were made on the same day at the University of Wollongong laboratory. The high strength concrete used in construction was provided by industry. All the steel bars were 500 grade steel with nominal diameters of 12, 16, 20, 25, 28, 32, 36 mm. For each bar size two concrete sizes (240 and 300 mm diameter) were conducted. Fig. (2) shows details of the test specimens.

Before conducting the pull-out tests, all reinforcing bars were tested for their tensile strength. Bars with the diameters 12, 16, 20, 25, and 28 mm were tested at the University of Wollongong and those with 32 and 36 mm diameter were tested at the University of New South Wales. One strain gauge was placed on each size of the bar surface to measure

the strain value during the tensile test. The change in length in millimeters was recorded at test completion. The experimental results are shown in Table 1. As the results of tensile test show that the bars were able to produce high value of strength in every specimens, except in the case of 32 mm bars where the bar failed suddenly during the test.

The average compressive strength of the concrete used in the pull out tests is 70.9 MPa

All the pullout specimens were constructed by using moulds made of PVC pipes (Fig. 3). Two sizes of the PVC pipes were used, which were 240 × 300 mm (denoted as A specimens) and 300 × 300 mm (denoted as B specimens) cylinders. The PVC pipes were cut into seven specimens for each size by the use of a cutting machine. The fourteen pipes were cleaned and the cut surface was smoothed by using a

file on the surface. All fourteen pipes were placed on a special wooden board, which was 650 mm wide by 2400 mm deep by using four brackets for each specimen. Screws were used to fix all the pipes on the board after the pipes were

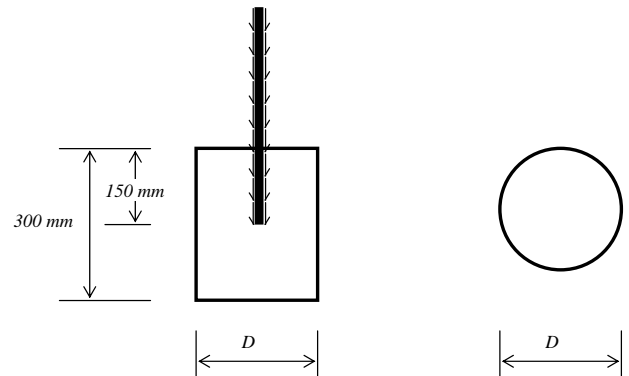


Fig. (2). Details of test specimens ($D = 240$ mm in group A specimens, = 300 mm in Group B specimens).

arranged parallel to each other on the board. Two square iron bars were prepared for holding the reinforcing bars by the use of brackets (Fig. 4). Before pouring the concrete into the pullout test moulds, the moulds were oiled around the moulds surface and at the bottom of the moulds. The concrete was poured into the PVC moulds in three layers. Each layer of the poured concrete was vibrated thoroughly with the penetrating vibrator placed vertically into the specimen and slowly removed. A 25.4 mm diameter-penetration vibrator was used for compacting the concrete. After the poured concrete was compacted properly, two square bars were placed on the short steel columns for holding the reinforcing bars vertically above the concrete specimens. One bar was placed into the fresh concrete specimen and embedded for 150 mm depth in the concrete. The reinforcing bars were approximately 600 mm length. Before using the bars, the external (free) end of each bar was threaded by the use of lathe for placing a nut. This nut would resist the loading during the pullout test.

Table 1. Results of Tensile Strength of the Bars

Bar Nom. Dia. mm	Ave. Bar Core Dia.mm	Yield Load kN	Ultimate Load kN	Yield Stress MPa
12	11.0	58.7	68.72	519.0
16	15.7	106.3	124.10	522.0
20	19.4	174.0	202.20	553.8
25	24.5	256.0	297.00	521.5
28	27.5	331.0	393.50	537.55
32	31.5	365.0	450.60	453.8
36	35.3	540.0	648.20	530.5

The pullout test specimens were cured by covering with wet Hessian bags, and kept moist by replenishing the water every day for approximately ten days. The PVC moulds were taken out after ten days and the specimens were kept moist by covering with plastic until 28 days. The cylinders, which were cast to determine the compressive strength were taken at the same day and cured in the water tank for 28 days.



Fig. (3). Moulds used in the experimental programme.



Fig. (4). Casting the specimens.

TESTING

The pullout test specimens were loaded by the hollow hydraulic machine, which has maximum loading 30 tons (300 kN). The hollow hydraulic machine was installed with Enerpac hydraulic hand-pump machine. The source of loading equipment and the load cell connected with strain indicator were used for the pullout test in 12A, 12B, 16A, 16B,

20A, 20B, 25A and 25B specimens. In the other specimens, which were 28A, 28B, 32A, 32B, 36A and 36B, the Enerpac RCH-603 was used for loading due to the bar size of these specimens which were unable to be fitted with the hollow hydraulic machine. The maximum load of Enerpac RCH-603 is 60 tons (600 kN). The pullout test set up is presented in Figs. 5 and 6. A dial gauge was used to measure the slip of the bar from the concrete. The dial gauge was fixed onto the load cell and the displacement was measured of the top off the loading equipment.



Fig. (5). Testing the specimens.

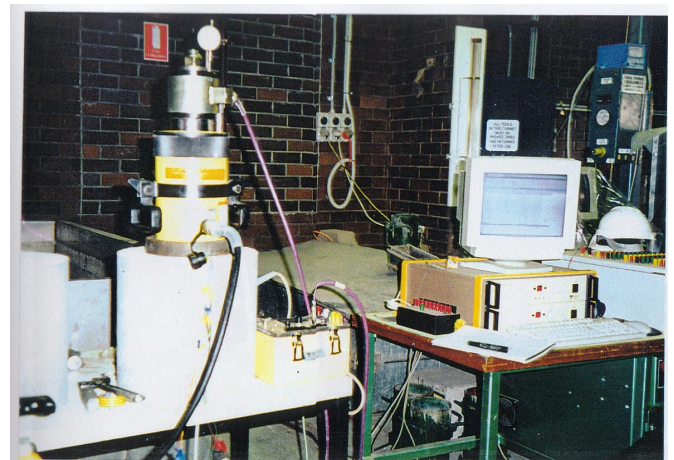


Fig. (6). Test set up.

RESULTS

The fourteen pullout specimens were divided into two groups according to the concrete cover of the specimen, the

first group, denoted as A, had about 120 mm (cylinder diameter 240 mm) concrete cover and the second group, denoted as B, had about 150 mm cover (cylinder diameter 300 mm) with seven specimens for each group. The high strength bar diameters were 12, 16, 20, 25, 28, 32 and 36 mm for each group. The embedded length of the bar was 150 mm from the top side of the concrete specimen. The test results and details are presented in Table 2. The bond stress for the pullout test was obtained by Equation 3. Also the equations of Orangun *et al.* [5], Darwin *et al.* [6], the Australian Standard 3600 [1] and Esfahani and Rangan [7] were used to calculate the bond strength. All these bond results are presented in Table 2.

The pullout test specimens failed by the following three modes of failures, pullout failure (P), splitting failure of the tested specimen (S) and steel rupture failure (CS). The pullout failure mode occurred when the concrete cover provided adequate confinement, thus preventing a splitting failure of the test specimen. The bond strength was mainly controlled by the capacity of the concrete specimen. The pullout failure was observed only in 300 mm diameter specimen with a 12 mm bar and was characterized by cracks on the top loaded face only. Splitting failure mode was the predominant type of failure of the tested specimen. It was characterised by splitting of the concrete specimen in a brittle mode of failure. Both transverse and longitudinal cracks were observed at failure.

The results of the pullout test show that the maximum bond stress value occurred in 16B and 20B specimens. The minimum bond stress value occurred in specimen 36A, which used the biggest reinforcing bar for the experiments.

The bond strength increased with the smaller bar sizes and the bigger concrete cover specimens.

Based on the measured bond strength for all the specimens and in order to take into account the higher strength of both the concrete and the reinforcing steel, a new formula is proposed. The formula is similar to the formula of Orangun *et al.* [5], which is shown in Equation 4. Statistical analysis is used to best fit the data. Based on this analysis, the following formula is proposed:

$$u = 0.083045\sqrt{f'_c} \left[22.8 - 0.208 \frac{c}{d_b} - 38.212 \frac{d_b}{L_d} \right] \quad (8)$$

Application of the new proposed formula to the test results of this study is presented in Table 2. Next the measured bond strengths together with the calculated ones based on the formulas of Orangun *et al.* [5], Darwin *et al.* [6], the Australian Standard 3600 [1] and Esfahani and Rangan [7] as well as the proposed formula are compared. These comparisons are presented for the 240 mm specimens in Fig. (7) and those for the 300 mm specimens in Fig. (8).

CONCLUSIONS

Based on the test results of fourteen pullout specimens, it can be stated that the pullout specimen with the smaller bar size has greater bond strength than the specimen with the larger diameter bar and the pullout test results also indicated that the bond strength and the initial stiffness increased as the amount of concrete surrounding the reinforcing bar increased. The maximum bond stress value occurred in specimens 16B and 20B whereas the minimum bond stress value was in specimen 36A.

Table 2. Summary of the Pullout Test Results

Spec.	Bar Core Dia. mm	Cylinder dia./len. mm/mm	Failure Mode*	P _{max} kN	Measured Bond Stress MPa	Calculated Bond Strength MPa				
						Orangun <i>et al.</i> [5]	Darwin <i>et al.</i> [6]	AS3600 [1]	Esfahani and Rangan [7]	Proposed Formula
12A	11	240/300	CS	50	9.6	25.2	20.0	24.3	27.3	12.5
12B	11.1	300/300	P	60	11.5	30.7	23.9	30.2	24.1	12.1
16A	15.7	240/300	S	90	12.2	19.5	16.8	17.1	22.0	12.1
16B	15.7	300/300	CS	100	13.5	23.5	19.7	21.3	19.7	11.8
20A	19.5	240/300	S	110	12.0	17.2	15.9	13.7	18.6	11.6
20B	19.1	300/300	S	120	13.3	20.7	18.3	17.5	17.3	11.5
25A	24.5	240/300	S	115	10.0	15.8	15.8	10.9	16.1	10.9
25B	24.6	300/300	S	150	12.9	18.3	17.6	13.6	29.1	10.7
28A	27.4	240/300	S	120	9.3	15.4	16.1	9.8	26.1	10.5
28B	27.5	300/300	S	155	12.0	17.6	17.7	12.2	24.3	10.3
32A	31.3	240/300	S	130	8.8	15.1	16.6	8.6	21.9	9.9
32B	31.5	300/300	S	150	10.1	17.1	18.1	10.6	20.8	9.7
36A	35.3	240/300	S	115	6.9	15.1	17.4	7.6	19.4	9.2

* CS = steel rupture failure, P = pullout failure, S = splitting failure.

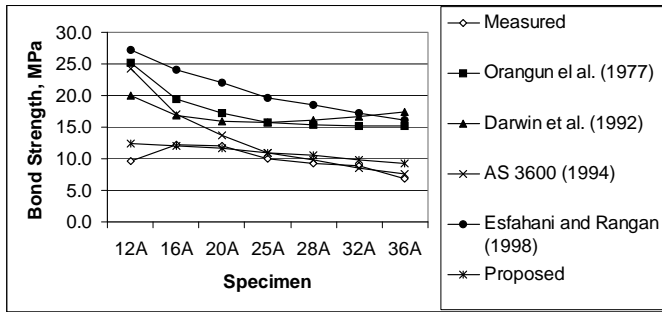


Fig. (7). Comparison of the bond strength for the 240 mm specimens.

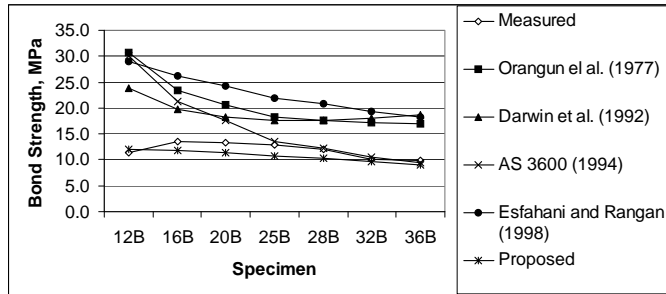


Fig. (8). Comparison of the bond strength for the 300 mm specimens.

For the pullout specimen failing, the predominant mode of failure of eleven of the tested specimens was splitting failure. The pullout failure only occurred in one specimen with the 12 mm bar with 300 mm cylinder and was characterized by cracks on the top loaded face only due to the adequate confinement of concrete cover. For the two specimens with the mode of steel rupture failure, the test specimens were broken by the exceeding load of the ultimate load of the reinforcing bar.

Based on the fourteen pull out tests, a new formula for the bond between high strength concrete and high strength steel is proposed.

ACKNOWLEDGEMENT

The author would like to express his gratitude for the financial assistance from the University of Wollongong through their Small Research Grant Scheme, which helped in conducting this research.

LIST OF NOTATIONS

A_b	=	Nominal cross-section area of reinforcing bar
A_{st}	=	Area of tensile reinforcement (mm^2)
c	=	Concrete cover
C_{max}^*	=	The highest of the lowest of C_x and $C_s/2$ and C_y
C_{min}	=	The smallest of C_x , C_y , $C_s/2$
C_s	=	Spacing between the bars.
C_x	=	Side cover
C_y	=	Bottom cover
d_b	=	Nominal diameter of the bar
dx	=	Short length of beam
f_c^*	=	Characteristic compressive strength of concrete
f_{ct}	=	Tensile strength of concrete
f_s	=	Maximum stress in bar
f_y	=	Yield stress of steel reinforcing bar
L_d	=	Embedded length of reinforced bar db
P_{max}	=	Maximum pullout load
u	=	Bond stress of the bar surface

REFERENCES

- [1] Australian Standard for Concrete Structures. AS3600, North Sydney, Australia, 1994.
- [2] S. U. Pillai, and D. W. Kirk, *Reinforced Concrete Design in Canada*, McGraw-Hill, 1983.
- [3] R. F. Warner, B. V. Rangan, A. S. Hall, and K. A. Faulkes, *Concrete Structures*, Longman, Australia, 1998.
- [4] H. H. Abrishami, and D. Mitchell, "Simulation of Uniform Bond Stress", *ACI Materials Journal*, vol.89, No. 2, pp. 161-168, March-April 1992.
- [5] C. O. Orangun, I. O. Jirsa, and J. E. Breen, "A Reevaluation of Test Data on Development Length and Splices", *ACI Journal*, vol. 74, no. 3, pp. 114-122, March 1977.
- [6] D. Darwin, S. L. McCabe, E. K. Idun, and S. P. Schoenekase, "Development Length Criteria: Bars Not Confined by Transverse Reinforcement", *ACI Structural Journal*, vol. 89, no. 6, pp. 709-720, Nov.-Dec. 1992.
- [7] M. R. Esfahani and B. V. Rangan, "Bond Between Normal Strength and High-Strength Concrete (HSC) and Reinforcing Bars in Splices in Beams", *ACI Structural Journal*, vol. 95, no. 3, pp. 272-280, May-Jun. 1998.

Received: July 24, 2008

Revised: October 20, 2008

Accepted: October 28, 2008

© Muhammad N.S. Hadi; Licensee Bentham Open.

This is an open access article licensed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/3.0/>) which permits unrestricted, non-commercial use, distribution and reproduction in any medium, provided the work is properly cited.