

# Carbon Onions: Synthesis and Electrochemical Applications

by John K. McDonough and Yury Gogotsi

Beginning with fullerenes, moving to carbon nanotubes, and most recently to graphene, carbon nanomaterials are widely studied and used in a range of applications including electronics, tribology, and energy storage. However, two kinds of carbon nanoparticles, nanodiamond<sup>1</sup> and carbon onions,<sup>2</sup> which were discovered before fullerenes and nanotubes, stayed for a long time in the shadow of more popular and better investigated nanocarbons. However, both have become increasingly studied in recent years. Carbon onions consist of spherical closed carbon shells and owe their name to the concentric layered structure resembling that of an onion. Carbon onions are sometimes called carbon nano-onions (CNOs) or onion-like carbon (OLC). Those names cover all kinds of concentric shells, from nested fullerenes to small (<100 nm) polyhedral nanostructures. This review is dedicated to those materials. We first discuss the structure of carbon onions and provide an overview of their synthesis methods. Also, electrochemical applications of carbon onions are reviewed with an emphasis on supercapacitor electrodes.

Sumio Iijima discovered OLC in 1980 while looking at a sample of carbon black in a transmission electron microscope. OLC was not produced in bulk, but rather was observed as a byproduct of carbon black synthesis.<sup>3</sup> About a decade later in 1992, Daniel Ugarte put forth a formation mechanism for the spherical graphitic

structure. By focusing an electron beam on a sample of amorphous carbon, he was able to observe the formation of OLC *in situ*. Under an electron beam, the amorphous carbon graphitizes and begins to curl, and after sufficient time, the graphitic carbon closes on itself, forming an onion. The curving and closure occurs in order to minimize the surface energy of the newly formed edge planes of graphite, which is about 30x that of the basal plane.<sup>4</sup>

## Synthesis of Carbon Onions


Although OLC has been synthesized by many different methods in the last 30 years, large scale production (gram quantities) of OLC was first realized in 1994 by Vladimir Kuznetsov and co-workers, who used vacuum annealing of a nanodiamond precursor.<sup>5,6</sup> Similar to vacuum annealing, other groups have also utilized annealing in inert gases to transform nanodiamond, which is currently produced in ton quantities,<sup>1</sup> to OLC.<sup>7</sup> This is one of the methods that has a potential for industrial applications, as the onion yield is close to 100% and the manufacturing volume is only limited by the size of the furnace, and can be scaled accordingly. This material rarely has ideal spherical carbon onions, but can be produced in large quantities and finds practical applications. The transition of nanodiamond to a carbon onion can be seen in a molecular dynamics (MD) simulation

(Fig. 1a-c). A 2-nm particle of nanodiamond (Fig. 1a) was annealed at 1400 °C (Fig. 1b) causing the outer layers of the nanodiamond to convert to graphitic carbon; however the annealing was not at high enough temperature to convert the entire particle. At higher temperatures (Fig. 1c), the entire particle is converted to an OLC particle.<sup>8</sup> At the highest annealing temperatures, the OLC particle begins to polygonize (Fig. 1d) as the structure becomes more ordered. The particle size of OLC produced via nanodiamond annealing is dependent on the nanodiamond precursor, which is generally about 5 nm in diameter,<sup>1</sup> producing onions in the 5-10 nm size range.

Arc discharge between two graphite electrodes in water represents another synthesis technique, generating OLC of slightly different structure than from annealing of nanodiamond. A dc current of 30 A and 17 V was applied between two graphite electrodes in water causing the carbon to evaporate at the location of the arc due to the extreme heat generated. The carbon vapor rapidly condenses into highly spherical OLC particles (Fig. 1e) and will float on the water surface, waiting to be collected for analysis. Consumption of the anode was about 100 mg/min, with the carbon products being produced at 20 mg/min. Synthesis by arc discharge can be performed at ambient pressure and temperature, avoiding the use of expensive equipment or catalysts, however the yield is low and samples contain nanotubes and amorphous carbon formed along with carbon onions.<sup>9,10</sup>

Hollow carbon onions have been produced with the aid of metal nanoparticles. First, the metal and carbon were evaporated by an arc discharge method, similar to the one described earlier. The resulting product is a metal particle encapsulated by layers of graphitic carbon. When the system is exposed to the beam of a transmission electron microscope (TEM), the metal particle migrates a few atoms at a time through the carbon layers, which can be seen *in situ*, and leaves a hollow OLC particle (Fig. 1f).<sup>11</sup>

Laser excitation of ethylene causes the gas to decompose and produces solid carbon at high temperatures. The process, used by Gao, *et al.*, is performed in air and uses a high-energy laser to convert the hydrocarbon to a solid carbon onion. This has potential to be used for large-scale production, as it can be scaled up, with authors showing a synthesis rate of 2.1 g/hour. This, along with annealing of detonation nanodiamond, is another feasible synthesis method for industry.<sup>12</sup>

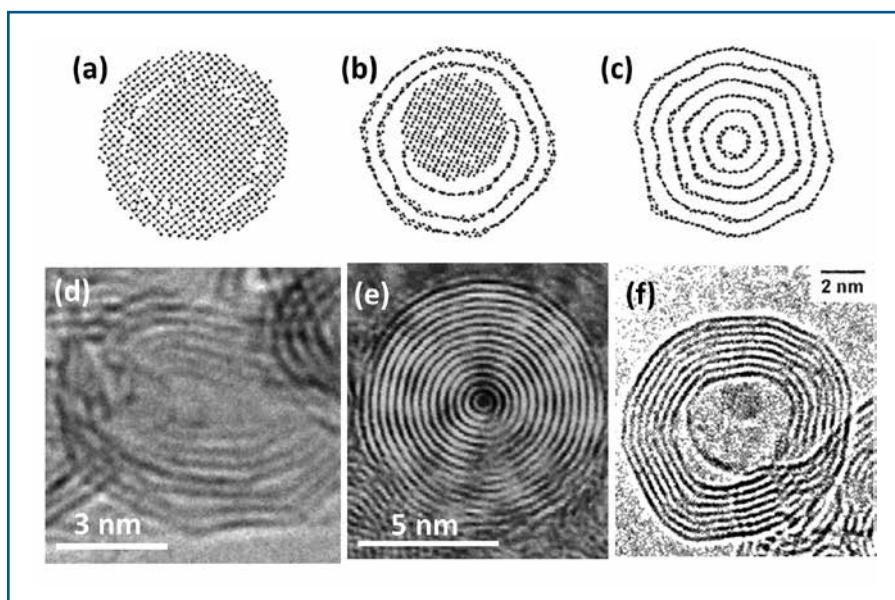

**FIG 1.** Molecular dynamics simulation of (a) pristine nanodiamond, (b) nanodiamond annealed at 1400 °C, (c) nanodiamond annealed at 2000 °C,<sup>8</sup> and carbon onions synthesized via (d) annealing of nanodiamond at 2000 °C,<sup>18</sup> (e) arc discharge between two carbon electrodes in water,<sup>9</sup> and (f) electron beam irradiation.<sup>11</sup>

(continued on next page)

There are several other processes that were reported to produce carbon onions. Synthesis of carbon onions via chemical vapor deposition (CVD) utilized an iron catalyst supported on sodium chloride to decompose acetylene gas at temperatures  $\sim 400$  °C. For less than 5 wt% iron, the carbon onions had an  $\text{Fe}_3\text{C}$  core. In contrast to other methods of carbon onion synthesis, this CVD process yields much larger diameter particles,  $\sim 50$  nm.<sup>13</sup> Carbon ion implantation is another method to produce carbon onions, first used in 1998 by Cabioch, *et al.*, which allowed the particle diameter to be tuned from 3 nm up to 30 nm by varying synthesis conditions such as temperature or implantation dose density.<sup>14</sup> Thermolysis is when a compound is decomposed by heat and has been shown to be a method for carbon onion synthesis. Using sodium azide ( $\text{NaN}_3$ ) and hexachlorobenzene ( $\text{C}_6\text{Cl}_6$ ) as the reagents, a redox reaction causes an abrupt increase in temperature and pressure, producing large diameter carbon

onions (30–100 nm) and other impurities, such as sodium chloride and amorphous carbon, which can be removed through a purification step.<sup>15</sup> Solid state carbonization of a phenolic resin precursor is a way to produce larger diameter carbon onions,  $\sim 40$  nm. The precursor material was a phenol-formaldehyde resin and required the aid of a ferric nitrate catalyst at temperatures  $\sim 1000$  °C.<sup>16</sup> High temperature evaporation of nanodiamond resulted in carbon condensing on a silicon substrate, with the carbon having the form of onions. The resulting particles had a diameter  $\sim 5$  nm. This paper does not show any information regarding mass or yield, and it seems like a low yield process.<sup>17</sup>

### Structure of Carbon Onions

The onions consist of graphene shells with pentagonal and other defects required to have closed-shell structures. Structural properties of OLC vary significantly depending on the synthesis conditions. Focusing on OLC derived from the annealing of nanodiamond between 1300 and 1800 °C, the BET specific

surface area (SSA) from  $\text{N}_2$  gas adsorption varies between 400 and 600  $\text{m}^2/\text{g}$  (Fig. 2a). There is no accessible internal porosity for OLC, so the SSA is dependent on the density of the material and the surface of the particles. At lower annealing temperatures, there is residual diamond in the sample causing a lower SSA due to a higher density of nanodiamond compared to graphitic carbon forming onion shells. A maximum at 1500 °C is found after all diamond is transformed to OLC and the particle has a rough (defective) surface, and the subsequent decrease in SSA is due to sintering and formation of larger polygonized particles as annealing temperature is increased. The pore size distribution of OLC is broad in the mesoporous range, as any “pore” is actually formed by the space between multiple onions, and does not vary significantly between synthesis conditions.<sup>18</sup>

Conversion from nanodiamond to fully graphitized onions was investigated using X-ray diffraction (XRD) (Fig. 2b). The nanodiamond precursor shows pronounced diamond peaks, as expected, in addition to a small peak for (002) graphite. Upon


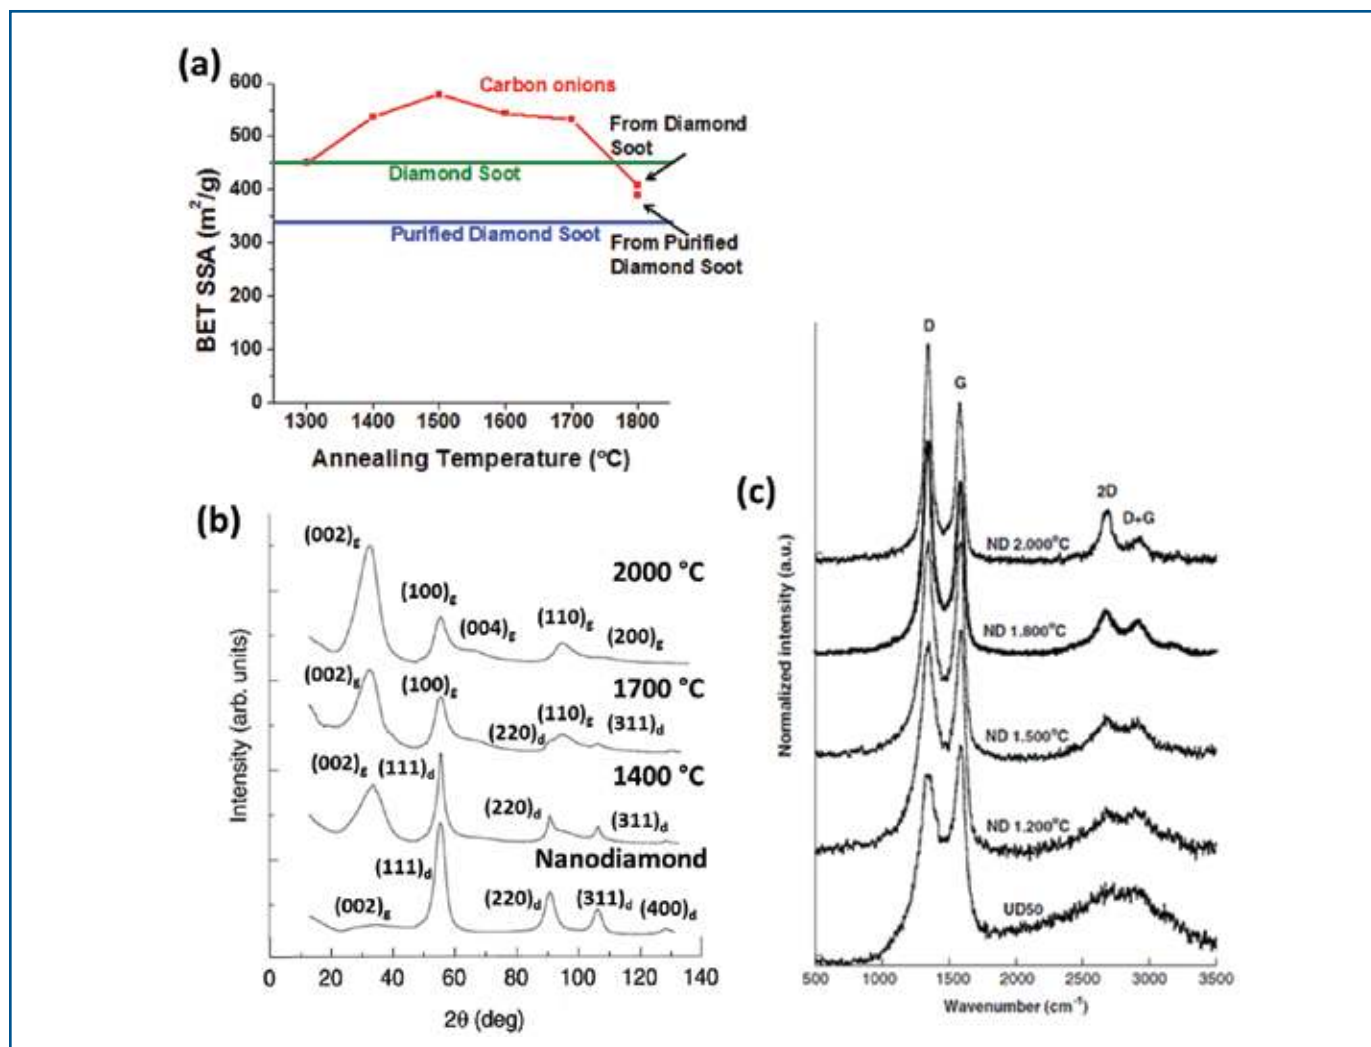


Fig. 2. (a) BET specific surface area of raw diamond soot and annealed nanodiamond (carbon onions),<sup>18</sup> (b) XRD patterns of annealed nanodiamond,<sup>19</sup> and (c) Raman spectra of annealed nanodiamond.<sup>22</sup>

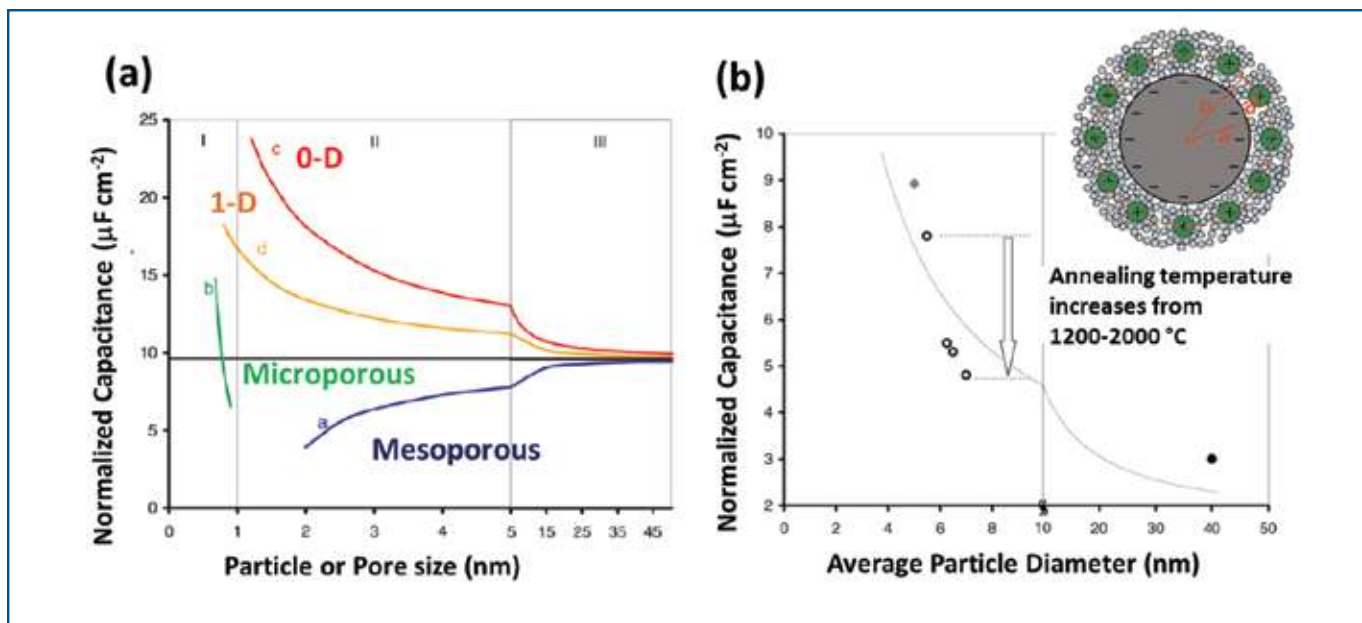

**Fig. 3.** (a) Capacitance normalized to specific surface area as a function of particle or pore size for mesoporous carbon, microporous carbon, zero-dimensional carbon onions, and one-dimensional carbon nanotubes, with the solid black line at  $10 \mu\text{F cm}^{-2}$  representing a parallel plate capacitor (graphite). (b) Capacitance normalized to specific surface area as a function of carbon onion particle diameter. Inset is an image displaying how cations adsorb on the surface of a charged carbon onion particle, forming a double layer.<sup>35</sup>

annealing for 30 minutes at 1400 °C, three peaks appear for graphite that are relatively broad and weak in intensity, probably because the graphitic carbon is still defective and incomplete shells are formed. The graphitic carbon peaks grow for the sample annealed at 1700 °C, with some residual diamond peaks. Finally, after annealing at 2000 °C for 30 minutes, no diamond peaks are present, with very pronounced peaks for graphite.<sup>19,20</sup>

Raman spectroscopy was used by Portet, *et al.* to study the surface structure of carbon onions as they are annealed from nanodiamond at temperatures between 1200 and 2000 °C (Fig. 2c). The nanodiamond precursor (UD50 grade<sup>1</sup>) used was a detonation nanodiamond soot, that is comprised of disordered carbon, carbon onions, and diamond nanoparticles, with ~25 wt% of  $sp^3$  carbon and ~75 wt% of  $sp^2$  carbon.<sup>21</sup> The Raman spectra for all samples contain two peaks at 1350 and 1600  $\text{cm}^{-1}$ , corresponding to the D-band for disordered carbon and the G-band for graphitic carbon, respectively, in addition to second order peaks for the 2D band at  $\sim 2700 \text{ cm}^{-1}$  and for the G+D band at  $\sim 2850 \text{ cm}^{-1}$ . The spectrum for UD50 shows two very broad D and G peaks, and the 2D and D+G peaks are unresolvable, implying a highly disordered graphitic carbon present in the detonation soot. Annealing the nanodiamond at 1200 °C causes a narrowing of all peaks, and appearance of the resonant peaks. As the samples are annealed at higher temperatures, up to 2000 °C, the peaks continue to narrow as the  $sp^3$  carbon and disordered carbon is further graphitized. The ratio of the D

to G band ( $I_D/I_G$ , not shown) decreases significantly upon annealing due to the increase in ordering of the carbon particles.<sup>22</sup>

### Electrochemical Applications of Carbon Onions

Electric double layer capacitors (EDLC), also known by their commercial names as supercapacitors or ultracapacitors, are non-faradaic electrical energy storage devices that store charge on the surface of a high surface area carbon electrode, often made of porous activated carbon.<sup>23,24</sup> Materials for supercapacitors range from microporous and mesoporous carbons, to one-dimensional carbon nanotubes, to two-dimensional graphene. The theoretical capacitance per surface area of these materials as a function of pore size and particle size is shown in Fig. 3a. Below a pore size or particle size of  $\sim 5 \text{ nm}$ , the normalized capacitance deviates from planar graphite, with mesoporous materials decreasing in capacitance and materials with a positive curvature, *i.e.*, carbon onions, increasing significantly. This figure shows that the smallest 0-D carbon onions can potentially outperform other materials in terms of capacitance per area.

Carbon onions debuted as a material for EDLCs in 2006–2007 in both aqueous<sup>25,26</sup> and organic<sup>22</sup> electrolytes. Since then, there has been an immense amount of attention given to OLC for both batteries<sup>27–29</sup> and supercapacitors,<sup>18,22,30–34</sup> as both active materials and easily dispersible conductive additives (ultimate carbon black). The high

power capabilities of carbon onions, with excellent capacitance retention at current densities as high as  $200 \text{ mA/cm}^2$  ( $15 \text{ A/g}$ ) have been highlighted in the very first paper.<sup>22</sup> The theoretical values from Fig. 3a compared to published data in Fig. 3b show a very good agreement and an increase in capacitance as onion size decreases.<sup>35</sup> A few years later, in 2010, the carbon onion micro-supercapacitor was fabricated and tested in comparison to other systems at the same length scale.<sup>30</sup> The micro-supercapacitor using interdigital OLC electrodes was able to operate efficiently at rates as high as  $100 \text{ V/s}$  (Fig. 4), much faster than conventional EDLCs operating at rates well below  $1 \text{ V/s}$ . A plot of the discharge current vs. scan rate derived from cyclic voltammetry should be linear for a capacitive system and will deviate at high enough rates due to diffusion limitations of the ions in electrolyte. From Fig. 4a, the OLC micro-supercapacitor has a linear relationship up to about  $100 \text{ V/s}$ . Tetraethylammonium ions at the surface of a carbon onion particle are shown in Fig. 4b. The performance of other systems in comparison with the OLC micro-supercapacitor is shown in a Ragone plot (Fig. 4c). Carbon onions have roughly 10x the power of activated carbon, however a lower energy density because of the lower surface area. Electrolytic capacitors have a comparable or higher power density, yet carbon onions have more than 10x the energy density.<sup>30</sup>

Recently, OLC and carbon nanotubes (CNTs) were used to store energy from  $-50$  to  $100 \text{ }^\circ\text{C}$ —a wider temperature range than

(continued on next page)



any porous activated carbons can deliver with organic or aqueous electrolytes. The exohedral carbons were combined with a eutectic mixture of ionic liquids, which remains liquid at temperatures down to  $-80\text{ }^{\circ}\text{C}$ . The arrangement of ions around the respective electrode materials can be seen in Fig. 5a and 5b. Both, carbon onions and nanotubes were found to operate efficiently at temperatures as low as  $-50\text{ }^{\circ}\text{C}$  and as high as  $+100\text{ }^{\circ}\text{C}$ . Conventional EDLC electrolytes utilize propylene carbonate (PC) as the solvent and begin to see a decrease in performance below  $0\text{ }^{\circ}\text{C}$  (Fig. 5c). Activated carbon was used in the same eutectic mixture of ionic liquids and failed at temperatures of  $-20\text{ }^{\circ}\text{C}$ , even at slow charge-discharge rates.<sup>36</sup> This shows that adsorption

of ions on the exohedral surfaces of onions (Fig. 5a) minimizes ion transport limitations allowing either very fast charge-discharge rates (Fig. 4a) or use of electrolytes with low mobility (Fig. 5c).

battery and supercapacitor electrodes, or as active material for supercapacitor electrodes for high-power applications and for low temperature devices using ionic liquid electrolytes.

## Conclusions

Carbon onions represent one of the least studied carbon nanomaterials, and are seeing a large increase in attention for energy storage applications. Because of their unique 0-D structure, small ( $<10\text{ nm}$ ) diameter, high electrical conductivity, and relatively easy dispersion, compared to 1-D nanotubes and 2-D graphene, OLC has been shown to be ideal as a conductive additive to

## Acknowledgments

This work was supported as part of the Fluid Interface Reactions, Structures and Transport (FIRST) Center, an Energy Frontiers Research Center funded by the US Department of Energy, Office of Science, Office of Basic Energy Sciences. The authors are thankful to Dr. Vadym Mochalin (Drexel University) for Fig. 4b. ■

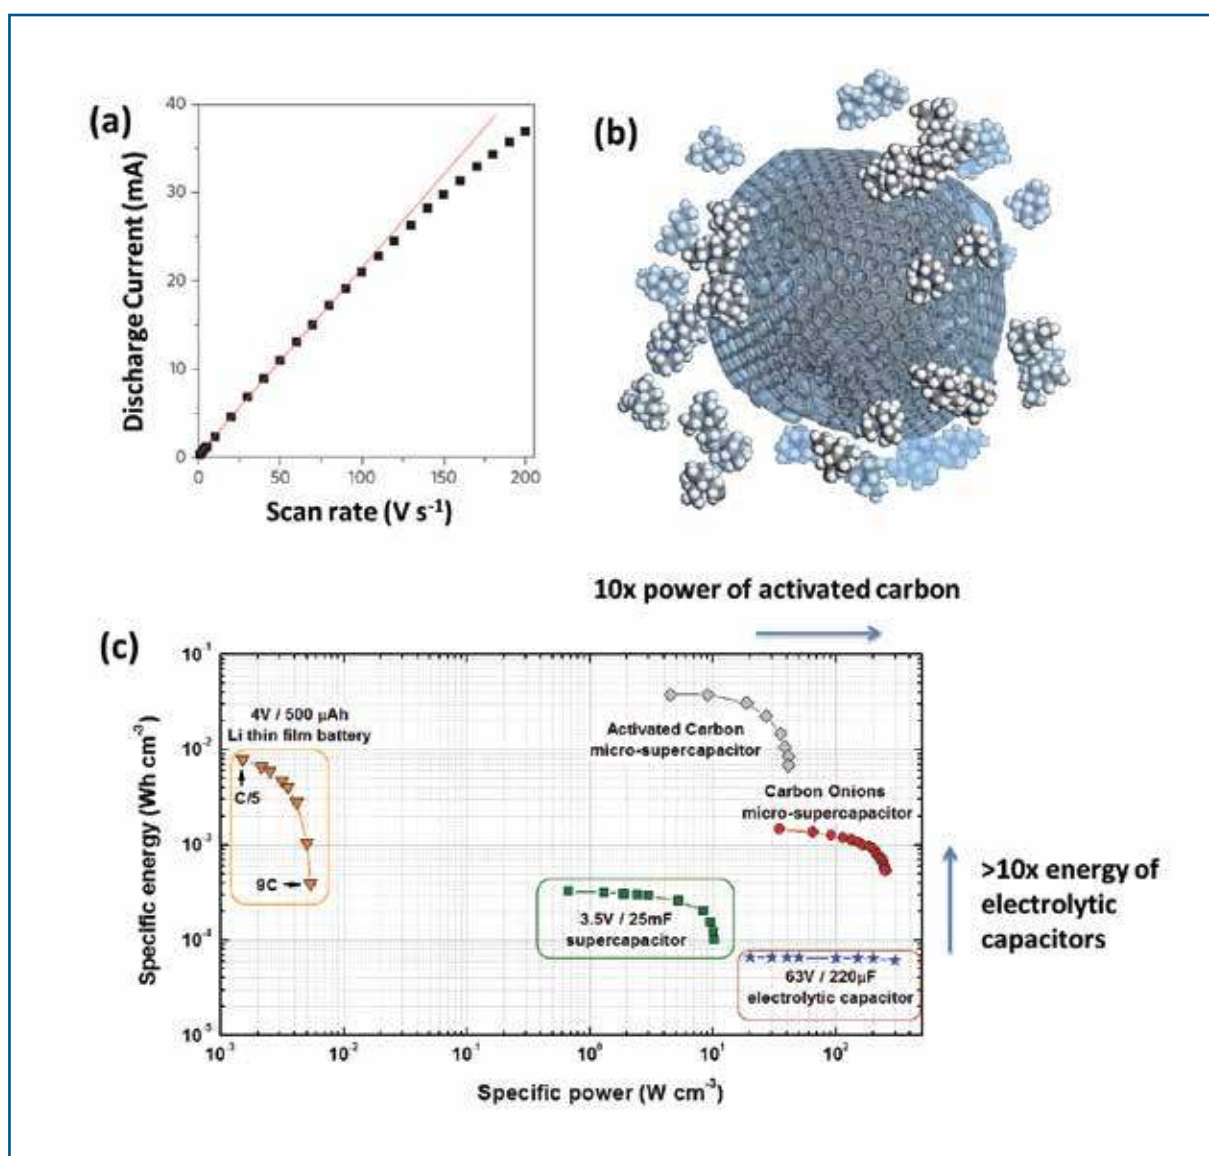


FIG. 4. (a) discharge current vs. scan rate for carbon onions in TEA-BF<sub>4</sub> in acetonitrile, (b) schematic image of a carbon onion surrounded by TEA<sup>+</sup> ions, and (c) Ragone plot of several micro-devices, highlighting the outstanding performance of a carbon onion micro-supercapacitor.<sup>30</sup>

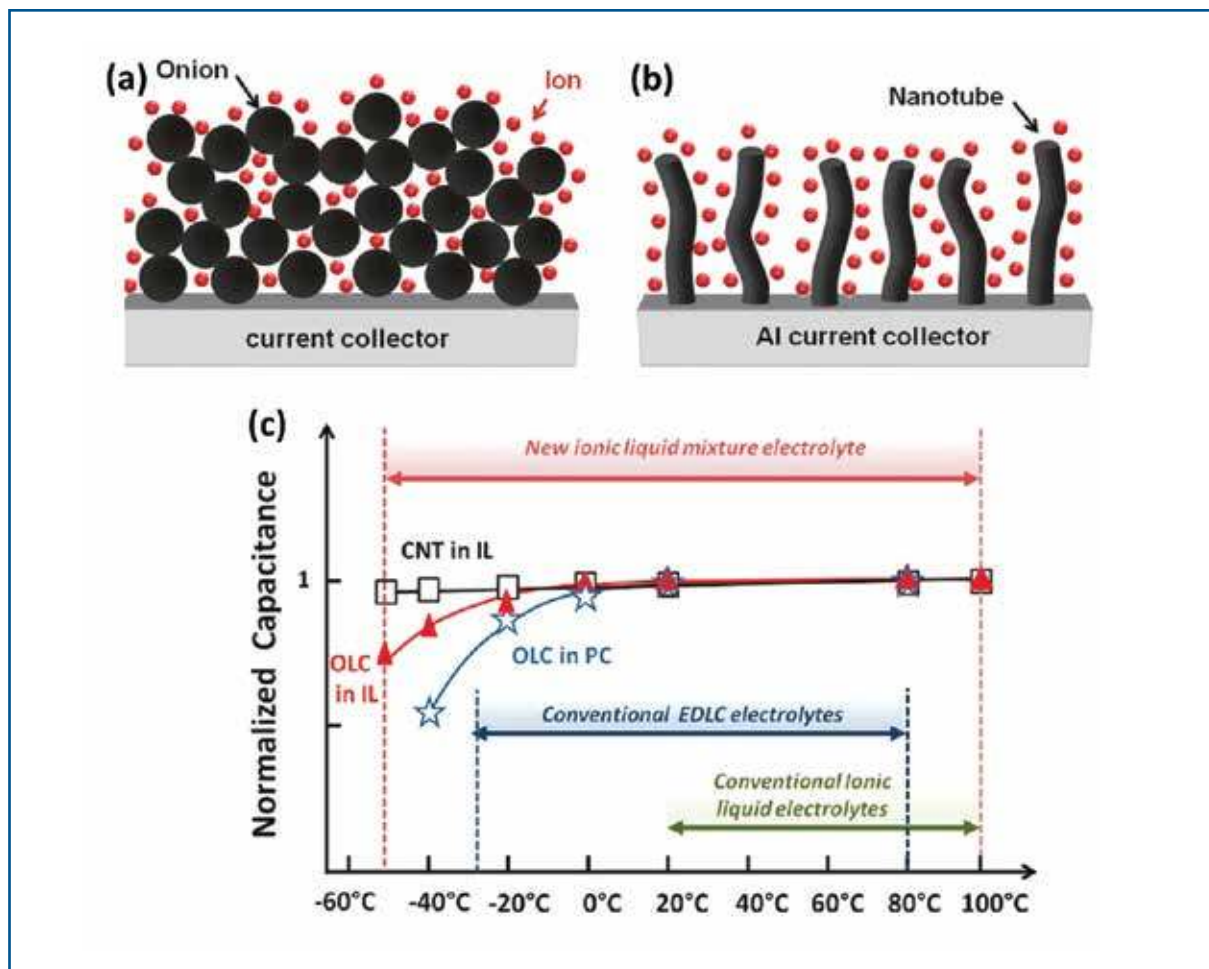


FIG. 5. Schematic of ions surrounding (a) carbon onions deposited on a current collector and (b) carbon nanotubes grown directly on a current collector, and (c) electrochemical performance of carbon nanotubes and carbon onions with their capacitance normalized to capacitance at 20 °C.<sup>36</sup>

## About the Authors

**JOHN K. McDONOUGH** received his BS in Physics in 2009 from Lycoming College. Presently, he is a PhD candidate at Drexel University, Philadelphia, in the Department of Materials Science and Engineering, studying under the guidance of Yury Gogotsi. His research focuses on carbon nanomaterials for electrical energy storage, specifically on onion-like carbon for electrochemical capacitors. McDonough serves as the President of the MRS Chapter at Drexel and is also highly involved in the ECS and ASM Chapters. He may be reached at jkm54@drexel.edu.

**YURY GOGOTSI** is a Distinguished University Professor and Trustee Chair of Materials Science and Engineering at Drexel University in Philadelphia. He also serves as Director of the A. J. Drexel Nanotechnology Institute. His PhD is in Physical Chemistry from Kiev Polytechnic and he holds a DSc in Materials Engineering from the Ukrainian Academy of Sciences. His research group works on nanostructured carbons, two-dimensional carbides, and their

electrochemical applications. He has co-authored more than 300 journal papers. He is a Fellow of ECS, AAAS, MRS, ACerS, and a member of the World Academy of Ceramics. He may be reached at Gogotsi@drexel.edu.

## References

1. V. N. Mochalin, O. Shenderova, D. Ho, and Y. Gogotsi, *Nature Nanotechnol.*, **7**, 11 (2012).
2. Yu. V. Butenko, L. Siller, and M. R. C. Hunt, in *Carbon Nanomaterials*, 2<sup>nd</sup> edition, Y. Gogotsi, V. Presser, Eds., CRC Press, pp. 279-231 (2013).
3. S. Iijima, *J. Cryst Growth*, **50**, 675 (1980).
4. D. Ugarte, *Nature*, **359**, 707 (1992).
5. V. L. Kuznetsov, A. L. Chuvilin, Y. V. Butenko, I. Y. Malkov, and V. M. Titov, *Chem. Phys. Lett.*, **222**, 343 (1994).
6. V. L. Kuznetsov, A. L. Chuvilin, E. M. Moroz, V. N. Kolomiichuk, S. K. Shaikhutdinov, Y. V. Butenko, and I. Y. Malkov, *Carbon*, **32**, 873 (1994).
7. J. Cebik, J. K. McDonough, F. Peeraly, R. Medrano, I. Neitzel, Y. Gogotsi, and S. Osswald, *Nanotechnology*, **24**, 205703 (2013).
8. L. Hawelek, A. Brodka, S. Tomita, J. C. Dore, V. Honkimäki, and A. Burian, *Diam. Relat. Mater.*, **20**, 1333 (2011).
9. I. Alexandrou, H. Wang, N. Sano, and G. A. J. Amaratunga, *J. Chem. Phys.*, **120**, 1055 (2004).
10. N. Sano, H. Wang, I. Alexandrou, M. Chhowalla, K. B. K. Teo, G. A. J. Amaratunga, and K. Iimura, *J. Appl. Phys.*, **92**, 2783 (2002).
11. F. Banhart, *Reports on Progress in Physics*, **62**, 1181 (1999).
12. Y. Gao, Y. S. Zhou, J. B. Park, H. Wang, X. N. He, H. F. Luo, L. Jiang, and Y. F. Lu, *Nanotechnology*, **22**, 165604 (2011).
13. Y. Yang, X. Liu, X. Guo, H. Wen, and B. Xu, *J. Nanopart. Res.*, **13**, 1979 (2011).
14. T. Cabioch, M. Jaouen, M. F. Denanot, and P. Bechet, *Appl. Phys. Lett.*, **73**, 3096 (1998).

(continued on next page)

## McDonough and Gogotsi

(continued from previous page)

15. M. Bystrzejewski, M. H. Rummeli, T. Gemming, H. Lange, and A. Huczko, *New Carbon Mater.*, **25**, 1 (2010).
16. M. Zhao, H. Song, X. Chen, and W. Lian, *Acta Mater.*, **55**, 6144 (2007).
17. S. Krishnamurthy, Y. V. Butenko, V. R. Dhanak, M. R. C. Hunt, and L. Šiller, *Carbon*, **52**, 145 (2013).
18. J. K. McDonough, A. I. Frolov, V. Presser, J. Niu, C. H. Miller, T. Ubieto, M. V. Fedorov, and Y. Gogotsi, *Carbon*, **50**, 3298 (2012).
19. S. Tomita, A. Burian, J. C. Dore, D. LeBolloch, M. Fujii, and S. Hayashi, *Carbon*, **40**, 1469 (2002).
20. S. Tomita, T. Sakurai, H. Ohta, M. Fujii, and S. Hayashi, *J. Chem. Phys.*, **114**, 7477 (2001).
21. S. Osswald, G. Yushin, V. Mochalin, S. O. Kucheyev, and Y. Gogotsi, *J. Amer. Chem. Soc.*, **128**, 11635 (2006).
22. C. Portet, G. Yushin, and Y. Gogotsi, *Carbon*, **45**, 2511 (2007).
23. P. Simon and Y. Gogotsi, *Philos. Trans. Royal Society A: Math., Phys. and Engin. Sci.*, **368**, 3457 (2010).
24. P. Simon and Y. Gogotsi, *Nature Materials*, **7**, 845 (2008).
25. E. G. Bushueva, P. S. Galkin, A. V. Okotrub, L. G. Bulusheva, N. N. Gavrilov, V. L. Kuznetsov, and S. I. Moiseev, *Phys. Status Solidi B*, **245**, 2296 (2008).
26. E. G. Bushueva, A. V. Okotrub, P. S. Galkin, V. L. Kuznetsov, and S. I. Moseenkov, in *Nanocarbon & Nanodiamond*, p. 11, St. Petersburg, Russia (2006).
27. F.-D. Han, B. Yao, and Y.-J. Bai, *J. Phys. Chem. C*, **115**, 8923 (2011).
28. H. J. Zhang, H. H. Song, J. S. Zhou, H. K. Zhang, and X. H. Chen, *Acta Phys-Chim. Sin.*, **26**, 1259 (2010).
29. W. Gu, N. Peters, and G. Yushin, *Carbon*, **53**, 292 (2013).
30. D. Pech, M. Brunet, H. Durou, P. H. Huang, V. Mochalin, Y. Gogotsi, P. L. Taberna, and P. Simon, *Nature Nanotechnol.*, **5**, 651 (2010).
31. C. Portet, J. Chmiola, Y. Gogotsi, S. Park, and K. Lian, *Electrochim. Acta*, **53**, 7675 (2008).
32. G. Feng, D.-E. Jiang, and P. T. Cummings, *J. Chem. Theory and Computation*, **8**, 1058 (2012).
33. M. M. Hantel, V. Presser, J. K. McDonough, G. Feng, P. T. Cummings, Y. Gogotsi, and R. Kötz, *J. Electrochem. Soc.*, **159**, A1897 (2012).
34. P. F. Fulvio, R. T. Mayes, X. Wang, S. M. Mahurin, J. C. Bauer, V. Presser, J. McDonough, Y. Gogotsi, and S. Dai, *Adv. Funct. Mater.*, **21**, 2208 (2011).
35. J. S. Huang, B. G. Sumpter, V. Meunier, G. Yushin, C. Portet, and Y. Gogotsi, *J. Mater. Res.*, **25**, 1525 (2010).
36. R. Lin, P.-L. Taberna, S. B. Fantini, V. Presser, C. R. Pérez, F. O. Malbosc, N. L. Rupasinghe, K. B. K. Teo, Y. Gogotsi, and P. Simon, *J. Phys. Chem. Lett.*, **2**, 2396 (2011).



## Advertise in *Interface* and STAND OUT

✓ More than 10,000 scientists and engineers worldwide have purchasing power and make recommendations about R&D products and services.

- precision instrumentation
- training
- photonics, lasers, and optics
- metals, ceramics
- alloys, semiconductors
- modeling
- micro- and opto-electronics
- polymers/organics
- biomaterials
- processing, assembly, packaging
- testing
- advanced software
- ... and articles on the latest in research and development in all areas of electrochemistry and solid state science and technology.

**They read *Interface* to find them!**



REQUEST an *Interface* Media Kit TODAY.  
Download Media Kit at <http://www.electrochem.org/mediakit>.  
Contact [dinia.agrawala@electrochem.org](mailto:dinia.agrawala@electrochem.org)

[www.electrochem.org](http://www.electrochem.org)