

Chitin Extraction from Crustacean Shells Using Biological Methods – A Review

Wassila Arbia¹, Leila Arbia¹, Lydia Adour^{1,2} and Abdeltif Amrane^{3,4*}

¹Laboratory of Environmental Biotechnology and Process Engineering (BIOGEP),
Department of Environmental Engineering, Polytechnic National School, 10 Avenue Hacene Badi,
BP 182, El Harrach, DZ-16200 Algiers, Algeria

²Department of Chemistry, Faculty of Science, Mouloud Mammeri University of Tizi Ouzou,
DZ-15000 Tizi Ouzou, Algeria

³National School of Chemistry of Rennes, CNRS, UMR 6226, Avenue du Général Leclerc, CS 50837,
FR-35708 Rennes Cedex 7, France

⁴European University of Brittany, 5 Boulevard Laënnec, FR-35000 Rennes, France

Received: June 17, 2011

Accepted: April 18, 2012

Summary

After cellulose, chitin is the most widespread biopolymer in nature. Chitin and its derivatives have great economic value because of their biological activities and their industrial and biomedical applications. It can be extracted from three sources, namely crustaceans, insects and microorganisms. However, the main commercial sources of chitin are shells of crustaceans such as shrimps, crabs, lobsters and krill that are supplied in large quantities by the shellfish processing industries. Extraction of chitin involves two steps, demineralisation and deproteinisation, which can be conducted by two methods, chemical or biological. The chemical method requires the use of acids and bases, while the biological method involves microorganisms. Although lactic acid bacteria are mainly applied, other microbial species including proteolytic bacteria have also been successfully implemented, as well as mixed cultures involving lactic acid-producing bacteria and proteolytic microorganisms. The produced lactic acid allows shell demineralisation, since lactic acid reacts with calcium carbonate, the main mineral component, to form calcium lactate.

Key words: chitin, crustacean shells, chitin extraction, biological methods

Introduction

Enormous amounts of chitin can be found in the biosphere; it is the major component of cuticles of insects, fungal cell walls, yeast or green algae (1–3). Fungi provide the largest amount of chitin in the soil (6–12 % of chitin biomass, which is in the range of 500–5000 kg/ha) (4). Chitin is also widely present in crab and shrimp shells (5).

A working estimate for the annual turnover is in the range of 10^{10} – 10^{11} tonnes (6,7), making chitin one of the most abundant biopolymers. Chitin can be readily obtained by simple extraction (8). To date, the major source

of industrial chitin comes from wastes of marine food production, mainly crustacean shells, *e.g.* shrimp, crab or krill shells (9–11).

In the processing of shrimps for human consumption, between 40 and 50 % of the total mass is waste. About 40 % of the waste is chitin, incrustated with calcium carbonate and astaxanthin, and containing meat and a small amount of lipid residues. A small part of the waste is dried and used as chicken feed (11), while the rest is dumped into the sea, which is one of the main pollutants in coastal areas (12,13). The utilization of shellfish waste has been proposed not only to solve environmental problems, but as a waste treatment alternative to

*Corresponding author; Phone: ++33 2 2323 8155; Fax: ++33 2 2323 8120; E-mail: abdelatif.amrane@univ-rennes1.fr

the disposal of shellfish wastes (14). Crustacean shell waste consists mainly of 30–40 % protein, 30–50 % calcium carbonate, and 20–30 % chitin (Table 1) (15–18), with species and seasonal variations (19).

Seafood processing and consumption generate each year hundreds of tonnes of shellfish waste, like in Taiwan (9) or Indonesia (20), whereas in Germany only 22 616 tonnes of shrimp waste is discarded on the sea-shore (11). By-products from marine food production, mainly shrimp shells, comprise almost 40 % of total prawn mass and have become a major environmental concern due to their slow degradation (8). The major components (on dry mass basis) of shrimp waste are proteins, chitin, minerals and carotenoids (20,21).

To extract chitin from shrimp shells using traditional chemical treatment, 4 % NaOH is used for deproteinisation and 4 % HCl for demineralization. This process presents some drawbacks since it is expensive and environmentally unfriendly (22), and hence finding alternative processes would be really helpful. Biotechnological production of chitin has not been commercially available up to now, but it can offer new perspectives for the production of highly viscous chitosan, with a promising potential for applications in biomedicine and pharmacy (23,24). Fermentation of this biowaste using lactic acid bacteria for the production of chitin has been studied and reported (25). The use of organic acids such as lactic acid for the demineralisation process is a promising idea since organic acids can be produced by bacteria at low cost, are less harmful to the environment, can preserve the characteristics of the purified chitin and the resulting organic salts from the demineralisation process can be used as an environmentally friendly deicing/anti-icing agents and/or as preservatives (22).

Properties of Chitin

Chitin is one of the most abundant biopolymers in nature (1) and is a major component in the supporting

tissues of organisms such as crustaceans, fungi and insects (26). It is a linear polysaccharide composed of α -(1–4)-linked 2-acetamido-2-deoxy-D-glucose units which may be de-N-acetylated to some extent (27). It is a structural polysaccharide similar to cellulose. Chitin molecules are known to be ordered into helicoidal, microfibrillar structures that are embedded into the protein material of the shells (28). Chitin is closely associated with proteins, minerals, lipids and pigments (29).

Several studies have clearly demonstrated that specific characteristics, namely degree of deacetylation and molecular mass of chitin and its deacetylated derivative, chitosan, vary with process conditions. The physico-chemical characteristics of chitin and chitosan influence their functional properties such as solubility, chemical reactivity and biological activities (30), namely biodegradability (2,31), which differ depending on the crustacean species and preparation methods (32). Recent studies have revealed notable variability in the dye, water, and fat binding capacities of various chitins, chitosans and their derivatives produced from crustacean shell wastes at laboratory scale (19), as well as notable variability in the antibacterial activities (32), biodegradability and immunological activities (33,34).

The degree of deacetylation, defined as the molar fraction of deacetylated units in the polymer chain (35), is one of the most important factors influencing the properties of chitin and chitosan (18), such as solubility, flexibility, polymer conformation and viscosity (16,24,36). The degree of acetylation can be employed to differentiate between chitin and chitosan; in the case of chitin it is greater than a given value (*e.g.* >50 %) and insoluble, while in the case of chitosan it is smaller than that value and soluble (37). A number of methods have been reported to determine the degree of deacetylation of chitin (2).

Molecular mass determines the viscosity and the rate of degradation, which can be determined by viscometer,

Table 1. Contents of chitin in different organisms (15–18)

| Organism | <i>w</i> (chitin)/% | Organism | <i>w</i> (chitin)/% |
|---|---------------------|---------------------------------|---------------------|
| Crustaceans: | | <i>Bombyx</i> (silk worm) | 44.2 ^c |
| <i>Cancer</i> (crab) | 72.1 ^c | <i>Galleria</i> (wax worm) | 33.7 ^c |
| <i>Carcinus</i> (crab) | 64.2 ^b | Mollusks: | |
| <i>Paralithodes</i> (king crab) | 35.0 ^b | clam | 6.1 |
| <i>Callinectes</i> (blue crab) | 14.0 ^a | shell oysters | 3.6 |
| <i>Crangon</i> and <i>Pandalus</i> (shrimp) | 17–40 | squid pen | 41.0 |
| Alaska shrimp | 28.0 ^d | krill, deproteinized shells | 40.2 |
| <i>Nephro</i> (lobster) | 69.8 ^c | Fungi: | |
| <i>Homarus</i> (lobster) | 60–75 ^c | <i>Aspergillus niger</i> | 42.0 ^e |
| <i>Lepas</i> (goose barnacle) | 58.3 ^c | <i>Penicillium notatum</i> | 18.5 ^e |
| Insects: | | <i>Penicillium chrysogenum</i> | 20.1 ^e |
| <i>Periplaneta</i> (cockroach) | 2.0 ^d | <i>Saccharomyces cerevisiae</i> | 2.9 ^e |
| <i>Blatella</i> (cockroach) | 18.4 ^c | <i>Mucor rouxii</i> | 44.5 |
| <i>Coleoptera</i> (ladybird) | 27–35 ^c | <i>Lactarius vellereus</i> | 19.0 |
| <i>Diptera</i> | 54.8 ^c | | |
| <i>Pieris</i> (butterfly) | 64.0 ^c | | |

^acompared to the body fresh mass, ^bwith respect to the body dry mass, ^cbased on the mass of the organic cuticle, ^dcompared to the total mass of the cuticle, ^erelative to the dry mass of the cell wall

light scattering and gel permeation chromatography (38). The chitins differ not only in molecular mass and degree of deacetylation, but also by their crystalline structure, which controls a number of properties (16). Chitin occurs in three polymorphic forms, α -, β -, and γ -chitins, which differ in the arrangement of molecular chains within the crystal cell (35,39). α -Chitin with its antiparallel chain arrangement is the most abundant chitin in nature (shrimps, crabs), β -chitin has parallel chains and occurs in squid pens (11,40,41), while γ -chitin presents the mixture of α - and β -chitins (39).

Similarly to cellulose, chitin is insoluble in water, aqueous solvents and common organic solvents, owing to its strong intra- and inter-molecular hydrogen bonds (18,42). Solubility, which is related to different parameters, is very difficult to control (16,41).

Chitosan, as a polyelectrolyte, is able to form electrostatic complexes under acidic conditions (41). It is a cationic polysaccharide and its cationic nature in acidic medium is unique among polysaccharides (43).

Owing to its chemical structure, chitosan is a substitute for biological media. Indeed, the glycosidic bond and the *N*-acetylglucosamine residues found in the chitosan macromolecules are also present in the structure of the extracellular matrix of most living tissues (16).

Methods of Chitin Extraction

Chemical methods

In the skeletal tissue, protein and chitin combine to form a protein-chitin matrix, which is then extensively calcified to yield hard shells. The waste may also contain lipids from the muscle residues and carotenoids, mainly astaxanthin and its esters (8).

A traditional method for the commercial preparation of chitin from crustacean shell (exoskeleton) consists of two basic steps (Fig. 1): (i) protein separation, *i.e.*

deproteinisation by alkali treatment, and (ii) calcium carbonate (and calcium phosphate) separation, *i.e.* demineralisation by acidic treatment under high temperature, followed by a bleaching step with chemical reagents to obtain a colourless product (44–46).

Deproteinisation is usually performed by alkaline treatment (29). Demineralisation is generally performed by acid treatment including HCl, HNO₃, H₂SO₄, CH₃COOH, and HCOOH; however, HCl seems to be the preferred reagent (29,44). It was shown that the order of the two steps may be reversed for shrimp waste containing large protein concentrations, which stem primarily from the skeletal tissue and to a lesser extent from the remaining muscle tissue (8).

The major concern in chitin production is the quality of the final product, which is a function of the molecular mass (average and polydispersity) and the degree of acetylation. Harsh acid treatments may cause hydrolysis of the polymer, inconsistent physical properties in chitin and are source of pollution (47). High NaOH concentrations and high deproteinisation temperatures can cause undesirable deacetylation and depolymerisation of chitin (8). Percot *et al.* (29) reported that using inorganic acids such as HCl for the demineralisation of chitin results in detrimental effects on the molecular mass and the degree of acetylation that negatively affect the intrinsic properties of the purified chitin (Table 2). Similarly, according to Crini *et al.* (16) this method allows almost complete removal of organic salts, but at the same time reactions of deacetylation and depolymerisation may occur (Table 2). Quality improvement can be obtained by improving the contact of chemicals with the shrimp waste, for instance by using stirred bioreactors. This would allow reactions to proceed with the same efficiency at shorter exposure time and at lower temperature (24). Comparing different chitins (degree of acetylation, molecular mass and optical activity), variations of the characteristics of the obtained polymer were observed according to the acid used for the demineralisation (16).

In addition, chemical chitin purification is energy consuming and somewhat damaging to the environment owing to the high mineral acid and base amounts involved (48). These chemical treatments also create a disposal problem for the wastes, since neutralisation and detoxification of the discharged wastewater may be necessary (49). Another disadvantage of chemical chitin purification is that the valuable protein components can no longer be used as animal feed (22,50).

Biological methods

An alternative way to solve chemical extraction problems is to use biological methods. The use of proteases for deproteinisation of crustacean shells would avoid alkali treatment (Fig. 1). Besides the application of exoenzymes, proteolytic bacteria were used for deproteinisation of demineralised shells (47). This approach allows obtaining a liquid fraction rich in proteins, minerals and astaxanthin and a solid chitin fraction. The liquid fraction can be used either as a protein-mineral supplement for human consumption or as an animal feed (25).

Deproteinisation processes have been reported for chitin production mainly from shrimp waste using me-

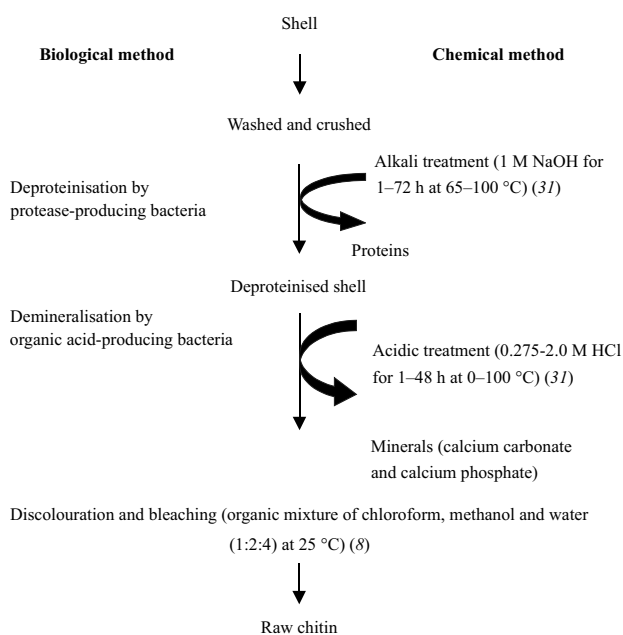


Fig. 1. Chitin recovery by chemical and biological methods (8,31)

Table 2. Comparison of chemical and biological methods for chitin recovery (31,38)

| | | Chemical method | Biological method |
|-----------------|---|--|--|
| Chitin recovery | | | <i>in situ</i> |
| | Demineralisation | Mineral solubilisation by acidic treatment including HCl, HNO ₃ , H ₂ SO ₄ , CH ₃ COOH and HCOOH. | Carried out by lactic acid produced by bacteria through the conversion of an added carbon source. |
| | Deproteinisation | Protein solubilisation by alkaline treatment. | Carried out by proteases secreted into the fermentation medium. In addition, deproteinisation can be achieved by adding exo-proteases and/or proteolytic bacteria. |
| | | Effluent treatment after acid and alkaline extraction of chitin may cause an increase in the cost of chitin. | Extraction cost of chitin by biological method can be optimised by reducing the cost of the carbon source. |
| | | | Solubilised proteins and minerals may be used as human and animal nutrients. |
| Chitin quality | The major concern in chitin production is the quality of the final product, which is a function of the molecular mass (average and polydispersity) and the degree of acetylation. | <p>A wide range of quality properties of the final product.</p> <p>Using inorganic acids such as HCl for chitin demineralisation results in detrimental effects on the molecular mass and the degree of acetylation that negatively affect the intrinsic properties of the purified chitin (31).</p> <p>This method allows almost complete removal of organic salts, but at the same time the reactions of deacetylation and depolymerisation may occur (38).</p> <p>The comparison of different chitins (degree of acetylation, molecular mass, optical activity) obtained with four different acids showed that the polymer characteristics varied according to the extraction method used (38).</p> | Homogeneous and high quality of the final product. |

chemical (47), enzymatic (51,52) and microbial processes involving species like *Lactobacillus* (25), *Pseudomonas aeruginosa* K-187 (53) and *Bacillus subtilis* (54). Biological demineralisation has also been reported for chitin production from crustacean shells; enzymatically, using for instance alcalase (52), or by microbial process involving species like *L. pentosus* 4023 (45) or by a natural probiotic (milk curd) (55). In these biological processes, demineralisation and deproteinisation occur mainly simultaneously but incompletely (47). An overview of the various biological methods available in the literature is given in Table 3 (11,25,45,46,48,49,53,56–70).

Fermentation has been applied to fish for many years and represents a low-level (artisanal) and affordable (neither capital nor energy intensive) technology (71). It consists in the ensilation of crustacean shells and a low-cost *in situ* production of lactic acid from by-products such as whey, lignocellulose and starch. Lactic acid production by lactic acid bacteria induced a liquefaction of the semi-solid waste and led to a low pH and activation of proteases (50). The protein-rich liquid could be separated from the chitin, which remained in the sediment (11). This method might offer a commercial route for the recovery of chitin (45).

Lactic acid is formed from the breakdown of glucose, creating the low pH, which improves the ensilation that suppresses the growth of spoilage microorganisms. Lactic acid reacts with the calcium carbonate component in the chitin fraction, leading to the formation of calcium

lactate, which precipitates and can be removed by washing. The resulting organic salts from the demineralisation process could be used as de- and anti-icing agents and/or preservatives (56). Deproteinisation of the bio-waste and simultaneous liquefaction of the shrimp proteins occurs mainly by proteolytic enzymes produced by the added *Lactobacillus*, by gut bacteria present in the intestinal system of the shrimp, or by proteases present in the bio-waste (25). It results in a fairly clean liquid fraction with a high content of soluble peptides and free amino acids (71).

Khanafari *et al.* (22) extracted chitin and chitosan from shrimp waste by chemical and microbial methods. Their results showed that the microbial method is more effective especially for the recovery of chitin, compared to chemical method.

Lactic acid fermentation of shrimp waste

Recently, biological processes for chitin production have been reported using bacteria that produce organic acids and enzymes for the demineralisation and deproteinisation of crustacean shells. Fermentation of shrimp (*Penaeus monodon*) waste with lactic acid bacteria for chitin recovery was studied with added carbohydrates such as lactose or cassava extract as a natural energy source (56) and date juice for extraction of chitin from head and shell of shrimp *Parapenaeus longirostris* using *Lactobacillus helveticus* (57). Raw heads of African river prawn (*Macrobrachium vollehovenii*) were fermented with *Lactobacillus*

Table 3. Overview of the biological methods for chitin recovery

| Waste source | Strains and/or proteolytic enzymes | Carbon source | Duration day | Efficiency /% | | Refs. |
|--|--|---------------|--------------|--------------------|--------------------|-------|
| | | | | deprotein-isation | demineral-isation | |
| Lactic acid fermentation | | | | | | |
| <i>Penaeus</i> sp. | <i>Lactobacillus</i> spp. B2 | sucrose whey | 6 | 85 | 87.6 | (59) |
| demineralised <i>Nephrops norvegicus</i> | Stabisil: <i>Streptococcus faecium</i> M74, <i>L. plantarum</i> , <i>Pediococcus acidilactici</i> | lactose | 7 | 40 | n.d. | (60) |
| <i>Nephrops norvegicus</i> | Sil-All ^{4x4} : <i>L. plantarum</i> , <i>L. salivarius</i> , <i>S. faecium</i> , <i>P. acidilactici</i> | glucose | 7 | n.d. | 90.99 | (48) |
| <i>Nephrops norvegicus</i> | <i>L. paracasei</i> A3 | glucose | 5 | 77.5 | 61 | (58) |
| one-step shrimp fermentation | <i>L. plantarum</i> 541 | glucose | – | 75 | 86 | (25) |
| pretreated <i>Procambarus clarkii</i> (crayfish) | <i>L. paracasei</i> A3 | dextrose | 3 | 94 | 97.2 | (61) |
| <i>Procambarus clarkii</i> | immobilized <i>Lactobacillus pentosus</i> 4023 | whey | 2.1 | 81.5 | 90.1 | (45) |
| <i>Chionoecetes japonicus</i> | <i>L. paracasei</i> ssp. <i>tolerans</i> KCTC-3074 | glucose | 1 | 54.7 | 55.2 | (56) |
| <i>Parapenaeus longirostris</i> | <i>L. helveticus</i> | date juice | 14 | 91 | 44 | (57) |
| Non-lactic acid fermentation | | | | | | |
| <i>Metapenaeus dobson</i> | <i>Bacillus subtilis</i> | jaggery | – | 84 | 72 | (62) |
| shrimp and crab shell | <i>Pseudomonas aeruginosa</i> K-187 | – | 5 | 82 | – | (49) |
| shrimp and crab shell powder | proteases of <i>P. aeruginosa</i> K-187 | – | 7 | 72 | – | (53) |
| natural shrimp shells | immobilized proteases of <i>P. aeruginosa</i> | | | 78 | | |
| acid treated natural shrimp shell | | | | 45 | | |
| shrimp and shell crab powder | | | | 67 | | (53) |
| crab shell powder | <i>P. aeruginosa</i> F722 | – | 7 | 63 | 92 | (63) |
| <i>Chionoecetes opilio</i> (natural crab shell waste) | <i>Serratia marcescens</i> FS-3 | | 7 | 47 | 84 | (64) |
| | Delvolase [®] | | | 90 | | |
| | Combination of Delvolase [®] and <i>Serratia marcescens</i> FS-3 | | | 85 | | |
| | <i>S. marcescens</i> FS-3 supernatant culture | | | 81 | | |
| shrimp shell waste | <i>Bacillus cereus</i> | | – | 97.1 | 95 | (65) |
| | <i>Exiguobacterium acetylicum</i> | | | 92.8 | 92 | |
| squid pen | <i>Bacillus</i> sp. TKU 004 | | | 73 | n.d. | (66) |
| <i>Penaeus monodon</i> | <i>Pediococcus acidilactici</i> CFR2182 | | | 97.9±0.3 | 72.5±1.5 | (70) |
| shrimp shells | <i>Pediococcus</i> sp. L1/2 | sucrose | 1.5 | n.d. | 83 | (46) |
| Cofermentation | | | | | | |
| two-step fermentation of <i>Penaeus monodon</i> and <i>Crangon crangon</i> | first step: anaerobic deproteinisation by autochthonous flora of Indonesian shrimp shells and/or proteolytic bacteria second step: <i>L. casei</i> MRS1 | | | 97.4 90.8 | 99.6 99.7 | (11) |
| prawn waste | <i>Lactobacillus lactis</i> <i>Teredinibacter turnerae</i> co-fermentation of both species | | | 66.5 77.8 95 | 78.8 23.3 95 | (67) |
| red crab shell waste | one-step fermentation: <i>L. paracasei</i> ssp. <i>tolerans</i> KCTC-3074 and <i>S. marcescens</i> FS-3 | | 7 | 52.6 94.3 | 97.2 68.9 | (68) |
| | successive two-step fermentation two <i>Bacillus licheniformis</i> strains with treatment of the final fermentation product with 0.9 % lactic acid | | 2 | 99 | 98.8 | (69) |

n.d.=not determined

plantarum using cane molasses (71). Lactic acid bacteria fermentation for demineralisation has also been reported for shrimp waste (50), crayfish exoskeleton (45), scampi waste (58) and prawn waste.

Lactic acid fermentation combined with chemical treatments has been studied as an alternative to chemical extraction of chitin, reducing the amount of alkali and acid required (59). It was considered as a pretreatment of shrimp waste followed by demineralisation and deproteinisation using low concentrations of HCl (0.5 M) and NaOH (0.4 M).

The production of chitin from prawn (*Nephrops norvegicus*) shell waste by fermentation was investigated by Healy *et al.* (60). In that study, previously demineralised shells were incubated for deproteinisation with commercial bacterial inocula (Stabisil and Nutrimink, both from Nutrimix Ltd, Lankashire, UK; and Sil-All^{4x4}, Sil-All, Alltech, Stamford, Lincolnshire, UK) together with lactose (Nutrimink) under both aerobic and anaerobic conditions for 7 days (Table 3). Stabisil is used mainly for the ensiling of fish offal and consists of active bacterial cultures (*Streptococcus faecium* M74, *Lactobacillus plantarum*, and *Pediococcus acidilactici*). In general, protein depletion of approx. 40 % was achieved irrespective of the considered conditions (aerobic or anaerobic).

The anaerobic fermentation of prawn (*Nephrops norvegicus*) shell waste using lactic acid bacteria, in combination with the inoculant Sil-All^{4x4} (Table 3), a powdered grass silage inoculant containing a mixture of selected proteolytic enzyme-producing bacteria (*L. plantarum*, *L. salivarius*, *S. faecium* and *P. acidilactici*), has been established as an effective method to break down shell waste and isolate the valuable components contained within the shell structure. The fermentation process employed in this study for the bioprocessing of prawn shell waste has achieved several desirable effects. The prawn shells were demineralised to a considerable degree. On average, the shells had 90.99 % of their original calcium removed. Elemental analysis showed that N-values were within a close range of the theoretically ideal chitin nitrogen content proposed in the literature (48).

Biological treatment of minced scampi (*Nephrops norvegicus*) waste supplemented with glucose in a bioreactor using the lactic acid bacterium *Lactobacillus paracasei* strain A3 was performed by Zakaria *et al.* (58). After 5 days of batch culture at 30 °C, high-protein liquid was produced as a result of proteolysis, with solubilisation of 77.5 and 61.0 % of protein and calcium respectively, initially present in the waste material, while the solid fraction contained 17.5 % chitin (on dry mass basis) (58) (Table 3).

The fermentation of shrimp waste by *Lactobacillus plantarum* 541 with and without pH control was examined by Rao *et al.* (25). Among four acids tested (glacial acetic, citric, hydrochloric and lactic acids) to control pH at the start and during fermentation, acetic and citric acids proved to be the most effective. In the presence of an additional carbon source, glucose, 75 % deproteinisation and 86 % demineralisation of biowaste were achieved at pH controlled at 6.0 with acetic acid, while without pH control, 68.1 and 64.1 % deproteinisation and demineralisation respectively, were achieved.

Crayfish (*Procambarus clarkii*) by-products were also used to recover chitin (61). The material was fractionated by sedimentation and flotation into two fractions: a proteinaceous and a chitinous fraction. Deproteinisation and demineralisation yields of the latter fraction by semi-solid state fermentation with *L. paracasei* and supplemented with dextrose were 94.0 and 97.2 %, respectively.

Demineralisation of crayfish (*Procambarus clarkii*) chitinous fraction (exoskeleton) has also been investigated by fed-batch fermentation using immobilized cells of *Lactobacillus pentosus* 4023 (49). Jung *et al.* (56) investigated the demineralisation of red crab (*Chionoecetes japonicus*) shell wastes by a lactic acid bacterium (*Lactobacillus paracasei* ssp. *tolerans* KCTC-3074) fermentation and compared these results with the chemical treatment efficiency using lactic acid. Relative residual ash content rapidly decreased to 49.1 and 16.4 % after 12 h in 5 and 10 % lactic acid, respectively. With 2.5, 5 and 10 % inocula of lactic acid bacteria, the residual ash content rapidly decreased on the first day to 55.2, 40.9 and 44.7 %, respectively. The protein content after demineralisation ranged from 51.3 to 54.7 % after chemical treatment and decreased to 32.3 % after lactic acid fermentation. These results suggested that lactic acid fermentation can be an alternative for crab shell demineralisation, even though demineralisation rate and efficiency were lower than those recorded during chemical treatment (56).

These authors also showed that microbial growth was mainly affected by the concentration of an additional carbon source like glucose instead of increasing the inoculum level. About 80 % of the relative residual ash content was removed over 5 days under the optimal conditions (10 % starter inoculum, 10 % glucose supply, along with 10 % red crab shells at 30 °C). These results confirmed that lactic acid fermentation could provide an alternative to chemical treatment, although a second run or milder acid treatment (such as 0.5 M HCl) may be needed (72).

Use of non-lactic acid bacteria for chitin recovery

Non-lactic acid bacteria have also been tested for chitin recovery. Fermentation of shrimp (*Metapenaeopsis dobsoni*) shell in jaggery broth using *Bacillus subtilis* for the production of chitin and chitosan showed that the level of acid produced as well as the proteolytic activity of *B. subtilis* allowed shell demineralisation and deproteinisation (62). About 84 % of the protein and 72 % of minerals were removed from the shrimp shell after fermentation (Table 3).

Pseudomonas aeruginosa K-187 strain isolated from the soil of northern Taiwan is a producer of protease and chitinase/lysozymes when cultured in a medium containing shrimp and crab shell wastes as the sole carbon sources (49). It was shown that *P. aeruginosa* K-187 is capable of shell waste deproteinisation in either solid-state, liquid-solid or liquid fermentation. Higher deproteinisation yield was recorded in solid-state fermentation, 82 % after 5 days, showing that *P. aeruginosa* K-187 is more efficient than the proteolytic bacterium *P. maltophilia*, known to be highly efficient in the deproteinisation of prawn shell waste. The use of protease produced by *P. aeruginosa* K-187 was therefore promising in deproteinisation of crustacean wastes (49).

Proteolytic enzymes for deproteinisation of crustacean wastes have also been investigated. Oh *et al.* (53) demonstrated that the proteases of *P. aeruginosa* K-187 led under optimal culture conditions to 72 % protein removal for shrimp and crab shell powder after a 7-day incubation, while that of natural shrimp shell and acid-treated shrimp and crab shell powder was 78 and 45 %, respectively. In the case of enzyme immobilization, 67 % deproteinisation of shrimp and crab shell powder was achieved (Table 3). After 7 days of incubation at the optimal temperature of 30 °C, 92 % demineralisation and 63 % deproteinisation of crab shell waste samples inoculated with the newly isolated *P. aeruginosa* F722 were achieved (63).

Deproteinisation and demineralisation of crab (*Chionoecetes opilio*) shell wastes was carried out by Jo *et al.* (64) using *Serratia marcescens* FS-3 isolated from environmental samples (seaside soil in the southwestern area of Korea) which exhibited strong protease activity. The demineralisation and deproteinisation of natural crab shell wastes with 10 % *Serratia marcescens* FS-3 as inoculum was 84 and 47 % after 7 days of fermentation. When the shell waste was treated with 1% Delvolase® (Gist-Brocades, DSM, Heerlen, The Netherlands) as a reference, deproteinisation rate was 90 %. With a combination of 10 % *Serratia marcescens* FS-3 culture supernatant and 1 % Delvolase®, deproteinisation rate of the shell waste was 85 %, while the rate was 81 % in 10 % *Serratia marcescens* FS-3 culture supernatant only (Table 3).

Two bacterial cultures were isolated and tested for the degradation of shrimp shell waste, *Bacillus cereus* and *Exiguobacterium acetylicum* (65). Fermentation of 3 % shell waste at 37 °C with *B. cereus* and *E. acetylicum* allowed to obtain 97.1 and 92.8 % deproteinisation and 95 and 92 % demineralisation, respectively. The protein content was reduced from 18.7 to 5.3 % with *B. cereus* and to 7.3 % with *E. acetylicum*. The high activity of the isolated strains in the decomposition of shrimp shell waste suggests broad potential for environmentally friendly application of these bacteria for chitin extraction from chitin-rich wastes (65).

In the preparation of β -chitin, deproteinisation of squid pen was carried out by means of a protease-producing bacterium isolated and identified as *Bacillus* sp. TKU004 (68). Under optimal conditions for protease production by *Bacillus* sp. TKU004, a deproteinisation yield of 73 % was achieved (Table 3).

Mahmoud *et al.* (73) proposed the use of organic acids (lactic and acetic) produced by cheese whey fermentation to demineralise northern pink shrimp (*Pandalus borealis*) shell wastes biologically deproteinised by fungus *Aspergillus niger* ATCC 16513. This study demonstrated that the effectiveness of lactic and/or acetic acids for shrimp shell demineralisation is similar to that of hydrochloric acid.

Cofermentation of various bacteria for chitin recovery

Chitin purification of *Penaeus monodon* and *Crangon crangon* shells was also tested in a two-step fermentation process involving anaerobic deproteinisation by means of the autochthonous flora of Indonesian shrimp shells and/or proteolytic bacteria from various sources, followed by homofermentative lactic acid fermentation using *L. casei* MRS1 in the second step (11). After deproteinisation and decalcification of *Penaeus monodon* and *Crangon*

shells, the protein content was 5.8 and 6.7 % and the calcium content was 0.3 and 0.4 %, respectively.

Different strategies were applied to extract chitin from prawn waste using a lactic acid-producing bacterium, *L. lactis*, and a protease-producing marine bacterium, *Teredinibacter turnerae* (67). Both bacteria were cultivated individually and cofermented. *L. lactis* removed the inorganic materials efficiently (66.5 % of deproteinisation, 78.8 % of demineralisation, and 52.2 % process yield), while *T. turnerae* was more efficient in deproteinisation (77.8 % of deproteinisation, 23.3 % of demineralisation and 49.2 % process yield) (Table 3). However, the highest process yield (95.5 %) was obtained during cofermentation of both bacteria. Although biological chitin extraction was incomplete compared to the chemical method, the biological treatment employed could still be considered as an alternative, more environmentally benign method (67).

A cofermentation of *L. paracasei* ssp. *tolerans* KCTC-3074 with *Serratia marcescens* FS-3, a protease-producing bacterium, was also tested in order to extract chitin from red crab shell wastes in one step (68). The cofermentation resulted in the highest level of demineralisation (97.2 %), but the level of deproteinisation was only 52.6 % after 7 days (Table 3), showing that cofermentation is applicable in one-step extraction of crude chitin from red crab shell waste, but the improvement of deproteinisation is needed (68). These authors also tested the biological extraction of chitin from red crab shell wastes in successive two-step fermentation involving *L. paracasei* ssp. *tolerans* KCTC-3074 and *Serratia marcescens* FS-3. The successive fermentation in the combination of KCTC-3074 and FS-3 strains gave the best result in the removal of CaCO₃ and proteins from crab shells. In this combination, final demineralisation and deproteinisation yields were 94.3 and 68.9 %, respectively (47).

Proteolytic but chitinase-deficient microbial cultures were isolated from shrimp shell waste and characterized. The most efficient isolate was found to be a mixed culture consisting of two *Bacillus licheniformis* strains. Fermentations were carried out at 42, 50 or 55 °C, 500 rpm and 2 volumes of air per volume of liquid per minute. After 48 h, the fermented shrimp shells were harvested and washed. The final fermentation product was demineralised with 0.9 % lactic acid for 3 h and then oven dried. The results showed more than 99 % deproteinisation and 98.8 % demineralisation (69) (Table 3).

Key factors for shrimp waste demineralisation

Many factors, such as inoculum size, initial pH value, carbon concentration and carbon to nitrogen ratio have been reported to influence the fermentation process and consequently the demineralisation efficiency (46,50).

Fermentation of shrimp (*Penaeus monodon*) biowaste was conducted using different lactic acid bacteria to select the most efficient starter culture based on pH reduction and acid production. *Pediococcus acidilactici* CFR2182 was found to be the most efficient among the five starter cultures tested. Fermentation conditions, inoculum, sugar level and incubation time were optimized using response surface methodology and led to an optimal pH of 4.3±0.1. The optimized conditions for fermentation of shrimp biowaste with *P. acidilactici* were found to be 5 % (by vol-

ume per mass) inoculum, 15 % (by mass) glucose and 72 h incubation time at $(37 \pm 1)^\circ\text{C}$ (final $\text{pH}=4.3$), leading to (97.9 ± 0.3) % deproteinisation and (72.5 ± 1.5) % demineralisation (70).

The type of the carbohydrate was also examined (59). Shrimp (*Penaeus* spp.) waste was fermented with *Lactobacillus* B2 at different amounts (0, 5 and 10 % by volume per mass), as well as different sources (lactose, sucrose and milk whey powder) and levels (10 or 20 % by mass) of carbohydrates. Sucrose was selected as the carbohydrate source in further experimental work due to its better acid production potential as compared to lactose and milk whey powder; it resulted in 56.8 and 63.5 % demineralisation and deproteinisation, respectively.

Various sucrose supplementations were also tested for shrimp shell demineralisation (46), showing that the addition of 5 % of pretreated shrimp shells with a chlorine solution into the culture broth of *Pediococcus* sp. L1/2 containing 50 g/L of sucrose can achieve 83 % demineralisation within 36 h. Further studies indicated that different surface areas of shrimp shell did not affect ash reduction (46).

The effect of the initial glucose concentration and the inoculation level of *L. casei* strain A3 and *Lactobacillus* sp. strain B2 in shrimp (*Penaeus* spp.) fermentation were examined by Shirai *et al.* (50). They showed that high initial glucose (10 %) and starter (5 %) mass fractions reduced the time and increased the amount of lactic acid produced (50).

However, on a commercial scale, glucose addition is an expensive alternative. The use of cheaper sources of carbon may be useful. With this aim, cassava flour in combination with amylolytic lactic acid bacteria was tested (74). Fermentation of shrimp biowaste was conducted with two *L. plantarum* strains under various salt concentrations. The non-amylolytic strain *L. plantarum* 541 and the amylolytic strain *L. plantarum* A6 showed reasonable growth in biowaste in the presence of 6 % salt (74). Higher deproteinisation and demineralisation efficiencies were recorded with strain 541, and were at the utmost 81.4 and 59.8 % under 2 % salt conditions, whereas strain A6 led to 65.5 and 52.2 % demineralisation and deproteinisation, respectively (74).

As another cheaper alternative, date juice was also tested as fermentation medium (57) and compared to glucose. The use of date juice with 208 g/L of total sugar led at best to 44 % demineralisation at 35°C , but with 80 g/L of total sugar deproteinisation was improved at 30°C until an almost total removal (91 %) (57).

The effect of temperature on chitin recovery from a mixture of cephalothoraxes of shrimp species *Litopenaeus vannamei*, *Litopenaeus stylirostris* and *Litopenaeus setiferus* using *L. plantarum* was examined (75). The fermentation was conducted in bed-column reactors at temperatures ranging from 15 to 45°C . Response surface methodology showed the highest demineralisation and deproteinisation yields in the range of 27–36 and $30\text{--}40^\circ\text{C}$. These results corroborate those of Adour *et al.* (57), who found an optimal demineralisation at 35°C .

The effect of crab shell size on biodemineralisation by means of *L. paracasei* ssp. *tolerans* KCTC-3074 was also

investigated (76). Demineralisation was performed using samples with four different particle sizes (0.84–3.35, 3.35–10, 10–20 and 20–35 mm) with 10 % inoculum, 5 % shell and 10 % glucose at 30°C and 180 rpm for 7 days. Shell size had a minor effect on demineralisation efficiency (76).

Applications of Chitin and Chitosan

Natural and non-toxic biopolymers chitin and chitosan are now widely produced commercially from crab and shrimp shell waste. During the past few decades, chitin and chitosan have attracted significant interest in view of a wide range of proposed novel applications (19). Their unique properties, biodegradability, biocompatibility and non-toxicity make them useful for a wide range of applications (Table 4; 1,11,18,29,40,41,44,69,73,75,77–131).

Chitin is mainly used as the raw material to produce chitin-derived products, such as chitosans, oligosaccharides, and glucosamine (1). There are now over 2000 concrete applications, and the field of nutrition is the largest user of chitosan with 1000 tonnes consumed in 2000. The worldwide industrial production of these derivatives in year 2000 is estimated to be above 10 000 tonnes (18).

Wastewater treatment with chitin and chitosan

Chitin and chitosan can be used for the adsorption or fixation of heavy metals (77) and dyes (Table 4). Chitosan is a polycation polymer effective in coagulation, flocculation and dehydration of activated sludge, and hence used in wastewater treatment (16,18). Another recent application is immobilization of microorganisms or sludge in chitosan matrices for wastewater treatment in extreme environmental conditions (extreme pH, presence of organic solvents), allowing the reuse of cells and hence their implementation in continuous process.

Applications of chitin and chitosan in food

Only limited attention has been paid to food application of these versatile biopolymers (96). They offer a wide range of unique applications, which are non-exhaustively listed in Table 4. The use of chitosan in the food industry is related to its functional properties, and nutritional and physiological activities. Chitosan exhibits water-, fat- and dye-binding capacity, as well as emulsifying properties (132); it was shown to be useful in the preparation of stable emulsions without any other surfactant (133). It has been used as a dietary supplement due to some interesting properties (Table 4).

Biomedical application of chitin and chitosan

Chitin and chitosan show excellent biological properties such as non-toxicity (134,135), which is illustrated by a dose limit per day of 17 g/kg (16), biodegradation in the human body (136–138), biocompatibility (139,140), and immunological, antibacterial, wound-healing (102, 141,142) and haemostatic activity (143,144), in cell culture, tissue engineering (103,145–147) and drug delivery (148,149), since it is highly biocompatible and biodegradable in physiological environment (150). Chitin is also used as an excipient and drug carrier in film, gel or powder form for applications involving mucoadhesivity.

Table 4. Applications of chitin, chitosan and their derivatives

| Application area | Specific use | Refs. |
|----------------------|---|-----------------|
| Wastewater treatment | removal/recovery of metal ions from wastewaters, copper, chromium, cadmium, lead, nickel, mercury, iron, silver, zinc, cobalt and arsenic | (78,80–89) |
| | removal and binding of dyes | (90–93) |
| | removal and binding of heavy metals | (1,11,44,77,78) |
| | sludge treatment and dehydration agent | (18) |
| | biological denitrification | (94,95) |
| | | |
| Food | food and nutrition | (73) |
| | bioconversion for the production of value-added food products | (96) |
| | preservation of food | (94) |
| | filmogenic properties – food wrapping | (96,97) |
| | filtration and clarification of fruit juices | (97) |
| | hypolipidemic and hypocholesterolic agent (slimming agent) | (98,99) |
| | antioxidant | (100) |
| | phenolic compound adsorption | (101) |
| | chitosan hydrogels for cell immobilization (lactic acid production) and for pigment encapsulation (astaxanthin) used in aquaculture to give typical salmon colour | (18) |
| | iron extract (to help in preventing bad odours in cooked meat) | (18) |
| Biomedicine | burn and wound dressings for humans and animals | (29,69) |
| | antitumour activity | (102) |
| | drug delivery, gene delivery | (103–105) |
| | artificial skin, pharmacy | (106) |
| | immunostimulating properties in mammals and plants | (107–109) |
| | antiviral and anti- <i>Candida albicans</i> activities | |
| | enhancing specific immunity (adjuvant properties) and stimulation of cytokine production | |
| | ocular drug delivery vehicles in ophthalmology | (110) |
| | as nerve conduit for nerve regeneration due to its ability to facilitate nerve cell attachment | (111) |
| | therapeutic agents in the treatment of tumours (chitin and chitosan conjugates of 5-fluorouracil) | (112,113) |
| | encapsulation applications due to chitosan ability to form gels in the presence of certain divalent cations such as calcium, barium and strontium | (114) |
| | nutraceutical value as a potent antioxidant and matrix metalloproteinase inhibitor <i>via</i> alleviations of radical-induced oxidative damage (water-soluble carboxymethyl derivatives of chitin and chitosan) | (115) |
| | self-hardening paste for guided tissue regeneration in the treatment of periodontal bone defects (hydroxyapatite-chitin-chitosan composite bone-filling material) | (40) |
| Agriculture | spermicide | (112) |
| | plant elicitor | (116) |
| | stimulation of chitinase and glucanase production (increased response to pathogen attack) | (116) |
| | stimulation of chitinase activity in compost (change of bacterial and fungal genetic diversity) | (117) |
| | antimicrobial (antifungal) agent and biopesticide | (118,119) |
| | enhancing plant vitality and ability to degrade walls of fungi upon entry | (120,121) |
| | fertilizer and biocontrol agent | (118,122) |
| Textile and paper | enhancing biocontrol efficiency by addition to plant growth-promoting rhizobacteria | (123–125) |
| | | |
| Textile and paper | textile fibres | (75) |
| | paper manufacture (additive) | (112) |
| Biotechnology | chitin affinity chromatography to selectively adsorb chitinase from a fermentation broth | (112,126) |
| | affinity matrix (chitosan) for the separation of wheat germ agglutinin | (112) |
| | enzyme and whole cell immobilizer | (41,90,127) |
| | <i>N</i> -acetyl chitobiose production from chitin using commercial hydrolytic enzymes | (125) |
| | chitinase and chitosanase production from <i>L. paracasei</i> , <i>Pseudomonas</i> and <i>Streptomyces</i> species | (128–131) |
| | microorganism immobilization for bioremediation of seawater polluted with crude oil | (79) |
| | support for biosensors | (41) |
| | bioseparation | (90,91) |
| Cosmetics | ingredients for hair and skin care (moisturizer) | (112) |

Other applications of chitin and chitosan derivatives

Chitin and chitosan derivatives may effectively reduce soil-borne diseases. In addition, chitin exhibits several functions, including retention of nutrients in the soil, and contributes to the nitrogen cycle (4). Chitin and chitosan have a versatile application potential in agriculture (Table 4). In addition, they have found various other applications (151). Chitin can also be transformed into saccharides under certain conditions (152). It can also be used as a slowly degrading substrate in microbial fuel cells (153).

Conclusions

The importance of biopolymers chitin and chitosan resides in their biological (biodegradability, biocompatibility and non-toxicity) and physicochemical properties (degree of acetylation and molecular mass). These unique properties offer many potential applications in different fields. Recently, they have been widely applied in agriculture, medicine, pharmaceuticals, food processing, environmental protection and biotechnology.

The recovery of chitin by chemical method using concentrated acids and bases in order to deproteinise and to demineralise shellfish waste (the most industrially exploited) at high temperature can deteriorate the physicochemical properties of this biopolymer and consequently its biological properties, which results in products of varying quality that are neither homogeneous nor reproducible. Biotechnology offers the opportunity to preserve the exceptional qualities of chitin and its derivatives. Nowadays, a new method based on the use of lactic acid bacteria and/or proteolytic bacteria has been used for chitin extraction. This method allows to produce a good quality chitin; it also leads to a liquid fraction rich in proteins which can be used for human and animal feed, and also produces pigments, mainly asthaxanthin.

Although the biological method seems to be a promising approach for demineralisation and deproteinisation, the use of this method is still limited to laboratory scale because demineralisation and deproteinisation have not yet reached the desired yields if compared to the chemical method. The physicochemical conditions that influence the fermentation are the keyfactors of this bioprocess. Determination of the optimal conditions for biodeproteinisation and biodemineralisation of shells, the use of an effective bacterium and an inexpensive carbon source are the main factors which have to be considered to optimize chitin recovery from shellfish waste by fermentation.

References

1. A. Einbu, K.M. Vårum, Characterization of chitin and its hydrolysis to GlcNAc and GlcN, *Biomacromolecules*, 9 (2008) 1870–1875.
2. H. Sato, S.I. Mizutani, S. Tsuge, H. Ohtani, K. Aoi, A. Takasu *et al.*, Determination of the degree of acetylation of chitin/chitosan by pyrolysis-gas chromatography in the presence of oxalic acid, *Anal. Chem.* 70 (1998) 7–12.
3. Y. Kikkawa, H. Tokuhisa, H. Shingai, T. Hiraishi, H. Houjou, M. Kanesato *et al.*, Interaction force of chitin-binding domains onto chitin surface, *Biomacromolecules*, 9 (2008) 2126–2131.
4. F. Shahidi, R. Abuzaytoun, Chitin, chitosan, and co-products: Chemistry, production, applications, and health effects, *Adv. Food Nutr. Res.* 49 (2005) 93–135.
5. X. Wang, B. Xing, Importance of structural makeup of biopolymers for organic contaminant sorption, *Environ. Sci. Technol.* 41 (2007) 3559–3565.
6. G.W. Gooday, J.I. Prosser, K. Hillman, M.G. Cross, Mineralization of chitin in an estuarine sediment: The importance of the chitosan pathway, *Biochem. Syst. Ecol.* 19 (1991) 395–400.
7. K.G. Nair, A. Dufresne, Crab shell chitin whisker reinforced natural rubber nanocomposites. 1. Processing and swelling behavior, *Biomacromolecules*, 4 (2003) 657–665.
8. G.T. Kjartansson, S. Zivanovic, K. Kristbergsson, J. Weiss, Sonication-assisted extraction of chitin from North Atlantic shrimps (*Pandalus borealis*), *J. Agric. Food Chem.* 54 (2006) 5894–5902.
9. K.L.B. Chang, G. Tsai, Response surface optimization and kinetics of isolating chitin from pink shrimp (*Solenocera melanthero*) shell waste, *J. Agric. Food Chem.* 45 (1997) 1900–1904.
10. J.S. Mojarrad, N. Nemati, H. Valizadeh, M. Ansarin, S. Bourbour, Preparation of glucosamine from exoskeleton of shrimp and predicting production yield by response surface methodology, *J. Agric. Food. Chem.* 55 (2007) 2246–2250.
11. Y. Xu, C. Gallert, J. Winter, Chitin purification from shrimp wastes by microbial deproteination and decalcification, *Appl. Microbiol. Biotechnol.* 79 (2008) 687–697.
12. X. Zhai, S.J. Hawkins, Interactions of aquaculture and waste disposal in the coastal zone, *J. Ocean Univ. China*, 1 (2002) 8–12.
13. M. Gimeno, J.Y. Ramírez-Hernández, C. Martínez-Ibarra, N. Pacheco, R. García-Arrazola, E. Bárzana, K. Shirai, One-solvent extraction of astaxanthin from lactic acid fermented shrimp wastes, *J. Agric. Food Chem.* 55 (2007) 10345–10350.
14. S.L. Wang, T.J. Chang, T.W. Liang, Conversion and degradation of shellfish wastes by *Serratia* sp. TKU016 fermentation for the production of enzymes and bioactive materials, *Biodegradation*, 21 (2010) 321–333.
15. C.F.V. Hobel, Access to biodiversity and new genes from thermophiles by special enrichment methods, *PhD Thesis*, University of Iceland, Reykjavik, Iceland (2004).
16. G. Crini, E. Guibal, M. Morcellet, G. Torri, P.M. Badot: Chitin and Chitosan. Preparation, Properties and Main Applications. In: *Chitin and Chitosan. Application of Some Biopolymers*, University Press of Franche-Comté, Besançon, France (2009) pp. 19–54 (in French).
17. G.H. Jo, R.D. Park, W.J. Jung: Enzymatic Production of Chitin from Crustacean Shell Waste. In: *Chitin, Chitosan, Oligosaccharides and Their Derivatives*, S.K. Kim (Ed.), CRC Press, Taylor & Francis Group, Boca Raton, FL, USA (2011) pp. 37–45.
18. K. Kurita, Chitin and chitosan: Functional biopolymers from marine crustaceans, *Marine Biotechnol.* 8 (2006) 203–226.
19. Y.I. Cho, H.K. No, S.P. Meyers, Physicochemical characteristics and functional properties of various commercial chitin and chitosan products, *J. Agric. Food Chem.* 46 (1998) 3839–3843.
20. A.D. Handayani, Sutrisno, N. Indraswati, S. Ismadij, Extraction of astaxanthin from giant tiger (*Panaeus monodon*) shrimp waste using palm oil: Studies of extraction kinetics and thermodynamic, *Bioresour. Technol.* 99 (2008) 4414–4419.
21. N.M. Sachindra, N. Bhaskar, G.S. Siddegowda, A.D. Sathisha, P.V. Suresh, Recovery of carotenoids from ensilaged shrimp waste, *Bioresour. Technol.* 98 (2007) 1642–1646.

22. A. Khanafari, R. Marandi, S. Sanatei, Recovery of chitin and chitosan from shrimp waste by chemical and microbial methods, *Iran J. Environ. Health Sci. Eng.* 5 (2008) 19–24.
23. S. Das, E.G. Anand Ganesh, Extraction of chitin from trash crabs (*Podophthalmus vigil*) by an eccentric method, *Curr. Res. J. Biol. Sci.* 2 (2010) 72–75.
24. M. Bajaj, J. Winter, C. Gallert, Effect of deproteinisation and deacetylation conditions on viscosity of chitin and chitosan extracted from *Crangon crangon* shrimp waste, *Biochem. Eng. J.* 56 (2011) 51–62.
25. M.S. Rao, J. Muñoz, W.F. Stevens, Critical factors in chitin production by fermentation of shrimp biowaste, *Appl. Microbiol. Biotechnol.* 54 (2000) 808–813.
26. J.D. Goodrich, W.T. Winter, α -Chitin nanocrystals prepared from shrimp shells and their specific surface area measurement, *Biomacromolecules*, 8 (2007) 252–257.
27. A. Einbu, S.N. Naess, A. Elgsaeter, K.M. Vårum, Solution properties of chitin in alkali, *Biomacromolecules*, 5 (2004) 2048–2054.
28. S. Ifuku, M. Nogi, K. Abe, M. Yoshioka, M. Morimoto, H. Saimoto, H. Yano, Preparation of chitin nanofibers with a uniform width as α -chitin from crab shells, *Biomacromolecules*, 10 (2009) 1584–1588.
29. A. Percot, C. Viton, A. Domard, Optimization of chitin extraction from shrimp shells, *Biomacromolecules*, 4 (2003) 12–18.
30. F.A. Al Sagheer, M.A. Al-Sughayer, S. Muslim, M. Elsabee, Extraction and characterization of chitin and chitosan from marine sources in Arabian Gulf, *Carbohydr. Polym.* 77 (2009) 410–419.
31. P. Sorlier, A. Denuzière, C. Viton, A. Domard, Relation between the degree of acetylation and the electrostatic properties of chitin and chitosan, *Biomacromolecules*, 2 (2001) 765–772.
32. H.K. No, S.H. Lee, N.Y. Park, S.P. Meyers, Comparison of physicochemical, binding, and antibacterial properties of chitosans prepared without and with deproteinization process, *J. Agric. Food Chem.* 51 (2003) 7659–7663.
33. Y. Suzuki, Y. Okamoto, M. Morimoto, H. Sashiwa, H. Saimoto, S.I. Tanioka *et al.*, Influence of physico-chemical properties of chitin and chitosan on complement activation, *Carbohydr. Polym.* 42 (2000) 307–310.
34. A. Tolaimate, J. Desbrières, M. Rhazi, A. Alagui, M. Vincendon, P. Vottero, On the influence of deacetylation process on the physicochemical characteristics of chitosan from squid chitin, *Polymer*, 41 (2000) 2463–2469.
35. Y. Zhang, C. Xue, Y. Xue, R. Gao, X. Zhang, Determination of the degree of deacetylation of chitin and chitosan by X-ray powder diffraction, *Carbohydr. Res.* 340 (2005) 1914–1917.
36. M. Dash, F. Chiellini, R.M. Ottenbrite, E. Chiellini, Chitosan – A versatile semi-synthetic polymer in biomedical applications, *Prog. Polym. Sci.* 36 (2011) 981–1014.
37. M.R. Kasaai, Various methods for determination of the degree of *N*-acetylation of chitin and chitosan: A review, *J. Agric. Food Chem.* 57 (2009) 1667–1676.
38. E. Khor: *Chitin: Fulfilling a Biomaterials Promise*, Elsevier Science, Amsterdam, The Netherlands (2001).
39. N. Dahiya, R. Tewari, G.S. Hoondal, Biotechnological aspects of chitinolytic enzymes: A review, *Appl. Microbiol. Biotechnol.* 71 (2006) 773–782.
40. Y. Noishiki, H. Takami, Y. Nishiyama, M. Wadaa, S. Okada, S. Kuga, Alkali-induced conversion of β -chitin to α -chitin, *Biomacromolecules*, 4 (2003) 896–899.
41. M. Rinaudo, Chitin and chitosan: Properties and applications, *Prog. Polym. Sci.* 31 (2006) 603–632.
42. T.G. Liu, B. Li, W. Huang, B. Lv, J. Chen, J.X. Zhang, L.P. Zhu, Effects and kinetics of a novel temperature cycling treatment on the *N*-deacetylation of chitin in alkaline solution, *Carbohydr. Polym.* 77 (2009) 110–117.
43. M.R. Kasaai, Determination of the degree of *N*-acetylation for chitin and chitosan by various NMR spectroscopy techniques: A review, *Carbohydr. Polym.* 79 (2010) 801–810.
44. H.K. No, E.Y. Hur, Control of foam formation by antifoam during demineralization of crustacean shell in preparation of chitin, *J. Agric. Food Chem.* 46 (1998) 3844–3846.
45. J. Bautista, M. Jover, J.F. Guttierrez, R. Corpas, O. Cremades, E. Fontiveros *et al.*, Preparation of crayfish chitin by *in situ* lactic acid production, *Process Biochem.* 37 (2001) 229–234.
46. W. Choorit, W. Patthanamane, S. Manurakchinakorn, Use of response surface method for the determination of demineralization efficiency in fermented shrimp shells, *Bioreour. Technol.* 99 (2008) 6168–6173.
47. W.J. Jung, G.H. Jo, J.H. Kuk, Y.J. Kim, K.T. Oh, R.D. Park, Production of chitin from red crab shell waste by successive fermentation with *Lactobacillus paracasei* KCTC-3074 and *Serratia marcescens* FS-3, *Carbohydr. Polym.* 68 (2007) 746–750.
48. M. Healy, A. Green, A. Healy, Bioprocessing of marine crustacean shell waste, *Acta Biotechnol.* 23 (2003) 151–160.
49. S.L. Wang, S.H. Chio, Deproteinization of shrimp and crab shell with the protease of *Pseudomonas aeruginosa* K-187 – Waste pretreatment, enzyme production, process design, and economic analysis, *Enzyme Microb. Technol.* 22 (1998) 629–633.
50. K. Shirai, I. Guerrero, S. Huerta, G. Saucedo, A. Casillo, G.R. Obdulia, M.G. Hall, Effect of initial glucose concentration and inoculation level of lactic acid bacteria in shrimp waste ensilation, *Enzyme Microb. Technol.* 28 (2001) 446–452.
51. A.U. Valdez-Peña, J.D. Espinoza-Perez, G.C. Sandoval-Fabian, N. Balagurusamy, A. Hernandez-Rivera, J.M. de-la-Garza-Rodriguez, J.C. Contreras-Esquivel, Screening of industrial enzymes for deproteinization of shrimp head for chitin recovery, *Food Sci. Biotechnol.* 19 (2010) 553–557.
52. J. Synowiecki, N.A.A.Q. Al-Khateeb, The recovery of protein hydrolysate during enzymatic isolation of chitin from shrimp *Crangon crangon* processing discards – Commercial uses and potential application, *Food Chem.* 68 (2000) 147–152.
53. Y.S. Oh, I.L. Shih, Y.M. Tzeng, S.L. Wang, Protease produced by *Pseudomonas aeruginosa* K-187 and its application in the deproteinization of shrimp and crab shell wastes, *Enzyme Microb. Technol.* 27 (2000) 3–10.
54. J.K. Yang, I.L. Shih, Y.M. Tzeng, S.L. Wang, Production and purification of protease from a *Bacillus subtilis* that can deproteinize crustacean wastes, *Enzyme Microb. Technol.* 26 (2000) 406–413.
55. K. Prameela, C.M. Mohan, P.V. Smitha, K.P.J. Hemalatha, Bioremediation of shrimp biowaste by using natural probiotic for chitin and carotenoid production an alternative method to hazardous chemical method, *IJABPT*, 1 (2010) 903–910.
56. W.J. Jung, J.H. Kuk, K.Y. Kim, R.D. Park, Demineralization of red crab shell waste by lactic acid fermentation, *Appl. Microbiol. Biotechnol.* 67 (2005) 851–854.
57. L. Adour, W. Arbia, A. Amrane, N. Mameri, Combined use of waste materials – Recovery of chitin from shrimp shells by lactic acid fermentation supplemented with date juice waste or glucose, *J. Chem. Technol. Biotechnol.* 83 (2008) 1664–1669.
58. Z. Zakaria, G.M. Hall, G. Shama, Lactic acid fermentation of scampi waste in a rotating horizontal bioreactor for chitin recovery, *Process Biochem.* 33 (1997) 1–6.

59. L.A. Cira, S. Huerta, G.M. Hall, K. Shirai, Pilot scale lactic acid fermentation of shrimp wastes for chitin recovery, *Process Biochem.* 37 (2002) 1359–1366.
60. M.G. Healy, C.R. Romo, R. Bustos, Bioconversion of marine crustacean shell waste, *Resour. Conserv. Recycl.* 11 (1994) 139–147.
61. O. Cremades, E. Ponce, R. Corpas, J.F. Gutiérrez, M. Jover, M.C. Alvarez-Ossorio *et al.*, Processing of crawfish (*Procambarus clarkii*) for the preparation of carotenoproteins and chitin, *J. Agric. Food Chem.* 49 (2001) 5468–5472.
62. T.K. Sini, S. Santhosh, P.T. Mathew, Study on the production of chitin and chitosan from shrimp shell by using *Bacillus subtilis* fermentation, *Carbohydr. Res.* 342 (2007) 2423–2429.
63. K.T. Oh, Y.J. Kim, V.N. Nguyen, W.J. Jung, R.D. Park, Demineralization of crab shell waste by *Pseudomonas aeruginosa* F722, *Process Biochem.* 42 (2007) 1069–1074.
64. G.H. Jo, W.J. Jung, J.H. Kuk, K.T. Oh, Y.J. Kim, R.D. Park, Screening of protease-producing *Serratia marcescens* FS-3 and its application to deproteinization of crab shell waste for chitin extraction, *Carbohydr. Polym.* 74 (2008) 504–508.
65. I. Sorokulova, A. Krumnow, L. Globa, V. Vodyanoy, Efficient decomposition of shrimp shell waste using *Bacillus cereus* and *Exiguobacterium acetylicum*, *J. Ind. Microbiol. Biotechnol.* 36 (2009) 1123–1126.
66. S.L. Wang, T.Y. Kao, C.L. Wang, Y.H. Yen, M.K. Chern, Y.H. Chen, A solvent stable metalloprotease produced by *Bacillus* sp. TKU004 and its application in the deproteinization of squid pen for β -chitin preparation, *Enzyme Microb. Technol.* 39 (2006) 724–731.
67. O. Aytakin, M. Elibol, Cocultivation of *Lactococcus lactis* and *Teredinobacter turnirae* for biological chitin extraction from prawn waste, *Bioprocess Biosyst. Eng.* 33 (2010) 393–399.
68. W.J. Jung, G.H. Jo, J.H. Kuk, K.Y. Kim, R.D. Park, Extraction of chitin from red crab shell waste by cofermentation with *Lactobacillus paracasei* subsp. *tolerans* KCTC-3074 and *Serratia marcescens* FS-3, *Appl. Microbiol. Biotechnol.* 71 (2006) 234–237.
69. J. Waldeck, G. Daum, B. Bisping, F. Meinhardt, Isolation and molecular characterization of chitinase-deficient *Bacillus licheniformis* strains capable of deproteinization of shrimp shell waste to obtain highly viscous chitin, *Appl. Environ. Microbiol.* 72 (2006) 7879–7885.
70. N. Bhaskar, P.V. Suresh, P.Z. Sakhare, N.M. Sachindra, Shrimp biowaste fermentation with *Pediococcus acidolactici* CFR2182: Optimization of fermentation conditions by response surface methodology and effect of optimized conditions on deproteinization/demineralization and carotenoid recovery, *Enzyme Microb. Technol.* 40 (2007) 1427–1434.
71. O.A. Fagbenro, Preparation, properties and preservation of lactic acid fermented shrimp heads, *Food Res. Int.* 29 (1996) 595–599.
72. W.J. Jung, G.H. Jo, J.H. Kuk, K.Y. Kim, R.D. Park, Demineralization of crab shells by chemical and biological treatments, *Biotechnol. Bioprocess Eng.* 10 (2005) 67–72.
73. N.S. Mahmoud, A.E. Ghaly, F. Arab, Unconventional approach for demineralization of deproteinized crustacean shells for chitin production, *Am. J. Biochem. Biotechnol.* 3 (2007) 1–9.
74. M.S. Rao, W.F. Stevens, Fermentation of shrimp biowaste under different salt concentrations with amylolytic and non-amylolytic *Lactobacillus* strains for chitin production, *Food Technol. Biotechnol.* 44 (2006) 83–87.
75. N. Pacheco, M. Garnika-González, J.Y. Ramírez Hernández, B. Flores-Albino, M. Gimeno, E. Bárzana, K. Shirai, Effect of temperature on chitin and astaxanthin recoveries from shrimp waste using lactic acid bacteria, *Bioresour. Technol.* 100 (2009) 2849–2854.
76. K.T. Oh, Y.J. Kim, V.N. Nguyen, W.J. Jung, R.D. Park, Effect of crab shell size on bio-demineralization with lactic acid-producing bacterium, *Lactobacillus paracasei* subsp. *tolerans* KCTC-3074, *Biotechnol. Bioprocess Eng.* 13 (2008) 566–570.
77. A. Bhatnagar, M. Sillanpää, Applications of chitin- and chitosan-derivatives for the detoxification of water and wastewater – A short review, *Adv. Colloid Interface Sci.* 152 (2009) 26–38.
78. G. Camci-Unal, N.L.B. Pohl, Quantitative determination of heavy metal contaminant complexation by the carbohydrate polymer chitin, *J. Chem. Eng. Data*, 55 (2009) 1117–1121.
79. A.R. Gentili, M.A. Cubitto, M. Ferrero, M.S. Rodríguez, Bioremediation of crude oil polluted seawater by a hydrocarbon-degrading bacterial strain immobilized on chitin and chitosan flakes, *Int. Biodeter. Biodegr.* 57 (2006) 222–228.
80. D. Zhou, L. Zhang, S. Guo, Mechanisms of lead biosorption on cellulose/chitin beads, *Water Res.* 39 (2005) 3755–3762.
81. A. Baran, E. Biçak, .H. Baysal, S. Önal, Comparative studies on the adsorption of Cr(VI) ions on to various sorbents, *Bioresour. Technol.* 98 (2007) 661–665.
82. R. Schmuhl, H.M. Krieg, K. Keizer, Adsorption of Cu(II) and Cr(VI) ions by chitosan: Kinetics and equilibrium studies, *Water SA*, 27 (2001) 1–7.
83. M. González-Dávila, J.M. Santana-Casiano, F.J. Millero, The adsorption of Cd(II) and Pb(II) to chitin in seawater, *J. Colloid Interface Sci.* 137 (1990) 102–110.
84. J.R. Evans, W.G. Davids, J.D. MacRae, A. Amirbahman, Kinetics of cadmium uptake by chitosan-based crab shells, *Water Res.* 36 (2002) 3219–3226.
85. H. Benaissa, B. Benguella, Effect of anions and cations on cadmium sorption kinetics from aqueous solutions by chitin: Experimental studies and modeling, *Environ. Pollut.* 130 (2004) 157–163.
86. A.T. Paulino, F.A.S. Minasse, M.R. Guilherme, A.V. Reis, E.C. Muniz, J. Nozaki, Novel adsorbent based on silkworm chrysalides for removal of heavy metals from wastewaters, *J. Colloid Interface Sci.* 301 (2006) 479–487.
87. O.S. Amuda, A.A. Giwa, I. Bello, Removal of heavy metal from industrial wastewater using modified activated coconut shell carbon, *Biochemical Eng. J.* 36 (2007) 174–181.
88. K.D. Trimukhe, A.J. Varma, Complexation of heavy metals by crosslinked chitin and its deacetylated derivatives, *Carbohydr. Polym.* 71 (2008) 66–73.
89. S.N. Kartal, Y. Imamura, Removal of copper, chromium, and arsenic from CCA-treated wood onto chitin and chitosan, *Bioresour. Technol.* 96 (2005) 389–392.
90. H.K. No, Y.I. Cho, S.P. Meyers, Dye binding capacity of commercial chitin products, *J. Agric. Food Chem.* 44 (1996) 1939–1942.
91. E. Longhinotti, F. Pozza, L. Furlan, M. de N. de M. Sanchez, M. Klug, M.C.M. Laranjeira, V.T. Fávere, Adsorption of anionic dyes on the biopolymer chitin, *J. Braz. Chem. Soc.* 9 (1998) 435–440.
92. G. Crini, P.M. Badot, Application of chitosan, a natural aminopolysaccharide, for dye removal from aqueous solutions by adsorption processes using batch studies: A review of recent literature, *Progr. Polym. Sci.* 33 (2008) 399–447.
93. G. Akkaya, I. Uzun, F. Güzel, Adsorption of some highly toxic dyestuffs from aqueous solution by chitin and its synthesized derivatives, *Desalination*, 249 (2009) 1115–1123.
94. E.I. Rabea, E.T.M. Badawy, C.V. Stevens, G. Smagghe, W. Steurbaut, Chitosan as antimicrobial agent: Applications and mode of action, *Biomacromolecules*, 4 (2003) 1457–1465.
95. M.A. Robinson-Lora, R.A. Brennan, The use of crab-shell chitin for biological denitrification: Batch and column tests, *Bioresour. Technol.* 100 (2009) 534–541.

96. F. Shahidi, J.K.V. Arachchi, Y.J. Jeon, Food applications of chitin and chitosans, *Trends Food Sci. Technol.* 10 (1999) 37–51.
97. S. Chatterjee, S. Chatterjee, B.P. Chatterjee, A.K. Guha, Clarification of fruit juice with chitosan, *Process Biochem.* 39 (2004) 2229–2232.
98. O. Kanauchi, K. Deuchi, Y. Imasato, E. Kobayashi, Increasing effect of a chitosan and ascorbic acid mixture on fecal dietary fat excretion, *Biosci. Biotech. Biochem.* 58 (1994) 1617–1620.
99. A.S. Chen, T. Taguchi, K. Sakai, Y. Matahira, M.W. Wang, I. Miwa, Effects of chitobiose and chitotriose on carbon tetrachloride-induced acute hepatotoxicity in rats, *Biol. Pharm. Bull.* 28 (2005) 1971–1973.
100. M.T. Yen, J.H. Yang, J.L. Mau, Physicochemical characterization of chitin and chitosan from crab shells, *Carbohydr. Polym.* 75 (2009) 15–21.
101. G. Spagna, P.G. Pifferi, C. Rangoni, F. Mattivi, G. Nicolini, R. Palmonari, The stabilization of white wines by adsorption of phenolic compounds on chitin and chitosan, *Food Res. Int.* 29 (1996) 241–248.
102. S.S. Koide, Chitin-chitosan: Properties, benefits and risks, *Nutr. Res.* 18 (1998) 1091–1101.
103. H. Nagahama, T. Kashiki, N. Nwe, R. Jayakumar, T. Furukake, H. Tamura, Preparation of biodegradable chitin/gelatin membranes with GlcNAc for tissue engineering applications, *Carbohydr. Polym.* 73 (2008) 456–463.
104. S. Özbas-Turan, C. Aral, L. Kabasakal, M. Keyer-Uysal, J. Akbuga, Co-encapsulation of two plasmids in chitosan microspheres as a non-viral gene delivery vehicle, *J. Pharm. Pharmaceut. Sci.* 6 (2003) 27–32.
105. P.V. Suresh, M. Chandrasekaran, Utilization of prawn waste for chitinase production by the marine fungus *Beauveria bassiana* by solid state fermentation, *World J. Microb. Biotechnol.* 14 (1998) 655–660.
106. E.F. Franca, R.D. Lins, L.C.G. Freitas, T.P. Straatsma, Characterization of chitin and chitosan molecular structure in aqueous solution, *J. Chem. Theory Comput.* 4 (2008) 2141–2149.
107. M. Otterlei, K.M. Vårum, L. Ryan, T. Espevik, Characterization of binding and TNF- α -inducing ability of chitosans on monocytes: The involvement of CD14, *Vaccine*, 12 (1994) 825–832.
108. S. Gogev, M.F. Versali, E. Thiry, Chitosans – Novel mucosal adjuvants for vaccination animals, *Ann. Med. Vet.* 147 (2003) 343–350 (in French).
109. A. Cuesta, A.M. Esteban, J. Meseguer, *In vitro* effect of chitin particles on the innate cellular immune system of gilt-head seabream (*Sparus aurata* L.), *Fish Shellfish Immunol.* 15 (2003) 1–11.
110. I. Morfin, P. Hazot, F. Guillot, C. Soler, C. Korwin-Zmiowska, K. Tahiri *et al.*, Percolating hydrogels for tissue engineering, *Eur. Cells Mater.* 4 (2002) 55–56.
111. R.A.A. Muzzarelli, C. Muzzarelli, Chitosan Chemistry: Relevance to the biomedical sciences, *Adv. Polym. Sci.* 186 (2005) 151–209.
112. P.A. Felse, T. Panda, Studies on applications of chitin and its derivatives, *Bioprocess Eng.* 20 (1999) 505–512.
113. A.B. Dhanikula, R. Panchagnula, Development and characterization of biodegradable chitosan films for local delivery of paclitaxel, *AAPS J.* 6 (2004) 88–89.
114. J. Han, A.S. Guenier, S. Salmieri, M. Lacroix, Alginate and chitosan functionalization for micronutrient encapsulation, *J. Agric. Food Chem.* 56 (2008) 2528–2535.
115. C.S. Kong, J.A. Kim, B. Ahn, H.G. Byun, S.K. Kim, Carboxymethylations of chitosan and chitin inhibit MMP expression and ROS scavenging in human fibrosarcoma cells, *Process Biochem.* 45 (2010) 179–186.
116. E. Ait Barka, P. Eullaffroy, C. Clément, G. Vernet, Chitosan improves development, and protects *Vitis vinifera* L. against *Botrytis cinerea*, *Plant Cell Rep.* 22 (2004) 608–614.
117. P.H.B. Poulsen, J. Møller, J. Magid, Determination of a relationship between chitinase activity and microbial diversity in chitin amended compost, *Bioresour. Technol.* 99 (2008) 4355–4359.
118. S.L. Wang, Y.H. Yen, G.C. Tzeng, C. Hsieh, Production of antifungal materials by bioconversion of shellfish chitin wastes fermented by *Pseudomonas fluorescens* K-188, *Enzyme Microb. Technol.* 36 (2005) 49–56.
119. W. San-Lang, I.L. Shih, C.H. Wang, K.C. Tseng, W.T. Chang, Y.K. Twu *et al.*, Production of antifungal compounds from chitin by *Bacillus subtilis*, *Enzyme Microb. Technol.* 31 (2002) 321–328.
120. A.A. Bell, J.C. Hubbard, L. Liu, R.M. Davis, K.V. Subbarao, Effects of chitin and chitosan on the incidence and severity of Fusarium yellows of celery, *Plant Dis.* 82 (1998) 322–328.
121. J. Hallmann, R. Rodríguez-Kábana, J.W. Kloepper, Chitin-mediated changes in bacterial communities of the soil, rhizosphere and within roots of cotton in relation to nematode control, *Soil Biol. Biochem.* 31 (1999) 551–560.
122. R. Vivekananthan, M. Ravi, D. Saravanakumar, N. Kumar, V. Prakasam, R. Samiyappan, Microbially induced defense related proteins against postharvest anthracnose infection in mango, *Crop Prot.* 23 (2004) 1061–1067.
123. R. Bharathi, R. Vivekananthan, S. Harish, A. Ramanathan, R. Samiyappan, Rhizobacteria-based bio-formulations for the management of fruit rot infection in chilies, *Crop Prot.* 23 (2004) 835–843.
124. L. Ge, H. Zhang, K. Chen, L. Ma, Z. Xu, Effect of chitin on the antagonistic activity of *Rhodotorula glutinis* against *Botrytis cinerea* in strawberries and the possible mechanisms involved, *Food Chem.* 120 (2010) 490–495.
125. T. Yu, L. Wang, Y. Yin, Y. Wang, X. Zheng, Effect of chitin on the antagonistic activity of *Cryptococcus laurentii* against *Penicillium expansum* in pear fruit, *Int. J. Food Microbiol.* 122 (2008) 44–48.
126. P.M. Kao, C.I. Chen, S.C. Huang, K.M. Lin, Y.C. Chang, Y.C. Liu, Preparation of fermentation-processed chitin and its application in chitinase affinity adsorption, *Process Biochem.* 44 (2009) 343–348.
127. B. Krajewska, Application of chitin- and chitosan-based materials for enzyme immobilizations: A review, *Enzyme Microb. Technol.* 35 (2004) 126–139.
128. S.L. Wang, S.J. Chen, C.L. Wang, Purification and characterization of chitinases and chitosanases from a new species strain *Pseudomonas* sp. TKU015 using shrimp shells as a substrate, *Carbohydr. Res.* 343 (2008) 1171–1179.
129. S.L. Wang, T.Y. Huang, C.Y. Wang, T.W. Liang, Y.H. Yen, Y. Sakata, Bioconversion of squid pen by *Lactobacillus paracasei* subsp. *paracasei* TKU010 for the production of proteases and lettuce growth enhancing biofertilizers, *Bioresour. Technol.* 99 (2008) 5436–5443.
130. K.J. Kim, Y.J. Yang, K.G. Kim, Purification and characterization of chitinase from *Streptomyces* sp. M-20, *J. Biochem. Mol. Biol.* 36 (2003) 185–189.
131. H. Schrempf, Recognition and degradation of chitin by streptomycetes, *Antonie van Leeuwenhoek*, 79 (2001) 285–289.
132. M.S. Rodríguez, L.A. Albertengo, E. Agulló, Emulsification capacity of chitosan, *Carbohydr. Polym.* 48 (2002) 271–276.
133. V. Speiciene, F. Guilmineau, U. Kulozik, D. Leskauskaitė, The effect of chitosan on the properties of emulsions stabilized by whey proteins, *Food Chem.* 102 (2007) 1048–1054.

134. M.N.V. Ravi Kumar, A review of chitin and chitosan applications, *React. Funct. Polym.* 46 (2000) 1–27.
135. M. Morimoto, H. Saimoto, Y. Shigemasa, Control of functions of chitin and chitosan by chemical modification, *Trends Glycosci. Glycotech.* 14 (2002) 205–222.
136. R.S. Patil, V. Ghormade, M.V. Deshpande, Chitinolytic enzymes: An exploration, *Enzyme Microb. Technol.* 26 (2000) 473–483.
137. H. Sashiwa, H. Yajima, S.I. Aiba, Synthesis of a chitosan-dendrimer hybrid and its biodegradation, *Biomacromolecules*, 4 (2003) 1244–1249.
138. Y.P. Yang, X.H. Xu, H.F. Chen, Treatment of chitin-producing wastewater by micro-electrolysis-contact oxidation, *J. Zhejiang Univ. Sci.* 5 (2004) 436–440.
139. Y. Bal, K.E. Bal, O. Laarabi-Bouamrane, A. Lallam, Copper(II) uptake by *Pleurotus mutilus* biomass, chitin and chitosan, *Mineral Eng.* 19 (2006) 1456–1458.
140. J. Majtán, K. Bíliková, O. Markovič, J. Gróf, G. Kogan, J. Šimúth, Isolation and characterization of chitin from bumblebee (*Bombus terrestris*), *Int. J. Biol. Macromol.* 40 (2007) 237–241.
141. E. Khor, Chitin: A biomaterial in waiting, *Curr. Opin. Solid State Mater. Sci.* 6 (2002) 313–317.
142. C. Muzzarelli, O. Francescangeli, G. Tosi, R.A.A. Muzzarelli, Susceptibility of dibutyl chitin and regenerated chitin fibres to deacylation and depolymerization by lipases, *Carbohydr. Polym.* 56 (2004) 137–146.
143. P. Vongchan, W. Sajomsang, W. Kasinrerak, D. Subyen, P. Kongtawelert, Anticoagulant activities of the chitosan polysulfate synthesized from marine crab shell by semi-heterogeneous conditions, *Sci. Asia*, 29 (2003) 115–120.
144. R. Jayakumar, N. Nwe, S. Tokura, H. Tamura, Sulfated chitin and chitosan as novel biomaterials, *Int. J. Biol. Macromol.* 40 (2007) 175–181.
145. H. Sashiwa, S.I. Aiba, Chemically modified chitin and chitosan as biomaterials, *Prog. Polym. Sci.* 29 (2004) 887–908.
146. Y. Maeda, R. Jayakumar, H. Nagahama, T. Furuike, H. Tamura, Synthesis, characterization and bioactivity studies of novel β -chitin scaffolds for tissue-engineering applications, *Int. J. Biol. Macromol.* 42 (2008) 463–467.
147. H. Nagahama, N. Nwe, R. Jayakumar, S. Koiwa, T. Furuike, H. Tamura, Novel biodegradable chitin membranes for tissue engineering applications, *Carbohydr. Polym.* 73 (2008) 295–302.
148. T.L. Yang, Chitin-based materials in tissue engineering: Applications in soft tissue and epithelial organ, *Int. J. Mol. Sci.* 12 (2011) 1936–1963.
149. F.L. Mi, Y.M. Lin, Y.B. Wu, S.S. Shyu, Y.H. Tsai, Chitin/PLGA blend microspheres as a biodegradable drug-delivery system: Phase-separation, degradation and release behavior, *Biomaterials*, 23 (2002) 3257–3267.
150. S. Nsereko, M. Amiji, Localized delivery of paclitaxel in solid tumors from biodegradable chitin microparticle formulations, *Biomaterials*, 23 (2002) 2723–2731.
151. K.V. Harish Prashanth, R.N. Tharanathan, Chitin/chitosan: Modifications and their unlimited application potential – An overview, *Trends Food Sci. Technol.* 18 (2007) 117–131.
152. L. Yang, A. Zhang, X. Zheng, Shrimp shell catalyst for biodiesel production, *Energy Fuels*, 23 (2009) 3859–3865.
153. F. Rezaei, T.L. Richard, B.E. Logan, Analysis of chitin particle size on maximum power generation, power longevity, and Coulombic efficiency in solid-substrate microbial fuel cells, *J. Power Sources*, 192 (2009) 304–309.