

AD-A101 163

TECHNICAL
LIBRARY

AD

MEMORANDUM REPORT ARBRL-MR-03108

COMBUSTION PROCESSES IN
CONSOLIDATED PROPELLANTS

Ingo W. May
Arpad A. Juhasz

May 1981



US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND
BALLISTIC RESEARCH LABORATORY
ABERDEEN PROVING GROUND, MARYLAND

Approved for public release; distribution unlimited.

DTIC QUALITY INSPECTED 3

Destroy this report when it is no longer needed.
Do not return it to the originator.

Secondary distribution of this report by originating
or sponsoring activity is prohibited.

Additional copies of this report may be obtained
from the National Technical Information Service,
U.S. Department of Commerce, Springfield, Virginia
22161.

The findings in this report are not to be construed as
an official Department of the Army position, unless
so designated by other authorized documents.

*The use of trade names or manufacturers' names in this report
does not constitute indorsement of any commercial product.*

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER MEMORANDUM REPORT ARBRL-MR-03108	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) COMBUSTION PROCESSES IN CONSOLIDATED PROPELLANTS		5. TYPE OF REPORT & PERIOD COVERED Memorandum Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Ingo W. May and Arpad A. Juhasz		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS U.S. Army Ballistic Research Laboratory ATTN: DRDAR-BLI Aberdeen Proving Ground, MD 21005		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 1L161102AH43
11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army Armament Research & Development Command U.S. Army Ballistic Research Laboratory ATTN: DRDAR-BL Aberdeen Proving Ground, MD 21005		12. REPORT DATE MAY 1981
		13. NUMBER OF PAGES 42
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release, distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES This report is based on a paper presented at the 10th International Annual Meeting on Propellants and Explosives held at ICT, Karlsruhe, Germany, June 1979.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Gun Propulsion Combustion Consolidated Propellants		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Jmk The use of consolidated or compacted conventional gun propellants offers the ballisticians the opportunity for significant performance increases through effective use of very high loading densities on the order of 1.2 g/cm ³ . Such loading densities will only be effective, however, if accompanied by an increase in surface area progressivity. We report the results of an experimental program surveying the effects of ignition stimulus and compaction density on the combustion of simple wafers of consolidated charges of single and double base propellants. We have found that sample confinement, surface inhibition, and grain		

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

geometric factors, have significant effects on charge break-up and propellant mass burning rate. In effect, the samples can behave with strong surface area progressivity. With a knowledge of the base grain propellant linear burning rate, independently arrived at, we have extracted instantaneous surface area profiles for burning consolidated propellants. The progressive character of the gas generation rate from burning consolidated charge samples can be explained on the basis of "macroscopic progressivity" defined as the controlled release of surface area through a continuous deconsolidation process.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

TABLE OF CONTENTS

	Page
LIST OF ILLUSTRATIONS.	5
1. INTRODUCTION	7
2. RATIONALE AND TEST PLAN.	9
3. EXPERIMENTAL DETAILS	10
3.1. Propellants.	10
3.2. Consolidation Process.	10
3.3. Igniters	14
3.4. Test Device and Measurements	14
3.5. Data Reduction	14
4. RESULTS.	14
4.1. Baseline Propellant Burning Rates.	17
4.2. Grain Deformation.	17
4.3. Reproducibility.	23
4.4. Compaction Density	23
4.5. Ignition Effects	23
5. SUMMARY.	31
REFERENCES	35
DISTRIBUTION LIST.	37

LIST OF ILLUSTRATIONS

Figure	Page
1. Geometric Progressivity of Multi-Perforated Propellant Grains.	8
2. Typical Process for Consolidating Propellants	13
3. Pressure-Time Profiles for the Two Igniters	15
4. Closed Vessel Test Device	16
5. Baseline Propellant Burning Rates	18
6. Inverse Reduction of Single Base Propellant Data.	19
7. Inverse Reduction of Double Base Propellant Data.	20
8. Single Base Propellant, M1 RAD 68108, Used in this Study.	21
9. Double Base Propellant, HES 8567.11E, Used in this Study.	22
10. Pseudo-Burning Rate for Deformed Single Base Propellant Grains.	24
11. Pseudo-Burning Rate for Deformed Double Base Propellant Grains.	25
12. Pseudo-Burning Rate for Whole, Consolidated, Double Base Propellant.	26
13. Reproducibility of Low Density Consolidated Wafers (M1, RAD 68108, 1.10 g/cm ³ , "Soft" Ignition)	27
14. Reproducibility of High-Density Consolidated Wafers (M1, RAD 68108, 1.35 g/cm ³ , "Soft" Ignition)	28
15. Compaction Effects on M1 Propellant with "Soft" Ignition.	29
16. Compaction Effects on HES Propellant with "Soft" Ignition	30
17. Ignition Effects on Low Compaction Density Double Base Propellant.	32
18. Progressive Burning in Consolidated Charges	33

1. INTRODUCTION

The quest for higher muzzle velocities in gun propulsion has led to the exploration of consolidated or compacted propellants as a means of increasing the charge-to-projectile mass ratio (c/m) for a given chamber volume. Typical high performance gun systems operate with propelling charge loading densities of about 0.9 g/cm³. Mechanical compaction of granular propellants allows loading densities as high as 1.25 g/cm³, with a resulting 40-percent increase in c/m. In certain cases, such as reported by Fortino¹, velocity increases of up to 13 percent have been achieved with consolidated charges without a significant increase in peak pressure.

Conventional interior ballistic theory, as shown by Witt² and Grollman³, requires, however, enhanced progressive burning of a propelling charge in order to obtain velocity increases at very high loading densities. A propelling charge burns progressively if the mass burning rate, \dot{m} , increases with projectile velocity. In conventional guns progressivity is usually enhanced through surface area modification or chemical tailoring of the propellant's linear burning rate, r . The common multi-perforated propellant geometry used in large caliber systems and the dented propellants used in small arms are typical examples. In a consolidated charge the objective is to enhance these methods using macroscopic progressivity which we define as a controlled release of surface area, S , through a continuous deconsolidation process.

The basic combustion law of interior ballistic theory is stated as:

$$dm/dt = \dot{m} = \rho \cdot r \cdot S$$

where ρ is the propellant density. Hence, the overall mass burning rate, \dot{m} , is proportional to the product of the instantaneous linear burning rate and the available burning surface area. In granular charges, surface area progressivity is obtained by choice of propellant geometry. Figure 1 illustrates the surface area enhancement, S/S_0 , as a function of mass fraction burned obtainable with multiperforated grain geometries, where S_0 is the initial propellant surface area. In consolidated charges enhanced progressivity results from surface area increases as the compacted charge burns through or fractures into smaller aggregates along natural stress lines in the charge. This breakup is aided by external or internal pressurization. There are some penalties to be paid in consolidating propellants, however. The compaction process may destroy or substantially

¹F.E. Fortino, "Improved Ballistic Performance for 30-mm Ammunition Using Consolidated Charges", Frankford Arsenal TR-76064, September 1976.

²W. Witt, E. Melchior, "Thermodynamisches Modell der Innenballistik", Wehrtechnik, Juni [1974] 222.

³B.B. Grollman, P.G. Baer, "Theoretical Studies of the Use of Multi-Propellants in High Velocity Guns", Ballistic Research Laboratory, Report No. R-1411, August 1968.

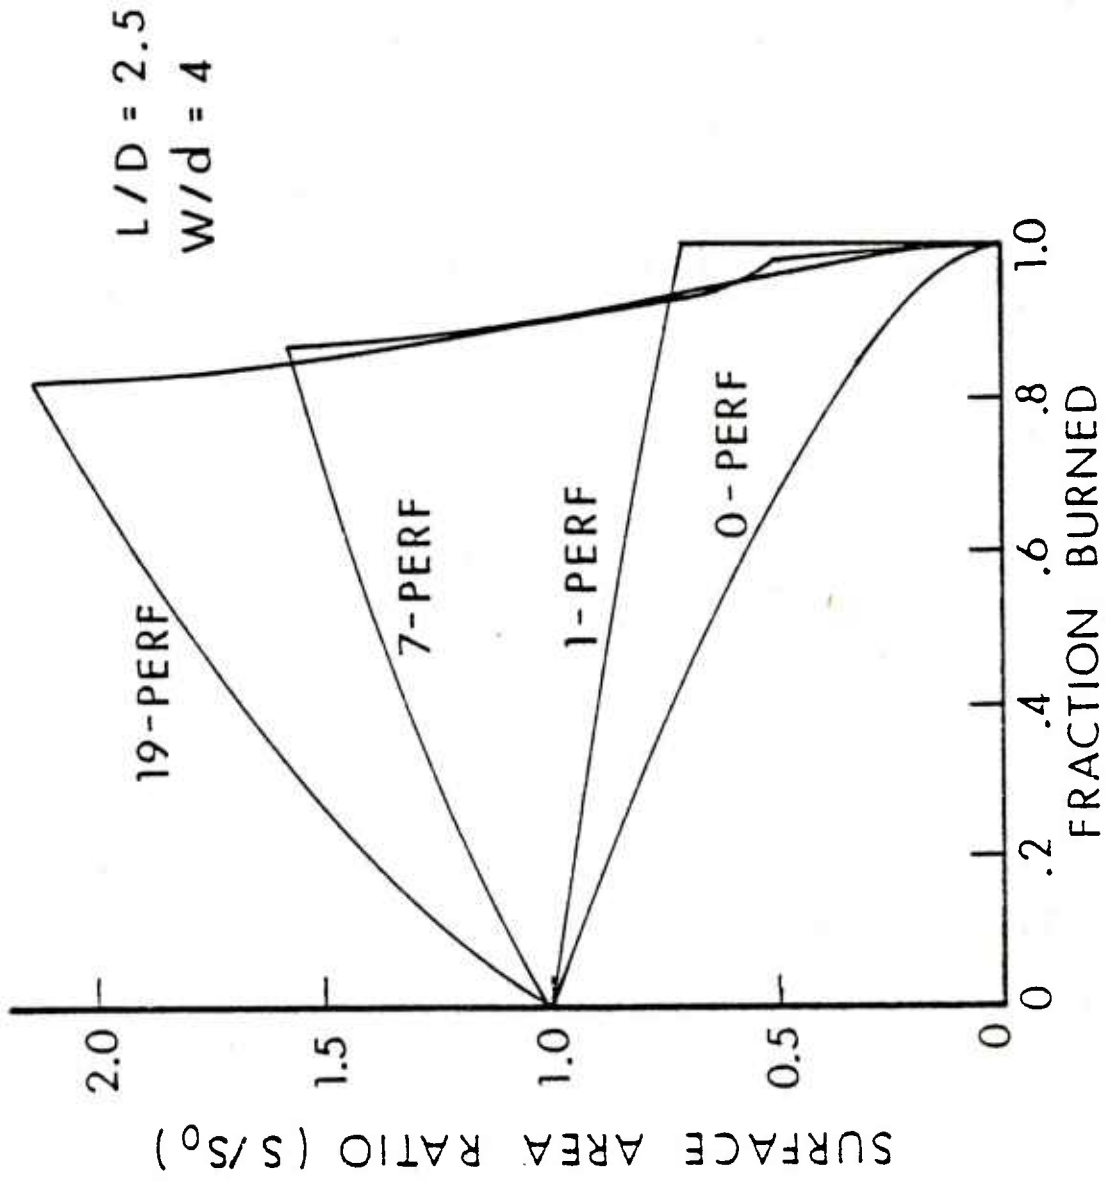


Figure 1. Geometric Progressivity of Multi-Perforated Propellant Grains

modify the original grain geometry. This may result in reduced single grain progressivity as well as a lower initial single grain surface area. One significant observation made in studies to date has been that, operating at a peak chamber pressure equivalent to that obtained with granular propellant, requires the use of faster burning propellants to compensate for the reduced surface area. It becomes important, therefore, to determine the overall or macroscopic progressivity for a consolidated propelling charge.

Although the development of the propelling charge surface area profile is a dominant factor of interest in conventional interior ballistic theory, other factors are also important and necessary for a more complete one-dimensional, two-phase flow, fluid dynamic modeling of the process. The details of flame propagation through a porous bed and of the eventual transition to a fluidized bed are also necessary. Such modeling of granular propelling charge performance has been quite successful recently⁴. It would be a significant advantage if such models could be applied to describing the functioning of consolidated charges. Details such as grain breakup, gas permeability, and gas flow resistance, are largely unknown and quite difficult to pin down for consolidated charges, as indicated in a previous study by Juhasz⁵. Yet, if quantitative measurements can be made of the qualitative phenomenology of consolidated charge functioning, the development of a successful consolidated charge design methodology, using a combined experimental and theoretical approach, would be greatly enhanced.

2. RATIONALE AND TEST PLAN

The basic purpose of our experiments was to extract quantitative information about the burning surface area development in consolidated charge combustion in an environment devoid of the complications of a moving projectile boundary. Previous work⁵ indicated that a systematic survey of the effects of compaction density, ignition stimulus, and propellant composition on macroscopic progressivity is a necessary first step towards a generalized description of S/S_0 for consolidated charges. Fortino⁶ recently reported some experiments directed at a similar goal. Given a general surface area progressivity relationship, useful a priori interior ballistic performance predictions are then possible. Of further interest in our study is the effect of these parameters on the variability of combustion behavior. Unacceptably large ballistic variability has been a major reason for the failure of consolidated propelling charges to find

⁴A.W. Horst, T.C. Minor, "Ignition-Induced Flow Dynamics in Bagged-Charge Artillery", 4th International Symposium on Ballistics, Monterey, California, October 1978.

⁵A.A. Juhasz, I.W. May, "The Effects of Consolidation on the Burning of Gun Propellants", 15th JANNAF Combustion Meeting, Chemical Propulsion Information Agency, Laurel, MD, Publication 297, December 1978.

⁶F.E. Fortino, "Effect of Consolidation Parameters on the Burning of Consolidated Propellant Charges", 1979 JANNAF Propulsion Meeting, Anaheim, California, March 1979.

their way into fielded gun systems. It must be noted at this point that the parameters studied here are by no means all inclusive. Process variables in the manufacture of consolidated propellants loom as serious complicating factors which may severely restrict any generalizations of our results.

3. EXPERIMENTAL DETAILS

In this study we restricted the scope to a consideration of two generic propellant compositions, compacted by one consolidation technique at several densities, and with two different igniters. Table 1 summarizes the test matrix.

3.1. Propellants

Available, single-perforated, undeterred, single base (SB) and double base (DB) propellants were chosen to be consolidated. Table 2 lists the basic compositions and grain dimensions. There is nothing unusual about their chemistry and they should, therefore, be considered as typical single and double base compositions. The webs and, perhaps more importantly, the grain length-to-diameter ratios (L/D), are quite different. The single base propellant with a L/D of 4.24 can be expected to consolidate somewhat differently from the double base propellant with an L/D of 1.18.

3.2. Consolidation Process

The propellants chosen for this study were consolidated under Contract DAAK11-77-C-0031 to BRL by Hercules, Inc.^{*7} The process is depicted schematically in Figure 2. The propellant surface is softened by a vapor solvation process before compacting and drying to the original presolvated weight. It is unlikely that the basic chemistry has changed significantly because of the consolidation process. Grain surface hardness changes are likely, however, with possible effects on ignitability and low pressure burning rates. The samples are molded into simple wafers with a diameter of nearly 40 mm and a length of 25 mm. The wafers were circumferentially inhibited with EA-946[†]. The coating covered the exposed outermost surface of the propellant grains, but did not penetrate into the consolidated charge. The samples were cemented into thin steel cylinders with fast acting epoxy. This procedure prevents flamespread down the cylinder walls of the wafers. Experimentally, it results in a more nearly one-dimensional flame propagation.

⁷L. Scott, "Consolidated Propellant Charge Investigation," Volume 1: Preparation of Consolidated Charge Increments," Ballistic Research Laboratory, Contract Report ARBRL-CR-00408, November 1979. (AD #B043967L)

^{*}Contract DAAK11-77-C-0031

[†]A product of the Hysol Division, Bendix Corporation.

TABLE 1. TEST MATRIX

COMPOSITION	SINGLE BASE M1 SP	DOUBLE BASE HES 8567.11E SP
COMPACTION DENSITIES	1.10 g/cm ³ 1.25 1.35	1.15 g/cm ³ 1.25
IGNITERS	"SOFT" (Atlas M100 Match plus 1.0 g FFFG Black Powder)	"HARSH" (M52 Primer plus 1.0 g FFFG Black Powder)
	"HARSH"	"SOFT"

TABLE 2. PROPELLANTS

INGREDIENTS (% Weight)	MI SINGLE BASE Lot No. RAD 68108	DOUBLE BASE Lot No. HES 8567.11E
Nitrocellulose	83.1	83.55
% Nitration	13.5	13.25
Dinitrotoluene	9.99	-----
Nitroglycerine	-----	10.76
Dibutylphthalate	5.04	3.23
Diphenylamine	1.01	0.57
Total Volatiles	0.86	0.85
Potassium Nitrate	-----	1.02
Graphite	-----	0.02
DIMENSIONS: (mm)		
Web	0.343	0.935
Length	5.05	2.76
Diameter	1.19	2.33

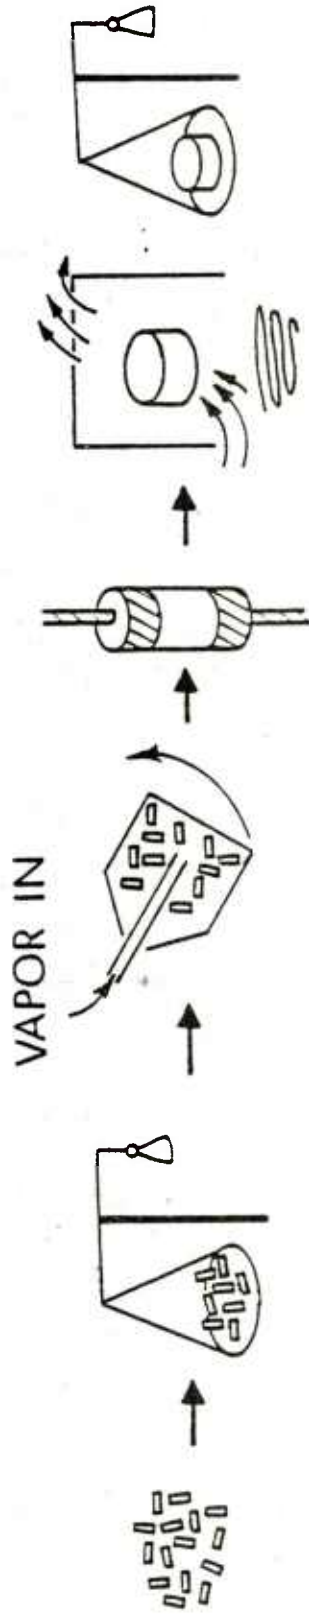
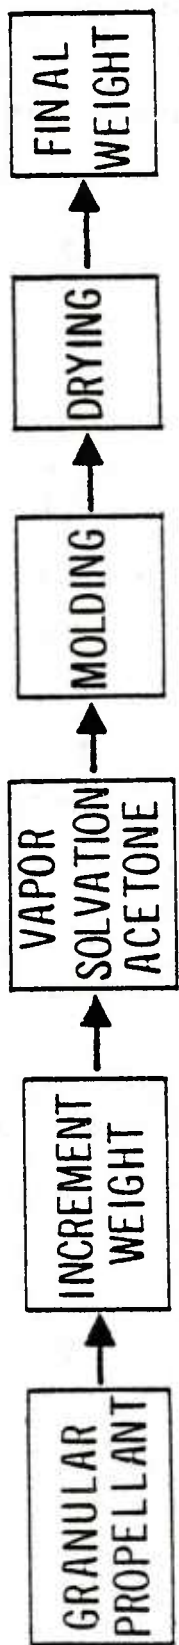


Figure 2. Typical Process for Consolidating Propellants

3.3. Igniters

The two igniter configurations were chosen to give what was felt to be a reasonable, though not overpowering difference in output characteristics. The M52 primer with 1 g of FFFG black powder results in substantially more rapid pressurization of the closed vessel than the relatively slow electric match with the same amount of black powder. The differences are readily apparent in Figure 3 which shows pressure-time characteristics of the two igniters only. The closed vessel was filled with an appropriate amount of inert filler. The "harsh" ignition obtained with the M52 primer results also in a higher final ignition pressure, and shorter igniter functioning time.

3.4. Test Device and Measurements

A closed vessel, illustrated in Figure 4, with an internal diameter of 40 mm was designed and built for this study. The steel-sleeved samples were slipped into the vessel and cemented in place to prevent movement during the experiment. A Kistler 607C piezoelectric gage was used to measure pressure versus time. The data were acquired digitally on a laboratory minicomputer, smoothed, and differentiated to obtain a basic data file of pressure, dp/dt , and time.

3.5. Data Reduction

The data obtained from an experiment are analyzed using a computer program, CBRED II. The program described previously by Price⁸ and Juhasz⁹ for the extraction of linear burning rates was modified to allow the inverse process of extracting surface area given linear burning rate information. The problem is, therefore, reduced to determining the linear burning rate of the unconsolidated propellant using the same closed vessel. The assumption is then made that the consolidation process has not significantly affected the chemistry and hence the burning rate. Finally the linear burning rate is then used to extract surface area profiles, S/S_0 , as a function of the fraction of propellant burned, z , using CBRED II. This information can then be used directly in a suitable gun interior ballistics model.

4. RESULTS

In the data to follow, it is important to keep in mind that in the

⁸Price, C.F., Juhasz, A.A., "A Versatile User-Oriented Closed Bomb Data Reduction Program (CBRED)", *Ballistic Research Laboratory R-2018*, September 1977. (AD #A049465)

⁹Juhasz, A.A., Price, C.F., "The Closed Bomb Technique for Burning Rate Measurement at High Pressure", *Experimental Diagnostics in Combustion of Solids*, ed. T.L. Boggs and B.T. Zinn, Vol. 63, *Progress in Astronautics and Aeronautics*, [1978] 129.

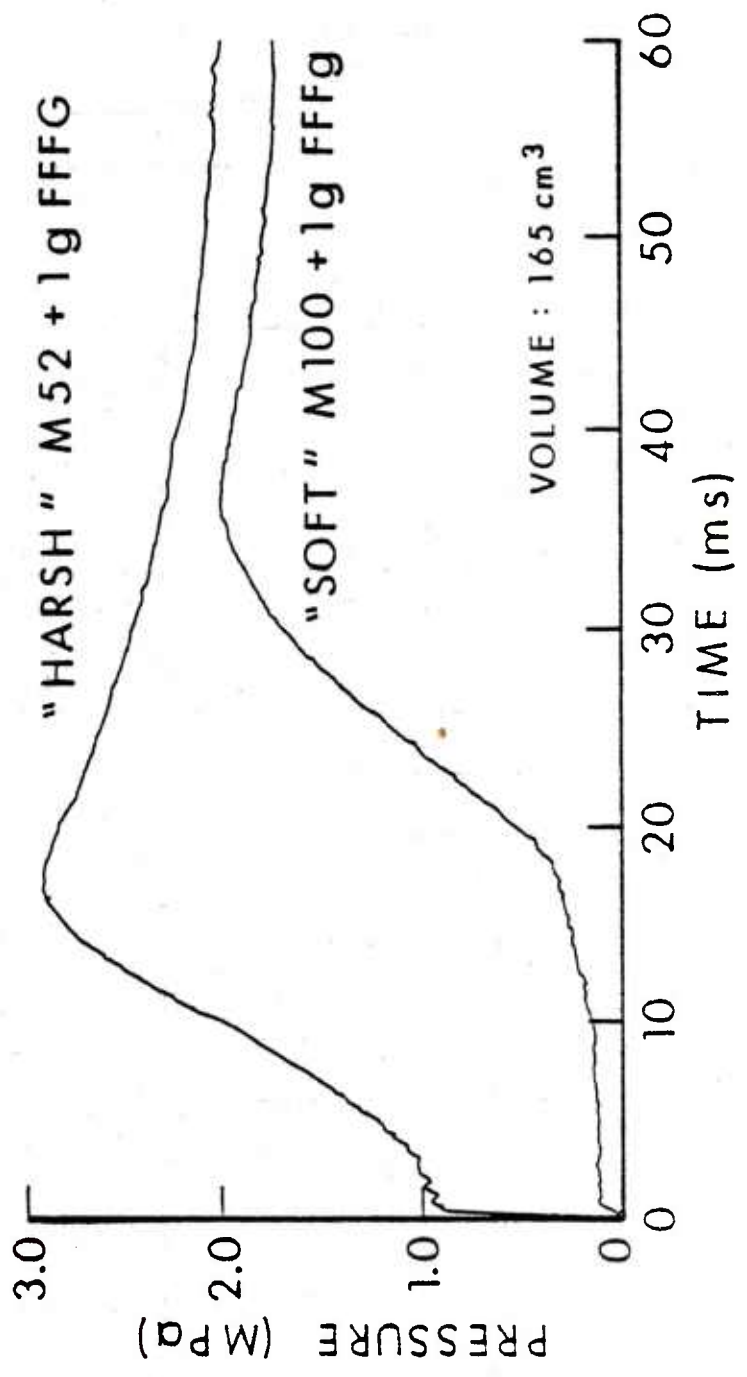


Figure 3. Pressure-Time Profiles for the Two Igniters

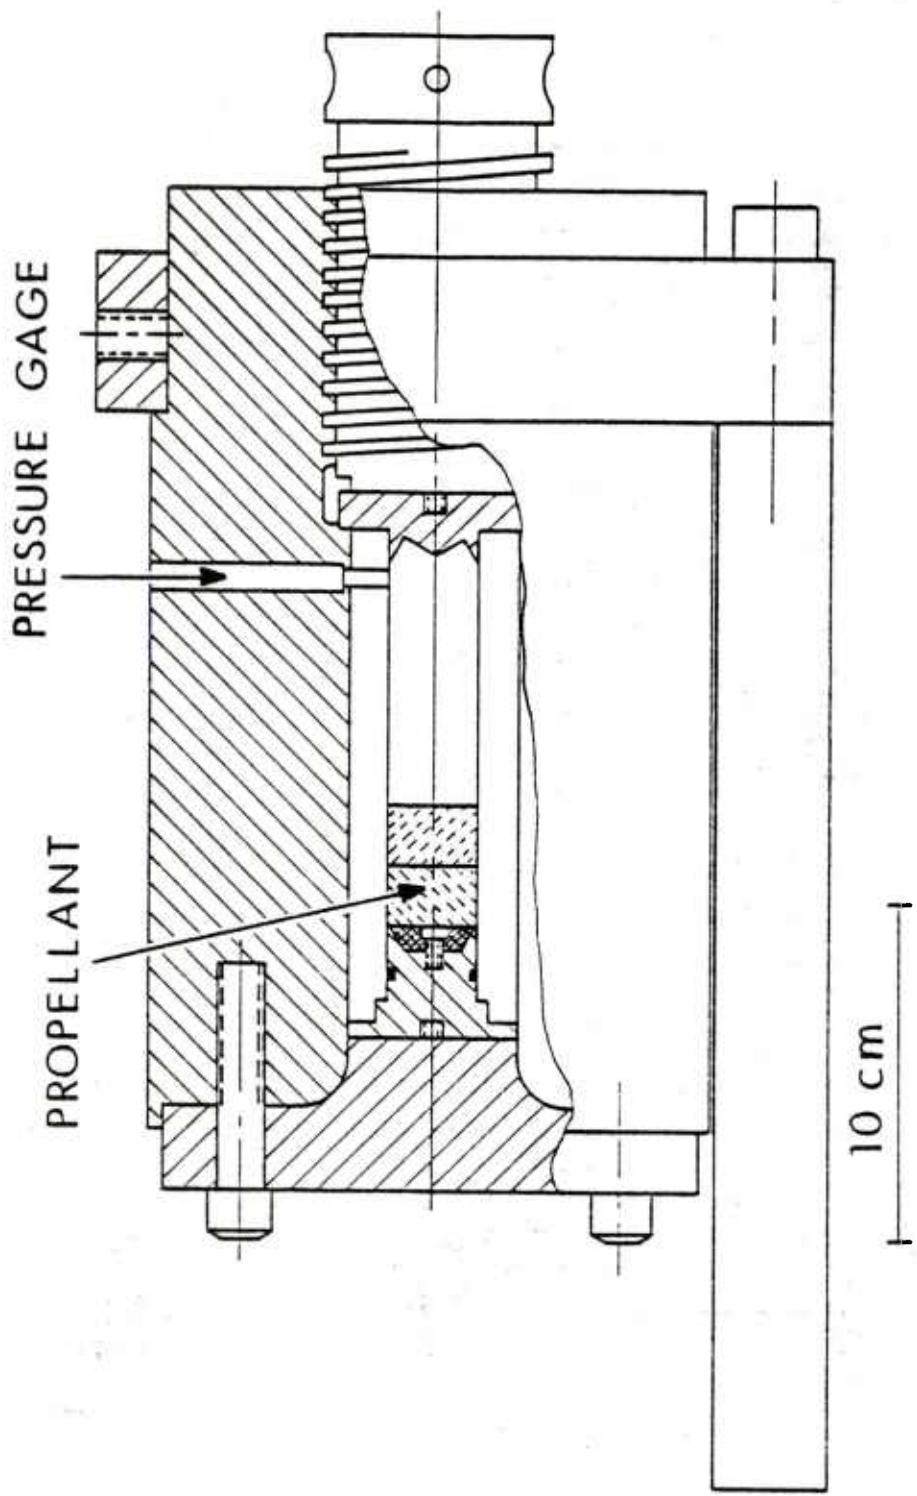


Figure 4. Closed Vessel Test Device

figures showing the surface area ratio, S/S_0 , as a function of the fraction of propellant burned, S_0 represents the initial surface area for the equivalent amount of loose, granular propellant.

4.1. Baseline Propellant Burning Rates

The results from standard closed vessel experiments on granular M1 and HES propellants are shown in Figure 5. Each propellant was burned at 21°C with excellent reproducibility down to nearly 3 MPa. Burning rate variability at low pressures is not at all uncommon for closed vessel burning rate tests. It is usually ascribed to ignition and flamespread variability. It should also be noted that the burning rate curves for both propellants are linear only above 40 MPa. As expected the more energetic double base propellant also burns substantially faster. For each of the propellants an average burning rate table was constructed for use in the surface-area ratio analysis.

To test the internal consistency of the surface-area extraction routine in CBRED II, S/S_0 was computed for the loose propellant data from which the burning rate table was constructed. The results are shown in Figures 6 and 7. Superimposed on the "inverse" experimental curves is the ideal, single-perforated grain progressivity curve obtained from purely geometric considerations. The agreement from 10 to 80 percent of the fraction burned is pleasing. Again, ignition and flamespread effects as well as imperfect grain geometries are sufficient to explain the discrepancies in the extremes. From this exercise it should be obvious that the experimental variability for consolidated charges can only be greater.

4.2. Grain Deformation

The effect of the mechanical deformation of the single grain geometry is of interest. Figures 8 and 9 show samples of the base grain, the consolidated wafer, and mechanically broken-apart consolidated wafers. The single base propellant (RAD 68108) was not graphited, the double base propellant (HES 8567.11E) had a 0.02 percent graphite coating. Sample deconsolidation was done by placing single wafers between the plateaus of a hydraulic press and pressing till initial wafer fracture took place. The differences in the grain break-up characteristics between the single and double base propellants are immediately apparent. Not so obvious, although of perhaps greater significance, is the observation of much less grain deformation with the lower L/D (1.18) DB propellant than with the high L/D (4.24) SB propellant. Physically, the single base wafers are stronger, presumably because of the greater intertwining of the longer grains. Of interest also, is the observation that the mechanical deconsolidation process results in granular aggregates of many different sizes. Some grain fracture is also observed. For the M1 propellant grains, collapse of the perforation is quite common. This is in distinct contrast with the double base propellant.

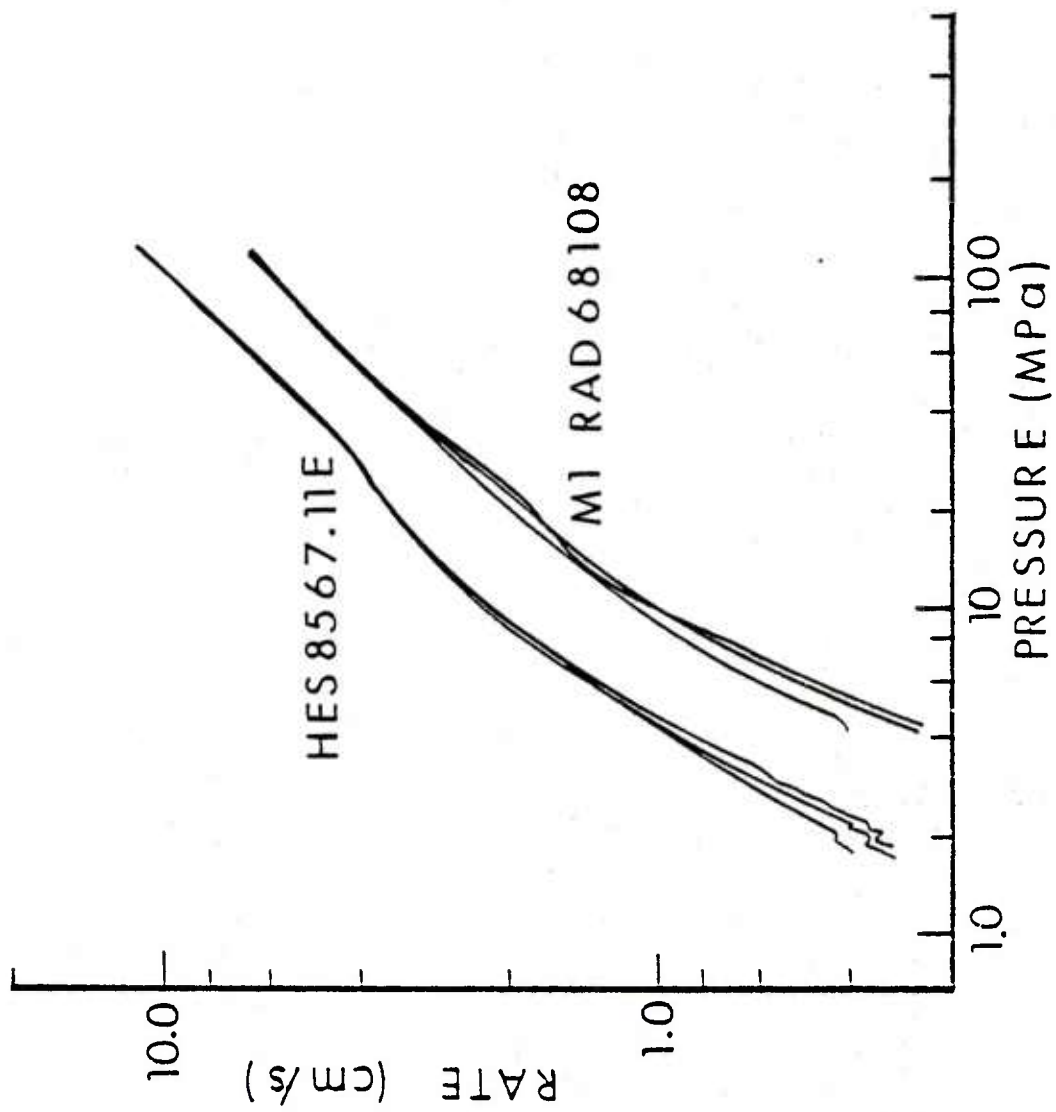


Figure 5. Baseline Propellant Burning Rates

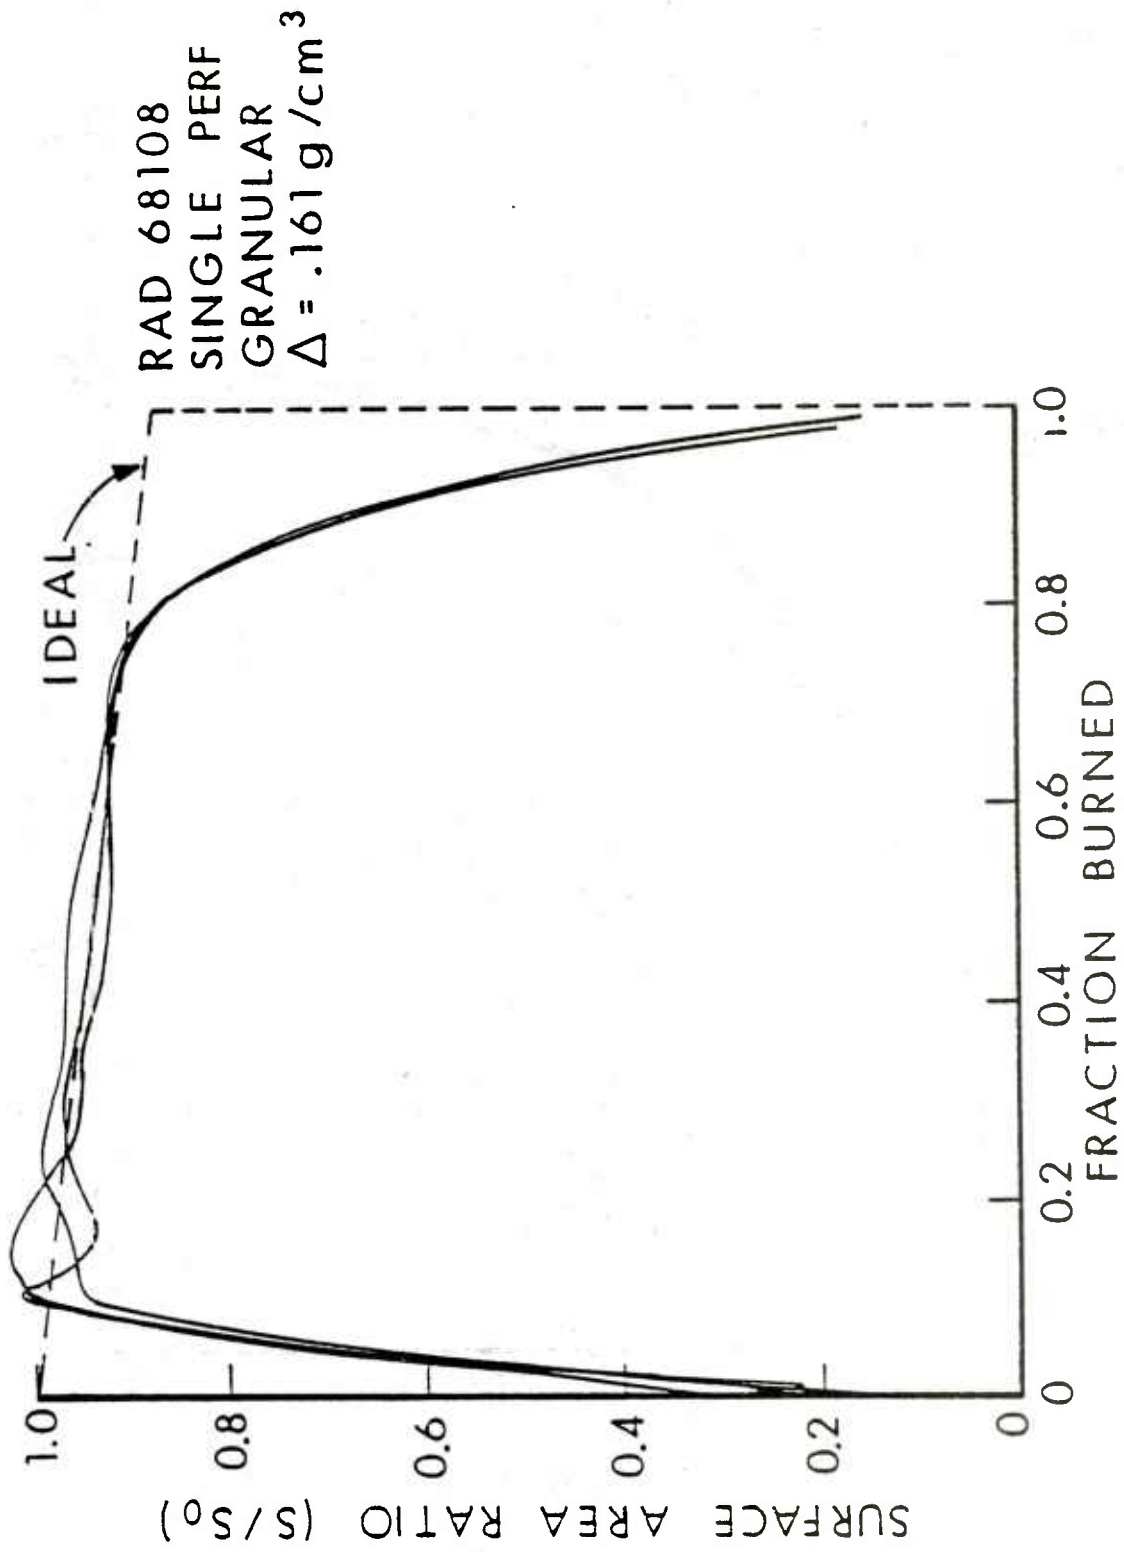


Figure 6. Inverse Reduction of Single Base Propellant Data

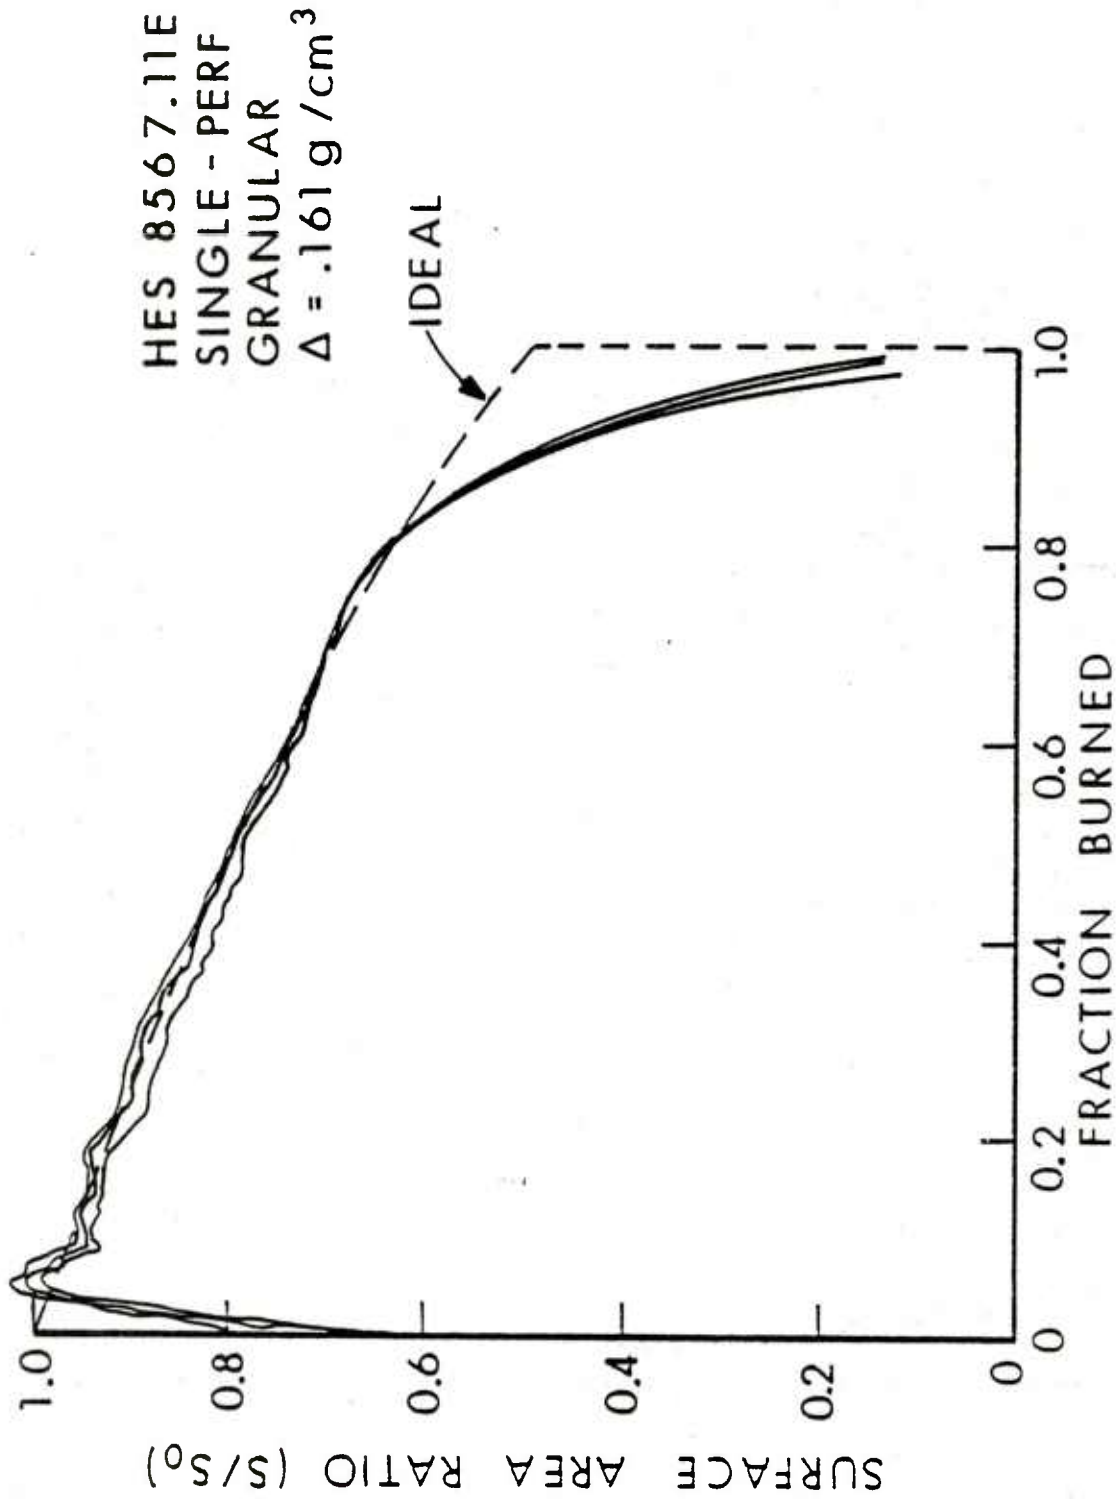


Figure 7. Inverse Reduction of Double Base Propellant Data

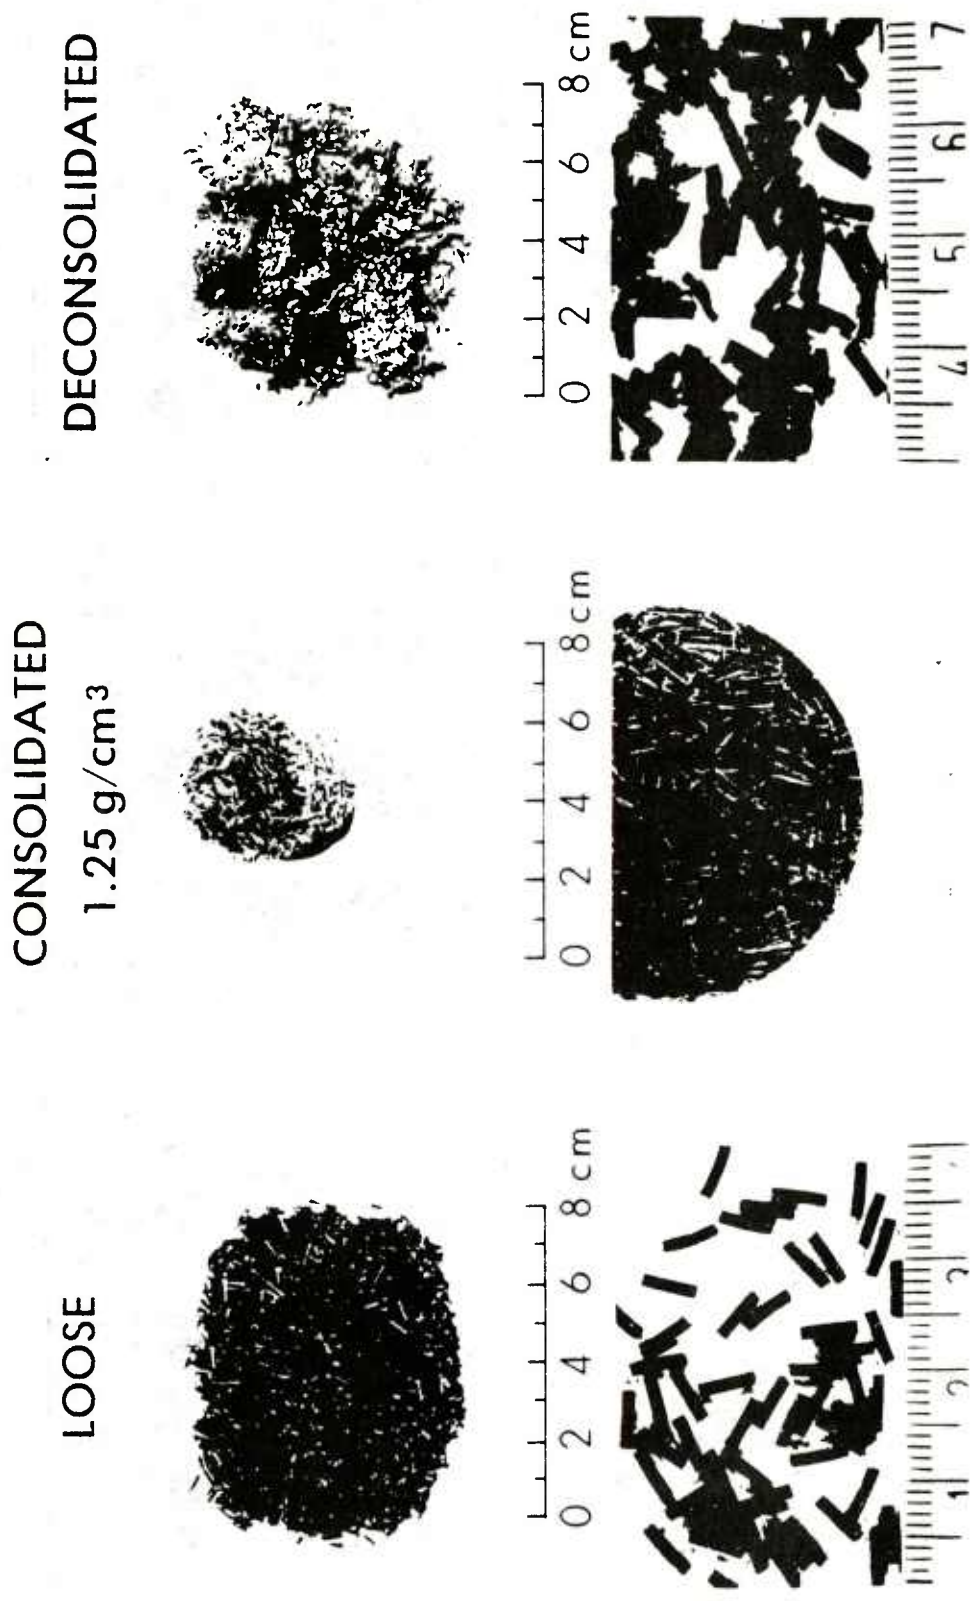


Figure 8. Single Base Propellant, M1 RAD 68T08, Used in this Study

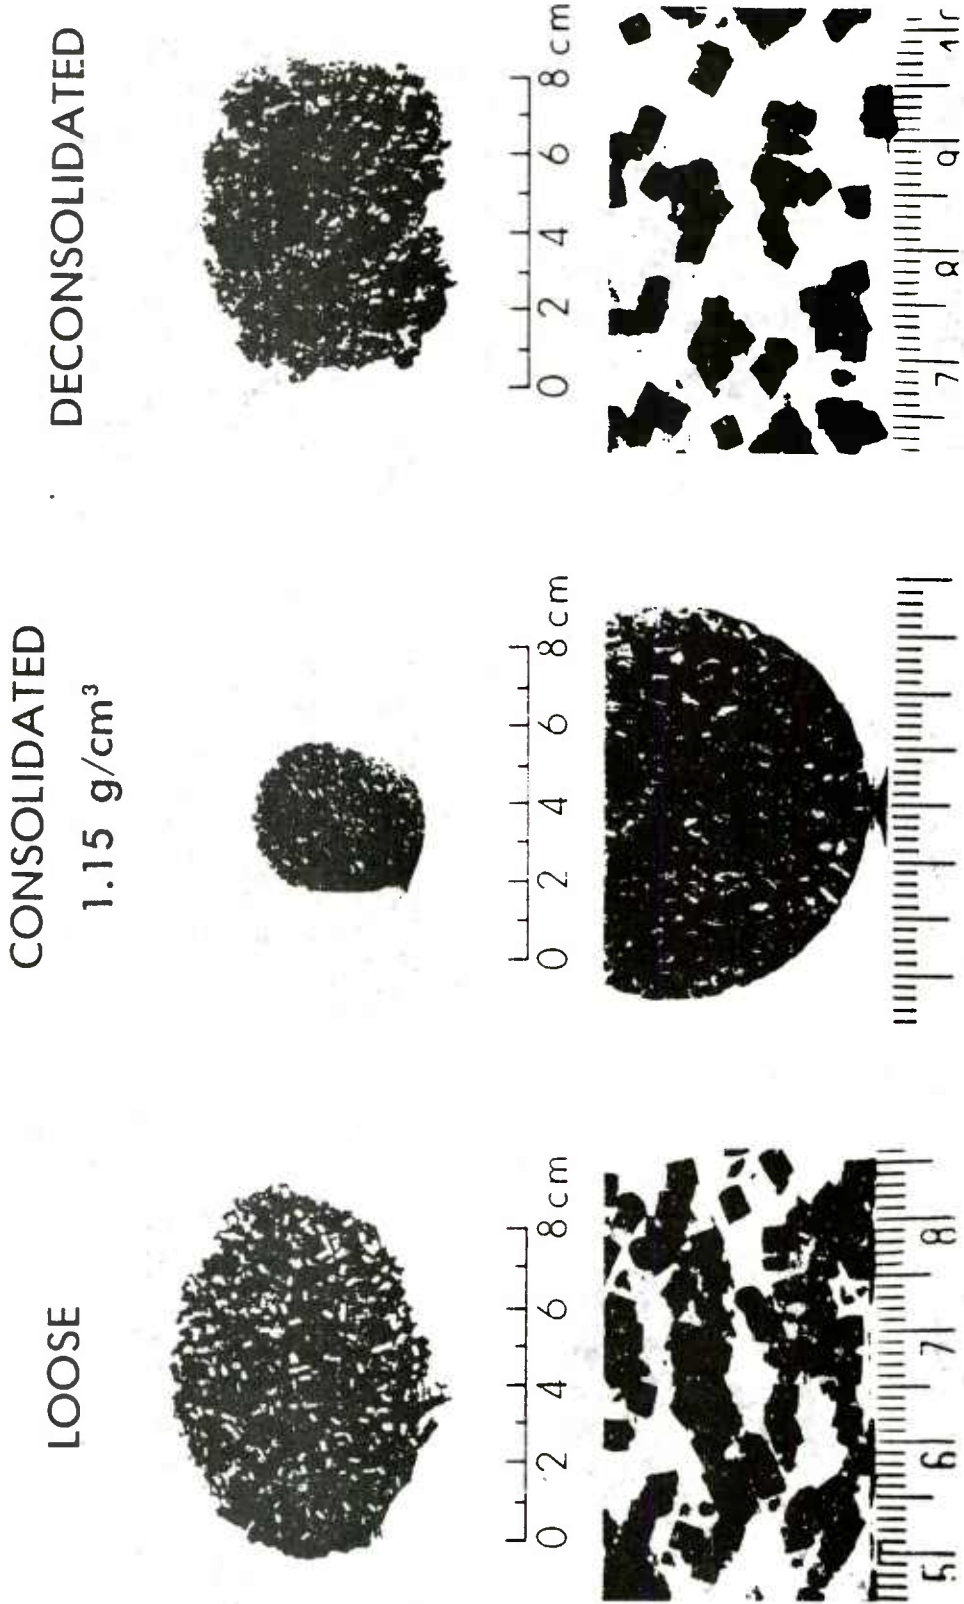


Figure 9. Double Base Propellant, HES 8567.11E, Used in this Study

Deconsolidated, whole, single grains were collected for standard closed vessel experiments. Assuming no geometry changes, pseudo-burning rates were then extracted as shown in Figures 10 and 11. For the M1 propellant, for which substantial perforation collapse is observed, the compaction process has a noticeable effect on the pseudo-burning rate. This is in distinct contrast to the double base propellant for which little change is noted. Our interpretation is that the greater single base grain L/D ratio is largely responsible for this effect, rather than any intrinsic composition effects. For comparison, pseudo-burning rates assuming perfect single grain geometry are shown in Figure 12 for consolidated double base wafers. The reduction in apparent burning rate due to the much lower burning surface area in the consolidated propellant is dramatic. To maintain ballistic equivalency in a gun firing, an approximately 50 percent reduction in web would be required in this particular case to compensate for the reduced surface area.

4.3. Reproducibility

Experimental variability of consolidated charges appears to be quite strongly correlated with compaction density. Figure 13 shows very poor reproducibility is obtained for the low compaction density samples. At high compaction densities much better reproducibility is observed as shown in Figure 14. We speculate that the higher strength wafers are much less susceptible to variations in igniter-induced grain break-up.

4.4. Compaction Density

Several trends emerge from the representative runs for the M1 propellant shown in Figure 15. The low density runs show a degressive behavior that is similar to the single grain surface profile although at a substantially reduced surface area. The high density (1.35 g/cm^3) surface area profile gives strong evidence of enhanced progressivity if S_0 is re-defined to be the initial surface area of the wafer at the end of the ignition-flame-spread phase. The intermediate density results fall in between the extremes. For the double base propellant data shown in Figure 16, the trends are not as clear. While the surface area decreases with increasing compaction density for the M1 propellant, as one would expect, the double base wafers show no such clear trend. With some imagination, the trend towards more progressivity with increased compaction density may, however, still be discerned. The concept of a macroscopic progressivity for consolidated propellants appears to be valid.

4.5. Ignition Effects

At the high compaction densities it was not possible to discern any substantial igniter-related effects. Apparently, if the wafers are strong enough to withstand a given ignition pulse, little changes in the combustion behaviors are to be expected. A modest, though not well understood, effect is, however, seen in the low density double base experiments shown

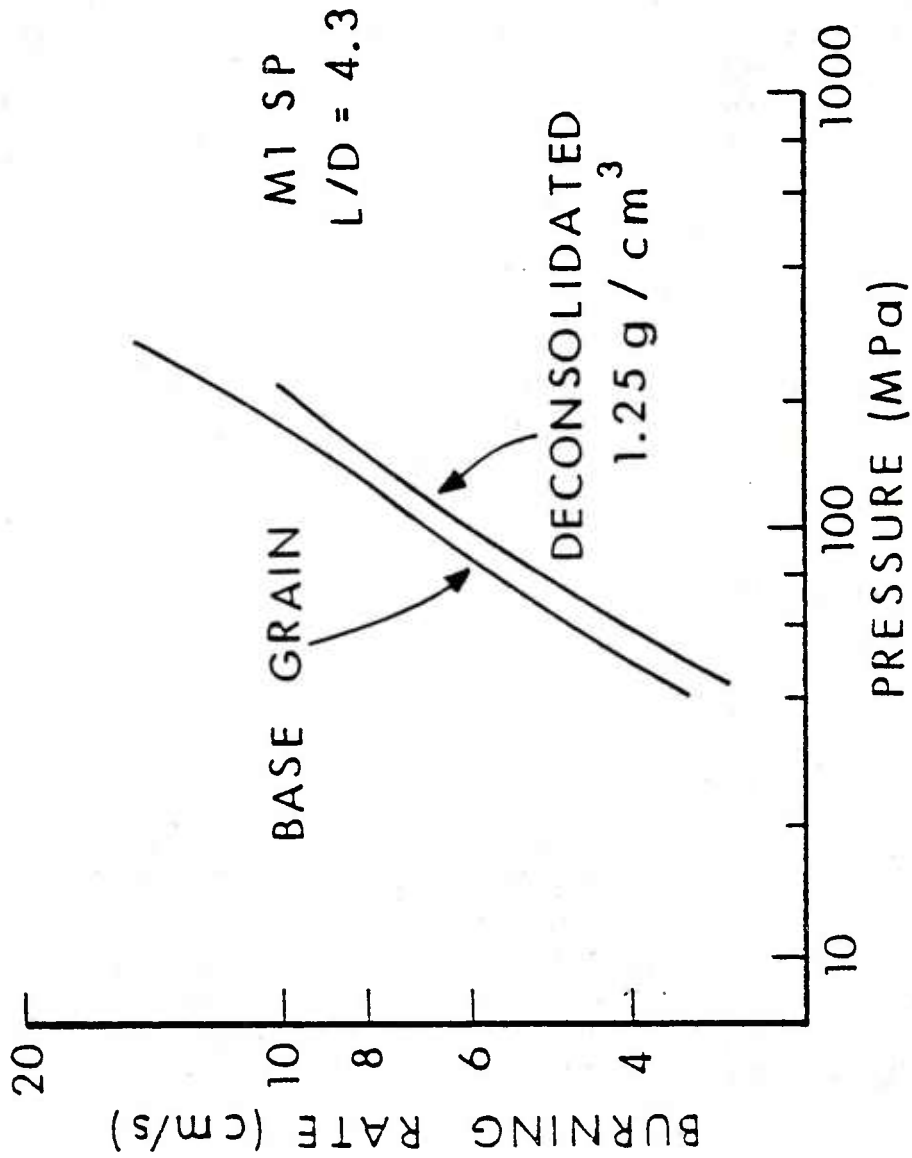


Figure 10. Pseudo-Burning Rate for Deformed Single Base Propellant Grains

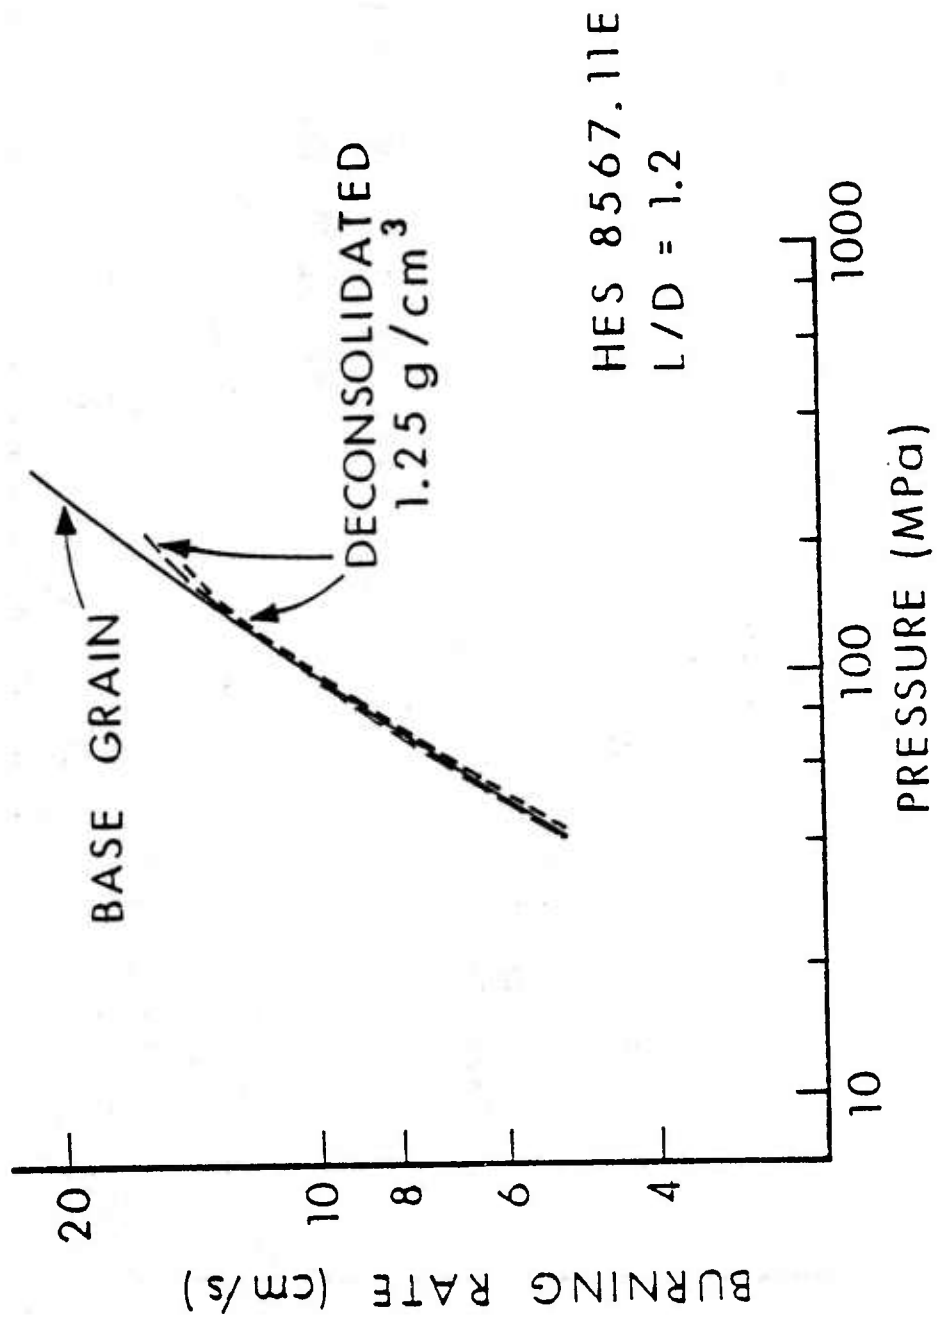


Figure 11. Pseudo-Burning Rate for Deformed Double Base Propellant Grains

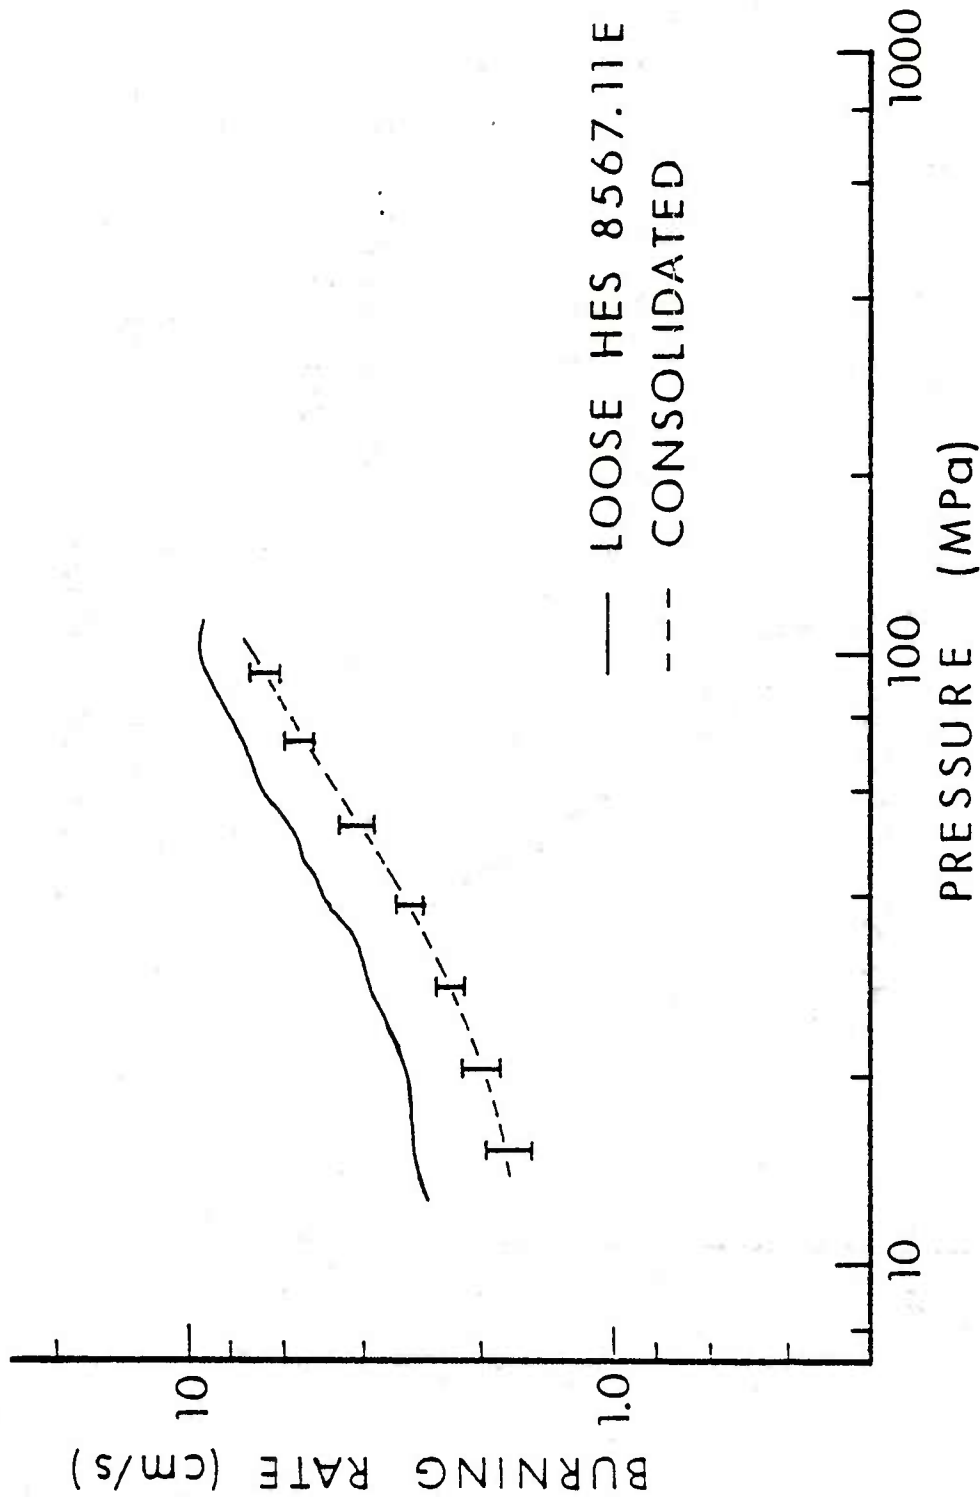


Figure 12. Pseudo-Burning Rate for Whole, Consolidated, Double Base Propellant Wafer (Reduction Assumed Perfect Single Grain Geometry)

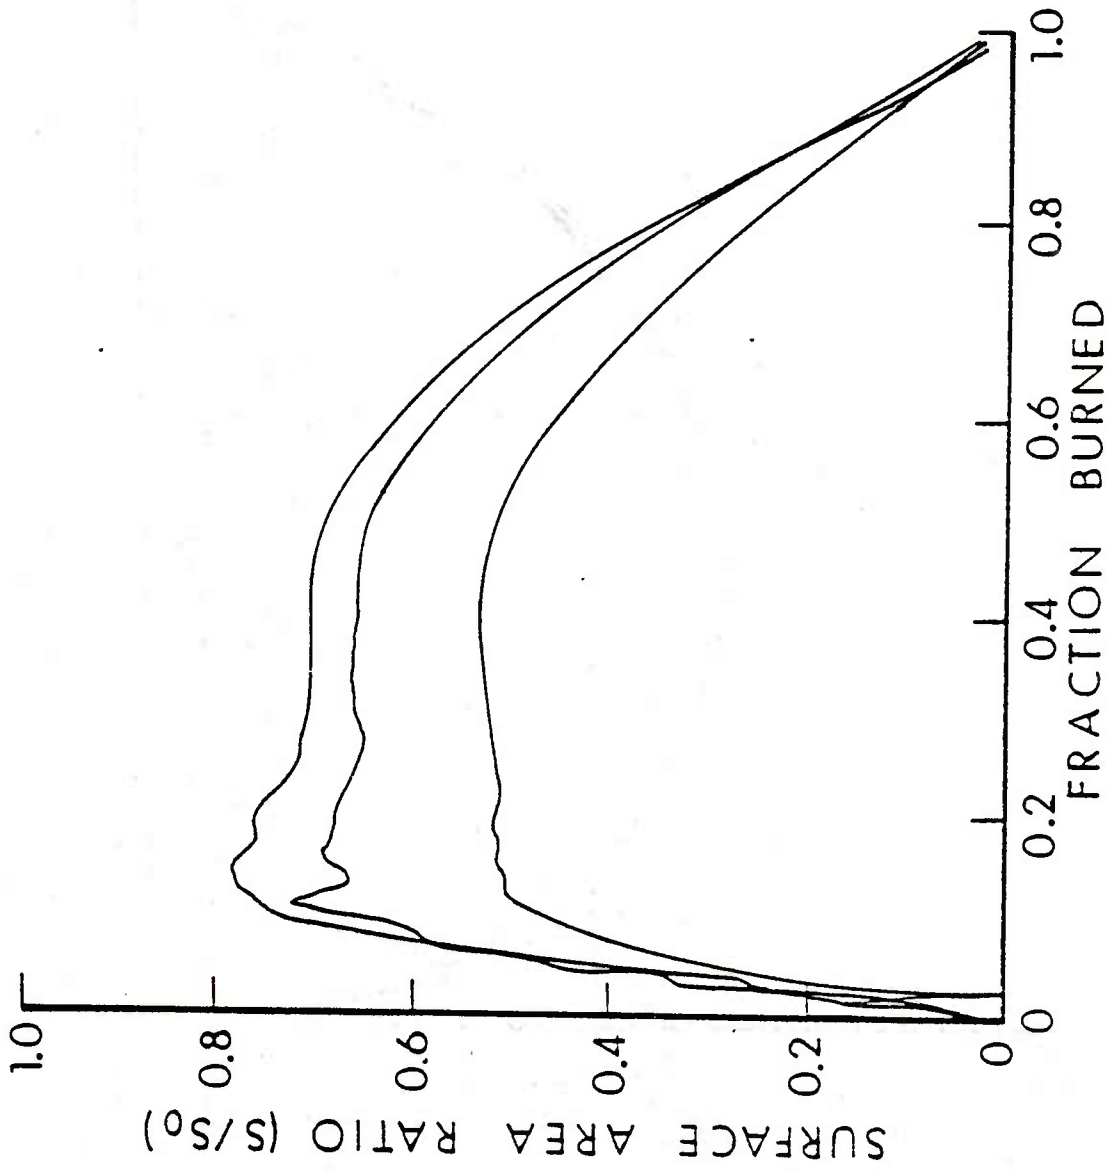


Figure 13. Reproducibility of Low Density Consolidated Wafers (MT, RAD 68108, 1.10 g/cm³, "Soft" Ignition).

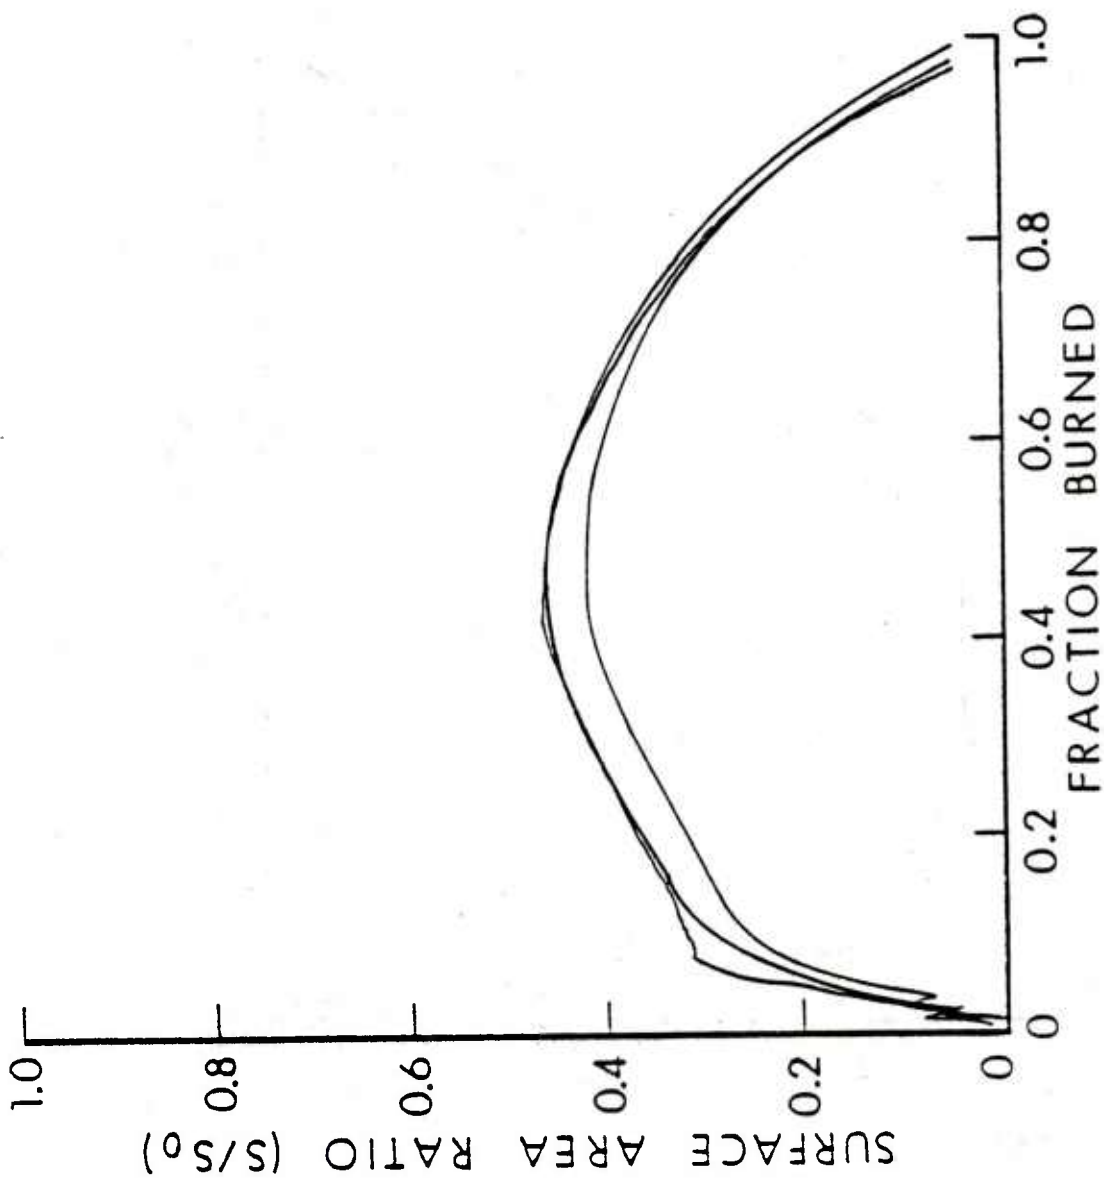


Figure 14. Reproducibility of High Density Consolidated Wafters (M1, RAD 68108, 1.35 g/cm³, "Soft" Ignition)

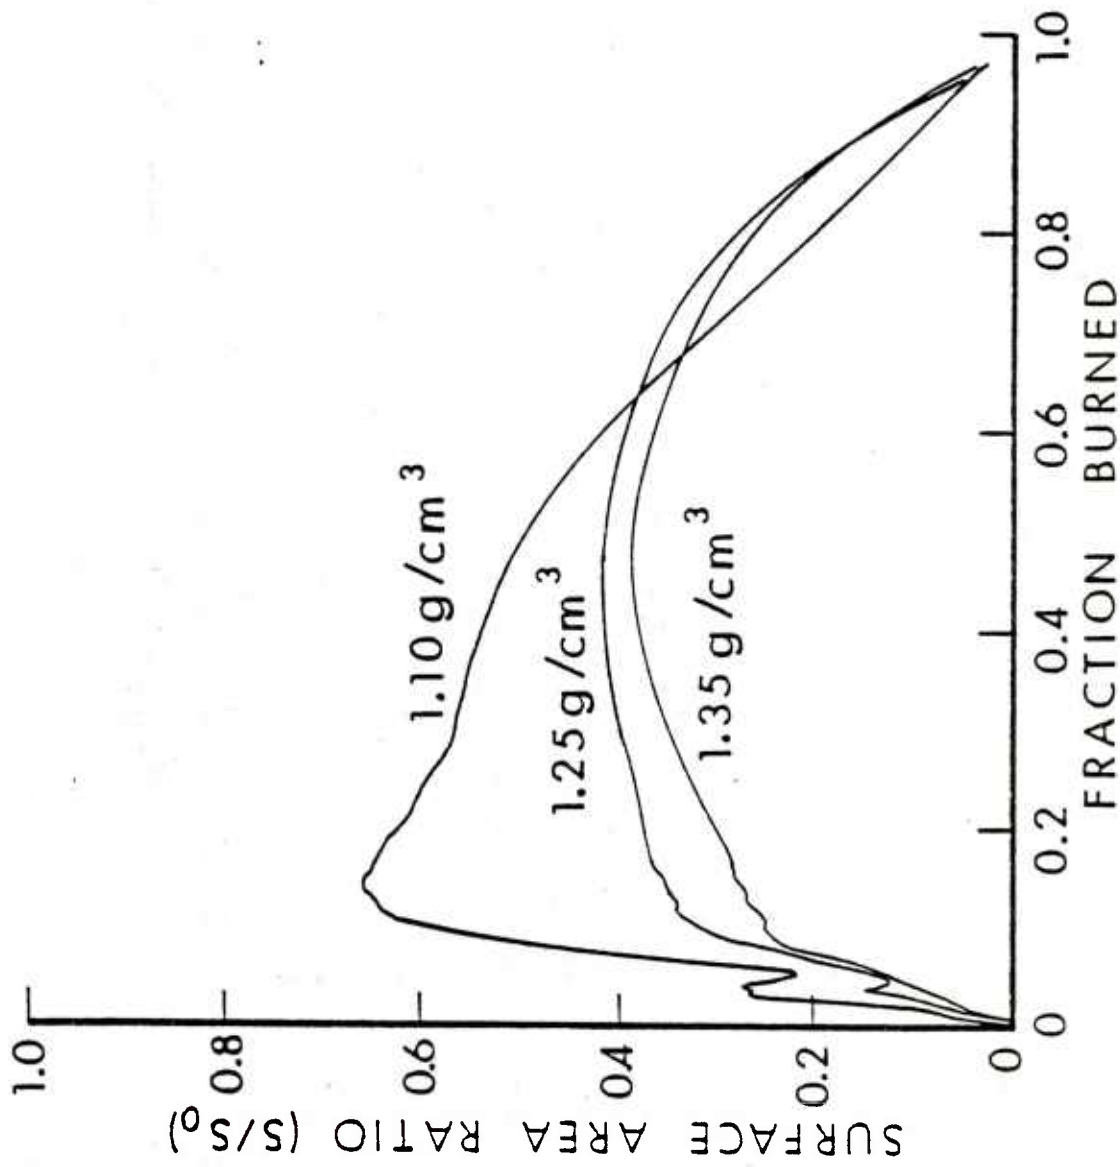


Figure 15. Compaction Effects on M1 Propellant with "Soft" Ignition

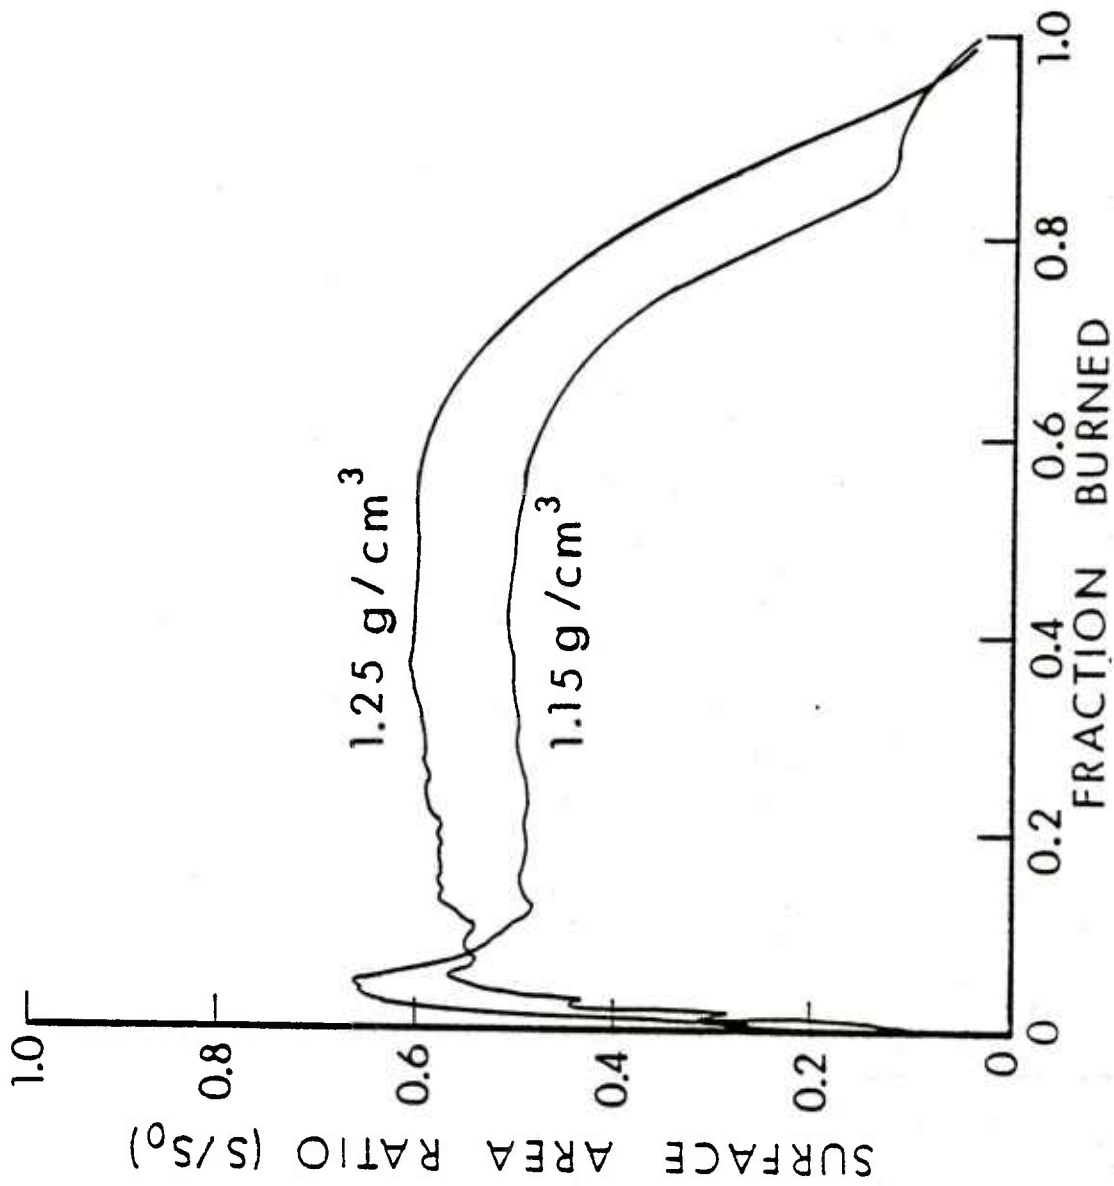


Figure 16. Compaction Effects on HES Propellant with "Soft" Ignition

in Figure 17. The "soft" ignition shows a fairly normal behavior. The initial overshoot in the surface area profile may be due to a small amount of igniter induced wafer break-up which is then burned up and collapses to the bulk wafer combustion mode. A rapidly damped, local pressure disturbance can also explain the overshoot. The "harsh" ignition case, however, shows clear evidence of pressure waves in the dp/dt data. These pressure wave disturbances then result in very erratic surface area profiles. At this time, we speculate that the "harsh" ignition, besides inducing a pressure wave disturbance in its own right, causes enhanced igniter-induced wafer fracture which may amplify the pressure wave problem. For future tests, it seems worthwhile to find the threshold ignition pulse which begins to have substantial effects on the combustion behavior of a consolidated charge of any compaction density.

Charge ignition delays were observed to be nearly 1.5 times longer for the soft igniter configuration. In addition, M1 is substantially less ignitable than the HES propellant as shown by a factor of two increase in ignition delay times.

5. SUMMARY

The postulated fracture-and flamespread-caused macroscopic surface area progressivity attributed to consolidated charges has indeed been experimentally verified, at least for the M1 single base propellant wafers. Figure 18 illustrates that even for the double base propellant an increase in the surface area ratio over loose, single-perforated grains is obtained. The compaction sensitivity of this phenomenon suggests that possibilities exist for improving and controlling the surface area profiles.

Reproducibility has been found to be strongly related to compaction density and, in this study, weakly ignition-dependent. We conjecture that with a much stronger ignition pulse than our "harsh" igniter, a larger igniter dependence might also be observed for the structurally-stronger, high-compaction density wafers. This hypothesis will be tested in the near future.

From the results of this experimental survey it has become apparent that sample burning characteristics can be related back to charge strength and base grain geometry characteristics. Some of the progressivity hoped for from consolidated propellants has already been realized. Further experimental efforts would do much to improve consolidated charge design capabilities. In addition to grain L/D, wafer strength can be controlled by other properties, such as presence/absence of graphite on the base grain or the use of a "binder" such as collodion in forming the base grain. The binder coating on the grains could act as a chemical deterrent as well. The combustion and progressivity characteristics of such samples could be readily examined via the closed bomb technique. Further, flash

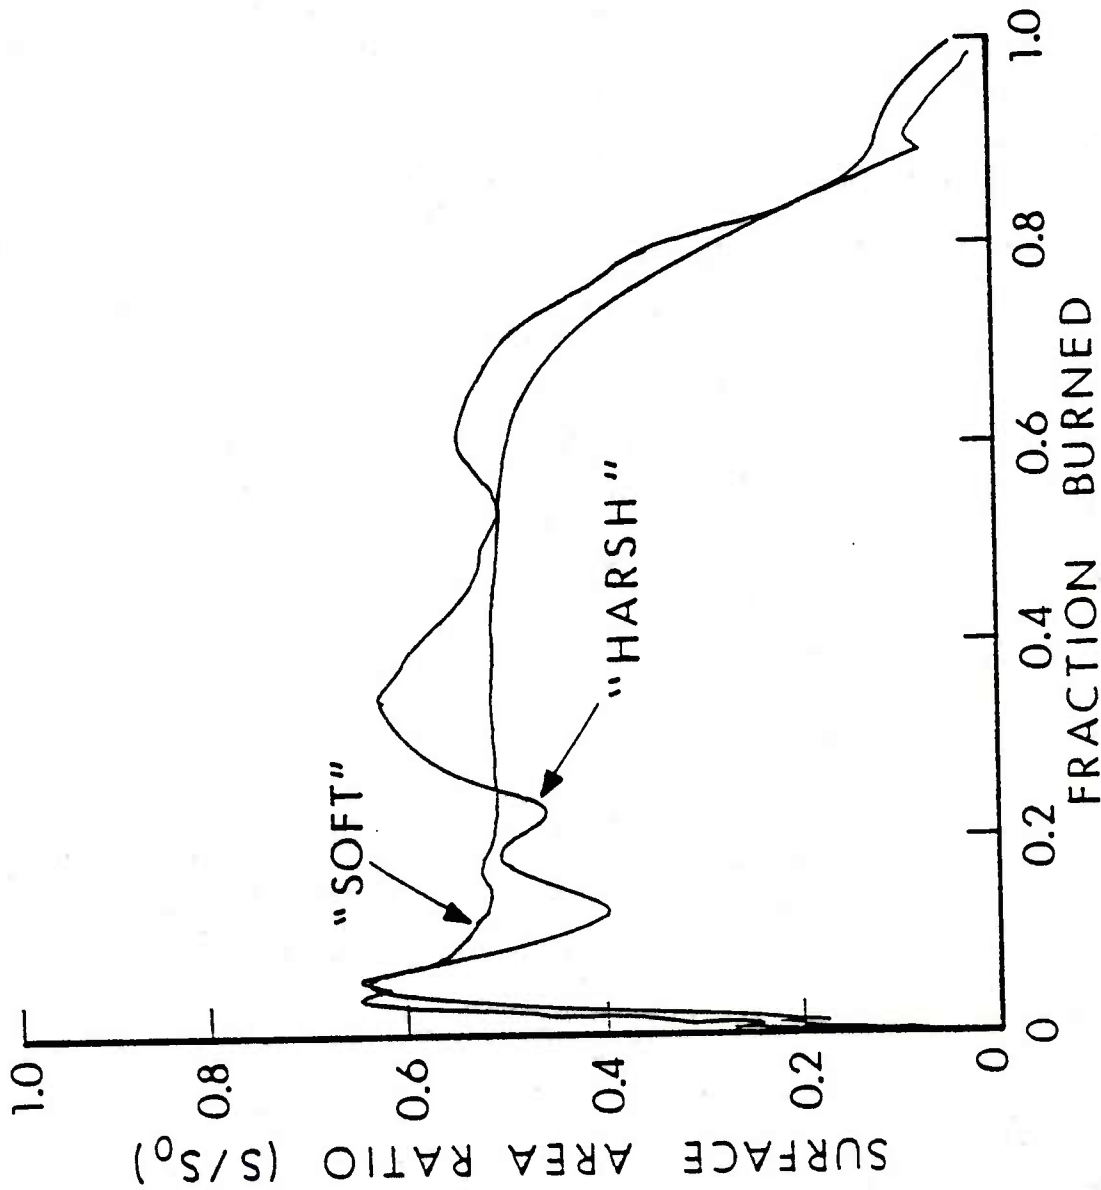


Figure 17. Ignition Effects on Low Compaction Density Double Base Propellant

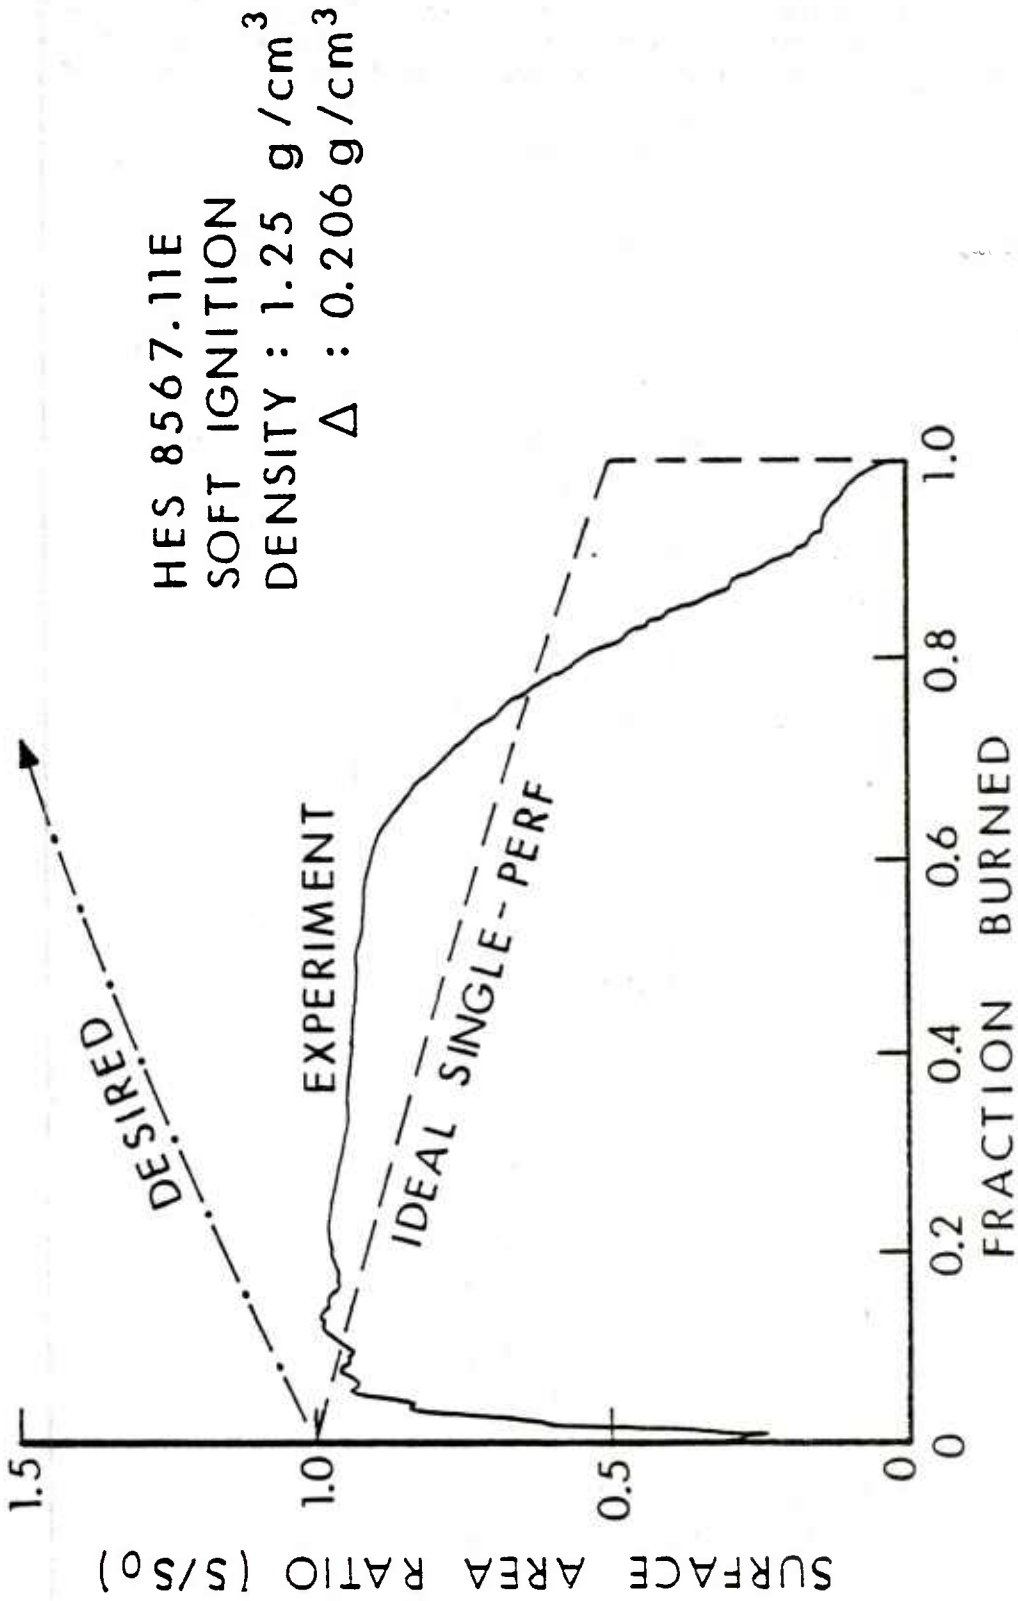


Figure 18. Progressive Burning in Consolidated Charges

x-ray diagnostics would be of great use in visualizing sample deconsolidation processes during burning. Real advances in consolidated charge design methodology can be realized through the interaction of preparation techniques, combustion diagnostics, and theoretical and experimental interior ballistic studies.

REFERENCES

1. F. E. Fortino, "Improved Ballistic Performance for 30-mm Ammunition Using Consolidated Charges," Frankford Arsenal TR-76064, September 1976.
2. W. Witt, E. Melchior, "Thermodynamics Modell der Innenballistik," Wehrtechnik, Juni [1974] 222.
3. B. B. Grollman, P. G. Baer, "Theoretical Studies of the Use of Multi-Propellants in High Velocity Guns," Ballistic Research Laboratory Report R-1411, August 1968.
4. A. W. Horst, T. C. Minor, "Ignition-Induced Flow Dynamics in Bagged-Charge Artillery," 4th International Symposium on Ballistics, Monterey, California, October 1978.
5. A. A. Juhasz, I. W. May, "The Effects of Consolidation on the Burning of Gun Propellants," 15th JANNAF Combustion Meeting, Chemical Propulsion Information Agency, Laurel, MD, Publication 297, December 1978.
6. F. E. Fortino, "Effect of Consolidation Parameters on the Burning of Consolidated Propellant Charges," 1979 JANNAF Propulsion Meeting, Anaheim, California, March 1979.
7. L. Scott, "Consolidated Propellant Charge Investigation, Volume 1: Preparation of Consolidated Charge Increments," Ballistic Research Laboratory Contract Report ARBRL-CR-00408, November 1979. (AD #B043967L)
8. C. F. Price, A. A. Juhasz, "A Versatile User-Oriented Closed Bomb Data Reduction Program (CBRED)," Ballistic Research Laboratory R-2018, September 1977. (AD #A049465)
9. A. A. Juhasz, C. F. Price, "The Closed Bomb Technique for Burning Rate Measurement at High Pressure," Experimental Diagnostics in Combustion of Solids, ed. T. L. Boggs and B. T. Zinn, Vol. 63, Progress in Astronautics and Aeronautics, [1978] 129.

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
12	Commander Defense Technical Info Center ATTN: DDC-DDA Cameron Station Alexandria, VA 22314	1	Director US Army ARRADCOM Benet Weapons Laboratory ATTN: DRDAR-LCB-TL Watervliet, NY 12189
1	Commander US Army Materiel Development and Readiness Command ATTN: DRCDMD-ST 5001 Eisenhower Avenue Alexandria, VA 22333	1	Commander US Army Aviation Research and Development Command ATTN: DRS AV-E P. O. Box 209 St. Louis, MO 63166
1	Commander US Army Materiel Development and Readiness Command ATTN: DRCDE-DW 5001 Eisenhower Avenue Alexandria, VA 22333	1	Director US Army Air Mobility Research and Development Laboratory Ames Research Center Moffett Field, CA 94035
10	Commander US Army Armament Research and Development Command ATTN: DRDAR-TSS (2 cys) DRDAR-LCA H. Fair E. Wurzel S. Bernstein J. Lannon D. Downs A. Beardell DRDAR-LCE, R. Walker DRDAR-SCA, L. Stiefel Dover, NJ 07801	1	Commander US Army Communications Rsch and Development Command ATTN: DRDCO-PPA-SA Fort Monmouth, NJ 07703
1	Commander US Army Armament Materiel Readiness Command ATTN: DRDAR-LEP-L, Tech Lib Rock Island, IL 61299	1	Commander US Army Electronics Research and Development Command Technical Support Activity ATTN: DELSD-L Fort Monmouth, NJ 07703
1	Commander US Army Watervliet Arsenal ATTN: SARWV-RD, R. Thierry Watervliet, NY 12189	1	Commander US Army Missile Command ATTN: DRSMI-R Redstone Arsenal, AL 35809
		2	Commander US Army Missile Command ATTN: DRSMI-YDL DRSMI-RK, R. Rhoades Redstone Arsenal, AL 35809

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Commander US Army Natick Research and Development Command ATTN: DRXRE, D. Sieling Natick, MA 01762	3	Commander Naval Surface Weapons Center ATTN: Code G33, J. East D. McClure Code DX-21, Tech Lib Dahlgren, VA 22448
1	Commander US Army Tank Automotive Research & Development Cmd ATTN: DRDTA-UL Warren, MI 48090	2	Commander Naval Surface Weapons Center ATTN: S. Jacobs/Code 240 Code 730 Silver Spring, MD 20910
2	Commander US Army Materials and Mechanics Research Center ATTN: DRXMR-ATL Tech Lib Watertown, MA 02172	1	Commander Naval Underwater Systems Ctr Energy Conversion Dept. ATTN: Code 5B331, R. Lazar Newport, RI 02840
1	Commander US Army Research Office ATTN: Tech Lib P. O. Box 12211 Research Triangle Park NC 27706	2	Commander Naval Weapons Center ATTN: Code 388, R. Derr C. Price China Lake, CA 93555
1	Director US Army TRADOC Systems Analysis Activity ATTN: ATAA-SL, Tech Lib White Sands Missile Range NM 88002	1	Superintendent Naval Postgraduate School Dept of Mechanical Engineering ATTN: A. Fuhs Monterey, CA 93940
1	Chief of Naval Research ATTN: Code 473, R. Miller 800 N. Quincy Street Arlington, VA 22217	3	Commander Naval Ordnance Station ATTN: P. Stang C. Smith S. Mitchell Indian Head, MD 20640
1	Commander Naval Sea Systems Command ATTN: SEA-62R2, J. Murrin National Center, Bldg. 2 Room 6E08 Washington, DC 20360	1	AFOSR (L. Caveny) Bolling AFB, DC 20332

DISTRIBUTION LIST

<u>No. of</u> <u>Copies</u>	<u>Organization</u>	<u>No. of</u> <u>Copies</u>	<u>Organization</u>
2	AFRPL (DYSC) ATTN: D. George J. Levine Edwards AFB, CA 93523	1	General Electric Company Armament Systems Dept. ATTN: M. Bulman, Rm. 1311 Lakeside Avenue Burlington, VT 05402
1	AFATL/DL DL (O. Heiney) Eglin AFB, FL 32542	1	Hercules, Inc. Allegany Ballistics Laboratory ATTN: R. Miller P. O. Box 210 Cumberland, MD 21502
1	Aerojet Solid Propulsion Co. ATTN: P. Micheli Sacramento, CA 95813	1	Hercules, Inc. Bacchus Works ATTN: K. McCarty P. O. Box 98 Magna, UT 84044
1	ARO Incorporated ATTN: N. Dougherty Arnold AFS, TN 37389	1	Hercules, Inc. Eglin Operations AFATL/DL DL ATTN: R. Simmons Eglin AFB, FL 32542
1	Atlantic Research Corporation ATTN: M. King 5390 Cherokee Avenue Alexandria, VA 22314	1	IITRI ATTN: M. J. Klein 10 W. 35th Street Chicago, IL 60615
1	AVCO Corporation AVCO Everett Rsch Lab Div ATTN: D. Stickler 2385 Revere Beach Parkway Everett, MA 02149	1	Lawrence Livermore Laboratory ATTN: M.S. L-355, A. Buckingham P. O. Box 808 Livermore, CA 94550
1	Calspan Corporation ATTN: E. Fisher P. O. Box 400 Buffalo, NY 14221	1	Olin Corporation Badger Army Ammunition Plant ATTN: R. Thiede Baraboo, WI 53913
1	Foster Miller Associates, Inc. ATTN: A. Erickson 135 Second Avenue Waltham, MA 02154	1	Olin Corporation Smokeless Powder Operations ATTN: R. Cook P. O. Box 222 St. Marks, FL 32355
1	General Applied Science Labs ATTN: J. Erdos Merrick & Stewart Avenues Westbury Long Island, NY 11590		

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Paul Gough Associates, Inc. ATTN: P. Gough P. O. Box 1614 Portsmouth, NH 03801	2	Thiokol Corporation Wasatch Division ATTN: John Peterson Tech Lib P. O. Box 524 Brigham City, UT 84302
1	Physics International Company 2700 Merced Street Leandro, CA 94577	2	United Technologies ATTN: R. Brown Tech Lib P. O. Box 358 Sunnyvale, CA 94086
1	Princeton Combustion Rsch Labs ATTN: M. Summerfield 1041 US Highway One North Princeton, NJ 08540	1	Universal Propulsion Company ATTN: H. McSpadden 1800 W. Deer Valley Road Phoenix, AZ 85027
1	Pulsepower Systems, Inc. ATTN: L. Elmore 815 American Street San Carlos, CA 94070	1	Battelle Memorial Institute ATTN: Tech Lib 505 King Avenue Columbus, OH 43201
1	Rockwell International Corp. Rocketdyne Division ATTN: BA08, J. Flanagan 6633 Canoga Avenue Canoga Park, CA 91304	1	Brigham Young University Dept of Chemical Engineering ATTN: Dr. M. Beckstead Provo, UT 84601
1	Science Applications, Inc. ATTN: R. Edelman 23146 Cumorah Crest Woodland Hills, CA 91364	1	California Institute of Tech 204 Karman Lab Mail Stop 301-46 ATTN: F.E.C. Culick 1201 E. California Street Pasadena, CA 91125
1	Scientific Research Assoc. Inc. ATTN: H. McDonald P. O. Box 498 Glastonbury, CT 06033	1	California Institute of Tech Jet Propulsion Laboratory ATTN: L. Strand 4800 Oak Grove Drive Pasadena, CA 91103
1	Shock Hydrodynamics, Inc. ATTN: W. Anderson 4710-16 Vineland Avenue North Hollywood, CA 91602		
2	Thiokol Corporation Huntsville Division ATTN: D. Flanigan Tech Lib Huntsville, AL 35807		

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Case Western Reserve University Division of Aerospace Sciences ATTN: J. Tien Cleveland, OH 44135	1	Purdue University School of Mechanical Engineering ATTN: J. Osborn TSPC Chaffee Hall West Lafayette, IN 47906
3	Georgia Institute of Tech Schcol of Aerospace Eng. ATTN: B. Zinn E. Price W. Strahle Atlanta, GA 30332	1	Rutgers State University Dept. of Mechanical and Aerospace Engineering ATTN: S. Temkin University Heights Campus New Brunswick, NJ 08903
1	Institute of Gas Technology ATTN: D. Gidaspow 3424 S. State Street Chicago, IL 60616	1	Rensselaer Polytechnic Inst. Department of Mathematics ATTN: D. Drew Troy, NY 12181
1	Johns Hopkins University Applied Physics Laboratory Chemical Propulsion Infor- mation Agency ATTN: T. Christian Johns Hopkins Road Laurel, MD 20810	1	SRI International Propulsion Sciences Division ATTN: Tech Lib 333 Ravenswood Avenue Menlo Park, CA 94024
1	Massachusetts Institute of Technology Dept. of Mechanical Engineering ATTN: T. Toong Cambridge, MA 02139	1	Stevens Institute of Tech Davidson Laboratory ATTN: R. McAlevy, III Hoboken, NJ 07030
1	Pennsylvania State University Applied Research Lab ATTN: G. Faeth P. O. Box 30 State College, PA 16801	1	University of California Los Alamos Scientific Lab ATTN: T3, D. Butler Los Alamos, NM 87554
1	Pennsylvania State University Dept. of Mechanical Engineering ATTN: K. Kuo University Park, PA 16802	1	University of Southern California Mechanical Engineering Dept ATTN: OHE200, M. Gerstein Los Angeles, CA 90007
		1	University of California, San Diego AMES Department ATTN: F. Williams P. O. Box 109 La Jolla, CA 92037

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>
1	University of Illinois AAE Department ATTN: H. Krier Transportation Bldg. Rm 105 Urbana, IL 61801
1	University of Massachusetts Dept. of Mechanical Engineering ATTN: K. Jakus Amherst, MA 01002
1	University of Minnesota Dept. of Mechanical Engineering ATTN: E. Fletcher Minneapolis, MN 55455
2	University of Utah Dept. of Chemical Engineering ATTN: A. Baer G. Flandro Salt Lake City, UT 84112
1	Washington State University Dept. of Mechanical Engineering ATTN: C. Crowe Pullman, WA 99163

Aberdeen Proving Ground

Dir, USAMSAA
ATTN: DRXSY-D
DRXSY-MP, H. Cohen
Cdr, USATECOM
ATTN: DRSTE-TO-F
STEAP-MTA
Dir, USACSL, Bldg. E3516, EA
ATTN: DRDAR-CLB-PA

USER EVALUATION OF REPORT

Please take a few minutes to answer the questions below; tear out this sheet, fold as indicated, staple or tape closed, and place in the mail. Your comments will provide us with information for improving future reports.

1. BRL Report Number _____

2. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which report will be used.)

3. How, specifically, is the report being used? (Information source, design data or procedure, management procedure, source of ideas, etc.) _____

4. Has the information in this report led to any quantitative savings as far as man-hours/contract dollars saved, operating costs avoided, efficiencies achieved, etc.? If so, please elaborate.

5. General Comments (Indicate what you think should be changed to make this report and future reports of this type more responsive to your needs, more usable, improve readability, etc.) _____

6. If you would like to be contacted by the personnel who prepared this report to raise specific questions or discuss the topic, please fill in the following information.

Name: _____

Telephone Number: _____

Organization Address: _____
