



9-9-1991

Comment on "Orientational Ordering Transition in Solid C₆₀"

Ravi Sachidanandam
University of Pennsylvania

A. Brooks Harris
University of Pennsylvania, harris@sas.upenn.edu

Follow this and additional works at: https://repository.upenn.edu/physics_papers

 Part of the [Physics Commons](#)

Recommended Citation

Sachidanandam, R., & Harris, A. (1991). Comment on "Orientational Ordering Transition in Solid C₆₀". *Physical Review Letters*, 67 (11), 1467-1467. <http://dx.doi.org/10.1103/PhysRevLett.67.1467>

This paper is posted at ScholarlyCommons. https://repository.upenn.edu/physics_papers/479
For more information, please contact repository@pobox.upenn.edu.

Comment on "Orientational Ordering Transition in Solid C₆₀"

Abstract

A Comment on the Letter by P. A. Heiney *et al.*, Phys. Rev. Lett. 66, 2911 (1991).

Disciplines

Physics

Comment on "Orientational Ordering Transition in Solid C₆₀"

In an interesting Letter, Heiney *et al.* [1] study the x-ray scattering from powdered solid C₆₀. For temperatures above 249 K they find an orientationally disordered phase in which the freely rotating molecules form an fcc lattice. At lower temperatures their data indicate an orientationally ordered structure (OOS), which, within their resolution, occurs without motion of the centers of the molecules away from their fcc positions. All the powder-diffraction peaks could be indexed according to a simple-cubic unit cell containing four C₆₀ molecules. However, since their fit to the intensities showed some discrepancies, we considered other structures for oriented icosahedra on an fcc lattice which would be consistent with simple-cubic indexing. We determined that most of the fifteen simple-cubic space groups [2] are excluded. For instance, when the icosahedra are on an fcc lattice their symmetry is higher (containing an inversion element) than permitted for space groups 195 and 198. In fact, there are two main possibilities [3]: the one actually used in Ref. [1], $P2_1/n\bar{3}$ (or $Pn\bar{3}$), and that [4] of solid H₂, $P2_1/a\bar{3}$ (or $Pa\bar{3}$), which Heiney *et al.* mentioned but did not actually use. These differ only in the way the molecular threefold axes are distributed over various $\langle 111 \rangle$ directions.

The most general OOS for space group $P2_1/a\bar{3}$ is obtained as follows. Start from a fcc crystal in which all molecules have their twofold axes aligned along the three (1,0,0) directions. Then the molecules centered at (0,0,0), $(\frac{1}{2}, \frac{1}{2}, 0)$, $(\frac{1}{2}, 0, \frac{1}{2})$, and $(0, \frac{1}{2}, \frac{1}{2})$ are rotated through an angle $\phi \neq 0$ about the (1,1,1), $(1, \bar{1}, \bar{1})$, $(\bar{1}, \bar{1}, 1)$, and $(\bar{1}, 1, \bar{1})$ directions, respectively, so that the 240 atoms in the unit cell occupy ten sets of "d" sites [2]. Even after this rotation, these directions remain threefold axes for each of the four sites in the unit cell.

The calculated powder-diffraction intensity for the $Pa\bar{3}$ structure was optimized with respect to the angle ϕ and the authors of Ref. [1] have kindly supplied the results shown in Fig. 1, which was obtained, following the procedures of Ref. [1], taking the lattice parameter to be

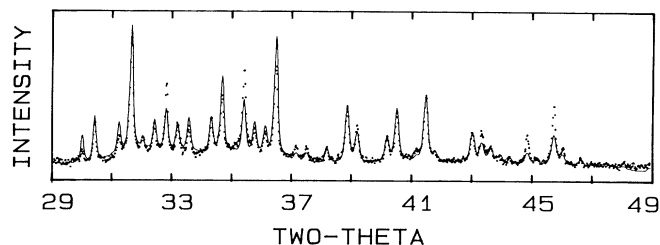


FIG. 1. Dots: A portion of the experimental 11-K x-ray profile from Ref. [1] in which most of the reflections are associated with the OOS. Wavelength 1.1992 Å. Continuous line: Model profile as in Ref. 1 but based on $Pa\bar{3}$ rather than $Pn\bar{3}$ space group.

$a = 14.05$ Å and $\phi = 26^\circ$ to best fit the 11-K data. This fit is significantly better than that found in Ref. [1]. We thus conclude that the OOS structure of solid C₆₀ is $P2_1/a\bar{3}$. The structural parameters and symmetry will be discussed elsewhere [3].

We thank P. A. Heiney for many helpful discussions and the National Science Foundation MRL Program, Grant No. DMR88-19885, for partial support. We thank the authors of Ref. [1] for supplying us with the fit shown in Fig. 1.

Ravi Sachidanandam and A. B. Harris
 Department of Physics
 University of Pennsylvania
 Philadelphia, Pennsylvania 19104

Received 21 June 1991

PACS numbers: 61.50.-f, 35.20.Bm

- [1] P. A. Heiney, J. E. Fischer, A. R. McGhie, W. J. Romanow, A. M. Denenstein, J. P. McCauley, Jr., A. B. Smith, III, and D. E. Cox, *Phys. Rev. Lett.* **66**, 2911 (1991).
- [2] *International Tables for Crystallography*, edited by Theo Hahn (Reidel, Boston, 1983), Vol. 4.
- [3] A. B. Harris and R. Sachidanandam (to be published).
- [4] A. B. Harris, S. Washburn, and H. Meyer, *J. Low Temp. Phys.* **50**, 151 (1983); see Sec. 3.1.