



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Comparative Raman study of isostructural $\text{YCrO}_3$ and $\text{YMnO}_3$ : Effects of structural distortions and twinning

N. D. Todorov, M. V. Abrashev, V. G. Ivanov, G. G. Tsutsumanova, V. Marinova, Y.-Q. Wang, and M. N. Iliev

Phys. Rev. B **83**, 224303 — Published 21 June 2011

DOI: [10.1103/PhysRevB.83.224303](https://doi.org/10.1103/PhysRevB.83.224303)

# Comparative Raman study of isostructural $\text{YCrO}_3$ and $\text{YMnO}_3$ : Effects of the structural distortions and the twinning

N. D. Todorov,<sup>1,\*</sup> M. V. Abrashev,<sup>1</sup> V. G. Ivanov,<sup>1</sup> G. G. Tsutsumanova,<sup>1</sup> V. Marinova,<sup>2</sup> Y.-Q. Wang,<sup>3</sup> and M. N. Iliev<sup>3</sup>

<sup>1</sup>*Faculty of Physics, University of Sofia, 1164 Sofia, Bulgaria*

<sup>2</sup>*Institute for Optical Materials and Technologies, Bulgarian Academy of Sciences, 1113 Sofia, Bulgaria*

<sup>3</sup>*Texas Center for Superconductivity and Department of Physics, University of Houston, Texas 77204-5002, USA*

(Dated: May 13, 2011)

Polarized Raman spectra of isostructural orthorhombic  $\text{YCrO}_3$  and  $\text{YMnO}_3$  single crystals were collected at same conditions using different laser excitation in the visible range. The symmetry of the observed lines was determined and they were assigned to definite atomic vibrations based on lattice dynamical calculations. The frequencies of the lines of the same origin in both compounds are close, however, their intensities differ significantly. While the different intensity of the modes, activated by the Jahn-Teller distortion, can be explained by the different magnitude of this distortion in the two compounds, the cause of the reduced intensity of other lines in low frequency region in the Raman spectra of  $\text{YMnO}_3$  is likely due to the fine twinning of the crystal.

PACS numbers: 78.30.Hv, 63.20.D-, 61.66.Fn

## INTRODUCTION

The interest in the transition-metal perovskite-like oxides  $ABO_3$  continues for decades because of many attractive phenomena observed in these compounds. Among them are structural second-order phase transitions, high- $T_c$  superconductivity, colossal magnetoresistance, charge- and orbital-ordering, complex magnetic properties, etc. As a rule the structural, electrical and magnetic properties of these compounds are strongly correlated. They can be tuned through the change of the mismatch of the A-O and B-O bond lengths, expressed by the tolerance factor  $t = (R_A + R_O)/\sqrt{2}(R_B + R_O)$ , where  $R_O$ ,  $R_A$  and  $R_B$  are the ionic radii of the oxygen and atoms in the A- and B-positions, respectively. Depending on the value of  $t$ , most of these compounds crystallize in superstructures of the ideal cubic perovskite (space group  $Pm\bar{3}m$ ) with  $R\bar{3}c$  or  $Pnma$  symmetry. Using the model of Glazer<sup>1</sup>, treating the  $BO_6$  octahedra as rigid ones, the superstructures can be obtained from the ideal cubic perovskite through some tilts (rotations) of the octahedra around the main crystallographic directions. In the Glazer's notations, the rhombohedral  $R\bar{3}c$  structure is of  $(a^- a^- a^-)$  type and the orthorhombic  $Pnma$  structure is of  $(a^- b^+ a^-)$  type.

Raman spectroscopy is a powerful experimental technique for study of perovskite-like oxides. Due to the fact that there are no Raman-active modes in the ideal cubic perovskite, all observed lines in the one-phonon region of the Raman spectra of the real perovskites have to be connected to some deviations of the real structure from the ideal one. For example, as shown in the pioneering work of Scott<sup>2</sup>, one of the Raman-active modes in the rare-earth aluminates of  $R\bar{3}c$  structure consists in a rigid octahedral tilt around  $[111]$  direction. This mode can be considered as a "soft mode" and its frequency goes to zero as the temperature approaches the critical temperature of the structural second-order phase transition. Iliev *et al.*<sup>3</sup> have shown that in the case of rare-earth manganites with orthorhombic  $Pnma$  structure, two of the observed lines in the Raman spectra originate from modes with a shape of the two static octahedral tilts, existing in the structure. Although that these compounds do not undergo second order transition to higher symmetry phase, the frequency of these lines directly scales the octahedral tilts as it is proportional to the tilt angle.

However, the model of rigid octahedra is inappropriate when the B ion is a Jahn-Teller (JT) ion (as the  $Mn^{3+}$ ). In manganites the JT effect results in presence of two pairs of Mn-O bonds of significantly different length and strongly deformed  $MnO_6$  octahedra. For this reason, to explain the relationship between the intensity of the Raman lines and the structural distortions in orthorhombic manganites, a structural model accounting for four distortions (the two rotations from the Glazer model, the additional JT distortion and the so called A-shift) was proposed<sup>4</sup>. Within the framework of the latter model, it can be concluded that the intensities of 20 out of the all 24 Raman-active modes in the  $GdFeO_3$ -type structure are connected with only one of the above mentioned distortions and the change of the intensities reflects the change of the structural distortions. Using this model it was possible to explain the significant difference of the relative intensity of the  $B_{2g}(1)$  mode, activated by the JT distortion in the spectra of  $CaMnO_3$  (containing non-JT  $Mn^{4+}$  ion) and  $YMnO_3$  (containing JT  $Mn^{3+}$  ion). Unfortunately, the strong dependence of the intensity of many of the rest lines in the Raman spectra of  $CaMnO_3$  on the excitation photon energy (i.e. the resonance effects) hampers the proof of the model in this case. In addition, the different charges of the A and B ions in  $Y^{3+}Mn^{3+}O_3$  and  $Ca^{2+}Mn^{4+}O_3$  impede the comparison of the Raman spectra of these two compounds.

For this reason here we present parallel Raman study of  $YBO_3$  ( $B = Cr, Mn$ ). The isostructural orthorhombic  $Pnma$  compounds have close lattice parameters as well as close values of three of the four structural distortions, as defined in Ref. 4. The only difference is the presence of the JT distortion in  $Mn^{3+}O_6$  octahedra, leading to their strong deformation, whereas the  $Cr^{3+}O_6$  ( $Cr^{3+}$  is not a JT ion) octahedra are symmetric with nearly equal Cr-O bonds. The polarized Raman spectra of each compound, collected using laser excitation with different photon energy in the visible region, are practically identical, which shows that the resonance effects are negligible. It is worth noting here that this could not be concluded from the previous works<sup>3,5-9</sup> because the spectra were obtained with a single laser line. Indeed, several papers on orthorhombic  $YMnO_3$  report polarized<sup>3,6,9</sup> or nonpolarized<sup>7,8</sup> Raman spectra, obtained with either 515 nm or 633 nm laser excitation. For  $YCrO_3$  there is only one early paper<sup>5</sup> on the polarized Raman spectra using 515 nm. In this work we show that there is a significant difference in the intensity of  $B_{2g}(1)$  line (activated by the JT distortion) in  $YCrO_3$  and  $YMnO_3$ . Surprisingly, the intensity of other lines in low frequency region is strongly suppressed in  $YMnO_3$ , despite the close values of the activating structural distortions in both compounds. A comparison with the Raman spectra of other isostructural rare-earth perovskites leads to the conclusion that this is a result of a fine twinning of  $YMnO_3$  single crystals.

## I. EXPERIMENTAL

$YCrO_3$  single crystals were grown by a high-temperature solution growth method in Pt crucibles. We used  $Y_2O_3$  and  $Cr_2O_3$  as starting materials. A solid phase synthesis of stoichiometric powder  $YCrO_3$  was performed at 1100 °C in an oxygen atmosphere for 48 hours. We used complexes  $PbF_2 : KF : B_2O_3$  in ratio 0.75 : 0.23 : 0.02 as solvents. The ratio of the ground material  $YCrO_3$  to the solvents was determined according to the phase diagrams<sup>10,11</sup> of the system  $Y_2O_3$ ,  $Cr_2O_3$ , and  $PbF_2$ . This ratio varies from 1/3 to 1/4. About 600 g of the mixture are semi-hermetically closed in the crucible with a cover in order to prevent the evaporation of  $PbF_2$  and  $KF$ , which have a high vapor pressure at the growth process temperature. The temperature was increased at a rate of 50 °C/h to 1200 °C. To completely dissolve the components of the materials and to achieve a homogeneous solution,

the temperature of 1200 °C was maintained for 48 hours. Then the crucible was slowly cooled at a rate of 0.5 °C/h to 920 °C. At the final temperature the crucible was taken out of the oven, the cover was drilled through and the solvent was poured out. The obtained crystals remained on the ground and the walls of the crucible.

Orthorhombic single crystals of  $\text{YMnO}_3$  were synthesized by solid state reaction under high pressure described in Ref. 12. The chemical composition of the samples was confirmed using scanning electron microscope (SEM; Tescan LYRA) equipped with energy-dispersive X-ray spectrometer (EDX; Bruker). The SEM-EDX observations revealed that both type of crystals had a homogeneous composition of  $\text{Y} : \text{B} = 1 : 1$  ( $\text{B} = \text{Cr}, \text{Mn}$ ) without any impurities.

Polarized Raman spectra were obtained in backscattering geometry from several scattering configurations:  $xx$ ,  $yy$ ,  $zz$ ,  $xz$  and  $yx'$ . In this notation the first and the second letter shows the polarization of the incident and the scattered light, respectively, and  $x$ ,  $y$ ,  $z$  and  $x'$  are parallel to the orthorhombic  $[100]$ ,  $[010]$ ,  $[001]$  and  $[101]$  crystal directions. It is not trivial to identify the orthorhombic  $\langle 100 \rangle$  crystal directions. To do this we use the fact that all quasi-cubic perovskites have good cubic cleavage. This leads to almost perfect cubic shape of their microcrystals with the naturally grown surfaces of cubic  $\{100\}$  type, see Fig. 1. Additionally preliminary measurements of polarized Raman spectra in special configurations according these surface could be made. Only the orthorhombic  $[010]$  direction ( $(010)_o$  surface) is perpendicular to  $\{010\}_c$  plane, so it can easily be identified. However, in  $(010)_o$  surface the  $[100]_o$  and  $[001]_o$  directions are parallel to the diagonals (in the case of rhomb-like surface) of the parallelogram-shaped surface. Because the lattice parameter  $a_o > c_o$ , it follows that  $[100]_o$  direction must be along the longer diagonal, see Fig. 1. The comparison of the angle between  $(101)_o$  and  $(\bar{1}01)_o$  planes (that can be calculated from the published structural data<sup>13</sup>) with the measured angle between the crystal edges  $AO$  and  $BO$  on the photo in Fig. 1 is excellent.

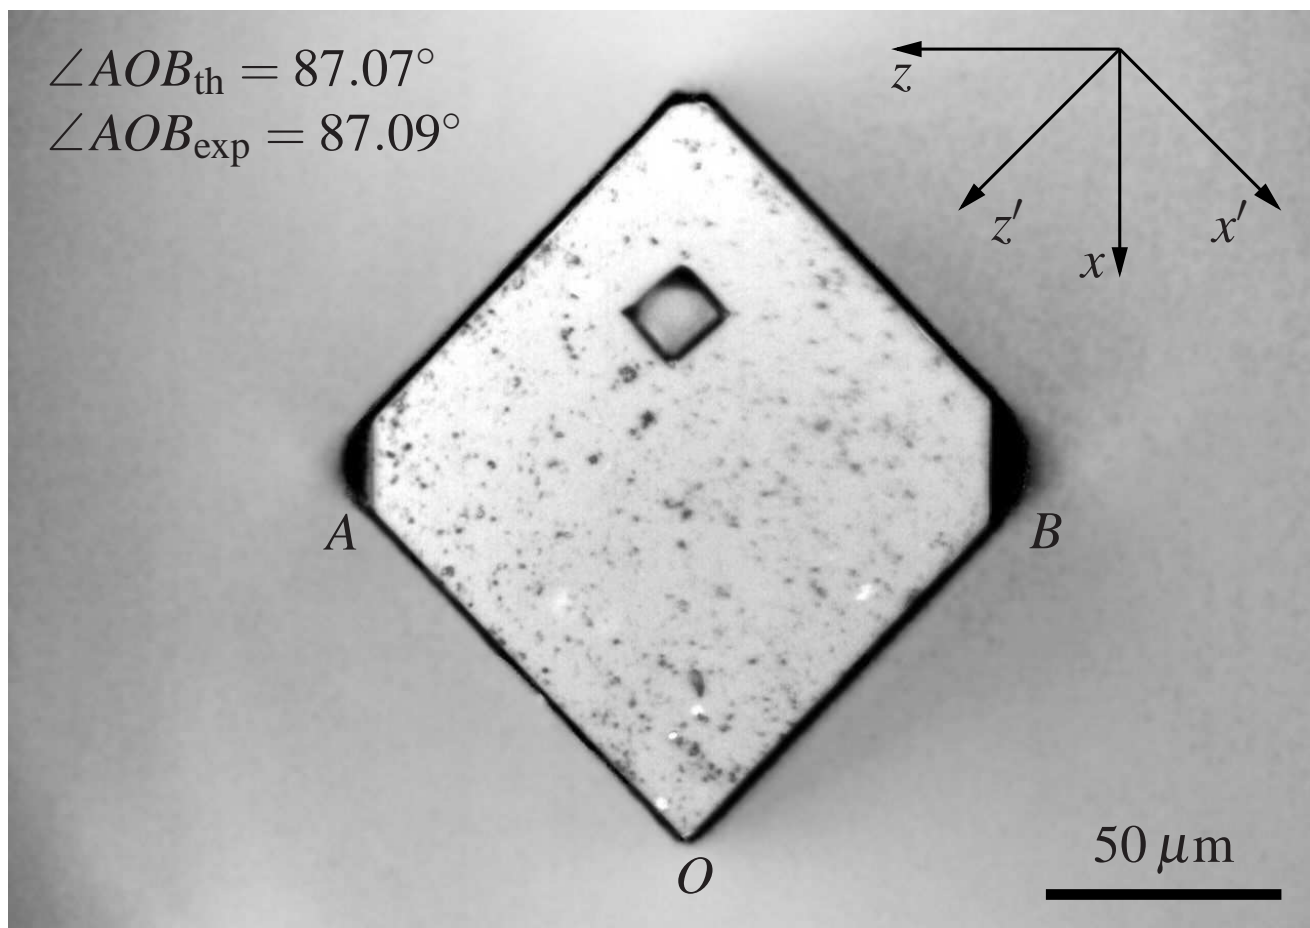


FIG. 1. Optical image of  $(010)$  surface of  $\text{YCrO}_3$  single crystal. The notations used for the crystallographic directions are also given. Comparison of the calculated angle between the vertical  $(101)$  and  $(\bar{1}01)$  orthorhombic surfaces (the crystal edges  $AO$  and  $BO$  on the photo) from the structural data<sup>13</sup> and measured angle directly from the image is done. The last helps us to distinguish  $x$  and  $z$  directions.

The measurements were carried out using micro-Raman spectrometer LabRAM HR800 at room temperature. An objective  $\times 100$  was used both to focus the incident laser beam and to collect the scattered light. To check the presence of resonance effects in the Raman spectra, He-Ne (633 nm) and  $\text{Ar}^+$  (514 and 458 nm) lasers were used as excitation sources. A small set of

preliminary measurements, in which the product (laser power) $\times$ (acquisition time) remains constant, has been done to find out the appropriate power for which the overheating of the samples is negligible. Thus, for both types of crystals and all laser lines the laser power used was about 2 mW. Due to the fine twinning of the YMnO<sub>3</sub> crystals, their nominally  $xx$  and  $zz$  spectra are identical. In contrast, the YCrO<sub>3</sub> crystals are twin-free, as  $xx$  and  $zz$  spectra are significantly different (Fig. 2).

To facilitate the assignment of the Raman lines we performed shell-model lattice-dynamical calculations (LDC) based on interatomic potentials represented as a sum of long-range Coulomb potential and short-range potential in the Born-Mayer-Buckingham form  $U_{\text{short-range}} = A \exp(-r/\rho) - C/r^6$ . In this model an ion is divided into a core with charge  $Z$ , which represent the nucleus and the inner electrons of the ion and has all of its mass, and a massless shell with charge  $Y$  representing the valence electrons of the ion. The ionic polarizability  $\alpha$  is accounted as the interaction between the core and the shell. This interaction can be modeled with a harmonic spring of force constant  $k$ , then the polarizability is given by  $\alpha = Y^2/k$ . The calculations were carried out using the GULP code<sup>14</sup>. The parameters  $Z$ ,  $Y$ ,  $k$ ,  $A$ ,  $\rho$  and  $C$  are listed in Table I. The cell parameters and atomic

TABLE I. Parameters of the potentials of the shell-shell and core-shell interactions. Due to different values of  $k$  for the oxygen in YMnO<sub>3</sub> and YCrO<sub>3</sub> it is marked as O<sub>Mn</sub> and O<sub>Cr</sub>, respectively. All the potentials are taken from Ref. 15, except the one for Cr-O pair which is from Ref. 16.

Ion	$Z( e )$	$Y( e )$	$k(e^2/\text{\AA}^3)$	Ionic pair	$A(eV)$	$\rho(\text{\AA})$	$C(eV\text{\AA}^6)$
Y	2.90			Y-O	1345.1	0.3491	0.000
Mn	0.30	2.80	51.20	Mn-O	715.8	0.3464	0.000
Cr	0.30	2.80	49.50	Cr-O	1763.0	0.2960	0.000
O <sub>Mn</sub>	0.82	-2.82	53.72	O-O	22764.3	0.1490	27.879
O <sub>Cr</sub>	0.82	-2.82	36.70	O-O	22764.3	0.1490	27.879

positions for YMnO<sub>3</sub> and YCrO<sub>3</sub>, used in the calculations, are taken from Ref. 17 and Ref. 13.

## II. DISCUSSION

The orthorhombic YBO<sub>3</sub> (B = Cr, Mn) crystals have GdFeO<sub>3</sub>-type structure<sup>13,17</sup> (space group  $Pnma$ ,  $Z = 4$ ,  $a_o \approx c_o \approx \sqrt{2}a_c$ ,  $b_o \approx 2a_c$ , where  $a_c$  is the lattice parameter of the ideal cubic perovskite). The group theory predicts  $7A_g + 5B_{1g} + 7B_{2g} + 5B_{3g}$  Raman-active modes from the  $\Gamma$ -point of the Brillouin zone<sup>18,19</sup>. The selection rules for these modes as well the symmetry-allowed directions of motion of the atoms, participating in them, are given in Ref. 4 and 6. Polarized Raman spectra, obtained from (010) and (101) surfaces of a YCrO<sub>3</sub> crystal with 515 nm laser excitation are shown in Fig. 2. It is seen in spectra with  $xx$ ,  $yy$  and  $zz$  polarization that 7 lines, observed at 152, 185, 281, 342, 426, 492, and 564  $\text{cm}^{-1}$ , have  $A_g$  symmetry and they correspond to the predicted  $7A_g$  modes. We observe additional eight broad line near 530  $\text{cm}^{-1}$  having also  $A_g$  symmetry. The width of this line is more than two times larger than the width of the other  $A_g$  lines. Its irregular shape is not of Lorentz type and differs in  $xx$ ,  $yy$  and  $zz$  scattering configurations. Therefore we suppose that it does not originate from one-phonon Raman-allowed scattering, rather it has two-phonon origin.

In the  $xz$ -spectrum of YCrO<sub>3</sub> only 4 out of 7 the Raman-allowed  $B_{2g}$  lines are observed. Comparison of  $yy$ - and  $xz$ -spectra of YCrO<sub>3</sub> and YMnO<sub>3</sub> (where all  $7B_{2g}$  are seen), obtained with 633, 515, and 458 nm laser excitation is made in Fig. 3 and Fig. 4, respectively. Their assignment to definite atomic vibrations, based on LDC, is also given. Due to the fact that the all faces of the naturally grown YCrO<sub>3</sub> crystals are with quasi-cubic  $\{100\}$  orientation, it was impossible to measure  $yx$  or  $yz$  spectra, where  $B_{1g}$  and  $B_{3g}$  lines could be observed separately. For this reason in Fig. 2 we present a spectrum with  $yx'$  polarization (obtained from  $(\bar{1}01)_o \equiv (100)_c$  surface), which contains both  $B_{1g}$  and  $B_{3g}$  lines. However, using the data, presented by Udagawa *et al.*<sup>5</sup>, as well as our LDC results, the symmetry of these line also can be determined. In Table II are summarized the frequencies of the observed lines and the calculated ones by LDC in this paper as well previously published data (Ref. 5 for YCrO<sub>3</sub>, Ref. 6 for YMnO<sub>3</sub>). It is seen that the experimental results for YMnO<sub>3</sub> are practically identical.

In the previously published papers<sup>3,6,9</sup>, the Raman spectra of YMnO<sub>3</sub> were obtained only with 633 nm laser excitation. As it can be seen from Figs. 3 and 4 the relative intensity of the observed lines does not depend on the photon excitation energy. Comparing the results for YCrO<sub>3</sub> presented in Ref. 5 and here, because of the much better quality of our spectra, two more weak lines are detected (the line at 611  $\text{cm}^{-1}$  of  $B_{2g}$  symmetry, and the line at 556  $\text{cm}^{-1}$  that based on LDC is a  $B_{1g}$  line). The lack of resonance effects holds also for the spectra of YCrO<sub>3</sub>. On the other hand, from Figs. 3 and 4 it is seen that the relative intensity for lines, corresponding to one and the same mode in both compounds, is very different. For example, the most intensive lines at 618 ( $B_{2g}$ ) and 497  $\text{cm}^{-1}$  ( $A_g$ ) in the YMnO<sub>3</sub> are very weak in YCrO<sub>3</sub>, where they correspond to the lines at 611 and 492  $\text{cm}^{-1}$ . In contrast, the most intensive lines in YCrO<sub>3</sub> (219  $\text{cm}^{-1}$  -  $B_{2g}$  and 281 and 342  $\text{cm}^{-1}$  -  $A_g$ ) are very weak in YMnO<sub>3</sub>. In general, the intensity of a line in a Raman spectrum in specific geometrical configuration is a complex function of the electronic structure of the compound, the energy of the incident photons, the specifics of the crystal structure and the

TABLE II. Comparison between experimental (from this paper and previously published results) and calculated frequencies of the Raman-active lines in  $\text{YCrO}_3$  and  $\text{YMnO}_3$ . The symmetry of the lines, the assignment (based on LDC) to the definite atomic vibrations, and the activating distortions (according Ref. 4) are also given.

Symmetry	$\text{YCrO}_3$			$\text{YMnO}_3$			Assignm.	Activating distortion
	Ref. [5]	exp.	calc.	Ref. [6]	exp.	calc.		
$A_g$	156	152	152	151	150	165	7	A-shift
$A_g$	188	185	185	188	187	217	5	[010]
$A_g$	282	281	229	288	289	265	6	A-shift
$A_g$	346	342	298	323	324	302	2	[010], JT
$A_g$	429	426	384	396	398	373	4	[101]
$A_g$	492	492	429	497	497	483	1	[010], JT
$A_g$	566	564	493	518	519	498	3	[101]
$B_{2g}$			160	151	152	179	7	A-shift
$B_{2g}$	223	219	209	220	222	234	5	[101]
$B_{2g}$			274	317	318	297	4	[101]
$B_{2g}$	318	313	339	341	342	351	6	A-shift
$B_{2g}$			444	481	481	497	3	[101]
$B_{2g}$	502	502	461	537	539	523	2	[010]
$B_{2g}$		611	611	616	618	618	1	JT
$B_{1g}$			193	205	205	226	5	A-shift
$B_{1g}$	272	266	267	284	285	269	4	[010], JT
$B_{1g}$	413	408	329	383	382	327	3	[101]
$B_{1g}$		556	466			414	2	[101]
$B_{1g}$			611			647	1	A-shift
$B_{3g}$	176	174	152	178	179	184	5	[101]
$B_{3g}$			308	336	337	332	4	[010], JT
$B_{3g}$	487	485	440			410	3	[101]
$B_{3g}$	569	567	482			491	2	[101]
$B_{3g}$			619			642	1	[101]

geometrical configuration. However, in our case of  $\text{YBO}_3$  ( $B = \text{Cr}, \text{Mn}$ ) there is no dependence of the relative intensity of a line on the exciting photon energy. Therefore, it is plausible to assume that this intensity is determined mainly by the structural distortion. In the model, proposed in Ref. 4, and adapted for this type of structure, it is concluded that the intensity of the most (20 out of 24) Raman-active lines is governed mainly by only one structural distortion and it will monotonously increases with its value. The assignment of the Raman-active modes and the structural distortion, activating them are shown in Table II (the numbering of the modes follows the notations from Ref. 4).

TABLE III. The values of the structural distortions of several  $\text{YBO}_3$  compounds ( $B = \text{Al}, \text{Ti}, \text{V}, \text{Cr}, \text{Mn}$ ) and  $\text{NdBO}_3$  ( $B = \text{Sc}, \text{Ni}$ ).

Compound	$D_{[101]}$ (deg)	$D_{[010]}$ (deg)	$D_{\text{JT}}$	$D_{\text{A-shift}}$	Ref.
$\text{YAlO}_3$	13.7	10.3	0.0000	0.1062	[20]
$\text{NdScO}_3$	17.5	12.1	0.0054	0.1064	[21]
$\text{YTiO}_3$	18.5	13.4	0.0020	0.1458	[22]
$\text{YVO}_3$	17.6	12.8	0.0102	0.1388	[23]
$\text{YCrO}_3$	16.7	12.2	0.0084	0.1324	[13]
$\text{YMnO}_3$	16.8	14.2	0.0542	0.1710	[17]
$\text{NdNiO}_3$	11.8	8.0	0.0070	0.0700	[24]

In Table III are given the calculated from structural data values of the four structural distortions for some perovskites. The values of rotational distortions  $D_{[101]}$  and  $D_{[010]}$  (in degrees) are calculated according the formulas:  $D_{[101]} = \arctan(2|x_{\text{O}2} - z_{\text{O}2}|)$  and  $D_{[010]} = \arctan\left(\frac{2\sqrt{2}|z_{\text{O}1} + 4\sqrt{2}|y_{\text{O}2}|}{2}\right)$ , where  $x_{\text{O}2}$ ,  $z_{\text{O}2}$ ,  $z_{\text{O}1}$ , and  $y_{\text{O}2}$  are the deviations of the fractional coordinates of oxygen atoms O1 and O2 from their positions in the idealized structure without this type of distortions<sup>4</sup>. As seen from Table III, the values of  $D_{[101]}$ ,  $D_{[010]}$  and  $D_{\text{A-shift}}$  distortions in  $\text{YMnO}_3$  and  $\text{YCrO}_3$  are close, whereas the value of  $D_{\text{JT}}$  is by a factor of 6 larger in  $\text{YMnO}_3$  compared to  $\text{YCrO}_3$ . Only the  $B_{2g}(1)$  mode (in-phase stretching vibration of O2 atoms) is activated solely by  $D_{\text{JT}}$ . Indeed, the line, corresponding to this mode in  $\text{YMnO}_3$ , is the most intensive one, while in  $\text{YCrO}_3$  it is very weak. Moreover, the

second in intensity  $A_g(1)$  line in  $YMnO_3$  is also activated by  $D_{JT}$ . On the other hand, in the Raman spectra of  $ABO_3$  perovskites, containing non-JT ion in B-position (or an JT-ion, which does not produce large difference in the B-O2 distances, as is the case of  $Ti^{3+}$ ), the  $B_{2g}(1)$  line is either weak or even not detectable (see, e.g., B = Al<sup>25</sup>, Sc<sup>26,27</sup>, Ti<sup>28,29</sup>, V<sup>30</sup>, Fe<sup>31,32</sup>, Ni<sup>33</sup>). Therefore, it appears that the intensity of the  $B_{2g}(1)$  line can be used as a measure of the JT-distortion of the  $BO_6$  octahedra.

The intensity of other  $A_g$  and  $B_{2g}$  lines in the low frequency range (below  $350\text{ cm}^{-1}$ ) in the spectra of  $YCrO_3$  are rather strong compared to the corresponding lines in the spectra of  $YMnO_3$  (except for the  $A_g(5)$  line, which has comparable intensity in both compounds). This is somewhat puzzling as both compounds have comparable values of the three other structural distortions, responsible for the intensity. Moreover, the comparison of the polarized Raman spectra (in particular those with  $yy$  polarization) of other isostructural compounds shows that all seven  $A_g$  lines have a relative intensity<sup>27,30</sup> similar to that of  $YCrO_3$ . The reasonable question is why the intensity of these lines in  $YMnO_3$  is so different? It seems that the reason is not in the large value of the JT distortion but rather in the twinning. It can be found that practically all synthesized and investigated single crystals from the type  $A^{3+}B^{3+}O_3$  ( $A^{3+}$  - rare-earth ion), except the manganites, are not twinned, whereas all single crystals of manganites are twinned in the (010) plane (the same plane where the JT orbital ordering holds). Actually, there is only one report<sup>34</sup> on untwinned  $LaMnO_3$  single crystal. In this case the untwinned crystal has been found by chance among the majority of twinned crystals in the ingot and probably it has been naturally detwinned by appropriately oriented uniaxial stress in a small region in the crucible during the cooling. Due to the fact that the size of the twin domains is much smaller than  $1\ \mu\text{m}$  (the diameter of the laser beam used), a considerable part of atoms in the structure are close to a twin boundary and therefore they have incoherent and variable atomic environment, leading to depressing of the corresponding Raman lines. This hypothesis can be proved in a parallel Raman study of twinned and detwinned manganite crystals.

### III. CONCLUSIONS

Single crystals of  $YCrO_3$  and finely twinned crystals of  $YMnO_3$  were studied by micro-Raman spectroscopy in backscattering geometry at room temperature with different scattering configurations. The symmetry of the observed lines was determined from the polarized spectra. In comparison to a previous paper<sup>5</sup> for  $YCrO_3$  two new lines,  $B_{1g}$  and  $B_{2g}$  at  $556$  and  $611\text{ cm}^{-1}$ , are registered. Based on performed lattice dynamical calculations the observed lines are assigned to definite atomic vibrations. The lines in the spectra of  $YCrO_3$  and  $YMnO_3$ , corresponding to same modes, have close frequencies, but significantly different relative intensities. The large intensity of two of the lines ( $B_{2g}(1)$  and  $A_g(1)$ ) in  $YMnO_3$  is explained by the presence of large Jahn-Teller distortion. The low intensity of the rest lines in the spectra of  $YMnO_3$ , if compared to these in  $YCrO_3$ , cannot be explained accounting for the structural distortions. It is concluded that the reduced intensity of these lines is caused by the fine twinning of the manganite crystals related to the JT ordering.

### ACKNOWLEDGMENTS

This work was supported in part by Grants DO02-167/2008, DO02-56/2008, and TK-X-1712/2007 of the Bulgarian National Science Fund, 25/2011 of the Science Fund of the University of Sofia, as well as by the State of Texas through the Texas Center for Superconductivity at the University of Houston (TcSUH).

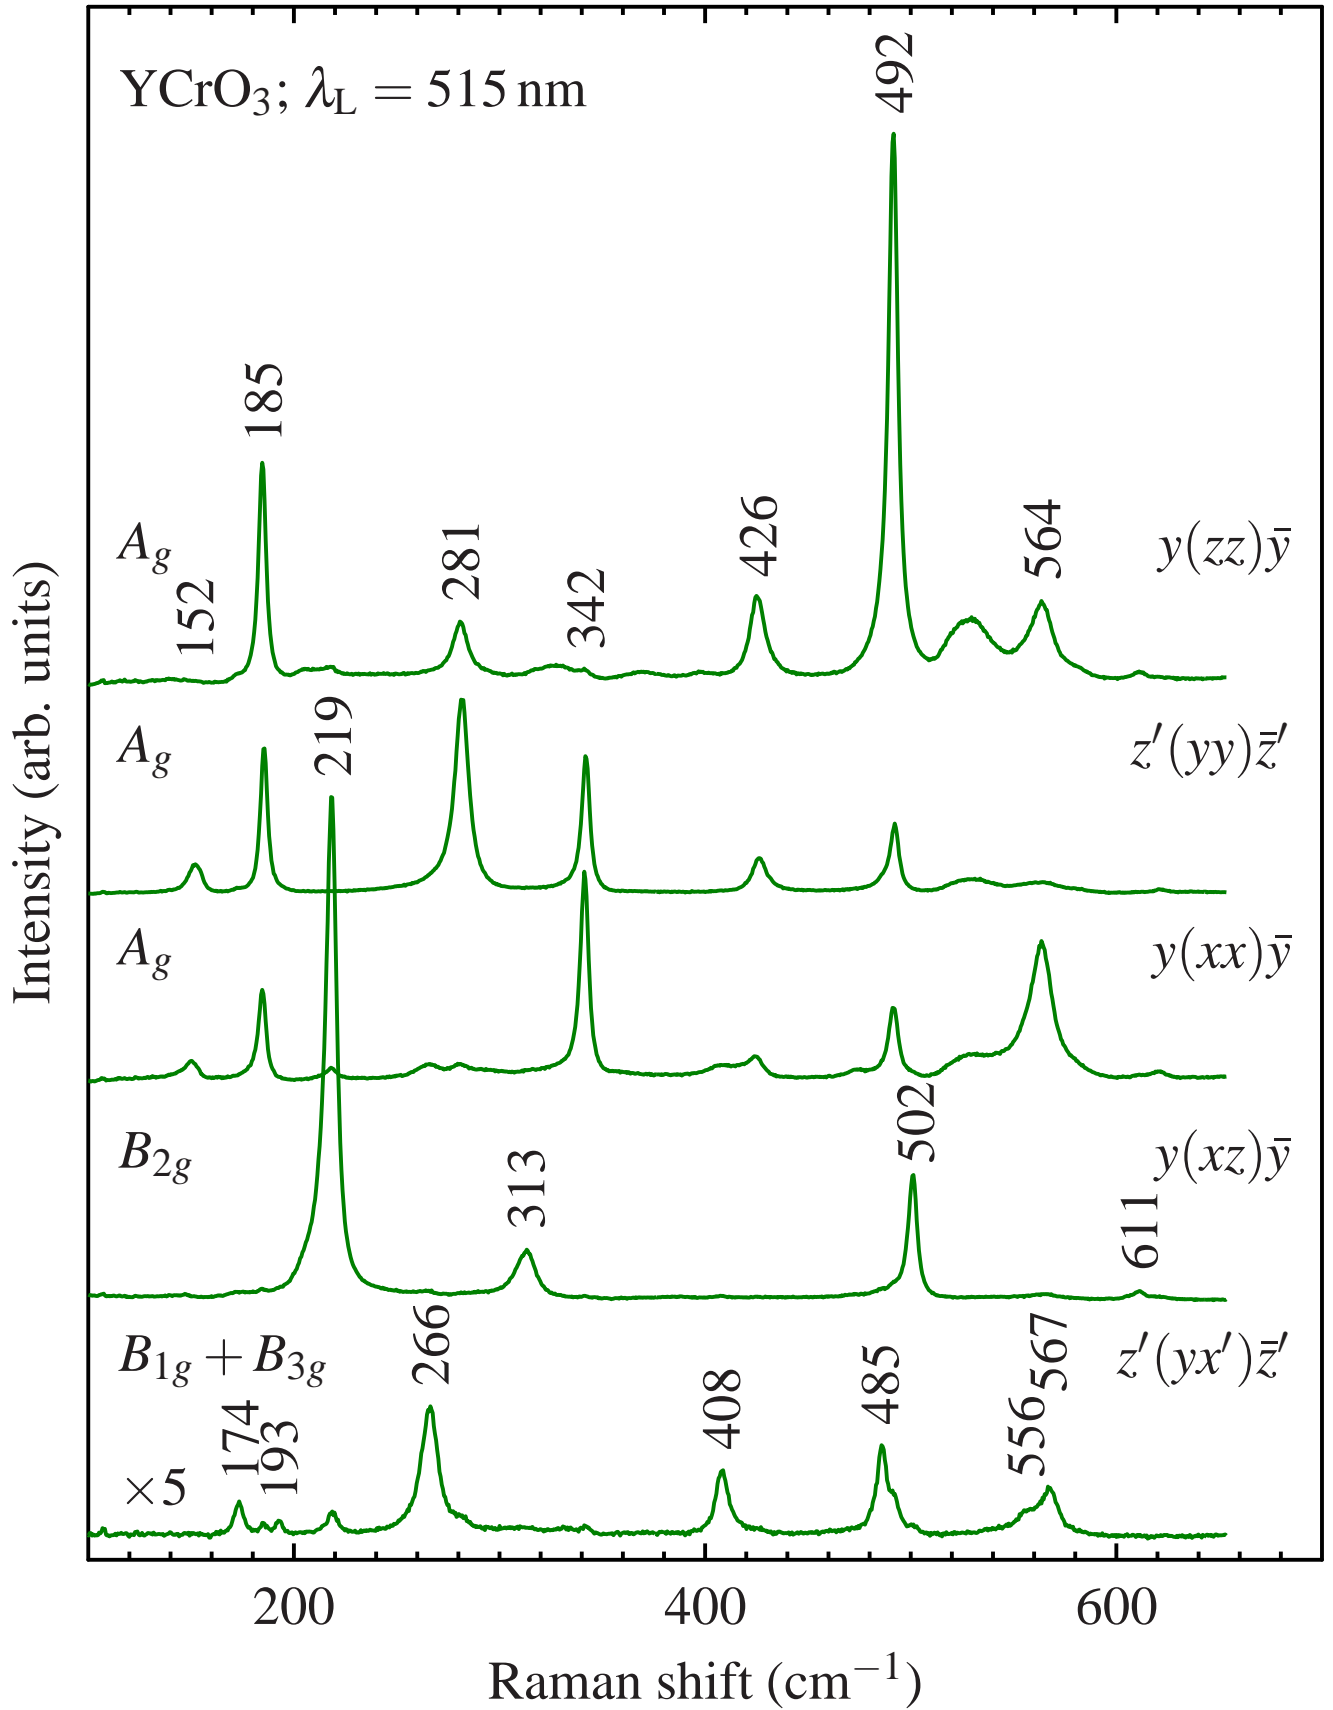


FIG. 2. (Color online) Polarized Raman spectra of YCrO<sub>3</sub> single crystal, obtained from (010) and (101) surfaces with 515 nm laser line. For better comparison  $z'(yx')\bar{z}'$  spectrum is multiplied by 5, and the other spectra are shifted along vertical axis for clarity.



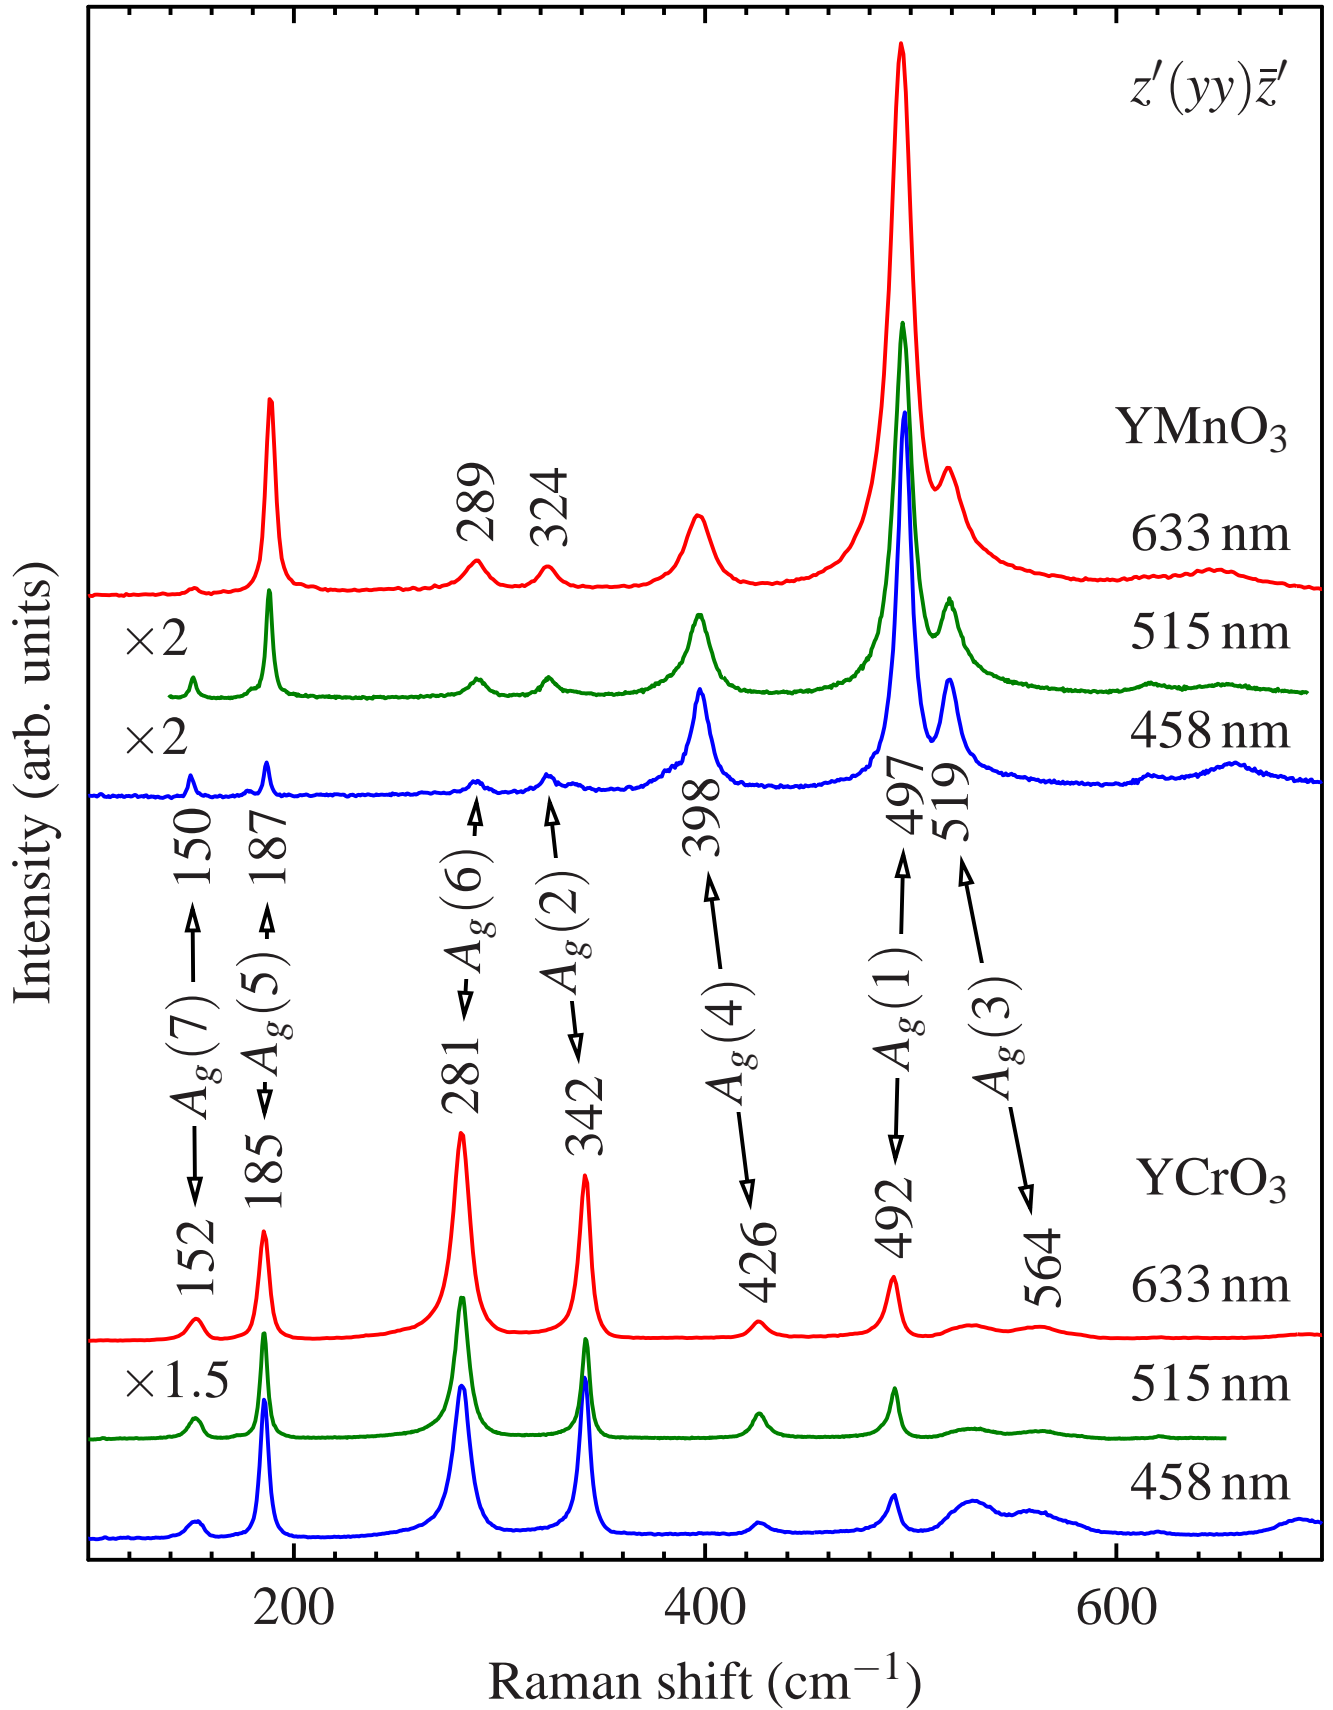


FIG. 3. (Color online) Raman spectra with  $z'(yy)\bar{z}'$  polarization (where only  $A_g$  lines are allowed), obtained from (101) surfaces of YMnO<sub>3</sub> and YCrO<sub>3</sub> single crystals using different laser excitation. For better comparison some of the spectra are multiplied by a number, indicated on the figure. The assignment of the corresponding lines, based on the LDC, is also given.

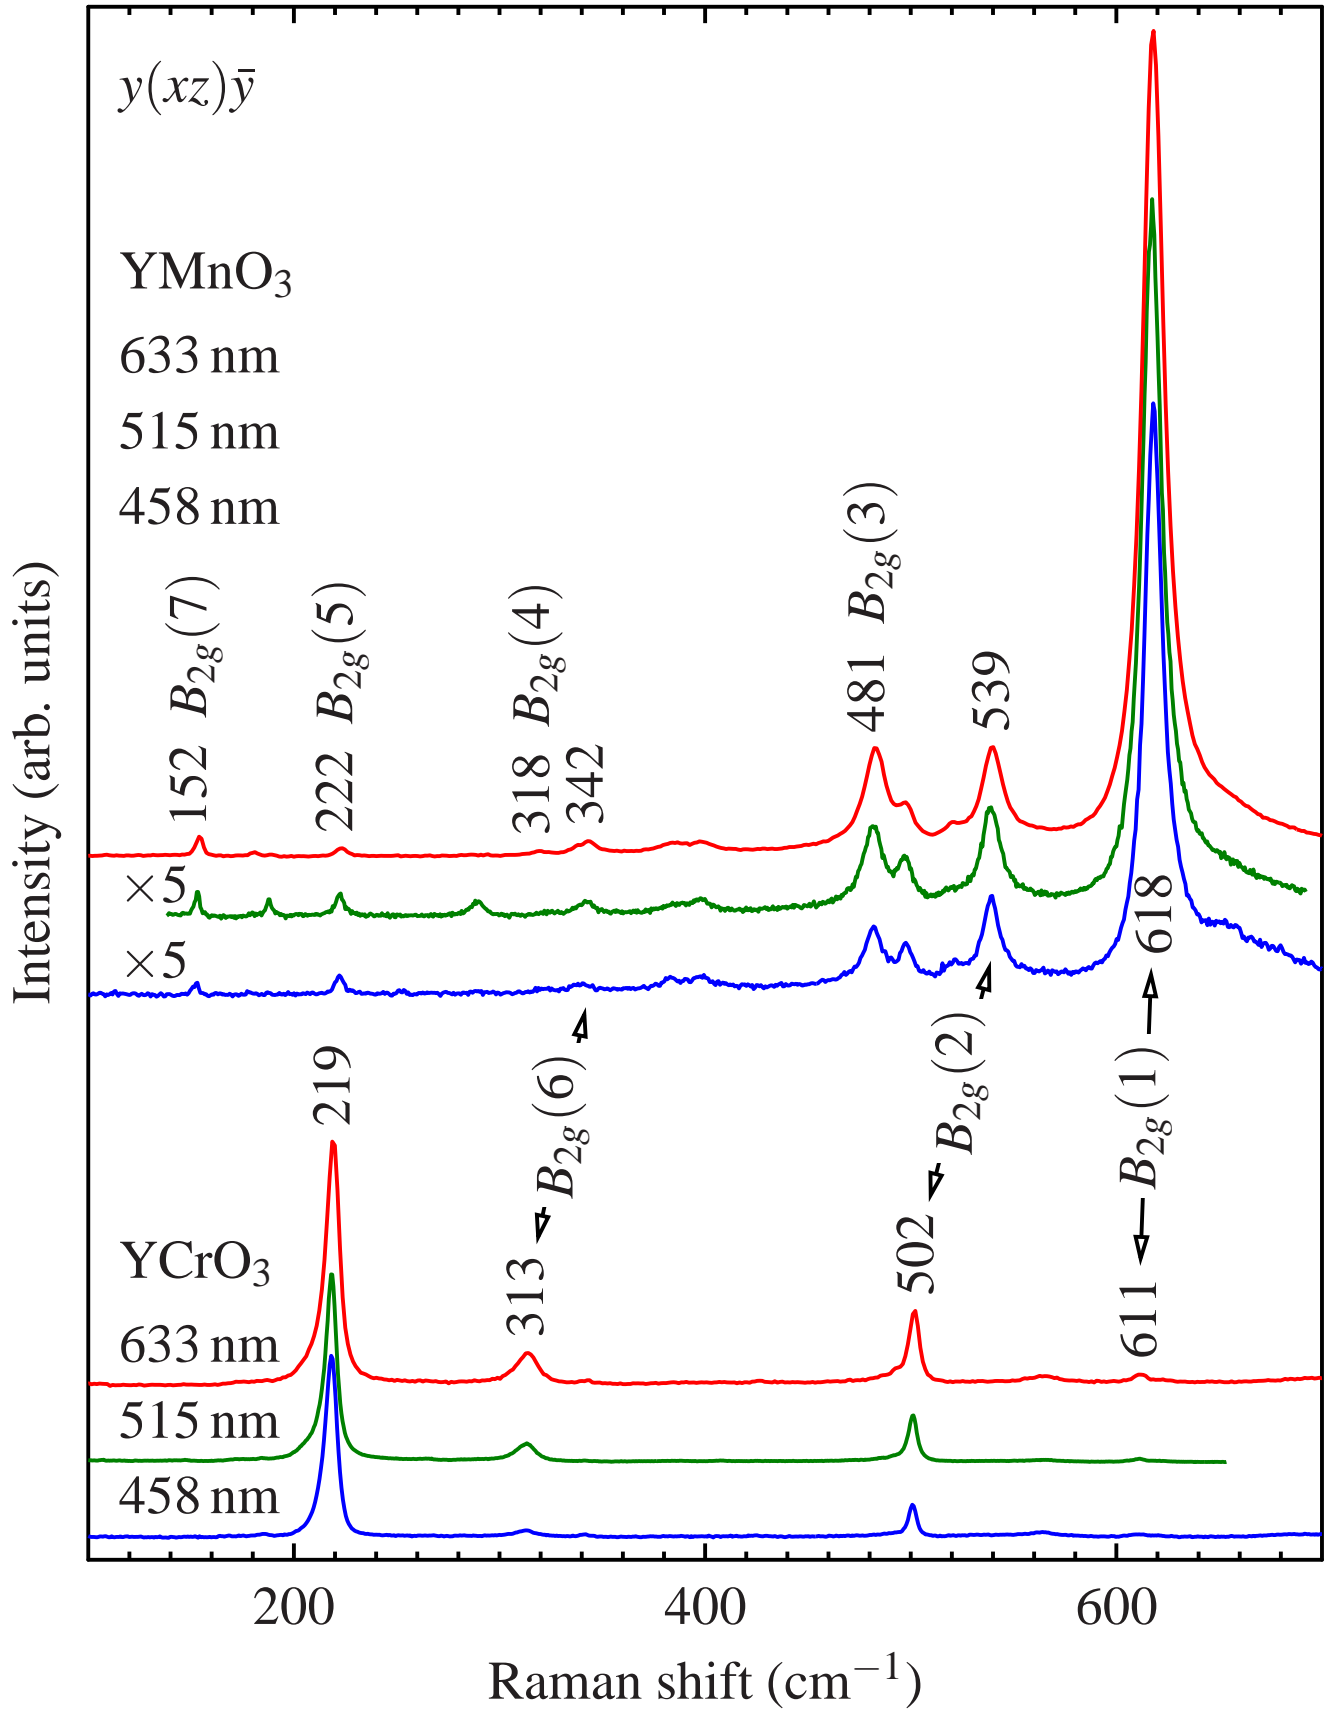


FIG. 4. (Color online) Raman spectra with  $y(xz)\bar{y}$  polarization (where only  $B_{2g}$  lines are allowed), obtained from (101) surfaces of YMnO<sub>3</sub> and YCrO<sub>3</sub> single crystals using different laser excitation. For better comparison some of the spectra are multiplied by a number, indicated on the figure. The assignment of the corresponding lines, based on the LDC, is also given.

- 
- \* [nenov@phys.uni-sofia.bg](mailto:nenov@phys.uni-sofia.bg); Faculty of Physics, University of Sofia, 1164 Sofia, Bulgaria
- 1 A. M. Glazer, *Acta. Crystallogr. B* **28**, 3384 (1972).
  - 2 J. F. Scott, *Phys. Rev.* **183**, 823 (1969).
  - 3 M. N. Iliiev, M. V. Abrashev, J. Laverdière, S. Jandl, M. M. Gospodinov, Y.-Q. Wang, and Y.-Y. Sun, *Phys. Rev. B* **73**, 064302 (2006).
  - 4 M. V. Abrashev, J. Bäckström, L. Börjesson, V. N. Popov, R. A. Chakalov, N. Kolev, R.-L. Meng, and M. N. Iliiev, *Phys. Rev. B* **65**, 184301 (2002).
  - 5 M. Udagawa, K. Kohn, N. Koshizuka, T. Tsushima, and K. Tsushima, *Solid State Commun.* **16**, 779 (1975).
  - 6 M. N. Iliiev, M. V. Abrashev, H.-G. Lee, V. N. Popov, Y. Y. Sun, C. Thomsen, R. L. Meng, and C. W. Chu, *Phys. Rev. B* **57**, 2872 (1998).
  - 7 I. Martín-Carrón, A. de Andrés, M. J. Martínez-Lope, M. T. Casais, and J. A. Alonso, *J. Alloy. Comp.* **323-324**, 494 (2001).
  - 8 L. Martín-Carrón and A. de Andrés, *J. Alloy. Comp.* **323-324**, 417 (2001).
  - 9 J. Laverdière, S. Jandl, A. A. Mukhin, V. Y. Ivanov, V. G. Ivanov, and M. N. Iliiev, *Phys. Rev. B* **73**, 214301 (2006).
  - 10 W. Wong-Ng, R. S. Roth, T. A. Vanderah, and H. F. McMurdie, *J. Res. Natl. Inst. Stand. Technol.* **106**, 1097 (2001).
  - 11 M. Yoshimura, M. Jayaratna, and S. Somiya, *J. Am. Ceram. Soc.* **65**, c166 (1982).
  - 12 M. N. Iliiev, B. Lorenz, A. P. Litvinchuk, Y.-Q. Wang, Y. Y. Sun, and C. W. Chu, *J. Phys.: Condens. Matter* **17**, 3333 (2005).
  - 13 K. Ramesha, A. Llobet, T. Proffen, C. R. Serrao, and C. N. R. Rao, *J. Phys.: Condens. Matter* **19**, 102202 (2007).
  - 14 J. D. Gale, *J. Chem. Soc., Faraday Trans.* **93**, 629 (1997).
  - 15 G. V. Lewis and C. R. A. Catlow, *J. Phys. C: Solid State* **18**, 1149 (1985).
  - 16 M. N. Iliiev, A. P. Litvinchuk, V. G. Hadjiev, Y.-Q. Wang, J. Cmaidalka, R.-L. Meng, Y.-Y. Sun, N. Kolev, and M. V. Abrashev, *Phys. Rev. B* **74**, 214301 (2006).
  - 17 J. A. Alonso, M. J. Martínez-Lope, M. T. Casais, and M. T. Fernández-Diáz, *Inorg. Chem.* **39**, 917 (2000).
  - 18 M. I. Aroyo, A. Kirov, C. Capillas, J. M. Perez-Mato, and H. Wondratschek, *Acta. Crystallogr. A* **62**, 115 (2006).
  - 19 M. I. Aroyo, J. M. Perez-Mato, C. Capillas, E. Kroumova, S. Ivantchev, G. Madariaga, A. Kirov, and H. Wondratschek, *Z. Kristallogr.* **221**, 15 (2006).
  - 20 N. Ross, J. Zhao, and R. Angel, *J. Solid State Chem.* **177**, 1276 (2004).
  - 21 B. Veličkov, V. Kahlenberg, R. Bertram, and M. Bernhagen, *Z. Kristallogr.* **222**, 466 (2007).
  - 22 M. Cwik, T. Lorenz, J. Baier, R. Müller, G. André, F. Bourée, F. Lichtenberg, A. Freimuth, R. Schmitz, E. Müller-Hartmann, and M. Braden, *Phys. Rev. B* **68**, 060401 (2003).
  - 23 G. R. Blake, T. T. M. Palstra, Y. Ren, A. A. Nugroho, and A. A. Menovsky, *Phys. Rev. B* **65**, 174112 (2002).
  - 24 J. L. García-Muñoz, M. A. G. Aranda, J. A. Alonso, and M. J. Martínez-Lope, *Phys. Rev. B* **79**, 134432 (2009).
  - 25 A. Casu, P. C. Ricci, and A. Anedda, *J. Raman Spectrosc.* **40**, 1224 (2009).
  - 26 C. Girardot, J. Kreisel, S. Pignard, N. Caillault, and F. Weiss, *Phys. Rev. B* **78**, 104101 (2008).
  - 27 O. Chaix-Pluchery and J. Kreisel, *Phase Transit.* **84**, 542 (2011).
  - 28 M. Reedyk, D. A. Crandles, M. Cardona, J. D. Garrett, and J. E. Greedan, *Phys. Rev. B* **55**, 1442 (1997).
  - 29 M. N. Iliiev, A. P. Litvinchuk, M. V. Abrashev, V. N. Popov, J. Cmaidalka, B. Lorenz, and R. L. Meng, *Phys. Rev. B* **69**, 172301 (2004).
  - 30 S. Miyasaka, J. Fujioka, M. Iwama, Y. Okimoto, and Y. Tokura, *Phys. Rev. B* **73**, 224436 (2006).
  - 31 N. Koshizuka and S. Ushioda, *Phys. Rev. B* **22**, 5394 (1980).
  - 32 S. Venugopalan, M. Dutta, A. K. Ramdas, and J. P. Remeika, *Phys. Rev. B* **31**, 1490 (1985).
  - 33 M. Zaghrioui, A. Bulou, P. Lacorre, and P. Laffez, *Phys. Rev. B* **64**, 081102 (2001).
  - 34 V. Skumryev, F. Ott, J. Coey, A. Anane, J.-P. Renard, L. Pinsard-Gaudart, and A. Revcolevschi, *Eur. Phys. J. B* **11**, 401 (1999).