

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE January 25, 1996	3. REPORT TYPE AND DATES COVERED preprint of journal article	
4. TITLE AND SUBTITLE Computational Determination of Heats of Formation of Energetic Compounds		5. FUNDING NUMBERS N00014-95-1-0028 Dr. Richard S. Miller R&T Code 33e 1806	
6. AUTHOR(S) Peter Politzer, Jane S. Murray and M. Edward Grice		8. PERFORMING ORGANIZATION REPORT NUMBER 87	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of New Orleans Department of Chemistry New Orleans, Louisiana 70148		10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research Code 333 800 N. Quincy Street Arlington, VA 22217		11. SUPPLEMENTARY NOTES	
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release. Unlimited distribution.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) <p style="text-align: center;">A recently-developed density functional procedure for computing gas phase heats of formation is briefly described and results for several categories of energetic compounds are summarized and discussed. Liquid and solid phase values can be obtained by combining the gas phase data with heats of vaporization and sublimation estimated by means of other relationships. Some observed functional group effects upon heats of formation are noted.</p>			
14. SUBJECT TERMS heats of formation; heats of vaporization; heats of sublimation density functional theory; energetic compounds		15. NUMBER OF PAGES 13	
17. SECURITY CLASSIFICATION OF REPORT Unclassified		16. PRICE CODE	
18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified		19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	
20. LIMITATION OF ABSTRACT Unlimited		20. LIMITATION OF ABSTRACT Unlimited	

19960208 079

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-95-1-0028

R&T Code 4131D02

Dr. Richard S. Miller

Technical Report No. 87

Computational Determination of Heats of Formation of Energetic Compounds

by

Peter Politzer, Jane S. Murray and M. Edward Grice

Prepared for Publication

in

Decomposition, Combustion, and Detonation Chemistry of Energetic Materials  
proceedings of the Materials Research Society, in press.

Department of Chemistry  
University of New Orleans  
New Orleans, LA 70148

January 25, 1996

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

## COMPUTATIONAL DETERMINATION OF HEATS OF FORMATION OF ENERGETIC COMPOUNDS

PETER POLITZER, JANE S. MURRAY AND M. EDWARD GRICE  
University of New Orleans, Department of Chemistry, New Orleans, Louisiana  
70148 USA

### ABSTRACT

A recently-developed density functional procedure for computing gas phase heats of formation is briefly described and results for several categories of energetic compounds are summarized and discussed. Liquid and solid phase values can be obtained by combining the gas phase data with heats of vaporization and sublimation estimated by means of other relationships. Some observed functional group effects upon heats of formation are noted.

### INTRODUCTION

The heat of formation is frequently viewed as a measure of the energy content of a compound. As such, it is an important factor to consider in designing new energetic materials or evaluating existing ones. For example, the heat of formation enters into the calculation of such key explosive and propellant properties as detonation velocity [1,2], detonation pressure [1,2] and specific impulse [3].

We have recently developed a nonlocal density functional procedure for computing gas phase heats of formation [4]. The advantages of a computational approach are of course that it can be applied to suggested target molecules prior to undertaking syntheses, and to newly-prepared compounds even when the available amount is insufficient for laboratory characterization. We have now applied our technique to a variety of molecules that are of potential interest as energetic materials [5-8]. These as well as more recent results will be summarized and discussed.

### THEORY

Our procedure [4] involves calculating  $\Delta E$  for the formation of the molecule from its elements at 0 K followed by conversion to  $\Delta H$  at 298 K by assuming ideal behavior and adding the translational, rotational and vibrational energies. Empirical correction terms corresponding to the various coordination states of the carbons, nitrogens and oxygens are also added.


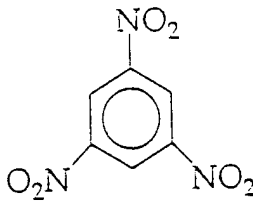


$\Delta E$  is computed by a nonlocal density functional procedure (Gaussian 94 [9], Becke exchange and Perdew correlation functionals [10,11], 6-31G\*\* basis set), using optimized geometries. The vibrational energy was originally determined from the normal mode frequencies, the calculation of which can be quite demanding in terms

of computer resources. We have found, however, that this energy can be estimated accurately from stoichiometry-based relationships [12]; accordingly we now compute the frequencies only when we wish to confirm that the geometry corresponds to a local minimum in the energy (indicated by the absence of imaginary frequencies [13]).

In Table I, our calculated heats of formation are compared to the experimental values for some compounds relevant to the area of energetic materials. Additional comparisons have been presented elsewhere [4]. The average absolute error in the test cases is 3.4 kcal/mole, indicating very satisfactory agreement.

The procedure that has been described yields gas phase heats of formation, and these will be the primary subject of this paper. For practical purposes, however, liquid and solid phase values are often of greater interest; these can be obtained if the heats of vaporization and sublimation are known, using eqs. (1) and (2):

Table I. Comparison of Some Calculated and Experimental Gas Phase Heats of Formation

	Molecule	Heat of formation, kcal/mole	
		Calculated	Experimental
1	$(\text{H}_3\text{C})_2\text{N}-\text{NO}_2$	-2.7 <sup>a</sup>	-1.1 <sup>b</sup>
2		31.4 <sup>c</sup>	33.56 <sup>b</sup>
3		18.2 <sup>c</sup>	14.9 <sup>b</sup>
4		124.3 <sup>d</sup>	130 <sup>e</sup>
5		125.1 <sup>d</sup>	124 <sup>g</sup>

<sup>a</sup>Reference 6.

<sup>b</sup>Reference 45.

<sup>c</sup>Reference 4.

<sup>d</sup>Reference 8.

<sup>e</sup>Extrapolated from the experimental values for the dibenzo- and monobenzo-derivatives, which are 142.8 and 136.4 kcal/mole, respectively.<sup>f</sup>

<sup>f</sup>Y. T. Chia and H. E. Simmons, J. Am. Chem. Soc. 89, 2638 (1967).

<sup>g</sup>Extrapolated from the experimental values for the dibenzo- and monobenzo-derivatives, which are 132.1 and 128.2 kcal/mole, respectively.<sup>f</sup>

$$\Delta H_f^{298}(\text{liquid}) = \Delta H_f^{298}(\text{gaseous}) - \Delta H_{\text{vap}}^{298} \quad (1)$$

$$\Delta H_f^{298}(\text{solid}) = \Delta H_f^{298}(\text{gaseous}) - \Delta H_{\text{sub}}^{298} \quad (2)$$


We have recently developed quantitative representations of both  $\Delta H_{\text{vap}}^{298}$  and  $\Delta H_{\text{sub}}^{298}$  in terms of computed quantities related to electrostatic potentials on molecular surfaces [14,15]; the approach is one that we have used successfully to relate a variety of liquid, solid and solution properties to quantities calculated for individual molecules [14,16,17]. These expressions for  $\Delta H_{\text{vap}}^{298}$  and  $\Delta H_{\text{sub}}^{298}$  can accordingly be used in conjunction with  $\Delta H_f^{298}(\text{gaseous})$  to obtain liquid and solid phase heats of formation, via eqs. (1) and (2).

## RESULTS AND DISCUSSION

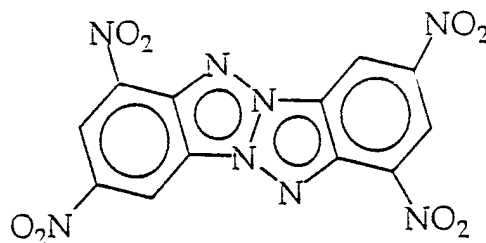
We will present and discuss our computed gas phase heats of formation for several classes of compounds that are currently of interest as potential energetic materials. Some of these data have been published elsewhere, as will be indicated. We will also mention two solid phase heats of formation that we have recently obtained, using eq. (2) and our expression for  $\Delta H_{\text{sub}}^{298}$ .

### 1. Tetraazapentalenes

The presence of several linked nitrogens in a molecule (nitrogen catenation) is frequently associated with instability [18]. It is therefore notable that certain derivatives of the tetraazapentalene **4** show unexpected stability [19-21]; of particular interest in the present context is TACOT, **6**, which has a melting/decomposition temperature of 378° C [22]. We have recently speculated that the surprising stability that has been observed experimentally for the molecular framework **4** may be due to the relatively positive character that we have found for the two triply-coordinated nitrogens [8].





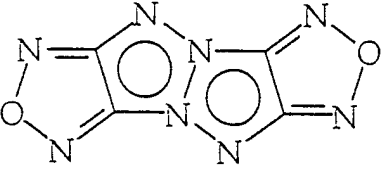
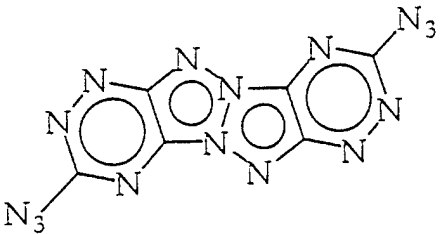
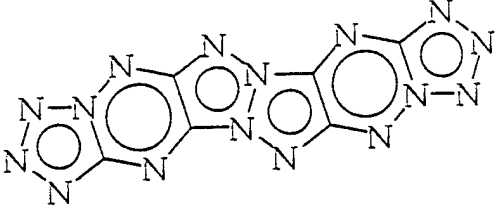
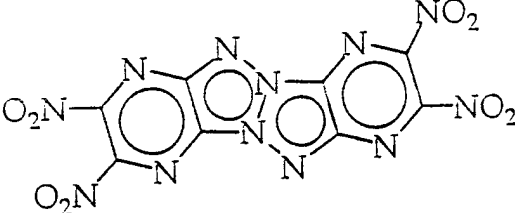
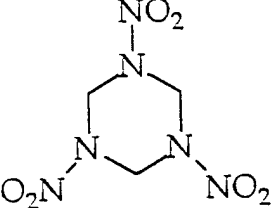
**4**



**6**

In Table II are listed our computed gas phase heats of formation for the two isomeric tetraazapentalenes **4** and **5** and for three of their derivatives. None of these compounds are known at present, although various other derivatives have been prepared [19-21,23,24], including **6** [22]. **7** [25] and **8** and **9** [26] have been proposed as target energetic materials, and synthesis efforts have been undertaken.

Table II. Calculated Gas Phase Heats of Formation of Some Tetraazapentalenes<sup>a</sup>

	Molecule	$\Delta H_f^{298}$ kcal/mole	$\Delta H_f^{298}$ cal/g
4		124	1151
5		125	1158
7		253	1318
8		426	1439
9		442	1493
10		247	630
11 RDX		45.7 (experimental value <sup>b</sup> )	206


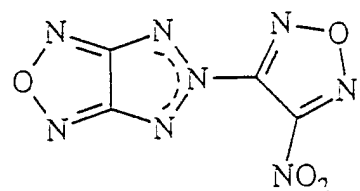
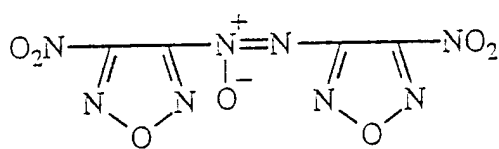

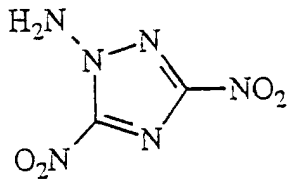
<sup>a</sup>The values for all of the tetraazapentalenes except 10 are from reference 8.

<sup>b</sup>References 27 and 28.

The data in Table II are given in both kilocalories/mole and calories/gram; it is the latter that is relevant for predicting detonation performance [1-3]. In order to provide a basis for comparison, the experimentally-determined gas phase heat of formation of RDX, 11, a prominent military explosive, is also included [27,28].

Most of the tetraazapentalenes in Table II have quite large positive heats of formation, greater by at least a factor of five, in calories/gram, than that of RDX; the high values obtained for the unsubstituted molecules 4 and 5 are particularly striking. The relatively low  $\Delta H_f^{298}$  found for 10 may indicate that

Table III. Calculated Gas Phase Heats of Formation of Some Furazans and Triazoles<sup>a</sup>

	Molecule	$\Delta H_f^{298}$ kcal/mole	$\Delta H_f^{298}$ cal/g
12		43	330
13 NOTO		202	903
14 DNAF		169	621
15 NTO		-5.7	-44
16 ADNT		87	502
11	RDX	45.7 (experimental value <sup>b</sup> )	206

<sup>a</sup>The value for NOTO, 13, is from reference 8.

<sup>b</sup>References 27 and 28.

framework nitrogens are more effective than nitro groups in producing a large heat of formation. The diazide 8 and the ditetrazole 9 are tautomers, which are expected to be related through a tautomeric equilibrium,  $8 \rightleftharpoons 9$ . Our results show the diazide to be the more stable, by about 16 kcal/mole. This could be a matter for concern, from the standpoint of an energetic material, because of the tendency of many azides toward facile decomposition [29].

## 2. Furazans and Triazoles

Like the tetraazapentalenes, the furazans and triazoles in Table III fit into the category of high-nitrogen compounds. However these have actually been synthesized: 12 [30,31], NOTO, 13 [32], DNAF, 14 [33], NTO, 15 [34,35], ADNT, 16 [36]. NOTO has the interesting feature of being a liquid at room temperature [32]. Table III shows that all of these compounds except NTO have positive heats of formation which are considerably larger, on a calories/gram basis, than that of RDX but much smaller than those of most of the tetraazapentalenes in Table II.

## 3. Nitramines and Difluoramines

The difluoramino group,  $-NF_2$ , continues to be of interest as an ingredient of energetic materials, particularly propellants [2,3,37,38]. A judicious combination of nitro and difluoramino substituents offers the possibility of enhanced propellant performance due to an increased number of moles of gaseous combustion products per gram of material (provided that some hydrogens are present) [3,6,39].






In conjunction with recent computational studies of various existing or proposed nitramine and difluoramine systems [6,40], we have calculated the gas phase heats of formation of the compounds in Table IV. While most of them are positive, only 18 has a gas phase value (in calories/gram) greater than that of RDX.

A consistent pattern in Table IV is that  $\Delta H_f^{298}$  is lower (less positive) for the difluoramine than for its nitramine analogue. (Leroy *et al* have observed the same to be true when the  $-NF_2$  and  $-NO_2$  are attached to carbons [41], as we do also for the pair 20, 22.) However the difluoramine may still have a higher specific impulse (a measure of propellant thrust [3,22,39]) due to producing more moles of gaseous products per gram upon combustion. Thus the specific impulse of 23 is predicted to be higher than that of RDX, 11, despite having a lower estimated heat of formation [3].





Table IV. Calculated Gas Phase Heats of Formation of Some Nitramines and Difluoramines<sup>a</sup>

	Molecule	$\Delta H_f^{298}$ kcal/mole	$\Delta H_f^{298}$ cal/g
1	$(H_3C)_2N-NO_2$	-2.7	-30
17	$(H_3C)_2N-NF_2$	-20	-206
18		44	297
19		29	186
20 TNAZ		31	160
21		16	79
22		7.4	38
11	RDX	45.7 (experimental value <sup>b</sup> )	206

<sup>a</sup>All of these calculated results except that for 22 are from reference 6.






<sup>b</sup>References 27 and 28.

#### 4. Some C, N, O, F Compounds

We have investigated computationally a group of 19 unsaturated molecules that contain only the elements C, N, O and F (Table V) [7]. Their high N/C and O/C ratios suggest that these are potential energetic molecules or precursors. To the best of our knowledge, most of these molecules are presently unknown, an exception being 26 [42,43].

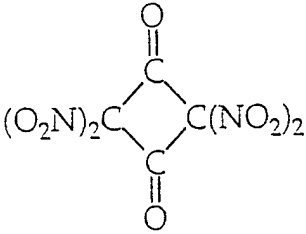
The calculated gas phase heats of formation are given in Table V. These were obtained by a slightly modified version of the method described earlier, in that *ab initio* HF/6-31G\* optimized geometries and vibrational frequencies were used and  $\Delta E$  was computed with the density functional program DeMon [44]. Structures 26A, dinitrosoacetylene, and 26B, which is more accurately designated as dinitrile-di-N-oxide, were both found to correspond to energy minima at the *ab initio* HF/6-31G\*

Table V. Calculated Gas Phase Heats of Formation of Some C, N, O, F Compounds<sup>a</sup>

	Molecule	$\Delta H_f^{298}$ kcal/mole	$\Delta H_f^{298}$ cal/g
24	$O_2N-C\equiv C-NO_2$	89	763
25	$O_2N-C\equiv C-NO$	100	1004
26A	$ON-C\equiv C-NO$	130	1550
26B	$ON\equiv C-C\equiv NO$	73	868
27	$O_2N-C\equiv C-NF_2$	74	606
28	$ON-C\equiv C-NF_2$	95	901
29	$N_3-C\equiv C-NO_2$	144	1287
30	$OCN-C\equiv C-NO_2$	54	486
31		80	426
32		108	572
33	$(O_2N)_2C=C=O$	3	22
34	$O_2N-N=C=N-NO_2$	87	659
35	$(O_2N)_2C=C=C=O$	39	274
36	$(O_2N)_2C=C=C=N-NO_2$	115	613
37	$O_2N-N=C=C=N-NO_2$	128	888
38	$O_2N-N=C=C=C=N-NO_2$	136	870
39		102	465
40		135	716
41		130	559

(continued)

Table V. Calculated Gas Phase Heats of Formation of Some C, N, O, F Compounds<sup>a</sup>  
(continued)

Molecule	$\Delta H_f^{298}$ kcal/mole	$\Delta H_f^{298}$ cal/g
42 	9	35
11 RDX	45.7	206 (experimental value <sup>b</sup> )

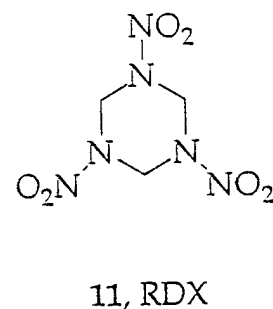
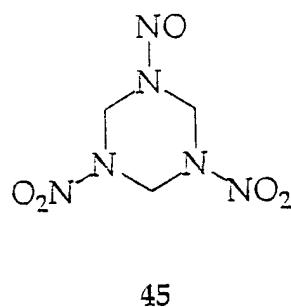


<sup>a</sup>The results for 24 - 30, 33-35, 37 and 38 are in reference 7.

<sup>b</sup>References 27 and 28.

level [7]. Table V shows that 26B is the more stable, which is consistent with experimental evidence [42,43].

Most of these compounds are predicted to have rather large positive heats of formation (calories/gram). One of the highest, not surprisingly, is the azide 29. The pairs 24, 27 and 25, 28 show again that replacing  $-\text{NO}_2$  by  $-\text{NF}_2$  lowers  $\Delta H_f^{298}$ , as observed above when these groups were on nitrogens.

Particularly striking, especially on a calories/gram basis, is the *increase* in  $\Delta H_f^{298}$  that occurs when the nitro group is replaced by the nitroso. This can be seen in 24, 25 and 26A and again in 27 and 28. (26B is more nitrile-N-oxide than nitroso in character, as mentioned above.) This effect has also been observed experimentally; the heat of formation of 43 is 46.44 kcal/mole (322.5 cal/g) vs. 13.9 kcal/mole (79.0 cal/g) for 44 [45]. In view of these findings, it is interesting to note evidence



suggesting the possibility of another desirable consequence of substituting  $-\text{NO}$  for  $-\text{NO}_2$ ; an experimental study showed that the impact sensitivity of 45 is significantly less than that of RDX, 11, while the explosive power (measured by dent depth) is essentially the same [46].

A further comparison of interest is between  $=\text{C}(\text{NO}_2)_2$  compounds and their  $=\text{N}(\text{NO}_2)$  analogues. The latter have the greater heats of formation, as can be seen from the pairs 36, 37 and 40, 41.

## 5. Solid Phase Heats of Formation

As was pointed out earlier in this paper, we now have the means for reliably estimating heats of vaporization and sublimation [14,15]. These permit us to convert our computed gas phase heats of formation to liquid and solid phase values, using eqs. (1) and (2), respectively. We have thus far applied this procedure to two compounds, 1,3,3-trinitroazetidine (20, TNAZ) and DNAF (14).

For TNAZ, we find  $\Delta H_{\text{sub}}^{298} = 22$  kcal/mole; when combined with  $\Delta H_{\text{f}}^{298}$  (gaseous) = 31 kcal/mole (Table IV) via eq. (2), the result is  $\Delta H_{\text{f}}^{298}$  (solid) = 9 kcal/mole. This is in excellent agreement with the experimental value, 8.7 kcal/mole [38]. For DNAF, we obtain  $\Delta H_{\text{sub}}^{298} = 32$  kcal/mole. Using  $\Delta H_{\text{f}}^{298}$  (gaseous) = 169 kcal/mole (Table III), eq. (2) gives  $\Delta H_{\text{f}}^{298}$  (solid) = 137 kcal/mole.

## CONCLUSIONS

We have presented and discussed the results of density functional calculations of gas phase heats of formation for several categories of energetic compounds. We have also demonstrated the feasibility of converting these to solid phase values.

For the systems investigated, some key observations are:

- (1) The tetraazapentalenes have particularly large positive heats of formation (calories/gram).
- (2) Replacement of a nitro by a difluoramino group, whether on a carbon or on a nitrogen, lowers the heat of formation.
- (3) Replacement of a nitro by a nitroso group increases the heat of formation.
- (4) Replacement of  $=\text{C}(\text{NO}_2)_2$  by  $=\text{N}-\text{NO}_2$  increases the heat of formation.

## ACKNOWLEDGMENT

We greatly appreciate the financial support of the Office of Naval Research, through contract No. N00014-95-1-0028 and Program Officer Dr. Richard S. Miller.

## REFERENCES

- <sup>1</sup>M. J. Kamlet and S. J. Jacobs, *J. Chem. Phys.* **48**, 23 (1968).
- <sup>2</sup>T. Urbanski, *Chemistry and Technology of Explosives* (Pergamon Press, New York, 1984).
- <sup>3</sup>P. Politzer, J. S. Murray, M. E. Grice and P. Sjöberg, in *Chemistry of Energetic Materials*, edited by G. A. Olah and D. R. Squire (Academic Press, New York, 1991), ch. 4.
- <sup>4</sup>D. Habibollahzadeh, M. E. Grice, M. C. Concha, J. S. Murray and P. Politzer, *J. Comp. Chem.* **16**, 654 (1995).
- <sup>5</sup>P. Politzer, P. Lane, P. Sjöberg and M. E. Grice, Technical Report No. 72, Contract No. N00014-91-J-4057, Office of Naval Research, Arlington, VA, October 20, 1994.

- <sup>6</sup>P. Politzer, P. Lane, M. E. Grice, M. C. Concha and P. C. Redfern, *J. Mol. Struct. (Theochem)* **338**, 249 (1995).
- <sup>7</sup>P. Politzer, P. Lane, P. Sjöberg, M. E. Grice and H. Shechter, *Struct. Chem.* **6**, 217 (1995).
- <sup>8</sup>M. E. Grice and P. Politzer, *J. Mol. Struct.*, in press.
- <sup>9</sup>M. J. Frisch, G. W. Trucks, H. B. Schlegel, P. M. W. Gill, B. G. Johnson, M. A. Robb, J. R. Cheeseman *et al.*, *Gaussian 94 (Revision B.3)* (Gaussian, Inc., Pittsburgh, PA, 1995).
- <sup>10</sup>A. D. Becke, *Phys. Rev. A* **38**, 3098 (1988).
- <sup>11</sup>J. P. Perdew, *Phys. Rev. B* **33**, 8822 (1986).
- <sup>12</sup>M. E. Grice and P. Politzer, *Chem. Phys. Lett.* **244**, 295 (1995).
- <sup>13</sup>W. J. Hehre, L. Radom, P. v. R. Schleyer and J. A. Pople, *Ab Initio Molecular Orbital Theory* (Wiley-Interscience, New York, 1986).
- <sup>14</sup>J. S. Murray and P. Politzer, in *Quantitative Treatments of Solute/Solvent Interactions*, edited by J. S. Murray and P. Politzer (Elsevier, Amsterdam, 1994), ch. 8.
- <sup>15</sup>M. DeSalvo, E. Miller, J. S. Murray and P. Politzer, unpublished work.
- <sup>16</sup>J. S. Murray, T. Brinck, P. Lane, K. Paulsen and P. Politzer, *J. Mol. Struct. (Theochem)* **307**, 55 (1994).
- <sup>17</sup>P. Politzer, J. S. Murray, T. Brinck and P. Lane, in *Immunoanalysis of Agrochemicals; Emerging Technologies*, edited by J. O. Nelson, A. E. Karu, and R. B. Wong (ACS, Washington, 1995), ch. 8.
- <sup>18</sup>F. R. Benson, *The High Nitrogen Compounds* (Wiley-Interscience, New York, 1984).
- <sup>19</sup>R. A. Carboni and J. E. Castle, *J. Am. Chem. Soc.* **84**, 2453 (1962).
- <sup>20</sup>R. Pflieger, E. Garthe and K. Raner, *Chem. Ber.* **96**, 1827 (1963).
- <sup>21</sup>R. A. Carboni, J. C. Kauer, J. E. Castle and H. E. Simmons, *J. Am. Chem. Soc.* **89**, 2618 (1967).
- <sup>22</sup>J. Köhler and R. Meyer, *Explosives*, 4th ed. (VCH Publishers, New York, 1993).
- <sup>23</sup>R. A. Carboni, J. C. Kauer, W. R. Hatchard and R. J. Harder, *J. Am. Chem. Soc.* **89**, 2626 (1967).
- <sup>24</sup>J. C. Kauer and R. A. Carboni, *J. Am. Chem. Soc.* **89**, 2633 (1967).
- <sup>25</sup>J. H. Boyer and M. L. Trudell, private communication.
- <sup>26</sup>M. L. Trudell, private communication.
- <sup>27</sup>D. R. Stull, E. F. Westrum and G. C. Sinke, *The Chemical Thermodynamics of Organic Compounds* (Wiley, New York, 1969).
- <sup>28</sup>J. M. Rosen and C. Dickinson, *J. Chem. Eng. Data* **14**, 120 (1969).
- <sup>29</sup>J. H. Boyer and F. C. Canter, *Chem. Rev.* **54**, 1 (1954).
- <sup>30</sup>G. D. Solodynk, M. D. Boldyrev, B. V. Gidasov and V. D. Nikolaev, *Zh. Org. Khim.* **17**, 861 (1981).
- <sup>31</sup>A. Gunasekaran, private communication.
- <sup>32</sup>A. Gunasekaran and J. H. Boyer, *Heteroatom Chem.* **4**, 521 (1993).
- <sup>33</sup>A. Gunasekaran, M. L. Trudell and J. H. Boyer, *Heteroatom Chem.* **5**, 441 (1994).

- <sup>34</sup>K.-Y. Lee and M. D. Coburn, U. S. Patent , 4,733,610 (1988).
- <sup>35</sup>K.-Y. Lee and R. Gilardi, in *Structure and Properties of Energetic Materials*, edited by D. H. Liebenberg, R. W. Armstrong and J. J. Gilman (Materials Research Society, Pittsburgh, 1993).
- <sup>36</sup>R. Schmitt and J. Bottaro, SRI International, private communication.
- <sup>37</sup>R. F. Gould, in *Advances in Chemistry Series, No. 54* (American Chemical Society, Washington, 1966).
- <sup>38</sup>T. G. Archibald, L. C. Garver, A. A. Malik, F. O. Bonsu, D. D. Tzeng, S. B. Preston and K. Baum, Report No. ONR-2-10, Office of Naval Research, Arlington, VA, Contract No. N00014-78-C-0147, February, 1988.
- <sup>39</sup>R. T. Holzmann, in *Advanced Propellant Chemistry*, edited by R. F. Gould (American Chemical Society, Washington, 1966), Ch. 1.
- <sup>40</sup>P. Politzer and M. E. Grice, *J. Chem. Res. (S)* , 296 (1995).
- <sup>41</sup>G. Leroy, M. Sana, C. Wilante, D. Peeters and S. Bourasseau, *J. Mol. Struct. (Theochem)* 187, 251 (1989).
- <sup>42</sup>C. Grundmann, *Angew. Chem.* 75, 450 (1963).
- <sup>43</sup>C. Grundmann, V. Mini, J. M. Dean and H.-D. Frommeld, *Liebigs. Ann. Chem.* 687, 191 (1965).
- <sup>44</sup>D. R. Salahub, R. Fournier, P. Mlynarski, I. Papai, A. St. Amant and J. Ushio, in *Density Functional Methods in Chemistry*, edited by J. K. Labanowski and J. W. Andzelm (Springer-Verlag, New York, 1991), ch. 6.
- <sup>45</sup>J. B. Pedley, R. D. Naylor and S. P. Kirby, *Thermochemical Data of Organic Compounds*, 2nd ed. (Chapman and Hall, London, 1986).
- <sup>46</sup>S. Iyer, *Propell. Expl. Pyrotech.* 7, 37 (1982).