

The laser threshold is extremely low since it takes very little pump power to almost fully invert the Er^{3+} ions. The FBG slope efficiency can be improved by increasing the EDF length, using higher erbium concentration EDF and reducing the cavity loss. The laser operates as a three level laser system when excited by a 980 nm pump laser so that a length of unpumped fiber absorbs strongly at the lasing wavelength. For a given fiber length, lasing can occur only if the gain available from the bleached section equals, or exceeds, the loss of the remaining length. The use of high concentration EDF will increase the absorption per unit length and it can reduce the EDF length requirement. The low cavity loss increases the oscillating laser power in the cavity.

Wavelength tuning in the fiber laser is achieved by heating the FBG. The laser oscillates at particular wavelength, corresponding to the center wavelength of the FBG. The variation in Bragg wavelength with respect to thermal variation is generally dependent on the fiber thermal expansion and thermo-optic effects. It is given by ^{[10],[11]}

$$\Delta\lambda / \lambda = (\alpha + \xi) \Delta T$$

where α is the thermal expansion coefficient and ξ is the thermo-optic coefficient.

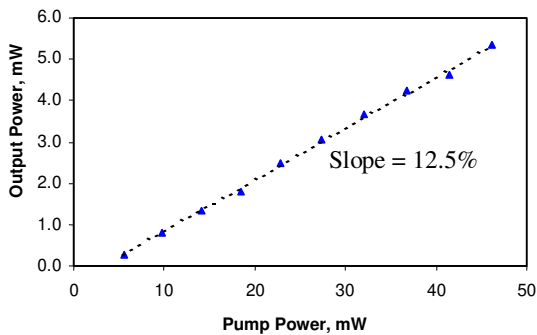


Fig. 2 Output power as a function of coupled in pump power

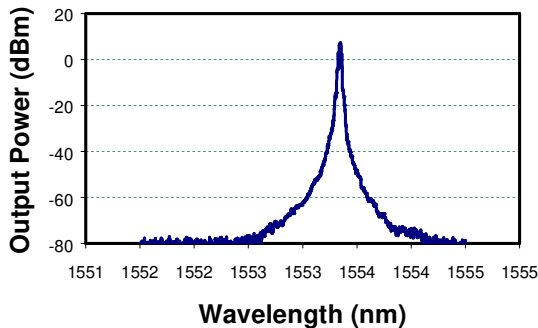


Fig. 3 Spectrum of laser output measured by optical spectrum analyzer

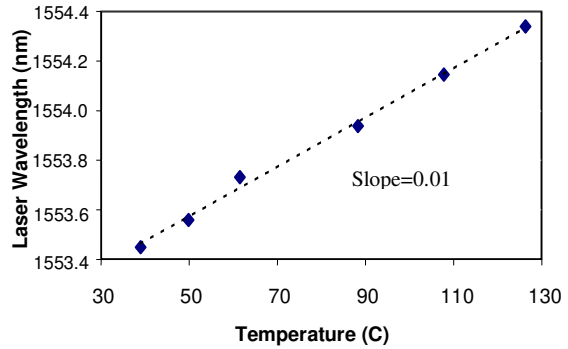


Fig. 4 Fiber laser wavelength against applied temperature

4. CONCLUSIONS

Tunable EDF ring laser using a high reflectivity FBG incorporated into the laser cavity by an optical circulator is investigated. Efficient lasing with a laser threshold of 3.43 mW and a slope efficiency of 12.5% is obtained. A tunability of 0.9 nm is obtained by varying the fiber temperature from 39 ~ 126°C. It is expected that an improved tuning range and tuning response would be found using a grating stretcher/compressor.

ACKNOWLEDGEMENT

S. W. Harun acknowledges the support of a National Science Fellowship (NSF), MOSTE.

REFERENCES

- [1] A. E. Siegman, "Laser," University Science Book, Mill Valley, California, 1986.
- [2] J. Zhang and J. W. Y. Lit, "Erbium doped fiber compound-ring laser with a ring filter," IEEE Photon. Technol. Lett., 6, 588, 1994.
- [3] J. L. Zyskind, J. W. Sulhoff, Y. Sun, J. Stone, L. W. Stulz, G. T. Harvey, D. J. Digiovanni, H. M. Presby, A. Piccirilli, U. Koren, and R. M. Jopson, "Singlemode diode-pumped tunable erbium doped fiber laser with linewidth less than 5.5 kHz," Electron. Lett., 27, 2148, 1991.
- [4] Y. T. Chieng and R. A. Minasian, "Tunable erbium-doped fiber laser with a reflection Mach-Zehnder Interferometer," IEEE Photon. Technol. Lett., 6, 153, 1994.
- [5] G. A. Ball, W. W. Morey, "Continuously tunable single-mode erbium fibre laser," Opt. Lett., 17(6), pp. 420-422, 1992.
- [6] J. T. Kringlebotn, J. L. Archambault, L. Reekie, J. E. Townsend, G. G. Vienne, and D. N. Payne, "Highly efficient, low-noise grating-feedback Er^{3+} : Yb^{3+} co-doped fibre laser," Electron. Lett., 30 (12), pp. 972-973, 1994.
- [7] J. L. Zyskind, V. Mizrahi, D. J. Digiovanni and J. W. Sulhoff, "Short single-frequency erbium-doped fiber laser," Electron. Lett., 28 (15), pp. 1385-1387, 1992.

- [8] S. W. Harun, P. Poopalan, and H. Ahmad, "Fabrication of fiber Bragg gratings in high germania boron co-doped optical fiber by the phase mask method," submitted to Jurnal Teknologi, UTM.
- [9] S. W. Harun, P. Poopalan, and H. Ahmad, "Temperature sensitivity of fiber Bragg gratings fabricated in high germania boron co-doped optical fiber," submitted to Journal SAINS MALAYSIANA, UKM.
- [10] G. Ghosh, "Temperature dispersion of refractive indexes in some silicate fiber glasses," IEEE Photon. Tech. Lett., Vol.30, pp.359-370, 1979.
- [11] G. Meltz and W. W. Morey, "Bragg grating formation and germanosilicate fiber photosensitivity," in. Proc. SPIE Photoinduced Self-Organization Effects in Optical Fiber, F. Ouellette, Ed., Vol.1516, pp.185-199, 1991.

BIOGRAPHIES

Sulaiman Wadi Harun received his B. Eng in electrical and electronic system engineering from Nagaoka University of Technology, Japan in 1996. Currently he is studying for his M.Sc. in Department of Physics, University of Malaya.

Prabakaran Poopalan received his B.Sc. and M.Sc from University of Malaya in 1994 and 1996, respectively. He is a researcher with Telekom Malaysia R & D and is involved in Fiber Bragg Grating Project.

Harith Ahmad is a professor at Physic department, Faculty of Science, University of Malaya. He obtained his Ph.D from University of Swansea (U.K) in Laser Technology, 1983 and has been involved in laser related research the past 15 years. He has numerous research papers published both local and international journals.