

Coordinative Chain Transfer Polymerization

Andreia Valente,^{i,1,2,3,4} André Mortreux,^{1,2,3,4} Marc Visseaux,^{1,2,3,4} Philippe Zinck*^{1,2,3,4}

1 Univ Lille Nord de France, F-5900 Lille, France

2 ENSCL, UCCS, CCM, F-59652 Villeneuve d'Ascq, France

3 USTL, UCCS, CCM, F-59655 Villeneuve d'Ascq, France

4 CNRS, UMR8181, F-59652 Villeneuve d'Ascq, France

1. Introduction	2
2. Coordinative chain transfer polymerization of single monomers	5
2.1. Ethylene	5
2.2. Propylene	9
2.3. Higher 1-alkenes	13
2.4. Styrene	14
2.5. Conjugated dienes	17
3. Statistical Coordinative Chain Transfer co-Polymerizations (CCTcoP).....	23
4. Chain Shuttling Polymerization (CSP)	31
4.1. CSP combined to Chain Walking Polymerization.....	31
4.2. CSP between enantiopure catalysts in a racemic mixture	31
4.3. Chain shuttling copolymerizations	32

ⁱ Current adress: Centro de Ciências Moleculares e Materiais, Faculdade de Ciências da Universidade de Lisboa, Campo Grande, 1749-016 Lisboa, Portugal

1. Introduction

The development of single-site catalysts has led to great potentialities for fine-tuning the microstructure of polyolefins and polydienes. Both regioselectivity and stereoselectivity of the polymerization can be controlled, together with the growth of well-defined branches onto the macromolecular backbone. Various types of microstructures and architectures are now reachable, particularly under conditions where a living polymerization is occurring, *i.e.* one molecule of catalyst leads to the growth of only one macromolecular chain (Scheme 1a). In order notably to reduce the consumption of highly expensive transition metal based catalysts and to control the molecular weight of the polymer, strategies enabling the growth of several macromolecular chains per catalyst, such as Coordinative Chain Transfer Polymerization (CCTP), have been developed.¹⁻⁸ CCTP involves the use of a single transition metal based catalyst and a chain transfer agent (CTA), usually in the form of a main group metal alkyl. In this case, the growing macromolecular chain is able to transfer from the catalyst (active species) to the chain transfer agent, which is usually considered as a dormant species in the course of the polymerization, via transalkylation. CCTP is thus a degenerative group transfer polymerization, *i.e.* a process involving a dynamical equilibrium between propagating and dormant species (Scheme 1b). In contrast with a classical living polymerization where each molecule of catalyst affords the growth of a single polymer chain (Scheme 1a), chain transfer from the catalyst to the CTA allows the growth of several polymer chains per catalyst molecule (Scheme 1b). The transfer has to be rapid *vs.* propagation, reversible, and other chain termination pathways, such as β H abstraction, must not occur, or occur in a negligible way. Narrow molecular weight distributions are obtained, and the macromolecular chains are end-capped with the chain transfer metal, enabling further functionalization based on the

chemistry of the main group metal. This can be viewed, as proposed by Gibson² and Kempe⁵, as a metal complex catalyzed *Aufbaureaktion*.⁹ If the chain transfer efficiency¹⁰ is high, *i.e.* most of the alkyl groups are involved in the transmetalation, the polymer appears to be growing on the main-group metal alkyl. These latter reactions involving fast and reversible transfer together with high transfer efficiencies and the non-occurrence of other chain termination pathways (*i.e.* CCTP with quantitative transfer efficiency *vs.* CTA) are conceptually close to controlled radical polymerization.¹¹ They were given the name of Catalyzed Chain Growth (CCG).² Note that this should not be confused with catalytic chain growth referring to metal-catalyzed olefin insertion into a growing alkyl chain. CCG reactions are interesting in terms of atom economy but also for the synthesis of block copolymers starting from the resulting polymer. For block copolymer synthesis, the chain transfer efficiency must be quantitative because, upon addition of the second monomer, the residual main group metal alkyls can lead to the growth of a homopolymer chain of the second monomer, resulting in a blend of block copolymer and homopolymer requiring purification work-up in order to recover the block copolymer pure.

In addition to the transfer efficiency, the ratio between the chain transfer agent and the catalyst is also a parameter of importance. Indeed, the higher this ratio and the higher the transfer efficiency, the higher the number of chains that can be grown per expensive catalyst molecules. This can be considered as a catalyst economy.

CCTP and CCG reactions thus afford a controlled polymerization in the absence of termination pathways other than chain transfer to the CTA which is of particular interest for monomers such as ethylene that are scarcely polymerizable via anionic or radical polymerizations. The coordination of the monomer on the transition metal in the course of the polymerization gives access to a stereoselective polymerization. This is of

particular interest for monomers, such as olefins and dienes (*e.g.* 1,4-*trans* stereoselective polymerization of 1,3 conjugated dienes, syndiospecific polymerization of propylene, styrene, etc...), as the stereoselective character cannot be achieved by classical living polymerizations (*i.e.* anionic and controlled radical polymerizations). Early CCTP studies were motivated by the beneficial effect that can be expected in terms of catalyst economy, control over the molecular weight and end-functionalization of the resulting polymer. Studies conducted in the recent years were in turn oriented toward catalytic systems for CCTP able to finely control the microstructure and the architecture of the polymer, in order to access to original macromolecular enchainments exhibiting new properties. In a cutting-edge study, Arriola and coworkers reported the straightforward synthesis of a new class of thermoplastic elastomers.³ Multi-block ethylene/1-octene copolymers with sequential crystallizable (low 1-octene content) and non-crystallizable (high 1-octene content) statistical copolymer segments were synthesized via chain shuttling copolymerization (Scheme 2). Such an original microstructure results from the simultaneous presence in the reactive medium of chains growing on two different catalysts and of a chain transfer or chain shuttling agent. The co-monomer reactivity ratios are different for the two catalysts, leading to ethylene-rich and 1-octene-rich segments. The chains are able to growth in a sequential way on the two different catalysts via transfer to the chain shuttling agent. This concept referred to as Chain Shuttling Polymerization (CSP) has been highlighted in numerous perspective articles.¹²

The present review will be devoted to CCTP with a focus on the factors enabling decreased occurrence of termination pathways other than transfer to the CTA such as β H abstraction and on the new concepts that can be derived for the control of the microstructure and the architecture of the resulting polymers. End-functionalizations

will not be dealt with, and interested readers are invited to consult other reviews on this subject.¹³ We will discuss the CCTP of single monomers, including ethylene, propylene and higher 1-alkenes, styrene and conjugated dienes. A particular emphasis will be given to the microstructure. As the CCTP of ethylene has been reviewed in 2007,⁵ we will focus on the work published after this period and briefly present the main earlier studies. We will further present the application of CCTP to statistical copolymerizations and the resulting new concepts that have been derived.¹⁴ The last part of this article will be devoted to chain shuttling polymerizations, including a brief discussion of the properties of the resulting polymers showing unprecedented microstructure and architecture.

2. Coordinative chain transfer polymerization of single monomers

2.1. Ethylene

The CCTP of ethylene has been reviewed in 2007.⁵ We thus present in this section a brief overview of the field, together with the studies published in the period 2007-2012. The different pre-catalysts used for ethylene CCTP are presented in Figure 1. Chain growth on a main group metal was first shown to proceed via a stepwise insertion of ethylene into the Al-C bonds at high temperature and pressure.⁹ Catalyzed versions of this reaction were proposed under smoother conditions with transition metals and rare earths using aluminum,¹⁵⁻²⁷ zinc^{2;28-31} and magnesium alkyls¹ as chain transfer agents.

The polyethylene chain transfer reaction using a main group metal and a transition metal based catalyst have been described in the patent literature to occur with AlEt₃ as the chain transfer agent and activated hafnocenes¹⁵ leading to Schulz-Flory distributions of aluminium alkyl chains. Actinidocenes¹⁶ gave in turn rise to Poisson

distributions under similar conditions, but the transfer efficiency cannot be calculated using the reported data. Using the samarocene precatalyst **1a** combined with dialkylmagnesium at 80 °C and 1.01 bar ethylene, Mortreux *et al.*¹ obtained with a 100% efficiency long chain dialkylmagnesium Grignard type reagents with a narrow polydispersity (Scheme 3). The resulting narrow polymer molecular weight distribution was found to be described by a Poisson distribution. The analogous neodymocene and ytrocene complexes **1b** and **1c**, were found to behave similarly. It should be noted that chain transfer reactions were later observed between the neodymocene **1b** and aluminum using an equimolar mixture of BuLi and AlH^{*i*}Bu₂ as co-catalyst, with the simultaneous occurrence of βH abstraction.²⁶

Aminopyridine yttrium compounds were used by Kempe *et al.* for the ethylene CCTP between organoyttrium cations derived from **2** and aluminum (tetraisobutylaluminumoxane) using 5 bar of ethylene pressure (Scheme 4).²¹ The stability of organoyttrium cations at 80 °C allowed the synthesis of relatively long-chain Al-terminated polyethylenes (M_n up to 4000 g mol⁻¹) with a narrow molecular weight distribution ($\mathcal{D}_M < 1.1$). At higher temperatures (100 °C), polymers with molecular weights up to 15600 g mol⁻¹ could be obtained at the expense of the dispersity ($\mathcal{D}_M \approx 1.4$). This effect was caused by the increase in the solution viscosity and consequent polymer precipitation. More recently, a series of amidinate supported organoyttrium cations derived from **3** allowed, at 80 °C and in combination with an excess of homoleptic trialkylaluminum compounds (AlR₃, R = Et, ^{*i*}Bu, *n*-Oct), a highly controlled ethylene CCTP, producing Al terminated polyethylenes (M_n up to 4200 g mol⁻¹).²⁴

The chromium (III) precatalyst **4**, when activated with B(C₆F₅)₃, and in combination with methylaluminumoxane (MAO) in toluene (Al/Cr = 1000, 23 °C, 1.01 bar ethylene) produced low molecular weight ethylene oligomers.^{17,18} Despite the low

polymerization temperatures, no precipitation was observed. In the presence of 415 equiv. of Al_2Me_6 in addition to the 1000 equiv. MAO, the GCMS (gas chromatography – mass spectroscopy) chromatogram revealed a shift in the distribution in favour of shorter alkanes which was accompanied by an overall activity decrease as well. This slower rate of ethylene consumption was explained by the formation of bridging species (Scheme 5), similar to binuclear neodymium-magnesium complexes initially suggested to account for the same behaviour upon increasing the Mg/Nd ratio in Mortreux's studies.^{1a} Using the neutral chromium allyl **5** without any activator, the polymerization of ethylene proceeded with a rapid precipitation of the polymer in toluene, at room temperature and 1.11 bar of ethylene pressure.¹⁹ In the presence of AlEt_3 , the activity of the system decreased, and the resulting polymers were shorter (up to 500 gmol^{-1}), indicating transmetalation reactions to the aluminum centre (Scheme 6). Similar results were observed using $[\text{Cp}^*\text{Cr}(\text{C}_6\text{F}_5)(\text{Bn})(\text{THF})]$ (Bn = benzyl) **6**, in combination with an excess of AlEt_3 .²⁰

Gibson and coworkers used the bis(imino)pyridine iron(II) dichloride complex **7** in combination with MAO as cocatalyst and diethylzinc as chain transfer agent.^{2,28} This catalytic system allowed the first Catalyzed polyethylene Chain Growth on zinc (Scheme 7). The polymerizations were performed under much smoother conditions than those using rare-earth pre-catalysts, *i.e.*, 1.0 bar of ethylene pressure at room temperature, affording molecular weights up to 3000 gmol^{-1} in transmetalation conditions. A detailed examination of the factors enabling this iron CCG led the authors to propose the key features for this process: i) relatively low steric hindrance around the zinc centre; ii) the monomeric nature of ZnEt_2 in solution; iii) the relatively weak Zn-C bond; and iv) a reasonably close match in Zn-C and Fe-C bond strengths. Concerning i), a direct correlation between the size of the ligand on the main group metal and the

extent of the observed chain transfer to the CTA was noticed. Additionally, the data showed that the CTA having a monomeric nature in solution are more active. Relatively to iii) and iv), a fine balance between these factors was needed to generate a catalyst latent state which is stable, yet highly reactive. A later study proved these findings to be relevant.²⁹

The methyl monocyclopentadienyl amidinate hafnium complex **8** in combination with a borate activator was found to be an efficient catalytic system for the CCTP of ethylene in the presence of various molar amounts of ZnR_2 ($R = Et$ or iPr ; 20-200 equiv.) in toluene at 25 °C under ≈ 1.34 bar of ethylene pressure, producing polyethylene with molecular weights up to 670 g mol^{-1} (Scheme 8).³⁰ Besides the non-occurrence of chain termination by β -hydrogen transfer, the reversible transfer and living character of these reactions was supported by a kinetic study by GC, which revealed a narrow Poisson distribution.

A hafnium pyridyl-amide catalyst **9** was assessed for ethylene CCTP in combination with $AlOct_3$ as CTA.²³ Fairly constant polymer yields were obtained with increasing quantities of CTA. The dispersity values were lower than 2, and decreased monotonically with the addition of CTA. Concerning the chain transfer efficiency, less than half of the available Al sites were occupied by polymer chains. This indicated that polymeryl-polymeryl exchange is kinetically competitive with polymer-alkyl exchange in this system.

A series of new aminopyridinato ligand stabilized hafnium complexes were also assessed for ethylene polymerization.²⁵ The catalyst giving the highest level of control, **10**, in the presence of high amounts of $AlEt_3$, produces linear aluminum-terminated polyethylene without significant β -H abstraction. However, this first study showed that

the transfer was relatively slow in relation to chain growth which leads to a lack of control over the molecular weight distribution.

The reversible chain transfer to Al in ethylene polymerization catalyzed by $\text{Cp}^*_2\text{ZrCl}_2$ **11** / MAO was also studied via comparison of the polymerization in the presence and absence of AlMe_3 contained in commercial MAO.²⁷ The molecular weight distributions of the products were found to be narrower in the presence of AlMe_3 at low Al/Zr ratios. Dispersities of about 1.3 or lower were attainable at temperatures up to 70 °C. A fast to moderate reversible chain transfer between $\text{Cp}^*_2\text{ZrR}^+$ and AlMe_3 was suggested in order to explain the decrease of the dispersity.

2.2. Propylene

Many of the pre-catalysts reported to afford chain transfer in the course of propylene polymerization are based on Zr.³²⁻³⁹ The first true CCTP of propylene was achieved recently by Sita and coworkers.⁴⁰

The influence of aluminum alkyl on the chain transfer polymerization of propylene was carried out in the presence of zirconium catalyst precursors (Figure 2, *rac*-ethylenebis(indenyl)-zirconium dichloride **12**, *rac*-dimethylenebis(indenyl)zirconium dichloride **13b** and isopropylidene(cyclopentadienyl)(9-fluorenyl)zirconium dichloride **14**) in combination with triphenylcarbenium tetrakis(pentafluorophenyl)borate ($\text{Ph}_3\text{CB}(\text{C}_6\text{F}_5)_4$ or trityl borate) and AlEt_3 or Al^iBu_3 .³⁶ In the isospecific polymerization with **12** and **13b**, the molecular weight of the resulting polymer was found to decrease with an increase in the molar ratio of AlEt_3 vs. Zr catalyst. An effect of the Al^iBu_3 concentration on molecular weight was in turn not observed. The considerably higher chain transfer efficiency of linear alkyl groups vs. isobutyl groups was also observed by Gibson *et al.* in the course of the polymerization of ethylene using **7** in combination

with aluminum alkyls.² The microstructure of the resulting polypropylene was studied by ¹³C NMR. An increase in the molar ratio of ethyl end groups (derived from chain transfer to AlEt₃) to *n*-propyl end groups (derived from β-hydrogen transfer and consecutive insertion of propylene into the metal hydride) was observed with increase in the AlEt₃/Zr molar ratio. Al^{*i*}Bu₃ was in turn found to lead to chain transfer when the polymerization was conducted with **14**, but its chain transfer efficiency remained lower than that observed using AlEt₃, confirming the aforementioned trend on linear *vs.* *n*-propyl alkyl groups. The relative constants of chain transfer to aluminum alkyl *vs.* chain propagation k_{tr}/k_p were found to be 5 times higher for AlEt₃ *vs.* Al^{*i*}Bu₃ in the course of the syndiospecific polymerization of propylene using **14** and (Ph₃CB(C₆F₅)₄).

The aforementioned βH abstraction occurring using **13b** could be suppressed using MAO containing AlMe₃ instead of trityl borate / AlR₃ as co-catalyst, and performing the reaction at low temperature (10 °C).³⁵ It was shown that the relative frequencies of chain terminations via both β-hydride and β-methyl transfer reactions gradually decrease with the decrease of polymerization temperature.

Propylene polymerization was also conducted using [η³.η¹-*tert*-butyl(dimethylfluorenylsilyl)amido]dimethyltitanium **15** combined with B(C₆F₅)₃ or MAO as cocatalyst in the presence of various trialkylaluminum CTA (AlMe₃, AlEt₃, Al^{*i*}Bu₃ and AlOct₃).⁴¹ Living polymerization was afforded at -50 °C with B(C₆F₅)₃ as cocatalyst and using AlEt₃ as CTA, giving Al-terminated polymers. AlOct₃ could act as an efficient CTA for high loadings only, while AlMe₃ and Al^{*i*}Bu₃ produced only oligomers. When MAO was used as cocatalyst, the temperature needed to be increased to 40 °C to observe a chain growth transfer which in this case strongly depends on the structure and electronic properties of the substituents on the CTA, which obviously must affect at least the rate of the first transfer step.

The isospecific zirconocene catalyst $\text{Me}_2\text{Si}(2\text{-Me-4-}^t\text{Bu-C}_5\text{H}_2)_2\text{ZrCl}_2$ **16** was also used in combination with trimethylaluminum and MAO, and chain transfer of the growing polypropylene chains to aluminum was thus observed.³² The polymerizations were carried out in the presence of an excess of MAO ($[\text{Al}]:[\text{Zr}] = 2000:1$) to give highly stereoregular (95-99 % [mmmm]) and regioregular (100 % 1,2-insertions) polypropylene with DP_n (number-average degree of polymerization) in the range 80-150. ^{13}C NMR studies of these polymers showed high contents of isopropyl end chains, proving that the growing polymer chains are transferred from Zr to Al. Using an excess of AlMe_3 in addition to MAO ($\text{AlMe}_3:[\text{Zr}] \approx 500\text{-}5000:1$) generated even shorter polymer chains, as expected in a chain transfer mechanism (Scheme 9), and the activity was increased.

The zirconocene catalyst **17** was used by Rieger *et al.* in combination with MAO or trityl borate in order to study the influence of reversible chain transfer in the polypropylene microstructure.³³ When MAO was used, transmetalation reactions between the catalyst and the aluminum centre were observed, together with a change in the stereoselectivity of the reaction. The authors proposed that the reversible chain transfer to aluminum is involved in the stereoerror formation. As a consequence, a pallet of materials with crystalline and amorphous segments could be synthesized, allowing to envisage applications in terms of microstructure control. Using several techniques, such as NMR, differential scanning calorimetry (DSC), wide angle X-ray scattering (WAXS) and scanning force microscopy (SFM), the distribution of stereoerrors along the polymer chain could be identified. Using MAO, a statistical polymer was obtained with increasing amounts of longer isotactic sequences with crystallizable blocks consisting of 23-32 monomers in isotactic sequences, which co-crystallized in different lamellae

phases. Better activities were obtained using oxygen-substituted asymmetric zirconocene dichlorides.⁴²

If chain transfer can play a role over the stereoselectivity of the reaction, the regioselectivity of the insertion of propylene can in turn influence the occurrence of chain transfer. Busico and coworkers⁴³ observed that occasional regio-irregular 2,1 insertions occurring in the course of the isotactic polymerization of propylene using **12a** and **13a** combined to MAO practically inhibit chain transfer to the monomer and to the aluminum alkyl cocatalyst.

The first true CCTP of propylene was reported by Sita *et al.* using ZnEt_2 as CTA and the hafnium catalyst **8** (Figure 1).^{30;40} NMR spectroscopy shows that chain termination pathways other than chain transfer to the CTA do not occur in the course of the polymerization. An efficient reversible chain transfer (Scheme 10) was evidenced by (i) a strictly linear relationship between molecular weights and the initial molar equivalents of main-group metal alkyl, and (ii) the narrow molecular weight distributions of all isolated polypropylene products. Higher molecular weights could be obtained in the presence of 5 and 10 equiv. ZnEt_2 using larger volumes of toluene and longer reaction times (atactic polypropylene is soluble under these conditions). This contrasts with polyethylene, where the polymer precipitation begins to occur for molecular weights around 2000 g/mol.^{1,21}

Recently, Sita *et al.* extended the catalytic system to the **8**/ ZnEt_2 / AlR_3 (R = ethyl, *n*-propyl, isobutyl) combination.⁴⁴ The CCTP of propylene using trialkylaluminum as the single chain transfer agent showed similar results when compared to those obtained with diethylzinc. When both are used together, trialkylaluminum plays the role of the CTA and diethylzinc acts as a chain transfer mediator, enhancing the rate of the transfer reaction between catalyst **8** and the

aluminum alkyl (Scheme 11). Attempts to scale up the CCTP in volume were successfully accomplished using 10 mol% of diethylzinc (relatively to triisobutylaluminum) in toluene under smooth conditions (20 °C, 1.34 bar) to produce atactic polypropylene with narrow molecular weight distributions. One key of this system is the possibility to use less of the more expensive Zn alkyl to get the same results.

2.3. Higher 1-alkenes

The application of CCTP to higher 1-alkenes is a rather emerging field. Using $\text{Cp}^*\text{HfMe}_2[\text{N}(\text{Et})\text{C}(\text{Me})\text{N}(\text{Et})]$ **8** as pre-catalyst and a borate activator $[\text{PhNHMe}_2][\text{B}(\text{C}_6\text{F}_5)_4]$, in combination with ZnEt_2 , Sita *et al.* reported the CCTP of 1-hexene in toluene at -10 °C giving high yields of atactic poly(1-hexene) (Scheme 12).³⁰ The molecular weights were found to be dependent on the initial molar equivalents of the main-group metal alkyl employed as CTA. A kinetic analysis confirmed the living character of the reaction.

Carpentier and Mortreux reported the use of the neodymium complexes $[\text{rac}\{-\{\text{Me}_2\text{Si}(\eta^5\text{-2-SiMe}_3\text{-4-}i\text{-Bu-C}_5\text{H}_2)_2\}\text{Nd}(\mu\text{-Cl})_2\text{Li}(\text{THF})_2]$ **18a**, $[\text{rac}\{-\{\text{Me}_2\text{Si}(\eta^5\text{-2,4-(SiMe}_3)_2(\text{C}_5\text{H}_2)_2)\}\text{Nd}(\mu\text{-Cl})_2\text{Li}(\text{THF})_2]$ **18b** and $[\{\text{Me}_2\text{Si}(\eta^5\text{-2,4-(SiMe}_3)_2\text{C}_5\text{H}_2)(\eta^5\text{-3,4-(SiMe}_3)_2\text{C}_5\text{H}_2)\}\text{Nd}(\mu\text{-Cl})_2\text{Li}(\text{THF})_2]$ **18c**, in combination with a dialkylmagnesium cocatalyst for the polymerization of 1-octene (Scheme 13).⁴⁵ Even if molecular weights decreased in the presence of higher amounts of dialkylmagnesium, the experimental molecular weights of the oligooctenes obtained are lower than the theoretical ones calculated assuming two growing chains per magnesium atom, suggesting significant βH abstraction. This assumption was confirmed by NMR analyses.

2.4. Styrene

The most commonly used CTA for styrene CCTP are based on magnesium^{4;46-52} and aluminum alkyls.⁵³⁻⁵⁴ One of the problems associated with styrene CCTP is the need for high temperatures that leads to the occurrence of radical polymerization. For example, the chlorolanthanidocene **1b**/ dialkyl magnesium system allowed when applied to styrene the simultaneous occurrence of radical and coordination polymerization (T = 105 °C, Scheme 14).⁴⁶ In the presence of *n*-butylethylmagnesium or *n,s*-dibutylmagnesium alone, styrene polymerization proceeded via thermal self-initiation, but was accompanied by a reversible transfer to dialkylmagnesium to yield in turn oligostyrylmagnesium species. MALDI-TOF (Matrix Assisted Laser Desorption/Ionization - Time of Flight mass spectroscopy) analyses indicated the presence of ethyl and butyl headgroups, consistent with the transfer process.

When combined with dialkylmagnesium, cerium (IV) alkoxides **19** and **20** (Figure 3) oligomerized styrene at high temperature (105 °C), providing chain transfer reactions to magnesium as evidenced by the decrease of molecular weights with the increase of Mg/Ce ratios.⁴⁷ Transmetalation efficiencies were in the range 32-79 % and the authors proposed the existence of two concomitant pathways which enable styrene polymerization: (a) radical polymerization initiated by free radicals generated from the redox-active metal precursors (being this the major pathway) and (b) coordination / insertion polymerization based on *in situ* produced Ce(III)- and/or Ce(IV)-alkyl species.

Using systems based on lanthanide trisborohydride complexes **21** the problem associated with high temperatures could be overcome since these catalysts are active in mild conditions for reactions times where the auto-initiated radical polymerization of styrene is nearly inexistent.^{48,52} Ln(BH₄)₃(THF)₃ (Ln = Nd, La) afforded the transfer

polymerization of styrene with substantial transfer efficiencies and good yields, but with the simultaneous occurrence of βH abstraction (Scheme 15). The occurrence of this undesirable termination pathway could further be overcome with a pentamethylcyclopentadienyl ligand in the coordination sphere of the rare earth metal. The electron donating ability of this latter ligand leads to a higher electron density around the metal centre that may disfavor agostic interactions. This may lead to less βH abstraction. The catalytic systems $\text{Cp}^*\text{Ln}(\text{BH}_4)_2(\text{THF})_2$ **22** / *n*-butylethylmagnesium (Ln = Nd, La) afforded, in this frame, the first example of a polystyrene CCG^{4,52} (Scheme 16) by allowing (i) all alkyl groups to be involved in the chain transfer and (ii) a living character as evidenced by a continued chain growth after a second addition of monomer. The reaction was further found to be 85% syndioselective. Based on steric considerations, an analogy was drawn between lanthanidocene catalyzed polyethylene chain growth on magnesium and half-lanthanidocene catalyzed polystyrene chain growth on magnesium considering an interaction between the rare earth centre and the aromatic ring (Scheme 17). It was also evidenced that lanthanum based complexes lead to less βH abstraction than neodymium based complexes in the course of the polymerization of styrene. This may be attributed to steric considerations but also to the lower Lewis acidity of lanthanum *vs.* neodymium that may lead to a lesser extent of agostic interactions, and thus to a decrease of βH abstraction. The polymerization of styrene using $\text{LaCl}_3(\text{THF})_3$ in combination with magnesium dialkyl was found to occur without βH abstraction in the presence of 1 to several equiv. magnesium dialkyl, and the quantitative transfer efficiency observed allowed to conclude that a CCG reaction is occurring using the latter combination. Other CCTPs of styrene reported in the literature were found to occur with lower chain transfer efficiencies. Syndioselective polystyrene CCTP to magnesium was reported by Carpentier *et al.* using an ansa-

chloroneodymocene dimer, [(Cp-CMe₂-Flu)Nd(μ -Cl)]₂ **23**, combined to di-*n*-butyl and diallylmagnesium at 60 °C (1-100 equiv. vs. Nd).⁴⁹ Substantial decrease of the number average molecular weight with the amount of magnesium compound is observed, with yields of isolated polymers lower than 20%. The experimental values of molecular weights were found to be systematically higher than those calculated, reflecting a modest initiation together with a modest transfer efficiency (1-7%). The latter could be substantially increased using the neutral allyl neodymocene **24**, highlighting interestingly a highly syndioselective and efficient CCTP (Scheme 18). Carpentier and coworkers also reported the first isoselective CCTP of styrene using the bis-indenyl yttrium pre-catalyst **25** combined to magnesium dialkyl, with dispersity in the range 1.4-1.8 and high transfer efficiency in certain cases (Scheme 18).⁵⁰⁻⁵¹ It is noteworthy that the growth of more than 200 macromolecular chains per yttrium centre can be achieved.

Catalysts based on titanium leading to the syndiospecific polymerization of styrene were also been reported for CCTP.⁵³ Using Ti(OEt)₄ **26** and CpTiCl₃ **27** with MAO combined with AlMe₃, the weight average molecular weight decreased almost linearly with increasing amounts of the CTA. A very sharp decrease of the molecular weights was in turn observed by the addition of even moderate amounts of Al^{*i*}Bu₃. This was explained by the propensity of the CTA to prevent from β -hydride abstraction. A ¹³C NMR analysis of the polymer end-groups showed that the occurrence of β -hydride abstraction tends to decrease with the amount of AlMe₃ introduced, and disappeared when Al^{*i*}Bu₃ was used as a chain transfer agent. Chain termination occurred exclusively by transfer to the aluminum centre in the latter case (Scheme 19). The transfer efficiency can unfortunately not be calculated from the reported values. It is noteworthy that this study reported the first example of a highly syndiospecific CCTP of styrene.

Syndiospecific styrene CCTP was also reported using Cp*Ti(OMe)₃ **28** / [C₆H₅N(CH₃)₂H][B(C₆F₅)₄] combined to triethyl-, tri-*n*-propyl and tri-isobutylaluminum.⁵⁴ Substantial decreases of the weight average molecular weight with the amount of trialkylaluminium were reported. The transfer efficiency could be classified in the following order: AlEt₃ > Al*n*-Pr₃ > Al^{*i*}Bu₃. However, it is not possible to quantify the amount of aluminum end-capped syndiotactic polystyrene chains from the reported data.

2.5. Conjugated dienes

CCTP of conjugated dienes was mainly reported to be 1,4-*cis* stereoselective.⁵⁵⁻⁶¹ The transmetalation of a growing polydiene chain could be accompanied by a decrease of the 1,4-*cis* selectivity of the reaction. Rare earth trichloride adducts and versatate were among the most studied precatalysts in the presence of aluminum and zinc based chain transfer agents. The chain transfer efficiency was only moderate with these systems (2 – 14 %). A major drawback was the simultaneous change of polymerization rates, as observed by Friebe *et al.* for the ternary system neodymium versatate **29** (Figure 4) / ethylaluminum sesquichloride / aluminum alkyl.^{56,58} This system allowed a reversible exchange of the living polybutadiene chains between neodymium and aluminum, however, the polymerization rate was highly decreased in transfer conditions.

The impact of aluminum alkyl on the polymerization kinetics and on the control of molecular weights was further studied using di-isobutyl aluminumhydride and tri-isobutylaluminum (Al^{*i*}Bu₃).⁵⁸ The difference between these two aluminum compounds in terms of transfer efficiency was significant. AlH^{*i*}Bu₂ was eight times more effective than Al^{*i*}Bu₃, and the substitution probability of Al-H was approximately 22-fold higher

that of Al-isobutyl (transfer efficiency for $\text{AlH}^i\text{Bu}_2 = 10\text{-}14\%$ and for $\text{Al}^i\text{Bu}_3 = 1\text{-}2\%$). This great difference reflects the importance of Al-based cocatalysts with Al-H moieties. The differences between their respective reaction rates and the equilibrium positions are schematically presented in Scheme 20. Although AlH^iBu_2 exhibited higher transfer efficiency than Al^iBu_3 , only one third of the total amount of AlH^iBu_2 was involved in the molecular weight control. This feature was further explained by the possible aggregation of AlH^iBu_2 , which could form trimers.

Diethyl zinc was added to the previous ternary system (neodymium versatate / ethylaluminum sesquichloride / AlH^iBu_2).⁶⁰ On the one hand, the addition of ZnEt_2 did not change the living nature of the polymerization and had limited impact on the polymerization rate. On the other hand, ZnEt_2 did not only reduce the molecular weight, but lead also to a reduction of the dispersities. However, a decrease of the 1,4-*cis* content was observed, as it was already observed for AlH^iBu_2 , from 94 to 84% with increasing quantities of diethylzinc up to 30 equiv. *vs.* Nd in the presence of 20 equiv. AlH^iBu_2 . The influence of Al^iBu_3 on the stereoselectivity was unfortunately not reported. In terms of molar mass control efficiencies, one can establish the following trend: $\text{AlH}^i\text{Bu}_2 > \text{ZnEt}_2 > \text{Al}^i\text{Bu}_3$.

The neodymium versatate **29** was also recently used in combination with dimethylchlorosilane (Me_2SiCl_2) and di-isobutylaluminum hydride for the CCTP of isoprene.⁶² The authors found out that only one third of the hydride moieties participates in the formation of the new polymer chains at a $[\text{Al-H}]/[\text{Nd}] = 20$, as already observed by Friebe.⁵⁸ Since termination reactions are negligible using this system, a chain-end functionalization was performed by introducing carbon dioxide to the polymerization solution. After treatment of the resulting polymer, FTIR spectra showed the presence of the carboxylic acid, but quantification informations were not reported.

Chain transfer between neodymium and aluminum in the course of the polymerization of isoprene was also reported using **30** in combination with $\text{Al}^i\text{Bu}_3/[\text{Ph}_3\text{C}][\text{B}(\text{C}_6\text{F}_5)_4]$. This resulted in a broadening of the molecular weight distribution of the resulting 1,4-*cis* enriched polyisoprene.⁶³ A ternary catalytic system composed of $\text{Nd}(\text{O}i\text{-Pr})_3$ **31a**, $[\text{HNMe}_2\text{Ph}]^+[\text{B}(\text{C}_6\text{F}_5)_4]^-$ and Al^iBu_3 also showed a decrease of molecular weights and a broadening of the dispersity in the presence of larger amounts of aluminum, together with a modest transfer efficiency (2-3%).⁶⁴ The polymers were highly 1,4-*cis* with dispersities between 2-3. The optimal composition for this catalytic system was found to be $[\text{borate}]/[\text{Nd}] = 1$ and $[\text{Al}]/[\text{Nd}] = 30$. Chain transfer between neodymium and aluminum was also observed using $\text{Nd}(\text{2,6-di-tert-butyl-OC}_6\text{H}_3)_3$ **32** combined with various amount of MAO and MMAO, yielding non-stereoregular polyisoprenes.⁶⁵ The neodymium isopropoxyde **31a** was also used in combination with Me_2SiCl_2 and di-isobutyl aluminum hydride for the CCTP of isoprene.⁶⁶ Quantitative yields together with dispersities in the range 1.2-1.5 were reported. Transfer efficiencies up to 12-14% were obtained, together with molecular weight up to 30 000 g/mol. It should be noted here that the molecular weight values of polyisoprene have to be divided by a factor of *ca.* 2 to get the true Mn, as polystyrene standards were used for the measurements of the Mn by size exclusion chromatography.⁶⁷⁻⁶⁹ This leads to transfer efficiencies as high as 24-28%, which are among the highest reported in the literature using aluminium based chain transfer agents. The living character of the CCTP was confirmed by a second isoprene feed, and the formation of polyisoprene-*block*-poly(ϵ -caprolactone) copolymers.

The cationic borohydrido lanthanide complex $[\text{Nd}(\text{BH}_4)_2(\text{THF})_5]^+[\text{B}(\text{C}_6\text{F}_5)_4]^-$, was found to be highly active towards isoprene polymerization upon activation with Al^iBu_3 .⁷⁰ The *in situ* prepared ternary system $\text{Nd}(\text{BH}_4)_3(\text{THF})_3$ **21** /

[HNMe₂Ph][B(C₆F₅)₄] / AlⁱBu₃ was less active but affords a higher *cis*-selectivity and a better control in terms of macromolecular data (Scheme 21). The amount of cocatalyst was found to be directly related to the selectivity and the molecular weight control. In the presence of a large excess of cocatalyst, lower molecular weights were obtained, showing transfer reactions between Nd and Al and confirming the role of Al as transfer agent; however the transfer efficiencies were quite low (4 – 6 %). The dispersity values remained narrow indicating a rapid exchange between Al and Nd, but with loss of both selectivity and activity.

Isoprene CCTP was also reported using aminophenyl functionalized cyclopentadienyl rare-earth metal allyl mediated cationic systems ((C₅Me₄-C₆H₄-*o*-NMe₂)Gd(η³-C₃H₅)₂) **33** by Hou, Cui *et al.*⁷¹ The obtained polymers were found to be highly 1,4-*cis* regular, and a transmetalation between gadolinium and aluminum was observed with transfer efficiencies between 6-8 %.

If CCTP of 1,3 dienes is well documented for 1,4-*cis* stereoselective reactions, few examples were reported in the case of 1,4-*trans* stereoselectivity. A brief description of 1,4-*trans* stereoselective chain transfer oligomerization of butadiene was reported using Nd(O-2,6-*t*-Bu-2,4-Me-Ph)₃ combined to dihexylmagnesium (Mn 1100 g/mol, 5 equiv. CTA).⁷² The first 1,4-*trans* stereospecific CCTP of isoprene was reported recently.^{69,73} A series of lanthanum and neodymium complexes (Ln(BH₄)₃(THF)₃ **21**, Cp*Ln(BH₄)₂(THF)₂ **22**, LaCl₃(THF)₃, NdCl₃(THF)₃, Ln(O^{*i*}Pr)₃ **31** and Nd(OC₆H₃-^{*t*}Bu-2,6)₃ **32**) were assessed for the CCTP of isoprene in combination with *n*-butylethylmagnesium.⁶⁹ Among these catalysts, rare earth borohydrides were found to be the most efficient for isoprene CCTP. Lanthanum and neodymium trisborohydrides led to chain transfer efficiencies in the range 50 - 60%, while the half-lanthanidocenes led to chain transfer efficiencies close to 100%,

highlighting the first example of a polyisoprene CCG (Scheme 22a). The polymerization activity was found to be higher for lanthanum vs. neodymium based catalysts. Lanthanum and neodymium chloride, isopropoxide and aryloxy were found to be poorly active under the same experimental conditions. One feature of these CCTP reactions is the fact that transmetalation was accompanied by a change in the selectivity of the reaction. Using increasing quantities of magnesium dialkyl, a gradual decrease of the 1,4-*trans* stereoselectivity of the reaction was observed at the benefit of 3,4-selectivity. This is particularly interesting regarding the work that would be required for the synthesis of the different catalysts able to lead to the same array of polyisoprenic materials by classical coordination/insertion polymerization. The higher quantities of 3,4 enchainments was proposed to be attributed to (i) steric hindrance induced by the presence of dialkyl or di-isoprenyl magnesium in excess, hindering the η^4 coordination mode of isoprene and leading to a η^2 coordination mode of the monomer and/or (ii) the propensity of magnesium-isoprene adducts to oligomerize isoprene in a 3,4-selective process.⁷⁴ Inspired by the earlier work of Yasuda,⁷⁴ it was shown that *n*BuMgEt was able to oligomerize isoprene without any additional transition metal based catalyst. The isoprenyl magnesium moieties formed in the course of a CCTP can thus no longer be considered as a dormant species, as usually accepted for a chain transfer agent metal – polymeryl moieties in the course of a CCTP. The reaction was thus considered to operate under a similar process to chain shuttling polymerization, however without the intervention of a third chain shuttling agent component. This is represented in Scheme 23. The overall approach was extended to the CCTP of a natural conjugated diene from the terpene family, myrcene, using $\text{Nd}(\text{BH}_4)_3(\text{THF})_3$ in combination with *n*-butylethylmagnesium.⁷⁵ Similar trends were observed, *i.e.* a high transfer efficiency together with a modification of the regioselectivity of the polymerization of myrcene

from 1,4-*cis* to 3,4. *n*-Butylethylmagnesium was also found to oligomerize myrcene in a 3,4 regioselective manner over long reaction times.

With the objective to preserve the 1,4-*trans* stereoselectivity along the chain transfer polymerization of isoprene, several CTAs based on aluminum, zinc and boron were assessed in combination with the active species derived from Cp*La(BH₄)₂(THF)₂ **22b** / 1 equiv. *n*BuMgEt that lead to the 1,4-*trans* stereoselectivity. Boron and zinc alkyls were found to be inefficient for the chain transfer polymerization. AlEt₃ and Al^{*i*}Bu₃ lead to a transmetalation of the growing polymer chain, with efficiencies in the range 22-26% per aluminum atom. A similar behavior was observed using AlH^{*i*}Bu₂, with an efficiency of 19%. The catalyst was found to be poorly active using AlEt₂Cl. It is noteworthy that using AlEt₃, Al^{*i*}Bu₃ and AlH^{*i*}Bu₂ the polymerization remained 1,4-*trans* stereospecific (96-98%, Scheme 22b), highlighting the first example of a 1,4-*trans* stereospecific CCTP of isoprene. It was proposed that the less pronounced ionic character of the metal-carbon bond in alkylaluminum vs. alkylmagnesium compounds does not allow to disturb the La – Mg bimetallic active species leading to the 1,4-*trans* stereoselectivity.

The *rac*-[Me₂C(Ind)₂]Y(1,3-(SiMe₃)₂-C₃H₃)] **25** catalyst was used by Carpentier *et al.* to polymerize isoprene, either as a single-site component catalyst or in combination with a CTA.⁷⁷ Using ZnEt₂ or Al^{*i*}Bu₃, the CCTP of isoprene was achieved while maintaining a 1,4-*trans* stereoselectivity (87-90%). When Mg^{*n*}Bu₂ was used, the 1,4-*trans* stereoselectivity gradually decreased with increasing quantities of this CTA at the expense of a 3,4-regioselectivity (1,4-*trans*: 53-78%), as already observed in the aforementioned studies.

Chain transfer within the course of a 3,4-selective polymerization of isoprene is rare. Modest chain transfer efficiencies were reported using nonmetallocene rare earth

metal bis(alkyl) by Cui *et al.*⁷⁶ The scandium complex [(NPN^{Ph})Sc-(CH₂SiMe₃)₂(THF)] (NPN^{Ph}: N(Ph)PPh₂=NC₆H₂Me₃-2,4,6) **34** in combination with [PhNHMe₂][B(C₆F₅)₄] and Al^{*i*}Bu₃ provides high activity and 3,4-selectivity towards isoprene polymerization (up to 94.7 % at -40 °C, Scheme 24). Interestingly, when increasing the [Al]/[Sc] ratio, a higher activity was observed, followed by a decrease of the molecular weights suggesting the occurrence of chain transfer reactions in the course of polymerization.

3. Statistical Coordinative Chain Transfer co-Polymerizations (CCTcoP)

In a statistical Coordinative Chain Transfer co-Polymerization (CCTcoP) one catalyst and one chain transfer agent are used to afford a statistical copolymer (Scheme 25). Chain transfer reactions in the course of copolymerizations have been assessed mainly for ethylene-based materials using transition metal catalysts in combination with alkylaluminum or alkylzinc CTAs.

The first synthesis of a poly(ethylene-*co*-comonomer) using the CCTP approach is reported for the copolymerization of ethylene with allylbenzene using *rac*-ethylenebis(indenyl) zirconium dichloride **12a** (Figure 2)/ MAO at 80 °C in toluene at a constant ethylene pressure of 1.2 bar.⁷⁸ The comonomer incorporation could be increased until 20 % changing the initial feed of allylbenzene. On the basis of end group analysis by NMR and the decrease of molecular weight of copolymers with the introduction of increasing amounts of trimethylaluminum, it was revealed that chain transfer to aluminum was the preferred chain transfer reaction during the copolymerization (dispersity 1.6 - 4.1). Chain termination through aluminum transfer was suggested to be induced by the allylbenzene unit incorporated in the propagating chain end. The introduction of increasing amounts of AlMe₃ in the reaction medium did

not induce substantial changes of the allylbenzene incorporation in the copolymer. A complementary study using catalysts **35** (Figure 5) and **11** (Figure 1) has also been performed in order to infer about possible mechanisms.⁷⁹ The catalysts structures were directly related to their ability to undergo β -H abstraction during the copolymerization. β -H abstraction was observed using Cp_2ZrCl_2 and $(n\text{-BuCp})_2\text{ZrCl}_2$, while using $(2\text{-MeInd})_2\text{ZrCl}_2$ and $\text{Cp}^*_2\text{ZrCl}_2$ chain transfer to aluminum was the preferred mechanism. This behaviour was rationalized in terms of the chain conformation for β -agostic interaction which is believed by many authors to stabilize the metal centre and favor β -H abstraction.⁸⁰⁻⁸³

CCTcoP of ethylene (60 °C, 1.5 bar) and propylene (50 °C, 1.5 bar) with long-chain amide and amine functional alkenes (Scheme 26) was assessed in the presence of the *rac*-ethylenebis(1-indenyl)zirconium dichloride **12a** and *rac*-dimethylsilylbis(2-methylindenyl)zirconium dichloride) **13b** zirconocenes / MAO systems.⁸⁴ The incorporation of the amide comonomer changed slightly with the amount of cocatalyst, remaining in the 0.24-1.3 mol % range with ethylene and in the 0.04-0.96 mol % range with propylene. The predominant end groups observed in ¹³C NMR spectra were saturated linear and isobutyl chain ends for ethylene and propylene copolymers, respectively, showing the chain transfer to the aluminum centre.

More hindered zirconocenes complexes, *rac*-dimethylsilylbis(2-methyl-4-phenyl-1-indenyl) zirconium dichloride **36a** and *rac*-dimethylsilylbis(2-isopropyl-4-[3,5-dimethylphenyl] indenyl)zirconium dichloride) **36b** were used for the CCTcoP of ethylene with propylene in combination with MAO (70 °C, 1.5 – 5.0 bar).⁸⁵ The most common termination pathway was chain transfer to aluminum for both catalysts, with however the occurrence of other chain termination reactions. Using **36a**, β H transfer to

the monomer and to the metal were observed, while using the more hindered **36b** leads to the occurrence of β H and β -methyl transfer to the metal.

The CCTcoP of ethylene with 1-alkenes was reported using pyridylamide Hf **9** and bis(phenoxy-imine) Zr **37** catalysts used for chain shuttling copolymerization.^{3;22-23} It is noteworthy that more than 200 growing chains per transition metal are observed in the presence of excess ZnEt₂ as chain transfer agent for the former, and more than 2000 for the latter. **37** combined to ZnEt₂ led furthermore to linear Mn vs. yield plots indicative of CCTP. Ethylene/1-hexene copolymerization experiments conducted using **9** and AlOct₃ as CTA²³ led to 13-16% 1-hexene in the copolymer. They were quenched with D₂O after varied reaction times. A detailed deuterium labelling study revealed that chain transfer to aluminum is the dominant termination mechanism under these conditions. Interestingly, ²H and ¹³C NMR experiments indicated that chain transfer from **9** to AlOct₃ occurs significantly faster after an ethylene insertion than after a hexene insertion.

Using {Cp*Hf(Me)[N(Et)C(Me)N(Et)]}[B(C₆F₅)₄] (Cp* = η^5 -C₅Me₅) or {Cp*Hf(Me)-[N(Et)C(Me)N(Et)]}[B(C₆F₅)₃Me] **8** in combination with diethylzinc affords the CCTcoP of ethylene with α -olefins (1-hexene and 1-octene) and α,ω -nonconjugated dienes (1,5-hexadiene) in toluene at 50 °C.³⁰ The decrease of molecular weights with increasing quantities of chain transfer agent evidenced the chain transfer reactions. The ethylene content in the copolymer remains unchanged, around 82-84%.

Polymer chain transfer in the course of norbornene / ethylene copolymerizations has been reported using the catalytic systems Me₂C(Ind)(Cp)ZrCl₂ **38** / MAO or *rac*-C₂H₄(2-^tBuMe₂SiO-Ind)₂ZrCl₂ **12b** / MAO in combination with aluminum or zinc alkyls (AlR₃ or ZnR₂, R = Me or Et).⁸⁶ The resulting decrease of the molecular weights of norbornene-ethylene copolymers indicates that the growing polymeric chains are able to

transfer from the Zr catalyst to the Al or Zn centres by alkyl-polymeryl exchange. It is noteworthy that the norbornene content is increased by a factor of *ca.* 4 upon addition of modest amounts of chain transfer agent, but decreased to about one-third of its initial value when the chain transfer agent was added in larger excess. The use of AlⁱBu₃ as potential chain transfer agent led in turn to an increase of the molecular weight. The mononuclear, tricoordinate geometry of AlⁱBu₃ enforced by its bulky alkyl ligands leads in the presence of trimethylaluminum to the formation of mixed species, which can form stable dimers with bridging Me groups (Scheme 27).⁸⁷ These latter species are probably too bulky to react with catalytically active alkyl zirconocene cations, explaining the increase in molecular weight observed.

The changes in comonomer incorporation with the amount of chain transfer agent are particularly interesting, especially if a more controlled character can be obtained. The CCTcoP of isoprene, styrene and hexene was studied in this frame using lanthanide based pre-catalysts in combination with magnesium or aluminum alkyls (Scheme 28).^{73,88-89} A series of lanthanum and neodymium borohydrido complexes, comprising the trisborohydrides Nd(BH₄)₃(THF)₃ and La(BH₄)₃(THF)₃ **21** and the half-lanthanidocenes Cp*Nd(BH₄)₂(THF)₂ and Cp*La(BH₄)₂(THF)₂ **22**, have been assessed for the CCTcoP of isoprene and styrene in the presence of butylethylmagnesium as CTA.^{73,88} For a monomer feed of 50 / 50 of styrene / isoprene, the amount of styrene inserted in the copolymer could be increased by a factor of 3.5 using 40 equiv. dialkylmagnesium *vs.* 1 equiv. in combination with **22** and the content of 3,4 isoprene units increased from 2 to 55 % at the expense of the 1,4 *trans*-selectivity. In addition, the number-average molecular weight of the copolymers decreased from 45200 to 3300 g.mol⁻¹, highlighting the occurrence of a transmetalation of the growing polymer chains. The resulting molecular weights were monomodal in all cases and the dispersities were

in the range 1.3 to 2.2 for a CCTP conducted in the presence of 2-40 equiv *n*BuMgEt. The comonomer content and the percentage of 3,4-enchainments increase gradually with the amount of CTA introduced for the half-lanthanidocenes **22**, highlighting attractive potential for microstructure control via CCTcoP. Concerning the metal nature, lanthanum affords narrower molecular weight distributions than neodymium, and the change in regioselectivity is less pronounced using the lanthanum trisborohydride **21b**. It should also be noted that the half-lanthanidocenes **22** afford higher activities under CCTcoP conditions than the trisborohydrides **21**.

$\text{Cp}^*\text{La}(\text{BH}_4)_2(\text{THF})_2$ / 1 equiv. *n*BuMgEt in the presence of aluminum-based chain transfer agents allowed CCTcoP while maintaining the 1,4-*trans* stereoselectivity of the polymerization of isoprene (Scheme 28b). From the molecular weight values, it could be concluded that transfer reactions were occurring in the presence of aluminum alkyls, however, the transfer efficiency is again less significant than that observed using *n*BuMgEt as CTA, as already observed in the case of isoprene CCTP.⁶⁹ The styrene incorporation is increased by a factor of 1.5 in the presence of aluminium based CTA with respect to the run without CTA.

The increasing quantities of 3,4-enchainments observed when *n*BuMgEt is used in excess can be explained on the same basis as that observed in the course of the homopolymerization of isoprene, *i.e.* (i) steric hindrance induced by the presence of magnesium dialkyl or di-isoprenyl and (ii) the ability of magnesium alkyls to oligomerize isoprene in a 3,4-regioselective manner. (i) could lead to sterically hindered associated species where the η^4 coordination mode of isoprene would be inhibited, leading to a η^2 coordination mode of the monomer. This hypothesis has also been advanced by other authors.⁹⁰⁻⁹⁴ (ii) implies in turn a chain-shuttling like copolymerization, as discussed previously. The 1,4-*trans* stereoselectivity observed in

the presence of 1 equiv. *n*BuMgEt and excess aluminum alkyls may be attributed to a lower ionic nature of the metal-carbon bond in aluminum alkyls vs. magnesium alkyls. The former may indeed not be able to disrupt the 1,4-*trans* stereospecific bimetallic active species formed using 1 equiv. *n*BuMgEt in combination with the borohydrido rare earth.

The observed change in the apparent reactivity ratio and comonomer content in the copolymer in the presence of excess magnesium alkyls has been attributed to two alternative pathways:

- i) A magnesium induced *co*-oligomerization of isoprene and styrene, leading to higher styrene content in the *co*-oligomer than that obtained using the Cp*La(BH₄)₂(THF)₂ / *n*BuMgEt combination.⁸⁸ Magnesium-based CTA may thus no longer be considered as dormant species, as observed for isoprene polymerizations.⁶⁹ A kind of chain shuttling could be therefore operating between the rare earth and the magnesium-based catalysts in the course of the CCTP of isoprene and styrene, as represented in Scheme 29.
- ii) A steric effect, considering the change in regioselectivity. In this case, styrene may be able to compete more efficiently during the coordination step to the lanthanide centre with a η^2 coordinated isoprene monomer vs. a η^4 coordinated isoprene monomer.

When aluminum alkyls are used as CTA the situation is different since aluminum species (i) are not able to *co*-oligomerize isoprene and styrene when used alone,⁸⁸ and (ii) as observed and discussed for isoprene CCTP, they do not disturb in an important manner the Mg-La active species. As a consequence, the quantity of styrene inserted in the copolymer increases only slightly, and the 1,4-*trans* stereoselectivity of the polymerization of isoprene is maintained as CCTcoP is operating.

From these results, CCTcoP can be viewed as a new concept for the control over the comonomer apparent relative reactivity in the course of a statistical

copolymerization, and as a consequence for the control of the microstructure of the resulting copolymers. The Cp*La(BH₄)₂(THF)₂ **22b** / *n*-butylethylmagnesium catalytic system was applied to the coordinative chain transfer polymerization of styrene and hexene (Scheme 28c).⁸⁹ Copolymers with number-molecular weights up to 7600 g/mol were obtained with dispersities around 1.4-1.5. The concept could be successfully extended, as chain transfer induced an increase of the amount of hexene inserted in the copolymer by a factor 3 when increasing the quantity of *n*BuMgEt from 1 equiv. (8.6% hexene in the copolymer) to 10 equiv. (23.2% hexene in the copolymer). Finally, it is also noteworthy that this study reports the first example of a rare-earth-mediated copolymerization of styrene and hexene.

Changes in apparent comonomer relative reactivity / incorporation with the nature of the chain transfer agent have also been reported in the course of the copolymerization of ethylene with polar monomers such as 10-undecen-1-ol, 5-hexen-1-ol and 3-buten-1-ol using vanadium(III) catalysts bearing bidentate [N,O] ligands.⁹⁵ Various alkylaluminums, such as Al^{*i*}Bu₃, AlEt₃, AlMe₃ and diethyl aluminum chloride were employed and the catalytic activity and monomer incorporation of the resulting copolymers were found to increase in the order: Al^{*i*}Bu₃ < AlEt₃ < AlMe₃ < diethyl aluminum chloride, in accordance with their increasing Lewis acidities. The activity of **39** (Figure 5) was gradually improved with higher Al/V molar ratios (1000-4000) while the comonomer incorporation was found to be independent of the catalyst concentration under these experimental conditions. Chain transfer to aluminum was observed as the molecular weights of the polymers decreased with increasing quantities of alkylaluminum compounds. Moreover, the ¹³C NMR spectra did not show any traces of terminal vinyl signals. The highest incorporation of 10-undecene-1-ol (13.9 mol%) was

obtained for a functional α -olefin charge of 0.5 mol/L; however, the activity of **39** was considerably decreased.

From these works, it can be seen that CCTcoP enables a control over both the regioselectivity of the reaction and the comonomer apparent relative reactivity / composition of the copolymer and can be viewed as a simple and convenient tool for tuning the microstructure of statistical copolymers.

4. Chain Shuttling Polymerization (CSP)

4.1. CSP combined to Chain Walking Polymerization

Besides statistical polymerizations, the chain shuttling approach was also applied to homopolymerizations. The synthesis of novel linear-hyperbranched multiblock polyethylene was reported via chain shuttling polymerization using **40** (Figure 6) and **12a** in combination with MAO and ZnEt_2 as a chain shuttling agent.⁹⁶ The α -diimine Ni(II) bromide catalyst **40** produces branched polyethylene in the presence of MAO via chain walking polymerization,⁹⁷ while the *ansa*-ethylenebis(1- η^5 indenyl) Zr chloride catalyst **12a** produces linear polyethylene. Linear-hyperbranched multiblock polyethylene is formed as a result of the statistical exchange of the growing polymer chains between the two catalysts yielding polyethylene with different architecture via the chain shuttling agent, as represented in Scheme 30.

4.2. CSP between enantiopure catalysts in a racemic mixture

Busico and coworkers smartly extended the CSP concept to the synthesis of isotactic stereoblock polypropylene using a racemic mixture of **9** in combination with MAO containing AlMe_3 as the chain transfer agent.⁹⁸ Isotactic stereoblock polypropylene (Scheme 31) is formed as a result of the statistical exchange of the growing polymer chains between the two active centres of opposite chirality via the chain shuttling agent. The chain shuttling was evidenced by the fact that, when single enantiomers were used, the stereoblock structure could not be observed. The synthesis of stereoblock polypropylene was also reported using Zr based catalysts⁹⁹ **16** and **41** leading to isotactic and syndiotactic polypropylene, respectively.

4.3. Chain shuttling copolymerizations

In a cutting-edge study, Arriola and coworkers reported the straightforward synthesis of a new class of thermoplastic elastomers.³ Multi-block ethylene / 1-octene copolymers with sequential crystallizable (low 1-octene content) and non-crystallizable (low ethylene content) statistical copolymer segments were synthesized via chain shuttling copolymerization (Scheme 2). Such an original microstructure results from the simultaneous presence in the reactive medium of chains growing on two different catalysts and of a chain transfer or chain shuttling agent. Pyridylamide Hf (**9**) and bis(phenoxy- imine) Zr (**37**) complexes combined to ZnEt_2 as chain shuttling agent have been selected for this purpose using high-throughput experiments. The comonomers reactivity ratios are different for the two catalysts, leading to ethylene-rich and 1-octene-rich segments respectively. The chains are able to growth in a sequential way on the two different catalysts via transfer to the chain shuttling agent. The transfer enables further control over the size and the relative amounts of the blocks are controlled by catalyst ratio, leading to shorter blocks as higher amounts of ZnEt_2 are added in the reactive medium.¹⁰⁰

The copolymers synthesized by Arriola *et al.* by chain shuttling are composed of crystallizable ethylene / 1-octene blocks with low 1-octene content and high melting temperature (hard blocks), and amorphous ethylene / 1-octene blocks with high 1-octene content and low glass transition temperature (soft blocks). Compared to statistical ethylene/1-octene copolymers, the new architecture leads to higher crystallization temperatures and rates, higher melting temperatures, and a better organized crystalline morphology, together with lower glass transition temperatures.^{100;101} The differences between the copolymers obtained by chain shuttling and those obtained by classical

statistical copolymerization become progressively more apparent as the total 1-octene content increases.

9 was also used for ethylene / 1-octene chain shuttling copolymerization in combination with Zr and Hf imine-amine catalysts **42-43** and ZnEt_2 as chain shuttling agent.¹⁰² For a same feed, the nature of the catalyst enabled to tune the hard block, allowing one to make olefin block copolymers with control over melting point, crystallinity and solubility.

Ethylene / alkene chain shuttling copolymerization was further reported by Sita *et al.* using **8** in combination with two different co-catalysts, the borate $[\text{PhNHMe}_2][\text{B}(\text{C}_6\text{F}_5)_4]$ and the borane $\text{B}(\text{C}_6\text{F}_5)_3$ and ZnEt_2 as chain shuttling agent.¹⁰³ The reactivity of ethylene and 1-hexene co-monomers *vs.* a tight and a loose ion pair generated *in situ* was found to be different, allowing a chain shuttling copolymerization similar to that reported by Arriola and coworkers³ with the use of a single transition metal based catalyst and three *co*-reagents. The inexistence of irreversible chain termination reactions together with a kinetic study allows to classify this copolymerization as *living*. Rytter *et al.* also advanced a possible ethylene / 1-hexene chain shuttling copolymerization using **11** and **44** combined to MAO in order to explain the presence of ethylene rich and 1-hexene rich blocks in the microstructure of the formed copolymers.¹⁰⁴

The scandium based pre-catalysts **45-47** were further used by Hou *et al.* for the styrene-isoprene chain shuttling copolymerization in combination with Al^iBu_3 as chain shuttling agent.¹⁰⁵ In contrast with the previous chain shuttling copolymerization, a multiblock microstructure of pure homopolymers was obtained (Scheme 32). The chain shuttling process induces this particular microstructure, as catalyst **45** when used alone is known to copolymerize efficiently isoprene and styrene, leading to a mixture of 1,4-

and 3,4- polyisoprene microstructure.¹⁰⁶ Interestingly, the polymerization remains highly regioselective and stereoselective in chain shuttling conditions. Using **45** and **46**, the multiblock is composed of syndiotactic polystyrene and poly(1,4-*cis* isoprene), while with **45** and **47**, poly(3,4-isoprene) blocks are obtained together with syndiotactic polystyrene. The styrene / butadiene / isoprene terpolymerization is finally reported, affording an unprecedented syndiotactic polystyrene / poly(1,4-*cis* isoprene) / poly(1,4-*cis* butadiene) multiblock microstructure.

It is noteworthy that, in order to reach a multiblock microstructure via CSP, the transfer rate must not be too fast *vs.* propagation in order to allow sufficient chain growth on each of the catalysts. Fast transfer rates would in turn result in a homogeneous microstructure, as observed in isoprene chain shuttling-like polymerization promoted by $\text{Cp}^*\text{Ln}(\text{BH}_4)_2(\text{THF})_2$ and *n*-butylethylmagnesium.⁷³ Kinetic studies¹⁰⁷ show further that a chain-shuttling rate constant that is too fast can alter the active-centre composition in a continuous stirring tank reactor, leading to different polymerization behaviour from that in the absence of the chain shuttling agent. It is also possible to observe a changing polymerization behaviour when a large amount of a chain shuttling agent allowing a moderate transfer rate is used.

5. Concluding comments and perspectives

CCTP can be considered as an approach of utmost importance considering the extension of the range of new polyolefin materials that can be obtained, using, many times, a single pre-catalyst. The versatility of chain transfer polymerization together with its ease of use relative to the synthetic effort required for the synthesis of different catalysts leading to the same pallet of materials or the difficulties encountered by other routes to reach an architecture control in polymerization makes this methodology an

attractive and promising field for the future of coordination polymerization. In comparison with other controlled polymerization techniques such as anionic or controlled radical polymerizations, CCTP can additionally afford a stereoselective character to the polymerization, leading to stereoregular polymeric microstructures and architectures under living conditions. Moreover, CCTP affords not only control over the regio- and stereo-selectivity of polymerizations, but also on the comonomer apparent relative reactivity in the course of statistical copolymerizations and thus on the composition of statistical copolymers. The combination of two or more CTA is of particular interest in this regard, allowing to play on the active species in a subtle manner in certain cases. The search for suitable CTA combinations can result in interesting and unexpected applications in the field of CCTP. CTA combinations can however lead to bulky mixed species that are not prone to induce transmetallation.

The search for fruitful precatalyst / CTA couples remains in turn a difficult task, owing to the numerous factors governing a synergistic combination. A deeper understanding of the factors favouring propagation and transfer *vs.* β H abstraction may certainly help in this regard,^{2;29;52} as well as high throughput techniques.³ The different metal combinations reported for CCTP in the literature are summarized in Table 1. If numerous transition metals and rare earths have been assessed as catalysts, CTAs are essentially based on aluminium, magnesium and zinc. The quest for CTAs based on other metals may open the way to new findings. A fine tuning of the ligand environment around the transition metal is certainly the major factor allowing the reversible process at a rate that allows the transfer reaction to occur more rapidly than the propagation, and with a total transfer efficiency (CCG reactions). These latter conditions have been presently fulfilled essentially using dialkylmagnesium and zinc, but not yet with aluminium alkyls; this may be due to the fact that the chain transfer reaction between

the transition metal and the aluminum alkyl is sterically more demanding for the three aluminium carbon bonds to grow concomitantly, especially at higher levels of oligomerization/polymerization. This requirement does not seem to be necessarily a prerequisite for industrial applications: this concept has already been claimed in early patents related to the synthesis of higher α -olefins or alcohols using catalytic amounts of hafniumocene¹⁵ or actinidocene¹⁶ based catalysts to provide chain growth on aluminium alkyls in the presence of MAO, in which cases Schultz-Flory as well as Poisson distributions of the oligomeric chains were obtained, respectively.

The nature of the active species in CCTP, with numerous metals – pre-catalyst, co-catalyst, CTA in excess – involved, which is surrounded by uncertainties, should be discussed. Proposals have been made by several authors to clarify this point.^{1f;2;21;26;108-}

¹⁰⁹ The *in situ* formation of heterobimetallic complexes, $[\text{TM}](\mu\text{-R})_2[\text{MGM}]$ (TM being a transition metal or a lanthanide and MGM a main group metal) depending on the co-catalyst is usually advanced (Scheme 33). The propagating species is in turn supposed to be a monometallic $[\text{TM}]\text{-R}$ alkyl deriving from the dissociation of the aforementioned bimetallic complex (Scheme 33). In the presence of three metals, an equilibrium between bridged bimetallics like $[\text{Fe}](\mu\text{-R})_2[\text{Zn}]$ and $[\text{Fe}](\mu\text{-R})_2[\text{Al}]$ was advanced (Scheme 34). This may also be the case in Chain Shuttling Processes, where two metal catalysts interact each on their own side with the same metal-CTA.

Most of the efforts have been directed till now toward the quest for suitable catalysts/CTA combinations. Progress has certainly to be made in the conception of chain transfer agents. The design of chain transfer agents allowing a controlled or targeted transfer rate to the transition metal catalyst may, for instance, allow a better control over the length of the blocks in multiblock structures. The combination of the transalkylation function of the chain transfer agent with an ability to influence the

selectivity of the reaction and/or the apparent co-monomer relative reactivity may be considered as a new paradigm for tuning (co-)polymer structures and even architectures via CCTP. This may take the form of a catalytic activity or an ability to play on the steric hindrance around the transition metal active species, among many others possibilities.

CCG reactions have been reported for various monomers, such as ethylene, styrene, and conjugated dienes. One of the challenges remaining is to find catalytic systems enabling perfect alkenes CCG, in which case the stereoselectivity has also to be addressed. If efficient isotactic and syndiotactic styrene CCTP have been reported, the 1,4-*trans* and 1,4-*cis* stereoselective CCTP of conjugated dienes occur with a modest transfer efficiency (2 to 15% and 10 to 26%, respectively). On the other hand, the CCG reported for conjugated dienes occurs with a gradual increase of 3,4 enchainments at the detriment of 1,4 enchainments. An objective to fulfill is clearly to reach highly 1,4-*cis* and 1,4-*trans* stereoselective and 3,4 regioselective and eventually isotactic or syndiotactic CCG for conjugated diene polymerizations. Noteworthy is that CCG being a process by which all polymer chains are linked to Al, Mg or Zn, further chemistries are still going on and may be exploited for the synthesis of chain end functionalized polymers via direct functionalization or block copolymerizations with suitable comonomers for the synthesis of new diblock copolymers.

A promising feature of CCTP lies in CSP. This process involving two catalytic sites in a sequential way enables the facile one pot synthesis of multiblock microstructures and architectures. Interestingly, these copolymers are now produced on an industrial scale since 2006, available as INFUSETM olefinic block copolymers.^{12d} The extension of chain shuttling copolymerization to other co-monomers combinations may afford the facile synthesis of a great variety of new thermoplastic elastomers. The

one pot synthesis of stereoblock polymers exhibiting a multiblock architecture is also very attractive and needs to be extended to other monomers and stereoconfigurations. The transposition of the CSP concept to the ring-opening polymerization of cyclic esters by Cui and Chen represents a smart example of what can be done.¹¹⁰

Acknowledgments

Andreia Valente thanks the Portuguese Foundation for Science and Technology for her postdoctoral scholarship (SFRH/BPD/80459/2011).

References

- 1 (a) X. Olonde, A. Mortreux, F. Petit, *J. Mol. Catal.* **1993**, 82, 75; (b) J.F. Pelletier, A. Mortreux, F. Petit, X. Olonde and K. Bujadoux in “*Catalyst Design for Tailor made Polyolefins*”, K. Soga and M. Terano Ed, Kodansha, Tokyo, **1994**, pp. 249; (c) J. F. Pelletier, K. Bujadoux, X. Olonde, E. Adisson, A. Mortreux, T. Chenal, Fr 9504203, April 5, **1995**, *US Patent 5,779,942*; (d) J. F. Pelletier, A. Mortreux, X. Olonde, K. Bujadoux, *Angew. Chem.* **1996**, 35, 1854; (e) K. Bujadoux, T. Chenal, C. Fouga, X. Olonde, J. F. Pelletier, A. Mortreux in : «*Metalorganic Catalysts for Synthesis and Polymerization*», W. Kaminsky, Ed., Springer, Berlin **1999**, pp. 590; (f) T. Chenal, X. Olonde, J. F. Pelletier, K. Bujadoux, A. Mortreux, *Polymer* **2007**, 48, 1844.
- 2 G. J. P. Britovsek, S. A. Cohen, V.C. Gibson, M. van Meurs, *J. Am. Chem. Soc.* **2004**, 126, 10701.
- 3 D. J. Arriola, E. M. Carnahan, P. D. Hustad, R. L. Kuhlman, T. T. Wenzel, *Science* **2006**, 312, 714.
- 4 P. Zinck, A. Valente, A. Mortreux, M. Visseaux, *Polymer* **2007**, 48, 4609.
- 5 R. Kempe, *Chem. Eur. J.* **2007**, 13, 2764.
- 6 S. B. Amin, T. J. Marks, *Angew. Chem.* **2008**, 47, 2006.
- 7 L. R. Sita, *Angew. Chem. Int. Ed.* **2009**, 48, 2464.
- 8 B. Heurtefeu, F. Vaultier, R. Leino, C. Boisson, H. Cramail, Single Site Catalysts in *Encyclopedia of Polymer Science and Technology* – Wiley 4th edition, 2012, 136.
- 9 K. Ziegler et al., *Angew. Chem.* **1952**, 64, 323.

10 The chain transfer efficiency is defined as the ratio of the alkyl groups of the chain transfer agent involved in the chain transfer, *i.e* leading to the growth of a macromolecular chain.

11 F. D'Agosto, C. Boisson, *Aust. J. Chem* **2010**, 63, 1155.

12 (a) V.C. Gibson, V.C. *Science* **2006**, 312, 703; (b) Busico, V. *Macromol. Chem. Phys.* **2007**, 208, 26; (c) Zintl, M.; Rieger B. *Angew. Chem. Int. Ed.* **2007**, 46, 333; (d) Hustad, P.D. *Science* **2009**, 325, 704; (e) Zinck, P. *Polym. Int.* **2012**, 61, 2.

13 (a) S.B Amin, T.J. Marks, *Angew. Chem.* **2008**, 47, 2; (b) T.C. Chung, *Prog. Polym. Sci.* **2002**, 27, 39; (c) J.Y. Dong, Y. Hu, *Coor. Chem. Rev.* **2006**, 250, 47; (d) R.C. Lopez, F. D'Agosto, C. Boisson, *Prog. Polym. Sci.* **2007**, 32, 419; (e) J. Mazzolini, E. Espinosa, F. D'Agosto, C. Boisson, *Polym. Chem.* **2010**, 1, 793.

14 The use of CCTP and chain shuttling to make olefin block copolymers has also been discussed in (a) P.D. Hustad, R.L. Kuhlman, C. Li Pi Shan, Chain Shuttling Catalysis and Olefin Block Copolymers. In: Matyjaszewski K and Möller M (eds.) Polymer Science: A Comprehensive Reference, Vol 3, Amsterdam, Elsevier, **2012**, 699; (b) T.T. Wenzel, D.J. Arriola, E.M. Carnahan, P.D. Hustad, R.L. Kuhlman, Metal Catalysts in Olefin Polymerization. Topics in Organometallic Chemistry, Vol. 26, Guan, Z, Springer-Verlag: Berlin, **2009**, 65.

15 Samsel, E.G. (Ethyl Corporation), EP 0539876, 1993

16 Samsel, E. G.; Eisenberg, D. C., (Ethyl Corporation), EP 0574854, 1993.

17 J. S. Rogers, G. C. Bazan, *Chem. Commun.* **2000**, 1209.

18 G. C. Bazan, J. S. Rogers, C. C. Fang, *Organometallics* **2001**, 20, 2059.

19 G. Mani, F. P. Gabbai, *Angew. Chem.* **2004**, 116, 2313.

20 G. Mani, F : P. Gabbai, *J. Organomet. Chem* **2005**, 690, 5145.

- 21 W. P. Kretschmer, A. Meetsma, B. Hessen, T. Schmalz, S. Qayyum, R. Kempe, *Chem. Eur. J.* **2006**, 12, 8969.
- 22 P.D. Hustad, R.L. Kuhlman, E.M. Carnahan, T.T. Wenzel, D.J. Arriola, *Macromolecules* **2008**, 41, 4081
- 23 R.L. Kuhlman, T.T. Wenzel, *Macromolecules* **2008**, 41, 4090
- 24 W. P. Kretschmer, T. Bauer, B. Hessen, R. Kempe, *Dalton Trans.* **2010**, 39, 6847.
- 25 I. Haas, W. P. Kretschmer, R. Kempe, *Organometallics* **2011**, 30, 4854.
- 26 C. Boisson, V. Monteil, D. Ribour, R. Spitz, F. Barbotin, *Macromol. Chem. Phys.* **2003**, 204, 5145.
- 27 F. Rouholahnejad, D. Mathis, P. Chen, *Organometallics* **2010**, 29, 294.
- 28 G. J. P. Britovsek, S. A. Cohen, V. C. Gibson, P. J. Maddox, M. van Meurs, *Angew. Chem. Int. Ed.* **2002**, 41, 489.
- 29 M. van Meurs, G. J. P. Britovsek, V. C. Gibson, S. A. Cohen, *J. Am. Chem. Soc.* **2005**, 127, 9913.
- 30 W. Zhang, J. Wei, L. R. Sita, *Macromolecules* **2008**, 41, 7829.
- 31 P. D. Hustad, R. L. Kuhlman, D. J. Arriola, E. M. Carnahan, T. T. Wenzel, *Macromolecules* **2007**, 40, 20, 7061.
- 32 S. Lieber, H.-H. Brintzinger, *Macromolecules* **2000**, 33, 9192.
- 33 S. Hild, C. Cobzaru, C. Troll, B. Rieger, *Macromol. Chem. Phys.* **2006**, 207, 665.
- 34 E. Barsties, S. Schaible, M.-H. Prosenc, U. Rief, W. Röhl, O. Weyand, B. Dorer, H. H. Brintzinger, *J. Organomet. Chem.* **1996**, 520, 63.
- 35 G. Fan, J.-Y. Dong, *J. Mol. Cat. A: Chemical* **2005**, 236, 246.
- 36 N. Naga, K. Mizunuma, *Polymer* **1998**, 39, 21, 5059.
- 37 R. Leino, H. J. G. Luttikhedde, P. Lehmus, C.-E. Wilén, R. Sjöholm, A. Lehtonen, J. V. Seppälä, J. H. Näsman, *Macromolecules* **1997**, 30, 3477.

- 38 L. Resconi, F. Piemontesi, I. Cammurati, D. Balboni, *Organometallics* **1996**, 15, 5046.
- 39 A. Tynys, J. L. Eilertsen, E. Rytter, *Macromol. Chem. Phys.* **2006**, 207, 295.
- 40 W. Zhang, L. R. Sita, *J. Am. Chem. Soc.* **2008**, 130, 442.
- 41 T. Shiono, S. Yoshida, H. Hagihara, T. Ikeda, *Applied Catalysis A: Chemical* **2000**, 200, 145.
- 42 J. Kukral, P. Lehums, M. Klinga, M. Leskelä, B. Rieger, *Eur. J. Inorg. Chem.* **2002**, 1349.
- 43 V. Busico, R. Cipullo, J.C. Chadwick, J.F. Modder, O. Sudmeijer, *Macromolecules* **1994**, 27, 7538.
- 44 J. Wei, W. Zhang, L. R. Sita, *Angew. Chem. Int. Ed.* **2010**, 49, 1768.
- 45 S. Bogaert, T. Chenal, A. Mortreux, G. Nowogrocki, C. W. Lehmann, J.-F. Carpentier, *Organometallics* **2001**, 20, 199.
- 46 S. Bogaert, J. F. Carpentier, T. Chenal, A. Mortreux, G. Ricart, *Macromol. Chem. Phys.* **2000**, 201, 1813.
- 47 Y. Sarazin, T. Chenal, A. Mortreux, H. Vezin, J. F. Carpentier, *J. Mol. Catal.* **2005**, 238, 207.
- 48 P. Zinck, M. Visseaux, A. Mortreux, *Z. Anorg. Allg. Chem.* **2006**, 632, 1943.
- 49 A. Rodrigues, E. Kirillov, B. Vuillemin, A. Razavi, J. F. Carpentier, *J. Mol. Catal. A* **2007**, 273, 87.
- 50 L. Annunziata, A.-S. Rodrigues, E. Kirillov, Y. Sarazin, J. Okuda, L. Perrin, L. Maron, J.-F. Carpentier, *Macromolecules* **2011**, 44, 3312.
- 51 Y. Sarazin, P. de Frémont, L. Annunziata, M. Duc, J.-F. Carpentier, *Adv. Synth. Catal.* **2011**, 353, 1367.

- 52 P. Zinck, A. Valente, F. Bonnet, A. Violante, A. Mortreux, M. Visseaux, S. Ilinca, R. Duchateau, P. Roussel, *J. Polym. Sci.: Part A : Polym. Chem.* **2010**, 48, 802.
- 53 R. Po, N. Cardi, L. Abis, *Polymer* **1998**, 39, 4, 959.
- 54 T. H. Newman, K. K. Borodychuk (Dow Chemical Co. USA). Patent US 5, 428, 120, **1995**.
- 55 L. Friebe, O. Nuyken, W. Obrecht, *Adv. Polym. Sci.* **2006**, 204, 1.
- 56 L. Friebe, O. Nuyken, H. Windish, W. Obrecht, *Macromol. Chem. Phys.* **2002**, 203, 1055.
- 57 G. S. S. Rao, V. K. Upadhyay, R. C. Jain, *Journal of Applied Polymer Science* **1999**, 71, 595.
- 58 L. Friebe, H. Windish, O. Nuyken, W. Obrecht, *J. Macromol. Sci.* **2004**, A41, 3, 245.
- 59 L. Friebe, J. M. Müller, O. Nuyken, W. Obrecht, *J. Macromol. Sci.* **2006**, 204, 1.
- 60 L. Friebe, J. M. Müller, O. Nuyken, W. Obrecht, *J. Macromol. Sci.* **2006**, 43, 11.
- 61 J. B. Nickaf, R. P. Burford, R. P. Chaplin, *J. Polym. Sci., Polym. Chem.* **1995**, 33, 1125.
- 62 C. Fan, C. Bai, H. Cai, Q. Dai, X. Zhang, F. Wang, *J. of Polym. Sci: Part A: Polym. Chem.* **2010**, 48, 4768.
- 63 S. Kaita, M. Yamanaka, A.C. Horiuchi, Y. Wakatsuki, *Macromolecules* **2006**, 39, 1359.
- 64 Y. Taniguchi, W. Dong, T. Katsumata, M. Shiotsuki, T. Masuda, *Polymer Bulletin* **2005**, 54, 173.
- 65 M.J. Vitorino, P. Zinck, M. Visseaux, *Eur. Polym. J.* **2012**, 48, 1289.
- 66 F. Wang, C. Zhang, Y. Hu, X. Jia, C. Bai, X. Zhang, *Polymer* **2012**, 53, 6027.
- 67 M.F.K. Takahashi, M. De Lima, W.L. Polito, *Polymer Bull.* **1997**, 38, 455.
- 68 P. Zinck, M. Terrier, A. Mortreux, M. Visseaux, *Polym. Test.* **2009**, 28, 106


- 69 A. Valente, P. Zinck, M. J. Vitorino, A. Mortreux, M. Visseaux, *J. Polym. Sci.: Part A: Polym. Chem.* **2010**, 48, 4640.
- 70 M. Visseaux, M. Mainil, M. Terrier, A. Mortreux, P. Roussel, T. Mathivet, M. Destarac, *Dalton Trans.* **2008**, 4558.
- 71 Z. Jian, D. Cui, Z. Hou, X. Li, *Chem. Commun.* **2010**, 46, 3022.
- 72 J. Gromada, L. le Pichon, A. Mortreux, F. Leising, J.F. Carpentier, *J. Organomet. Chem.* **2003**, 683, 44.
- 73 A. Valente, P. Zinck, A. Mortreux, M. Visseaux, *Macromol. Rapid Commun.* **2009**, 30, 528.
- 74 H. Yasuda, Y. Nakano, K. Natsukawa, H. Tani, *Macromolecules* **1978**, 11, 586.
- 75 S. Loughmari, A. Hafid, A. Bouazza, A. El Bouadili, P. Zinck, M. Visseaux, *J. Polym. Sci., Polym. Chem* **2012**, 50, 2989.
- 76 S. Li, W. Miao, T. Tang, W. Dong, X. Zhang, D. Cui, *Organometallics* **2008**, 27, 718.
- 77 L. Annunziata, M. Duc, J.F. Carpentier, *Macromolecules* **2011**, 44, 7158.
- 78 D.-J. Byun, D.-K. Shin, S. Y. Kim, *Macromol. Rapid Commun.* **1999**, 20, 419.
- 79 D.-J. Byun, S. Y. Kim, *Macromolecules* **2000**, 33, 1921.
- 80 T. Yoshida, N. Koga, K. Morokuma, *Organometallics* **1995**, 14, 746.
- 81 T. K. Woo, L. Fan, T. Ziegler, *Organometallics* **1994**, 13, 2252.
- 82 B. J. Burger, M. E. Thompson, W. D. Cotter, J. E. Bercaw, *J. Am. Chem. Soc.* **1990**, 112, 1566.
- 83 K. Thorshaug, E. Rytter, M. Ystenes, *Macromol. Rapid Commun.* 1997, 18, 715.
- 84 K. Hakala, T. Helaja, B. Löfgren, *Polymer Bulletin* **2001**, 46, 123.
- 85 A. Tynys, T. Saarinen, K. Hakala, T. Helaja, T. Vanne, P. Lehmus, B. Löfgren, *Macromol. Chem. Phys.* **2005**, 206, 1043.

- 86 N. N. Bhriani, H.-H. Brintzinger, D. Ruchatz, G. Fink, *Macromolecules* **2005**, 38, 2056.
- 87 (a) E. G. Hoffmann, *Trans. Faraday Soc.* **1962**, 58, 642; (b) O. Yamamoto, K. Hayamizu, *J. Phys. Chem.* **1968**, 72, 822.
- 88 A. Valente, P. Zinck, A. Mortreux, M. Visseaux, *J. Polym. Sci. Part A : Polym. Chem.* **2011**, 49, 1615.
- 89 A. Valente, P. Zinck, A. Mortreux, M. Bria, M. Visseaux, *J. Polym. Sci Part A : Polym. Chem.* **2011**, 49, 3778.
- 90 B. Wang, D. Cui, K. Lv, *Macromolecules* **2008**, 41, 1983.
- 91 L. Zhang, Y. Luo, Z. Lou, *J. Am. Chem. Soc.* **2005**, 127, 14562.
- 92 S. Li, D. Cui, D. Li, Z. Hou, *Organometallics* **2009**, 28, 4814.
- 93 C. Döring, W. P. Kretschmer, R. Kempe, *Eur. J. Inorg. Chem.* **2010**, 18, 2853.
- 94 M. Visseaux, F. Bonnet, *Coord. Chem. Rev.* **2011**, 255, 357.
- 95 J.-S. Um, J.-Y. Liu, S.R. Liu, Y.-S. Li, *Polymer* **2009**, 50, 5059.
- 96 A. Xiao, L. Wang, Q. Liu, H. Yu, J. Wang, J. Huo, Q. Tan, J. Ding, W. Ding, A. M. Amin, *Macromolecules* **2009**, 42, 1834.
- 97 In a chain walking polymerization, the active growing site isomerizes to an internal position on the polymer backbone during propagation, so that the next monomer unit can be assembled onto the polymer backbone instead of at the end. See Z. Guan, P. M. Cotts, E. F. McCord, S. J. McLain, *Science* **1999**, 283, 2059.
- 98 F. Alfano, H. W. Boone, V. Busico, R. Cipullo, J. C. Stevens, *Macromolecules* **2007**, 40, 7736.
- 99 A. Tynys, J. L. Eilertsen, J. V. Seppala, E. Rytter, *J. Polym. Sci., Polym. Chem.* **2007**, 45, 1364.


- 100 H. P. Wang, D. U. Khariwala, W. Cheung, S. P. Chum, A. Hiltner, E. Baer, *Macromolecules* **2007**, 40, 2852.
- 101 D. U. Khariwala, A. Taha, S. P. Chum, A. Hiltner, E. Baer, *Polymer* **2008**, 49, 1365.
- 102 R.L. Kuhlman, J. Klosin, *Macromolecules* **2010**, 43, 7903.
- 103 J. Wei, W. Zhang, R. Wickham, L. R. Sita, *Angew. Chem. Int. Ed.* **2010**, 49, 9140.
- 104 I. Bruaseth, E. Rytter, *Macromolecules* **2003**, 36, 3026.
- 105 L. Pan, K. Zhang, M. Nishiura, Z. Hou, *Angew. Chem.* **2011**, 50, 12012.
- 106 H. Zhang, Y. Luo, Z. Hou, *Macromolecules* **2008**, 41, 1064.
- 107 M. Zhang, T.W. Karjala, P. Jain, *Ing. Eng. Chem. Res.* **2010**, 49, 8135.
- 108 (a) M. Bochmann, S.J. Lancaster, *J. Organomet. Chem.* **1995**, 497, 55; (b) M. Bochmann, S. J. Lancaster, *Angew. Chem.*, **1994**, 33, 1634.
- 109 J.M. Camara, R.A. Petros, J.R.Norton, *J. Am. Chem. Soc.* **2011**, 133, 5263.
- 110 W. Zhao, Y. Wang, X. Liu, X. Chen, E.Y.X Chen, *Chem. Com.*, **2012**, 48, 6375.

CTA	Cat.	Monomers ^a	Transfer efficiency ^b	Copo	Ref.
Al	Cr	E	nd	-	17-20
	Fe	E	Low to High	-	2
	Gd	I (<i>cis</i>)	Low	-	71
	Hf	E, P (<i>atactic</i> & <i>iso</i>)	Low to High	CSP	25;44;98
	Nd	E, B (<i>cis</i>), I (<i>cis</i> & <i>trans</i>), copo I/S, E/B	Low to High	IRR	26;56;58;60;62-70;69;78
	Sc	I (3,4), Copo I (<i>cis</i> or 3,4) /S (<i>syndio</i>), I (<i>cis</i>)/ B (<i>cis</i>)/ S(<i>syndio</i>)	Low	CSP	76;105
	Th	E	High	-	16
	Ti	P, S (<i>syndio</i>)	Medium to High	-	41;53-54
	V	Copo E/ α -olefin	Low		95
	Y	E	High	-	21;24
	Zr	E, P (<i>iso</i>), Copo E/P, E/H, Et/N, Et/allylbenzene, Et/functional alkene, Pr/functional alkene	Low to High	IRR-CSP	27;32-33;35-36;43;78-79;84-85;99;104
Mg	Ce	S	Medium to High	-	47
	La	I, S(<i>syndio</i>), Copo S/H, I/S	Medium to High-CCG	IRR	4;48;52;73;88-89
	Nd	E, O, S (<i>syndio</i>), I, Myrcene, Copo I/S	Medium to High-CCG	IRR	1;4;45-46;48-49;52;69;75;88
	Sm	E	High-CCG	-	1
	Y	E, S (<i>iso</i>), I	High-CCG	-	1;50-51;77
Zn	Fe	E	High-CCG		2;28-29
	Hf	E, P (<i>atactic</i>), H, O, 1,5-hexadiene Copo E/ α -olefin	Low to High	IRR-CSP	3;30;40-44;103
	Nd	B	Medium	-	60
	Zr	E, Copo E/O, Et/N	Low to High	IRR-CSP	3;86;96
	Ni	E	Low	CSP	96
	Y	I (<i>trans</i>)	High	-	77
Pb,Sn	Fe	E	Low	-	2
Ga			Medium to High-CCG		


Table 1. Metal combinations used for CCTP. ^a E=ethylene, P=propylene, H=1-hexene, O=1-octene, S=styrene, B=butadiene, I=isoprene, N=norbornene; ^b Transfer efficiency rating : low 0-33%, medium 33-66%, high >66%, CCG 100% or close to; ^c when copolymerization is concerned, CSP=chain shuttling polymerization; IRR=increase in comonomer reactivity ratio

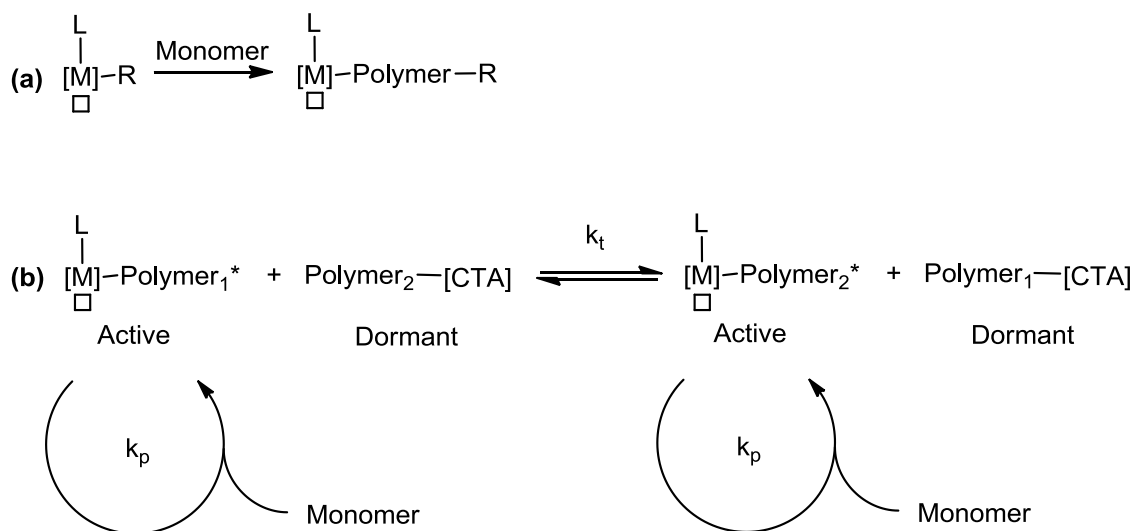


Scheme 1. Classical coordinative polymerization (a) vs. Coordinative Chain Transfer Polymerization (b)

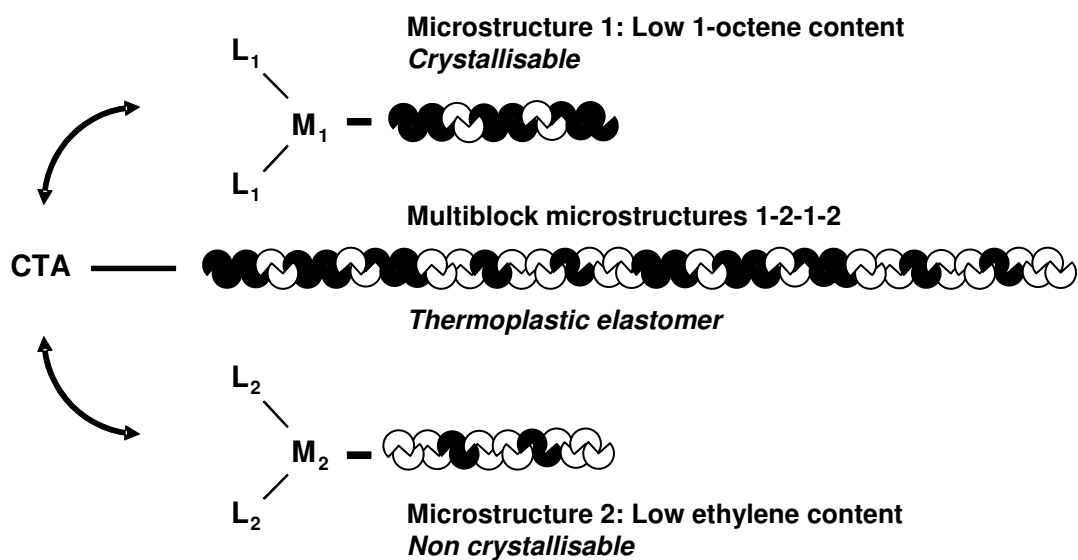


Scheme 2. Chain shuttling copolymerization.³ M_i represents transition metals allowing propagation, L_i ligands, and CTA the chain transfer or chain shuttling agent.

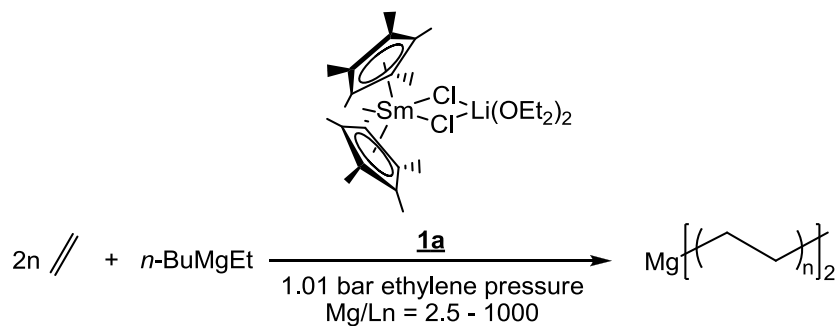


Scheme 3. Lanthanide catalyzed polyethylene chain growth on magnesium (CCG)¹; reaction conducted at 80 °C producing up to 2000 g/mol polyethylene.

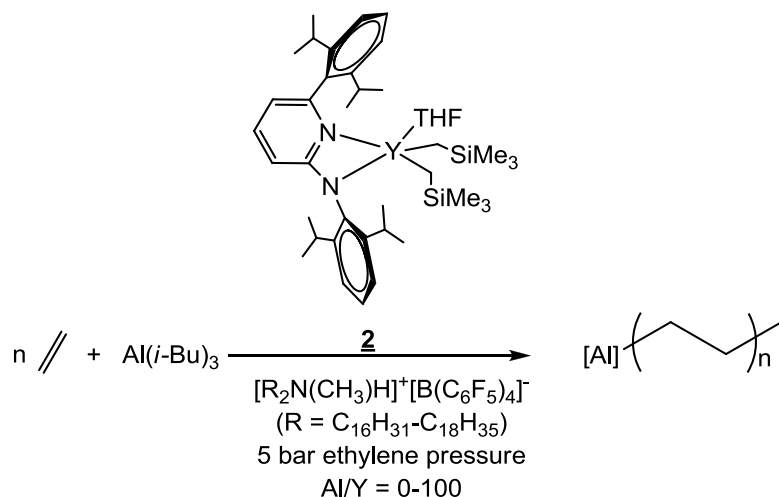


Scheme 4. Ethylene CCTP using organoyttrium cation derived from 2 and Al^iBu_3 ²¹; reaction conducted at 80 °C producing up to 4000 g/mol polyethylene.

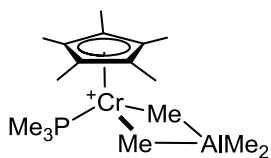


Scheme 5. Bridging species that could be formed during the polymerization of ethylene using 4 and MAO^{17,18}

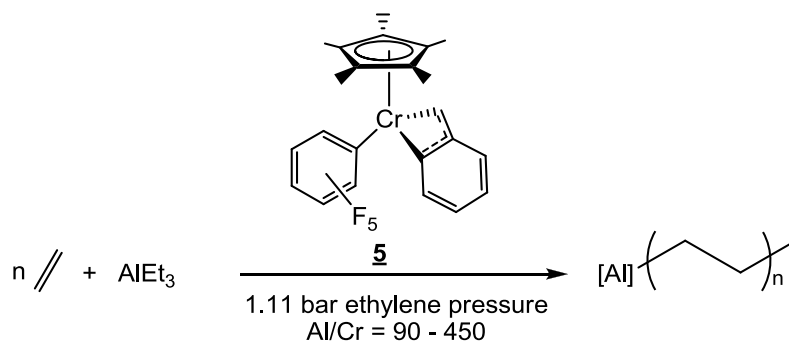


Scheme 6. Ethylene CCTP using catalyst 5 and AlEt_3 ¹⁹; reaction conducted at 25 °C producing up to 500 g/mol polyethylene.

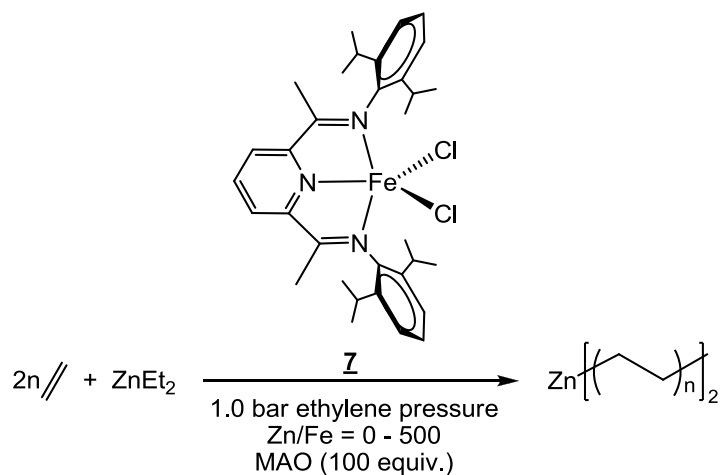


Scheme 7. Iron catalyzed polyethylene chain growth on zinc (CCG)^{2,28}; reaction conducted at room temperature producing up to 3000 g/mol polyethylene.

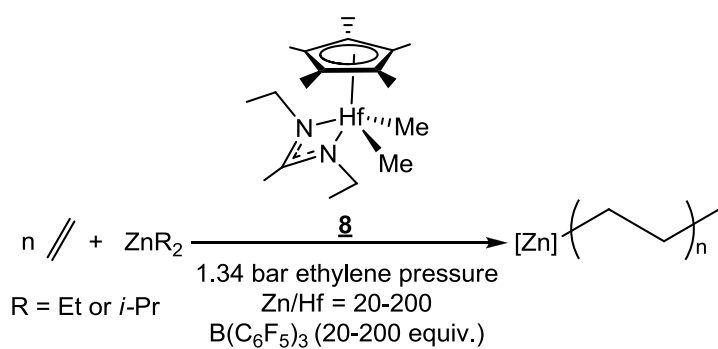


Scheme 8. Ethylene CCTP between the catalyst 8 and ZnR₂³⁰; reaction conducted at 25 °C producing up to 670 g/mol polyethylene.

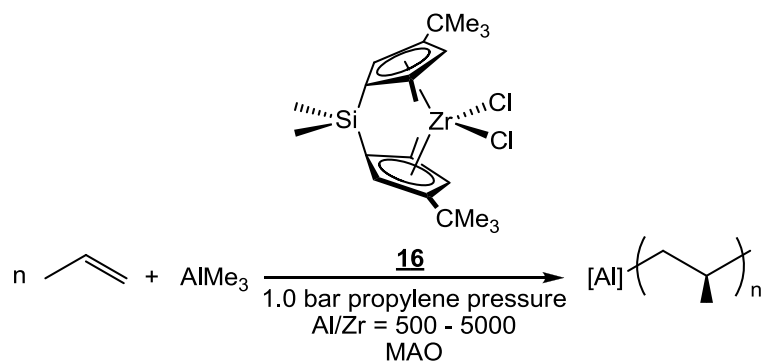


Scheme 9. Propylene CCTP using catalyst 16 and AlMe_3 ;³² reaction conducted at 40 °C producing up to 2100 g/mol 95-99% [mmmm] polypropylene.

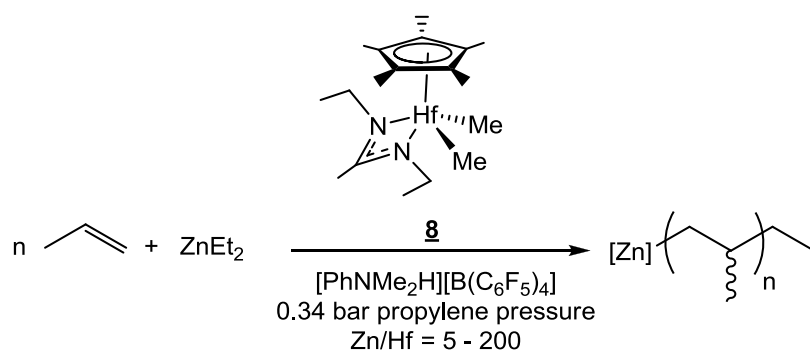


Scheme 10. Propylene CCTP using 8 and ZnEt_2 ;^{30,40} reaction conducted at 0 °C producing up to 33300 g/mol atactic polypropylene with PDI \leq 1.1.

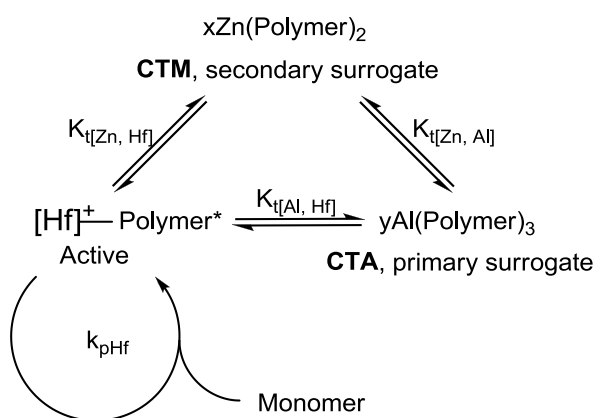

Scheme 11. Propylene ternary CCTP using 8 as the active chain-growth initiator, AlR_3 ($\text{R} = \text{ethyl}, n\text{-propyl}, \text{isobutyl}$) as the chain transfer agent (CTA) and ZnEt_2 as chain transfer mediator (CTM).⁴⁴ Polymer* represents a growing polymeric chain. $k_{p\text{Hf}}$ and K_t are the rate constants for propagation on the hafnium and reversible transfer, respectively.

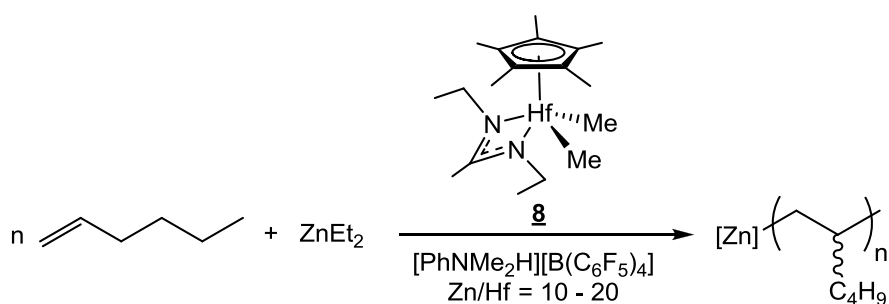


Scheme 12. Hexene CCTP using Hf based complex 8 and ZnEt_2 ,³⁰ reaction conducted at $-10\text{ }^\circ\text{C}$ producing up to 6650 g/mol atactic polyhexene.

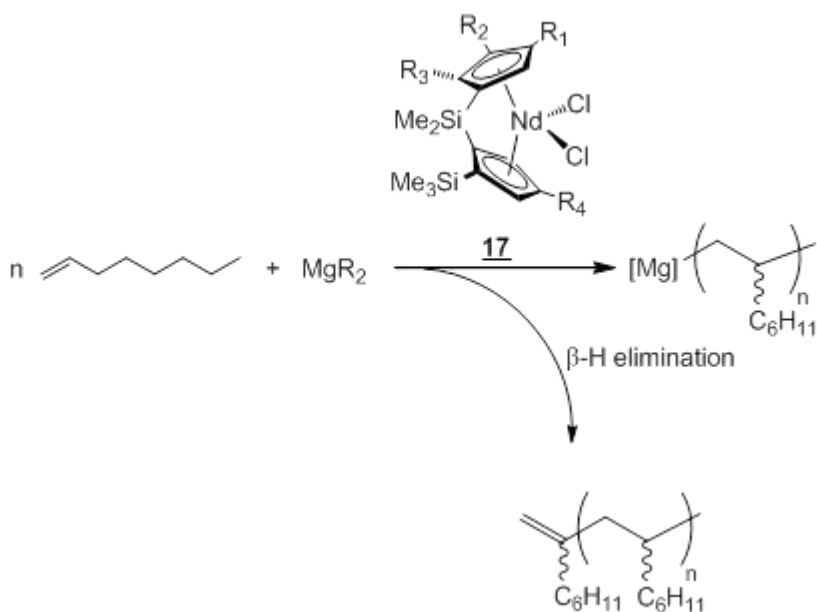


Scheme 13. Octene polymerization using neodymocenes and dialkylmagnesium showing the simultaneous occurrence of β -H elimination.⁴⁵


Chain transfer polymerization

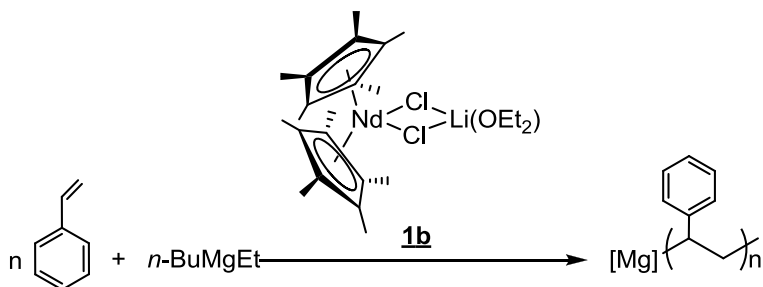


Radical Polymerization

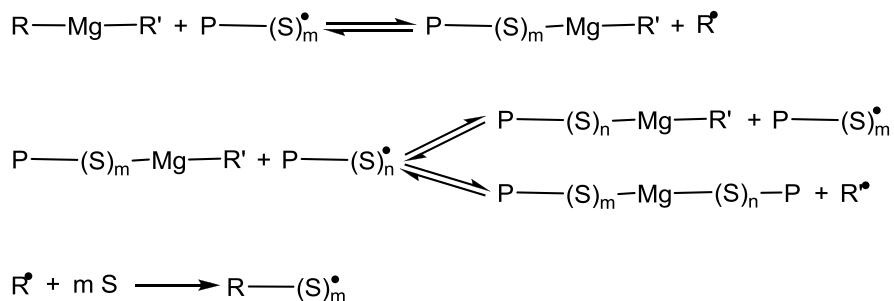


Scheme 14. Polymerization of styrene by chlorolanthanidocene/dialkyl magnesium system⁴⁶; S = styrene monomer and R, R' = Bu and Et.

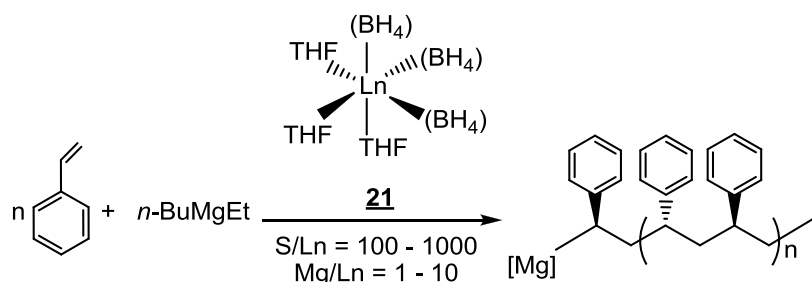


Scheme 15. Styrene polymerization using $\text{Ln}(\text{BH}_4)_3(\text{THF})_3$ and $n\text{BuMgEt}$;⁴⁸ reaction conducted at 50 °C producing up to 19200 g/mol atactic polystyrene with 81% chain transfer efficiency; S = styrene monomer.

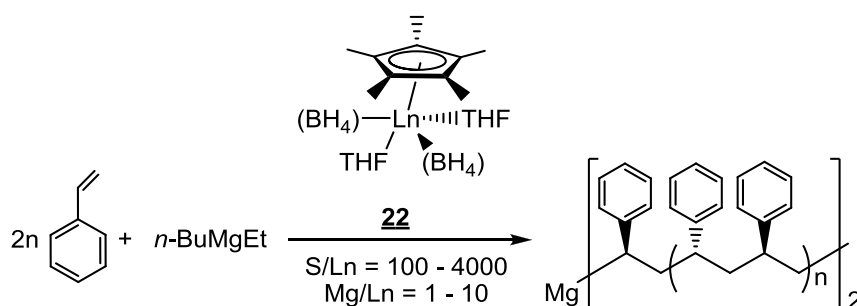


Scheme 16. Half-lanthanidocene catalyzed polystyrene chain growth polymerization on magnesium (CCG);^{4,52} reaction conducted at 50 °C producing up to 16000 g/mol 85 % syndiotactic polystyrene with $\approx 100\%$ chain transfer efficiency; R = Bu or Et and S = styrene monomer.

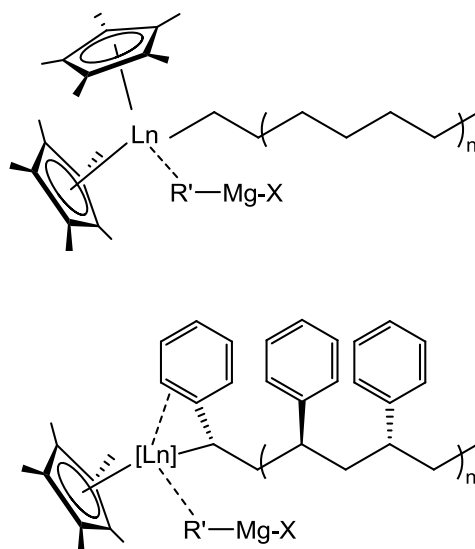


Scheme 17. Analogy between lanthanidocene mediated polyethylene CCG and half-lanthanidocene mediated polystyrene CCG.

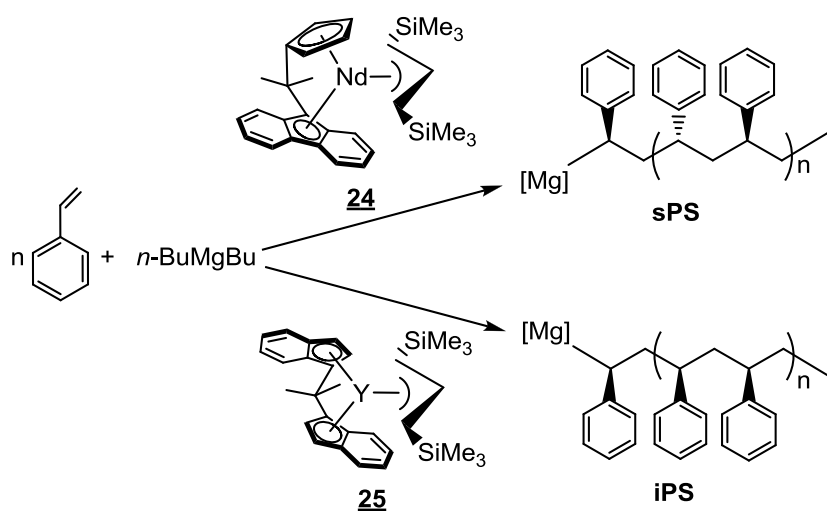


Scheme 18. Styrene polymerization using the allyl ansa-lanthanidocenes 24 and 25 and $n\text{BuMgBu}$;⁵¹ reaction conducted at 80-100 °C producing syndiotactic or isotactic polystyrenes, respectively.

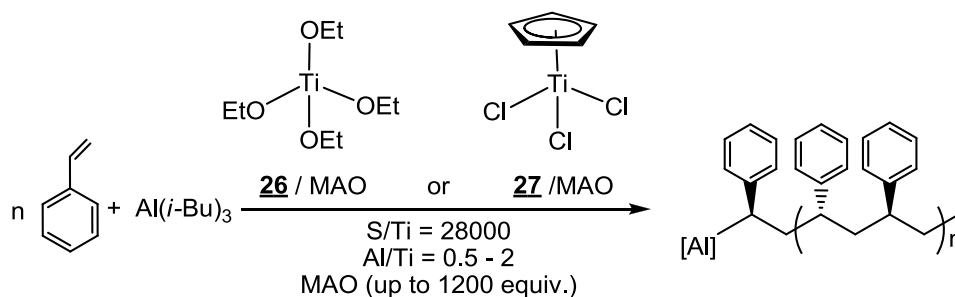


Scheme 19. Syndiotactic polystyrene CCTP using titanium complexes and $\text{Al}i\text{Bu}_3$;⁵³ reaction conducted at 60 °C producing up to 400000 g/mol highly syndiotactic polystyrene; S = styrene monomer.

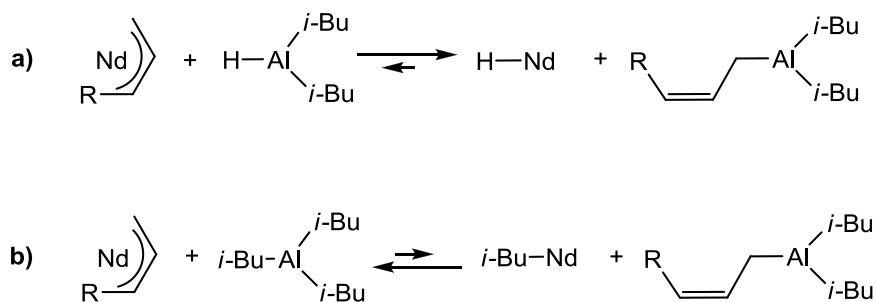


Scheme 20. Transfer reactions with a) AlH^iBu_2 ; b) Al^iBu_3 ⁵⁸

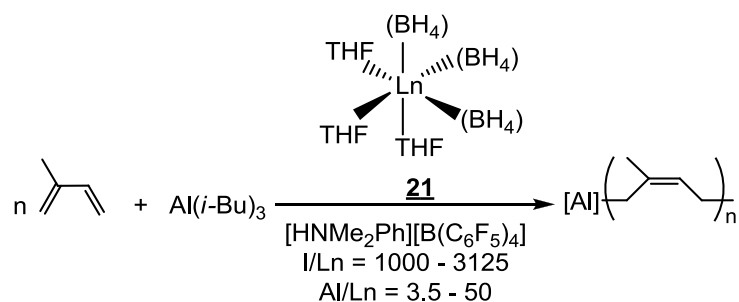


Scheme 21. Cationic 1,4-*cis* isoprene polymerization using **21 in combination with Al^iBu_3 ;⁷⁰ reaction conducted at 20-50 °C producing up to 120000 g/mol of high *cis*-polyisoprene with 4-6% chain transfer efficiency; I = isoprene monomer.**

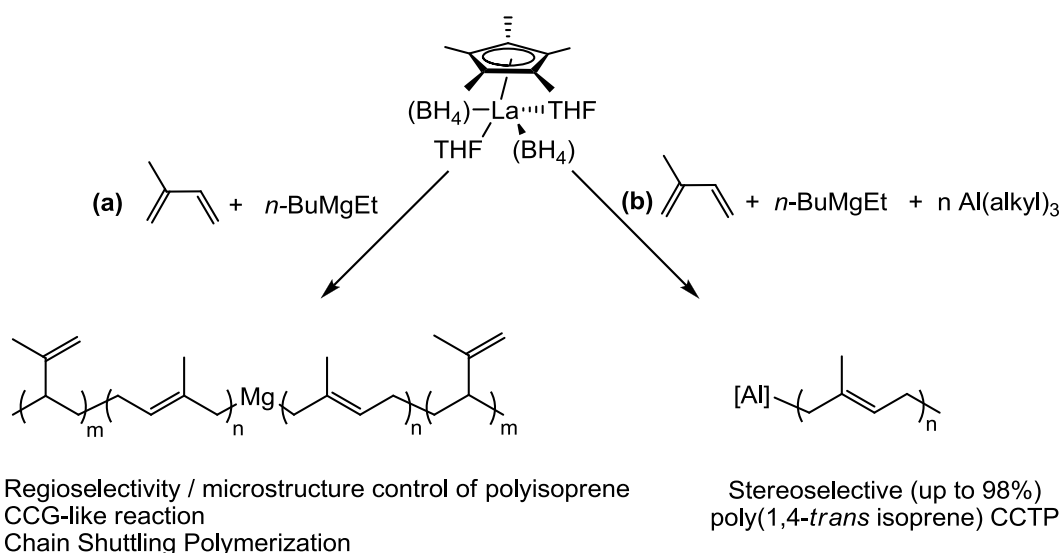


Scheme 22. Isoprene CCTP reactions using (a) $n\text{BuMgEt}$ and (b) $n\text{Al(alkyl)}_3$ or $n\text{AlH}^i\text{Bu}_2$ as CTA^{69,73}

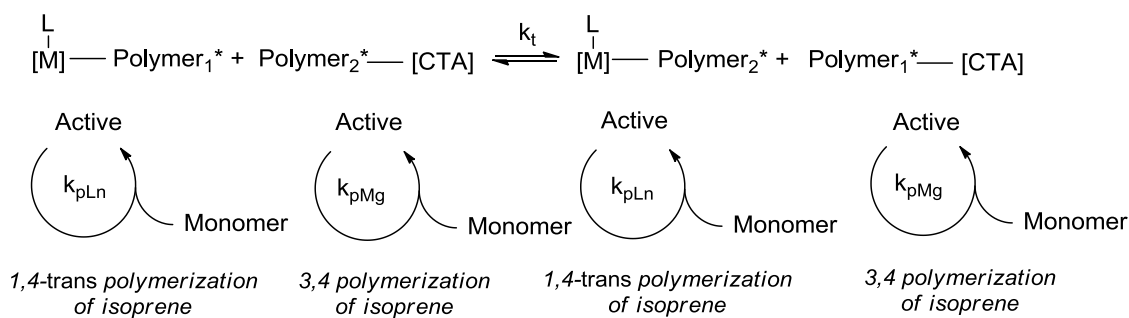


Scheme 23. Chain shuttling-like polymerization of isoprene using lanthanide based pre-catalysts and a magnesium dialkyl chain transfer agent able to co-oligomerize the monomers.^{69,73} Polymer* represents a growing polymeric chain, M the metal allowing propagation, L a ligand, and CTA the chain transfer agent. $k_{p\text{Ln}}$, $k_{p\text{Mg}}$ and k_t are the rate constants for propagation on the lanthanide, propagation on magnesium and reversible transfer respectively.

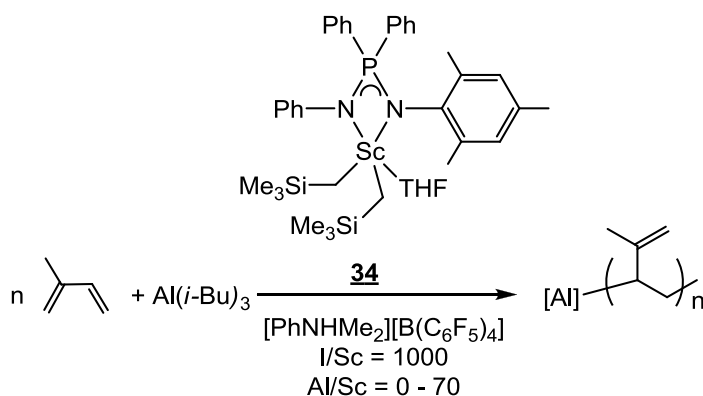


Scheme 24. 3,4 selective polymerization of isoprene using a Sc complex in combination with $\text{Al}(i\text{-Bu})_3$;⁷⁶ reaction conducted at -60 - 20 °C; I = isoprene monomer.

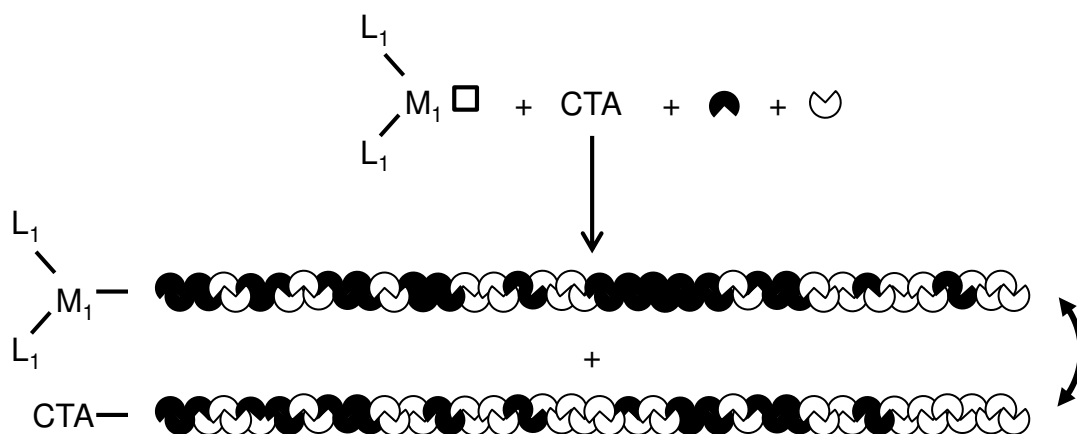


Scheme 25. Statistical copolymerization, where M = catalyst and CTA = chain transfer agent

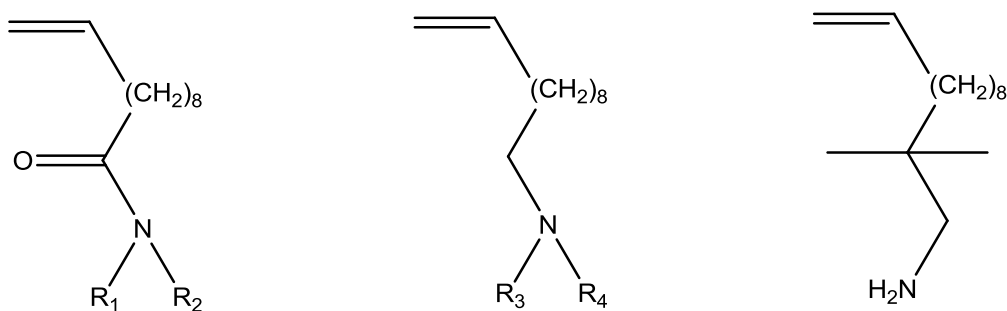


Scheme 26. Amide and amine functional alkenes. $R_{1-4} = \text{H}$, alkyl or benzyl.

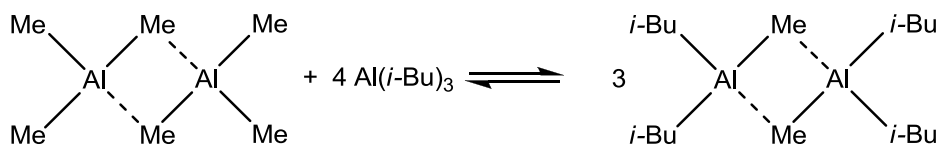


Scheme 27. Formation of stable dimers with bridging Me groups between AlMe_6 and $\text{Al}i\text{Bu}_3$ ⁸⁷

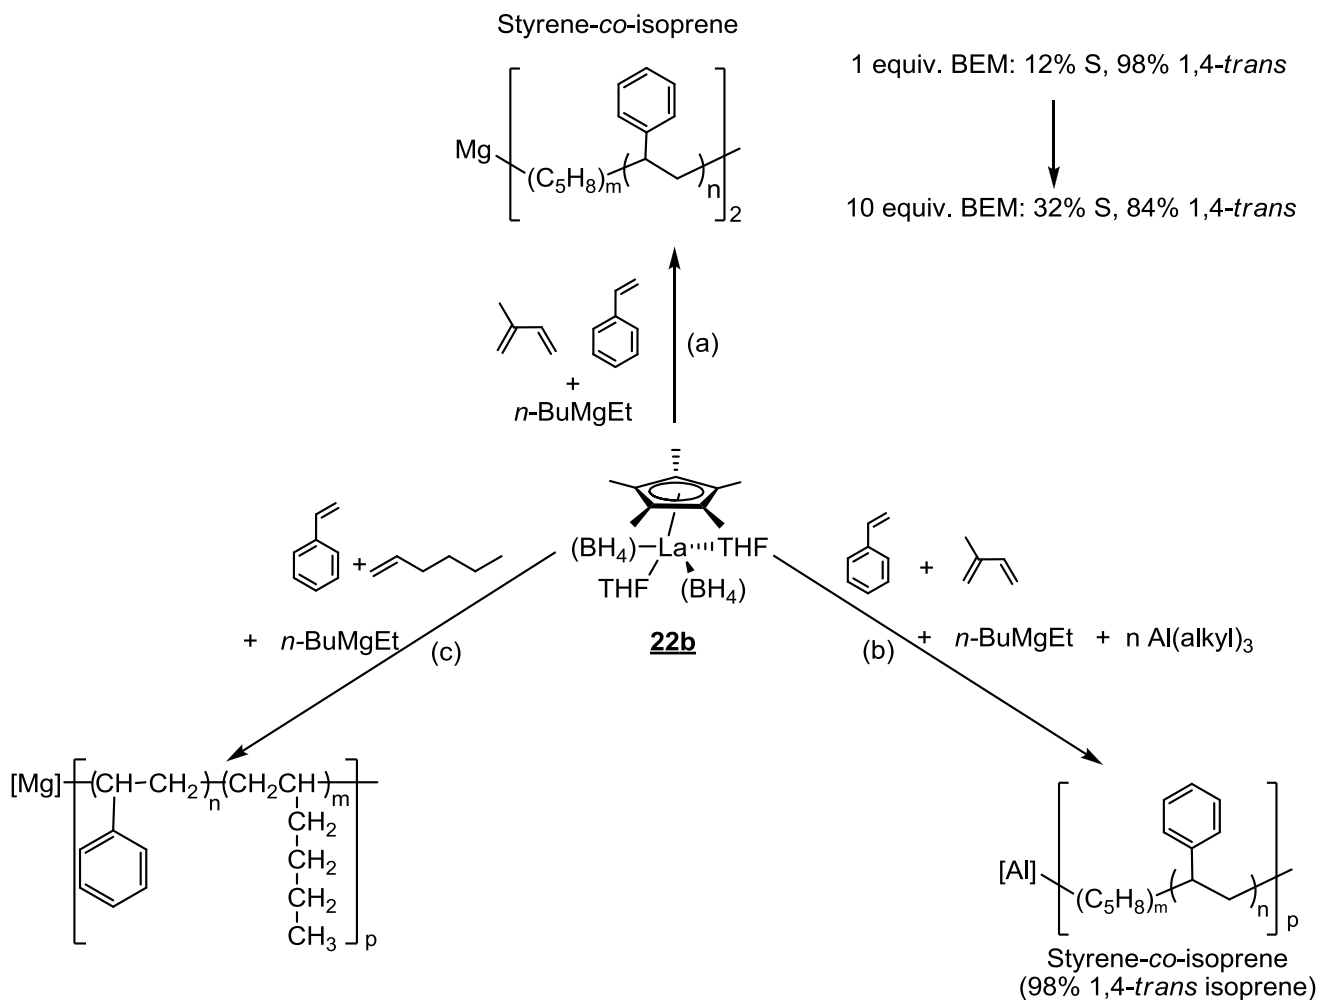


Scheme 28. Coordinative chain transfer copolymerizations of (a) Styrene and isoprene using $n\text{BuMgEt}$ as CTA;^{73,88} (b) Styrene and isoprene using 1 equiv. $n\text{BuMgEt}$ and Al(alkyl)_3 as CTA^{73,88} and (c) Styrene and 1-hexene using $n\text{BuMgEt}$ as CTA⁸⁹

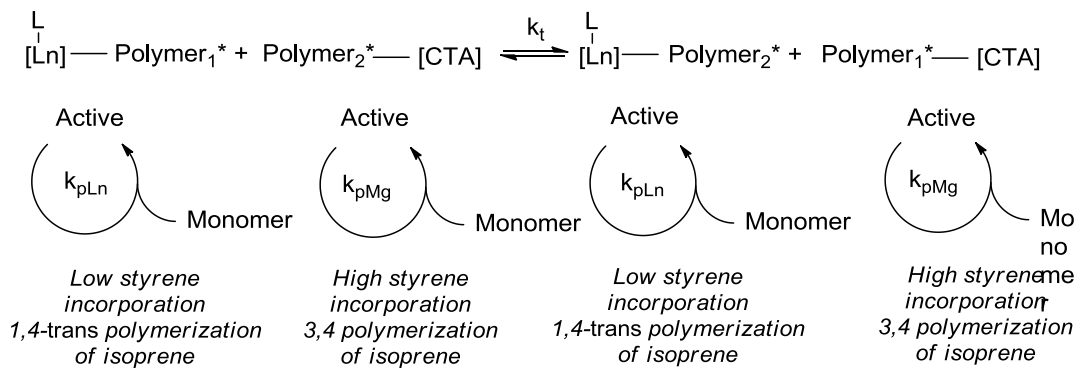


Scheme 29. Chain shuttling-like copolymerization of isoprene and styrene using lanthanide based pre-catalysts and a magnesium dialkyl chain transfer agent able to co-oligomerize the monomers.^{73,88} Polymer* represents a growing polymeric chain, M the metal allowing propagation, L a ligand, and CTA the chain transfer agent. $k_{p\text{Ln}}$, $k_{p\text{Mg}}$ and k_t are the rate constants for propagation on the lanthanide, propagation on magnesium and reversible transfer respectively.

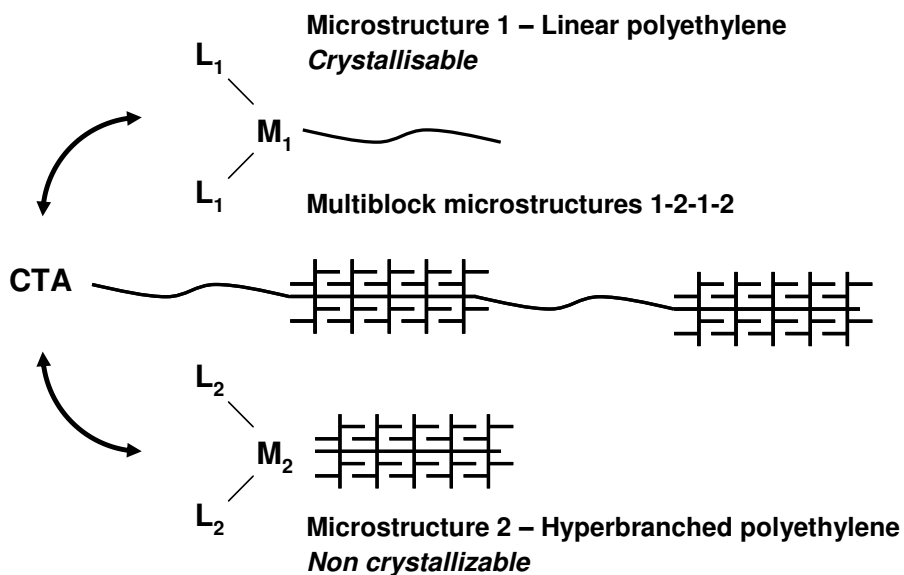


Scheme 30. Ethylene chain shuttling homopolymerization.⁹⁶ M_i represents transition metals allowing propagation, L_i ligands, and CTA the chain transfer or chain shuttling agent




Scheme 31. Isotactic stereoblock polypropylene synthesized via chain shuttling polymerization⁹⁸

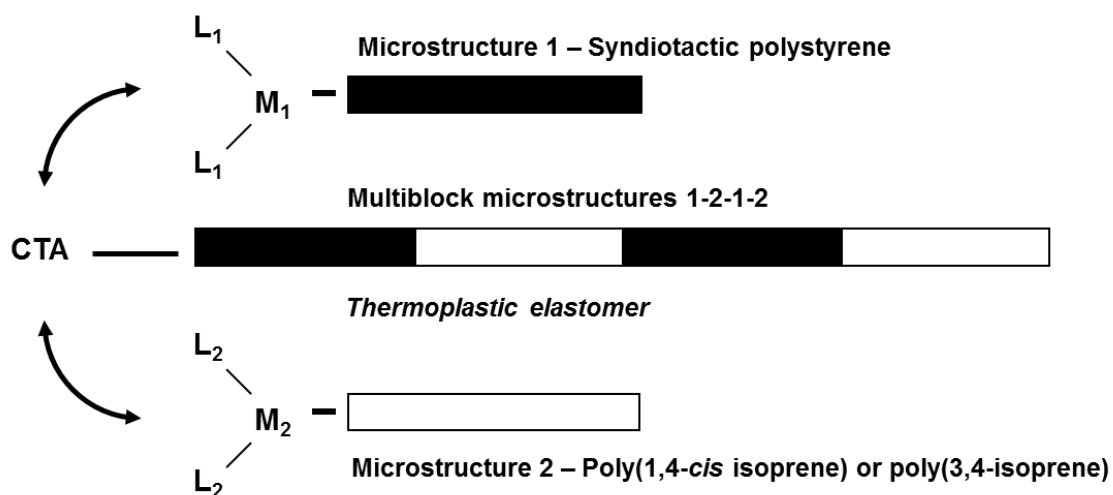

Scheme 32. Isoprene / styrene chain shuttling copolymerization leading to a multiblock microstructure of stereospecific homopolymers.¹⁰⁵ M_i represents the scandium metal allowing propagation, L_i ligands, and CTA the $Al\dot{i}Bu_3$ chain transfer or chain shuttling agent.

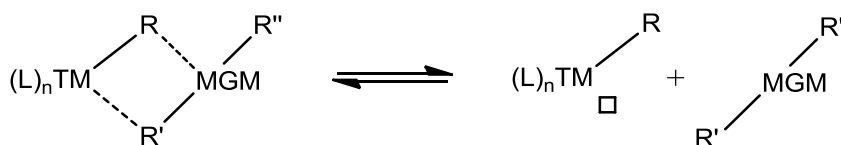

Scheme 33. Bimetallic active species involved in CCTP. TM represents a transition metal, MGM a main group metal, L a ligand and R, R', R'' alkyl groups or macromolecular chains.

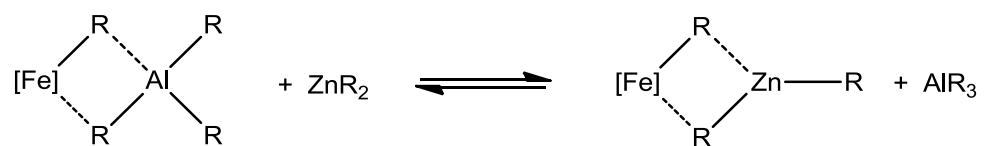

Scheme 34. Equilibrium between bridged bimetallics²

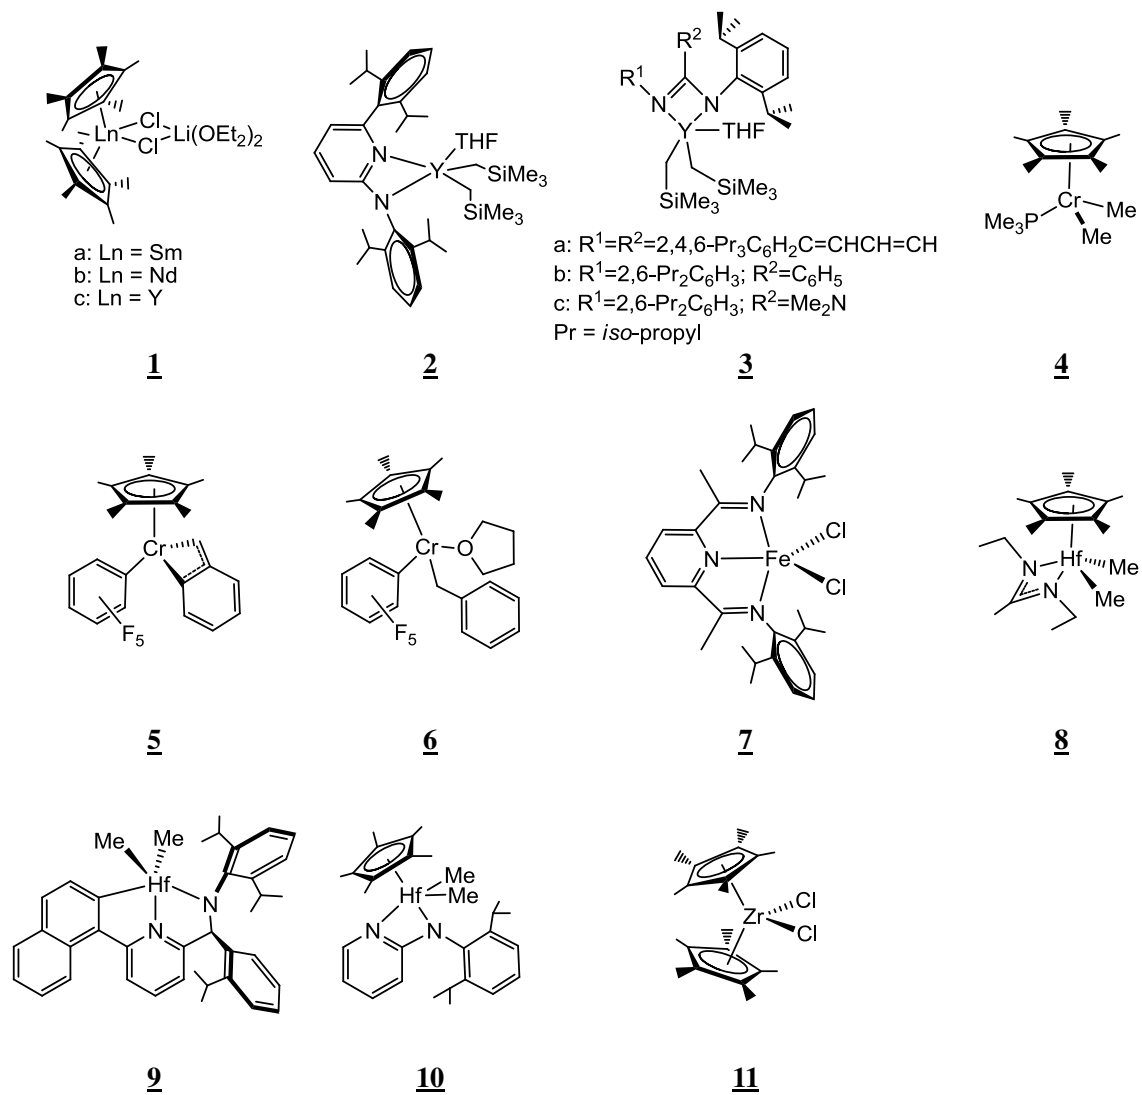


Figure 1. Pre-catalysts used for ethylene CCTP

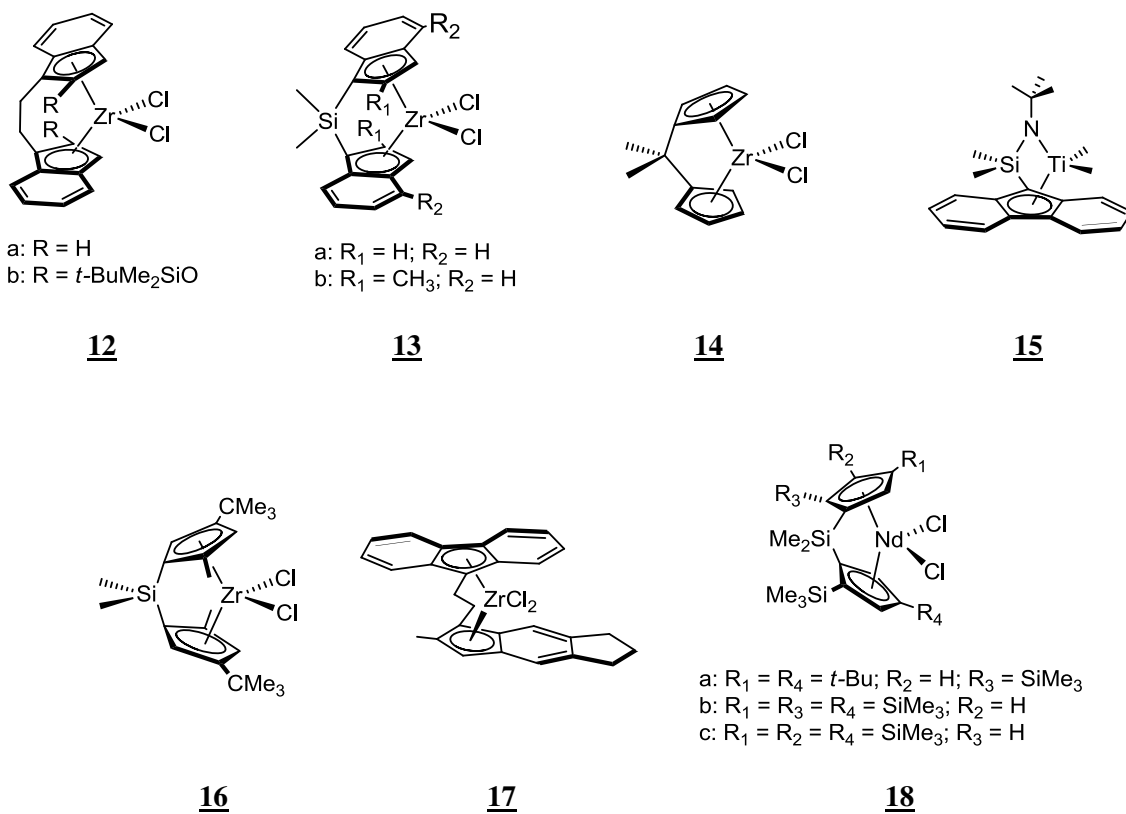


Figure 2. Pre-catalysts used for propylene and higher 1-alkenes CCTP

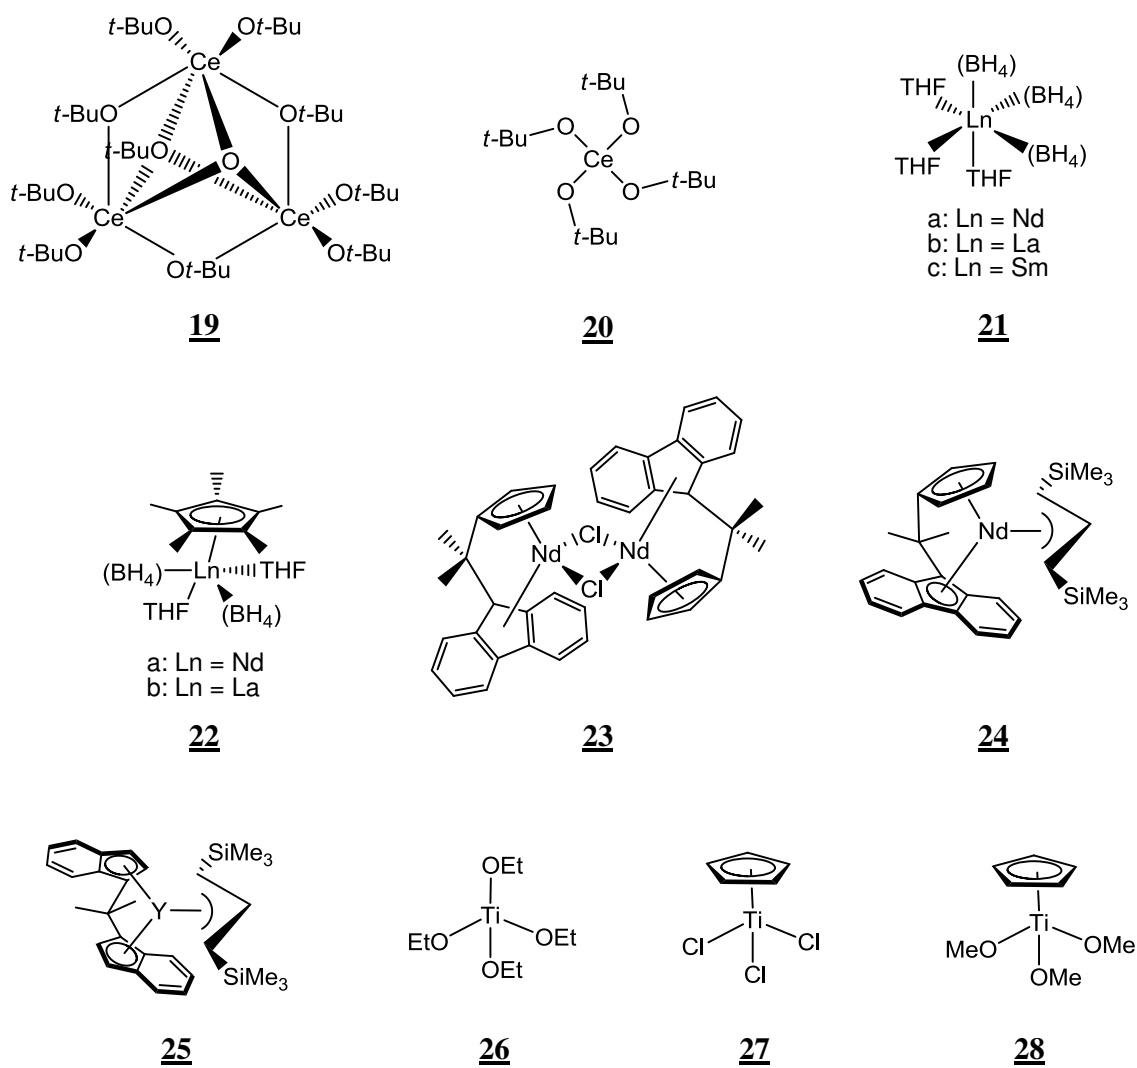


Figure 3. Pre-catalysts used for styrene CCTP



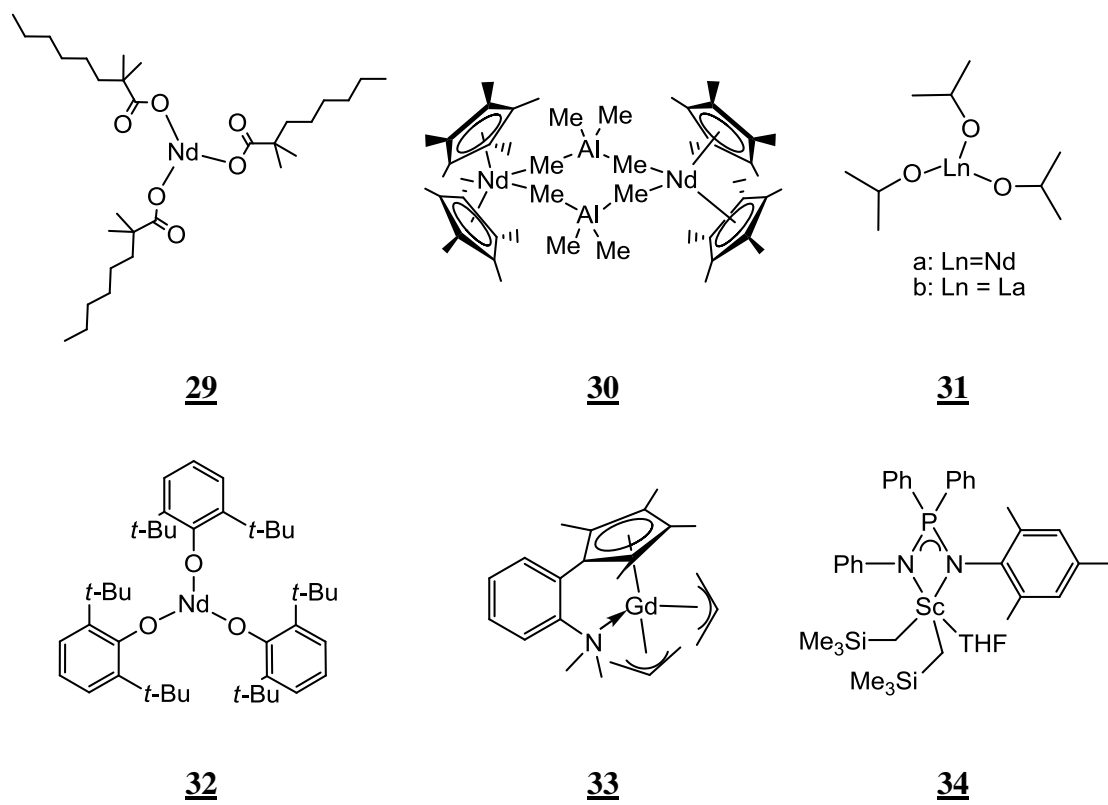


Figure 4. Pre-catalysts used for conjugated dienes CCTP




a: RCp = C₅H₅
 b: RCp = *n*-BuC₅H₄
 c: RCp = 2-MeInd

35




a: R₁ = CH₃; R₂ = C₆H₅
 b: R₁ = *i*-Pr; R₂ = *m*-xylyl


36

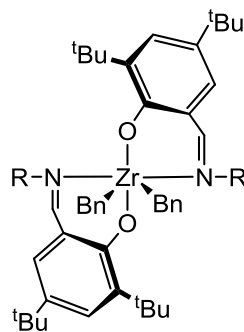

37



38

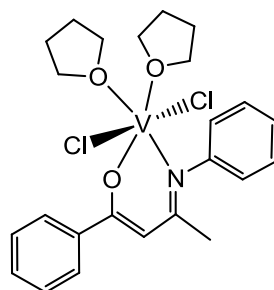

39

Figure 5. Pre-catalysts used for coordinative chain transfer copolymerizations

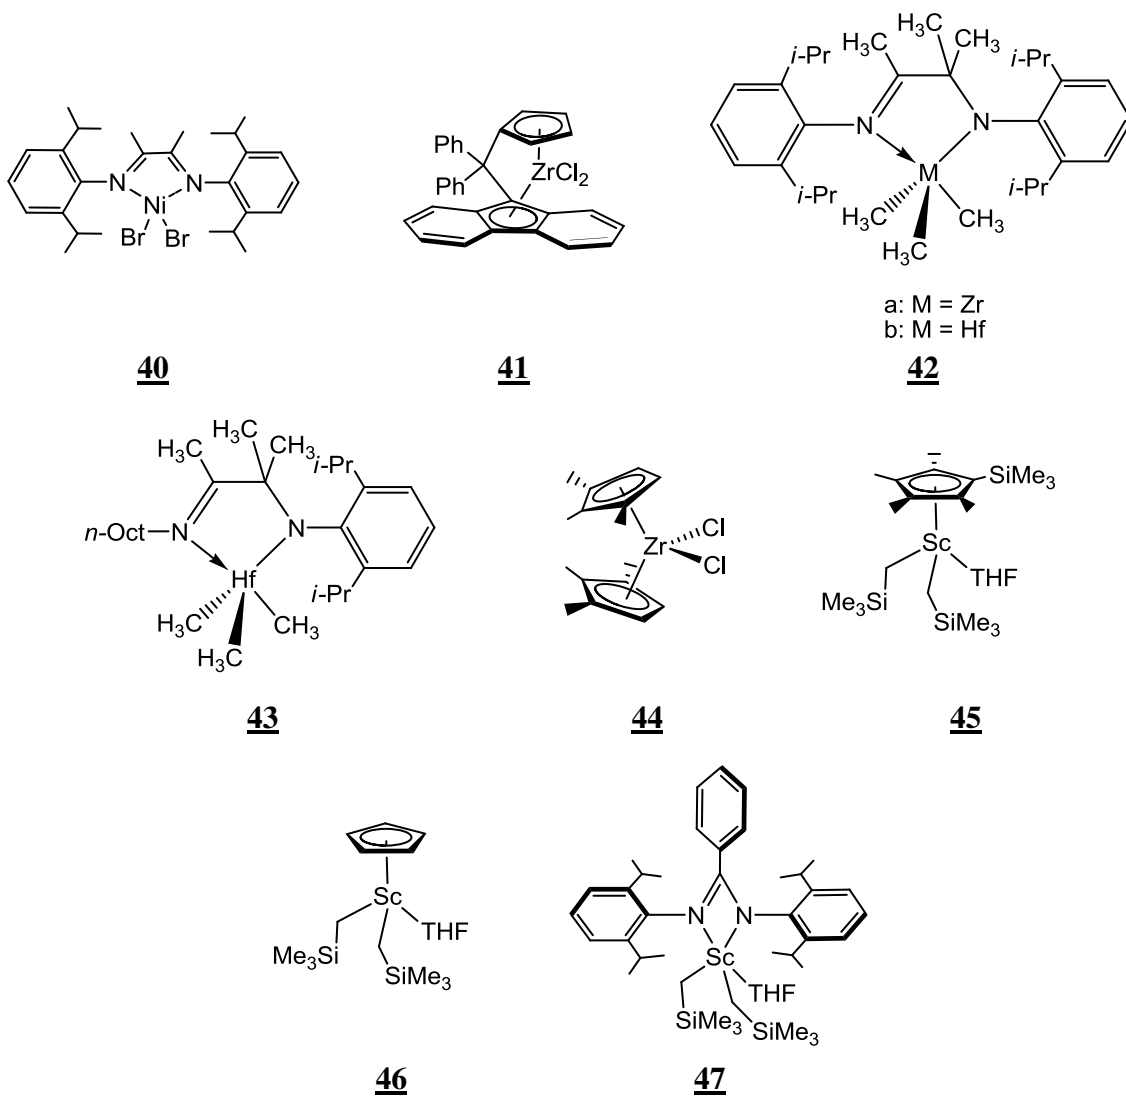


Figure 6. Pre-catalysts used for Chain Shuttling polymerization



Andreia Valente is graduated in Technological Chemistry by the Faculty of Sciences from the University of Lisbon, Portugal. She continued her studies in this institution, where she got her Master degree in Biomedical Inorganic Chemistry. Then, she joined the Unity of Catalysis and Solid State Chemistry in Lille, France, where she obtained her PhD in 2010 in the field of Polymerization Catalysis. She moved back to Portugal where she is now postdoctoral researcher in the field of Polymeric Metal Complexes for biomedical applications.



André Mortreux is currently Emeritus professor at Lille University. His former interest and achievement in homogeneous catalysis came from the discovery of the first homogeneous catalyst for alkyne metathesis in 1974 during his PhD mostly devoted to heterogeneous catalysis with Professor Blanchard in Poitiers. After a postdoctoral position in 1976 with Professor FGA Stone in Bristol, he moved back to Lille University to join his former colleague and friend Professor Petit to create a laboratory entirely devoted to Homogeneous Catalysis. His main research topics were then asymmetric catalysis (synthesis of new chiral ligands from the chiral pool-aminophosphine phosphinite ligands), the use of carbon monoxide and methyl formate as synthons for several carbonylation reactions (hydroformylation, hydroesterification, Fischer Tropsch synthesis ...), dimerization, polymerization and telomerization of dienes (iron, nickel and palladium based catalysts), olefin metathesis (electrochemical synthesis of tungsten metallocarbene species), olefin polymerization on titanium and lanthanide based catalysts, and more recently polyols catalyzed functionalizations within the frame of sustainable chemistry.

He is author and coauthor of more than 300 publications and 34 patents, and has been elected as a member of the Institut Universitaire de France in 2001 (Homogeneous Catalysis chair)

The search for new catalytic reactions has been one of his main interests all along his career: together with the discovery of the first catalyst for disubstituted alkyne metathesis, a further major achievement in this area has been the design of well-defined homogeneous catalyst for the challenging *terminal* alkyne metathesis. Another seminal discovery is the first evidence for a catalytic and reversible “living” transfer reaction between a lanthanidocene based catalyst and magnesium dialkyls during ethylene polymerization. This concept has been developed intensively during the last decade using other catalyst/transfer reagent couples on ethylene as well as on other substrates, and is nowadays mature enough to justify the present review.



Marc Visseaux received the degree of “Docteur de l’Université de Dijon” (Burgundy, France) in 1992, under the supervision of D. Barbier-Baudry. After a position of Maitre de Conférences in Dijon, he obtained his “Habilitation à Diriger des Recherches” in 2000. He was appointed full Professor in 2003 at the University of Science and Technology of Lille (USTL) in the group of A. Mortreux.

Marc Visseaux is since 2005 head of the Polymerization Catalysis Team of UCCS (Unité de Catalyse et Chimie du Solide, UMR 8181 CNRS). During his scientific career, Marc Visseaux moved from fundamental organometallic chemistry of the rare earths at the very beginning, to applications in polymerization catalysis, and finally today to the elaboration of specialty polymers by means of molecular catalysis. His fields of interest include organometallic chemistry of the lanthanides, synthesis of tailor-made coordination rare-earths catalysts, mechanistic investigations including theoretical aspects, Ziegler-Natta type polymerization catalysis and Ring Opening Polymerization with low valent f-element initiators. Marc Visseaux spent a sabbatical period in 2009 as an Invited Professor in Polly L. Arnold’s group in Edinburgh.



Philippe Zinck was graduated and obtained his PhD from the National Institute of Applied Science in Lyon in 1999. He was then awarded an individual Marie Curie Fellowship for a post-doctoral position at the Weizmann Institute of Science. After post-doctoral stays at the Polytechnic Federal School of Lausanne and at the Ecole Supérieure de Physique et Chimie Industrielles de la Ville de Paris, he joined the Unity of Catalysis and Solid State Chemistry, University of Lille in 2004 where he is currently Professor. He is member of the French Chemical Society (North section Board), the French Group of Polymer (North section Board), the Marie Curie Fellowship Association (Advisory Board) and the Editorial Board of the journals *Polymer Science and Reviews in Environmental Science and Biotechnology* as Science Career Editor. His current research interests concerns polymerization catalysis.