

Lawrence Berkeley National Laboratory

Recent Work

Title

Creation of Magnetic Skyrmion Bubble Lattices by Ultrafast Laser in Ultrathin Films.

Permalink

<https://escholarship.org/uc/item/7fg3r0xp>

Journal

Nano letters, 18(11)

ISSN

1530-6984

Authors

Je, Soong-Geun
Vallobra, Pierre
Srivastava, Titiksha
[et al.](#)

Publication Date

2018-11-01

DOI

10.1021/acs.nanolett.8b03653

Peer reviewed

Creation of Magnetic Skyrmion Bubble Lattices by Ultrafast Laser in Ultrathin Films

Soong-Geun Je,^{*,†,§} Pierre Vallobra,[‡] Titiksha Srivastava,[†] Juan-Carlos Rojas-Sánchez,[‡] Thai Ha Pham,[‡] Michel Hehn,[‡] Gregory Malinowski,[‡] Claire Baraduc,[†] Stéphane Auffret,[†] Gilles Gaudin,[†] Stéphane Mangin,[‡] Héléne Beaú,[†] and Olivier Boulle^{*,†}

[†]INAC-SPINTEC, CNRS, CEA, Grenoble INP, Université Grenoble Alpes, 38000 Grenoble, France

[‡]Institut Jean Lamour, CNRS UMR 7198, Université de Lorraine, Nancy F-54500, France

ABSTRACT: Magnetic skyrmions are topologically non-trivial spin textures which hold great promise as stable information carriers in spintronic devices at the nanoscale. One of the major challenges for developing novel skyrmion-based memory and logic devices is fast and controlled creation of magnetic skyrmions at ambient conditions. Here we demonstrate controlled generation of skyrmion bubbles and skyrmion bubble lattices from a ferromagnetic state in sputtered ultrathin

magnetic films at room temperature by a single ultrafast (35 fs) laser pulse. The skyrmion bubble density increases with the


laser fluence, and it finally becomes saturated, forming disordered hexagonal lattices. Moreover, we present that the

skyrmion bubble lattice configuration

leads to enhanced topological stability as compared to isolated skyrmions, suggesting its promising use in data storage. Our

findings shed light on the optical approach to the skyrmion bubble lattice in commonly accessible materials, paving the road toward the emerging skyrmion-based memory and synaptic devices.

KEYWORDS: *Magnetic skyrmion, magnetic skyrmion bubble, ultrafast laser, skyrmion lattice, writing skyrmion*

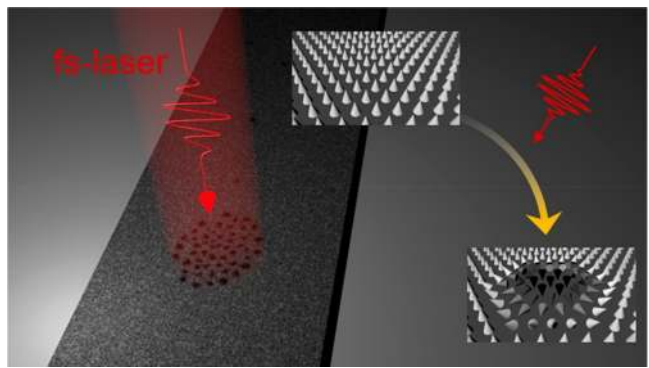

Ultrathin magnetic films have been the subject of intense research for data storage applications such as domain-wall (DW) racetrack memory¹ and magnetic random access memory.^{2,3} Recently, considerable attention has been given to ultrathin multilayers composed of heavy metal (HM) and/or oxide layers in contact with ultrathin 3d transition metals (TM). In this system with perpendicular magnetic anisotropy (PMA), the strong spin-orbit coupling and the structural inversion asymmetry are found to lead to unexpected rich physics such as the spin-orbit torque (SOT)⁴⁻⁷ and the interfacial Dzyaloshinskii-Moriya interaction (DMI).⁸⁻¹⁴ These phenomena immediately became key ingredients for the ultrathin film-based spintronic devices, including efficient current-induced manipulation of magnetization as well as

fascinating nontrivial and noncollinear magnetization structures.⁹⁻¹⁹ One of the most prominent examples, promoted by both the SOT and DMI, is magnetic skyrmions in ultrathin magnetic materials²⁰⁻²³ that possess rich physical and topological properties^{24,25} and prospects of applications.^{26,27}

Skyrmions were first observed in bulk B20 chiral magnets at low temperature²⁸⁻³¹ where Bloch-like skyrmions are stabilized by the DMI^{32,33} due to the noncentrosymmetric crystal structure. Later, they were found in epitaxial ultrathin films at low temperature³⁴⁻³⁶ and more recently at room temperature

in sputtered HM/TM ultrathin films.^{20–23,38–40} In these ultrathin films, the interfacial DMI,³⁷ which arises from the asymmetric interfaces, leads to Néel skyrmions with fixed chirality.²⁰ It was recently shown that these chiral Néel skyrmions can efficiently be driven by electric currents using the SOT.^{21,23,41–46} This has suggested novel concepts of memory devices that would combine very high-density data storage, fast access time and low-power consumption by exploiting topologically stable nanometre-scale skyrmions as information carriers.^{27,47} Moreover, skyrmion-based neuro-morphic and stochastic computing schemes^{48,49} have lately been proposed, expanding their use beyond data storage applications.

For such devices, one essential requirement is to achieve low power, fast and controllable writing of skyrmions. To date, various room-temperature skyrmion creation schemes have been reported. With well-tuned material parameters, dc magnetic fields allow the system to reach the skyrmion state by shrinking pre-existing small worm domains,^{38,41} but the contracted skyrmions are generally placed at the strong pinning

sites.⁵⁰ Skyrmion creation schemes using electric currents, accompanied by the SOT,^{23,51,52} thermal assistance^{43,46} and Oersted field,²¹ have been proposed. In the electric current-induced scheme, however, power consumption is generally high, and special geometric setups are required.^{23,51} Moreover, the nucleation currents are generally higher than the driving currents,^{46,51} resulting in crosstalk between writing and driving operations. Electric field-induced manipulation of skyrmions has been demonstrated,⁴⁰ but the operation time can be limited by the RC time constant. Besides, achieving both the sensitive response to the electric field and high thermal stability of skyrmions imposes significant constraints on the choice of materials.

Ultrafast all-optical manipulation of magnetization, observed for a wide range of materials,⁵³⁻⁵⁵ can provide a breakthrough in the fast and efficient writing of skyrmions. So far, it has been

shown that the direction of the magnetization can be set by laser in a helicity-dependent or helicity-independent way.^{56,57} Recently, it was also reported that the ultrafast laser pulses drive domain walls in cooperation with temperature gradient.⁵⁸ All those achievements might point toward the possibility of optical manipulation of skyrmions. Moreover, as laser acts locally, this could be particularly relevant to the skyrmion synapse device⁴⁸ where creating clusters of skyrmions in a specific region of the device is a key for high resolution synaptic weights.

Recently, it was theoretically proposed that local heating using laser excitation would allow the nucleation of magnetic skyrmions and antiskyrmions on a sub-ns time scale.⁵⁹ Experimentally, several works demonstrated the laser-induced nucleation of nontrivial magnetic textures. However, the experiments were carried out in materials exhibiting non-homochiral magnetic textures⁶⁰ or in a bulk material at low temperature,⁶¹ which are not relevant for devices based on skyrmion manipulation. Thus, the demonstration of the optical generation of homochiral magnetic skyrmions at room temperature would be an important milestone toward the manipulation of magnetic skyrmion in memory and logic devices and would open a path for an ultrafast, low energy consuming writing scheme.

Here we report on the ultrafast laser-induced generation of skyrmion bubbles and skyrmion bubble lattices in an ultrathin ferromagnetic layer. An ensemble of skyrmion bubbles is created from a ferromagnetic state by a 35 fs single laser pulse with low fluences. With the increasing laser fluence, the transition from an isolated skyrmion bubble state to a skyrmion bubble lattice state with controllable bubble density is observed. The laser heating-induced skyrmion bubble lattice formation is explained in the framework of the analytic bubble and

bubble lattice models and micromagnetic simulations. We also found that the skyrmion bubble lattices possess enhanced


interfacial DMI is large enough to stabilize chiral bubbles, thus enabling the SOT-induced skyrmion bubble motion.^{23,42,45,62} More detailed study on the DMI in the present structure can be found in ref 62. Magnetic domains are imaged using the magneto-optical Faraday effect, allowing observation during laser illumination (Figure 1a). Parts b–e of Figure 1 show the

Figure 1. (a) Schematic representation of the film structure and the experimental setup. The film is excited by fs laser pulses, and a 680 nm monochromatic LED (light-emitting diode) light is used to image magnetic domains. (b) Evolution of the normalized perpendicular component of the magnetization m_z with respect to the perpendicular field H_z . (c–e) Magnetic domain patterns obtained at the points c, d, and e as marked in Figure 1b.

magnetic hysteresis loop and corresponding domain images taken at the FeCoB thickness of about 9 Å. Bright and dark contrasts correspond to magnetization pointing up (+z) and down (−z), respectively. At zero magnetic field, labyrinthine domains are observed (Figure 1d). The spontaneous formation of periodic up and down domains is explained by the long-range dipolar field that also favors immunity against to the magnetic field perturbations as compared to the isolated skyrmion bubbles, suggesting the promising prospects of skyrmion lattices for data storage. Our results highlight the role of thermal effect in the creation of the skyrmion bubble lattice. It also offers an alternative way of

ultrafast excitation and massive writing of clusters of skyrmions that decouples the writing operation from the skyrmion driving operation in the skyrmion-based shift register and that could be used in the emerging skyrmion-based synaptic devices. For this study, a Ta(30 Å)/Fe₇₂Co₈B₂₀(wedge, 7.5–10.3 Å)/TaO_x(12 Å, naturally oxidized) trilayer film is grown on a glass substrate. This stack structure is chosen because the

the formation of skyrmions and bubbles. We note, however, that the labyrinthine domains never transform into skyrmion bubbles by applying external magnetic fields in the films. The stripe domains pointing antiparallel to the external field just get narrower (Figure 1e) and the film is finally saturated (Figure 1c). This behavior is observed over the whole FeCoB thickness range (7.5–10.3 Å), and thus we will mainly discuss the data obtained for 9 Å thick film unless otherwise mentioned.

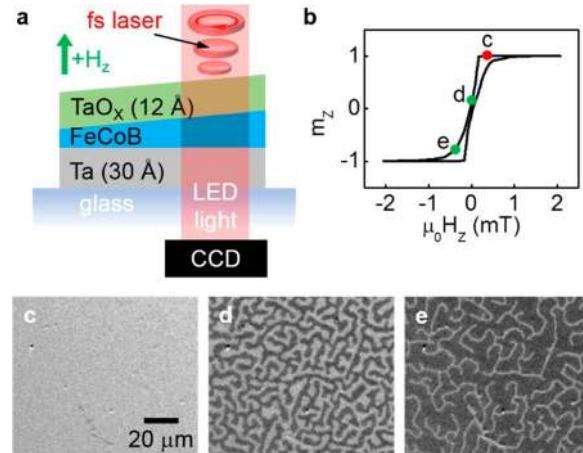

The labyrinthine domain pattern allows us to determine the DMI strength in the present film. In the parallel stripe domain model,⁶³ the labyrinthine domain width L_0 is given by $L_0 = d \pi \exp\left(\frac{\sigma_{DW}}{4} - \frac{1}{4}\right)$ as a function of the film thickness d , the domain wall energy σ_{DW} and the dipolar energy constant $\lambda = \frac{\mu_0}{4} M_S^2$ with the saturation magnetization M_S . In Figure 1d, we determine $L_0 = 1.85 \mu\text{m}$ using a fast Fourier transform. The experimental d (=9 Å) and M_S (=1 MA/m) lead to $\sigma_{DW} = 2.76 \text{ mJ/m}^2$. Note that this value is smaller than $\sqrt{\frac{4 A_{ex} K_{eff}}{4}} = 3.25 \text{ mJ/m}^2$, calculated from the experimental effective anisotropy K_{eff} and the typical exchange stiffness $A_{ex} = 12 \text{ pJ/m}$ ⁶² implying the DMI contribution $(-\pi|D|)$ to σ_D ($= \sqrt{\frac{4 A_{ex} K_{eff}}{4} - \pi|D|}$). We estimate the DMI energy $D = 0.16 \text{ mJ/m}^2$, in agreement with the reported value.⁶² The stripe width with respect to the external magnetic field also

leads to the same D value, and a micromagnetic simulation with such value of D predicts the DMI-stabilized chiral Néel domain wall in the present film (Supporting Information).

The influence of the laser pulse on the magnetic system is then investigated. First, we prepare a saturated initial state (marked by c in Figure 1b) by saturating the film and reducing the magnetic field down to +0.31 mT to suppress natural nucleation of reversed domains. The initial state is then exposed to a linearly polarized 35 fs single laser pulse with a spatial full-width half-maximum (FWHM) of $\sim 60 \mu\text{m}$. Figure 2a shows the magnetic configuration after the laser excitation.

our film are homochiral Néel walls due to the presence of DMI, the created bubbles are chiral skyrmion bubbles that bear the topological similarity to skyrmions.

To see whether there is laser helicity dependence, such as the all-optical helicity dependent switching,^{53,54} the bubble generation is also tested for circularly polarized lights (right

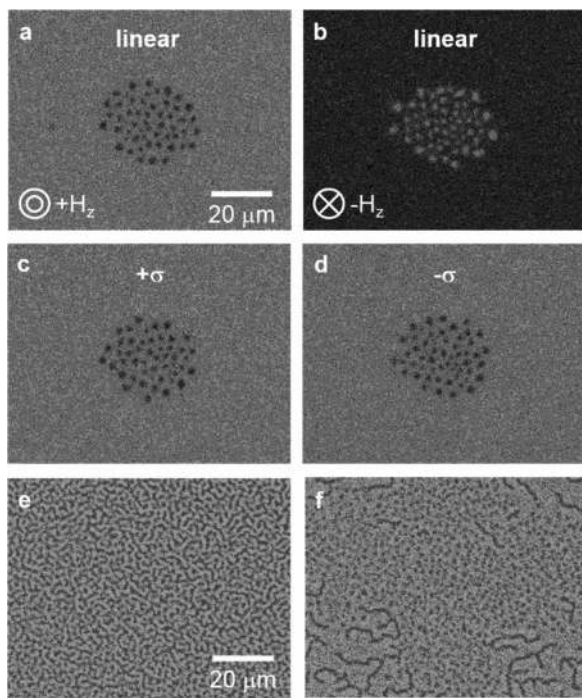


Figure 2. (a) Nucleated bubbles from a saturated state (+z) by a 35 fs single laser pulse with a laser fluence of $1.84 \text{ mJ}/\text{cm}^2$ and linear polarization. (b) Bubble creation from an oppositely saturated state (-z) with linearly polarized light. c-d. Bubble creation by a single laser with right-handed σ^+ polarization (c) and left-handed σ^- polarization (d). The dc magnetic field is +0.31 mT for parts a, c, and d and -0.31 mT for part b. The magnetization of the bubble center is antiparallel to the field. (e, f) Much narrower stripe domains for a thicker FeCoB ($\sim 10 \text{ \AA}$) at zero field (e) and created bubbles smaller than $1 \mu\text{m}$ in diameter under the $\mu_0 H_z$ of +0.7 mT (f). In particular for part f, the laser was swept over the film to increase the number of bubbles for visibility.

Interestingly, bubble domains of $\sim 2.5 \mu\text{m}$ in diameter with the magnetization antiparallel to the magnetic field are created.

Bubbles with opposite magnetization are also generated for the opposite initial state and field as shown in Figure 2b. It is worth noting that the bubble nucleation is achieved by excitation about a thousand times shorter than the recent demonstration using an electric current.⁵¹ As mentioned above, since the domain walls in

polarized σ^+ and left polarized σ^-) as shown in parts c and d of Figure 2. The two circularly polarized lights result in no noticeable difference, implying that the laser-induced skyrmion bubble generation is mainly attributed to laser-induced transient heating. The bubble lattice area is 2 times smaller than the FWHM of the laser. We attribute this to a Gaussian intensity profile of the beam, and this indicates that there is a fluence threshold above which skyrmion bubbles are nucleated. As there is no helicity dependence, we will focus on the case of the linearly polarized light for simplicity.

For a thicker FeCoB (10 Å) region, narrower labyrinthine domains are observed (Figure 2e). Accordingly, smaller chiral bubbles (<1 μm in diameter) are nucleated by laser (Figure 2f). This might indicate that the laser heating-induced method can be applicable to the generation of much smaller skyrmions that are beyond the resolution of the current experimental setup. Moreover, this method can also be used for single skyrmion creation, provided that the laser is much more focused with a micro-sized beam spot⁵⁹ or the laser is a vortex beam.⁶⁴ Hereafter, we focus on the sample region where the larger bubbles are generated for the convenience of image analysis.

Next, we examine the dependence of the laser fluence on the skyrmion bubble generation. Parts a–e of Figure 3 present the ensemble of bubbles generated by the laser for various fluences in the presence of $\mu_0 H_z = +0.28$ mT. To obtain bubbles on a large area, laser pulses with a repetition rate of 5 kHz were swept on the film ± 20 μm in the x and y directions (dashed circle and arrows in Figure 3a). At low laser fluences (Figure 3a,b), individual bubbles are randomly nucleated, resulting in scattered bubbles. As the laser fluence increases, however, the bubble distribution becomes denser and starts to completely cover all the area swept by the laser. The bubbles then finally form a weakly ordered lattice structure. A distinct feature can be found at higher laser fluences (Figure 3c–e). In those cases, the size of the bubbles in the central region, where bubbles are surrounded by bubbles, is smaller than that of bubbles lying on the boundary of the bubble area.

Figure 3f shows the bubble density, the number of bubbles in a unit area, as a function of the laser fluence. With increasing laser fluence, the bubble density increases, and it is finally saturated at higher laser fluence. Note that when exposed to laser pulses of much higher fluences than those required for the saturation shown in Figure 3f, the film properties irreversibly changed, implying the link between the onset of densely packed bubbles and the significant heating effect.

The above observations can be understood in the framework of the long-range dipolar

repulsion between bubbles.^{65,66} The increase in the laser fluence leads to the nucleation of an increased number of bubbles on a larger area. As a result, a larger resultant repulsive force is felt by the bubbles in the center of the lattice, leading to larger bubble density and smaller bubble radii. For much more bubbles in the lattice, a saturation occurs as the outermost bubbles have a less and less effect on the bubble in the center.

The bubble lattice is analyzed using Delaunay triangularization³⁸ as exemplarily shown in Figure 3g. The statistics of the nearest neighbor number (N_{NN}) and the angle of Delaunay triangles (θ_{DT}) are plotted in parts h and i of Figure 3, respectively. At low laser fluences, the distributions are broad without distinct peaks. For higher laser fluences, however, the distributions show clear peaks at $N_{NN} = 6$ and $\theta_{DT} = 60^\circ$, indicating that the laser-generated bubbles form a disordered

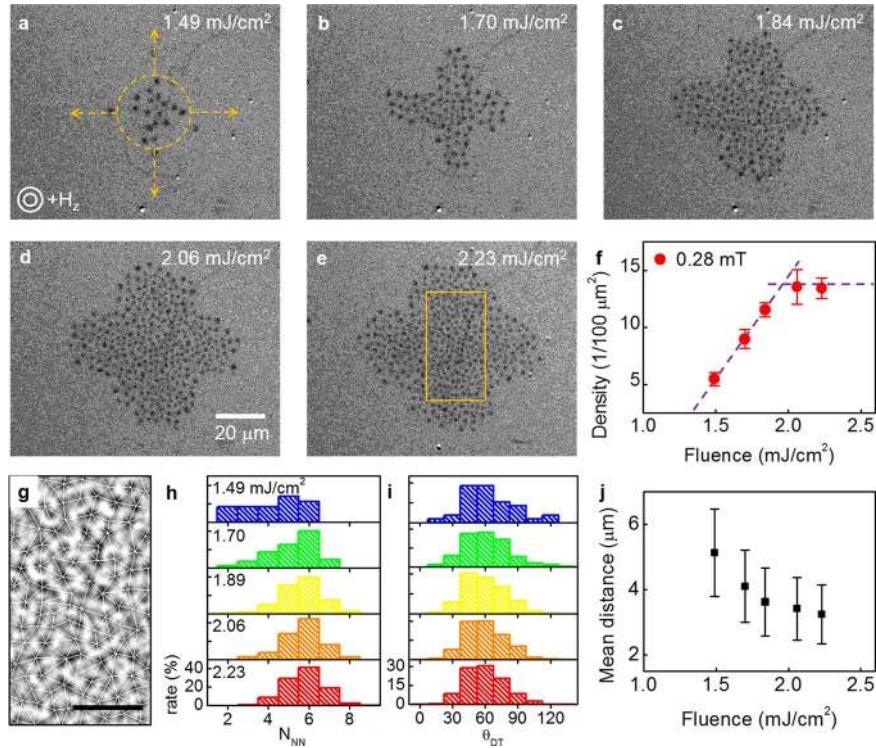


Figure 3. (a–e) Magnetic images of ensemble of bubbles made by sweeping laser with laser fluences of 1.49 (a), 1.70 (b), 1.84 (c), 2.06 (d), and 2.23 mJ/cm² (e) in the presence of $\mu_0 H_z = +0.28$ mT. The orange rectangular marks the same area shown in part g. (f) Bubble density with respect to the laser fluence. We covered the bubble area with square boxes with lateral sizes between 10 and 20 μm and we only counted the bubbles present in the squares. The dashed lines are guides for the eye. (g) Typical example of Delaunay triangularization cropped from the rectangular in part e. The scale bar is 10 μm . A band-pass filtering and mean filtering are used to enhance the magnetic contrast and thus to capture the centers of bubbles using a 2D Gaussian fit. (h, i) Statistics of the nearest neighbor number N_{NN} and the angle of Delaunay triangles θ_{DT} obtained from Delaunay triangularization. Laser fluence increases from the top panel to the bottom panel. (j) Mean distance between nearest bubbles as a function of laser fluence.

hexagonal bubble lattice. The mean distance between nearest neighbors shows a decreasing trend with increasing laser fluence (Figure 3j) that is in line with the dense bubble distribution in the central region.

We then analyze the laser heating-induced skyrmion bubble generation in the framework of the analytic bubble energy model,^{40,63,67,68} which describes the stable bubble domain size and the energy barrier for its occurrence. Slightly different forms of equations in the various works stem from different treatments of magnetostatic energy. However, we note that

they yield the same numerical results in our case (bubble radius \gg film thickness). The energy of an isolated magnetic state is written as

$$E_B = 2\pi R A d \frac{\sigma_{DW}}{M_S} - 4d \ln\left(\frac{R}{\lambda}\right) + Rh$$

where h is the reduced external magnetic field $4\pi H_z / M_S$ and e is Euler's number.⁶³ Using the previously determined σ_{DW} and the experimental values, the bubble energies as a function of R for various magnetic fields h are plotted in Figure 4a. For small h ($< 4.15 \times$

10^{-9} mT), E_B has two local energy

the spontaneous transition to the skyrmion bubble state cannot happen. In our case, however, laser heating provides sufficient energy to the system, enhancing the nucleation of the nanoscale skyrmion and, at the same time, enabling them to easily hurdle the energy barrier E_n . In Figure 4a, we estimate E_n to be very high, around 4×10^{-21} J. For the typical laser fluence of 1.4 mJ/cm², the estimate of the energy on a nanoscale spin structure is of the order of 10^{-17} J. This energy is large compared to the nucleation barrier energy and thereby allows bubbles to be reliably nucleated.

The skyrmion bubble lattice nucleation can then be understood as follows: as shown in Movie 1 in the Supporting Information, during laser pulse, heating almost demagnetizes

the saturated area, creating fluctuating tiny domains. Immediately after the laser pulse, bubble domains that overcame the energy barrier E_n stabilize with a radius around R^* . Due to the dipolar interaction, these bubbles repel each other and finally settle down in the quasi-hexagonal lattice formation. The energy of the hexagonal bubble lattice per unit

volume is given by $\frac{4}{3}\pi R^3$

0 and at some R^* where the energy is lower than zero (i.e. a global minimum). As discussed by Schott et al. (1973), a thermally nucleated nanoscale bubble with $R = 0$ needs to grow by overcoming the energy barrier (E_n , the local maximum). If $k_B T$ is comparable to the energy barrier, the bubble state can be achieved by simply applying an external field in materials with well-tuned parameters. On the other hand, if E_n is large compared to $k_B T$,

$$= \frac{4\pi R \lambda}{3} \frac{\sigma_{DW}}{\lambda} - 4d \ln \left(\frac{8R}{d} \frac{h}{e} \right) + 6\pi d \sum_{k=0}^{\infty} S_k \left(\frac{L_B}{L_B} \right)^k$$

where the last term accounts for the dipolar energy from neighboring bubbles with the coefficient S_k , which diminishes with increasing k , and L_B is the distance between neighboring bubble centers. By assuming that we have sufficient number of

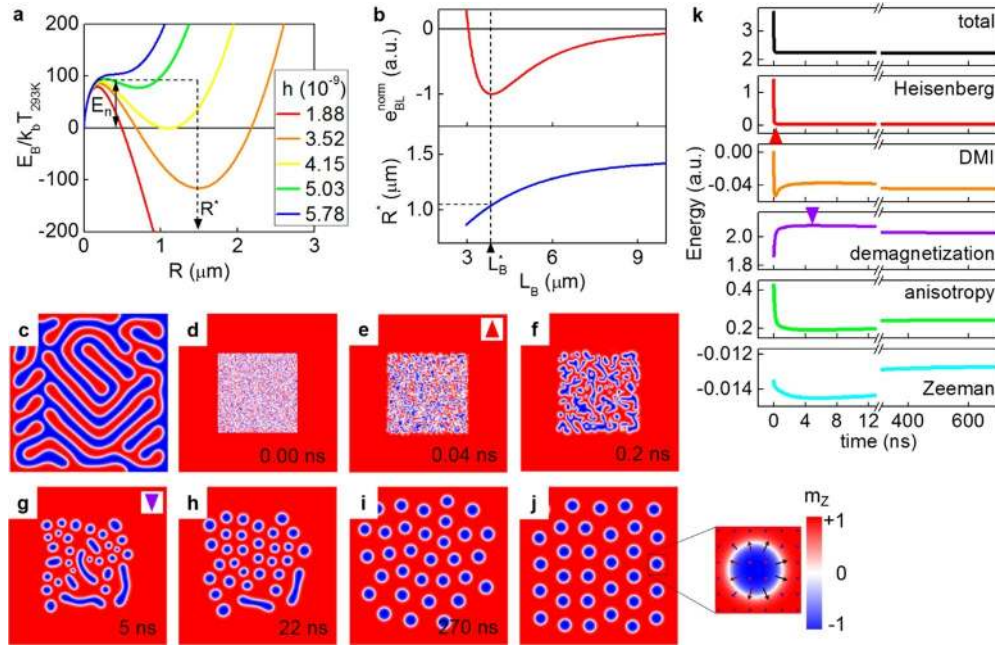


Figure 4. (a) Free energy of the isolated bubble as a function of the bubble radius R . E_n stands for the energy barrier for nucleation of the microsize bubble. (b) Normalized free energy of a hexagonal bubble lattice as a function of the bubble spacing L_B (upper panel) and the radius of bubbles (lower panel) which minimizes the bubble lattice energy for a given L_B . The calculation is performed for $\mu_0 H_z = +0.28$ mT. Dashed vertical line represents the minimum energy point of the bubble lattice, resulting in the saturation of the bubble density in Figure 3f. (c) A labyrinthine domain pattern obtained using a micromagnetic simulation at zero field. (d–j) Generation process of the skyrmion lattice. The simulation area is $2 \mu\text{m} \times 2 \mu\text{m}$ and a randomly oriented magnetization state is embedded in the central area of $1 \mu\text{m} \times 1 \mu\text{m}$ as an initial magnetization state (d). The simulation is performed in the presence of a magnetic field of +5 mT. The images show domain morphology with respect to the simulation time. Inset of part j details a single skyrmion structure and the lateral size of the image is 240 nm. (k) Time evolution of each energy term. The red triangle (purple triangle) corresponds to part e (part g).

bubbles to build a hexagonal lattice, the minimum of e_{BL} and the corresponding R^* with respect to L_B are plotted in Figure 4b. There exists a global minimum point at L_B^* , implying that

having the bubble spacing below L_B^* is not preferred. Since L_B^2

is inversely proportional to the bubble density, the existence of L_B^* explains the saturation of the bubble density in Figure 3f. Moreover, the smaller R^* ($\sim 1.1 \mu\text{m}$) than that of the single bubble case ($R^* = 1.4 \mu\text{m}$ in Figure 4a, $h = 3.52 \times 10^{-9}$) agrees

with the observation that the size of the bubbles become smaller in the central area with increasing the number of bubbles.

To better understand the stabilization of the skyrmion bubble lattice, we carried out micromagnetic simulations.^{69,70} Although atomistic spin dynamics or the three-temperature model would be needed to describe the laser-induced demagnetization and the dynamics just after the laser pulse on the ps time scale,^{71,72} micromagnetic simulation allows one to capture most of the physics of the domain formation after the laser-induced demagnetization on a longer time scale. Besides, it should be noted that, since the micromagnetic simulations on the experimental length scales require an enormous computational time, we performed

the simulations with magnetic parameters yielding smaller skyrmions in a small simulation area ($2 \times 2 \mu\text{m}^2$) and a larger damping constant than the experimental value in a similar magnetic system,⁷³ thus providing qualitative understanding. The parameter set for smaller skyrmions (see Methods) produces the labyrinthine domain pattern at remanence (Figure 4c). Parts d–j of Figure 4 show the time evolution of the domain morphology. To mimic the laser heating area, the initial state (Figure 4d) was prepared by relaxing the uniform magnetization state in the

presence of randomly fluctuating fields in the central area (see [Methods](#)). The time evolution of individual energy terms is also investigated as shown in [Figure 4k](#).

The energy terms ([Figure 4k](#)) with respect to simulation time t exhibit remarkable features. First, the total energy very quickly decreases in a very short time scale ($t < 0.04$ ns, red triangle in [Figure 4k](#)). The decrease is mainly due to the rapid decrease in the Heisenberg exchange energy, resulting in small up and down magnetization regions connected by in-plane magnetized regions. The presence of in-plane magnetized regions (encoded by white in [Figure 4d,e](#)), which can also be deduced from the high anisotropy energy level ([Figure 4k](#)), might imply the coplanar and noncollinear in-plane spin configuration that is crucial for the topological charge transition.⁷⁴ On this time scale, the chirality does not clearly appear in the domain morphology. However, soon after, domain walls possess the chiral nature around 0.2 ns ([Figure 4f](#)), at which the DMI energy also shows a dip. After the rapid drop in the exchange energies, the uniaxial anisotropy plays a role and creates well-defined perpendicular domains (0.04 ns $< t < 5$ ns, [Figure 4g](#) and purple triangle in [Figure 4k](#)), and consequently the demagnetization energy increases due to the reduced amount of in-plane magnetization components. After the domain morphology is clearly established in the central area, the demagnetization energy dominantly reduces the total energy by the repulsion⁶⁶ between skyrmions ([Figure 4h,i](#)) and they are finally arranged in a hexagonal skyrmion lattice ([Figure 4j](#)).

In real materials, however, the formation of a hexagonal bubble lattice can be impeded by the presence of micro- structural disorders, thereby leading to the disordered

hexagonal lattice. To examine how the repulsive interaction works in real materials, we have measured the evolution of skyrmion bubble positions perturbed by laser in a disordered lattice. Parts a–h of Figure 5 show the sequence of images after

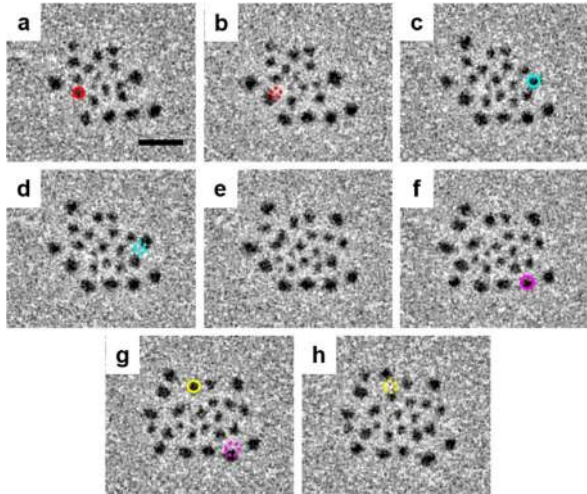


Figure 5. (a–h) Sequence of images taken after every single laser pulse. The circles with a dashed line indicate their previous positions labeled as circles with a solid line. Bubbles labeled with red, cyan, and pink circles are pushed out from the central area while the yellow bubble is divided into two which repel each other. The applied field $\mu_0 H_z$ is $+0.28$ mT. The scale bar is $10 \mu\text{m}$.

every single laser pulse. The laser fluence is adjusted to minimize the bubble creation and thus allows us to track the single bubble behaviors. Bubbles are sometimes pushed out of the central area (red, cyan and pink circles) or are divided into two which repel each other while keeping apart from neighboring bubbles (yellow circles). The motions after each laser pulse can be explained by the depinning and the dipolar fields: bubbles are initially located at pinning sites which might act as local energy minima at the same time. Once a bubble is depinned by laser heating, then the repulsive dipolar forces from other bubbles push out the depinned bubble. For much higher laser fluence, more enhanced cooperation between the nucleation process and the repulsive process can drive the bubbles to form the disordered hexagonal lattice structure more easily (the process is clearly shown in Movie 2 in the Supporting Information).

As the skyrmion bubbles in a lattice closely interact with each other, their response to an external magnetic perturbation can be different from that of a single bubble. To verify this, we first prepared a bubble lattice by sweeping the laser (Figure 6a), and the magnetic field is then turned off (Figure 6b). Interestingly, the initial closely packed bubbles hold their circular morphology and the lattice pattern while new stripe domains grow outside the lattice and cover the external area (Figure 6b). When a reversed field is applied, the bubbles expand,

but their expansion is limited by the adjacent bubbles, constructing a Voronoi-like network (Figure 6c) which originates from the topological prevention of annihilation of paired Néel domain walls.⁷⁵ On the other hand, initially less packed bubbles (Figure 6d) elongate or transform into stripe domains at zero field (Figure 6e). When the field is reversed, the number of isolated domains, which carry the topology of their initial bubble states, decreases (Figure 6f). This fact implies that the bubble lattice protects bubbles against

advantageous for preventing information loss in the outlook of memory and logic devices.

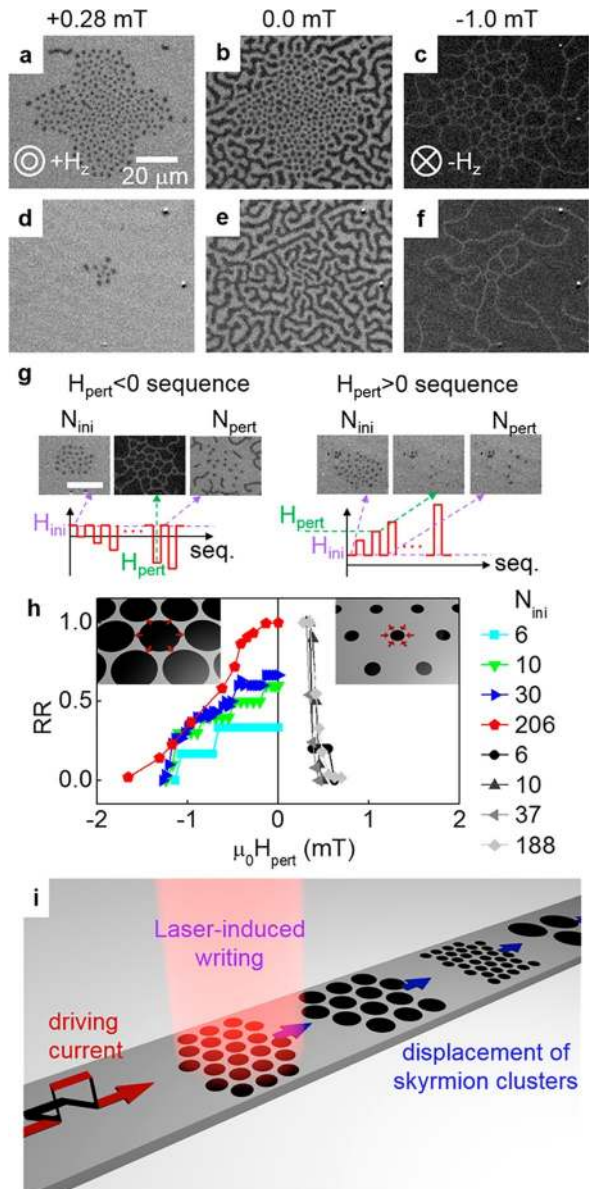


Figure 6. (a–c) Change of magnetic domain morphology of a bubble lattice with respect to $\mu_0 H_z$. Initially, the bubble lattice is generated by laser pulses in the presence of $\mu_0 H_z$ of +0.28 mT (a). Applied magnetic fields for parts b and c) are 0 and -1 mT, respectively. (d–f) Change of magnetic domain morphology of sparsely distributed bubbles with respect to $\mu_0 H_z$. The magnetic fields for parts d–f are +0.28, 0, and -1 mT, respectively. (g) Schematic representation of the sequence of the magnetic perturbation for the negative H_{pert} and positive H_{pert} . The scale bar is 20 μm . (h) Bubble retention ratio RR with respect to H_{pert} . The legend on the right shows N_{ini} . The insets illustrate the experimental situations for the negative (expansion) and positive (shrinking) H_{pert} sequences. (i) Schematic of the skyrmion lattice shift register where information is encoded in the form of ensembles of skyrmions of different densities. The density is controlled by laser fluence. Once a skyrmion cluster is written by laser, clusters including newly written one can be shifted (blue arrows) by the current pulse flowing through the track, resulting in the motion of trains of skyrmion clusters.

perturbative magnetic fields that could be

We systematically study how quickly the number of skyrmion bubbles decays with the external magnetic field perturbation depending on the initial number of bubbles. The magnetic field sequence is schematically shown in Figure 6g. We first create the initial bubbles at the base field $\mu_0 H_{ini}$ of +0.28 mT. The initial number of bubbles N_{ini} is controlled by tuning the laser fluence. The number of the bubbles N_{pert} is counted each time when the field goes back to $\mu_0 H_{ini}$ after each magnetic field perturbation $\mu_0 H_{pert}$. As an indicator of the preservation of the overall topology, we introduce the retention

$$\text{ratio } RR = \frac{N_{pert}}{N_{ini}} \text{ and } RR \text{ is plotted with respect to } \mu_0 H_{pert} \text{ as}$$

shown in Figure 6h.

This plot shows two distinct effects. First, in the positive $\mu_0 H_{pert}$ region where the magnetic field tends to shrink the bubbles, RR exhibits no clear N_{ini} dependence. In this case, the bubble–bubble interaction is suppressed so that the bubbles behave like a single bubble even in a lattice. On the other hand, in the negative $\mu_0 H_{pert}$ region where the magnetic field tends to expand the bubbles, RR exhibits clear N_{ini} dependence. The more bubbles we have, thus having the more packed lattice formation, the more the bubbles survive under the stronger $\mu_0 H_{pert}$, implying the role of the bubble–bubble interaction and thus enhanced topological stability. The faster decrease in RR for the shrinking bubble case may indicate the lack of topological protection of isolated skyrmions due to the discrete nature of materials.^{76,77} However, the twice larger $\mu_0 H_{pert}$ of the expanding case than that of the shrinking case (positive $\mu_0 H_{pert}$) means that the annihilation of the paired homochiral domain walls requires much higher energy (higher stability) than the skyrmion bubble annihilation. These results highlight the distinct topological feature of the closely packed skyrmion bubble lattice in terms of the immunity to the external interference and might provide important insight into storing information in the form of skyrmion lattices of different densities (Figure 6i).

Finally, our results open intriguing prospects for the manipulation of skyrmions in skyrmion-based neuromorphic computing. Huang et al.⁴⁸ recently proposed a synaptic device where the synaptic weight corresponds to the number of skyrmions in a box. Our results show that potentiation and depreciation of the synapse, i.e., increase and decrease of the synaptic weight, can be achieved using respectively ultrafast laser pulses and magnetic fields. Indeed, the potentiation phase can be realized by the increasing skyrmion density (synaptic weight) with the laser fluence (Figure 3f). On the other hand, the depreciation phase can be accomplished using magnetic field pulses as

bubble lattice, which might pave a new way toward the use of the ensemble of skyrmions for memory and logic devices.

Methods. Sample Preparation and Experimental Setup. The Ta(30 Å)/Fe₇₂Co₈B₂₀(wedge)/TaO_x(12 Å, naturally oxidized) film was grown by DC magnetron sputtering. The wedged Fe₇₂Co₈B₂₀ thickness (nominal) ranges from 7.5 to 10.3 Å. The wedged layer is made using off-axis deposition. The film is then annealed at 250 °C for 30 min to enhance PMA. For the laser excitation, we use a Ti: sapphire fs-laser (35 fs duration, 5 kHz repetition, 800 nm wavelength, and a spatial FWHM of ~60 μm). A quarter-wave plate is used to change the helicity of the laser. The magnetic domains are shown in Figure 6h.

In this work, we demonstrated the ultrafast laser heating- induced generation of disordered hexagonal skyrmion bubble lattices in ultrathin magnetic films at room temperature. The skyrmion bubble density was controlled by laser fluence, suggesting the reliable means of manipulating skyrmion lattices. As this creation scheme is straightforward and free from complicated setups, it can be an efficient platform to quickly and widely search for the materials giving skyrmions at the film level. It can also be utilized for the writing operation in the skyrmion-based shift register (Figure 6i) without disturbing the current-induced driving operations. Moreover, the control of the skyrmion density using laser pulses opens a promising outlook for skyrmion-based synaptic devices. While the manipulation of the single skyrmions has been the primary focus of interest, we presented enhanced stability of skyrmion

imaged using a magneto-optic Faraday microscope.

Micromagnetic Simulations. Micromagnetic simulations were performed using Object Oriented Micromagnetic Framework (OOMMF) with DMI package^{69,70} on $2 \times 2 \mu\text{m}^2$ area with a cell size of 5 nm. To produce skyrmions in the micro-sized simulation area, the following parameters are used for qualitative understanding: $D = 1.0 \text{ mJ/m}^2$, a uniaxial anisotropy $K = 6.8 \times 10^5 \text{ J/m}^3$, $M_s = 1 \text{ MA/m}$, $A_{\text{ex}} = 12 \text{ pJ/m}$, $d = 0.9 \text{ nm}$, a damping constant $\alpha = 0.5$, and a dc magnetic field of +5 mT. To mimic the thermally demagnetized region by laser heating, a saturated state is sufficiently relaxed in the presence of randomly fluctuating fields and the dc field with the same simulation parameters except for K ($2.3 \times 10^5 \text{ J/m}^3$) and A_{ex} (4 pJ/m). Then the relaxed magnetization area ($1 \times 1 \mu\text{m}^2$) is embedded in the center of the $2 \times 2 \mu\text{m}^2$ simulation area for the initial magnetization.

AUTHOR INFORMATION

Corresponding Authors

*(S.-G.J.) E-mail: soonggeun.je@gmail.com.

Telephone: +1- 510-486-5783.

*(O.B.) E-mail: olivier.boulle@cea.fr. Telephone:

+33-4-38-

78-21-56.

ORCID

Soong-Geun Je: [0000-0001-9320-0017](https://orcid.org/0000-0001-9320-0017)

Michel Hehn: [0000-0002-4240-5925](https://orcid.org/0000-0002-4240-5925)

Hélène Beá: [0000-0002-3762-4795](https://orcid.org/0000-0002-3762-4795)

Present Address

[§]Center for X-ray Optics, Lawrence Berkeley National Laboratory, Berkeley, California 94720, and Department of Emerging Materials Science, Daegu Gyeongbuk Institute of Science & Technology, Daegu 42988, Republic of Korea

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We appreciate helpful discussions with Dr Liliana D. Buda-Prejbeanu. This work was supported by the ANR-15-CE24-0009 UMAMI and by the ANR-Labcom Project LSTNM, by the Institut Carnot ICEEL for the project Optic-switch and Matelas, and by the French PIA project Lorraine Université d'Excellence, Reference ANR-15-IDEX-04-LUE. Experiments were performed using equipment from the TUBE-Daum funded by FEDER (EU), ANR, Région Grand Est and Metropole Grand Nancy. The authors also acknowledge funding by the French ANR (contract no. ELECSPIN ANR-16-CE24-0018), and by the Nanosciences Foundation (T.S.).

Work at the Advanced Light Source was supported by the U.S. Department of Energy (DE-AC02-05CH11231). S.-G.J thanks Dr Kyoung-Woong Moon for useful discussions. S.-G.J. also acknowledges support from the Future Materials Discovery Program through the NRF funded by the MSIP (2015M3D1A1070465) and from the DGIST R&D program (18-BT-02).

REFERENCES

- (1) Parkin, S. S. P.; Hayashi, M.; Thomas, L. Magnetic domain-wall racetrack memory. *Science* 2008, *320*, 190–194.
- (2) Ikeda, S.; Hayakawa, J.; Lee, Y. M.; Matsukura, F.; Ohno, Y.; Hanyu, T.; et al. Magnetic tunnel junctions for spintronic memories and beyond. *IEEE Trans. Electron Devices* 2007, *54*, 991–1002.
- (3) Mangin, S.; Ravelosona, D.; Katine, J. A.; Carey, M. J.; Terris, B. D.; Fullerton, E. E. Current-induced magnetization reversal in nanopillars with perpendicular anisotropy. *Nat. Mater.* 2006, *5*, 210–215.
- (4) Miron, I. M.; Garello, K.; Gaudin, G.; Zermatten, P.-J.; Costache, M. V.; Auffret, S.; Bandiera, S.; Rodmacq, B.; Schuhl, A.; Gambardella, P. Perpendicular switching of a single ferromagnetic layer induced by in-plane current injection. *Nature* 2011, *476*, 189–193.
- (5) Garello, K.; Miron, I. M.; Avci, C. O.; Freimuth, F.; Mokrousov, Y.; Blügel, S.; Auffret, S.; Boulle, O.; Gaudin, G.; Gambardella, P. Symmetry and magnitude of spin-orbit torques in ferromagnetic heterostructures. *Nat. Nanotechnol.* 2013, *8*, 587–593.
- (6) Liu, L.; Lee, O. J.; Gudmundsen, T. J.; Ralph, D. C.; Buhrman, R. A. Current-Induced Switching of Perpendicularly Magnetized Magnetic Layers Using Spin Torque from the Spin Hall Effect. *Phys. Rev. Lett.* 2012, *109*, 096602.
- (7) Haazen, P. P. J.; Mure, E.; Franken, J. H.; Lavrijsen, R.; Swagten, H. J. M.; Koopmans, B. Domain wall depinning governed by the spin Hall effect. *Nat. Mater.* 2013, *12*, 299–303.
- (8) Bode, M.; Heide, M.; von Bergmann, K.; Ferriani, P.; Heinze, S.; Bihlmayer, G.; Kubetzka, A.; Pietzsch, O.; Blügel, S.; Wiesendanger, R. Chiral magnetic order at surfaces driven by inversion asymmetry.

Nature 2007, *447*, 190–193.

(9) Thiaville, A.; Rohart, S.; Jue, E.; Cros, V.; Fert, A. Dynamics of Dzyaloshinskii domain walls in ultrathin magnetic films. *Europhys. Lett.* 2012, *100*, 57002.

(10) Chen, G.; Zhu, J.; Quesada, A.; Li, J.; N'Diaye, A. T.; Huo, Y.;

Ma, T. P.; Chen, Y.; Kwon, H. Y.; Won, C.; et al. Novel Chiral Magnetic Domain Wall Structure in Fe/Ni/Cu(001) Films. *Phys. Rev. Lett.* 2013, *110*, 177204.

(11) Je, S.-G.; Kim, D.-H.; Yoo, S.-C.; Min, B.-C.; Lee, K.-J.; Choe, S.-B. Asymmetric magnetic domain-wall motion by the Dzyaloshinskii-Moriya interaction. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2013, *88*, 214401.

(12) Pizzini, S.; Vogel, J.; Rohart, S.; Buda-Prejbeanu, L. D.; Jue, E.;

Bouille, O.; Miron, I. M.; Safeer, C. K.; Auffret, S.; Gaudin, G.; et al. Chirality-induced asymmetric magnetic nucleation in Pt/Co/AlO_x ultrathin microstructures. *Phys. Rev. Lett.* 2014, *113*, 047203.

- (13) Tetienne, J.-P.; Hingant, T.; Martínez, L. J.; Rohart, S.; Thiaville, A.; Herrera Diez, L.; Garcia, K.; Adam, J.-P.; Kim, J.-V.; Roch, J.-F.; et al. The nature of domain walls in ultrathin ferromagnets revealed by scanning nanomagnetometry. *Nat. Commun.* 2015, *6*, 6733.
- (14) Emori, S.; Bauer, U.; Ahn, S.-M.; Martinez, E.; Beach, G. S. D. Current-driven dynamics of chiral ferromagnetic domain walls. *Nat. Mater.* 2013, *12*, 611–616.
- (15) Ryu, K.-S.; Thomas, L.; Yang, S.-H.; Parkin, S. Chiral spin torque at magnetic domain walls. *Nat. Nanotechnol.* 2013, *8*, 527–533.
- (16) Yang, S.-H.; Ryu, K.-S.; Parkin, S. Domain-wall velocities of up to 750 m s⁻¹ driven by exchange-coupling torque in synthetic antiferromagnets. *Nat. Nanotechnol.* 2015, *10*, 221–226.
- (17) Garello, K.; Avci, C. O.; Miron, I. M.; Baumgartner, M.; Ghosh, A.; Auffret, S.; Boulle, O.; Gaudin, G.; Gambardella, P. Ultrafast magnetization switching by spin-orbit torques. *Appl. Phys. Lett.* 2014, *105*, 212402.
- (18) Yoshimura, Y.; Kim, K.-J.; Taniguchi, T.; Tono, T.; Ueda, K.; Hiramatsu, R.; Moriyama, T.; Yamada, K.; Nakatani, Y.; Ono, T. Soliton-like magnetic domain wall motion induced by the interfacial Dzyaloshinskii–Moriya interaction. *Nat. Phys.* 2016, *12*, 157–161.
- (19) Bogdanov, A.; Hubert, A. The stability of vortex-like structures in uniaxial ferromagnets. *J. Magn. Magn. Mater.* 1999, *195*, 182–192.
- (20) Boulle, O.; Vogel, J.; Yang, H.; Pizzini, S.; de Souza Chaves, D.; Locatelli, A.; Mentès, T. O.; Sala, A.; Buda-Prejbeanu, L. D.; Klein, O.; et al. Room-temperature chiral magnetic skyrmions in ultrathin magnetic nanostructures. *Nat. Nanotechnol.* 2016, *11*, 449–454.
- (21) Woo, S.; Litzius, K.; Krüger, B.; Im, M.-Y.; Caretta, L.; Richter, K.; Mann, M.; Krone, A.; Reeve, R. M.; Weigand, M.; et al. Observation of room temperature magnetic skyrmions and their current-driven dynamics in ultrathin Co films. *Nat. Mater.* 2016, *15*, 501–506.
- (22) Moreau-Luchaire, C.; Moutafis, C.; Reyren, N.; Sampaio, J.; Vaz, C. A. F.; Van Horne, N.; Bouzehouane, K.; Garcia, K.; Deranlot, C.; Warnicke, P.; et al. Additive interfacial chiral interaction in multilayers for stabilization of small individual skyrmions at room temperature. *Nat. Nanotechnol.* 2016, *11*, 444–448.
- (23) Jiang, W.; Upadhyaya, P.; Zhang, W.; Yu, G.; Jungfleisch, M. B.; Fradin, F. Y.; Pearson, J. E.; Tserkovnyak, Y.; Wang, K. L.; Heinonen, O.; et al. Blowing magnetic skyrmion bubbles. *Science* 2015, *349*, 283.
- (24) Braun, H.-B. Topological effects in nanomagnetism: from superparamagnetism to chiral quantum solitons. *Adv. Phys.* 2012, *61*, 1–116.
- (25) Nagaosa, N.; Tokura, Y. Topological properties and dynamics of magnetic skyrmions. *Nat. Nanotechnol.* 2013, *8*, 899–911.
- (26) Sampaio, J.; Cros, V.; Rohart, S.; Thiaville, A.; Fert, A. Nucleation, stability and current-induced motion of isolated magnetic skyrmions in nanostructures. *Nat. Nanotechnol.* 2013, *8*, 839–844.
- (27) Fert, A.; Cros, V.; Sampaio, J. Skyrmions on the track. *Nat. Nanotechnol.* 2013, *8*, 152–156.
- (28) Mühlbauer, S.; Binz, B.; Jonietz, F.; Pfleiderer, C.; Rosch, A.; Neubauer, A.; Georgii, R.; Böni, P. Skyrmion lattice in a chiral magnet. *Science* 2009, *323*, 915–919.
- (29) Yu, X. Z.; Onose, Y.; Kanazawa, N.; Park, J. H.; Han, J. H.; Matsui, Y.; Nagaosa, N.; Tokura, Y. Real-space observation of a two-dimensional skyrmion crystal. *Nature* 2010, *465*, 901–904.
- (30) Yu, X. Z.; Kanazawa, N.; Onose, Y.; Kimoto, K.; Zhang, W. Z.; Ishiwata, S.; Matsui, Y.; Tokura, Y. Near room-temperature formation of a skyrmion crystal in thin-films of the helimagnet FeGe. *Nat. Mater.* 2011, *10*, 106–109.
- (31) Shibata, K.; Yu, X. Z.; Hara, T.; Morikawa, D.; Kanazawa, N.; Kimoto, K.; Ishiwata, S.; Matsui, Y.; Tokura, Y. Towards control of the size and helicity of skyrmions in helimagnetic alloys by spin-orbit coupling. *Nat. Nanotechnol.* 2013, *8*, 723–728.
- (32) Moriya, T. Anisotropic superexchange interaction and weak Ferromagnetism. *Phys. Rev.* 1960, *120*, 91–98.

- (33) Dzyaloshinskii, I. E. Thermodynamic theory of "Weak" ferromagnetism in antiferromagnetic substances. *J. Exp. Theor. Phys.* 1957, 5, 1259.
- (34) Heinze, S.; von Bergmann, K.; Menzel, M.; Brede, J.; Kubetzka, A.; Wiesendanger, R.; Bihlmayer, G.; Blügel, S. Spontaneous atomic-scale magnetic skyrmion lattice in two dimensions. *Nat. Phys.* 2011, 7, 713–718.
- (35) Romming, N.; Hanneken, C.; Menzel, M.; Bickel, J. E.; Wolter, B.; von Bergmann, K.; Kubetzka, A.; Wiesendanger, R. Writing and deleting single magnetic skyrmions. *Science* 2013, 341, 636–639.
- (36) Romming, N.; Kubetzka, A.; Hanneken, C.; von Bergmann, K.; Wiesendanger, R. Field-dependent size and shape of single magnetic skyrmions. *Phys. Rev. Lett.* 2015, 114, 177203.
- (37) Fert, A. Magnetic and transport properties of metallic multilayers. *Mater. Sci. Forum* 1991, 59-60, 439–480.
- (38) Soumyanarayanan, A.; Raju, M.; Gonzalez Oyarce, A. L.; Tan, A. K. C.; Im, M.-Y.; Petrovic, A. P.; Ho, P.; Khoo, K. H.; Tran, M.; Gan, C. K.; et al. Tunable room temperature magnetic skyrmions in Ir/Fe/Co/Pt multilayers. *Nat. Mater.* 2017, 16, 898–904.
- (39) Pollard, S. D.; Garlow, J. A.; Yu, J.; Wang, Z.; Zhu, Y.; Yang, H. Observation of stable Néel skyrmions in cobalt/palladium multilayers with Lorentz transmission electron microscopy. *Nat. Commun.* 2017, 8, 14761.
- (40) Schott, M.; Bernand-Mantel, A.; Ranno, L.; Pizzini, S.; Vogel, J.; Beá, H.; Baraduc, C.; Auffret, S.; Gaudin, G.; Givord, D. The skyrmion switch: turning magnetic skyrmion bubbles on and off with an electric switch. *Nano Lett.* 2017, 17, 3006–3012.
- (41) Yu, G.; Upadhyaya, P.; Li, X.; Li, W.; Kim, S. K.; Fan, Y.; Wong, K. L.; Tserkovnyak, Y.; Amiri, P. K.; Wang, K. L. Room-temperature creation and spin-orbit torque manipulation of skyrmions in thin films with engineered asymmetry. *Nano Lett.* 2016, 16, 1981–1988.
- (42) Jiang, W.; Zhang, X.; Yu, G.; Zhang, W.; Wang, X.; Jungfleisch, M. B.; Pearson, J. E.; Cheng, X.; Heinonen, O.; Wang, K. L.; et al. Direct observation of the skyrmion Hall effect. *Nat. Phys.* 2017, 13, 162–169.
- (43) Hrabec, A.; Sampaio, J.; Belmeguenai, M.; Gross, I.; Weil, R.; Cherif, S. M.; Stashkevich, A.; Jacques, V.; Thiaville, A.; Rohart, S. Current-induced skyrmion generation and dynamics in symmetric bilayers. *Nat. Commun.* 2017, 8, 15765.
- (44) Litzius, K.; Lemesh, I.; Krüger, B.; Bassirian, P.; Caretta, L.; Richter, K.; Büttner, F.; Sato, K.; Tretiakov, O. A.; Förster, J.; et al. Skyrmion Hall effect revealed by direct time-resolved X-ray microscopy. *Nat. Phys.* 2017, 13, 170–175.
- (45) Yu, G.; Upadhyaya, P.; Shao, Q.; Wu, H.; Yin, G.; Li, X.; He, C.; Jiang, W.; Han, X.; Amiri, P. K.; et al. Room-temperature skyrmion shift device for memory application. *Nano Lett.* 2017, 17, 261–268.
- (46) Legrand, W.; Maccariello, D.; Reyren, N.; Garcia, K.; Moutafis, C.; Moreau-Luchaire, C.; Collin, S.; Bouzheouane, K.; Cros, V.; Fert, A. Room-temperature current-induced generation and motion of sub-100 nm skyrmions. *Nano Lett.* 2017, 17, 2703–2712.
- (47) Tomasello, R.; Martinez, E.; Zivieri, R.; Torres, L.; Carpentieri, M.; Finocchio, G. A strategy for the design of skyrmion racetrack memories. *Sci. Rep.* 2015, 4, 6784.
- (48) Huang, Y.; Kang, W.; Zhang, X.; Zhou, Y.; Zhao, W. Magnetic skyrmion-based synaptic devices. *Nanotechnology* 2017, 28, 08LT02.
- (49) Prychynenko, D.; Sitte, M.; Litzius, K.; Krüger, B.; Bourianoff, G.; Kläui, M.; Sinova, J.; Everschor-Sitte, K. Magnetic skyrmion as a nonlinear resistive element: a potential building block for reservoir computing. *Phys. Rev. Appl.* 2018, 9, 014034.
- (50) Juge, R.; Je, S.-G.; de Souza Chaves, D.; Pizzini, S.; Buda-Prejbeanu, L. D.; Aballe, L.; Foerster, M.; Locatelli, A.; Mentès, T. O.; Sala, A.; et al. Magnetic skyrmions in confined geometries: Effect of the magnetic field and the disorder. *J. Magn. Magn. Mater.* 2018, 455, 3–8.
- (51) Büttner, F.; Lemesh, I.; Schneider, M.; Pfau, B.; Günther, C.; Hessing, P.; Geilhufe, J.; Caretta, J.; Engel, D.; Krüger, B.; et al. Field-free deterministic ultrafast creation of magnetic skyrmions by spin-orbit torques. *Nat. Nanotechnol.* 2017, 12, 1040–1044.

- (52) Woo, S.; Song, K. M.; Zhang, X.; Ezawa, M.; Zhou, Y.; Liu, X.; Weigand, M.; Finizio, S.; Raabe, J.; Park, M.-C.; et al. Deterministic creation and deletion of a single magnetic skyrmion observed by direct time-resolved X-ray microscopy. *Nat. Electron.* 2018, *1*, 288–296.
- (53) Mangin, S.; Gottwald, M.; Lambert, C.-H.; Steil, D.; Uhlir, V.; Pang, L.; Hehn, M.; Alebrand, S.; Cinchetti, M.; Malinowski, G.; et al. Engineered materials for all-optical helicity-dependent magnetic switching. *Nat. Mater.* 2014, *13*, 286–292.
- (54) Lambert, C.-H.; Mangin, S.; Varaprasad, B. S. D. Ch. S.; Takahashi, Y. K.; Hehn, M.; Cinchetti, M.; Malinowski, G.; Hono, K.; Fainman, Y.; Aeschlimann, M.; et al. All-optical control of ferromagnetic thin films and nanostructures. *Science* 2014, *345*, 1337.
- (55) Vallober, P.; Fache, T.; Xu, Y.; Zhang, L.; Malinowski, G.; Hehn, M.; Rojas-Sánchez, J.-C.; Fullerton, E. E.; Mangin, S. Manipulating exchange bias using all-optical helicity-dependent switching. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2017, *96*, 144403.
- (56) El Hadri, M. S.; Pirro, P.; Lambert, C.-H.; Petit-Watelot, S.; Quessab, Y.; Hehn, M.; Moutaigne, F.; Malinowski, G.; Mangin, S. Two types of all-optical magnetization switching mechanisms using femtosecond laser pulses. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2016, *94*, 064412.
- (57) El Hadri, M. S.; Hehn, M.; Pirro, P.; Lambert, C.-H.; Malinowski, G.; Fullerton, E. E.; Mangin, S. Domain size criterion for the observation of all-optical helicity-dependent switching in magnetic thin films. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2016, *94*, 064419.
- (58) Quessab, Y.; Medapalli, R.; El Hadri, M. S.; Hehn, M.; Malinowski, G.; Fullerton, E. E.; Mangin, S. Helicity-dependent all-optical domain wall motion in ferromagnetic thin films. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2018, *97*, 054419.
- (59) Koshibae, W.; Nagaosa, N. Creation of skyrmions and antiskyrmions by local heating. *Nat. Commun.* 2014, *5*, 5148.
- (60) Finazzi, M.; Savoini, M.; Khorsand, A. R.; Tsukamoto, A.; Itoh, A.; Duò, L.; Kirilyuk, A.; Rasing, Th.; Ezawa, M. Laser-induced magnetic nanostructures with tunable topological properties. *Phys. Rev. Lett.* 2013, *110*, 177205.
- (61) Berruto, G.; Madan, I.; Murooka, Y.; Vanacore, G. M.; Pomarico, E.; Rajeswari, J.; Lamb, R.; Huang, P.; Kruchkov, A. J.; Togawa, Y.; et al. Laser-Induced Skyrmion Writing and Erasing in an Ultrafast Cryo-Lorentz Transmission Electron Microscope. *Phys. Rev. Lett.* 2018, *120*, 117201.
- (62) Srivastava, T.; Schott, M.; Juge, R.; Krizáková, V.; Belmeguenai, M.; Roussigne, Y.; Bernard-Mantel, A.; Ranno, L.; Pizzini, S.; Cherif, S.-M.; et al. Large voltage tuning of Dzyaloshinskii-Moriya Interaction: a route towards dynamic control of skyrmion chirality. *Nano Lett.* 2018, *18*, 4871–4877.
- (63) Saratz, N.; Ramsperger, U.; Vindigni, A.; Pescia, D. Irreversibility, reversibility, and thermal equilibrium in domain patterns of Fe films with perpendicular magnetization. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2010, *82*, 184416.
- (64) Fujita, H.; Sato, M. Ultrafast generation of skyrmionic defects with vortex beams: Printing laser profiles on magnets. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2017, *95*, 054421.
- (65) Lin, S. Z.; Reichhardt, C.; Batista, C. D.; Saxena, A. Particle model for skyrmions in metallic chiral magnets: dynamics, pinning, and creep. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2013, *87*, 214419.
- (66) Zhang, X.; Zhao, G. P.; Fangohr, H.; Liu, J. P.; Xia, W. X.; Xia, J.; Morvan, F. J. Skyrmion-skyrmion and skyrmion-edge repulsions in skyrmion-based racetrack memory. *Sci. Rep.* 2015, *5*, 7643.
- (67) Thiele, A. A. The theory of cylindrical magnetic domains. *Bell Syst. Tech. J.* 1969, *48*, 3287.
- (68) Hubert, A.; Schäfer, R. *Magnetic Domains, The Analysis of Magnetic Microstructures*; Hubert, A., Schäfer, R., Eds.; Springer: Berlin, 1998.

(69) Donahue, M. J.; Porter, D. G. *OOMMF User's Guide, Version 1.0 Interagency Report NISTIR 6376*; National Institute of Standards and Technology: Gaithersburg, MD, 1999.

(70) Rohart, S.; Thiaville, A. Skyrmion confinement in ultrathin film nanostructures in the presence of Dzyaloshinskii–Moriya interaction. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2013, *88*, 184422.

(71) Koopmans, B.; Malinowski, G.; Dalla Longa, F.; Steiauf, D.; Fañlle, M.; Roth, T.; Cinchetti, M.; Aeschlimann, M. Explaining the paradoxical diversity of ultrafast laser-induced demagnetization. *Nat. Mater.* 2010, *9*, 259–265.

(72) Cornelissen, T. D.; Córdoba, R.; Koopmans, B. Microscopic model for all optical switching in ferromagnets. *Appl. Phys. Lett.* 2016, *108*, 142405.

(73) Brächer, T.; Fabre, M.; Meyer, T.; Fischer, T.; Auffret, S.; Boulle, O.; Ebels, U.; Pirro, P.; Gaudin, G. Detection of short-waved spin waves in individual microscopic spin-wave waveguides using the inverse spin Hall effect. *Nano Lett.* 2017, *17*, 7234–7241.

(74) Yin, G.; Li, Y.; Kong, L.; Lake, R. K.; Chien, C. L.; Zang, J. Topological charge analysis of ultrafast single skyrmion creation. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2016, *93*, 174403.

(75) Benitez, M. J.; Hrabec, A.; Mihai, A. P.; Moore, T. A.; Burnell, G.; McGrouther, D.; Marrows, C. H.; McVitie, S. Magnetic microscopy and topological stability of homochiral Néel domain walls in a Pt/Co/AlO_x trilayer. *Nat. Commun.* 2015, *6*, 8957.

(76) Rohart, S.; Miltat, J.; Thiaville, A. Path to collapse for an isolated Néel skyrmion. *Phys. Rev. B: Condens. Matter Mater. Phys.* 2016, *93*, 214412.

(77) Büttner, F.; Lemesh, I.; Beach, G. S. D. Theory of isolated magnetic skyrmions: From fundamentals to room temperature applications. *Sci. Rep.* 2018, *8*, 4464.