

# CUTTING TOOL LIFE TESTS OF CERAMIC INSERTS FOR CAR ENGINE SLEEVES

*Robert Čep, Adam Janásek, Branislav Martinický, Marek Sadílek*

Original scientific paper

This article is focused on the experimental determination of tool life tests for indexable ceramic cutting inserts. The set criterion of tool wear was  $V/B_{\text{Bmax}} = 0,6$  mm (in accordance with ISO 3685) or 30 pieces of machined sleeves. After at least one of the mentioned parameters was achieved, the tests were stopped and evaluated. Two types of cutting material by Saint Gobain Advanced Ceramics s.r.o. Company – ZTA 7 NI and D 250 were tested. We monitored their tool life at the same cutting parameters. The experiments were performed on machine tool – CHEMNITZ NILES N22. The machined material was the cast iron 25P mainly used for car engines. Tool wear was monitored on every fifth machined sleeve. Microgeometry was measured after tool wear test on each fifth sleeve. The aim was to determine the arithmetic tolerance of  $Ra$  profile, the greatest height of  $Rz$  profile and the external diameter  $D$ . The measurement was carried out four times; arithmetic average was performed subsequently as it is shown in the tables.

**Keywords:** cutting tool tests, machining, surface roughness, tool wear

## Ispitivanje trajnosti reznog alata keramičkih uložaka za tuljke automobilskih motora

Izvorni znanstveni članak

Ovaj članak je usredotočen na eksperimentalno određivanje trajnosti alata za indeksiranje keramičkih reznih uložaka. Postavljen je kriterij trošenja alata  $V/B_{\text{Bmax}} = 0,6$  mm (sukladno ISO 3685) ili 30 komada obrađenih tuljaka. Kada je postignut barem jedan od ovih parametara, ispitivanje je zaustavljeno i procijenjeno. Ispitivane su dvije vrste reznog materijala uz pomoć tvrtke Saint Gobain Advanced Ceramics s.r.o. – ZTA 7 NI i D 250. Pratili smo njihovu trajnost kod istih parametara obrade. Eksperimenti su izvedeni na alatnom stroju – CHEMNITZ NILES N22. Obradivani materijal bio je lijevano željezo 25P koje se koristi za motore automobila. Trošenje alata praćeno je za svaki peti obrađeni tuljak. Mjerena je mikrogeometrija nakon ispitivanja trošenja alata na svakom petom tuljku. Cilj je bio odrediti aritmetičku toleranciju  $Ra$  profila, najveću visinu  $Rz$  profila i vanjski promjer  $D$ . Mjerenje je provedeno četiri puta, aritmetička sredina je izvedena naknadno i prikazana je u tablicama.

**Ključne riječi:** ispitivanje reznog alata, hrapavost površine, obrada rezanjem, trošenje alata

## 1

### Introduction

#### Uvod

Tool wear tests belong to one of the basic parameters of machining technology. The results of successful application, which were obtained in practice, remarkable increase of the quality of production and indirect affect on the position of the enterprise in the sharp competition [3, 4]. That experimental determination of tool life can provide additional information about cutting process in next tests [5].

Roughness is a sum of surface imperfections with a small distance. These phenomena arise from the production or effect of production effect [6]. Surface defects not assumed as the roughness are: random irregular geometry (lines, crevices, etc.) and defects which arise by material production [2].

## 2

### Experimental part

#### Eksperimentalni dio

#### 2.1

##### Machine tool

##### Alatni stroj

The machine tool CHEMNITZ NILES N22 (Fig. 1) was used for test sample machining. The machine tool has rigid structure and it provides a sufficient clamping condition. Jaws have recessed cone with the same apical angle as the cast iron sleeves.



Figure 1 Machine tool CHEMNITZ NILES N22  
Slika 1. Alatni stroj CHEMNITZ NILES N22

#### 2.2

##### Measuring machines

##### Mjerni strojevi

$Ra$  and  $Rz$  values were evaluated on portable surface roughness tester - Mitutoyo SurfTest SJ-400. A wide range, high-resolution detector and an ultra-straight drive unit provide a class-leading accuracy. Cylinder surface roughness is possible to be evaluated by the skid less measurement and R-surface compensation functions.

An external diameter was determined by SOMET micrometer (ČSN 25 1420; 50÷75 mm).

#### 2.3

##### Machined material

##### Obrađeni materijal

As the machining material were used sleeves for car

engines (Fig. 3), which were supplied by the contracting authority. The class of material was 25P. Due to conical shape of sleeves it was necessary to machine a cylindrical surface and the same diameter. Supposing we had not done it, a constant depth of cut  $a_p$  would not have been maintained during tests.



Figure 2 Portable Surface Roughness Tester Mitutoyo Surftest SJ-400 [1]

Slika 2. Prijenosni mjerač hrapavosti površine Mitutoyo Surftest SJ-400 [1]

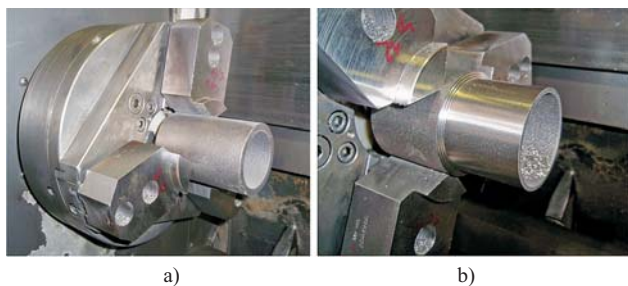


Figure 3 Clamped sleeves: before machining (a) and after machining (b)  
Slika 3. Stegnuti tuljci: prije obrade (a) i nakon obrade (b)

Table 1 Chemical composition of the material  
Tablica 1. Kemijski sastav materijala

C / %	Si / %	Mn / %	P / %	S / %	Ti / %	Cu / %
2,8÷3,3	1,8÷2,5	0,6÷0,8	0,5÷0,8	<0,1	0,03÷0,1	≤0,8

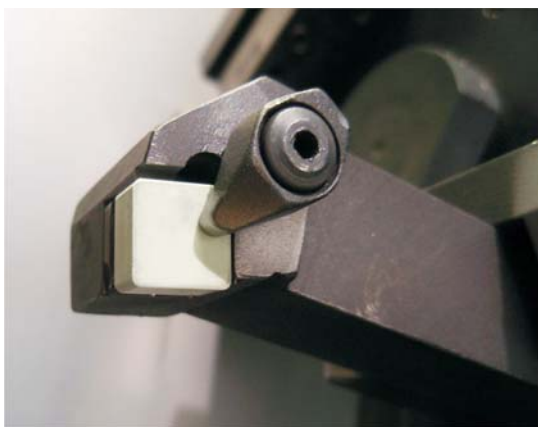


Figure 4 The tool-holder with clamped ceramic cutting insert  
Slika 4. Držać alata s pričvršćenim keramičkim uloškom

## 2.4

### Used tools

#### Korišteni alati

A tool-holder CSSNR 2525 M12-K (Fig. 4) was used in accordance with ISO 3685, with defined by an angle  $\kappa_r = 45^\circ$ . Machining system is shown in (Fig. 5).

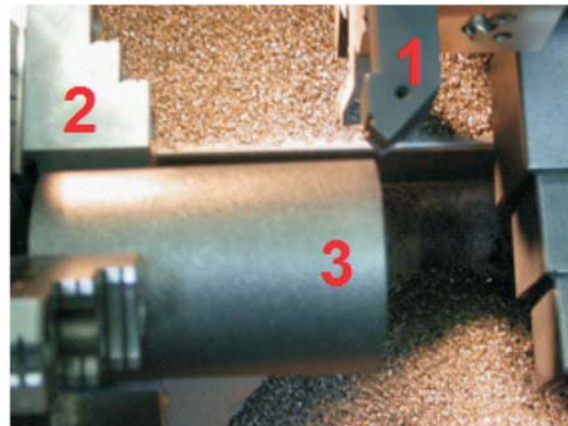


Figure 5 Machining system: 1 - tool-holder; 2 - chuck; 3 - workpiece  
Slika 5. Obradni sustav: 1 - držać alata, 2 - glava, 3 - izradak

## 2.5

### Indexable cutting inserts

#### Rezne pločice

Two types of ceramic cutting inserts were tested in total (the first type – 2 pieces and the second type – 4 pieces). Only one cutting edge was tested on the plate of each type. The cutting plates had the following marks:

- D 250\_1
- ZTA\_7\_NI\_2
- ZTA\_7\_NI\_1
- D 250\_2
- D 250\_3
- D 250\_4

## 2.6

### Cutting parameters

#### Parametri rezanja

Cutting parameters were selected on the basis of experience and consultations of the research team with a contracting authority. The aim was to get as near as possible to real operation conditions.

- cutting speed  $v_c = 500$  m/min
- feed  $f = 0,4$  mm
- cutting depth  $a_p = 2$  mm
- number of chips per one sleeve: 4
- machining length: 1<sup>st</sup> chip 61 mm, 2<sup>nd</sup> chip 60 mm, 3<sup>rd</sup> chip 59 mm, 4<sup>th</sup> chip 58 mm
- total machining length: 238 mm
- dry machining.

## 3

### Experiments' evaluation

#### Procjena eksperimenata

The contracting authority supplied a semi-product of

machined materials and two kinds of ceramic cutting inserts. The criterion of tool wear was chosen  $VB_{Bmax} = 0,6$  mm. If the 30<sup>th</sup> sleeve was machined and the critical value of tool wear was not reached, the tests were stopped. The tool life was determined as follows:

$$T = t \cdot p \tag{1}$$

$$t = \frac{4 \cdot l}{n \cdot f}, \tag{2}$$

where:

- $T$  – tool life, min
- $t$  – machining time, min
- $p$  – number of machined pieces, –
- $l$  – machining length, mm
- $n$  – spindle speed, 1/min
- $f$  – feed, mm.

Microgeometry was measured after the tool wear test - on each 5<sup>th</sup>, 10<sup>th</sup>, 15<sup>th</sup>, 20<sup>th</sup>, 25<sup>th</sup> and 30<sup>th</sup> machined sleeve. The aim of this experiment was to determine the arithmetic tolerance of  $Ra$  profile, the greatest height of  $Rz$  profile and the external diameter  $D$ .

Arithmetic tolerance of  $Ra$  profile, the greatest height of  $Rz$  profile and the external diameter  $D$  are shown in the following tables. Measurements were evaluated four times – as shown in (Fig. 6). The arithmetic average was calculated from these measurements.

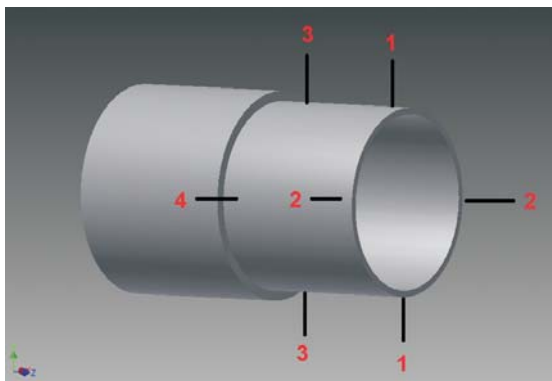


Figure 6 Measured surface – machined insert  
Slika 6. Mjerena površina – obrađen uložak

### 3.1 Tool life and tool wear – individual cutting inserts Vijek i trošenje alata – pojedinačni rezni ulošci

The number of machined pieces by individual ceramic cutting inserts is shown in the following graph (Fig. 7). D 250 series of cutting inserts machined the maximum number of 30 pieces except for D 250\_1 insert. The D 250\_1 insert probably reached this maximum as well. There was a crack of sleeve (at machining the 27<sup>th</sup> sleeve) and it resulted in cutting edge destruction. ZTA\_7\_NI inserts reached the criteria of tool wear at 26<sup>th</sup>, respectively at 15<sup>th</sup> machined sleeves. Fig. 8 shows the tool life of plates calculated according to formula (1) and (2) in minutes.

Table 2 The number of machined pieces for individual cutting inserts  
Tablica 2. Broj obrađenih komada za pojedinačne rezne uloške

	D 250_1	ZTA_7_NI_2	ZTA_7_NI_1	D 250_2	D 250_3	D 250_4
Machined pieces	27	26	15	30	30	30

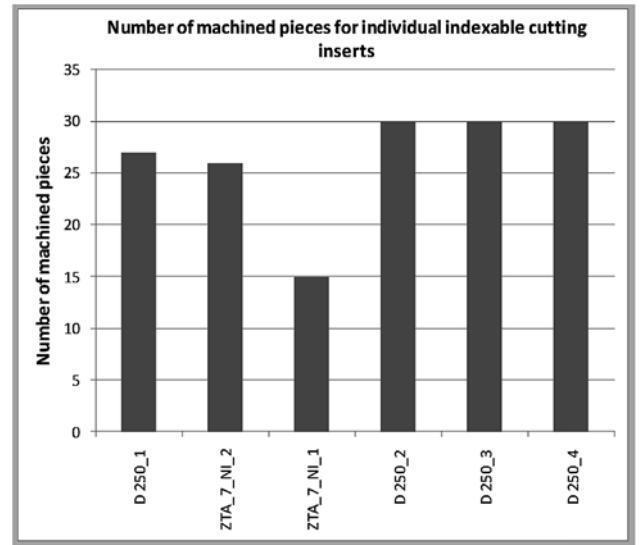


Figure 7 The number of machined pieces for individual indexable cutting inserts

Slika 7. Broj obrađenih komada za indeksirane rezne uloške

Table 3 Tool life for individual indexable cutting inserts  
Tablica 3. Postojanost alata za pojedine rezne pločice

	D 250_1	ZTA_7_NI_2	ZTA_7_NI_1	D 250_2	D 250_3	D 250_4
Tool life, min	8,03	7,74	4,46	8,93	8,93	8,93



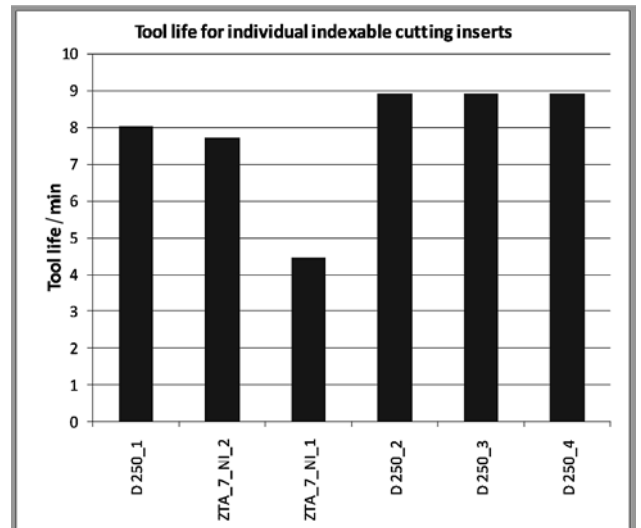


Figure 8 Tool life for individual indexable cutting inserts  
Slika 8. Vijek alata za indeksirane rezne uloške




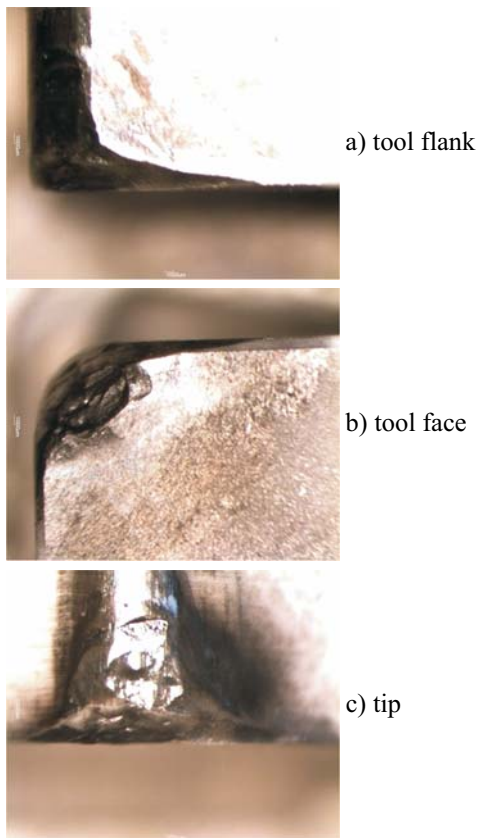


**Figure 9** Tool wear – indexable cutting insert type D 250\_1  
**Slika 9.** Trošenje alata – rezna pločica tipa D 250\_1

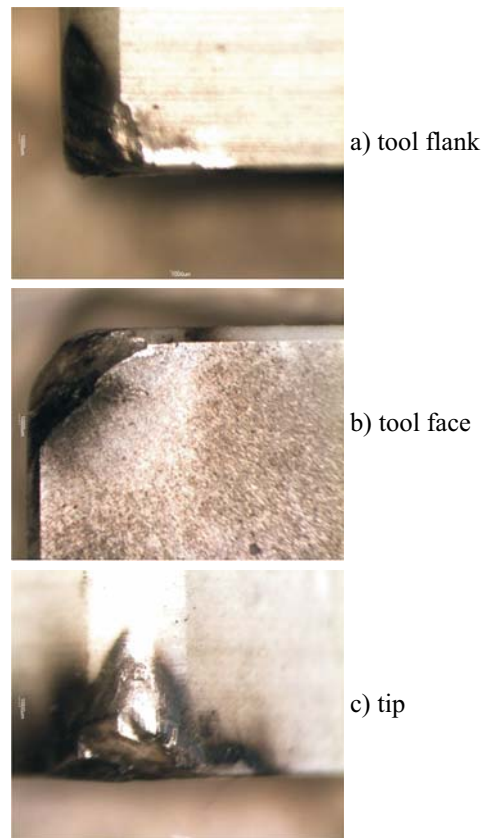

**Figure 11** Tool wear – indexable cutting insert type ZTA\_7\_NI\_1  
**Slika 11.** Trošenje alata – rezna pločica tipa ZTA\_7\_NI\_1

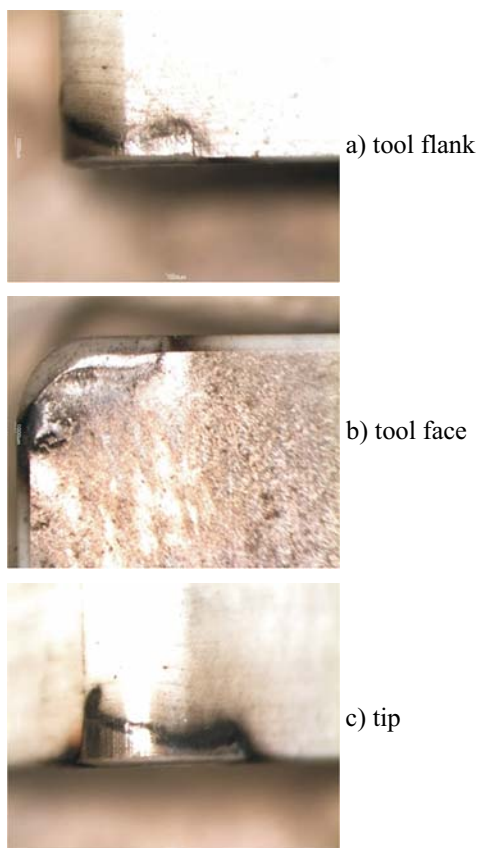

**Figure 10** Tool wear – indexable cutting insert type ZTA\_7\_NI\_2  
**Slika 10.** Trošenje alata – rezna pločica tipa ZTA\_7\_NI\_2

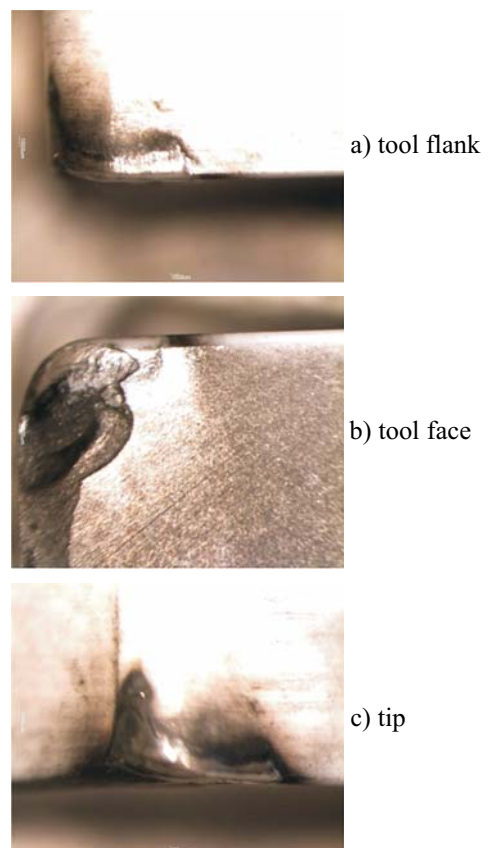

**Figure 12** Tool wear – indexable cutting insert type D 250\_2  
**Slika 12.** Trošenje alata – rezna pločica tipa D 250\_2

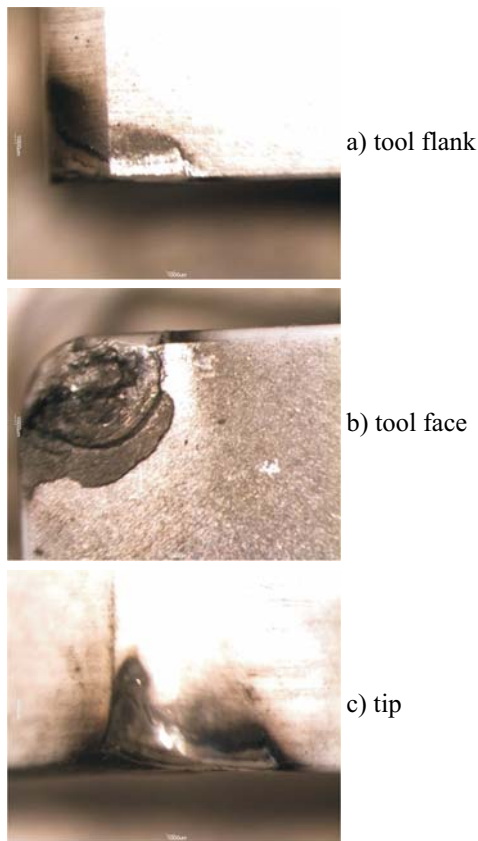


Figure 13 Tool wear – indexable cutting insert type D 250\_3  
Slika 13. Trošenje alata – rezna pločica tipa D 250\_3

Comment (Fig. 9):

- Tool face chipped from 17<sup>th</sup> piece;
- 28<sup>th</sup> piece – workpiece snapped and destroyed insert.

Comment (Fig. 10):

- 25<sup>th</sup> piece – tool wear on lateral tool flank;
- Tool wear increases very slowly.

Comment (Fig. 11):

- Insert sparks almost from the beginning;
- 14<sup>th</sup> piece - significant deterioration of the surface and significant sparks;
- 15<sup>th</sup> piece - unsatisfactory roughness - terminated.

Comment (Fig. 12):

- Calm cut without sparking;
- Tool wear is very small and almost not growing;
- Chipped tool face – at the end of tests.

Comment (Fig. 13):

- 16<sup>th</sup> piece - inserts begin to sparkle slightly;
- 28<sup>th</sup> piece - spark ceased;
- Small tool wear.

Comment (Fig. 14):

- 8<sup>th</sup> piece - inserts begin to sparkle;
- 24<sup>th</sup> piece - spark is of low intensity;
- Small tool wear.

### 3.2

#### Surface roughness

#### Hrapavost površine

Table 4 Values of arithmetic tolerance of Ra profile  
Tablica 4. Vrijednosti aritmetičke tolerancije Rz profila

Number workpiece	Ra / μm					
	D 250_1	ZTA 7 NI_2	ZTA 7 NI_1	D 250_2	D 250_3	D 250_4
5	3,17	6,09	4,22	5,68	6,58	5,94
10	4,07	5,7	2,76	4,72	2,33	5,77
15	2,39	5,23	10,61	5,06	1,69	4,70
20	1,82	4,26	not measured	4,15	1,78	4,03
25	1,61	3,03	not measured	3,54	2,28	3,70
27	1,98	-	-	-	-	-
30	-	not measured	not measured	4,37	1,97	2,02

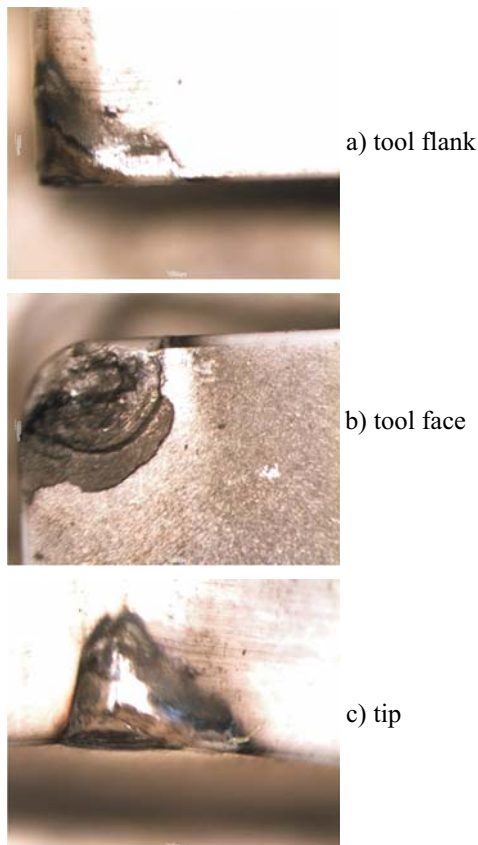


Figure 14 Tool wear – indexable cutting insert type D 250\_4  
Slika 14. Trošenje alata – rezna pločica tipa D 250\_4

The value of surface roughness (*Ra*) decreases with the number of machined pieces of almost all sleeves. It is a characteristic for the ceramic cutting tools. If we want to achieve maximum performance, we have to "wear down" lightly these inserts. If the plate achieved the maximum tool life, roughness would begin to rise slightly. This could be caused by increasing tool wear.

ZTA 7 NI\_1 inserts caused sparking that increased with the number of machined sleeves. This test was finished for unsatisfactory roughness at the 15<sup>th</sup> piece as shown in the graph.

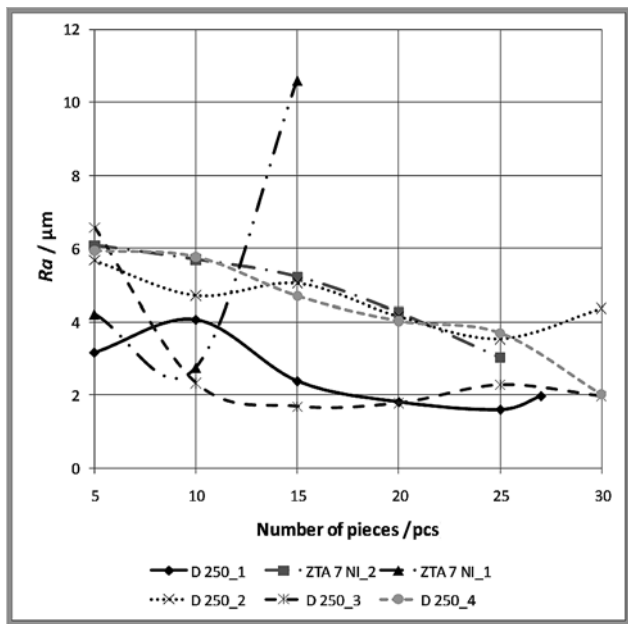


Figure 15 Arithmetic tolerance of Ra profile  
Slika 15. Aritmetička tolerancija Ra profila

Table 5 Values of the greatest height of Rz profile  
Tablica 5. Vrijednosti najveće visine Rz profila

Number workpiece	Rz / μm					
	D 250_1	ZTA 7 NI_2	ZTA 7 NI_1	D 250_2	D 250_3	D 250_4
5	20,33	28,50	19,80	29,33	36,90	28,23
10	20,20	26,50	19,80	22,45	15,35	26,50
15	17,60	25,10	53,95	26,58	11,25	23,83
20	12,80	19,85	not measured	22,70	11,48	20,15
25	10,20	16,75	not measured	21,68	15,73	18,63
27	14,50	-	-	-	-	-
30	-	not measured	not measured	27,53	14,20	14,43

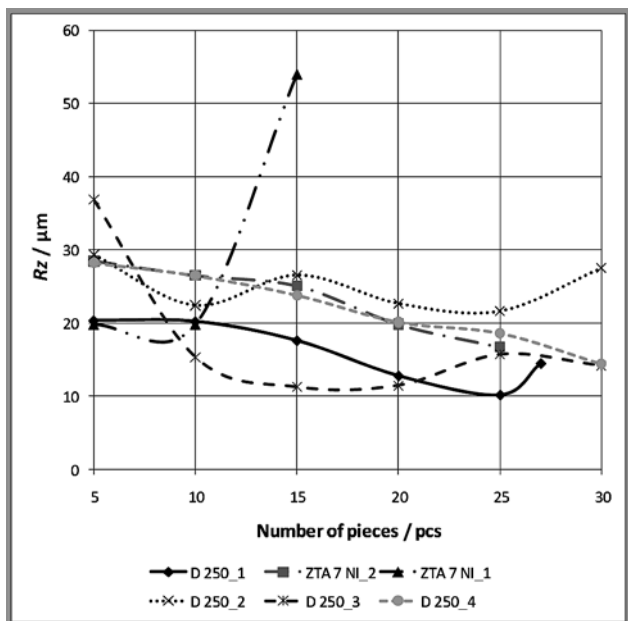


Figure 16 The greatest height of Rz profile  
Slika 16. Najveća visina Rz profila

Roughness is the most correlated with the Ra value. This parameter is the most common in engineering practice in the Czech Republic. Unfortunately, it is influenced by unique extreme surface roughness.

Parameter of roughness of Rz profile decreases with the number of machined pieces of almost all inserts with slight deviations, as shown in the previous measurement. Rz parameter nearly replicates Ra parameter.

### 3.3 External diameter Vanjski promjer

Table 6 Values of the external diameter D  
Tablica 6. Vrijednosti vanjskog promjera D

Number workpiece	Ø D / mm					
	D 250_1	ZTA 7 NI_2	ZTA 7 NI_1	D 250_2	D 250_3	D 250_4
5	73,56	73,51	73,49	73,50	73,58	73,47
10	73,56	73,55	73,64	73,60	73,64	73,51
15	73,72	73,59	74,03	73,70	73,69	73,63
20	73,75	73,62	not measured	73,83	73,72	73,64
25	73,81	73,71	not measured	73,86	73,79	73,90
27	73,81	-	-	-	-	-
30	-	not measured	not measured	73,88	73,89	73,96
Δ	0,25	0,20	0,534	0,38	0,31	0,49

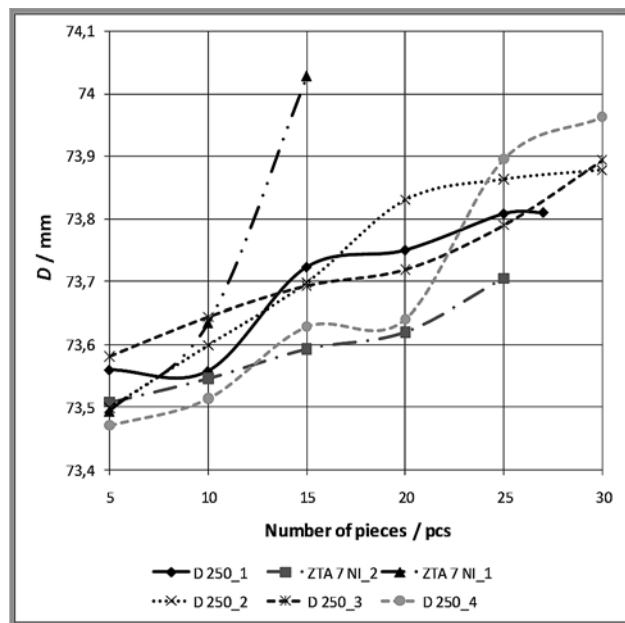


Figure 17 External diameter D  
Slika 17. Vanjski promjer D

The value of external diameter D grows with increasing number of machined sleeves. This process is caused by the tool wear. The tool wear was created especially on lateral tool flank (edge) and on the tip which was "burned". It changed a decrease in dimensional accuracy (first and last piece did not have the same diameter). The difference was in several tenths of

millimetres (see in Tab. 6). Abrasion and peeling off were created at the tool face of inserts. This phenomenon should not have any significant effect on dimensional accuracy. Tool wear is caused by high thermal and mechanical load. The tool is not able to perform its function (after a period) as a result of this process. Tool wear arises from abrasive wear, plastic deformation and brittle fracture.

#### 4

### Conclusion

#### Zaključak

The requirements are very high on the parameters of surface integrity in engineering practice. Cutting speed is being constantly increased. This leads to the CNC machining; these machines can secure the optimal working conditions so it is possible to produce products with the finest precision.

ZTA 7 NI inserts did not reach the maximum number of 30 machined inserts. The reason was impaired surface roughness in both cases. Tests were finished for unsatisfactory surface. The cutting inserts reached the prescribed criterion of tool wear ( $VB_{Bmax}$ ).

D 250 inserts had significantly better results. Almost all plates machined the maximum number of inserts at tool wear ( $VB_{Bmax}$ ) about 0,2 mm, except the first. The D 250\_1 insert could reach this maximum as well. The sleeve cracked (hollow in the casting) – the result was the destruction of the cutting edge. We will need to focus more on these parameters in other experiments – secondary edge, tool tip and tool face. The tool wear arises on the secondary edge and the tip. There is reduction of dimensional accuracy as a consequence (first and last piece have not the same diameter). The difference is in several tenths of millimetres.

Figures 15 and 16 show that the value of both roughness parameters is lower after 30 pieces machined. Roughness ( $Ra$ ) is below 6,3. Roughness ( $Ra$ ) gets even under 3,2 with an increasing number of machined inserts – D 250 series. This can be attributed to the properties of ceramics material which must be "abrade" first and then its potential can be fully realized.

D 250 inserts are suitable for cutting inserts made from 25P material at given cutting parameters and cutting geometry. The whole machining was carried out in dry (without using the liquid process) and it is environmentally friendly.

#### 5

### References

#### Literatura

- [1] www.mitutoyo-czech.cz [online]. 2009 [cit. 2011-01-08]. Mitutoyo SJ-400. <<http://www.mitutoyo-czech.cz/cz/pdf/SJ%20400-CZ.pdf>>.
- [2] Orlovsky, I.; Hatala, M. Sprinkle Drying Kiln Ceramic Granulate Drying Characteristic and Experimental Measurements of the Drying Process Parameters. // *Tehnicki Vjestnik - Technical Gazette*, 16, 2(2009), 27-30. ISSN 1330-3651.
- [3] Čep, R.; Neslušán, M.; Barišič, B. Chip Formation Analysis During Hard Turning. // *Strojarstvo*, 50, 6(2008), 337 – 345. ISSN 0562-1887.
- [4] Neslušán, M.; Turek, S.; Brychta, J.; Čep, R.; Tabaček, M. Experimentálne metódy v trieskovom obrábaní. Žilina : EDIS Žilina, 2007. 343 p. ISBN 978-80-8070-711-8.

- [5] Cep, R.; Ocenasova, L.; Novakova, J., Kouril, K.; Valicek, J.; Barisic, B. Influence of Thermal and Mechanical Shocks to Cutting Edge Tool Life. // *Proceedings of World Academy of Science, Engineering and Technology*, 56, (2009) (August), pp. 754-757. ISSN 2070-3740.
- [6] Cebalo, R.; Stoić, A. Optimisation of the roughness of the ground surface by diamond roller dressing. // *Tehnicka gazdeta*. 9, 3-4 (2003), pp 3-8, ISSN 1330-3651.
- [7] Jurkovic, Z.; Cukor, G.; Andrejcek, I. Improving the surface roughness at longitudinal turning using the different optimization methods // *Tehnicka Gazette*. 17, 4 (2010), pp 397-402, ISSN 1330-3651.

#### Authors' addresses

Adrese autora

**Robert Čep, Assoc. prof. Ing. PhD.**

**Adam Janásek, Ing.**

**Marek Sadílek, Ing., Ph.D.**

VŠB - Technical University of Ostrava

Faculty of Mechanical Engineering

346 - Department of Machining and Assembly

17. listopadu 15/2172

708 33 Ostrava - Poruba

Czech Republic

+420 597323193

robert.cep@vsb.cz

**Branislav Martinický, Ing., Ph.D.**

University of Žilina

Faculty of Mechanical Engineering

Department of Machining and Manufacturing Technology

Univerzitna 1

010 26 Zilina

Slovakia