



Title	Durability Performances of Carbon Fiber Reinforced Polymer and Concrete Bonded Systems under Moisture Conditions
Author[s]	Shrestha, Justin; Zhang, Dawei; Ueda, Tamon
Citation	Journal of composites for construction 2015 04016023 https://doi.org/10.1061/(ASCE)CC.1943-5614.0000674
Issue Date	2016.10
Doc URL	http://hdl.handle.net/2115/63552
Type	article (author version)
File Information	241115 Revised Manuscript [JS].pdf



[Instructions for use](#)

1 **Durability performances of carbon fiber reinforced polymer (CFRP) and**
2 **concrete bonded systems under moisture conditions**

3 Justin Shrestha⁽¹⁾, Dawei Zhang⁽²⁾, Tamon Ueda⁽³⁾

4 (1) PhD, Division of Engineering and Policy for Sustainable Environment, Graduate School
5 of Engineering, Hokkaido University, Email: justin@eng.hokudai.ac.jp

6 (2) Associate Professor, Department of Civil Engineering, College of Civil Engineering and
7 Architecture, Zhejiang University, Hangzhou, China, 310058. Email: dwzhang@zju.edu.cn
8 (corresponding author)

9 (3) Professor, Division of Engineering and Policy for Sustainable Environment, Faculty of
10 Engineering, Hokkaido University, Email: ueda@eng.hokudai.ac.jp

11 **ABSTRACT**

12 The information on long-term durability of the carbon fiber reinforced polymer (CFRP)-
13 concrete bond interfaces in various environmental conditions is necessary to predict the
14 service life of the structures. The assessment of the bond interfaces under moisture conditions
15 were evaluated by shear and tension bond tests using 6 popular commercial CFRP and epoxy
16 resin systems in the world for the maximum immersion period of 18 months. The bond tests
17 were also accompanied by the test in the mechanical properties of the resins and concrete.
18 Two of systems showed 25% and 16% reductions in average shear bond strengths, while the
19 remaining systems showed either improvement or a small reduction. Observation of the
20 failure modes suggested that, the durability against water related deterioration are worst when
21 the adhesion bonds between concrete and resin interface are weaker than the cohesive bonds
22 of the adjacent layers. Similarly, the average tensile bond strength reduction was found to

23 vary from 19% to 41% indicating that the durability of the bond is highly dependent on the
24 CFRP composite systems.

25 **INTRODUCTION**

26 The strengthening of concrete structural members with fiber reinforced polymer (FRP) is
27 very common and popular recently due to its various advantages over other materials and
28 methods. In spite of wide applicability, the durability information of such materials and the
29 systems under long-term exposure in severe environments are quite limited. In this regard,
30 the environmental deterioration factor currently being proposed by some of the guidelines
31 (ACI-440.2R-08, 2008, CNR-DT-200, 2004) does not extensively cover deteriorations in
32 various environmental conditions under long-term due to insufficient research in the field.
33 Realizing the importance of durability issues in the FRP composites, ACI committee has been
34 developing a guide to accelerated conditioning protocols for durability assessment of internal
35 and external FRP reinforcements for concrete (ACI-440.9R-15, 2015).

36 During the service life of the structures, some of the common severe environments which can
37 affect the durability of the FRP bonded concrete structures are moisture, high temperature,
38 freeze-thaw cycles, wet-dry cycles, UV radiation, etc. and their synergies. In order to study
39 the above mentioned durability related issues for the FRP bonded concrete structures,
40 researchers around the world have been using accelerated laboratory ageing method with
41 wide variety of testing methods, materials and exposure durations. Due to lack of guidelines
42 to perform such tests and diversity in availability of materials used, there is no uniformity in
43 the results and the degree of its effect. Some of the relevant literatures related to the long-
44 term investigation on durability of FRP-concrete bond under moisture are summarized
45 hereafter.

46 Karbhari and Ghosh (2009) conducted an experimental study to determine the effects of
47 environmental exposure on durability of bond strength between different commercially
48 available FRP strengthening systems and concrete using direct pull-off test. When 10
49 different FRP systems were exposed for 2 years, the maximum deterioration was noted for
50 the case of exposure to a sub-zero environment compared to immersion in salt water and
51 deionized water. The authors also suggested that the deterioration of the bond between FRP
52 and the concrete substrate should be considered in the design for rehabilitation measures. Dai,
53 et al. (2010) investigated on the influence of moisture on the tensile and shear bond behavior
54 of FRP to concrete interfaces subjected to accelerated wet-dry cycles (4 days wet at 60°C and
55 3 days dry) for the maximum duration of 2 years. The authors reported contradiction in the
56 behavior of tensile and shear bond properties after the exposure. The interfacial bond strength
57 degraded asymptotically with the exposure time, while the flexural capacity of the FRP sheet
58 bonded to concrete beams increased. However, the transition of failure modes occurred in all
59 the cases from concrete cohesion failure to the interface adhesion failure between primers and
60 concrete after the exposure. Till date, the longest duration of such exposure test was
61 performed by Nishizaki and Kato (2011), in which the durability of bond between carbon
62 fiber reinforcement polymer (CFRP) and concrete through outdoor exposure in a moderate
63 climate for 14 years. The authors evaluated the adhesive bond properties using the pull-off
64 and peel test methods. The pull-off strengths were slightly decreased but the residual values
65 still indicated quite good adhesion properties. In all the cases, failures occurred in the
66 concrete substrate, therefore, the authors pointed out that the reductions observed may not be
67 necessarily related to the degradation of the resin bond properties. In contrast, the results of
68 the peel test showed distinct differences in the failure modes after immersion. Benzarti, et al.
69 (2011) chose 4 different composite systems to perform durability test of adhesive bond
70 between concrete and CFRP under accelerated condition (40°C and 95% relative humidity)

71 using pull-off test and single lap shear test. After a year of exposure, even though transition
72 of failure mode occurred from cohesive concrete failure to the adhesive interface for most of
73 the cases, the results from the pull-off test were not always consistent with those of the shear
74 test. Significant reductions in the tensile bond strength was observed for most of the systems
75 while there was an increase in shear bond strength. Similarly, Choi, et al. (2012) conducted
76 large experimental program to investigate the effects of various exposure conditions
77 (hygrothermal, outdoor and chloride, alkali and UV/water cycles) on concrete beams
78 externally reinforced with different commercially available CFRP composites. The results
79 showed that the flexural strength of the beam specimens were reduced with exposure, but,
80 significant differences in the relative strength losses were observed in different commercial
81 systems indicating that the durability in such exposures are dependent on the FRP composite
82 system. Based on the strength reduction due to such exposure, the environmental reduction
83 factor which was close to 85% as suggested by ACI-440.2R-08 (2008). Recently, Al-
84 Tamimi, et al. (2014) conducted several single lap shear test on the CFRP precured plates
85 bonded to concrete prisms after being subjected to two marine environment exposures along
86 with the controlled laboratory atmosphere for the comparison. The specimens were preloaded
87 with 3 kN and 5 kN for the period of 150 days before the test. The results indicated that the
88 specimens exposed to the sun and saline environments experienced an increase in the bond
89 strength. The reason for such increase in performance was explained by increase in greater
90 polymer crosslinking of adhesive due to exposure in elevated temperature. All of the above
91 review on the literatures point out that the exposure to moisture condition could be harmful to
92 the FRP-concrete bond interfaces resulting in some reductions in bond strength along with
93 the transition of failure modes, however, the degrees of such effects are vastly dependent on
94 several factors but most importantly the selection of FRP materials along with the epoxy
95 resins.

96 This paper is the continuation effort of the authors' study on the moisture effect on the FRP-
97 concrete bond interfaces in order to explain different mechanisms and issues associated with
98 long-term degradation of bond. The authors have published some interesting findings of the
99 study in Shrestha, et al. (2014) which include discussion on the results of moisture effect on
100 FRP-concrete bond interfaces using normal and high strength substrate concrete evaluated by
101 single lap shear bond test for the maximum duration of 24 months. The results showed
102 average reduction in bond strength up to 32% and 12% for high-strength and normal-strength
103 concrete substrate respectively. The study also confirmed transition of failure mode from
104 concrete cohesion to mixed failure which is partially at the concrete and partially at primer-
105 concrete interface. But there exists a major limitation of mismatch between exposure and
106 testing conditions (temperature and humidity) in most of the previous studies. The authors
107 figured out that although specimens subjected to water or high humidity at different
108 temperatures, the tests are usually conducted in laboratory environmental conditions. This
109 may affect the bond behavior due to variability of moisture content at the interface as it can
110 change during the setup and testing period as a result of not maintaining the testing
111 conditions. Therefore, it is necessary to maintain the similar exposure condition even during
112 the testing period. The current research program was carried out overcoming such limitation
113 by conducting the test inside high humidity chamber. The long-term durability of 6
114 commercial CFRP systems bonded to concrete under the influence of moisture exposure and
115 normal temperature were evaluated. This paper contains some interesting results and
116 discussion on effect of moisture on the constituent materials and the bond behavior including
117 various aspects of long-term durability performances of those selected systems which would
118 serve in clarifying the understanding of moisture behavior in CFRP-concrete bonds. The
119 results and findings of the study would also add valuable contribution towards development
120 of durability related guidelines under different environmental conditions in future.

121 **EXPERIMENTAL PROGRAM**

122 The experimental program includes both material and bond tests. Two types of bond tests,
123 single lap shear test and direct pull-off test were conducted to evaluate the shear and tensile
124 performance of CFRP-concrete interface after different moisture exposure durations,
125 respectively. The material test includes epoxy tension test and concrete compression test by
126 standard coupons and cylinder specimens, respectively.

127 **Materials description**

128 Altogether 6 commercially available CFRPs and epoxy resins from different regions of the
129 world were selected for the study. The CFRP systems are from the most popular Japanese,
130 European and US based manufactures that include plate, strand sheet and continuous fiber
131 sheets along with their suggested epoxy resins. All of the epoxy resins were room
132 temperature curing resin for standard applications. For two of the CFRP systems, primer
133 layer was used as recommended by the manufacturers before attaching the CFRP sheet onto
134 the concrete surface. Detailed chemical information of the resins and their compositions were
135 not disclosed by the manufacturers, however, some of the general information was extracted
136 from the material safety data sheet (MSDS) of the resins. Based on the information given,
137 primary component of the epoxy curing agents used in the current study is modified
138 polyamine which is either aliphatic polyamine or combination of aliphatic polyamine with
139 cycloaliphatic polyamine. The properties of CFRP reinforcements and the resins are
140 summarized in Table 1.

141 **Preparation of the specimens**

142 The dog-bone shaped resin specimens for the uniaxial tensile test were prepared following
143 JIS.K.7113 (1995). The specimens were prepared using all the 8 kinds of epoxy resin which
144 include 2 types of primer. The base and hardener was mixed in a recommended proportion

145 and transferred into a vacuum chamber to remove the small air bubbles. The vacuumed resin
146 was then poured into the mold and tapped several times to remove any trapped air from
147 within the specimens. The specimens were cured in an ambient room temperature (Fig. 1) for
148 more than one month before being subjected to any kind of exposures.

149 Schematic details of the shear bond specimen and direct pull-off specimen are shown in Fig.
150 2 and Fig. 3 respectively. For the preparation of bond specimens, concrete prisms were
151 roughened with a disk grinder conforming to concrete surface profile (CSP) of level 4,
152 cleaned properly with compressed air and CFRP sheet/plate was attached on 3 sides on the
153 prism in turn. In two of the systems, primer layer was allowed to harden for a day before
154 attaching the CFRP sheet. As it was difficult to control the thickness of the resin layer, the
155 quantity of the resin was measured and applied based on surface area coverage
156 recommendation provided by the manufacturers. On each surface of the concrete prism,
157 CFRP was attached at two different areas to perform both shear and pull-off bond test as
158 shown in Fig. 4 (a). The upper part of the concrete prism was used for the shear bond test;
159 whereas the lower part was used for the pull-off test. After attaching the CFRP on all three
160 sides, specimens were put in the laboratory conditions for more than one month as a curing
161 period before giving any kind of environmental exposure. The final set of all 6 specimen
162 types are shown in Fig. 4 (b). The naming system used for the CFRPs, epoxy resins and all
163 the specimens are presented in Table 2.

164 **Exposure and testing conditions**

165 The specimens were either kept at an ambient condition inside the laboratory until the test
166 which is referred as 0 month (non-immersion case) or completely submerged in water tank
167 maintained at a constant temperature of 20 °C for the maximum period of 18 months. The
168 reason behind selecting only a single temperature range was mainly based on results of the

169 elevated temperature test. When the six systems were tested at 20 °C, 40 °C and 50 °C, none
170 of the cases showed any form of reductions in the bond strength (Shrestha, 2015). In addition,
171 to investigate the sole effect of moisture conditions, it was necessary to eliminate the changes
172 in the properties of the materials and the bonds due to temperature. Therefore, by selecting
173 the room temperature well below the glass transition temperature of the resins, it eliminates
174 any possibility of altering the property due to temperature. As for the testing, a set of
175 specimens was taken out from the water in every 3 months interval and quickly taken into the
176 temporary environmental chamber built around the testing machine in order to keep the
177 exposure and testing conditions similar. Both the shear bond test and resin tensile test were
178 conducted inside the environmental chamber which could maintain the desired temperature
179 and humidity. The schematic of the testing arrangement of the shear specimen inside the
180 controlled chamber along with the specimen during the test is shown in Fig. 5. Throughout
181 the test period, the temperature of 20 ± 3 °C and humidity over 85% was maintained in order
182 to prevent the loss of moisture from the specimens. As for the direct pull-off test, shown in
183 Fig. 6, no such arrangement was made to control the temperature and humidity of the testing
184 condition as the setting and testing period was very short which could be assumed to have
185 negligible effect. At the end of 18 months immersion, a set of specimens were removed from
186 the water and transferred into a chamber for the purpose of drying. The specimens were kept
187 inside the chamber for 4 days at a constant temperature of 28 °C. The specimens were
188 assumed to have dried when the change in weight within a day was less than 0.1%. The main
189 reason for this is to investigate the reversible or irreversible effects caused due to immersion
190 in water. Three specimens were tested for each exposure condition in order to ensure the
191 reliability of the obtained results.

192 **Test Procedures and Instrumentation**

193 Tensile test of the resin specimens and the single lap shear bond tests were conducted in a
194 universal testing machine (UTM) at the loading rate of 2 mm/min and 0.2 mm/min
195 respectively. As for the setup of the bond specimens, the CFRP-concrete bond interface was
196 aligned with the centerline of the upper loading grip in order to ensure the pure shear stresses
197 at the interface. The specimens were fixed on the testing machine by four long bolts, inserted
198 through the hollow PVC pipes. On the top of the specimen, a steel plate was placed to ensure
199 reaction during the loading. The arrangements are shown clearly in the Fig. 5. CFRP The
200 pull-off test was conducted in accordance to JSCE (2001) with the dolly size of 40x40 mm. A
201 portable adhesion testing device of maximum capacity of 10 kN was used. Loading was
202 applied in the rate of 5-10 kN per minute manually.

203 **RESULTS AND DISCUSSION**

204 **Moisture absorption by epoxy resin specimens and its effect on the** 205 **mechanical properties**

206 To address the moisture effect on the CFRP-concrete bond properties, it is crucial to know
207 the effect on the constituent material properties. In this regard, it is necessary to understand
208 the moisture transportation, absorption characteristics and its influence in the mechanical
209 behavior of the epoxy resins. Therefore, water absorption was monitored in the epoxy
210 samples at different interval of time using gravimetric method. The exponential rising curve
211 showed good fitting to represent the relationship between water absorption and the exposure
212 duration in months as shown in Fig. 7. The regression coefficient in all the cases were greater
213 than 0.98. The diffusion rate of water and the absorption capacities were found to be varied
214 greatly based on the resin type. However, even after 18 months of water immersion, none of
215 the resin specimens showed fully saturated condition. The maximum water absorbed by the
216 resins were in the range of 0.71% to 2.65% after 18 months of immersion in water. Five of

217 the cases (TR-A, TR-B, TP-B, TR-C, TR-D) showed similar water absorption behavior. On
218 the other hand, the resin specimens, TP-A, TR-E and TR-F, showed relatively lower water
219 diffusion rate and the water absorption. TR-E and TR-F contain higher filler materials (silica,
220 calcium carbonate etc.) which could have also contributed towards lowering the free volume
221 inside the resin resulting in the lower absorption. Tu and Kruger (1996) reported similar
222 absorption nature by the higher filled adhesive.

223 Previous researchers have reported that the water absorption by the epoxy resin in the range
224 between 1 to 7% by weight based on their formulations (Soles, et al., 1998). There are several
225 existing theories on the factors contributing to the moisture absorption. Struik (1977)
226 proposed that the quantity of water absorbed is dependent on the amount of free volume
227 which depends on the molecular packing and is affected by the crosslinking density and the
228 physical aging. In contrast, Li, et al. (2009) proposed that the free volume is not a decisive
229 factor but the polarity of the resin system plays a key role. Soles, et al. (1998) argued that the
230 polarity is the significant factor in determining the ultimate moisture uptake, however, the
231 free volume fraction also influences the moisture uptake. The above discussion may explain
232 the possible reasons of large variation in the moisture absorption capacities shown by the
233 different resin specimens.

234 In Fig. 8, the relationship between average tensile strength and water absorption shows two
235 distinct trends. Except in two of the cases (TR-B and TR-C), the increase in the moisture
236 absorption resulted in reduction of the tensile strength. However, depending on the resin type,
237 the degree of such effect varied. The highest reduction in tensile strength occurred in the resin
238 TR-F with an average reduction of around 38% after exposure, but, the ultimate water
239 absorption was only 0.71%. Whereas, those with the water absorption of over 2% showed
240 reduction in between 11% to 22%. In two of the cases, TR-B and TR-C, there was no effect

241 despite the water absorption of around 2%. Therefore, all the above results indicate that the
242 durability of the resins are highly dependent on the materials and the amount of water
243 absorption alone cannot be used as an indicator to judge or predict the effects caused by itself.

244 Figure 9 shows the relationship between average tensile strength of the resin and the exposure
245 duration. The duration of the moisture exposure resulted in reduction of the tensile strength of
246 the resins expect in the case of TR-B and TR-C. Plasticization, hydrolysis, cracking and
247 crazing are few of the existing reasons for such moisture related deteriorations in the
248 properties of the resins, however, there is no proper explanation yet for better resistance
249 shown by two of the resin types. In contrast to the tensile strength behavior, the tensile
250 modulus was not significantly affected by the exposure duration as shown in Fig. 10.

251 Figure 11 and Fig. 12 show the comparison of the tensile strength and modulus of the resin
252 specimens respectively tested under wet and dry condition after 18 months of exposure. The
253 results show that drying of the resins after 18 months of immersion in water does not recover
254 the initial mechanical properties, indicating that the exposure due to the moisture
255 conditioning caused some irreversible effect in the resin properties. These irreversible effects
256 could be due to loss of crosslinking density and permanent swelling of the resins (Tuakta and
257 Büyüköztürk, 2011).

258 **Effect of moisture on the shear bond failure modes**

259 Based on the observation of the failure surfaces after the shear test, the failure modes can be
260 categorized into 3 groups. Cohesion failure at the concrete layer (C) (Fig. 13a), mixed failure
261 (M) (Fig. 13b) and finally, the interface failure between concrete and resin layer (I) (Fig. 13c).
262 Among above three, concrete cohesion failure is the common mode of failure under normal
263 environmental condition. This failure mode was common in specimens SB-A, SB-E and SB-
264 F, indicating good adhesion bond between the CFRP and concrete. As for the specimens SB-

265 B and SB-D, the failures were usually of mixed type defined as the partial failure in concrete
266 cohesion and resin-concrete interface adhesion failure. The failure percentage in concrete to
267 the resin-concrete interface varied even within the similar exposure condition, but, no
268 distinction is made between such cases and generalized as a mixed failure mode. The last
269 failure mode was the adhesion failure at the interface between resin and concrete. This failure
270 mode is the least desired implying either insufficient surface preparation or the weak
271 adhesion bonding of the resin with the concrete. The latter could be the reason in specimen
272 SB-C, as similar degree of surface preparation was done in all the systems.

273 Transition of failure mode from the concrete cohesion to either mixed or interfacial failure
274 was observed as an effect of moisture. Most of the specimens within SB-A, SB-B, SB-E and
275 SB-F showed such transitions after the exposure. Likewise, the mixed failure mode before the
276 exposure either retained the same or changed to interfacial failure as in cases of SB-B and
277 SB-D. Lastly, the interfacial failure cases observed in SB-C, retained the same failure modes
278 irrespective of the exposure and its duration. Even drying the specimens after 18 months of
279 immersion did not affect the failure modes. Most of the results were comparable with the wet
280 cases. The distinction of all the failure modes after different exposure durations are
281 summarized in Table 3.

282 Analysis of the failure modes indicate that among four different wet-layup systems, the cases
283 with primer layer (SB-A and SB-B) showed relatively better adhesion bond with the concrete.
284 In both the cases, the greater percentage of failures occurred in concrete layer near the
285 interface before and after the exposure. In addition to this, reduction in the shear bond
286 strength after the exposure was comparatively lower than other wet-layup systems without
287 the primer layer. The results indicate that the primer could be a beneficial layer in case of
288 durability against moisture related effects. However, comparing the separate systems may not

289 be fair enough, as difference in material properties could affect the result. In future, it may be
290 necessary to conduct some further similar exposure tests without applying the primer layer to
291 make a direct comparison within the system in order to clarify the role of primer in case of
292 moisture related durability issues. But, in a separate study (Shrestha, et al., 2014), the authors
293 confirmed the effect of primer and surface preparation on the CFRP-concrete bond interface
294 without any form of environmental exposure. In such normal condition, the results revealed
295 no additional benefit of applying primer layer in terms of shear bond strength and direct pull-
296 off strength.

297

298 **Moisture effect on the shear bond strength**

299 Figure 14 shows the variation of the average shear bond strength with the exposure duration.
300 Initially, in the first 3 months of exposure, the moisture seems to show significant reduction
301 in the bond strength after which it was retained in most of the cases in extended exposure
302 duration. From the figure, it is also evident that the bond strength increased significantly in
303 case of SB-F system after 3 months of immersion till the 9 months and then remained almost
304 constant till the 18 months. As for SB-E system, the bond strength remained fairly unchanged
305 until 9 months followed by a small increment in 12 months and then remained almost
306 constant until the 18 months. For rest of the cases, it is rather difficult to see the clear trend
307 from the figure due to overlapping of data points. Therefore, Fig. 15 shows the shows the
308 relationship between average bond strength at each exposure duration normalized by the
309 average bond strength for non-immersion case. The average value was calculate based on the
310 results 3 specimens tested for each exposure condition. Based on the changes in the average
311 bond strength with the exposure duration, results could be categorized into 3 groups. The
312 systems such as SB-A, SB-B and SB-E with less than 5% reduction in the average bond
313 strength between non-immersion and immersion is grouped in the first category. As for the

314 duration of immersion period, there is no strong correlation between the change in the bond
315 strength and the exposure duration. The failure modes for these sets remained either as
316 concrete cohesion or the mixed mode after such exposure.

317 The second group includes SB-F type specimen, the CFRP plate bonded to the concrete,
318 which shows significant gain in bond strength after exposure. Compared to the non-
319 immersion case, the average bond strength increment of 34% was found after immersion case
320 implying some positive effects of water on the bond properties. This increment in the bond
321 strength was mainly started after 3 months of exposure duration. This is in contrary to some
322 of the previous reported results in which the CFRP plates bonded to concrete specimens
323 performed poorer than the sheets (Dolan, et al., 2009, Grace and Singh, 2005). Despite the
324 better properties of CFRP plate compared to the sheet, the main reason for such poorer
325 performance is attributed to durability issues of the epoxy adhesives used in such systems.
326 Even in the present case, the epoxy resin used for this system showed significant degradation
327 in the mechanical property, but that effect was not reflected in the ultimate bond strength as
328 the failure occurred at concrete cohesion layer. This indicates that the shear strength of the
329 degraded resin is still higher than that of the concrete but this still does not explain the reason
330 for enhancement in the bond strength. Similar increase in bond strength was also reported by
331 Al-Tamimi, et al. (2014) in the case of CFRP plate. The main reason for such increase in
332 strength was attributed to the enhancement of the polymer strength due to increase in
333 temperature during the exposure. In contrast, the temperature in the current study was always
334 close to 20 °C from initial curing of specimens to the exposure condition and then the testing
335 temperature, so such post-curing effect is highly unlikely to be the reason for increase in bond
336 strength. Further, the specimens were cured for more than a month before exposing them into
337 water, which was considered as a sufficient period for proper curing of the resins. There are
338 some other possibilities as well which could justify such improvement in the shear bond

339 strength after exposure. The first one could be due to increment in the concrete strength due
340 to better curing conditions provided by curing under water but, the results obtained from the
341 concrete compression test, as presented in Fig. 16, clearly showed that the compression
342 strength remained fairly constant throughout the exposure duration implying no enhancement
343 in concrete properties. In addition, despite of being the same batch of concrete with similar
344 failures in concrete cohesion, specimens such as SB-A and SB-B did not show any
345 improvement in the bond strength. Therefore, these evidences totally eliminate any chances
346 for concrete to be the reason for strength enhancement after exposure. Other remaining
347 possibilities for improvement could be either due to increase in the stiffness of CFRP or the
348 softening of the resins due to exposure. From the measurements of the strains at the unbonded
349 region during the shear bond test confirms that the stiffness of CFRP did not vary even after
350 the exposure. As for the resin, the tensile modulus was slightly lower but considering the
351 scatter at different durations, it is insignificant. Therefore, the improvement in the load
352 transfer mechanism between the CFRP and concrete due to exposure is still unknown and
353 needs further investigation.

354 The shear bond strength in the third category of the specimens SB-C and SB-D was
355 significantly reduced by the exposure. The average losses in bond strength after the exposure
356 are 25% and 16% respectively. Significant reductions could be observed in just 3 months of
357 exposure duration and remained almost in the same range throughout the exposure duration.
358 This indicates that the effect of moisture on the bond strength can be reflected in a very short
359 duration of time. The failure modes are also distinct in these two systems. In contrast to the
360 remaining systems, which mostly failed by concrete cohesion, specimens SB-C and SB-D
361 showed failure at the interface between concrete and resin layer. Despite the similar degree of
362 surface preparation, the failures at the interface even before the exposure imply weaker
363 adhesion between them. At the interface between concrete and resin, mechanical and

364 chemical bond are two key mechanisms which govern the bond action (Shrestha, et al., 2014).
365 The reduction in bond strengths after the exposure indicates that either one or both of the
366 mechanisms are affected by the presence of water. Water at the interface can reduce the
367 mechanical interlocking action or destroys the chemical bonds between resin-concrete at the
368 interface. These two factors may have contributed towards the reduction of the bond strength.
369 The degradation of such mechanical interlocking capacity at the epoxy-concrete interface due
370 to absorbed water was also reported by Dolan, et al. (2009). In summary, the effect of water
371 is prominent in cases when the surface roughness is not sufficient enough or the adhesion
372 bonds between resin and concrete is not strong enough, resulting in the adhesion failure at the
373 interface. In such a situation, significant loss in bond strength could occur after immersion.
374 Similar result was also observed by Shrestha et al. (Shrestha, et al., 2014) when CFRP
375 bonded to high strength substrate concrete failed at the interface after immersion in water. A
376 year of exposure in water resulted in 30% and 32% reduction in average bond strength
377 respectively for two types of specimen with different primer layer. In the same research, such
378 deterioration of bond strength was not observed for normal strength concrete substrate despite
379 the use of same CFRP composites and the exposure condition. The failure surfaces in those
380 cases were always mixed type. These evidences and discussions could clearly demonstrate
381 that the interfacial failure of bond is the most severe case at which the water deteriorates the
382 bond strength significantly. It also highlights the necessity of proper surface preparation of
383 the substrate concrete and the use of appropriate epoxy resin with higher adhesion strength to
384 ensure stronger bond at the interface than the adjacent layers and remain durable against the
385 moisture environments.

386 The effect of wet and dry testing conditions were also examined on the shear bond strength
387 after 18 months of immersion in water as shown in Fig. 17. About less than 5% recovery of
388 average bond strength was found in specimens SB-C and SB-F, whereas the recovery was

389 over 10% in case of specimens SB-A and SB-B but no such effect was observed in SB-D
390 case. The results of specimen SB-E was not included due to some problems associated with
391 the specimen during preparation process. In conclusion, even though slight recovery of bond
392 strength was noticed in some cases after drying, it could not restore back to the original state
393 indicating that the deteriorations due to water causes irreversible effect on the bond properties.

394 **Moisture effect on the tensile bond strength**

395 The pull-off test method is a simple method to evaluate the quality of tensile bond in the field.
396 This method was used to determine the relative performances of CFRP-concrete bond after
397 different moisture exposure conditions shown in Fig. 18. Despite the large variation in the
398 results, reduction in the average tensile bond strength is evident in most of the cases as a
399 result of the exposure. In few of the cases, the value of the tensile bond strength after the
400 exposure was even lower than the minimum pull-off strength of 1.4 MPa which is
401 recommended by ACI-440.2R-08 (2008). Except system TB-B, the average reduction in the
402 tensile bond strength varied from 19% to 41% in 18 months period after the exposure. Table
403 4 shows the ratio of the average tensile bond strength at different duration, normalized by the
404 non-immersion (0 month) case. Some of the other researchers have also observed such
405 adverse effects due to moisture exposure conditions resulting in reductions in tensile bond
406 strengths, but, in most cases such reductions were accompanied by transition of failure
407 surfaces from concrete to mixed or complete interfacial failures (Au and Büyüköztürk, 2006,
408 Benzarti, et al., 2011, Dai, et al., 2010, Karbhari and Ghosh, 2009). In contrast to the above
409 behavior, the present study didn't observe such transition of failure modes after the exposure
410 despite some reductions in the tensile bond strengths. The concrete cohesion failure mode
411 remained unchanged in majority of the cases even after the exposure. Comparison of a typical
412 failure mode before and after exposure is shown in Fig. 19. Similar kind of observation was
413 also reported by Nishizaki and Kato (2011), in which the authors suggested that such

414 reductions without the transition of failure modes maybe due to change in behavior of
415 concrete properties rather than the degradation of the bond properties. However, no
416 information on the durability of the concrete properties were provided. Nonetheless, in the
417 current study, the concrete compression behavior was not affected by the exposure duration
418 (Fig. 16), so based on that, it can be assumed that the tensile behavior may not have affected
419 as well, implying the reductions could have caused by environmental degradation of the
420 resins.

421 Figure 20 shows tensile bond strength comparison tested under wet and dry condition after 18
422 months of exposure in water. Similar to the shear bond behavior, drying process helped
423 recovery of the tensile bond strength, but was not able to retain back the original state. Only
424 in the case of specimen TB-B, the resulting strength was higher than the original strength.
425 Even in the failure modes, no distinction could be made between those conditions as most of
426 them failed in concrete.

427 In summary, the effect of exposure in water caused significant reductions in tensile bond
428 strengths which could be partially recovered by drying process. The distinction between
429 durability performances in different CFRP systems cannot be made as the failure were
430 governed by the concrete cohesion strength. Despite some reductions in the bond strength,
431 the good adhesion was still retained between CFRP composite and the concrete substrate
432 even after the exposure. Nevertheless, the tensile bond strengths obtained here can just be
433 used as indicative values to compare the relative changes in the performances over different
434 environmental conditions.

435 **CONCLUSIONS**

436 The durability of CFRP-concrete bond interfaces for 6 commercially available CFRP and
437 epoxy resin systems were evaluated with single lap shear bond test and direct pull-off test

438 together with tensile test of the resins. Based on the observed results of immersion for the
439 period of 18 months, following conclusions can be drawn:

- 440 1. The water absorption capacities of the resin varied greatly from 0.71% to 2.65% after
441 18 months of immersion in water at 20°C. The water absorption by the resin proved
442 to be harmful affecting the tensile strength in most of the cases but no strong
443 relationship was found between amount of moisture absorption and the tensile
444 strength. In contrast to the strength behavior, the modulus was not much affected by
445 such exposure.
- 446 2. In response to moisture exposure, the shear bond behavior showed either reduction or
447 increment in the bond strength depending on the CFRP systems. After the exposure,
448 less than 5% change in bond strength was observed for types SB-A, SB-B and SB-E,
449 whereas, such reductions increased to 16% and 25% respectively in SB-C and SB-D
450 types. In contrast, there was an increase in average bond strength of about 34% in
451 case of SB-F type. It can also be concluded that longer duration of exposure does not
452 necessarily mean greater effect. At the later stages of exposure duration, the bond
453 strength remained almost constant.
- 454 3. As for the failure modes in shear bond tests, three typical failure modes were
455 observed, which are concrete cohesion failure, partial concrete cohesion and resin-
456 concrete interface failure and lastly adhesion failure between resin and concrete. As
457 an effect of water immersion, transition of failure modes occurred from concrete
458 cohesion to mixed mode or interface failure but significant reductions in bond
459 strength were observed only in the cases of complete interface failures. This
460 emphasizes the importance of proper surface preparation required in substrate
461
462

463 concrete and use of the resin with good adhesion bond strength with concrete to
464 ensure greater durability of CFRP-concrete bond against moisture related effects.

465
466 4. Tensile bond strengths obtained from direct pull-off tests were reduced significantly
467 in most of the cases after exposure, but the failure modes, which were concrete
468 cohesion failures remained unchanged. This fact suggests that there are some harmful
469 effects of water immersion in tensile bond properties, however no reasonable
470 explanation can be made for the reason of strength reduction.

471
472 5. A set of specimens was also tested in dry condition after 18 months of exposure in
473 water to evaluate reversible and irreversible effects. In general, the results revealed
474 that the mechanical properties of the resins were further deteriorated after drying, in
475 contrast, both the shear and tensile bond strengths were partially recovered but not
476 restored to the original strength. These results indicate that the effects caused due to
477 exposure in moisture are mostly irreversible.

478
479 Based on the above conclusions, it is clear that moisture condition is one of the key
480 environmental durability issues which could prematurely degrade the bond between the FRP
481 and the concrete. Therefore, such consideration should be made during the design stage to
482 ensure safety and longevity of the structure. While the authors will propose the relevant
483 constitutive laws for the interfaces in case of moisture conditions in the next paper, the
484 present paper would serve to clarify some of the key issues related to the moisture effect on
485 the bond properties. The bond values obtained as the result of exposure could be utilized to
486 calculate the reduction factor. Such factor could be used as an additional reduction coefficient
487 in the member resistance to consider the bond degradation between FRP and concrete due to
488 the moisture dominant environment condition in the field applications. However, this factor

489 should be limited only to the bond critical applications for strengthening with the wet-layup
490 CFRP system under normal temperature range of 20 °C.

491

492 **Acknowledgements**

493 The authors acknowledge the support of Nippon Steel and Sumikin Materials Co., Ltd.,
494 Mitsubishi Plastics Infratec Co., Ltd., FYFE Japan Co., Ltd, Simpson Strong-Tie Asia Ltd.
495 and Sika Ltd for providing necessary materials to conduct this research work. The financial
496 supports from the Fundamental Research Funds for the Central Universities of China
497 (2015FZA4018), Grant-in-Aid for Scientific Research (A) of Japan Society of Promotion of
498 Science (No. 26249064) and NEXCO Group Companies' Support Fund to Disaster
499 Prevention Measures on Expressways are greatly appreciated. The authors would also like to
500 thank Mr. Thierry Birset for providing test results.

501

502 **References**

- 503 ACI-440.2R-08 (2008). "Guide for the design and construction of externally bonded FRP systems for
504 strengthening concrete structures." American Concrete Institute (ACI), Farmington Hills, MI.
- 505 ACI-440.9R-15 (2015). "Guide to Accelerated Conditioning Protocols for Durability Assessment of
506 Internal and External Fiber-Reinforced Polymer (FRP) Reinforcement." American Concrete Institute
507 (ACI), Farmington Hills, MI.
- 508 Al-Tamimi, A. K., Hawileh, R. A., Abdalla, J. A., Rasheed, H. A., and Al-Mahaidi, R. (2014).
509 "Durability of the bond between CFRP plates and concrete exposed to harsh environments." *Journal*
510 *of Materials in Civil Engineering*, 27(9), 04014252.
- 511 Au, C., and Büyüköztürk, O. (2006). "Peel and Shear Fracture Characterization of Debonding in FRP
512 Plated Concrete Affected by Moisture." *Journal of Composites for Construction*, 10(1), 35-47.

- 513 Benzarti, K., Chataigner, S., Quiertant, M., Marty, C., and Aubagnac, C. (2011). "Accelerated ageing
514 behaviour of the adhesive bond between concrete specimens and CFRP overlays." *Construction and*
515 *Building Materials*, 25(2), 523-538.
- 516 Choi, S., Gartner, A., Etten, N., Hamilton, H., and Douglas, E. (2012). "Durability of Concrete
517 Beams Externally Reinforced with CFRP Composites Exposed to Various Environments." *Journal of*
518 *Composites for Construction*, 16(1), 10-20.
- 519 CNR-DT-200 (2004). "Guide for the Design and Construction of Externally Bonded FRP Systems for
520 Strengthening Existing Structures." National Research Council, Rome.
- 521 Dai, J., Yokota, H., Iwanami, M., and Kato, E. (2010). "Experimental Investigation of the Influence
522 of Moisture on the Bond Behavior of FRP to Concrete Interfaces." *Journal of Composites for*
523 *Construction*, 14(6), 834-844.
- 524 Dolan, C., Tanner, J., Mukai, D., Hamilton, H., and Douglas, E. (2009). "Research report for
525 evaluating the durability of bonded CFRP repair/strengthening of concrete beams." *NCHRP*,
526 *Washington DC*.
- 527 Grace, N. F., and Singh, S. (2005). "Durability evaluation of carbon fiber-reinforced polymer
528 strengthened concrete beams: experimental study and design." *ACI Structural Journal*, 102(1), 40-53.
- 529 JIS.K.7113 (1995). "Testing methods for tensile properties of plastics." Japanese Standards
530 Association, Tokyo, Japan (In Japanese).
- 531 JSCE (2001). "Recommendations for upgrading of concrete structures with use of continuous fiber
532 sheets." Research Committee on Upgrading of Concrete Structures with use of Continuous Fiber
533 Sheets, Japan Society of Civil Engineers, Tokyo, Japan.
- 534 Karbhari, V. M., and Ghosh, K. (2009). "Comparative durability evaluation of ambient temperature
535 cured externally bonded CFRP and GFRP composite systems for repair of bridges." *Composites Part*
536 *A: Applied Science and Manufacturing*, 40(9), 1353-1363.
- 537 Li, L., Yu, Y., Wu, Q., Zhan, G., and Li, S. (2009). "Effect of chemical structure on the water sorption
538 of amine-cured epoxy resins." *Corrosion Science*, 51(12), 3000-3006.

- 539 Nishizaki, I., and Kato, Y. (2011). "Durability of the adhesive bond between continuous fibre sheet
540 reinforcements and concrete in an outdoor environment." *Construction and Building Materials*, 25(2),
541 515-522.
- 542 Shrestha, J. (2015). "Investigation on long-term durability of FRP-concrete bond interfaces under
543 moisture conditions." PhD dissertation, Hokkaido University, Sapporo, Japan.
- 544 Shrestha, J., Ueda, T., and Zhang, D. (2014). "Durability of FRP concrete bonds and its constituent
545 properties under the influence of moisture conditions." *Journal of Materials in Civil Engineering*,
546 27(2), A4014009.
- 547 Shrestha, J., Ueda, T., and Zhang, D. "Effect of Primer and Surface Preparation on the FRP-Concrete
548 Bond " *Proc., The 7th International Conference on FRP Composites in Civil Engineering*, Vancouver,
549 Canada.
- 550 Soles, C. L., Chang, F. T., Bolan, B. A., Hristov, H. A., Gidley, D. W., and Yee, A. F. (1998).
551 "Contributions of the nanovoid structure to the moisture absorption properties of epoxy resins."
552 *Journal of Polymer Science Part B: Polymer Physics*, 36(17), 3035-3048.
- 553 Struik, L. C. E. (1977). "Physical aging in amorphous polymers and other materials." PhD dissertation,
554 TU Delft, Delft University of Technology.
- 555 Tu, L., and Kruger, D. (1996). "Engineering properties of epoxy resins used as concrete adhesives."
556 *ACI Materials Journal*, 93(1).
- 557 Tuakta, C., and Büyükoztürk, O. (2011). "Conceptual Model for Prediction of FRP-Concrete Bond
558 Strength under Moisture Cycles." *Journal of Composites for Construction*, 15(5), 743-756.

Table 1. Properties of the FRPs and the epoxy resins

Description	System-A		System-B		System-C	System-D	System-E	System-F
Type	Carbon fiber sheet		Carbon fiber sheet		Carbon fiber sheet	Carbon fiber sheet	Carbon fiber strand sheet	Carbon fiber plate
Fiber content	200 g/m ²		200 g/m ²		393 g/m ²	200 g/m ²	600 g/m ²	>68%
Thickness	0.111 mm		0.111 mm		0.218 mm	0.176 mm	0.333 mm	1.4 mm
Width of the plate	-		-		-	-	-	50 mm
Strength (MPa)	3400		3400		3790	3800	3400	3200
Young's modulus (GPa)	230		230		230	240	245	210

Description	Epoxy-A		Epoxy-B		Epoxy-C	Epoxy-D	Epoxy-E	Epoxy-F
Type	matrix	primer	impregnating resin	primer	matrix	matrix	adhesive paste	adhesive paste
Mixing ratio (B:H)	2:1	2:1	4:1	4:1	100:34.5	2:1	4:1	3:1
Main composition (Base)	Bisphenol A type epoxy resin				Modified epoxy resin		Bisphenol A type epoxy resin	
Main composition (Hardener)	Modified aliphatic polyamine				Polyoxypropylenediamine (aliphatic amine), Polyetheramine (aliphatic amine)	blend of cycloaliphatic, isophoronediamine, Triethylenetetramine (aliphatic amine)	Modified aliphatic polyamine	Trimethyl hexamethylene diamine (aliphatic amine)
Tensile strength (MPa)	56.74	64.02	39.66	52.62	56.50	53.87	55.96	32.55
Young's modulus (GPa)	3.10	3.30	3.90	3.40	3.80	2.73	5.63	10.70
Poisson's ratio	0.35	0.38	0.34	0.43	0.33	0.37	0.38	0.29
Glass transition temperature (°C)	48.7	45.9	49.5	55	54.3	53.6	49.3	56.5

Except the tensile strength, Young's modulus, Poisson's ratio and the Glass transition temperature of the resins, all other information are provided by the manufacturers

Table 2. Naming scheme for the specimens

Composite System	Epoxy	Tensile resin specimens		Shear bond specimens	Tensile bond specimens
		Matrix/ Adhesive	Primer		
A	Epoxy-A	TR-A	TP-A	SB-A	TB-A
B	Epoxy-B	TR-B	TP-B	SB-B	TB-B
C	Epoxy-C	TR-C	-	SB-C	TB-C
D	Epoxy-D	TR-D	-	SB-D	TB-D
E	Epoxy-E	TR-E	-	SB-E	TB-E
F	Epoxy-F	TR-F	-	SB-F	TB-F

3 specimens were tested for each case

Table 3. Summary of the failure modes in shear bond test

Exposure duration (Months)	Testing condition	Failure modes																	
		SB-A			SB-B			SB-C			SB-D			SB-E			SB-F		
		1	2	3	1	2	3	1	2	3	1	2	3	1	2	3	1	2	3
0	Wet	C	C	C	C	M	C	I	I	I	M	M	M	C	C	C	C	C	C
3	Wet	C	C	C	M	M	C	I	I	I	I	I	I	C	C	C	M	I	C
6	Wet	C	M	C	C	M	C	I	I	I	I	I	I	C	C	C	M	M	M
9	Wet	C	C	C	M	I	M	I	I	I	I	I	I	C	C	C	C	M	M
12	Wet	M	M	C	C	M	I	I	I	I	I	I	I	C	C	M	C	M	M
15	Wet	C	M	M	M	I	M	I	I	I	I	I	I	M	C	C	M	M	M
18	Wet	C	M	M	M	M	M	I	I	I	I	I	I	M	M	M	M	M	C
18	Dry	M	M	M	M	M	M	I	I	I	I	I	I	-	-	-	M	M	M

C=Concrete cohesion; M=Partial concrete cohesion and resin-concrete interface; I=Resin-concrete interface

Table 4. Summary of the average tensile bond strength normalized by the non-immersion (0 month) case

Exposure duration (Months)	Testing condition	Normalized value of average tensile bond strengths by 0 month					
		TB-A	TB-B	TB-C	TB-D	TB-E	TB-F
0	Wet	1.00	1.00	1.00	1.00	1.00	1.00
3	Wet	0.61	1.19	0.66	0.81	0.59	0.51
6	Wet	0.44	1.27	0.88	0.84	0.60	0.59
9	Wet	0.44	1.59	0.58	0.97	0.71	0.52
12	Wet	0.82	1.25	0.97	0.90	0.75	0.68
15	Wet	0.96	1.69	1.21	0.81	1.02	0.75
18	Wet	0.52	0.85	0.56	0.33	0.89	0.51
18	Dry	0.72	1.49	0.66	0.74	-	0.61



Fig. 1. Epoxy resin specimens for the tensile test

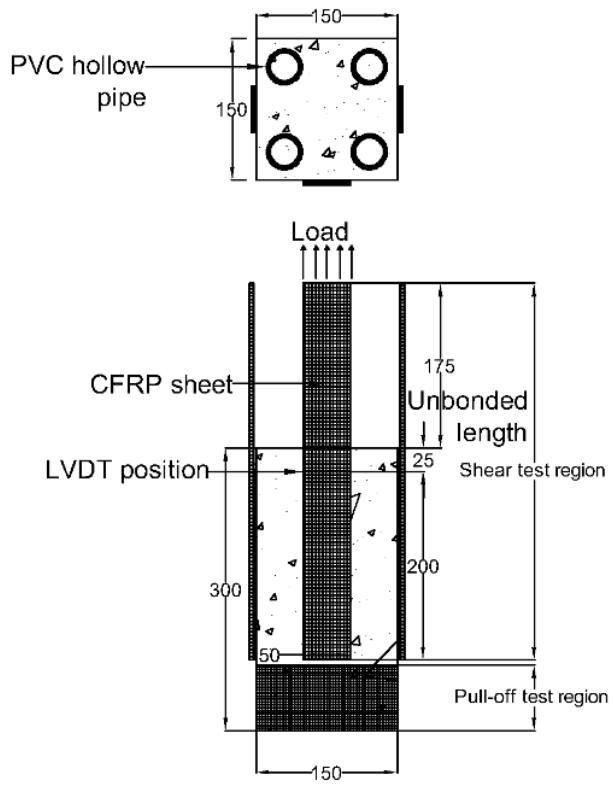


Fig. 2. Details of bond specimen (unit: mm) for single lap shear test



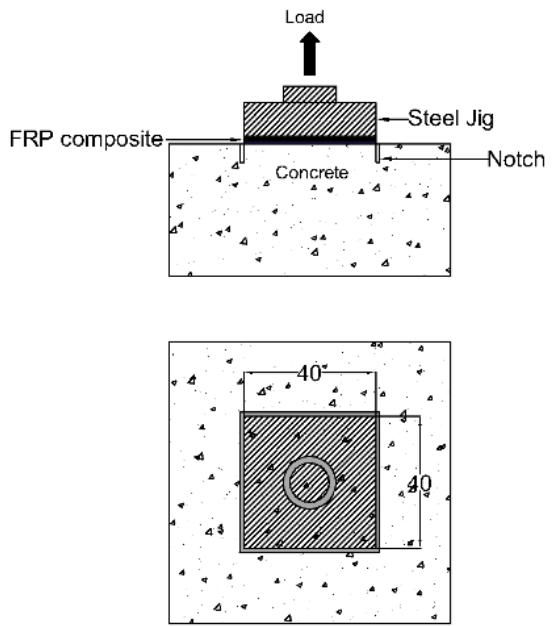


Fig. 3. Details of direct pull-off test specimen (unit: mm)

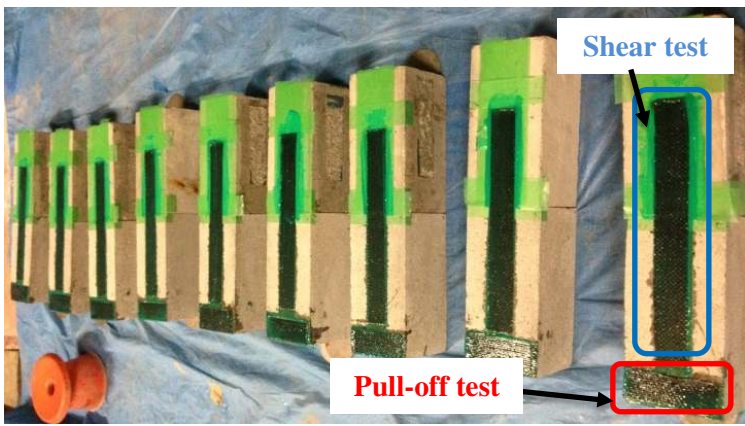


(a)

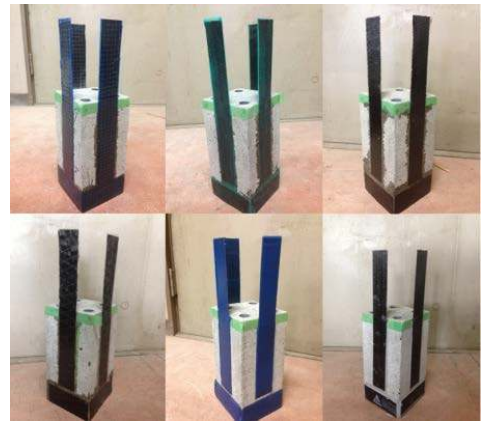

(b)

Fig. 4. (a) Preparation of the bond specimens; (b) Sample specimen for each FRP system

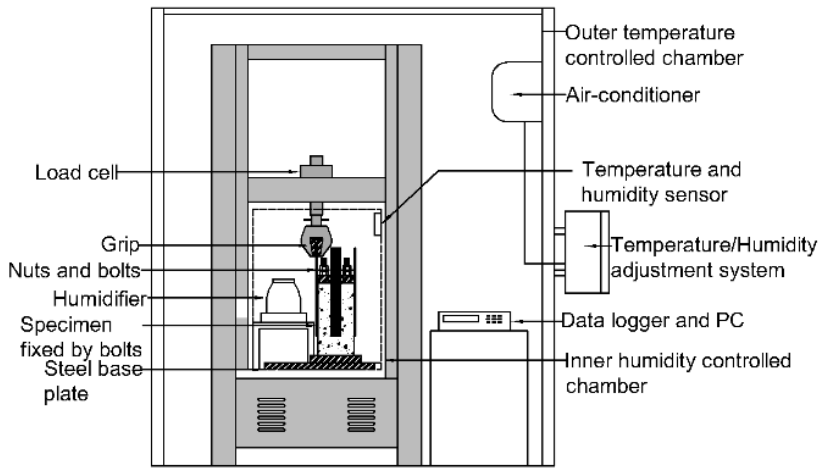

(a)



(b)

Fig. 5. (a) Test arrangement schematic for the bond specimen inside the environmental testing chamber ; (b) Specimen during the test inside the chamber



Fig. 6. Direct pull-off test setup

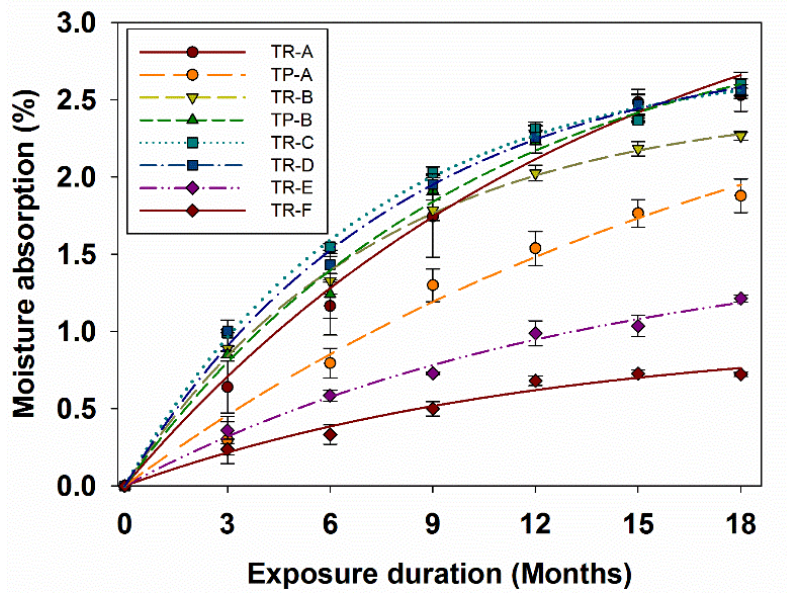


Fig. 7. Moisture absorption by epoxy resin specimens

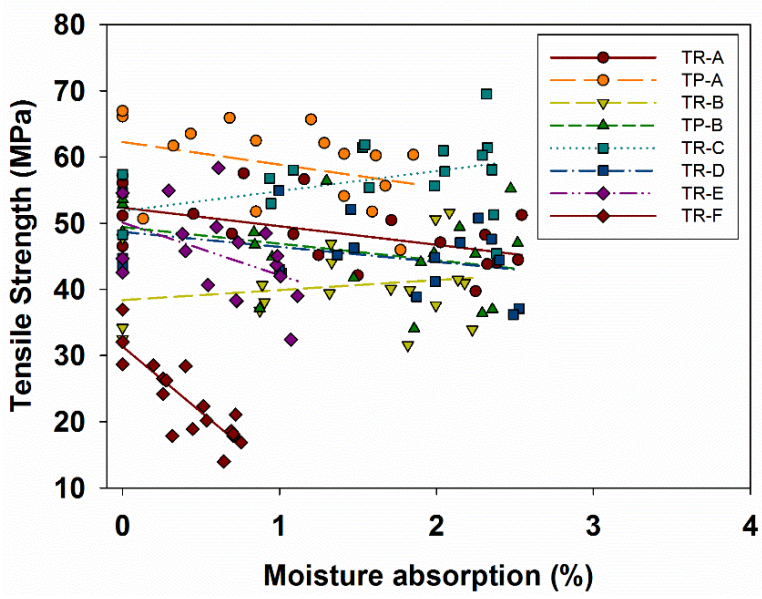


Fig. 8. Relationship between tensile strength with the moisture absorption by the resins

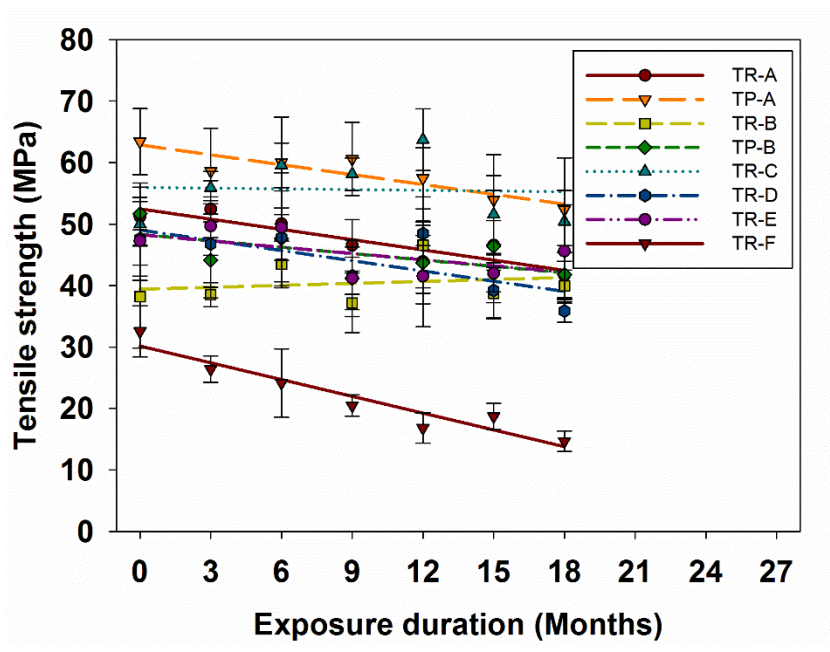


Fig. 9. Exposure duration effect on the tensile strength of the resins

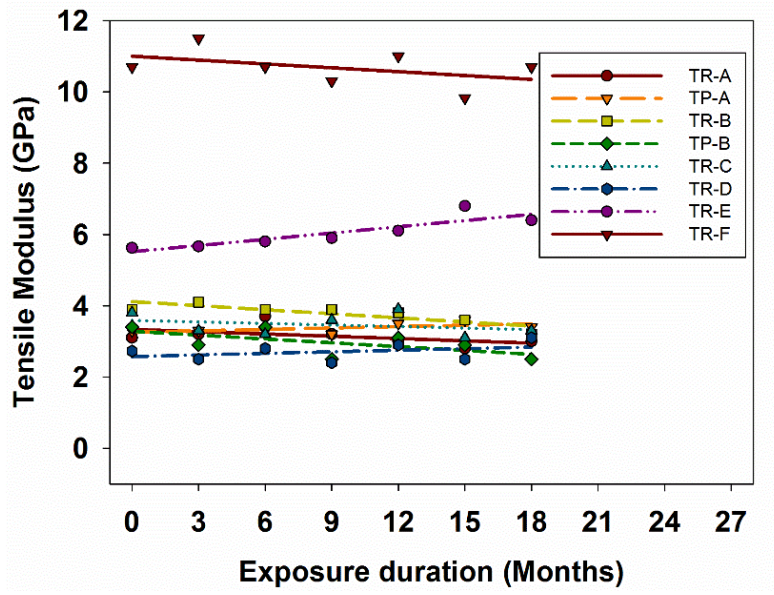


Fig. 10. Effect of the exposure duration on the tensile modulus of the resins

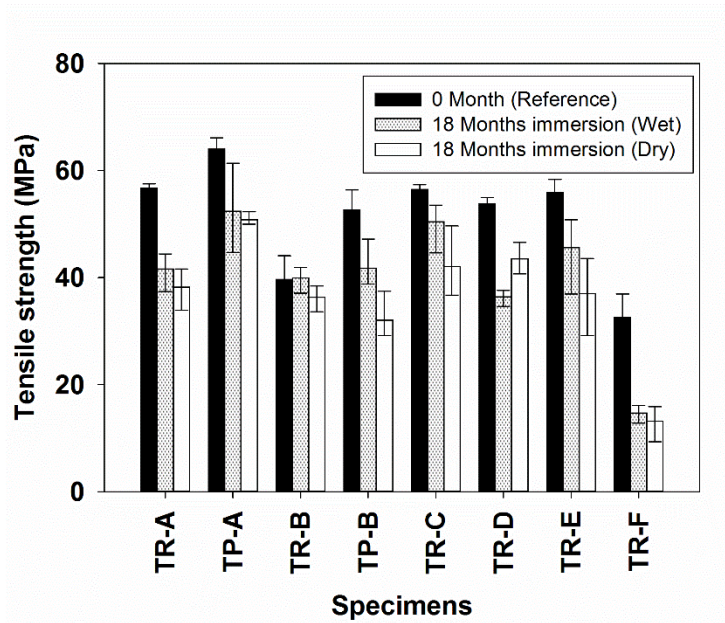


Fig. 11. The effect of testing condition (wet/dry) on the tensile strength of the resins after 18 months of immersion in water


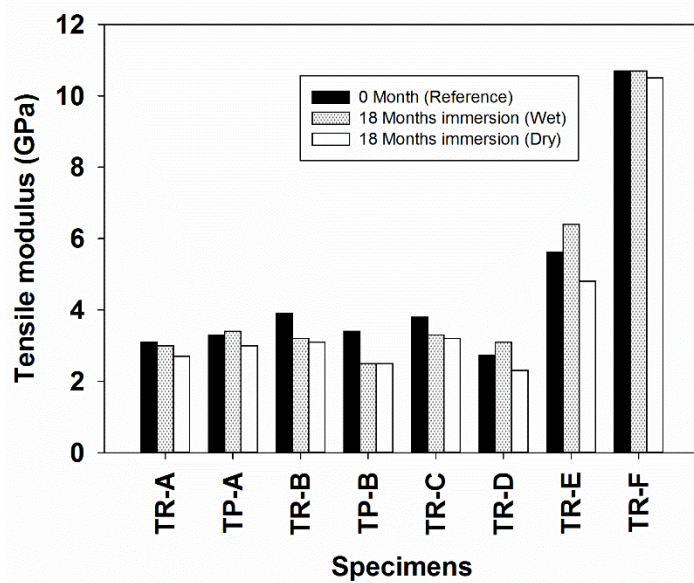



Fig. 12. The effect of testing condition (wet/dry) on the tensile modulus of the resins after 18 months of immersion in water



(a) Concrete cohesion failure

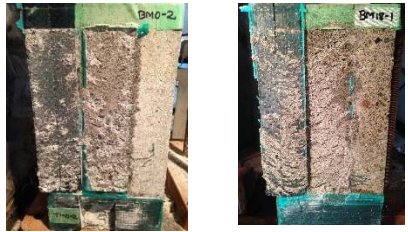

(b) Mixed failure

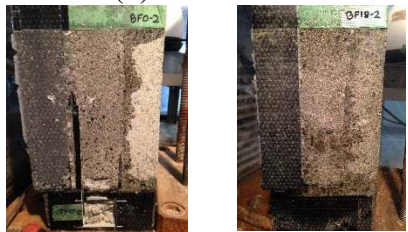

(c) Adhesion failure

Fig. 13. Comparison of three typical failure modes before and after 18 months of exposure

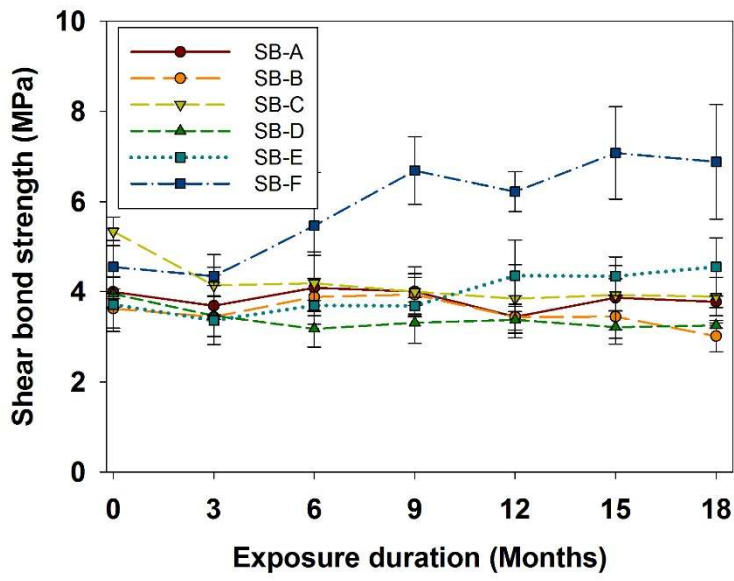


Fig. 14. Shear bond strength variation with the exposure duration

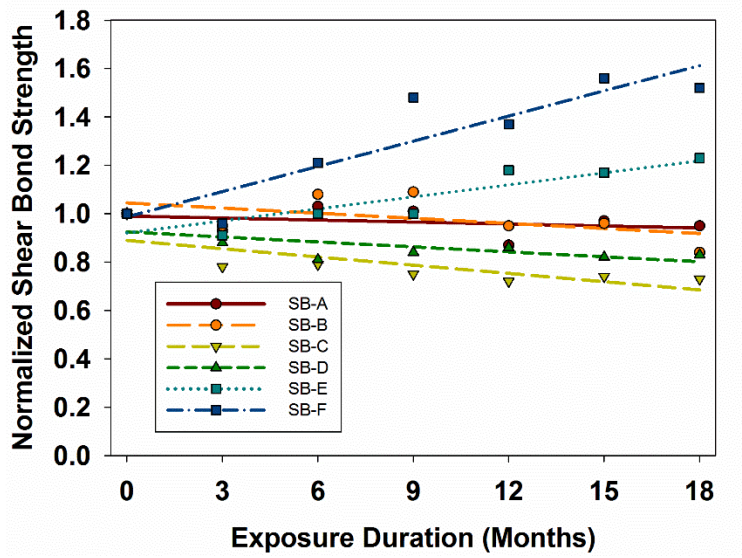


Fig. 15. Relationship between normalized shear bond strength and the exposure duration

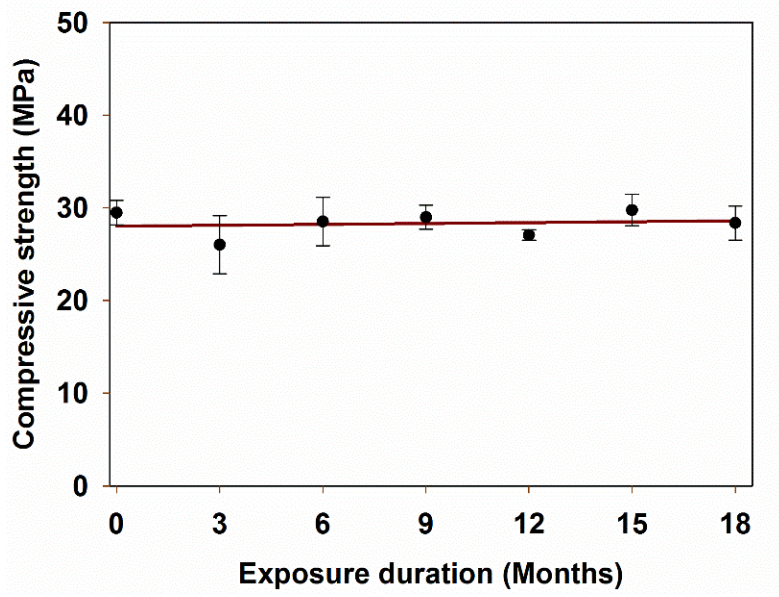


Fig. 16. Effects of exposure on the concrete compressive strength

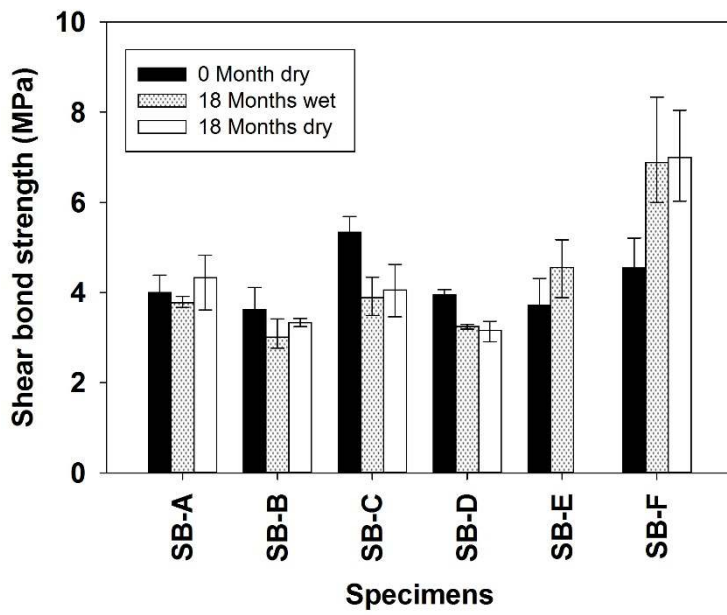


Fig. 17. Effect on shear bond strength after 18 months of immersion and different testing conditions (wet/dry)

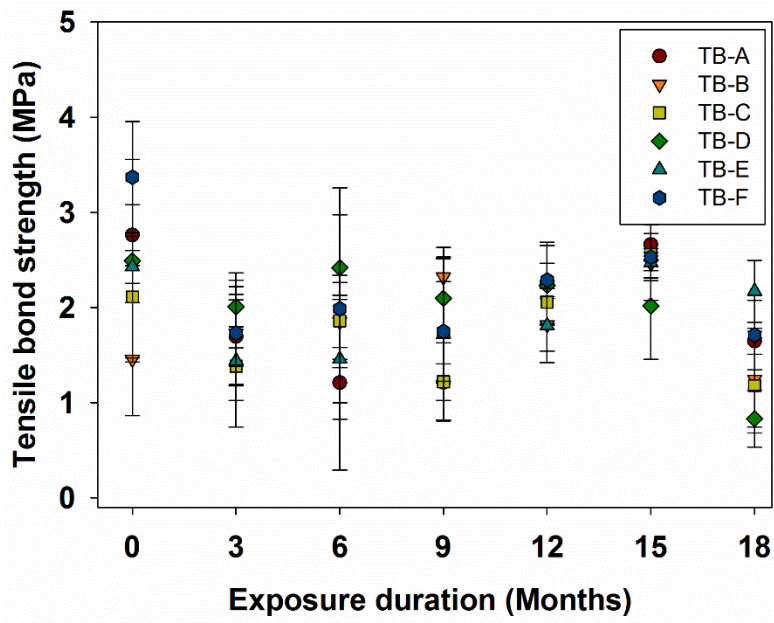


Fig. 18. Effect of tensile bond strength on the exposure duration

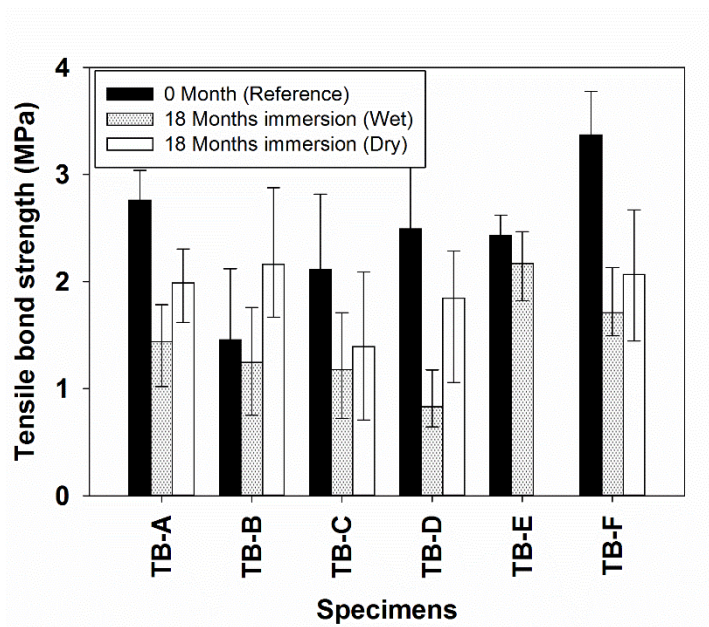


Fig. 19. The effect on tensile bond strength after 18 months of immersion and different testing condition (wet/dry)

0 month

18 months



Complete failure at concrete layer

Fig. 20. Comparison of typical failure mode before and after 18 months of exposure