

Dust and Soiling Issues and Impacts Relating to Solar Energy Systems: Literature Review Update for 2012-2015

Suellen C.S. Costa^{*}, Antonia Sonia A.C. Diniz^{*}, and Lawrence L. Kazmerski^{*,**,†}

^{*}Pontifícia Universidade Católica Minas Gerais (PUC Minas), Belo Horizonte, Brasil

^{**}Renewable and Sustainable Energy Institute (RASEI), a partnership between the University of Colorado Boulder, Boulder, Colorado & the National Renewable Energy Laboratory (NREL), Golden, Colorado ([†]*Corresponding author: solarpvkaz@gmail.com*)

Abstract

The purpose of this review survey is to provide a literature compilation, updating materials reported in several review papers on solar-device soiling and mitigation approaches published over the past 5 years. The focus is on the period 2013-2015, but an updated listing is also provided for the year 2012 for completeness. This literature review also provides the first update for a periodic, single collation report on such publications proposed in this journal two years ago. This review presents a listing of the publications, their publication source, and some brief tabulated information to help guide the reader into the focus of each of the works.

1. Introduction and Background

Soiling of solar collector surfaces ranks with climate conditions (temperature, humidity) and irradiance (spectrum, uniformity, intensity) as the major concerns for component and system reliability. Though R&D on soiling or dust accumulation has now spanned into its 8th decade, many mechanisms remain to be understood and problems to be solved. These needs are intensified by the growing markets in the solar-rich areas of the northern Africa, the Middle East, India, as well as the desert areas of China, Australia, and the United States. Coincidentally, these areas are also characterized by high airborne-particle environments, intense dust storms, and water-availability concerns.

The interests and critical nature of these soiling issues are reflected by the publication history, represented in the histogram of Fig. 1. The initial period includes contributions from the solar pioneers (Hottel, Woertz, Tomlinson, Garg – are among the leaders) who envisioned that avoiding soiling would be important for the future adoption and use of collectors for their solar-thermal applications. The coming of the oil embargo in the early- to mid-1970s brought a focus on solar energy and expanded terrestrial applications—with the rise in publications during this period primarily on the effects on heliostats and mirrors used with concentrating solar-thermal power (CSP). Political changes at the start of the 1980s (and the diminishing of energy costs/crises) resulted in a loss of funding and related publications in solar and dust issues. The 1990s heralded some shifts. First, the rise of market experiments (e.g., “1000-, 10,000-, 100,000-, million-roof programs” worldwide), large central-station CSP, and then the successes of space exploration, and some limited renewed funding for solutions to soiling reliability issues. There was, for example, a major rise in investments coming from the PV-powered NASA Mars rover (“Sojourner”)—which experienced extreme dust conditions with a remoteness that would not allow firsthand manual cleaning! This invigorated research into prevention approaches (coatings, vibration/ultrasonics, electrostatics, and especially electrodynamic screens) that would, in turn, reignite such high-tech remedies for earth-based systems as well.

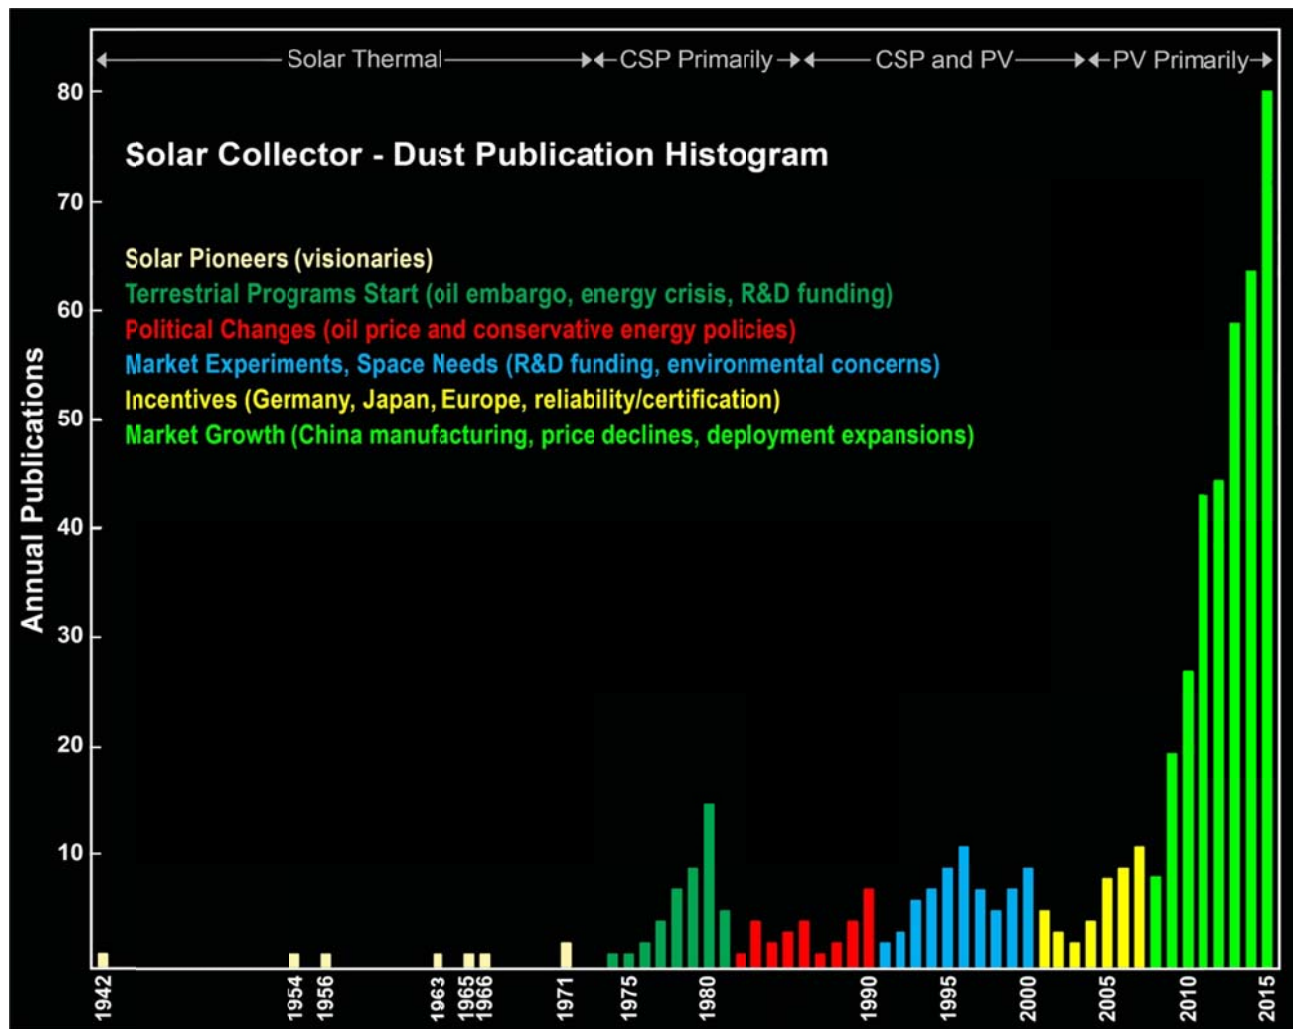


Figure 1. Histogram of publications on dust and soiling showing general technology emphasis and driving forces (colored regions) underlying the positive or negative growth of the publication levels. Recent rise in publication volume responds to the significant lowering of PV costs and opening of markets in the solar-rich and dust-environment-rich areas of the world.

The new century was marked by a growth in PV, both research and market expansions. This is attributed primarily to *incentive programs* such as the *feed-in tariffs* in Germany and Europe, and *system buy-down subsidies* in Japan and the U.S. Soiling research and product developments shifted as well toward PV because of the rise in applications and country programs. With the China dominance of manufacturing (and accompanying beneficial collapse in PV prices) starting in 2009/2010—as well as the rise in interest in new markets and investments in the desert locations (Saudi Arabia, Qatar, U.A.E. and other Gulf countries, Egypt, India, as well as the U.S., Australia, and China), the publications addressing dust and soiling issues rose to their highest annual levels; levels that can be expected to grow further because of the economic and energy benefits of dust mitigation for these solar-electric generators.

This survey follows on reference databases provided in several reviews that have been published on dust/soiling since 2010 (Table 1, discussed in the next section). It also builds on a commitment in a 2013 publication in this journal [see Tarver, et al. 2013 in Table 1] to provide a periodic update to the publication reference base, as a “living document” to afford readers,

researchers, developers, and system deployers with a literature base of research investments, product advancements, and latest research/advancements addressing of critical issues relating to this dust/soiling reliability area. This document covers the period 2013 through what has transpired through 2015. However, we have included a compilation, a more complete single listing for 2012—contained in the first section of the Literature Summary (References Section). The majority of these 2012-papers continue to cover the effect of soiling and dust accumulation on the performance of various solar technologies in various locations in the world. However, the focus of this literature review is on 2013-2015. In this period, we emphasize journal and conference publications that can be found through their “DOI” or web identifications—though some open-literature articles are also listed because of their content and interest.

2. Review Papers (2010-2015)

Several key review papers covering PV, CPV, and CSP dust and soiling have been published over the past few years, and all have fairly high citation indices indicative of their coverage, interest, and significance. These papers are summarized in Table 1, which provides the source authors, the publication year, a summary of the review contribution and focus, and the solar technology covered. This also gives the reference base cited in each. Certainly prominent among these is that in 2010 by M. Mani and R. Pillai, which summarized performance investigations, recommendations for mitigation of dust issues, and documented a useful and important categorization of climatic-zone influences for flat-panel and concentrating PV. This review paper ushered a series of other important contributions—each with a specific intent, area, and focus. These review papers provide a very useful basis for understanding the issues, what has been accomplished—from monitoring performance through mitigating the problems; from basic adhesion mechanisms to dust composition and morphology; from theory and modeling through experimental and measurement techniques; and from current comprehension to future research needs.

3. Discussion of Publications 2013-2015

The number of publications during this period continue the trend beginning in 2009—with a growing volume reflecting both the investment in research funding in reliability and in the incredible expansion of installations worldwide. Most of these are concerned with the effect of dust or soiling at various locations in the world. This remains an important contribution to the knowledge base for several reasons. First, this provides inputs to a growing interest in establishing a global encyclopedia of actual dust and soiling trends. Second, these data provide important information for installers and system holders. The information benefits range from assisting in better site location to establishing reasonable cleaning schedules that can be an immense benefit to the operation and maintenance costs for the PV systems. And finally, these studies provide a basis for collaboration among research and developers (e.g., for PV power plants) to address the issues of soiling and mitigation.

The publications also indicate some trends toward these concerns with mitigation. This spans the spectrum from *restoration* (cleaning with brushes, pressurized air/gas, wiping, and use of water and various solvents and hybrid methods) to higher-technology approaches based on superhydrophobic/superhydrophilic coatings and electrodynamic and electrostatic screens. Though some of the publications address CSP (mirrors, heliostats) and CPV, the overwhelming number of these are directed toward PV flat-plate technologies (reflecting the price benefits of this solar approach and the large number of investments in installations). Finally, some “special

reports of interest” are included at the end of the annual references. These are reports that include aspects of soiling or dust conditions, though the major focus of these pertain to other aspects of solar technology concerns.

Tables 2, 3, and 4 provide summaries of the research and development publications for the years 2013, 2014, and 2015 respectively. The corresponding references (provided in section 5. Literature Summary) have the “DOI” or internet access links wherever possible. The tables provide the geographical location and duration of the study (if appropriate), the technology addressed, the major results, and some related observations on the publication. Included at the end of the Literature Summary are several specialized reports and publications that include some higher level discussions of the importance of soiling issues to solar technology reliability. These range from “country programs” and professional organization reports/forecasts to specialized efforts at establishing solar device reliability/durability associated with specific climate or installation requirements.

Again, the primary purpose of this paper is to provide a “one-stop”, complete-as-possible reference listing of the publications for the period 2012 through 2015 (with 2015 having the highest number of annual publications to date) as an assistance to those involved with these soiling and dust issues for their own work.

4. Summary

This paper has provided an update of publications for the timeframe 2012-2015, guided by the proposal in the earlier review in this journal. This compilation builds on the reference basis provided in the review papers (Table 1) that have appeared in the past 5 years. It is acknowledged that there is a best-effort, knowing that with the extended literature and publication base in our multi-media world that some significant contributions are not included through this period to the end of 2015. Again, we ask the help of those working in this area to provide us with any publications that we have inadvertently missed. We do anticipate updating this compilation again for 2016, and annually thereafter.

Acknowledgements: *The authors would like to acknowledge the help of many of the authors of the publications listed in this compilation for providing information on their excellent contributions. This is especially true for the PVQAT group (which meets via webinar regularly) and helped to review this listing. The authors would also like to gratefully acknowledge the partial support of CAPES for part of this work through subcontract PVE11/14 under their “Pesquisa Visitante Estrangeiro” program, and to Ciência sem Fronteiras that supports the student and postdocs involved with our Brasil dust/soiling reliability project. The feedback and additions provided by many members of PVQAT have been extremely beneficial in building this database of publications. Finally, we acknowledge the help and assistance of the Solar Energy Institute for India and the United States (SERIUS), which maintains a strong leading research and development program in soiling and dust research and mitigation. This group is funded jointly by the United States Department of Energy and the India Office of Science and Technology in the Ministry of New and Renewable Energy.*

5. Literature Summary (References Presented by Year in Alphabetical Order)

The formatting for the following publications deviates from the conventional protocol for this journal. The reason is to provide an alphabetical listing by year—and resulting simplified

reference in the accompanying Tables 1-4 by first-author last name. The access to the publication is given by the “doi” or the web access identification. (Note that for a doi-designated paper access is gained in most cases by typing <http://dx.doi/xxx> in your search engine, where “xxx” is the series of numbers, letters, and symbols following “doi:” that is provided with the particular reference.)

2012

Bakirci, K., “General models for optimum tilt angles of solar panels: Turkey case study,” *Renewable and Sustainable Energy Reviews*, 16, 6149-6159 (2012). REVIEW
doi: [10.1016/j.rser.2012.07.009](https://doi.org/10.1016/j.rser.2012.07.009)

Beattie, N.S., R.S. Moir, C. Chacko, G. Buffoni, S.H. Roberts, and Nicola M. Pearsall, “Understanding the effects of sand and dust accumulation on photovoltaic modules,” *Renewable Energy* 48, 448-452 (2012).
doi: [10.1016/j.renene.2012.06.007](https://doi.org/10.1016/j.renene.2012.06.007)

Benatiallah, A., A. Mouly, F. Abidi, D. Benatiallah, A. Harrouz, and I. Mansouri, “Experimental study of dust effect in multi-crystal PV solar module,” *International Journal of Multidisciplinary Sciences and Engineering*, Vol. 3, No. 3 (2012).
<http://www.ijmse.org/Volume3/Issue3/paper1.pdf>

Brown K., T. Narum, and J. Naiyong, “Soiling test methods and their use in predicting performance of photovoltaic modules in soiling environments,” *Proceedings of the 38th IEEE Photovoltaic Special Conference (IEEE, New York; 2012)* p. 1881–5.
doi: [10.1109/PVSC.2012.6317960](https://doi.org/10.1109/PVSC.2012.6317960)

Caron, J.R., and B. Littmann, “Direct Monitoring of Energy Lost Due to Soiling on First Solar Modules in California,” *Proc. of the 38th IEEE Photovoltaic Specialists Conference*, Austin, TX (IEEE, New York; 2012).
doi: [10.1109/JPHOTOV.2012.2216859](https://doi.org/10.1109/JPHOTOV.2012.2216859)

Catelani, M., L. Ciani, L. Cristaldi, M. Faifer, M. Lassaroni, and M. Rossi, “Characterization of photovoltaic panels: The effects of dust,” *Proc. Energy Conf. and Exhibition-EnergyCON 2012* (IEEE, New York; 2012) pp. 49-50.
doi: [10.1109/EnergyCon.2012.6348198](https://doi.org/10.1109/EnergyCon.2012.6348198)

Chapuis, Valentin, Raphael Roth, Laure-Emmanuelle Perret-Aebi, Christophe Ballif, Hamid, Kayal, and Venkatachalam Lakshmanan, “Effect of soiling on performances of PV systems deployed in arid climates,” *Proc. European Photovoltaic Solar Energy Conf. (WIP, Germany; 2012)*.

Access:

<http://rakric.com/wp-content/uploads/2015/06/EFFECT-OF-SOILING-ON-PERFORMANCES-OF-PV-SYSTEMS-DEPLOYED-IN-ARID-CLIMATE.pdf>

Charabi Y, and A. Gastli, “Spatio-temporal assessment of dust risk maps for solar energy systems using proxy data.” *Renewable Energy* 44, 23–31 (2012).
doi: [10.1016/j.renene.2011.12.005](https://doi.org/10.1016/j.renene.2011.12.005)

Christo, F.C., “Numerical modeling of wind and dust patterns around a fullscale paraboloidal solar dish.” *Renewable Energy* 39. 356–66 (2012).

doi: [10.1016/j.renene.2011.08.038](https://doi.org/10.1016/j.renene.2011.08.038)

Cristaldi, L., M. Faifer, and M. Rossi, "Economical evaluation of PV system losses due to the dust and pollution," Proc. Energy Conf. and Exhibition-EnergyCON 2012 (IEEE, New York; 2012) pp. 614-618.

doi: [10.1109/I2MTC.2012.6229521](https://doi.org/10.1109/I2MTC.2012.6229521)

Ebert, D., and B. Bhushan, "Transparent, superhydrophobic, and wear-resistant coatings on glass and polymer substrates using SiO₂, ZnO, and ITO nanoparticles," Langmuir 28, 11391-11399 (2012).

doi: [10.1021/la301479c](https://doi.org/10.1021/la301479c)

Hee, J.Y., L.V. Kumar, A.J. Danner, H. Yang, and C.S. Bhatia, "The effect of dust on transmission and self-cleaning property of solar panels," Energy Proc. 15, 421-427 (2012).

doi: [10.1016/j.egypro.2012.02.051](https://doi.org/10.1016/j.egypro.2012.02.051)

Kazem, Hussein A., M.T. Chaichan, I.M. Al-Shezawi, H.S. Al-Saidi, H.S. Al-Rubkhi, J.K. Al-Sinani, and A.H.A. Al-Waeli, "Effect of Humidity on the PV Performance in Oman," Asian Transactions on Engineering 2, 29-32 (2012a).

Access:

https://www.researchgate.net/publication/257840932_Effect_of_Humidity_on_the_PV_Performance_in_Oman

Kazem, Hussein A., Said Al-Bahri, Saud Al-Badi, Haifa Al- Mahkladi, and Ali H A Al-Waeli, "Effect of Dust on Photovoltaic Performance," Proc. International Conference on Frontiers of Mechanical Engineering, Materials and Energy (ICFMEME 2012), pp. 1-4, December 2012b.

doi: [10.4028/www.scientific.net/AMR.875-877.1908](https://doi.org/10.4028/www.scientific.net/AMR.875-877.1908)

Kumar, Shobhit, and P.B.L. Chaurasia, "Experimental Study on the Effect of Dust Deposition on Solar Photovoltaic Panel in Jaipur (Rajasthan)," Internl. J. Sci. and Res. 3, 1690-1693 (2012).

ISSN (Online): 2319-7064; Paper ID: 02014532

Liqun, L., L. Zhiqi, and S.Z.L. Chunxia, "Degraded output characteristic at atmospheric air pollution and economy analysis of PV power system: a case study," Przegł. Elektrotech. (Electr. Rev.) 88 (9A), 281-284 (2012).

ISSN 0033-2097, R. 88 NR 9a/2012

Sun, Q., N. Yang, X. Cai, G. Hu, "Mechanism of dust removal by a standing wave electric curtain," Sci. China Phys., Mech. Astron. 55(6), 1018-1025 (2012).

doi: [10.1007/s11433-012-4722-9](https://doi.org/10.1007/s11433-012-4722-9)

Mekhilef, S., R. Saidur, and M. Kamalisarvestani, "Effect of dust, humidity and air velocity on efficiency of photovoltaic cells," Renewable and Sustainable Energy Reviews 16, 2920-2925 (2012).

REVIEW

doi: [10.1016/j.rser.2012.02.012](https://doi.org/10.1016/j.rser.2012.02.012)

Mohamed A.O., and A. Hasan, "Effect of dust accumulation on performance of photovoltaic solar modules in Sahara environment," Journal of Basic and Applied Scientific Research 2(11), 11030-6 (2012). ISSN 2090-4304

Access:

<http://rollingwash.net/docs/Effect%20of%20Dust%20Accumulation%20on%20PV%20Solar%20Modules%20in%20Sahara%20Environment.pdf>

Niknia, I., M. Yaghoubi, and R. Hessami, "A novel experimental method to find dust deposition effect on the performance of parabolic trough collectors," *International J. Environ. Studies* 69, 233-252 (2012).

doi: [10.1080/00207233.2012.664810](https://doi.org/10.1080/00207233.2012.664810)

Qassem H, H. AlBusairi, T.R. Betts, and R. Gottschaig, "Measurements of dust-induced performance losses on micromorph photovoltaic modules in Kuwait," *Proceedings of the European Photovoltaic Solar Energy Conference - Frankfurt*, (WIP, Germany; 2012).

doi: [10.4229/27thEUPVSEC2012-4CO.10.6](https://doi.org/10.4229/27thEUPVSEC2012-4CO.10.6)

Qasem H., T.R. Betts, H. Müllejans, H. AlBusairi, and R. Gottschalg, "Dust induced shading on photovoltaic modules," *Progress in Photovoltaics* 22(2), 218-226 (2012).

doi: [10.1002/pip.2230](https://doi.org/10.1002/pip.2230).

Qian D., J.S. Marshall, and J. Frolik, "Control analysis for solar panel dust mitigation using an electric curtain," *Renewable Energy* 41, 134-44 (2012).

doi: [10.1016/j.renene.2011.10.014](https://doi.org/10.1016/j.renene.2011.10.014)

Rahman M., A. Islam, A.H.M. Zadidul Karim, and A.H. Ronee, "Effects of natural dust on the performance of PV panels in Bangladesh," *International Journal of Modern Education and Computer Science* 4, 26-32 (2012).

doi: [10.5815/ijmecs.2012.10.04](https://doi.org/10.5815/ijmecs.2012.10.04)

Sanchez D., P. Trujillo, M. Martinez, J.P. Ferrer, and F. Rubio, "CPV performance versus soiling effects: cleaning policies," *AIP-Proceedings of the 8th international conference on concentrating photovoltaic systems*, Vol. 1477 p. 3480351 (2012).

doi: [10.1063/1.4753902](https://doi.org/10.1063/1.4753902)

Sanusi Y.K., "The performance of amorphous silicon PV system under Harmattan dust conditions in a tropical area," *Pacific Journal of Science and Technology* 13(1), 168-75 (2012).

<http://www.akamaiuniversity.us/PJST.htm>

Siddiqui R., and U. Bajpai, "Deviation in the performance of solar module under climatic parameter as ambient temperature and wind velocity in composite climate," *International Journal of Renewable Energy Research* 2(3), 486-90 (2012).

<http://ijrer.org/ijrer/index.php/ijrer/article/viewFile/277/pdf>

Siddiqui R., and U. Bajpai, "Correlation between thicknesses of dust collected on photovoltaic module and difference in efficiencies in composite climate," *International Journal of Energy and Environmental Engineering* 3, 1-7 (2012).

doi: [10.1186/2251-6832-3-26](https://doi.org/10.1186/2251-6832-3-26)

Sharma, V., and S. Bowden, "Peak load offset and the effect of dust storms on 10MWp distributed grid tied photovoltaic systems installed at Arizona State University," *Proc. 38th IEEE Photovoltaic Spec. Conf. (IEEE, New York; 2012)* pp. 590-95.

doi: [10.1109/PVSC.2012.6317682](https://doi.org/10.1109/PVSC.2012.6317682)

Schill, C., S. Bachmann, M. Heck, K.-A. Weiss, and M. Koehl, "Impact of heavy soiling on the power output of PV modules," Proc. SPIE (SPIE, Bellingham, WA; 2012) pp. 8112-9.
doi: [10.1117/12.893721](https://doi.org/10.1117/12.893721)

Slamova K., R. Glaser, C. Schill, S. Wiesmeier, and M. Köhl, "Mapping atmospheric corrosion in coastal regions: methods and results," Journal of Photonics for Energy 2, 022003-1–9 (2012).
doi: [10.1117/1.JPE.2.022003](https://doi.org/10.1117/1.JPE.2.022003)

Sorloaica-Hickman, N., J. McFall, S. Nason, K. Davis, and E. Arens, "Optimization of the photovoltaic powered systems with dust mitigation technology for future lunar and martian missions," Proc. 38th IEEE Photovoltaic Spec. Conf. (IEEE, NY; 2012) pp. 02815-02818.
doi: [10.1109/PVSC.2012.6318177](https://doi.org/10.1109/PVSC.2012.6318177)

Sun, Q.X., N.N. Yang, Z.K. Xiao, X. Cai, and G. Hu, (2012) "Experimental Study on Efficiency of Dust Removal by Standing Wave Electric Curtain," Spacecraft Engineering 21, 72-79 (2012).
http://en.cnki.com.cn/Article_en/CJFDTOTAL-HTGC201203017.htm

Sun, Q.X. N.Yang, X. Cai, and G. Hu, "Advance in Lunar Surface Dust Removal Method by Electrodynamic Field," Advances in Mechanics 42, 785-803 (2012).
doi: [10.6052/1000-0992-12-054](https://doi.org/10.6052/1000-0992-12-054)

Stridh, B. "Evaluation of economical benefit of cleaning of soiling and snow in PV plants at three European locations," Proc. IEEE Photovoltaic Spec. Conf. (IEEE, New York; 2012) pp. 1448-1451.
doi: [10.1109/PVSC.2012.6317869](https://doi.org/10.1109/PVSC.2012.6317869)

Touati, F., M. Al-Hitmi, and H. Bouchech, "Towards understanding the effects of climatic and environmental factors on solar PV performance in arid desert regions (Qatar) for various PV technologies," Proc. of the Renewable Energies and Vehicular Technologies (REVET), March 2012, pp 26-28.
doi: [10.1109/REVET.2012.6195252](https://doi.org/10.1109/REVET.2012.6195252)

Wolfertstetter, F., K. Pottler, A.A. Merrouni, A. Mezrhab, and R. Pitz-Paal, "A Novel method for automatic real-time monitoring of mirror soiling rates," Proc. SolarPACES- Marrakesch (2012).
http://www.researchgate.net/publication/236033074_A_Novel_Method_for_Automatic_Real-Time_Monitoring_of_Mirror_Soiling_Rates

2013

Adinoyi, M.J., and S.A. Said, "Effect of dust accumulation on the power outputs of solar photovoltaic modules." *Renew. Energy* 60, 633–636 (2013).

doi: [10.1016/j.renene.2013.06.014](https://doi.org/10.1016/j.renene.2013.06.014)

Ahmed Darwish, Zeki, Hussein A. Kazem, and K. Sopian, "Effect of dust on photovoltaic performance: Review and research status," in *Latest Trends in Renewable Energy and Environmental Informatics, Proc. 7th International Conference on Renewable Energy Sources (RES '13) and 1st International Conference on Environmental Informatics (ENINF '13)* (Wseas LLC; 2013a) REVIEW

ISBN: 1618041754, 9781618041753

Access: <http://www.wseas.us/e-library/conferences/2013/Malaysia/RESEN/RESEN-32.pdf>

Ahmed Darwish, Zeki, Hussein A. Kazem, K. Sopian, M.A. Alghoul, and Miqdam T. Chaichan, "Impact of Some Environmental Variables with Dust on Solar Photovoltaic (PV) Performance: Review and Research Status," *International J. of Energy and Environment* 7, 152-159 (2013b).
[http://www.researchgate.net/publication/258051333_Impact_of_Some_Environmental_Variables_with_Dust_on_Solar_Photovoltaic_\(PV\)_Performance_Review_and_Research_Status](http://www.researchgate.net/publication/258051333_Impact_of_Some_Environmental_Variables_with_Dust_on_Solar_Photovoltaic_(PV)_Performance_Review_and_Research_Status)

Al-Ammri, A.S., A. Ghazi, and F. Mustafa, "Dust effects on the performance of PV street lights in Baghdad City," *Proc. Renewable and Sustainable Energy Conference (IRSEC), 2013 International*, 18–22, 2013.

doi: [10.1109/IRSEC.2013.6529687](https://doi.org/10.1109/IRSEC.2013.6529687)

Al-Sabounchi, Ammar M., Saeed A. Yalyali, and Hamda A. Al-Thani, "Design and performance evaluation of a photovoltaic grid-connected system in hot weather conditions," *Renewable Energy* 53, 71-78 (2013).

doi: [10.1016/j.renene.2012.10.039](https://doi.org/10.1016/j.renene.2012.10.039)

Appels, Reinhart, Buvaneshwari Lefevre, Bert Herteleer, Hans Goverde, Alexander Beerten, Robin Paesen, Klaas De Medts, Johan Driesen, and Jef Poortmans, "Effect of soiling on photovoltaic modules," *Solar Energy* 96, 283–91 (2013).

doi: [10.1016/j.solener.2013.07.017](https://doi.org/10.1016/j.solener.2013.07.017)

Awwad, R., M. Shehadeh, and A. Al-Salaymeh, "Experimental investigation of dust effect on the performance of photovoltaic systems in Jordan," *Proc. GCREEDER 2013, Amman, Jordan*, (Academia.edu; 2013) pp. 1-4.

http://www.academia.edu/5486676/Rund_Awwad_PV_Dust_Effect_Paper_Jordan_2013

Bai, Y., B. Kokanos, and G.G. Karady, "Performance of a residential PV system in the desert southwest," *Proc. 2013 IEEE Power and Energy Society General Meeting (PES), (IEEE, NY; 2013)* pp. 1–5.

doi: [10.1109/PESMG.2013.6672248](https://doi.org/10.1109/PESMG.2013.6672248)

Bao Guan-jun, Lin-wei Zhang, Shi-bo Cai, Jian-dong Jiang, Fang Xv, and Gui-hong Jia, "Review on dust depositing on PV module and cleaning techniques," *Journal of Mechanical & Electrical Engineering* 8 (2013). REVIEW

TM615;;TK513.3;TM925.31

Access: http://en.cnki.com.cn/Article_en/CJFDTotal-JDGC201308004.htm

Bi, X., S. Liang, and X. Li, "A novel in-situ method for sampling urban soil dust: particle size distribution, trace metal concentrations, and stable lead isotopes," *Environ. Pollution* 177, 48-57 (2013).
[doi: 10.1016/j.envpol.2013.01.045](https://doi.org/10.1016/j.envpol.2013.01.045)

Boyle, L., H. Flinchpaugh, and M. Hannigan, "Impact of natural soiling on the transmission of PV cover plates," *Proc. 39th IEEE Photovoltaic Specialists Conference*, (IEEE, NY; 2013) pp. 3276–78.
[doi: 10.1109/PVSC.2013.6745150](https://doi.org/10.1109/PVSC.2013.6745150).

Brooks, A.E., D.N. DellaGiustina, S.M. Patterson, and A.D. Cronin, "The consequence of soiling on PV system performance in Arizona; Comparing three study methods," *Proc. 39th IEEE Photovoltaic Specialists Conference*, (IEEE, NY; 2013) pp. 754–58.
[doi: 10.1109/PVSC.2013.6744259](https://doi.org/10.1109/PVSC.2013.6744259).

Canada, Scott, "Quality assurance: Impact of soiling on utility-scale PV system performance," *SolarPro Magazine*, Issue 6.3, April/May 2013.
<http://solarprofessional.com/articles/operations-maintenance/impacts-of-soiling-on-utility-scale-pv-system-performance>

Caron, R.J. and B. Littmann, "Direct monitoring of energy lost due to soiling on First Solar modules in California," *Proc. 39th IEEE Photovoltaic Spec. Conf.* (IEEE, New York; 2013). Also, published in *IEEE J. Photovoltaics*, 3, 336-340 (2013).
[doi: 10.1109/JPHOTOV.2012.2216859](https://doi.org/10.1109/JPHOTOV.2012.2216859)

Charabi, Y. and A. Gastli, "Integration of temperature and dust effects in siting large PV power plant in hot arid area," *Renewable Energy* 57, 635-644 (2013).
[doi: 10.1016/j.renene.2013.02.031](https://doi.org/10.1016/j.renene.2013.02.031)

Dastoori, K., G. Al-Shabaan, M. Kolhe, D. Thompson, and B. Makin, "Charge Measurement of Dust Particles on Photovoltaic Module," *Proceedings of the 8th International Symposium on Advanced Topics in Electrical Engineering* (IEEE, New York; 2013) pp. 1-4
[doi: 10.1109/ATEE.2013.6563411](https://doi.org/10.1109/ATEE.2013.6563411)

Della-Giustina, Daniella, Adria Brooks, Michael St. Germaine, Scott Patterson, and Alexander Cronin, "Characterization and use of a Sinton FMT-350 flash tester at the Tucson Electric Power solar test yard," *Renewable Energy and the Environment, RW2D.4. OSA Technical Digest* (online). Optical Society of America, (2013).
[doi: 10.1364/OSE.2013.RW2D.4](https://doi.org/10.1364/OSE.2013.RW2D.4).

Dunn, L., B. Littmann, J.R. Caron, and M. Gostein, "PV module soiling measurement uncertainty analysis," *Proc. 39th Photovoltaic Specialists Conference* (IEEE, NY; 2013) pp. 658–63.
[doi: 10.1109/PVSC.2013.6744236](https://doi.org/10.1109/PVSC.2013.6744236).

El-Din, A.M.A.M.S., A.K. Abel-Rahman, A.H.H. Ali, and S. Ookawara, "Effect of dust deposition on performance of thin film photovoltaic module in harsh humid climate," *Proc. 2013 International Conference on Renewable Energy Research and Applications (ICRERA)*, pp. 674–79 (2013).
[doi: 10.1109/ICRERA.2013.6749839](https://doi.org/10.1109/ICRERA.2013.6749839).

Ghazi, Sanaz, Kenneth Ip, and Ali Sayigh, "Preliminary study of environmental solid particles on solar flat surfaces in the UK," *Energy Procedia, Mediterranean Green Energy Forum 2013, Proc. of an International Conference MGEF-13*, 42 (2013), pp. 765–74 (2013).

doi: [10.1016/j.egypro.2013.11.080](https://doi.org/10.1016/j.egypro.2013.11.080).

Gostein, M., B. Littmann, J.R. Caron, and L. Dunn, "Comparing PV power plant soiling measurements extracted from PV module irradiance and power measurements," *Proc. 39th IEEE Photovoltaic Specialists Conference (IEEE, NY; 2013)* pp. 3004–9.

doi: [10.1109/PVSC.2013.6745094](https://doi.org/10.1109/PVSC.2013.6745094).

Gottschalg, R., T.R. Betts, A. Eeles, S.R. Williams, and J. Zhu, "Influences on the energy delivery of thin film photovoltaic modules," *Sol. Energy Mat. and Solar Cells* 119, 169-180 (2013).

doi: [10.1016/j.solmat.2013.06.011](https://doi.org/10.1016/j.solmat.2013.06.011).

Hirohata, Takuya, Yasuyuki Ota, and Kensuke Nishioka, "Effect of anti-soiling coating on performance of Fresnel lens for concentrator photovoltaic module," *Applied Mechanics and Materials* 372, 575–78 (2013).

doi: [10.4028/www.scientific.net/AMM.372.575](https://doi.org/10.4028/www.scientific.net/AMM.372.575).

Horenstein, Mark N., Malay Mazumder, and Robert C. Summers, Jr., "Predicting particle trajectories on an electrodynamic screen – Theory and experiment," *J. of Electrostatics* 71, 185-188 (2013).

doi: [10.1016/j.elstat.2012.10.005](https://doi.org/10.1016/j.elstat.2012.10.005)

John, J.J., M.C. Raval, A. Kottantharayil, and C.S. Solanki, "Novel PV module cleaning system using ambient moisture and self-cleaning coating," *Proc. 39th IEEE Photovoltaic Spec. Conf. (IEEE, NY; 2013)* pp. 1481–83.

doi: [10.1109/PVSC.2013.6744425](https://doi.org/10.1109/PVSC.2013.6744425).

Kalogirou, Soteris A., Rafaela Agathokleous, and Gregoris Panayiotou, "On-site PV characterization and the effect of soiling on their performance," *Energy* 51, 439-46 (2013).

doi: [10.1016/j.energy.2012.12.018](https://doi.org/10.1016/j.energy.2012.12.018).

Kawamoto, H., and T. Shibata, "Electrostatic cleaning system for removal of sand from solar panels," *Proc. 39th IEEE Photovoltaic Specialists Conference (PVSC)*, 16–21 June. Tampa, FL, (IEEE, New York; 2013) pp. 0094–0098.

doi: [10.1109/PVSC.2013.6744107](https://doi.org/10.1109/PVSC.2013.6744107)

Kazem, H.A., T. Khatib, K. Sopian, F. Buttinger, W. Elmenreich, and A.S. Albsaidi, "Effect of dust deposition on the performance of multi-crystalline photovoltaic modules based on experimental measurements," *International J. Renewable Energy Research* 3, 850-853 (2013).

<http://www.ijrer.com/index.php/ijrer/article/viewFile/876/pdf>

Klimm, E., T. Lorenz, and K.-A. Weiss, "Can anti-soiling coating on solar glass influence the degree of performance loss over time of PV modules drastically?" *Proc. 28th European PV Solar Energy Conf., Paris (WIP, Berlin; 2013)*.

<https://www.ise.fraunhofer.de/de/veroeffentlichungen/konferenzbeitraege/konferenzbeitraege-2013/28th-eupvsec/klimm.pdf>

Kumar, E. Suresh, D. Bijan Sarkar, and D.K. Behera, "Soiling and dust impact on the efficiency and the maximum power point in the photovoltaic modules," *International Journal of Engineering Research & Technology* 2, 1-8 (2013).

ISSN: 2278-0181

Also, ESRA Publications, Vol. 2, Issue 2 (February, 2013).

<http://www.ijert.org/view.php?id=2295&title=soiling-and-dust-impact-on-the-efficiency-and-the-maximum-power-point-in-the-photovoltaic-modules>.

Leviton, David, "Is anything stopping a truly massive build-out of desert solar power?" *Scientific American*, July 1, 2013.

<http://www.scientificamerican.com/article/challenges-for-desert-solar-power/>

Marion, B. R., Schaefer, H. Caine, and G. Sanchez, "Measured and modeled photovoltaic system energy losses from snow for Colorado and Wisconsin locations," *Solar Energy* 97, 112-121 (2013).

doi: 10.1016/j.solener.2013.07.029

Massi Pavan, A., A. Mellit, D. De Pieri, and S.A. Kalogirou, "A comparison between BNN and regression polynomial methods for the evaluation of the effect of soiling in large scale photovoltaic plants." *Applied Energy* 108, 392–401 (2013).

doi: 10.1016/j.apenergy.2013.03.023.

Mejia, Felipe A., and Jan Kleissl, "Soiling losses for solar photovoltaic systems in California." *Solar Energy* 95, 357–63 (2013).

doi: 10.1016/j.solener.2013.06.028.

Midtdal, K. and B.P. Jelle, "Self-cleaning glazing products: a state-of-the-art review and future research pathways." *Solar Energy Mater. Solar Cells* 109, 126-141 (2013). REVIEW

doi: 10.1016/j.solmat.2012.09.034

Moharram, K.A., M.S. Abd-Elhady, H.A. Kandil, and H. El-Sherif, 2013. Influence of cleaning using water and surfactants on the performance of photovoltaic panels. *Energy Conversion Management* 68 (0), 266–272.

doi: 10.1016/j.enconman.2013.01.022

Ndiaye, A.C., M.F. Kébé, P.A. Ndiaye1, A. Charki, A. Kobi, and V. Sambou, "Impact of dust on the photovoltaic (PV) modules characteristics after an exposition year in Sahelian environment: The case of Senegal." *Intl. J. Phys. Sci.* 8, 1166-73 (2013)

doi: 10.5897/IJPS2013.3921

Piliouguine, M., C. Cañete, R. Moreno, J. Carretero, J. Hirose, S. Ogawa, and M. Sidrach-de-Cardona, "Comparative analysis of energy produced by photovoltaic modules with anti-soiling coated surface in arid climates," *Applied Energy* 112, 626–34 (2013).

doi: 10.1016/j.apenergy.2013.01.048.

Qasem, H., T. R. Betts, and R. Gottschalg, "Spatially-resolved modelling of dust effect on cadmium telluride photovoltaic modules," *Solar Energy* 90, 154–63 (2013).

doi: 10.1016/j.solener.2013.01.013.

Qasem, Hassan, "Effect of accumulated dust on the performance of photovoltaic modules." Ph.D Thesis, 2013. **THESIS**
<https://dspace.lboro.ac.uk/dspace-jspui/handle/2134/11735>.

Rajput, D.S., and K. Sudhakar, "Effect of dust on the performance of solar PV panel," International J. ChemTech Research 5, 1083-1086 (2013).
ISSN: 0974-4290; Also
https://www.researchgate.net/profile/K_Sudhakar/publication/235929242_Effect_Of_Dust_On_The_Performance_Of_Solar_PV_Panel/links/00b7d5145c8d878786000000.pdf

Rao A., R. Pillai, M. Mani, and P. Ramamurthy, "An experimental investigation into the interplay of wind, dust and temperature on photovoltaic performance in tropical conditions," Proceedings of the 12th International Conference on Sustainable Energy Technologies; pp. 2303-2310 (2013).

Sabah, K., and S.N. Faraj, "Self-cleaning solar panels to avoid the effects of accumulated dust on solar panes transmittance," International Journal of Science and Research 2, 246-7 (2013).
ISSN: 2319-7064; Also <http://www.ijsr.net/archive/v2i9/MTIwOTEzMDU=.pdf>

Santana-Rodríguez, G, O. Vigil-Galan, D. Jimenez-Olarte, G. Contreras-Puente, B.M. Monroy, and A. Escamilla-Esquivel, "Evaluation of a grid-connected photovoltaic system and in-situ characterization of photovoltaic modules under the environmental conditions of Mexico City," *Revista Mexicana de Fisica*, 59, 88–94 (2013).
PACS: 725.40.+w; 78.56.-a; 87.61.Ff

Sarver, Travis, Ali Al-Qaraghuli, and Lawrence L. Kazmerski, "A comprehensive review of the impact of dust on the use of solar energy: History, investigations, results, literature, and mitigation approaches," Renewable and Sustainable Energy Reviews 22, 698-733 (2013).
REVIEW
doi: [10.1016/j.rser.2012.12.065](https://doi.org/10.1016/j.rser.2012.12.065)

Sayyah, A., M.N. Horenstein, and M.K. Mazumder, "Mitigation of soiling losses in concentrating solar collectors," Proc 39th IEEE Photovoltaic Specialists Conference (IEEE, NY: 2013) pp. 480–85.
doi: [10.1109/PVSC.2013.6744194](https://doi.org/10.1109/PVSC.2013.6744194).

Schaeffer, D. A., P. G. Datskos, S. R. Hunter, S. Rajic, J. K. Sharma, and G. Polizos, "Large area transparent superhydrophobic coatings," IEEE Future of Instrumentation International Workshop (IEEE, New York; 2013).
http://www.researchgate.net/profile/Daniel_Schaeffer/publication/259383677_Large_Area_Transparent_Superhydrophobic_Coatings/links/0046352b496d98edec000000.pdf

Sharma V, and S.S. Chandel, "Performance and degradation analysis for long-term reliability of solar photovoltaic system: a review," Renewable Sustainable Energy Reviews 2013; 27:753-767.
REVIEW
doi: [10.1016/j.rser.2013.07.046](https://doi.org/10.1016/j.rser.2013.07.046)

Sueto, Tsuyoshi, Yasuyuki Ota, and Kensuke Nishioka, "Suppression of dust adhesion on a concentrator photovoltaic module using an anti-soiling photocatalytic coating," Solar Energy 97, 414–17 (2013).
doi: [10.1016/j.solener.2013.09.006](https://doi.org/10.1016/j.solener.2013.09.006).

Smith, Matthew K., Carl C. Wamser, Keith E. James, Seth Moody, David J. Sailor, and Todd N. Rosensteil, "Effects of natural and manual cleaning on photovoltaic output," *Journal of Solar Energy Engineering* 135, 034505–034505 (2013).

doi: [10.1115/1.4023927](https://doi.org/10.1115/1.4023927)

Touati, F., M.A. Al-Hitmi, and H.J. Boucheck, "Study of the effects of dust, relative humidity, and temperature on solar PV performance in Doha: Comparison between monocrystalline and amorphous PVs," *International J. Green Energy* 10, 680-689 (2013a).

doi: [10.1080/15435075.2012.692134](https://doi.org/10.1080/15435075.2012.692134)

Touati, F., A. Massoud, J. Abu Hamad, and S.A. Saeed, "Effects of environmental and climatic conditions on PV efficiency in Qatar," *Proc. International Conference on Renewable Energies and Power Quality (ICRE PQ'13)*, 20–22 March 2013, Bilbao, Spain, pp. 275–281 (2013b).

ISSN 2172-038 X; Also <http://large.stanford.edu/courses/2013/ph240/alshakhs2/docs/275-touati.pdf>

Tylim, A., "The importance of a PV system washing program," *Renewable Energy World*, 11, Nov. 29 (2013).

<http://www.renewableenergyworld.com/articles/2013/11/the-importance-of-a-pv-system-washing-program.html>

doi: [10.1080/10584587.2014.903135](https://doi.org/10.1080/10584587.2014.903135)

Wang, J., Y. Li, X. Liang, and Y. Liu, "Research of adhesion force between dust particles and insulator surface using atomic force microscope," *High Voltage Engineering* 39, 1352–1359 (2013).

doi: [10.3969/j.issn.1003-6520.2013.06.010](https://doi.org/10.3969/j.issn.1003-6520.2013.06.010)

Yadav, N.K., D. Pala, and L. Chandra, "On the understanding and analyses of dust deposition on heliostat," *Energy Procedia* 57, 3004-3013(2013).

doi: [10.1016/j.egypro.2014.10.336](https://doi.org/10.1016/j.egypro.2014.10.336)

Zhou, C.D., G.F.He, J. Zhang, Z. Li, and X. Deng, "Research on the motion pattern of dust particles and self-cleaning mechanism of solar cells under traveling-wave electric curtain," *Journal of Hebei University of Science and Technology*, 34, 27-32 (2013).

Access: http://en.cnki.com.cn/Article_en/CJFDTOTAL-HBQJ201302001.htm

Zorrilla-Casanova, J., M. Piliougine, J. Carretero, P. Bernaola-Galván, P. Carpena, L. Mora-López, and M. Sidrach-de-Cardona, "Losses produced by soiling in the incoming radiation to photovoltaic modules," *Progress in Photovoltaics: Research and Applications* 21, 790-796 (2013).

doi: [10.1002/pip.1258](https://doi.org/10.1002/pip.1258)

2014

Abrams, Ze'ev R., Peter Gonsalves, Brenor Brophy, and Jean Posbic, "Field and lab verification of hydrophobic anti-reflective and anti-soiling coatings on photovoltaic glass," Proc. European PV Solar Energy Conference (WIP, Germany; 2014). 5BV.1.50
http://enkitech.com/wp-content/uploads/2015/09/5BV.1.50_EUPVSEC-2014.pdf

Amarnadh T.G., Akshay Gupta, and Vijay Shyam, "Investigation of the effects of dust accumulation, and performance for mono and poly crystalline silica modules," Internl. J. Renewable Energy Research 4 (2014)
<http://www.ijrer.org/ijrer/index.php/ijrer/article/view/1390/0>

Al-Jawah, Mohammad J., Ph.D. Thesis, "Decision Aiding Framework for Investing in Cleaning Systems for Solar Photovoltaic (PV) Power Plants in Arid Regions," The George Washington University, Washington, DC (2014) **THESIS**
ISBN: 9781303575860

Anshir Bashir, M., H.M. Ali, S. Khalil, M. Ali, and A.M. Siddiqui, "Comparison of performance measurements of photovoltaic modules during winter months in Taxila, Pakistan," International Journal of Photoenergy 2014, 1-8 (2014)
doi: 10.1155/2014/898414

Boyle, Liza, Holly Flinchpaugh, and Mike Hannigan. "Ambient airborne particle concentration and soiling of PV cover plates," Proc. 40th IEEE Photovoltaic Specialist Conference, (IEEE, NY; 2013), pp. 3171–73.
doi: 10.1109/PVSC.2014.6925609

Burton, P.D., and B.H. King, "Application and characterization of an artificial grime for photovoltaic soiling studies," IEEE Journal of Photovoltaics 4, 299-303 (2014a).
doi: 10.1109/JPHOTOV.2013.2270343

Burton, P.D., and B.H. King, "Spectral sensitivity of simulated photovoltaic module soiling for a variety of synthesized soil types," IEEE Journal of Photovoltaics 4, 890-98 (2014b).
doi: 10.1109/JPHOTOV.2014.2301895

Burton, Patrick D., and Bruce H. King, "Determination of a minimum soiling level to affect photovoltaic devices," Proc. 40th IEEE Photovoltaic Specialist Conference (IEEE, NY; 2014c) pp. 193–97.
doi: 10.1109/PVSC.2014.6925529

Butuza, Andrei, "Reference selection procedure for studying the soiling effect on PV performance," *Acta Techna Napocencis - Series: APPLIED MATHEMATICS, MECHANICS, and ENGINEERING* 57, no. 1 (2014). REVIEW
<http://atna-mam.utcluj.ro/index.php/Acta/article/view/182>

Cano, Jose, Jim Joseph John, Sai Tatapudi, and GovindaSamy TamizhMani, "Effect of tilt angle on soiling of photovoltaic modules," Proc. 40th IEEE Photovoltaic Specialist Conference, (IEEE, NY; 2014) pp. 3174–76.
doi: 10.1109/PVSC.2014.6925610

Chamaria, P., A. Dube, M. Ruchika, and A.P. Mittal, “Consequences of dust on solar photovoltaic module and its generation,” Proc. International Conf. on Power Electronics (IICPE) (IEEE, New York; 2014).

doi: [10.1109/IICPE.2014.7115776](https://doi.org/10.1109/IICPE.2014.7115776)

Cristaldi, Loredana, Marco Faifer, Marco Rossi, Sergio Toscani, Marcantonio Catelani, Ciani, Lorenzo, and Massimo Lazzaroni, “Simplified method for evaluating the effects of dust and aging on photovoltaic panels,” Measurement 54, 207–14 (2014).

doi: [10.1016/j.measurement.2014.03.001](https://doi.org/10.1016/j.measurement.2014.03.001)

Fernández-García, A., L. Álvarez-Rodrigo, L. Martínez-Arcos, R. Aguiar, and J.M. Mårtinez-Payés, “Study of different cleaning methods for solar reflectors used in CSP plants,” Energy Procedia 49, 80-89 (2014).

doi: [10.1016/j.egypro.2014.03.009](https://doi.org/10.1016/j.egypro.2014.03.009)

Ghazi, Sanaz, Ali Sayigh, and Kenneth Ip, “Dust effect on flat surfaces—A review paper,” Renewable and Sustainable Energy Reviews 33, 742-51 (2014). REVIEW

doi: [10.1016/j.rser.2014.02.016](https://doi.org/10.1016/j.rser.2014.02.016)

Gostein, Michael, J. Riley Caron, and Bodo Littmann, “Measuring soiling losses at utility-scale PV power plants,” Proc. 40th IEEE Photovoltaic Specialist Conference (IEEE, NY; 2014) pp. 885–90.

doi: [10.1109/PVSC.2014.6925056](https://doi.org/10.1109/PVSC.2014.6925056)

Griffith, O.J., L. Vhengani, and M. Maliange, “Measurements of Mirror Soiling at a Candidate CSP Site,” Energy Procedia 49, 1371-1378 (2014).

doi: [10.1016/j.egypro.2014.03.146](https://doi.org/10.1016/j.egypro.2014.03.146)

Ghosh, B. and A.K. Ghosh, “Effect of Dust on PV Module Efficiency,” Science and Culture 80, 290-297 (2014).

http://www.solar-skin.eu/files/RC_Effect-of-Dust-on-Solar...by_B-Ghosh_Pg.290.pdf

Hernandez, R.R., S.B. Easterb, M.L. Murphy-Mariscal, F.T. Maestre, M. Tavassoli, E.B. Allen, C.W. Barrows, J. Belnap, R. Ochoa-Hueso, S. Ravi, and M.F. Allen, “Environmental impacts of utility-scale solar energy,” Renewable and Sustainable Energy Reviews 29, 766-779 (2014).

REVIEW

doi: [10.1016/j.rser.2013.08.041](https://doi.org/10.1016/j.rser.2013.08.041)

Herrmann, Jan, Timo Lorenz, Karolina Slamova, Elisabeth Klimm, Michael Koehl, and Karl-Anders Weiss, “Desert applications of PV modules,” Proc. 40th IEEE Photovoltaic Specialist Conference (IEEE, NY: 2014a) pp. 2043–46.

doi: [10.1109/PVSC.2014.6925328](https://doi.org/10.1109/PVSC.2014.6925328)

Herrmann, Jan, Karolina Slamova, Rüdiger Glaser, and Michael Köhl, “Modeling the soiling of glazing materials in arid regions with geographic information systems (GIS),” Energy Procedia, Proc. of the 2nd International Conference on Solar Heating and Cooling for Buildings and Industry (SHC 2013b), 48, pp. 715–20.

doi: [10.1016/j.egypro.2014.02.083](https://doi.org/10.1016/j.egypro.2014.02.083)

Hunter, Scott R., D. Barton Smith, Georgios Polizos, Daniel A. Schaeffer, Dominic F. Lee, Panos, and G. Datskos, "Low cost anti-soiling coatings for CSP collector mirrors and heliostats," Proc. SPIE, Vol. 9175 (SPIE, Bellingham, WA; 2014).

doi: [10.1117/12.2061845](https://doi.org/10.1117/12.2061845)

Iberraken, Fairouz, "Competing risk of degradation processes of a photovoltaic system under several conditions," International J. of Electrical Energy 2, 295-299 (2014).

doi: [10.12720/ijoe.2.4.295-299](https://doi.org/10.12720/ijoe.2.4.295-299).

John, J.J., S. Tatapudi, and G. Tamizhmani, "Influence of soiling layer on quantum efficiency and spectral reflectance on crystalline silicon PV modules," Proc. Photovoltaic Spec. Conf. 2595-2599 (2014a)

doi: [10.1109/PVSC.2014.6925462](https://doi.org/10.1109/PVSC.2014.6925462)

John, J., V. Rajasekar, S. Boppana, S. Tatapudi, and G. Tamizhmani, "Angle of incidence effects on soiled PV modules," Proc. SPIE (SPIE, Bellingham, Washington; 2014b) 9179:91790D–91790D–7.

doi: [10.1117/12.2063351](https://doi.org/10.1117/12.2063351)

Kazem, Imad Jawad, Mahdi, Imad Jalil, and Mohsen, Imad Tired, "Periodic cleaning effect on the output power of solar panels," J. of Kerbala University 2, 116-122 (2014a).

ISSN: 18130410

Kazem, A.A., M.T. Chaichan, and H.A. Kazem, "Dust effect on photovoltaic utilization in Iraq: Review Article," Renewable and Sustainable Energy Reviews 37, 734-749 (2014b). REVIEW

doi: [10.1016/j.rser.2014.05.073](https://doi.org/10.1016/j.rser.2014.05.073)

Kazmerski, Lawrence L., Mohammed Al Jordan, Yasser Al Jnoobi, Yousef Al Shaya, and Jim J. John, "Ashes to Ashes, Dust to Dust: Averting a potential showstopper for solar photovoltaics," Proc. 40th IEEE Photovoltaic Specialist Conference, (IEEE, NY; 2014), pp. 187–92.

doi: [10.1109/PVSC.2014.6925524](https://doi.org/10.1109/PVSC.2014.6925524).

Ketjoy, N., and M. Konyu, "Study of dust effect on photovoltaic module for photovoltaic power plant," Energy Procedia 52, 431-437 (2014).

doi: [10.1016/j.egypro.2014.07.095](https://doi.org/10.1016/j.egypro.2014.07.095)

Khonkar, Hussam, Abdulaziz Alyahya, Mazzen Aljuwaied, Mohammad Halawani, Abdulrahman Al Saferan, Al-khaldi Fawwaz, Fawaz Alhadlaq, and Brent A. Wacaser, "Importance of cleaning concentrated photovoltaic arrays in a desert environment," *Solar Energy* 110, 268–75 (2014).

doi: [10.1016/j.solener.2014.08.001](https://doi.org/10.1016/j.solener.2014.08.001).

Kumar, Subhash, and Tarlochan Kaur, "Solar PV performance-issues and challenges," Internl. J. of Innovative Res. In Electrical, Electronics, Instrumentation and Control Eng. 2, 2168-2172 (2014). ISSN 2321-2004

<http://www.ijireeice.com/upload/2014/november/IJIREEICE10%20subhash%20Solar%20PV%20Performance-Issues%20and%20Challenges.pdf>

Leloux, Jonathan, Eduardo Lorenzo, Beatriz García-Domingo, Jorge Aguilera, and Christian A. Gueymard, “A Bankable Method of Assessing the Performance of a CSP Plant,” *Applied Energy*, 118, 1-11 (2014)

doi: [10.1016/j.apenergy.2013.12.014](https://doi.org/10.1016/j.apenergy.2013.12.014)

Lombardo, T., A. Chabas, A. Verney-Carron, H. Cachier, S. Triquet, and S. Darchy, “Physico-chemical characterisation of glass soiling in rural, urban and industrial environments,” *Environmental Science and Pollution Research* 21, 9251–58 (2014).

doi: [10.1007/s11356-014-2853-4](https://doi.org/10.1007/s11356-014-2853-4).

Lorenz, Timo, Elisabeth Klimm, and Karl-Anders Weiss, “Soiling and anti-soiling coatings on surfaces of solar thermal systems—Featuring an economic feasibility analysis,” *Energy Procedia, Proceedings of the 2nd International Conference on Solar Heating and Cooling for Buildings and Industry (SHC 2013)*, 48, 749–56 (2014).

doi: [10.1016/j.egypro.2014.02.087](https://doi.org/10.1016/j.egypro.2014.02.087).

Lorenzo, E., R. Moretón, and I. Luque, “Dust effects on PV array performance: In-field observations with non-uniform patterns,” *Progress in Photovoltaics: Research and Applications* 22, 666–70 (2014).

doi: [10.1002/pip.2348](https://doi.org/10.1002/pip.2348).

Maghami, M. R., Hashim Hizam, Chandima Gomes, and A. G. Ismail, “Characterization of dust materials on the surface of solar panel,” *Life Science Journal* 11(4s), 387-390 (2014).

ISSN: 1097-8135)

Access:

https://www.researchgate.net/publication/262673734_Characterization_of_dust_materials_on_the_surface_of_solar_panel

Mallineni, J., K. Yedidi, S. Shrestha, B. Knisely, S. Tatapudi, J. Kuitche, and G. TamizhMani, “Soiling losses of utility-scale PV systems in hot-dry desert climates: Results from four 4-16 years old power plants,” 40th IEEE Photovoltaic Specialists Conference (IEEE, New York; 2014).

doi: [10.1109/PVSC.2014.6925615](https://doi.org/10.1109/PVSC.2014.6925615)

Mazumder, Malay, Julius Yellowhair, Jeremy Stark, Calvin Heiling, John Hudelson, Fang Hao, Hannah Gibson, and Mark Horenstein, “Optical and adhesive properties of dust deposits on solar mirrors and their effects on specular reflectivity and electrodynamic cleaning for mitigating energy-yield loss,” *Proc. SPIE*, 9175:91750K–91750K–16, (2014).

doi: [10.1117/12.2066328](https://doi.org/10.1117/12.2066328)

Mejia, F., J. Kleissl, and J. L. Bosch. “The effect of dust on solar photovoltaic systems,” *Energy Procedia, Proceedings of the SolarPACES 2013 International Conference*, 49 (2014), pp. 2370–76.

doi: [10.1016/j.egypro.2014.03.251](https://doi.org/10.1016/j.egypro.2014.03.251).

Ndiaye, Ababacar, Cheik M. F. Kebe, Pape A. Ndiaye, Abderafi Charki, Abdessamad Kobi, and Vincent Sambou, “Impact of dust on the photovoltaic (PV) modules characteristics after an exposition year in Sahelian environment: The case of Senegal,” *International Journal of Physical Sciences* 8, 1166–73 (2014).

doi: [10.5897/IJPS2013.3921](https://doi.org/10.5897/IJPS2013.3921)

Naeem, Mohammad Hussain, "Soiling of Photovoltaic Modules: Modelling and Validation of Location-Specific Cleaning Frequency Optimization," M.S. Thesis, Arizona State University, (2014). **THESIS**
http://repository.asu.edu/attachments/140875/content/Naeem_asu_0010N_14391.pdf

Pape, Benedikt, Javier Batlles, Norbert Geuder, Rayco Zurita Piñero, Fernando Adan, and Benedikt Pulvermueller, "Soiling impact and correlation formulas in solar measurements for CSP Projects," Proc. SolarPaces Conf., Berlin (2014)
[doi: 10.13140/2.1.4355.0406](https://doi.org/10.13140/2.1.4355.0406)

Polizos, Georgios, Daniel A. Schaeffer, D. Barton Smith, Dominic F. Lee, Panos Ge. Datskos, and Scott Hunter, "Enhanced durability transparent superhydrophobic anti-reflection coatings for CSP applications," ASME Proc. Vol. 1: Concentrating Solar Power, Solar Thermochemistry and Energy Storage, Paper No. ES2014-6505, pp. V001T02A030; 4 pages (2014a)
[doi: 10.1115/ES2014-6505](https://doi.org/10.1115/ES2014-6505)

Polizos, G. Kyle Winter, Michael J. Lance, Harry M. Meyer, Beth L. Armstrong, Daniel A. Schaeffer, John T. Simpson, Scott R. Hunter, and Panos G. Datskos, "Scalable superhydrophobic coatings based on fluorinated diatomaceous earth: Abrasion resistance versus particle geometry," Appl. Surf. Sci. 292, 563-569 (2014b).
[doi: 10.1016/j.apsusc.2013.12.009](https://doi.org/10.1016/j.apsusc.2013.12.009)

Qasem, H., Thomas R. Betts, Harald Müllejans, Hassan AlBusairi, and Ralph Gottschalg, "Dust-induced shading on photovoltaic modules," Prog. in Photovoltaics 22, 218-226 (2014).
[doi: 10.1002/pip.2230](https://doi.org/10.1002/pip.2230)

Rao, Abhishek, Rohit Pillai, Monto Mani, and Praveen Ramamurthy, "Influence of dust deposition on photovoltaic panel performance," Energy Procedia, 4th International Conference on Advances in Energy Research (ICAER 2013), 54 (2014) pp. 690–700.
[doi: 10.1016/j.egypro.2014.07.310](https://doi.org/10.1016/j.egypro.2014.07.310).

Sakhuja, M., J., Son, H. Yang, C.S. Bhatia, and A.J. Danner, "Outdoor performance and durability testing of antireflecting and self-cleaning glass for photovoltaic applications," Solar Energy 110, 231-238 (2014).
[doi: 10.1016/j.solener.2014.07.003](https://doi.org/10.1016/j.solener.2014.07.003)

Sansom, Christopher, Paul Comley, Debabrata Bhattacharyya, and Nastja Macerol, "A comparison of polymer film and glass collectors for concentrating solar power," Energy Procedia 49, 209-219 (2014).
[doi: 10.1016/j.egypro.2014.03.023](https://doi.org/10.1016/j.egypro.2014.03.023)

Said, Syed A. M., and Husam M. Walwil, "Fundamental studies on dust fouling effects on PV module performance," Solar Energy 107 328–37 (2014).
[doi: 10.1016/j.solener.2014.05.048](https://doi.org/10.1016/j.solener.2014.05.048).

Sayyah, Arash, Mark N. Horenstein, and Malay K. Mazumder. "Energy yield loss caused by dust deposition on photovoltaic panels." Solar Energy 107 576–604 (2014). **REVIEW**
[doi: 10.1016/j.solener.2014.05.030](https://doi.org/10.1016/j.solener.2014.05.030).

Schaeffer, Daniel A., Georgios Polyzos, D Barton Smith, Dominic F Lee, Slobodan Rajic, Panos G. Datskos, and Scott R Hunter, “Spray-on anti-soiling coatings that exhibit high transparency and mechanical durability,” Proc. SPIE Defense + Security Conf. (SPIE, Bellingham, Washington; 2014a) pp. 90740C-90740C-6
doi: [10.1117/12.2053387](https://doi.org/10.1117/12.2053387)

Schaeffer, Daniel A., Georgios Polyzos, D Barton Smith, Dominic F Lee, Slobodan Rajic, Panos G Datskos, and Scott R Hunter, “Spray-on superhydrophobic coatings with high mechanical durability for anti-corrosion and anti-soiling applications,” Proc. SPIE 9248, Unmanned/Unattended Sensors and Sensor Networks X, 924806 (October 17, 2014b)
doi: [10.1117/12.2072072](https://doi.org/10.1117/12.2072072)

Semaoui, S., A. Hadj Arab, S. Bacha, H. Zeraia, and E.K. Boudjelthia, “Sand effect on photovoltaic array efficiency in Algerian desert,” in 2nd International Congress on Energy Efficiency and Energy Related Materials, A.Y. Oral, Z.B. Bahsi Oral, and M. Ozer, Eds. (Springer, New York; 2014).
ISSN 2352-2434, ISBN 978-3-319-16901-9

Sharma, Vikrant, O. S. Sastry, Arun Kumar, Birinchi Bora, and S. S. Chandel, “Degradation analysis of a-Si, (HIT) hetero-junction intrinsic thin layer silicon and M-C-Si solar photovoltaic technologies under outdoor conditions,” Energy 72 536–46 (2014).
doi: [10.1016/j.energy.2014.05.078](https://doi.org/10.1016/j.energy.2014.05.078).

Sibai, Fadi N., “Modelling and output power evaluation of series-parallel photovoltaic modules,” Internl. J. Advanced Computer Science and Applications 5, 139-146 (2014).
<http://citeseerx.ist.psu.edu/viewdoc/download?doi=10.1.1.428.9529&rep=rep1&type=pdf>

Sinha, Parikhit, William Hayes, and Lauren Ngan, “Regional atmosphere-solar PV interactions,” Proc. 40th IEEE Photovoltaic Specialist Conference, (IEEE, NY; 2014) pp. 1486–91.
doi: [10.1109/PVSC.2014.6925197](https://doi.org/10.1109/PVSC.2014.6925197).

Smith, Matthew K., Hanny Selbak, Carl C. Wamser, Nicholas U. Day, Mathew Krieske, David J. Sailor, and Todd N. Rosenstiel, “Water cooling method to improve the performance of field-mounted, insulated, and concentrating photovoltaic modules,” *Journal of Solar Energy Engineering* 136, 34503–34503 (2014).
doi: [10.1115/1.4026466](https://doi.org/10.1115/1.4026466).

Stark, Jeremy, Julius Yellowhair, John N. Hudelson, Mark Horenstein, and Malay Mazumder, “Optical modeling of reflectivity loss caused by dust depositon on CSP mirrors and restoration of energy yield by electrodynamic dust removal,” ASME Proceedings on Concentrating Solar Power, Solar Thermochemistry and Thermal Energy Storage (ASME; 2014). pp. V001T02A031: 7 pages
doi: [10.1115/ES2014-6506](https://doi.org/10.1115/ES2014-6506)

Sulaiman, S. A., A.K. Singh, M.M.M. Mokhtar, and M.A. Bou-Rabee, “Influence of dirt accumulation on performance of PV panels,” Energy Procedia 50, 50-56 (2014).
doi: [10.1016/j.egypro.2014.06.006](https://doi.org/10.1016/j.egypro.2014.06.006)

Tan, C. L. C., Gao, S., Wee, B. S., Asa-Awuku, A., and Thio, B. J. R. “Adhesion of dust particles to common indoor surfaces in an air-conditioned environment,” *Aerosol Sci. Tech.* 48, 541–551 (2014).
[doi: 10.1080/02786826.2014.898835](https://doi.org/10.1080/02786826.2014.898835)

Toivola, Kristopher, Paul F. Robusto, Ajay Saproo, and Bill Kessler, “Outdoor performance of CIGS modules in different climates,” *Proc. SPIE 9179, Reliability of Photovoltaic Cells, Modules, Components, and Systems VII*, 917909, October 8, 2014.
[doi: 10.1117/12.2063308](https://doi.org/10.1117/12.2063308)

Weber, Thomas, Matthias Hanusch, Simon Koch, Michael Trawny, Andreas Janker, Anja Boettcher, Juliane Berghold, and Paul Grunow, “From the impact of harsh climates and environmental conditions on PV-Modules - Development of a Soiling and Abrasion Test,” *European PVSEC, Amsterdam*, (2014)
[doi: 10.4229/EUPVSEC20142014-5DO.11.5](https://doi.org/10.4229/EUPVSEC20142014-5DO.11.5)

Wolfertstetter, F., K. Pottler, N. Geuder, R. Affolter, A.A. Merrouni, A. Mezrhab, and R. Pitz-Paal, “Monitoring of mirror and sensor soiling with TraCS for improved quality of ground based irradiance measurement,” *Energy Procedia* 49, 2422 – 2432 (2014).
[doi: 10.1016/j.egypro.2014.03.257](https://doi.org/10.1016/j.egypro.2014.03.257)

Wu, G.M., T.L. Yin, S. Tong, Dewen Gao, Yao Ding, and Pensu Mao, “Study of Dust Removal by Transparent Fork Electrodes,” *Integrated Ferroelectrics* 153, 164-170 (2014).
[doi: 10.1080/10584587.2014.903135](https://doi.org/10.1080/10584587.2014.903135)

2015

Alami Merrouni, A., F. Wolfertstetter, A. Mezrhab, S. Wilbert, and R. Ritz-Paal, "Investigation of soiling effect on different solar mirror materials under Moroccan climate," *Energy Procedia* 69, 1948-1957 (2015)

doi: [10.1016/j.egypro.2015.03.194](https://doi.org/10.1016/j.egypro.2015.03.194)

Ali, Hafiz Muhammad, Muhammad Abdullah Zafar, Muhammad Anser Bashir, Muhammad Ali Nasir, Muzaffar Ali, and Aysha Maryam Siddiqui, "Effect of Dust Deposition on the Performance of Photovoltaic Modules in Taxila, Pakistan," *Thermal Science*, 00, 46 (2014).

doi: [10.2298/TSCI140515046A](https://doi.org/10.2298/TSCI140515046A)

Alnaser, N.W., A. A. Dakhel, M.J. Al Othman, I. Batarseh, J. K. Lee, S. Najmaii, and W. E. Alnaser, "Dust accumulation study on the Bapco 0.5MWp PV project at University of Bahrain," *International Journal of Power and Renewable Energy Systems* 2, 38-54 (2015).

www.as-se.org/ijpres/Download.aspx?ID=22792

Alqatari, S., A. Alhassan, O. de Weck, and A. Alfaris, "Spatiotemporal model for dust impact and mitigation for solar PV using Saudi Arabia as a case study," *Proc. 31st European Photovoltaics Solar Energy Conference*, 1770-1774 (2015).

doi: [10.4229/EUPVSEC20152015-5CO.14.5](https://doi.org/10.4229/EUPVSEC20152015-5CO.14.5)

Al Saluos, Wasif, "Dust effect on photovoltaic electric systems." *Internl. J. Emerging Emerging Engineering Research and Technology* 3, 4-0 (2015)

ISSN 2349-4395 (Print) & ISSN 2349-4409; Also <http://www.ijeert.org/pdf/v3-i10/2.pdf>

Benatiallah, A., D. Benatiallah, A. Harrouz, F. Abaidi, and S. Mansouri, "Effect of Dust on Performances of Single Crystal Photovoltaic Solar Module," *International Journal of Energy and Power Engineering* 2, No, 5, (2015).

<http://waset.org/abstracts/energy-and-power-engineering/25259>;

Also: waset.org/pdf/books/?id=25259&pageNumber=348

Bhasker, Vinay, and Rahul Arya, "Effects of natural dust on the performance of solar PV panel in India," *J. Energy, Environment & Carbon Credits* 5, 1-6 (2015).

ISSN: 2249 – 8621;

Access:

<http://stmjournals.com/index.php?journal=JoEECC&page=article&op=view&path%5B%5D=5706>

Bhattacharya, T., A.K. Chakraborty, and K. Pal, "Influence of environmental dust on the operating characteristics of the solar PV module in Tripura, India," *International Journal of Engineering Research* 4, 141-144 (2015).

ISSN:2319-6890) (online)

Access: http://www.ijer.in/ijer/publication/v4s3/IJER_2015_313.pdf

Biryukov, B., and P. Pokrass, "PV module soiling: quantifying energy losses and protection against dust," *Proc. 19th Sede Boqer Symposium on Solar Electricity Production*, February 2015, Ben-Gurion University of the Negev (2015). [Abstract]

Bohra, R., R.G. Gowda, and M.R. Krishnan, "Soiling loss analysis on various photovoltaic technologies installed at rooftop in metropolitan/urban environment," Proc. 31st European Photovoltaics Solar Energy Conference, 2588-2591 (2015).

doi: [10.4229/EUPVSEC20152015-5CV.2.43](https://doi.org/10.4229/EUPVSEC20152015-5CV.2.43)

Boppana, Sravanthi, "Outdoor Soiling Loss Characterization and Statistical Risk Analysis of Photovoltaic Power Plants," Master of Science Thesis, Arizona State University (2015) **THESIS**
Access: http://repository.asu.edu/attachments/150806/content/Boppana_asu_0010N_15080.pdf

Bouaddi, S., and A. Ihlal, "A study of soiling of different (CSP) candidate solar mirrors in Southwest Morocco," The Energy and Materials Research Conference – EMR2015, Madrid, Spain, 25-27 February, 2015 p. 52.

Access: <http://www.emr2015.org/files/EMR2015-Book-Abstracts.pdf>

Bouchalkha, Abdellatif, "Modeling of dust effect on solar panels in Abu Dhabi," *following a presentation at the Second International Energy 2030 Conf.-Abu Dhabi* (The Petroleum Institute; Abu Dhabi; 2015) pp. 234-238 (on-line).

Access: <http://www.energy-2030.com/08/pdfs/r-t5-3.pdf.pdf>

Boyle, L., H. Flinchbaugh and M.P. Hannigan, "Natural soiling of photovoltaic cover plates and the impact on transmission," *Renewable Energy* 77, 166-173 (2015).

doi: [10.1016/j.renene.2014.12.006](https://doi.org/10.1016/j.renene.2014.12.006)

Brophy, B., Z.R. Abrams, P. Gonsalves, and K. Christy, "Field performance and persistence of anti-soiling coatings on photovoltaic glass," Proc. 31st European Photovoltaics Solar Energy Conference, 2598-2602 (2015).

doi: [10.4229/EUPVSEC20152015-5CV.2.47](https://doi.org/10.4229/EUPVSEC20152015-5CV.2.47)

Burton, P. D., L. Boyle, J.J.M. Griego, and B.H. King, "Quantification of a minimum detectable soiling level to affect photovoltaic devices by natural and simulated soils," *IEEE Journal of Photovoltaics* 5, 1143-1149 (2015a).

doi: [10.1109/JPHOTOV.2015.2432459](https://doi.org/10.1109/JPHOTOV.2015.2432459)

Burton, Patrick D., Bruce H. King, Daniel Riley, "Predicting the spectral effects of soils on high concentrating photovoltaic systems," *Solar Energy* 112, 469-474 (2015b).

doi: [10.1016/j.solener.2014.11.022](https://doi.org/10.1016/j.solener.2014.11.022)

Cáceres, Gustavo, Shahriyar Nasirov, Huili Zhang, and Gerardo Araya-Letelier, "Residential solar PV planning in Santiago, Chile: Incorporating the PM10 parameter," *Sustainability* 7, 4220440 (2015).

doi: [10.3390/su7010422](https://doi.org/10.3390/su7010422)

Cekirge, Huseyin Murat, and Ammar Elhassan, "A comparison of solar power systems (CSP): Solar tower (ST) systems versus parabolic trough (PT) systems," *J. Energy Engineering* 3, 29-36 (2015)

doi: [10.11648/j.ajee.20150303.11](https://doi.org/10.11648/j.ajee.20150303.11)

Chakraborty, Suprava and Pradip Kumar Sadhu, "Technical mapping of solar photovoltaic for the Coal City of India," *Renewables: Wind, Water, and Solar* 2, 11 (2015).
doi: [10.1186/s40807-015-0013-1](https://doi.org/10.1186/s40807-015-0013-1)

Choi, Minkyu, Jung Woo Leem, and Jae Su Yu, "Antireflective gradient-refractive-index material-distributed microstructures with high haze and superhydrophilicity for silicon-based optoelectronic applications," *RSC Adv.* 5, 25616 (2015)
doi: [10.1039/c4ra15686b](https://doi.org/10.1039/c4ra15686b)

Darwish, Zeki Ahmed, Hussein A. Kazem, K. Sopian, M.A. Al-Goul and Hussain Alawadhi, "Effect of dust pollutant type on photovoltaic performance," *Renewable and Sustainable Energy Reviews* 41, 735-744 (2015). REVIEW
doi: [10.1016/j.rser.2014.08.068](https://doi.org/10.1016/j.rser.2014.08.068)

Doumane, R., M. Balistrrou, P.O. Logerais, O. Riou, J.F. Durastanti, and A. Charki, "A Circuit-Based Approach to Simulate the Characteristics of a Silicon Photovoltaic Module with Aging." *J. Solar Energy Engineering* 137, (2015).
doi: [10.1115/1.4029541](https://doi.org/10.1115/1.4029541)

Ferrada, P., F. Araya, A. Marzo, and E.L. Fuentealba Vidal, "Performance analysis of photovoltaic systems of two different technologies in a coastal desert climate zone of Chile." *Solar Energy* 114, 356-363 (2015).
<http://dx.doi.org.ez93.periodicos.capes.gov.br/10.1016/j.solener.2015.02.009>

Fuentealba, Edward, Pablo Ferrada, Francisco Araya, Aitor Marzo, Cristóbal Parrado, and Carlos Portillo, "Photovoltaic performance and LCoE comparison at the coastal zone of the Atacama Desert, Chile," *Energy Conversion and Management* 95, 181-186 (2015).
doi: [10.1016/j.enconman.2015.02.036](https://doi.org/10.1016/j.enconman.2015.02.036)

Guo, Bing, W. Javed, B. W. Figgis, and T. Mirza, "Effect of dust and weather conditions on photovoltaic performance in Doha, Qatar," *Proc. 2015 Smart Grid and Renewable Energy (SGRE) Workshop*, March, 2015, Doha, Qatar.
[QD-002658](https://doi.org/10.1109/SGRE.2015.7355711)

Hacke, Peter, Patrick Burton, Alexander Hendrickson, Sergiu Spataru, Stephen Glick, and Kent Terwilliger, "Effects of photovoltaic module soiling on glass surface resistance and potential-induced degradation," *Proc. 43rd IEEE Photovoltaic Specialists Conf. (IEEE, NY)* pp 1-4 (2015)
doi: [10.1109/PVSC.2015.7355711](https://doi.org/10.1109/PVSC.2015.7355711)

Jasim, Kareem K., Abbas Z. Salman, and Mahdi Sarhan, "An analytical study to reduce the effect of dust on the performance of solar panels using water systems," *Iraqi Academic Scientific Journals*, 21, 85-100 (2015).
<http://www.iasj.net/iasj?func=fulltext&aId=102166>

Jiang, Yu, and Lin Lu, "A study of dust accumulating process on solar photovoltaic modules with different surface temperatures," *Energy Procedia*, 75 337-342 (2015)
doi: [10.1016/j.egypro.2015.07.378](https://doi.org/10.1016/j.egypro.2015.07.378)

Jin, Chao, Tomasz Glowdel, Carolyn L. Ren, and Monica B. Emelko, "Non-linear, non-monotonic effect of nano-scale roughness on particle deposition in absence of an energy barrier: Experiments and modeling," *Scientific Reports* **5**, Article number: 17747 (2015).

doi: [10.1038/srep17747](https://doi.org/10.1038/srep17747)

John, Jim J., Sonali Warade, Govindasamy Tamizhmani, and Anil Kottantharayil, "Study of soiling loss on photovoltaic modules with artificially deposited dust of different gravimetric densities and compositions collected from different locations in India," *Proc. 42nd IEEE PVSC- New Orleans* (IEEE, New York; 2015). pp. 236-243

doi: [10.1109/JPHOTOV.2015.2495208](https://doi.org/10.1109/JPHOTOV.2015.2495208)

John, J.J., V. Rajasekar, S. Boppana, S. Chattopadhyay, A. Kottantharayil and G. Tamizhmani, "Quantification and modeling of spectral and angular losses of naturally soiled PV modules," *IEEE Journal of Photovoltaics* **5**, 1727-1734,(2015)

doi: [10.1109/JPHOTOV.2015.2463745](https://doi.org/10.1109/JPHOTOV.2015.2463745);

Also, *IEEE J. Photovoltaics* **6**, 1-8 (2015)

doi: [10.1109/JPHOTOV.2015.2495208](https://doi.org/10.1109/JPHOTOV.2015.2495208)

Karim, M., S. Naamane, C. Delord, and A. Bennouna, "Study of surface damage of glass reflectors used in concentrated solar power plants," *Energy Procedia* **69**, 106-115 (2015)

doi: [10.1016/j.egypro.2015.03.013](https://doi.org/10.1016/j.egypro.2015.03.013)

Kawamoto, H., and T. Shibata, "Electrostatic cleaning system for removal of sand from solar panels," *J. Electrostatics* **73**, 65-70 (2015).

doi: [10.1016/j.elstat.2014.10.011](https://doi.org/10.1016/j.elstat.2014.10.011)

Kazmerski, Lawrence L., Antonia Sonia A.C. Diniz, Cristiana Brasil Maia, Marcelo Machado Viana, Suellen C. Costa, Pedro P. Brito, Cláudio Dias Campos, Lauro V. Machado Neto, Sergio de Moraes Hanriot, and Leila R. de Oliveira Cruz, "Fundamental studies of the adhesion of dust to PV module surfaces: chemical and physical relationships at the microscale," *Proc. 42nd IEEE Photovoltaic Spec. Conf.-New Orleans* (IEEE, New York; 2015) pp. 1-7

doi: [10.1109/PVSC.2015.7356135](https://doi.org/10.1109/PVSC.2015.7356135)

Also *IEEE J. Photovoltaics* **PP**, 1-22 (2016).

doi: [10.1109/JPHOTOV.2016.2528409](https://doi.org/10.1109/JPHOTOV.2016.2528409)

King, Bruce, "Advanced measurement and analysis PV derate factors," Sandia National Laboratories Report, Albuquerque, NM (SAND2015-10998R) (2015).

Access: <http://prod.sandia.gov/techlib/access-control.cgi/2015/1510998r.pdf>

Klimm, E., Thomas Kaltenbach, Daniel Philipp, Marvin Masche, Karl-Anders Weiss, and Michael Koehl, "Soiling and abrasion testing of surfaces for solar energy systems adapted to extreme climatic conditions," *Proc. 31st European PV Solar Energy Conf, Hamburg* (WIP, Germany; 2015).

Access:

https://www.ise.fraunhofer.de/de/veroeffentlichungen/konferenzbeitraege/konferenzbeitraege-2015/31st-eupvsec-hamburg-germany/klimm_5cv.2.22.pdf

Klugmann-Radziemska, Eva, "Degradation of electrical performance of a crystalline photovoltaic module due to dust deposition in northern Poland," *Renewable Energy* **78**, 418-426 (2015).

doi: [10.1016/j.renene.2015.01.018](https://doi.org/10.1016/j.renene.2015.01.018)

Lee, Chin Yin, Jui Kang Chiang, Pei Chin Lin, Katsushi Suzuki, Osamu Nishimaniwa, Lai Pheng Gan, and Fred Chen, "An innovative approach to examine soiling impact on photovoltaic module performance," WIKI-Cleantech.com (internet publication) (2015).

<http://wiki-cleantech.com/uncategorized/an-innovative-approach-to-examine-soiling-impact-on-photovoltaic-module-performance>

Leem, Jung Woo, and Jae Su Yu, "Artificial inverted compound eye structured polymer films with light-harvesting and self-cleaning functions for encapsulated III-V solar cell applications," RSC Adv. 5, 608004 (2015)

doi: [10.1039/c5ra05991g](https://doi.org/10.1039/c5ra05991g)

Li, Jianghua, Kangqu Zhou, Hengxiang Gong, and Xincai Zhu, "A PV Module Surface Dust Removal Device Simulation," Appl. Mechanics and Materials 779, 259-267 (2015a)

doi: [10.4028/www.scientific.net/AMM.779.259](https://doi.org/10.4028/www.scientific.net/AMM.779.259)

Li, Kangping, Fei Wang, Zhao Zhen, Yujing Sn, Zengqiang Mi, Hongbin Sun, Chun Liu, Bo Want, and Jing Lu, "Photovoltaic plant operating statuses identification model based on support vector machine using loss quantity of electricity feature parameters," Proc. International Conference on Renewable Power Generation (RPG 2015) (IET Digital Library; 2015b) p 6.

doi: [10.1049/cp.2015.0504](https://doi.org/10.1049/cp.2015.0504)

Lim, Joo Ho, Jung Woo Leem, and Jae Su Yu, "Solar power generation enhancement of dye-sensitized solar cells using hydrophobic and antireflection polymers with nanoholes," RSC Adv. 5, 61284 (2015)

doi: [10.1039/c5ra10269c](https://doi.org/10.1039/c5ra10269c)

Lopes de Jesus, M.A.M., J.T. da Silva Neto, G. Timó, P.R.P. Paiva, M.S.S. Dantas, and A.de Mello Ferreira, "Superhydrophilic self-cleaning surfaces based in TiO₂ and TiO₂/SiO₂ composite films for photovoltaic module cover glass," Appl. Adhesion Sci. 3, 5 (2015)

doi: [10.1186/s40563-015-0034-4](https://doi.org/10.1186/s40563-015-0034-4)

Maghami, Mohammad Reza, Hashim Hizam, Chandima Gomes, Mohd Amran Radzi, Mohammad Ismael Resadad, and Shahrooz Hajjighorbani, "Power loss due to soiling on solar panel: A review," Renewable and Sustainable Energy Reviews 59, 1307-1316 (2016). REVIEW

doi: [10.1016/j.rser.2016.01.044](https://doi.org/10.1016/j.rser.2016.01.044)

Martinez-Plaza, Diego, Amir Abdallah, Benjamin W. Figgis, and Talha Mizra, "Performance improvement techniques for photovoltaic systems in Qatar: Results of first year of outdoor experiments," Energy Procedia 77, 386-396 (2015)

doi: [10.1016/j.egypro.2015.07.054](https://doi.org/10.1016/j.egypro.2015.07.054)

Martinez, D., A. Abdallah, and B. Figgis, "A study of several thin-film technologies performance under desert environmental conditions in Qatar," Proc. 31st European Photovoltaics Solar Energy Conference (2015).

ISBN 3-936338-39-6

Michels, Roger Nabeyama, Marcelo Giovanetti Canteri, Marcelo Augusto de Aguiar e Silva, Estor Gnoatto, José Airton Azevedo dos Santos and Manuel Messias Alvino de Jesus, "Yield from photovoltaic modules under real working situation in west Paraná – Brazil," *Acta Scientiarum* 37, 19-24 (2015)
doi: [10.4025/actascitechnol.v37i1.19191](https://doi.org/10.4025/actascitechnol.v37i1.19191)

Mondal, Amit Kumar, and Kamal Bansal, "Structural analysis of solar panel cleaning robotic arm," *Current Science* 108, 1047-1052 (2015).
Access: <http://www.currentscience.ac.in/Volumes/108/06/1047.pdf>

Nazar, Rupali, "Improvement of efficiency of solar panel using different methods," *International J. of Electrical and Electronics Engineers* 7 (2015).
Access: <http://www.arresearchpublication.com/images/shortpdf/117.pdf>

Negash, Tariku and Tassew Tadiwose, "Experimental investigation of the effect of tilt angle on the dust photovoltaic module," *Internl. J. of Energy and Power Engineering* 4, 227-231 (2015)
doi: [10.11648/j.ijepe.20150404.15](https://doi.org/10.11648/j.ijepe.20150404.15)

Naeem, Mohammad, and Govindasamy Talizhmani, "Climatological Relevance to the Soiling Loss of Photovoltaic Modules," *Proc. Saudi Arabia Smart Grid Conference, Jeddah, Saudi Arabia, 7-9 Dec, 2015.*

Pettersen, A. Deråas, J.H. Krogh Selj, and E. Stensrud Marstein, "PV modules in Nordic climate: Effects of soiling and snow," *Proc. 31st European Photovoltaics Solar Energy Conference* (2015). (Also, http://bipvno.no/publications/EUPVSEC2015_Poster_IFE_Soiling&Snow.pdf)
ISBN 3-936338-39-6
Access: http://bipvno.no/publications/EUPVSEC2015_Poster_IFE_Soiling&Snow.pdf

Pettersen, Anna Derås, "Simulation and experimental study of power losses due to shading and soiling on photovoltaic (PV) modules," *Masters Thesis (Norwegian University of Life Sciences, Norway; 2015) THESIS*
<http://hdl.handle.net/11250/278807>

Penetta, Selene, Shengzhe Yu, John Barry, Zhiqiang Guan, "A case study on parameters influencing dust accumulation on CSP reflectors," in *SuNEC 2015*, M. Pagliaro and F. Meneguzzo, Eds. (Sun New Energy Conf., Sicily, Italy; 2015) OP-2.
doi: [10.17265/1934-8975/2016.02.001](https://doi.org/10.17265/1934-8975/2016.02.001)

Phinikarides, A., G. Makrides, B. Zinsser, M. Schuber, and G.E. Georghiou, "Analysis of photovoltaic system performance time series: Seasonality and performance loss," *Renewable Energy* 77, 51-63 (2015)
doi: [10.1016/j.renene.2014.11.091](https://doi.org/10.1016/j.renene.2014.11.091)

Piotrowska-Woroniak, Joana, G. Woroniak, and W. Zaluska, "Energy production from PV and carbon reduction in great lakes region of Masuria Poland: A case study of water part in Elk," *Renewable Energy* 83, 1315-1325 (2015).
doi: [10.1016/j.renene.2015.05.034](https://doi.org/10.1016/j.renene.2015.05.034)

Rahman, M.M., M. Hasanuzzaman, and N.A. Rahim, "Effects of various parameters on PV-module power and efficiency." *Energy Conversion and Management* 103, 348-358 (2015).
doi: [10.1016/j.enconman.2015.06.067](https://doi.org/10.1016/j.enconman.2015.06.067)

Rajasekar, Vidyashree, "Indoor Soiling Method and Outdoor Statistical Risk Analysis of Photovoltaic Power Plants," Master of Science Thesis, Arizona State University (2015) **THESIS**
Access: <https://repository.asu.edu/items/30053> , and
https://repository.asu.edu/attachments/150884/content/Rajasekar_asu_0010N_14973.pdf

Sansom, C., P. Comley, P. King, H. Almond, C. Atkinson, and E. Endaya, "Predicting the effects of sand erosion on collector surface in CSP plants," *Energy Procedia*, 69, 198-207 (2015)
doi: [10.1016/j.egypro.2015.03.023](https://doi.org/10.1016/j.egypro.2015.03.023)

Scanlon, B. "Assuring solar modules will last for decades," *Renewable Energy World*, May 19 (2015).
<http://www.nrel.gov/news/features/2015/16488>

Schaeffer, Daniel A., Georgios Polizos, D. Barton Smith, Dominic F. Lee, Scott R. Hunter, and Panos G. Datskos, "Optically transparent and environmentally durable superhydrophobic coating based on functionalized SiO₂ nanoparticles," *Nanotechnology* 35, 055602-055609 (2015).
doi: [10.1088/0957-4484/26/5/055602](https://doi.org/10.1088/0957-4484/26/5/055602)

Schill, Christian, Stefan Brachmann, and Michael Koehl, "Impact of soiling on IV-curves and efficiency of PV-modules," *Solar Energy* 12, 259-162 (2015).
doi: [10.1016/j.solener.2014.12.003](https://doi.org/10.1016/j.solener.2014.12.003)

Sengupta, M., A. Habte, S. Kurtz, A. Dobos, S. Wilbert, E. Lorenz, T. Stoffel, D. Renne, C. Gueymard, D. Myers, S. Wilcox, P. Blanc, and R. Perez, "Best Practices Handbook for the Collection and Use of Solar Resource Data for Solar Energy Applications," 255 pp.; NREL Report No. TP-5D00-63112 (2015).
<http://www.nrel.gov/docs/fy15osti/63112.pdf>

Shi, Meiling, "Market Analysis of Israeli CSP Technologies in the Chinese Market," M.S. Thesis, Duke University (2015) **THESIS**
<http://dukespace.lib.duke.edu/dspace/bitstream/handle/10161/9602/Meiling%20Shi-Master%20Project-2015.pdf?sequence=1>

Shirakawa, M. A., R. Zilles, A. Mocelin, C.G. Christine, A.G. Gorbushina, Heidrich, M.C. Giudice, G.M.B.D. Negro, and V.M. John, "Microbial colonization affects the efficiency of photovoltaic panels in a tropical environment," *Journal of Environmental Management* 157, p. 160-167 (2015)
doi: [10.1016/j.jenvman.2015.03.050](https://doi.org/10.1016/j.jenvman.2015.03.050)

Sleiman, Mohamad, Sharon Chen, Haley E. Gilbert, Thomas W. Kirchstetter, Paul Berdahl, Erica Bibian, Laura S. Bruckman, Dominic Cremon, Roger H. French, Devin A. Gordon, Marco Emiliani, Justin Kable, Liyan Ma, Milena Martarelli, Riccardo Paoliniⁿ, Matthew Prestia^o, John Renowden^e, Gian Marco Revel^p, Olivier Rosseler, Ming Shiao, Giancarlo Terraneo, Tammy Yang, Lingtao Yu, Michele Zinzi, Hashem Akbari, Ronnen Levinson, Hugo Destailats, "Soiling

of building envelope surfaces and its effect on solar reflectance – Part III: Interlaboratory study of an accelerated aging method for roofing materials,” *Solar Energy Materials and Solar Cells* 143, 581-590 (2015).

doi: [10.1016/j.solmat.2015.07.031](https://doi.org/10.1016/j.solmat.2015.07.031)

Spataru, S., Deszo. Sera, Tamas Kerekes, and Remus Therodorescu, “Diagnostic method for photovoltaic systems based on light I-V measurements,” *Solar Energy* 119, 29-44 (2015).

doi: [10.1016/j.solener.2015.06.020](https://doi.org/10.1016/j.solener.2015.06.020)

Sulaiman, Shaharin A., Haizantul H. Hussain, Nik Siti Leh, and Mohd S.I. Razali, “Effects of dust on the performance of PV panels,” *World Academy of Science and Technology* 5, 10-20 (2015).

<http://waset.org/Publication/effects-of-dust-on-the-performance-of-pv-panels/10305>

Tanesab, Julius, David Parlevliet, Jonathan Whale, Tania Urmee, and Trevor Pryor, “The contribution of dust to performance degradation of PV modules in temperate climate zone,” *Solar Energy* 120, 147-157 (2015).

doi: [10.1016/j.solener.2015.06.052](https://doi.org/10.1016/j.solener.2015.06.052)

Verma, Ashish, and Shivya Singhal, “Solar PV performance parameter and recommendation for optimization of performance in large scale grid connected solar PV plant—case study,” *J. Energy and Power Sources* 2, 40-53 (2015)

<http://www.ethanpublishing.com/uploadfile/2015/0202/20150202034553486.pdf>

Weber, Thomas, Nicoletta Ferretti, Felix Schneider, Andreas Janker, Michael Trawny, and Juliane Berghold, "Impact & Consequences of Soiling and Cleaning of PV Modules," NREL PV Module Reliability Workshop, Golden, CO, February 2015.

Access: http://www.nrel.gov/pv/performance_reliability/pdfs/2015_pvmrw_105_weber.pdf

Wu, Guangming, Dan Li, Jianxiang Yu, Tianlan Yin, and Dongdong Feng, “Further study of electric dust removal with transparent fork electrodes,” *American Journal of Analytical Chemistry* 6, 196-201 (2015).

doi: [10.4236/ajac.2015.63018](https://doi.org/10.4236/ajac.2015.63018)

Xu, Q.F., Y. Zhao, B. Kujan, and A. Lyons, “An Anti-reflective and anti-soiling coating for photovoltaic panels,” *Proc. TechConnect: World Innovations Conf.*, Washington, DC (2015).

<http://www.techconnectworld.com/World2015/a.html?i=413>

Yang, F. D. Itskhokine, S. Benmarraze, M. Benmarraze, A. Hofer, F. Lecat, and A. Ferrière, “Acceptance testing procedure for linear Fresnel reflector solar systems in utility-scale solar thermal solar plants,” *Energy Procedia*, (2015).

Access:

http://www.solareuromed.com/sites/default/files/publications/solareuromed_solarpaces2014_acceptance.pdf

Yilbas, Bekir Sami., Haider Ali, Mazen M. Khaled, Nasser Al-Aqeeli, Numan Abu-Dheir, and Kripa K. Varanasi, Influence of dust and mud on the optical, chemical, and mechanical properties of PV protective glass, *Scientific Reports*, 5, 15833 (2015)

doi: [10.1038/srep15833](https://doi.org/10.1038/srep15833)

Zell, Erica, Sami Gasim, Stephen Wilcox, Suzan Katmoura, Thomas Stoffel, Husain Shibli, Jill Engle-Cox, and Madi Al Subie, "Assessment of solar radiation resources in Saudi Arabia," *Solar Energy* 119, 422-438 (2015)
<http://dx.doi.org/10.1016/j.solener.2015.06.031>

Special Reports of Interest

International Finance Corporation, World Bank Group, “Utility Scale Solar Power Plants: A Guide for Developers and Investors.” World Bank (2012)
<https://www2.unece.org/wiki/download/attachments/25267247/SOLAR%2BGUIDE%2BBOOK.pdf?api=v2>

National Centre for Photovoltaic Research and Education, Indian Institute of Technology-Bombay, “All India Survey of PV Module Degradation 2013.” IIT Bombay (2013)
http://www.ncpre.iitb.ac.in/pages/publications_reports.html

Universidade Federal de Santa Clara, Grupo de Pesquisa Estratégica em Energy Solar, and Instituto Para o Desenvolvimento das Energias Alternativas na América Latina, **REPORT**: “Scientific review of CdTe photovoltaic technology: Impacts and benefits of First Solar’s CdTe technology for large-scale deployment in Brazil – Performance, environmental, health and safety assessment” (2015)

The report can be accessed on the First Solar website through: www.aguacalientesolarproject.com

International Energy Agency (IEA), Photovoltaic Power Systems Program, “Energy from the Desert: Very Large Scale PV Power Plants for Shifting to Renewable Energy Future.” IEA PVPS Task 8, (2015).
ISBN 978-3-906042-29-9, February 2015.

Simon P. Philipps, Andreas W. Bett, Kelsey Horowitz, Sarah Kurtz, “The Status of Concentrator Photovoltaics (CPV) Technology.” Fraunhofer ISE and NREL (U.S. Department of Energy, Office of Scientific and Technical Information, Washington, DC; 2015).
TP-6A20-63916

Groupe Reaction, “CSP Prospects in Saudi Arabia,” MENSOL 2014, Report published by CSP Today (2014)
<http://www.csptoday.com/menasol/pdf/cspsaudi Arabia.pdf>

R. Pitz-Paal, A. Amin, M. Bettzüge, Philip Eames, Fabrizio Fabrizi, G. Flamant, F. Garcia Novo, J. Holmes, A. Kribus, H. van der Laan, C. Lopez, P. Papagiannakopoulos, E. Pihl, P. Smith and H. J. Wagner, “Concentrating Solar Power in Europe, the Middle East and North Africa: Achieving its Potential.” J. Energy and Power Engineering, 7, 219-228 (2013).

E. E. Houssos, T. Chronis, A. Fotiadi, and F. Hossain, “Atmospheric Circulation Characteristics Favoring Dust Outbreaks over the Solar Village, Central Saudi Arabia.” Monthly Weather Rev., 143, 3263–3275 (2015).

S. Naseema Beegum, Imen Gherboudj, Naira Chaouch, and Hosni Ghedira, “Atmospheric composition modeling over the Arabian Peninsula for solar energy applications.” Proc. ICEM 2015, Boulder, Colorado (2015).
http://icem2015.org/wp-content/uploads/2015/07/1130_NaseemaShyju.pdf

Sarah Kurtz, International PV Quality Assurance Task Force (PVQAT), Solar ABCs Workshop (2015)
www.nrel.gov/docs/fy15osti/65121.pdf

ACWA Power and 5 Capitals, “Noor III Tower CSP Plant, Ouarzazate, Morocco: Specific Environmental and Social Impact Assessment Volume 1 (Discussions of impact of dust on CSP, mitigation, and dust prevention site preparations)

<http://www->

[wds.worldbank.org/external/default/WDSContentServer/WDSP/IB/2015/04/07/000477144_20150407101229/Rendered/PDF/E44890V90P131200Box391417B00PUBLIC0.pdf](http://www-wds.worldbank.org/external/default/WDSContentServer/WDSP/IB/2015/04/07/000477144_20150407101229/Rendered/PDF/E44890V90P131200Box391417B00PUBLIC0.pdf)

S. Naseema Beegum, Priya Vijayan and Hosni Ghedira, “Irradiance modeling using SBDART on clear and cloudy conditions: sensitivity to aerosol and cloud parameters.” Proc. ICEM 2015, Boulder, Colorado (2015).

http://icem2015.org/wp-content/uploads/2015/07/1810_NaseemaShyju.pdf

M. Sleiman, G. Ban-Weiss, H.E. Gilbert, D. Francois, P. Berdahl, T.W. Kirchstetter, H. Destailats, R. Levinson, “Soiling of building envelope surfaces and its effect on solar reflectance – Part I: analysis of roofing product databases” Sol. Energy Mater. Sol. Cells, 95 (2011), pp. 3385–3399 (2011).

[doi: 10.1016/j.solmat.2013.11.028](https://doi.org/10.1016/j.solmat.2013.11.028)

M. Sleiman, T.W. Kirchstetter, P. Berdahl, H.E. Gilbert, S. Quelen, L. Marlot, C.V. Preble, S. Chen, A. Montalbano, O. Rosseler, H. Akbari, R. Levinson, H. Destailats, “Soiling of building envelope surfaces and its effect on solar reflectance – Part II: development of an accelerated aging method for roofing materials” Sol. Energy Mater. Sol. Cells, 122 (2014), pp. 271–281 (2014).

[doi: 10.1016/j.solmat.2011.08.002](https://doi.org/10.1016/j.solmat.2011.08.002)

Tagawa, Kotaro, Akifumi Kutani, and Pio Qinglin, “Effect of sand erosion of glass surface on performances of photovoltaic module,” Sustainable Research and Innovation Proc. 4, 75-77 (2012).

[ISSN 2079-6226](https://doi.org/10.1016/j.sri.2012.08.002)

Augustin McEvoy, Luis Castañer, Tom Markvart, Solar Cells: Materials, Manufacture and Operation (Elsevier Scientific and Academic Press; Waltham, MA; 2013). Part II: Testing, Industry and Environment

[ISBN: 978-1-85617-457-2](https://doi.org/10.1016/B978-1-85617-457-2)

Peter Gervorkian, Large-Scale Solar Power Systems: Construction and Economics (Cambridge University Press, UK; 2012) Chapter 7.

[ISBN: 9781107697171](https://doi.org/10.1017/C9781107697171)

World Bank. 2015. “Tower CSP Plant : environmental report - specific environmental and social impact assessment.” Washington, DC : World Bank Group.

<http://documents.worldbank.org/curated/en/2015/03/24315946/morocco-second-third-phase-noor-concentrated-solar-power-project-vol-9-tower-csp-plant-environmental-report-specific-environmental-social-impact-assessment>

Table 1. Noteworthy Recent Review Papers Addressing Soiling and Dust Issues.

Source	Contribution/Focus of Review	Technology
Mani and Pillai (2010)	Evaluation of current research status on impact of dust on performance of PV systems. In-depth analysis of dust accumulation mechanisms and potential mitigation approaches. Climate zone definitions—and comprehensive evaluation of potential severity of soiling in various world climate regions/conditions. [23 References]	Flat-panel and concentrating PV
Bakirci (2012)	Review of methodologies to determine optimum tilt angles for solar collectors; irradiance with indications for soiling/dust. Case study for irradiance situation in Turkey. [57 References]	General solar collectors
Mekhilef, Rahman, and Kamalisarvestani (2012)	Review of the effects of dust accumulation, air velocity, and humidity on the performance of PV cells/systems—and the interrelationships among these three components. Indications of the effects of these on system design and deployment. Specific results for Malaysia region highlighted. [39 References]	Flat-panel PV
Ahmed Darwish, Kazem, and Sopian (2013)	Summary review of impact of dust and related environmental conditions on PV performance. Scope of the review encompasses: dust properties (physical size, morphology, electrostatic deposition behavior), particle biological and electro-chemical properties, optimization and modeling studies, effects in various geographical/climatic zones (latitude) considering factor of tilt, altitude, and orientation, wind patterns and minimum dust accumulation for various PV module configurations, dust-particle geometry effects on its deposition behavior, electrostatic attraction on dust settlement, impact of progressive water (cement formation, staining, etc.) on performance. Review considers work in periods before and after 1990. Discussion of dust accumulation models. [22 References]	PV (flat plate) technologies
Bao, Zhang, Cai, Jiang, Xv, and Jia (2013)	Review of dust effects on PV performance (efficiency); dust deposition models/mechanisms, transmission losses and the effects of environmental/weather conditions on dust deposition. Commonly used PV module cleaning techniques (electrode screen dust mitigation and mechanical dust cleaning techniques) are discussed. Research directions evaluated. [14 References]	Flat-panel PV
Midtdal and Jelle (2013)	Comprehensive review of current-market, self-cleaning glazing products for soiling mitigation. Future research and technology directions—emphasis on solar applications. In-depth evaluation of optical property effects/aberrations. Hydrophobic, catalytic hydrophilic, etc. covered in detail. [48 References]	Solar applications (using glazing products)
Sharma and Chandal (2013)	Review and literature on performance and degradation of PV modules under outdoor operation for identifying research gaps for long term reliability of PV modules and improving the PV qualification standards for various geographical and climatic conditions. Reliability includes soiling issues. [84 References]	PV modules (outdoor exposure)
Tarver, Al-Qaraghuli, and Kazmerski (2013)	Comprehensive overview of soiling problems, primarily those associated with “dust” (e.g. dry sand) and combined dust-moisture conditions. Discussion of key contributions to the understanding, performance effects, and mitigation of these problems based on nature, pre-emption (e.g., siting), restoration (cleaning) and preventions (coatings, etc.).	PV (flat-panel and concentration), flat-panel solar thermal, CSP (mirrors, heliostats, etc.)

	<p>Compilation of compositional, chemical, and morphological analysis of dust from throughout the world.</p> <p>Discussion of research needs and directions.</p> <p>[256 References]</p>	
Butuza (2014)	<p>Focused literature search for the effects of soiling, dust and other surface deposits, on the performance of solar photovoltaic collectors. (Primarily provides a procedure for searching.)</p> <p>[16 References]</p>	PV Panels
Ghazi, Sayigh, and Ip (2014)	<p>Review of dust effects on performance PV and solar thermal collectors from 4 different climate zones. Separates review of studies from 3 historical time periods. Guidelines for mitigation and cleaning procedures pertinent to climate conditions presented.</p> <p>[92 References]</p>	Flat-panel PV primarily, some flat plate solar thermal
Hernandez, Easterb, Murphy-Mariscal, Maestre, Tavassoli, Allen, Barrows, Belnap, Ochoa-Hueso, Ravi, and Allen (2014)	<p>Review direct and indirect environmental impacts – both beneficial and adverse – of utility-scale solar energy (USSE) development, including impacts on biodiversity, land-use and land-cover change, soils, water resources, and human health.</p> <p>Environmental effects of panel washing (water).</p> <p>Soil erosion and effect on soil accumulation on panels; reducing effects by vegetation.</p> <p>Performance effects reviewed.</p>	Large-scale solar PV and CSP plants
Kazem, Chaichan, and Kazem (2014)	<p>Review of effects of soiling and dust conditions on the PV performance in Iraq. Review of studies on the degradation rates and mechanisms. Effects of moisture and cleaning requirements.</p> <p>Climate zone issues presented and discussed in relationship to the soiling problems.</p> <p>Written to interest research, design, and installer groups.</p> <p>[130 References]</p>	Flat-panel PV
Sayyah, Horrenstein, and Mazumder. (2014)	<p>Comprehensive review of energy-yield losses due to soiling and dust accumulation with some focus on the semi-arid and desert locations. Effects of tilt angle, time exposures, various surfaces (materials), and locations (climate zones). Laboratory and outdoor experiments are included. Summary and evaluation of cleaning techniques (natural, traditional, and emerging).</p> <p>[120 References]</p>	Flat-panel PV primarily (<i>various technologies included</i>)
Darwish, Kazem, Sopian, Al-Ghoul, and Alawadhi (2015)	<p>Review of dust pollutant type on performance of PV panels. In-depth evaluation of various reports and various compositions of dust, the accumulation properties/mechanisms, and relationships to various PV parameters.</p> <p>[42 References]</p>	Flat-panel PV
Maghami, Hizam, Gomes, Radzi, Resdad, Hajighorbani (2016)	<p>Review of “key contributions” to the understanding, performance effects, and power loss due to soiling and dust on solar panels. Categorization of two shading types. Included are discussions of several cleaning techniques and dust adhesion prevention approaches.</p> <p>[55 References]</p>	PV Panels

Table 2. Summary of dust and soiling papers in 2013 indicating primary focus, device/materials investigate, conditions and findings. The *Focus Code* (for primary contributions) is: *P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning; *A=ambient conditions/effects; *I=Instrumentation, *S=spectral effects, *TO=Tilt/Orientation

Publication Source	Focus* (see code below)	Location [Duration]	Solar Device Type	Key Findings	Comments/Other Conditions
Adinoyi and Said (2013)	P, C	Saudi Arabia (Eastern Province) [6 months]	Crystalline Si Modules	50% power loss for uncleaned modules over this period. Power tracking improves output and decreases dust accumulation. Dust sample evaluated for composition/particle size	Temperature effects compared between single-crystal and multicrystalline technologies
Ahmed Darwish et al. (2013b)	P, CM, ME	Laboratory Studies	Crystalline Si Modules	Discusses and investigates the effect of some environmental variables with dust on the PV performance. Evaluates and compares result to other research on effect of dust properties, effect of PV system parameters and effects of environment parameters. Use of artificial soils for investigations.	Effects of wind speed and direction. Modeling of dust coverage effects. Module cleaning (effects).
Al-Ammri et al. (2013)	P, CM, MC	Laboratory Studies Urban lights Baghdad, Iraq [3-6 months]	Street Lights, Si Modules	Power losses by month, with >60% for 3-month period Feb-Apr; Comprehensive data provided. Morphology evaluations by microscope indicated particles with irregular shapes (roughly spherical) Particles have concentrations of carbon-based chemicals from local refineries (enhanced adhesion) Cleaning requirements discussed.	Indications of performance loss of the panels due to dust accumulation. Panels at 26 meters on streetlights. Temperature/irradiance measured. Bird dropping problems (including chemical interactions with modules)
Al-Sabounchi et al. (2013)	P, MC	Abu Dhabi, UAE [>6 months]	Si Modules-36KW system	Monthly monitoring of PV system loss. July timeframe worst with 27% loss due to dust. Monthly cleaning cycle proposed.	Complete system evaluation (temperature, irradiance, time of day parameters, inverters, etc.)
Appels et al. (2013)	P, CM, MC, TR	Central Europe (Belgium) [5 weeks]	Module cover glass; Si PV modules	3%-4% loss after 5 weeks exposure. Water cleaning with soft water required (transmission loss due to hard water shown). Studies of glass transmission loss with artificial dust.	SEM studies of accumulated particles (dust, pollen, etc.). Cleaning cycles discussed.
Awwad et al. (2013)	P	Amman, Jordan [3 month period]	240-W c-Si modules	Comparison in power output between cleaned and dust-accumulated modules; "Energy Gap" evaluated	Cleaning schedule indicated (daily)
Bai et al. (2013)	MS, CE	Modeling of Phoenix, Arizona systems [>9000 hours]	Si modules, 2-residential systems, 5KW and 6KW (glass surface)	Empirical modeling assuming annual 5% soiling loss Extensive and detailed cost, payback, tariff data. Financial modeling for PV systems	Study of assumed soiling rates to model costs and other consumer issues.
Bi et al. (2013)	CM, I	Urban Environments	General Technique for Sampling and Analysis	Novel method for collecting and evaluating dust samples collected from roadside locations Focus on evaluation of trace elements (e.g., Pb, anthropogenic contamination in urban areas)	Mainly a technique that can be applied to solar collector evaluations

Boyle et al. (2013)	TR	Outdoors, Commerce City, Colorado USA [1.5 years]	Module cover glasses	For dust accumulations <math>< 1.5 \text{ g/m}^2</math>, light transmission was reduced by 6% per $\text{g/m}^2</math> of dust accumulation; Incidence angle does not impact the transmission reduction caused by dust deposition.$	Periodic procedure to prevent volatilization of deposited dust Sampling of >100
Brooks et al. (2013)	P, MC	Tucson, Arizona USA	Flat-plate PV Modules	Comparison of 3 methodologies comparing cleaned and soiled modules: (1) Energy yields at MPP; (2) I-V characteristics of individual modules in field; (3) I-V characteristics of individual modules under simulator Method 3 reported most precise.	All modules indicate ~1% gain in efficiency after cleaning
Canada (2013)	P, TO	Desert Southwest USA [Data - 20-year period]	Utility-Scale c-Si PV	Soiling evaluated considering: Tilt angle, human activity Annual power loss rates: 3%-6%	Washing procedures
Caron and Littmann (2013)	P, I	California USA [>1 month]	Thin-Film CdTe	Automated technique (monitoring station) to evaluate effects of dust accumulation on performance. Complex setup that eliminates sources of errors for precise evaluations. Soiling rates of 11.5%/month reported (agricultural areas);	Periodically cleaned module compared to uncleaned module. Small rainfalls (~0.5 mm rain) enough to restore performance of frameless module.
Charabi and Gastli (2013)	MS, P	Case Study for Oman	General PV Installations Modeled; CPV Focus	Effects of dust & temperature during the site assessment for large PV power plant in order to mitigate their vulnerability (performance losses) and optimize their operation efficiency. Case study use to eliminate areas from site consideration.	Different PV technologies are evaluated with CPV technology providing higher potential for implementing large solar plants. In fact, if all highly suitable land is exploited for CPV plants, supplying more than 750 times the current total power supply in Oman (estimated at 16.1 TWh in 2010).
Dastoori et al. (2013)	P,A,TO	Laboratory Simulations/Tests (effects of dust charge)	Amorphous Si Modules (3)	Experiments to investigate the relation between the amount of charge on dust particles and their impact on the reduction of the PV modules output voltage. Complementary effects of tilt angle	Results: Significant effect on PV module voltage Epoxy powder used to simulate dust.
Della-Guistina et al. (2013)	P, I	Laboratory Studies	Reference Modules	Sinton Instruments FMT-350 to measure the effect of soiling and light induced degradation on PV modules.	Sinton Instruments FMT-350 module I-V flash tester using NREL primary calibration reference modules
Dunn et al. (2013)	P	Field testing of Soiling Monitoring Station	Thin-Film CdTe Modules	Soiling Ratio (SR) defined and determined. Soiling monitoring station designed and evaluated Uncertainty analysis provided (corrections for external parameters-T, irradiance, wind, etc.)	Detailed description and evaluation of two-module (one cleaned, one not) station with instrumentation
El-Din et al. (2013)	P, A	Alexandria, Egypt [2 months]	Thin-Film PV Module	As dust deposition density increased from 0 to $0.36 \text{ mg cm}^{-2}</math>, the corresponding reduction of efficiency and short circuit current I_{sc}</math> are degraded by 17.71%.Reduction in V_{oc}</math> was only to 97.86 of the clean module value.The average degradation of power and efficiency during the entire period of work (30 days) is 9.86%.$	Effect of humidity since site was located near Mediterranean Sea. Dust effects more pronounced on cloudy days.

Ghazi et al (2013)	P, TO	Brighton, UK [1 month] and Laboratory experiments	Glass cover sheets; Examination of c-Si module installation	Transmission as function of soiling for various tilt angles (Brighton outdoor conditions) as function of average dust density Comparisons to indoor controlled tests.	Rainy conditions in UK tended to clean panels—so soiling was not a major issue. Other sources (birds) provided issues for PV modules (shading)
Gostein et al. (2013)	P, A	General outdoor measurement conditions/locations	Thin-Film CdTe and Cryst-Si Modules	Examines the difference between a soiling ratio (SR) metric calculated from measured temperature-corrected short-circuit current values (SR^{Isc}) (the fraction of irradiance reaching the soiled modules) versus a SR calculated from measured temperature-corrected PV module maximum power values (SR^{Pmax}) (the fraction of power produced by the soiled modules compared to clean modules). Clearly shows the need to determine power and Isc monitoring as representative.	Establishes differences and needs in monitoring power or short-circuit current.
Gottschaig et al. (2013)	P, S, A	Loughborough, UK [6 years]	Thin-Film a-Si, c-Si and CIGS modules	Focus primarily on operating conditions (temperature, irradiance, spectrum) Good analysis our outdoor exposure testing.	Minor focus on soiling/snow
Hirohata et al. (2013)	P	Japan [5 months]	PMMA Fresnel Lens (CPV)	Measurements with and without superhydrophobic (SH) coatings (anti-soiling) Without SH: 7.1% reduction after 5 months; With SH: 4.2% in same period.	Relationship between dust accumulation and wind conditions discussed.
John et al. (2013)	P	India	Super-hydrophobic antisoiling coatings	Development of TiO ₂ -based SH coating for dust mitigation, coupled with water delivery system. System design presented.	Prototype system
Kalogirlou et al. (2013)	P, MC	Cyprus and Controlled Experiments [>1 year]	Mono-, Multicrystalline and Amorphous Si Modules	Performance under prevailing Cyprus soiling conditions. Artificial dust & dust/moisture controlled experiments Power reductions comparisons among 3 technology types (as high as 43% loss in power) Dry dust affects a-Si module less than other two types	Interesting experiments with moisture. Cleaning experiences related (little required in summer; periodic cycles recommended during other times).
Kawamoto and Shibata (2013)	MC	Laboratory Testing	PV Panel Cleaning System	Electrodynamic system using electrostatic force to remove sand from module surface. Design uses parallel wire electrodes embedded in a cover glass plate of a solar pane (with single-phase voltage applied)—80% effective in dust removal	Power used is near zero.
Kazem et al. (2013)	P	Laboratory controlled study with outdoor tests	Multicrystalline Si module	Study of different dust/particle/pollutant types (ash, sand, red soil, calcium carbonate, silica gel) on the performance parameters of a commercial PV module.	Power output reported as function of time.
Klimm et al. (2013)	P, MC, CE	Laboratory Studies	10 MW PV plant as baseline	Anti-soiling coatings evaluated for effectiveness (dust mitigation and durability). Economic analysis of financial gain for 10MW PV plant with anti-soil investment.	Comparison of glass types
Kumar et al.	CM	Laboratory studies	Si panel	Modeled showing both exponential and linear	Dust: Bentonite-clay (aluminium

(2013)		(controlled conditions)	(12 cm x 8 cm; glass surface)	dependence of the efficiency on the gram-accumulation.	phyllosilicate)
Levitan (2013)	P	Deserts	CSP and Other Solar Technologies	Popular discussion of what may limit the deployment of solar technologies in the desert regions (dust, water)	Scientific American “Clean Energy Wars”
Marion et al. (2013)	P, MS	Colorado, USA [2 winter periods (2010-2012)]	6 PV systems	Focus on <i>snow</i> Measured monthly PV losses of up to 90%, annual losses from 1% to 12%. Residential and non-residential systems	Good analogies for particulate soiling (models useful)
Massi Pavan et al. (2013)	MS	Italy (PV plant data) Laboratory modeling effort	Large-scale PV plants	Comparison between two different modeling techniques for the determination of the effect (power losses) of soiling on large-scale PV plants (neural network based). Comparisons to standard test condition results.	Modeling and results useful for determining cleaning cycles.
Mejia and Kleissl (2013)	P, TO	California, USA [year-long study]	Residential and Commercial PV Installations	Changes in efficiency of 186 residential and commercial PV sites were quantified during dry periods during 2010 Soiling losses averaged 0.051% per day overall and 26% of the sites had losses greater than 0.1% per day Module tilt angles investigated	Losses reported by geographical location in California Annual energy yield data
Midtdal and Jelle (2013)	P, MS	General	Mitigation Coatings for Solar Collectors	Extensive examination and evaluation of mitigation coatings for solar products. Currently, photocatalytic hydrophilic self-cleaning (dust) products appear superior to the hydrophobic. Perhaps it is that the the hydrophobic products are “easy-to-clean” rather than “self-cleaning”. Hydrophobic products have substantial benefits indoors, seeing that photocatalytic actions does not work without UV radiation, whereas photocatalytic hydrophilic products seem to have the greatest potential for further use with outdoor glazing products. Photocatalytic hydrophilic products require manual cleaning as well as the hydrophobic products.	Excellent presentation on mitigation coatings, their use, their limitations, and their benefits.
Moharram et al. (2013)	P, MC	Cairo, Egypt [~45 days]	14-KW power plant-Crystalline Si Modules	Efficiency decreased 50% after 45 days of cleaning with non-pressurized water Using cleaning solution of anionic and cationic surfactants, efficiency remained constant (no degradation) “Cleaning the PV panels using the developed water system and a mixture of surfactants minimizes the amount of water needed for cleaning as well as the energy for spraying the water”	German University in Cairo Focus on minimizing water use in cleaning Detailed system description/design
Ndaiye et al. (2013)	P	Senegal [1-year study]	Commercial Multi- and Polycrystalline Si modules (2 locations)	Losses in module parameters (Voc, Isc, Pm, FF) as a function of dust accumulation over annual exposure. Power loss 18%-78% (mainly through Im) Losses in FF differing significantly for mc and pc	Power loss rates up to 17%/month observed. Consideration of shading effects.

				modules (different manufacturers)	
Piliougine et al. (2013)	TR, P	Southern Spain [1-year]	6-Crystalline Si Modules	Evaluation of a new, commercial self-cleaning coating for photovoltaic applications Mean daily loss: 3.3%/day for uncoated; 2.5%/day for coated. Transmission losses: 12% uncoated, 10% coated.	3 coated/3 uncoated modules for comparison. Inhomogeneity of dust distribution caused additional power losses.
Qasem et al. (2013)	P, MS, CM, TO	Kuwait [Several years]	CdTe Modules	Spatially-resolved 3 dimensional model is developed using circuit analysis software PSPICE to investigate inhomogeneous, deposited dust on PV modules Effect of tilt angle on dust accumulation Extensive performance and reliability information	Temperature-performance for CdTe Module hot-spots due to dust shading
Rajput and Sudhakar (2013)	P	Outdoors; Bopal, India [undefined timeframe]	Two Si panels (Each 0.404 m ²) glass surface	Power and efficiency monitored as function of accumulation; Power reduction up to 92% and efficiency loss up to 89%)	Monitored solar radiation, temperature
Rao et al. (2013)	P, A	Tropical Locations India	PV Technologies	Focus PV in tropical locations. Effects of wind, temperature, dust and other environmental conditions are evaluated and discussed.	Experimental evaluations of panels in field. Similar to paper published in 2014
Sabah and Faraj (2013)	MC	Laboratory	Automated Robotic Cleaning System	Cleaning cycles determined using sensors Robotic, automated brushing system design is presented for PV panels	Though title indicated “self cleaning solar panels”, an automated robotic system with sensors is described.
Santana-Rodriguez, et al. (2013)		Mexico City, Mexico	PV System (Power Plant) 6.1 kW	Grid-connected system evaluation 4 solar PV technologies: mono-Si, poly-Si, a-Si:H, and CdS/CdTe Comparison for soiling and other environmental conditions Typical environmental pollution throughout the year in Mexico City causes the deposition of a fine dust layer onto the system “practically in a permanent way.” An estimated loss of around 10% due to dust typical.	Detailed information about overall system performance
Sayyah et al. (2013)	P, MC	General	CSP	Focus on the impact of dust accumulation on concentrated photovoltaic (CPV) and concentrated solar power (CSP) systems. Electrodynamic Screens (EDS) as mitigation methodology	Compare natural (rain) cleaning, manual cleaning, and EDS
Schaeffer et al. (2013)	MC	General	Dust Mitigation Coatings	Development of transparent superhydrophobic coatings for large surface areas—based on <i>functionalized silica nanoparticles</i> to coat optical elements and measured their transmission between 400 nm to 800 nm.	Application to instrument protection but also to dust mitigation. Interesting micro-level physical studies and spectral effects.
Smith et al. (2013)	P, MC	Portland, Oregon USA [>4 months]	PV Arrays (Si)	Power losses up to 4% for uncleaned panels (17 days). Beneficial effects of rainfall and manual cleaning reported.	Temperature effects reported Cleaning procedures documented
Sueto et al. (2013)	MC	Laboratory experiments	PMMA Fresnel Lens (CPV)	Anti-soiling coating structure: WO ₃ /Graded Layer/Acrylic Urethane Capping Layer/PMMA Lens	Applied coatings to commercial Fresnel lens used in CPV (effective

				Coating effective in reducing particle adhesion and the surface electrostatic potential Relationship between these parameters investigated	in reducing particle adhesion) Detailed information on coating application.
Touati et al. (2013a)	P	Qatar [100 days]	Monocrystalline Si and Amorphous Si Modules	10% decrease in efficiency due to dust accumulation during this period. Amorphous panel surfaces less affected by dust accumulation than the crystalline Si ones	Cleaning schedules indicated. Temperature effects on technology types reported.
Touati et al. (2013b)	P, CM	Qatar	Monocrystalline Si Modules	Mono-crystalline PV panels, caused the efficiency to decrease by 10%. This limitation makes solar PV an less reliability power source for unattended/remote locations Cleaning challenges discussed (regular cycles)	Some indications and evaluations of durability (e.g., undergoing cleaning)
Tylim (2013)	P, CE, MC	General	PV	Discussions of effects on annual energy delivery (case studies). Requirements for periodic cleaning	Cleaning schedule requirements Cost-benefits
Wang, et al. (2013)	CM,MC,	Laboratory studies; microscale force investigations	General studies of adhesion	AFM evaluations of force between particles and insulating surfaces. Result showed that charge is a factor in attracting particles, but not in the force holding them to the insulator	Use of AFM to measure force. Good fundamental study.
Yadav et al. (2013)	A,CM	Laboratory-wind tunnel experiments	Heliostats (CSP)	Understanding of deposition of dust on heliostats (planar); Air flow and deposition studied for single and multiple heliostat configurations; Velocity distribution and flow pattern critical to determining deposition	Soil composition of Jodpur studied and saltation in region; Ash used for experiment comparable to particles collected from PV panels in region.
Zhou et al. (2013)	MC	Laboratory Studies Western China	Electrodynamic Screens	Physical investigations of dust particle movements on surfaces for dust electrodynamic screens. Mathematical model of the dust removal efficiency and the optimization method for electric curtain design (multivariate function optimization methods). Theory basis for the development of self-cleaning techniques for large solar systems under climate conditions of western China	Detailed modeling and analysis.

*P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning;

*A=ambient conditions/effects; *I=Instrumentation; *S=Spectral Effects; TO=Tilt/Orientation

Table 3. Summary of dust and soiling papers in 2014 indicating primary focus, device/materials investigate, conditions and findings. The *Focus Code* (for primary contributions) is: *P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning; *A=ambient conditions/effects; *I=Instrumentation, *S=spectral effects, *TO=Tilt/Orientation

Publication Source	Focus* (see code below)	Location [Duration]	Solar Device Type	Key Findings	Comments/Other Conditions
Abrams et al. (2014)	P,TR, MC	12 field stations across the USA [1 year]	Si (module glass)	Report of robust dual-function anti-reflective and anti-soiling coating that is hydrophobic and self-cleaning	Installations by Sun Edison Procedures on preparation of glass included
Amarnadh et al. (2014)	P, TR, TO, A	Vellore, India (Southeast India) [1 month]	Monocrystalline and Polycrystalline Si Modules; Glass Plates	Orientation (,) of module data. Efficiency vs. days of exposure; dust density vs. days of exposure Transmission of test plates reported vs. dust coverage; Function of tilt.	Temperature, humidity, and solar irradiance data provide.
Al-Jawah et al. (2014) (Dissertation)	MS, MC	Hypothetical 1-MW PV Plant in Saudi Arabia	PV	Development, testing, and evaluation of a framework to assist investors in photovoltaic (PV) power plants in dust-prone and arid regions make informed decisions regarding selection among PV panel cleaning alternatives. Multi-criteria decision method (MCDM) used to select among cleaning alternatives in light of competing criteria.	Questionnaire developed for experts to rate the degree of their agreement or disagreement on a Likert scale. Average results indicate agreement that the study can improve selection among PV panel cleaning alternatives.
Anshir Bashir et al. (2014)	P, A, TO	Taxila, Pakistan [Winter Months-January - March]	a-Si (single junction), single-crystal & multicrystalline Si modules	Some review of past performance reports associating performance with dust accumulation. Indications that soiling lowers the module operating temperature. Discussion of tilt, humidity, and wind effects.	Mono- and polycrystalline modules: Better performance in high-irradiance condition with lower power output at low irradiance. Amorphous Si: Good performance in low irradiance (better light absorption)
Boyle et al. (2014)	TR, A, CM	Colorado	Glass Cover Plates	Airborne concentrations of particles (smaller than 10 μm) are collected simultaneously dust accumulated on PV glass cover plates. Differences reported; effects of wind velocity.	Purpose for future modeling and dust accumulation interpretations.
Burton and King (2014a)	P, TR, CM	Laboratory Studies (standardized soil testing)	Multicrystalline Si Cells	Laboratory techniques to apply (simulated) soil to a specimen with quantification of results of the film on the transmission of incident light. Artificial soil is used and applied by aerosol spray device. Transmission performance loss due to deposited soil is predicted over a range of mass loadings. Demonstration that the composition (NIST traceable) of the blend, (termed "standard grime" by the authors) had a significant and reproducible influence on measured	Aim at correlating laboratory studies with outdoor results and mitigation of soiling effects.

				performance loss.	
Burton and King (2014b)	P, CM, S	Laboratory Studies	PV glass coupons	Spectral loss due to the <i>color profile</i> (spectral effects) of the accumulated soiling material investigated. Use mixtures of previously reported “standard grime” with common mineral pigments (Fe ₂ O ₃ and göthite). Results show: Soils rich in red pigments (Fe ₂ O ₃) - greater integrated response than göthite containing soils rich in yellow pigment. The yellow soils caused a greater attenuation in 300-450 nm spectrum region and can have significant implications to specific devices (e.g., CdTe and mutlicrystalline Si technologies).	Focus on laboratory studies that can link with outdoor soiling results and effects of spectral content and relationships to “color” effects of soils.
Burton and King (2014c)	I, TR, MC	Laboratory Studies	Glass Cover Sheets	Expansion of earlier technique to measure the optical losses due to an artificially applied dust film. Sprayed artificial soil (described in paper). 1 gm/m ² determined to be the limit of mass sensitivity to changing reflection characteristics (about same as a daily observed soil accumulation) Linear decreases observed between 1 gm/m ² and 5 gm/m ²	Interesting observations and analysis about ensuring that the losses due to soil accumulation are outside the instrumental error. Also, importance to CPV of these particular studies are stressed.
Cano et al. (2014)	P, CM, A, TO, I	Mesa, Arizona USA [3-month January through March period]	Crystalline Si Reference Cell Coupons	Investigations of the interrelationships among soiling loss, terrain of the installation, tilt angle, rain frequency/intensity. Design and development of inexpensive soiling station which evaluates soiling loss at different tilt angles (0°, 5°, 10°, 15°, 20°, 23°, 30°, 33°, 40°). Hot-dry climate results: the 0° tilt angle showed a 2.02% loss whereas 23° and 33° showed soiling loss close to 1% (during the first 3 months of 2011).	Detailed discussions, descriptions, and applications of developed test station. Computations of the solar irradiance performed.
Chamaria et al. (2014)	MS	Laboratory Simulation and Modeling India	50 kW c-Si System	Loss modeled and calculated in terms of kWh. Low latitudes having medium dust density should also have daily cleaning due to lower tilt angle and higher dust deposition. Less of a problem in higher latitude regions.	Modeling and simulation of this 50kW system in India. Discussions of critical impact factors for dust loss for PV panels.
Cristaldi et al. (2014)	I, P, A, M	Milan, Italy and Laboratory Studies	Commercial Si module	Development of a (simple) method to evaluate dust on the performance of PV modules. Estimates reduction in PV performance. Accuracy/errors of measurements/technique evaluated. System includes pyramometer and PV module.	Good discussion of techniques and limitations Computations of the solar irradiance performed. Method differentiates between dust issues and other module ageing problems.
Fernández-García et al. (2014)	MC, TR	Spain	CSP	Outdoor exposure of solar reflectors and applying different cleaning methods. Most effective cleaning method is using demineralized	Interesting investigation of a variety of cleaning processes for reflectors.

				water and a brush, with an average efficiency of 98.8 % in rainy periods and 97.2 % in dry seasons. Innovative cleaning method based on a steam device with a soft tissue was inefficient (efficiency of 97.3 % in a rainy period).	
Ghosh and Ghosh (2015)	P,MS,MC	India	PV	Evaluation of the effects of dust adherence to module surface on efficiency. Modeling of the efficiency loss (Power, IV characteristics, irradiance) Evaluation of mitigation approaches (coatings, cleaning)	Description of cell and system operation.
Gostein et al. (2014)	P, MC	Desert Southwest USA, Arabian Peninsula, Western Australia [Annual Data]	Thin-Film CdTe Power Plants	Discussion on correct data collection methods. Soiling levels correlated with PV power plant performance. Discussions of measurement precision, non-uniformity soiling issues, & rainfall required for performance recovery.	Soiling Ration (SR) utilized. Identified soiling as “3 rd most significant factor affecting PV power plant performance”—after irradiance and temperature.
Griffith et al. (2014)	P	South Africa [~1 year]	CSP Mirrors	Candidate CSP site cleanliness assessment using dust collection buckets and loss of reflectivity on mirror samples installed at the site. Instrumentation design presented.	Reflectivity loss (soiling) measured on a monthly cycle using a specially designed portable imaging-instrument. this purpose.
Herrmann et al. (2014b)	MS, A	Laboratory Studies	General GIS Analysis for Dust Risks at Geo Locations	Use of Geographic Information Systems (GIS) to model the soiling potentials in Middle East and North Africa (MENA) countries. Major result: Dust risk map of the MENA region, showing significant differentiation of soiling potentials.	Contribution to the development of appropriate indoor durability testing procedures and the identification of the most favorable solar locations.
Herrmann et al. (2014a)	MS, A	Focus on MENA region	PV	Discussions of parameters and events controlling soiling. Modeling of soiling (influences of climate conditions and collector characteristics). Global soiling rates estimated by GIS.	Preliminary but important modeling directions. Discussions of soiling conditions, controlling environments, etc. MENA information.
Hunter et al. (2014)	MC	Southwest U.S. Laboratory Studies	CSP mirrors and heliostats	Development and discussion of low cost, easy to apply anti-soiling coatings based on superhydrophobic (SH) functionalized nano-silica materials and polymer binders that mitigate dust adhesion problems and significantly reducing mirror cleaning costs/facility downtime	Coatings have excellent SH properties with water contact angles >165° and rolling angles <5°.
Iberraken (2014)	P, A	Sahara Desert (Maghreb Countries, primarily Algeria)	Crystalline Si Modules	Effects of fine dust, dust wind, & sandstorms on the PV I-V characteristics reported.	Extensive report on reliability issues in these harsh, desert climates (e.g., EVA discoloration).
John et al. (2014b)	P, TO, MS	Arizona	Crystalline Si Modules from Field	Tilt evaluations (angle-of-incidence-AOI) and effects. PV modules retrieved from the field that had different dust densities have been measured for the dependence of the AOI curves on the dust gravimetric densities.	Performed on specially developed tilt fixtures for precise evaluations.

				Measured AOI curves were fitted and validated with the analytical/empirical models (literature reports).	
John et al. (2014a)	P, TR, S, CM	Mesa, Arizona USA [1.5 years]	Crystalline Si Modules	Spectral reflectance and quantum efficiency changes at various wavelengths for dust accumulations. Heavily soiled solar cell (~74.6gm/m ²): very high reflectance loss and very low quantum efficiency at all wavelengths (measured vs cleaned panel). Examined 3-soiled solar cells cleaned using 3 different cleaning techniques - 60psi compressed air clean, brush assisted 30psi compressed air clean and water cleaned. Short circuit current, spectral reflectance's and quantum efficiency's dependence on wavelengths is reported before and after each cleaning steps	Various dust layer thickness studies for spectral changes/effect.
Kazem et al. (2014a)	P, TR	Iraq (outdoor) [1 year]	Crystalline Si Modules	Compares the energy performance of four identical PV-panels with 20 watt power; one cleaned daily, one weekly, and one uncleaned. by using Solmetric PV Analyzer for a period of Efficiency of panels determined: significant decrease in the relative conversion efficiency which was (7.9%, 20%, 27%) for the weekly cleaned, monthly cleaned and seasonally cleaned panels respectively relative to daily cleaned panel and the reduction in average performance factor was (5.7 , 12.6 ,17.2) for weekly cleaned, monthly cleaned and seasonally cleaned panels respectively.	Climatic and weather conditions included.
Kazmerski et al. (2014)	P, MC	MENA and India [>1 year]	Crystalline Si primarily; Some CdTe thin film	Microanalysis of the chemistry and morphology of dust particles from these desert regions. Scanning of individual grains for composition. Effectiveness of dust mitigation coatings (from Saudi Arabia measurements) Overview of ongoing and past research.	Indications and evaluation of cementitious-layer formations due to moisture.
Ketjoy and Kony (2014)u	P,MS	Thailand [5-month perio]	Mono- and Multi-crystalline and Amorphous Si	Approach: 40 W of amorphous silicon, 75 W of monocrystalline silicon and 125 W of multicrystalline silicon; cleaned and exposed module from each group. Dust accumulation measured by dust-fall jar methods. The quantity of dust on PV module 55 mg/m .d, 260 mg/m .d and 425 mg/m effect to decrease solar radiation of 3.71 %, 11.15 % and also effect to decrease electrical energy output from PV module of; 3.50 % of amorphous silicon when quantity of dust is equal to 260 mg and 7.28 % when quantity of dust is equal to 425 mg, 2.96 % of mono crystalline silicon when quantity of dust is equal to 260 mg and 5.79 % when quantity of dust is equal to 425 mg and 2.83 % of multi crystalline silicon when quantity of dust is equal to 260 mg and	Modeling; relationship between the accumulative dust on photovoltaic module and electrical energy output of PV module

				6.03 % when quantity of dust is equal to 425 mg.	
Khonkar et al. (2014)	P, MC, CE	Saudi Arabia Desert Conditions	CPV arrays (>1000x concentration)	Differences between CPV (high conc.) and flat-plate PV. Dust 5-times greater effect on these CPV than flat-plate PV. I-V characteristics monitored to determine soiling effects. Current cleaning procedures discussed for these CPV	Study indicates need for further modeling. Questions on cost-effectiveness of cleaning in desert regions.
Kumar and Kaur (2014)	P	China [~1 year]	PV general	Impact: blocking transmission of sunlight, increasing of temperature of the and surface corrosion (due to chemical nature of the dust).	Discussions of general reliability issues and operation of PV cells/systems
Leloux et al. (2014)	P, M	High DNI Regions	CSV	Bankability issues relating to soiling, dust, climate, performance	DNI and environmental conditions
Lombardo et al. (2014)	P, MC	Various European Locations	Glass Materials in the Built Environment	Examination of rural, urban, and industrial environments for particulate matter deposited on glass. The formation of the deposit at the glass surface is a quite complex phenomenon controlled by the deposition of both gaseous and or particulate matter--complex reactions taking place before (in the atmosphere), during and after the deposition (at the glass surface)	Extensive chemical analysis. Indications for solar panel issues (including possible ageing)
Lorenz et al. (2014)	P, MS, CE	Laboratory Simulations	Module Cover Glass Sheets	Evaluation of hydrophobic and hydrophilic dust mitigation coatings. Gains of >3% over uncoated surfaces (transmittance) Cost simulations and modeling based on lab simulations of dust coverage (with and without mitigation coatings)	Detailed modeling results for “dry years” and “wet years”
Lorenzo et al. (2014)	P	Southeast Spain	2-MW PV Plant	Non-uniform dust deposits lead to more than the short-circuit current reduction resulting from transmittance losses. When the affected PV modules are in a string together with other cleaned (or less dusty) ones, operation voltage losses arise-leading to power losses.	Non uniform temperature distributions result from the “shading” effects of the non-uniform dust distribution—‘hot spots’
Maghami et al. (2014)	MC	Malaysia, Industrial Area	Si Modules	Identified industry-source dust on panel surface: siliceous, alumina and cement identified by EDX Impurity distributions on particle surfaces (maps of dust samples)	Also, highway (traffic) pollutants and bird droppings. Elemental identifications
Mallineni et al. (2014)	P, A, TO	Arizona	4-16 year-old PV Power Plants	Soiling losses in hot-dry climate zone. Soiling losses in 4-PV power plants with two different surroundings (urban and rural) and 3-different installation types (ground mount - fixed tilt, 1-axis tracking and rooftop - fixed tilt) Major Results: Site 3 (Glendale, Arizona) - rural, 1-axis tracking, 12 years, 6.9% soiling loss; Site 4b (Mesa, Arizona) - urban, horizontal tilt (ground), 16 years, 11.1% soiling loss; Site 4c (Mesa, Arizona) - urban, 1-axis tracking, 4 years, 5.5% soiling loss; Site 6 (Tempe, Arizona) - urban, 5o fixed tilt (rooftop), 8 years, 3.8% soiling loss.	Excellent basis from reliability observations on these installations.

Mazumder et al. (2014)	P, I, TR, CM	Laboratory Studies	Electrodynamic Screen Systems for PV (and CSP)	Report on transparent electrodynamic screens (EDS) and their applications for self-cleaning operation of solar mirrors - primary focus on the removal dust particles <30- μ m diameter while maintaining specular reflection efficiency < 90%. Focus: (1) loss of specular reflection efficiency as a function of particle size distribution of deposited dust, and (2) the effects of the electrode design and materials used for minimizing initial loss of specular reflectivity in producing EDS-integrated solar mirrors.	Very detailed description of technique, use, limitations, and effectiveness.
Mejia et al. (2014)	P, I	San Diego, CA USA [~3 months summer]	Large PV (86.4 KW) System	Large PV system: Soiling losses were found to be 0.21% per day, with an observed efficiency decrease from 7.2% to 5.6% during a 108 day dry period (summer). Following this observation, rain event restored most of the lost efficiency to 7.1%.	Correlated with weather station data located about 3.4 Km from site. Good irradiance correlations.
Ndiaye et al. (2014)	P	Dakar, Senegal	Multi- and Monocrystalline Si Modules	Pmax loss from 18 to 78% respectively for the polycrystalline module (pc-Si) and monocrystalline module (mc-si). Imax loss from 23 to 80% respectively pc-Si and mc-Si modules. Vmax and Voc are not affected by dust accumulation for both technologies.	Exposure times (dust accumulation) FF also monitored.
Naeem (2014)	P,MC	Metro Phoenix, Arizona USA	Si Modules	Two studies that focus on investigating the soiling effect on the performance of the PV modules: (1) investigate the optimum cleaning frequency for cleaning PV modules installed in Mesa, AZ (2) evaluating the soiling loss in different locations of Metro Phoenix area of Arizona, to validate the daily soiling rate obtained from the mock rooftop setup Soiling rates: (1) -0.061% for 20° tilt, and (2) -0.057 to -0.85% for 13-28° tilt.	5 cities in Phoenix area considered. Good description of experimental setup.
Pape et al. (2014)	P, ME, MC	Spain [Cleaning 3-26 day periods]	CSP systems (solar resource monitoring systems)	Effects of dust on irradiance affecting solar thermal plant performance and monitoring systems. Soiling characteristics of the rotating shadow band pyranometers compared to pyroheliometers. The pyroheliometer suffered of linearly growing errors of up to 30% after one month, the soiling impact on the rotating shadow band device generally stayed below 2%, without any visible trend of growing errors	Very useful discussions of solar resource monitoring equipment under various environmental conditions. Correction algorithms to improve the accuracy of the RSP sensors explained and presented. Instrument cleaning evaluated.
Polizos et al. (2014a)	MC	Coatings (Laboratory Studies)	CSP	Transparent superhydrophobic (SH) coatings based on multifunctional silica nanoparticles and polymeric binders developed and evaluated. Key findings: • The optical clarity of the coatings. The particles (average size smaller than 200 nm) were uniformly	Promising long-life coatings for CSP applications and PV as well

				<p>dispersed in organic binders and resulted in coatings with an average roughness value smaller than 30 nm. The nano-particles do not scatter light at wavelengths > 250 nm because of their small dimensions.</p> <ul style="list-style-type: none"> • Enhanced particle binder interfaces with multifunctional configuration significantly improves the abrasion resistance of the coatings without degrading their SH properties. • Accelerated weathering durability (UV exposure). Indications that the coatings are environmentally durable over several years of simulated UVA exposure. 	
Polizos et al. (2014b)	MC	Laboratory Studies	Coating Development	<ul style="list-style-type: none"> • Method for fabricating scalable and cost-effective superhydrophobic coatings. • Chemical modification of diatomaceous earth nanostructured particles. • Abrasive resistance depends on the size and geometry of the diatomaceous earth (potential for long life). 	Potential application for dust mitigation/protection for modules
Qasem et al. (2014)	P, TO, S, TR	Laboratory Studies (comparisons to Kuwait data)	Amorphous Si, CIGS, CdTe, and Crystalline Si Modules (and glass sheets)	<p>PV performance and cover glass transmittance measurements.</p> <p>Experiments as functions of tilt angle.</p> <p>Demonstration of relationship between dust density and light transmittance (through glass) for dust below $\sim 19\text{mg/cm}^2$.</p> <p>Higher-bandgap technologies (e.g., a-Si) more affected because of spectral response than lower bandgap (e.g., c-Si)</p>	<p>Extensive correlations among dust density, light transmission, and performance degradation.</p> <p>Chemical and physical data of dust used in these studies.</p>
Rao et al. (2014)	P	Bangaluru, India (Laboratory and Outdoor Testing)	Si PV modules	<p>Effect of outdoor exposure (dust) on I-V characteristics</p> <p>Indoor simulations</p> <p>Isc is sensitive to measuring dust-induced losses (from both indoor and outdoor measurements)</p>	Extensive I-V measurements and comparisons between outdoor and laboratory (controlled conditions) measurements.
Sakhuja et al. (2014)	TR, MC, CM	Singapore [3 months]	Si Modules (glass surfaces)	<p>Development, production, and testing of self-cleaning nanostructured glasses for mitigation.</p> <p>Results: Loss of 2% in efficiency for planar glass packaged solar module; and loss of 0.3% in efficiency for nanostructured glass packaged solar module.</p>	Durability results promising for these nanostructured layers.
Sansom et al. (2014)	P, MC	Laboratory Studies	CSP (polymer and glass covers)	<p>Comparisons of the optical properties and surface texture of glass and polymer film collectors for concentrating applications.</p> <p>Degradation of glass and polymer reflecting surfaces with sand and dust abrasion.</p> <p>Anti-soiling and self-cleaning coatings tested on glass and polymer film collector surfaces</p>	<p>Measurements: specular and hemispherical reflectance, surface roughness, and electron microscopy.</p> <p>Results interesting for CPV as well.</p> <p>Cleaning processes.</p>
Said and Walwil	P, MC, TR, A	Dhahran, Saudi Arabia [45 days]	Module glass covers and PV	Effects of dust deposition of PV performance and cover glass transmission.	Interesting and novel AFM studies of adhesive forces (fundamental

(2014)			panels	ARC glass effects (indicated reduction in soiling) Higher particle size—higher adhesion forces Effects of moisture on enhanced adhesion 20% reduction in power output (5 gm ² dust accumulation) after 45 days exposure	studies of adhesion). Extensive studies of composition.
Sayyah et al. (2014)	P	Laboratory Studies (Electrodynamic Screens)	PV modules	<ul style="list-style-type: none"> • Database reported for soiling losses in different parts of the world. • Environmental and design parameters of dust deposition discussed and evaluated. • Laboratory, outdoor, and predictive soiling studies. • Emerging method of electrodynamic screen for dust removal introduced and evaluated 	Detailed overview of electrodynamic screen effectiveness and use.
Schaeffer et al. (2014b)	MC	Laboratory (superhydrophobic)	Solar anti-soiling coatings	Simple, durable spray-on SH coating based on functionalized SiO nanoparticles that can easily be applied to surfaces (e.g., optical sensors, photovoltaics, sights and lenses, textiles, construction materials, and electronic devices). Durability and mechanical properties reported.	See also paper Schaeffer et al. (2014a).
Schaeffer et al. (2014c)	MC, ME	Laboratory (superhydrophobic)	Solar anti-soiling coatings (large area)	Development of silica nanoparticle-based nano-coatings that can be applied to large surface areas (modules). Focus on transparency between 400 nm and 800 nm.	Contact angles, morphology, etc. reported. Modeling of coatings
Semaoui et al. (2014)	P	Algeria (Southern desert)	Si Modules	Dust accumulation over several months, with average loss of 4.38%/month	Ghardaia region, 600 km south of Algiers
Sharma et al. (2014)	P, A	Gurgaon, India [>28 months]	HIT and multicrystalline Si Modules	Reliability and performance of HIT and multicrystalline Si modules under operating conditions, including soiling. All tested modules had observed soiling issues. Enhanced soiling effects at module edges (mounting points)	Wide-ranging investigations of the performance of two module technologies under operating conditions at the SERC (now NISE) test facility near New Delhi.
Sibai (2014)	P,MS	Saudi Arabia (hot dry desert)	Modeling of PV module performance	Mathematical model for series-parallel photovoltaic modules, evaluate the model, and present the I-V and P-V characteristic plots for various temperatures, irradiance, and diode ideality factors – dust considerations.	Modeling for general hot climate conditions—with additional analysis for dust
Sinha et al. (2014)	P, A	Various	Si technologies	Atmospheric variables considered: temperature, humidity, aerosols, clouds, soiling, and snowfall, for arid versus temperate regions, with specific comparison of the U.S. Southwest and Saudi Arabia with the U.S. Southeast and Ontario, Canada. Specific dust/snow results: -3% for soiling with cleaning, and 0 to <-5% for snowfall	Temperature and humidity effects received special attention.
Smith et al. (2014)	P	Laboratory and Outdoor Testing	Crystalline Si Modules	Flowing water system investigated to improve PV module performance, including the avoidance of soiling.	Focus on temperature and irradiance benefits for improvements in performance.

Stark et al. (2014)	P,TR	Laboratory Experiments, Modeling	CSP	Investigation of the application of electrodynamic screens for “efficient and cost-effective” dust removal from CSP mirrors Prototype mirrors constructed and evaluated Incorporation of transparent EDS causes an initial loss of 3% but would be able to maintain specular reflectivity more than 90% to meet the industrial requirement for CSP plants	Modeling, ray tracing Specular reflectivity measured inside weather chamber
Sulaiman et al. (2014)	P, I	Laboratory Testing (controlled conditions)	Crystalline Si	Focus: dust, water, sand and moss on the surface of solar photovoltaic panel: Primarily development of experimental system for controlled observations. Up to 86% loss in performance reported.	Cleaning requirements discussed.
Tan, et al. (2014)	MS, MC	Indoor issues with dust and surfaces	Indoor surfaces (general)	Air-conditioned environments (emphasis) for these indoor studies of dust adhesion to various surfaces. Interrelationships of dust adhesion with degree of surface roughness. Modeling using van de Waals forces.	Some focus on health issues, but studies of science interest to dust and soiling for PV
Toivola, et al. (2014)	P	Arizona, Florida, Ohio-USA [Multiyear outdoor testing]	CIGS Modules	Outdoor testing for reliability of Miasolé thin-film CIGS modules. Testing conditions and apparatus described; data shows soiling effects.	Product reliability investigation for thin film CIGS product.
Weber et al. (2014)	A, P, MC, I	Laboratory Studies	Si Modules	Development of soiling and abrasion tests for PV module surfaces. Beneficial effects of anti-soiling coatings demonstrated (anti abrasive and soil mitigation) Cleaning procedures discussed/demonstrated-including impact of cleaning on surface Abrasive tests and instrumentation designed and tested	Test procedure key to determining the service lifetime of module glass and coatings (dust mitigation, antireflection, etc.) under soiling conditions.
Wolfertstetter et al. (2014)	I, P	General Locations	Metrology Stations	Effect of dust on MHP monitoring stations. Pyrheliometers extremely sensitive to dust (DNI). Reductions of measured DNI values exceeding 25% in only a few weeks are common. Methods to improve examined, the soiling level of each individual sensor can be determined by following a special sequence of sensor cleaning and brief breaks combined with a close examination of the sensor responses.	Dust observations on the effects on monitoring equipment.
Wu et al. (2014)	MD	Laboratory Studies	ITO Electrodes on Glass (Electrodynamic)	ITO (transparent) electrons deposited in “forked” pattern on a glass substrate to electrostatically mitigate dust issues. Report of 95% effective.	First of two studies (other in 2015 that improves on this approach)

*P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning;

*A=ambient conditions/effects; *I=Instrumentation; *S=Spectral Effects; TO=Tilt/Orientation

Table 4. Summary of dust and soiling papers in 2015 indicating primary focus, device/materials investigate, conditions and findings. The *Focus Code* (for primary contributions) is: *P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning/Maintenance; *A=ambient conditions/effects; *I=Instrumentation, *S=spectral effects, *TO=Tilt/Orientation

Publication Source	Focus Code*	Location [Duration]	Solar Device Type	Key Findings	Comments/Other Conditions
Alami Merrouni et al. (2015)	TR, MC	Morocco (Eastern) [3 months]	Solar Mirrors (CSP)	<p>First reporting of the effect of dust on different solar mirror materials in Morocco.</p> <p>For glass and aluminum mirror materials, the "drop on cleanliness per time interval" was same for all the mirrors (over all the test periods).</p> <p>Highest average cleanliness drop per month for the horizontal mirrors was 45 % and 33 % for the glass and aluminum mirrors</p> <p>The +45° mirrors are less effective with a cleanliness drop of about 14 % for both reflectors.</p> <p>Mirrors installed on the 0° and -45° angles remained cleaner with a cleanliness average of about 97 % for both mirrors</p>	Detailed analysis of the cleanliness of the mirror materials under the outdoor exposure conditions.
Ali et al. (2015)	P	Taxila, Pakistan [3-4 month]	Si PV Modules (single and poly)	<p>Two modules of each type exposed for 3 months in winter timeframe.</p> <p>Monocrystalline and polycrystalline modules showed about 20% and 16% decrease of average output power respectively compared to the clean modules.</p> <p>Loss of output power and module efficiency in monocrystalline module was more compared to the polycrystalline module</p>	Decrease of module efficiency (clean - dirty) in case of monocrystalline and polycrystalline module was 3.55% and 3.01%, respectively
Alnaser et al. (2015)	P, MC, CM	Bahrain [~6 months]	Crystalline Si 500-kWp Array	<p>Density of accumulated dust ranged from 5-12 g/m² with an average PV power loss up to 40% of maximum available.</p> <p>Compositional analysis: Si (~15%) and Ca (~15%) in addition to Al (~6%), Mg (~5%), and Fe (~5%).</p> <p>Modeling with result of prediction (equation) of loss in transmission with dust accumulation.</p>	<p>Interesting study and discussions of the 8 of 2088 panels in array.</p> <p>Detailed explanation of performance of this large array with micro inverters (individual for each panel)</p> <p>Some discussion of cleaning.</p> <p>Energy management discussions.</p>
Alqatari et al. (2015)	M, P, MC	Saudi Arabia	Modeling of dust mitigation in Saudi Arabia	<p>Case study: modeling for dust mitigation in Saudi Arabia (large-scale PV)</p> <p>Spatiotemporal model analyzes atmospheric dust in the simulation of PV system performance in KSA.</p> <p>Modeling and analysis also considers dust mitigation, allowing for optimizing choice of self-cleaning technology at a particular time and location (aimed at recovering losses due to the soiling)</p>	Modeling uses Saudi Arabia as a test case for validity.

Al Saluos (2015)	P,CM	Jordan, Laboratory Studies	Crystalline Si Modules	Module parameters (Voc, Jsc, Pm) as a function of dust depositions showing power losses of 90%. Investigation of dust characteristics	Reduction in system efficiency reported.
Bashker and Arya (2015)	P,	India	PV Panels (Si)	Accumulated dust on the surface of PV solar panel can decrease the PV system's overall efficiency up to 35% per month. Performance of PV panes is studied experimentally and used in calculating the effect of deposited dust on the energy efficiency of PV systems.	Specific for India. Discussions of maintenance.
Benatiallah et al. (2015)	P, A	Sahara Areas	Crystalline Si Modules	Interrelated dust and wind effects on the electrical performance of modules	Abstract of studies
Bhattacharya et al. (2015)	P, MC	Tripura, India [~6 months]	2-identical 37-W crystalline Si modules	Reduction of Voc, Isc, and efficiency reported (ranging from 9% to 13% loss in efficiency for 6 month duration). One module cleaned other left for exposure.	Data on Isc and Voc as function of irradiance level. Cleaning recommended.
Bohra et. Al (2015)	P	Bangalore, India Urban environments [1-month]	Rooftop PV	4 technologies: Poly-Si, Mono-Si, HIT, and CdTe thin film studied (for suitability in the urban environment). CdTe had highest soiling loss (10.88%) after one-week and Poly-Si the least (4.21%).	Metropolitan areas considered for dust effects on PV performance Rooftop installations for these studies.
Boppana (2015)	P, M	Arizona USA	PV Power Plants (Si and CdTe)	Outdoor characterization of dust on two power plants located in cold, dry climate. Statistical risk analysis for power plant through failure mode, effect, and criticality analysis based on non-destructive field techniques and count data of the failure modes.	18 and 19-year old power plants analyzed. Frameless and framed modules compared
Bouaddi and Ihlal (2015)	P, TR	Southwest Morocco	CSP Mirrors	Evaluation of the rate of soiling of exposed solar mirrors by performing extensive reflectance measurements every 3-4 days Results: summer period (dry with predominant wind from Northeast) the cleanliness of the mirrors has dropped significantly: average monthly cleanliness is 69%, 68%, 76% for glass mirrors, and 76%, 74%, 72% for first type Al mirrors measured respectively in July, August, and September.	Agadir, Southwest Morocco (30°26'3.8"N 9°29'31.1" W), a site isolated from urban pollution and industrial activity. Weather data provided.
Bouchalkha (2015)	MS, MC	Modeling for Solar PV Panels in Abu Dhabi	PV	Light scattering calculations from dust particles using the <i>T-matrix model</i> to estimate the effect of dust accumulation on the module surface Results: 10% reduction in module output after few days. Conclusion: Cleaning every 10-15 days (under normal Abu Dhabi ambient conditions)	Detailed layer-by-layer modeling to calculate dust effects on transmitted light.
Boyle et al. (2015)	P	Colorado USA (2-Front Range Locations) [1-5 weeks]	PV Glass Cover Plates	Mass accumulation rates between 1 and 50 mg/m ² /day were observed (with variations over the year, location, and tilt angle). Total mass accumulations up to 2 g/m ² for 1-5 week	Uncertainties in the measurements evaluated and discussed. Semi-arid area.

				period, with transmission losses to 11%. Transmission was a linear function of the mass of the dust accumulation (and not a function of the tilt or location)—with reduction of ~4.1% for every g/m ² accumulation.	
Brophy et al. (2015)	P, MC	Field and Laboratory Studies	PV modules	Field performance of anti-soiling coatings on PV modules Local conditions (climate zone) are critical to performance of the coatings. Tests on “robust dual-function antireflective and anti-soiling coating that is dense, homogeneous and intrinsically hydrophobic.” Hydrophobic coatings have strongest anti dust adhesion properties	Hydrophobic, low surface energy coatings Dual purpose (also ARC) Two years data in field
Burton et al. (2015a)	TR, MC	Laboratory Studies	Module Glass Coupons	Objective: Low mass loadings of soil of PV module surfaces are common but difficult to quantify. Synthetic soil analog was sprayed onto glass coupons at with a high-volume, low-pressure pneumatic sprayer. A 0.1-g/m ² soil loading determined to be the limit of mass measurement sensitivity (similar to some reports of daily soil accumulation).	Collected field-soil samples analyzed to develop a compositional analog for lab studies.
Burton et al. (2015b)	TR, MS, P	Laboratory Studies	High-Concentration PV Systems (CPV)	Modeling of the performance of 3-junction concentrator cell systems to various color pigments mixed in naturally occurring soils (spectral response changes). Wide changes in the responses (transmission) with different soils shown to be important for these CPV technologies. Major effect on altering the current balance between the top and middle cells in the 3-cell structure, especially with “yellow” pigmented soils.	Transmission changes evaluated on glass coupons. Modeling of effects of these different soils on the solar spectrum.
Cáceres et al (2015)	CE	Santiago, Chile	PV	Economic study of PV installations for residential PV in Santiago, Chile. Effects of dust on panel performance and on the LCOE for on-grid and off-grid.	PM-10 considerations
Cekirge and Elhassan (2015)	P	General	CSP (Towers and Parabolic Troughs)	Modeling of tower and trough systems for viability and operation <i>Small discussion of dust effects and potential impacts</i>	Good system comparisons
Chakraborty and Sadhu (2015)	P	Coal City, India	Mono-Si, HIT, Poly-Si, Micromorph, a-Si:H, CIGS, CdTe Modules	“Technical mapping of PV” A-Si:H modules perform better under the typical temperature variant and dry environmental condition of the Coal City of India	Environmental conditions include soiling. Technology comparisons.
Choi et al. (2015)	MC	Development of dust prevention coatings (laboratory)	Dust mitigation coatings	Superhydrophobic coatings with high haze (microstructured films) Studied gradient-index (<i>n</i>) material-based microstructures, <i>i.e.</i> , magnesium fluoride (MgF ₂ , <i>n</i> ~	Optoelectronic applications of these anti dust coating is the intent.

				1.37) film-coated SU8 ultraviolet curable polymer ($n \sim 1.59$) microcones (MCs) with tapered architectures, on silicon (Si, $n \sim 3.9$) substrates Some report of antireflection properties of layers	
Doumane et al. (2015)	MS	Laboratory	Si PV	Module modeled by an equivalent electrical circuit (components have time-dependent characteristics determined under accelerated tests). Optical transmission loss leads to as much as a 11.5% over 25 years.	Extensive electrical engineering treatment of the module (circuit approach)
Ferrada et al. (2015)	P	Chile (coastal desert zone) [16 months]	mc-Si and crystalline Si modules	Difference of energy yield between the technologies larger for summer and smaller for winter. Performance ratio decreased due to the dust accumulation between $-0.04\%/day$ up to $-0.13\%/day$ (positive ambient temperature gradient), and between $-0.13\%/day$ up to $-0.18\%/day$ (negative ambient temperature gradient).	Studies include uncertainty analysis.
Fuentealba et al. (2015)	P	Atacama Desert, Chile [638 days]	a-Si/ μ c-Si tandem cell and Multicrystalline Si Modules	<i>Thin-film module performance:</i> Decreased due to the dust accumulation at a rate from 4.2%-3.7%/month (decreasing temperature conditions) and from 4.8%-4.4%/month (increasing temperature). <i>Multicrystalline silicon module performance:</i> Degradation rates were 2.4%-1.8%/month (decreasing temperature), and 6.2%-3.7%/month (increasing temperature).	Coastal zone of Chile. Electricity rate costs reported for each technology—based on performance measurements. Cleaning thin-film modules had better return on electricity price than for cleaning the mc-Si technology.
Guo et al. (2015)	P, MS	Doha, Qatar [7 months]	Si Modules in Test Field	PV performance, ambient dust and weather conditions measured continuously from June 1 through December 31, 2014 Performance losses: 0.0042 +/-0.0080 per day for modules cleaned every sixth month, and 0.0045 +/-0.0091 per day for modules cleaned every second month, in terms of a “cleanness index” based on the PV module’s temperature. Modeling of dust performance.	Very good discussion of conditions and of measurement approaches.
Hacke et al.	P, MC	Laboratory	Reliability links with dust/soiling	Effects of module soiling on module glass surface resisting and resulting potential induced degradation (PID) Compared 3-soil types (Arizona road dust, soot, and sea salt) Variation in results for the soil type PID correlation with resistance.	“Sea salt yielded a 3.5 orders of magnitude decrease in resistance on the glass surface when the RH was increased over this RH range. Arizona road dust showed reduced sheet resistance at lower RH, but with less humidity sensitivity over the range tested. The soot sample did not show significant resistivity change compared to the unsoiled control.”

Jasim et al. (2015)	P,MC,CE		Crystalline Si PV (cleaning systems)	Effects of dust on PV panel performance. Presents automated, closed-water cleaning system Techno-economic analysis is provided	
Jiang and Lu	P,A	Laboratory studies (Effect of module surface T on dust deposition)	Monocrystalline Si Modules (156 mm x 156 mm)	Effects of temperature on dust accumulation on Si modules. Measured deposition densities of dust particles were found to range from 0.50 mg/ m ² -0.84 mg/m ² . Higher surface temperature modules has a lower density due to the effect of thermophoresis force arising from the temperature gradient between its surface and the surrounding air; energy output ratios were found to increase from 0.947 to 0.971 with the increase of temperature gradient.	“Most obvious temperature gradient” for the thermophoresis force was found to be lower than 40 C.
Jin et al. (2015)	MS	Modeling and experimental studies (Laboratory)	Modeling of nanoscale roughness effects on particle collection	General studies of colloidal- and nano-scale particles on surfaces. Interesting look at surface roughness at the nanoscale and the effect of adhesion. Non-PV overall	This is a general paper on how particle are deposited on surface and how they interact with the surface. Mostly modeling—some experimental results.
John et al. (2015)	P,S	Laboratory Studies (India dust samples from various locations)	Si, CdTe, CIGS	Controlled artificial dust (from various climate-zone locations in India) deposition on module surfaces. Example: Soiling loss on a Si cell with Mumbai dust (17.1%) is about two times that of Jodhpur dust (9.8%) for the same soil gravimetric density of 3g/m ² . Spectral effects is highlighted by technology (Si, CIGS, CdTe)—corresponding to those bandgaps.	Excellent report on spectral effects (quantum efficiency measurements on cells). “The dust collected from Mumbai showed highest spectral loss, followed by Pondicherry, Agra, Hanle, Jodhpur and Gurgaon. The worst affected module technology was amorphous silicon (17.7%) followed by cadmium telluride (15.7%), crystalline silicon (15.4%) and CIGS (14.5%) for the same density (2.5g/m ²) of dust from Mumbai”
Karim et al. (2015)	A,S,TR	Morocco	CSP	Exposed mirrors in natural aging sites present low loss in reflectivity which doesn't exceed 0.4% after 240 days of outdoor exposure. The effect of sand properties on erosion phenomenon was found that the sand hardness affect the roughness parameters, while the sharp forms influence on the impacts properties(roughness parameters, impacts number, impacted area, impacts size diameter). Increasing the sand particle's size also increases the impacted area and the losses in relative specular	Ageing studies involving outdoor testing and laboratory experiments.

				reflectivity.	
Kawamoto and Shibata (2015)	MC	Laboratory Studies	Si Modules	Cleaning using electrostatic force to remove sand from the surface of solar panels. Effectiveness: more than 90% of the adhering sand is repelled from the surface of the slightly inclined panel after the cleaning operation.	Power consumption ~0. Parallel wires embedded in cover glass plate.
Kazmerski et al. (2015)	P, MC	Laboratory Studies of individual dust particles (from Middle East and from Brasil)	Module glass surfaces	Chemical/compositional measurements of dust samples from various geographical locations. Adhesion measurement by AFM of individual soiling grains on module glass surfaces indicating the relationship between particle surface chemistry and the adhesion. Comparative measurements on glass and glass coated with superhydrophobic and superhydrophilic films.	Studies of fundamental adhesion of single-dust particles to PV module glass surfaces. Cementation effects of moisture and from diesel fuel emissions indicated. Samples from Saudi Arabia and Brasil.
King (2015)	P, MS	Laboratory Simulations and Experimental Studies	PV module performance	Derating of PV module performance for many factors, including environmental ones such as soiling and dust. Advanced Soiling Study determining the influence of soil composition and morphology on light attenuation and scattering. Developed an improved modeling of angle-of-incidence accounting for diffuse utilization and soiling Validated a methodology to predict the string mismatch "derate factor" from available module characterization results (also relating to soiling)	The advanced soiling portions of this report are important and detailed. Very good gathering of the influences sources and factors for soiling.
Klimm et al. (2015)	A,MC,TR	Laboratory and Field Testing	PV Module Glass	Soiling and abrasion testing for harsh climates. Laboratory sand trickling test stand according to DIN 52 348. Results of the outdoor and indoor tested material show the strong influence of dust types and material properties on soiling and durability of the surfaces.	Laboratory apparatus description for testing
Klugmann-Radziemska (2015)	P, MC, CM	Gdansk, Poland (3 locations)	Si PV Modules	Linear relationship between the thickness of the soiling layer and the performance of the module (with reported observation of 25.5%/mm loss in power for naturally deposited dust). Maximum observed daily loss of 0.8%. Studies of morphology and chemistry of collected dust.	Module cleaning methods reported. Good background section providing foundation for these studies.
Lee et al. (2015)	MC	Taiwan	CIGS Modules	Development of a dust-monitoring platform system. CIGS modules monitored since 12/2012 Daily soiling loss (up to 30%/month) reported and impact on utility-scale plants and return-on-investment discussed	WIKI site that is providing fast access to PV monitoring results.
Leem et al. (2015)	MC	Laboratory	Si mini-modules	2-dimensional periodic conical micrograting structured (MGS) polymer films are studied for both "light harvesting"-ARC and self-cleaning for Si PV modules. Careful and detailed experimental studies.	Fabrication procedures provided for the nanostructured PET films.

Leem and Yu (2015)	MC	Laboratory [Month]	III-V solar cells	Self-cleaning surfaces for III-V solar cell applications. "Artificial inverted compound eye structured (ICESs)" (polydimethylsiloxane (PDMS) films with ARC and self-cleaning functions for the enhancement of solar power generation in encapsulated GaAs solar cells	Used GaAs cells with a cover glass
Li et al. (2015a)	MS, MC	Modeling and simulation	PV Modules	Modeling and simulation of a device for the removal of dust from module surfaces. PV module light electrical parameters analyzed for various directions of dust removal from the module.	Brush studies primarily
Li et al. (2015b)	MS, P	Modeling of Performance	PV Plant	Electricity quality and performance modeling based upon operating factors (including dust) Operating Statuses Identification (OSI) is utilized in the simulation formulation.	Modeling that includes effects of shading (e.g., from dust)
Lim et al. (2015)	MC, TR, P	Laboratory Studies	Dye-sensitized solar cells (DSSC)	Hydrophobic polymers evaluated for dust mitigation and for antireflection properties for PV modules. polydimethylsiloxane (PDMS) patterned with negatively tapered nanoholes (NHs) as a protective antireflection layer of the external glass surface.	Studies of the degree of hydrophobicity of the surfaces of these films. ARC-dust mitigation dual purpose.
Lopes de Jesus et al. (2015)	TR, MC, CM	Laboratory Studies	PV Module Glass	Hydrophilic, transparency, and adhesion studies of TiO ₂ /SiO ₂ composites containing different titanium content. Contact angles near 0° obtained. Abrasion and durability data provided.	Self-cleaning attributes of these films reported. Superhydrophilic coatings.
Martinez-Plaza et al. (2015)	P, MC	Qatar	PV (tracking, fixed)	Results of outdoor exposure of a specific model of multicrystalline silicon (mc-Si) photovoltaic (PV) modules after their first complete year of operation at STF. Impact of module cleaning frequency, use of commercial anti-soiling coatings and module mounting on either fixed, one-axis-tracking or two-axis-tracking systems was studied.	Discussions of durability and cleaning requirements (detailed)
Martinez et al. (2015)	P, MC	Qatar	Various PV technology performance evaluation for dust situations	Description of the Qatar Foundation test facility (testing PV technologies most suited for the Qatar climate). Study examines several thin-film technologies for environmental conditions (including dust)	The Qatar Foundation group has extensive facilities and staffing for dust investigations. Possible indications of the better performance of high Eg thin films in heat/dust
Michels et al. (2015)	P, TO	Paraná, Brasil	Solarex MSX56 Si Modules	Dust levels reduced electricity production (power) levels by approximately 16%.	Mainly study of outdoor performance reliability
Mondal and Bansal (2015)	MC	General	PV Modules	Cleaning of PV panels with specially designed robotic arm (SPCRA) with 4-degrees of freedom. Arm has 2 prismatic and 2 revolute joints; system has unique end effector with water sprinkler, air blower and wiper.	Cost effectiveness and versatility of the system is discussed. System design and operation is provided. Nice summary of various cleaning systems

Negash and Tadiwose (2015)	P,TO	Ethiopia	Si PV Modules (site of 10kW PV plant)	Soiling losses for eight different tilt angle (0°, 5°, 11.6°, 15°, 21.5°, 25°, 30° and 35°) including the latitude of Bahir Dar City (11.6°), Ethiopia	25° tilt angle had a least insolation loss and largest amount of energy absorbed
Nazar (2015)	P, MC	Discussions and Effects	General PV Modules	Improving the efficiency of panel by dust cleaning. Robots, self-cleaning surfaces (electrodynamic screens, robotic vacuum cleaners are discussed.	Includes discussion of solar trackers
Naeem and Talizhmani (2015)		Jeddah, Saudi Arabia		Correlations between climate zone (meteorological and other) conditions and the dust conditions. Requirements for local cleaning of PV module frequency and needs. Modeling of dust conditions on performance over time.	Conference paper presentation that summarized useful information for Jeddah, KSA and similar climate zones.
Pettersen et al. (2015)	P	Nordic Climates	Soiling/Snow on PV modules	SPICE modeling. Effects of panel orientation for snow and dust. Experiments for dust on mini-modules with and without anti-soiling coatings. Dry and wet cleaning of modules evaluated	Cleaning in all cases provided better results than coatings. Snow especially critical for non-uniformity (shading) issues.
Pettersen (2015) <i>Masters Thesis</i>	P, MS	Modeling and Experiment (Various Norway Conditions) [~1 year]	Si PV Module and Module Glass	Model to predict and quantify the effects of partial shading (e.g., by dust) on PV module output using <i>LTspiceIV</i> . Experimental validation under Norway climatic conditions: reduction in transmission of 0.92% for untreated module glass and 1.1% with anti-soiling coating (no effectiveness of coating)-over 1 week. Snow accumulations and effect on output also studied.	Results for snow depth reported. Extensive modeling results provided on shading effects.
Penetta et al. (2015)	P,TR	Queensland, Australia	CSP Reflectors	Dust accumulation effects on CSP performance. Correlations among humidity, temperature, and dust accumulation	Discussion of dust compromising mirror reflectivity.
Phinikarides et al. (2015)	P, MS	Cyprus [3-4 years]	PV System Performance PV (c-Si, CIGS, CdTe)	Seasonable variations, including those due to dust and soiling; estimated linear degradation rates Seasonal variations varied by technology. Differences in degradation rates reported by technology	Not significant focus on dust and soiling
Piotrowska-Woroniak et al. (2015)	P, MS	Poland (Great Lakes Region) [2012-2013]	PV 264 Si panels [50.16 kW]	Dust emissions modeled (kg/year) Analysis showed the installation resulted in reduction of dust emissions into the atmosphere—as well as greenhouse gases.	Indirect analysis of dust effects on performance
Rahman et al. (2015)	P	Laboratory Studied	Si PV Module (90W)	Observed module power reduced by 7.70 W due to dust falling on the surface of the solar module.	Studies primarily directed to temperature and climate effects.
Rajasekar (2015)		Laboratory Studies of Soiling; Field Studies for Power Plant	PV Panel Surfaces; Poly-Si minimodules and single mono-Si cells	Development of indoor experimental simulation techniques for soiling of PV surfaces. Failure and degradation modes of about 744 poly-Si glass/polymer frameless modules fielded for 18 years under the cold-dry climate of New York was evaluated. Thesis reports primarily results of indoor soiling studies.	Characterization tests: I-V, reflectance and quantum efficiency (QE) on both soiled, & cleaned coupons Controlled and well-reported laboratory experiments

Sansom et al. (2015)	P,MC	Egypt and Libya	CSP	Methodology to predicting the optical performance and physical topography of the glass collector surfaces of any given CSP plant in the presence of sand and dust storms, providing that local climate conditions are known & representative sand and dust particles samples are available	Characterization of dust particles CSP plant in Egypt, plus sand and dust samples from two desert locations in Libya
Scanlon (2015)	P	International	All PV Technologies	Summary of NREL R&D efforts in reliability, testing, standards development, and quality assurance—and coordinating such work internationally. Portion on importance of dust effects.	General report on reliability. Reference to NREL webcast.
Schaeffer et al. (2015)	MC	Laboratory (superhydrophobic coatings)	Solar Collectors	Functionalized silica nanoparticles to coat various optical elements with measured contact angles and optical transmission between 190 and 1100 nm on these elements. A described solution of the functionalized silica nanoparticles exhibited superhydrophobic behavior with a static contact angles $\geq 160^\circ$.	Focus on windows and mirrors. Discussions of various hydrophobic properties.
Schill et al. (2015)	P	Gran Canary Island (Spain) [>5 months]	Crystalline Si Modules	Soiling due primarily to building construction in area. 20% loss in efficiency (monitoring of I-V characteristics) in 5-month period. Non-uniformity in distribution (caused by rain effect) detected by shape of I-V characteristics. Heavy rain event reported to clean the modules—and completely restore the performance.	Extensive instrumentation for monitoring of performance, climatic conditions, and irradiance. Detailed information on experimental setup and data acquisition.
Sengupta et al. (2015)	I, S	General (worldwide best-practices)	General best practices for solar measurements	Effect of dust and other airborne particles on the measured solar resource; Effect of these particles and other atmospheric components on the calibration of instrumentation. Very detailed information on maintenance and calibration of instrumentation.	Handbook links with major research and solar resource determinations in harsh climates such as Saudi Arabia (see KACARE portal:
Shi (2015)	P,CE	China	CSP	Viability of CSP technology in China power market. Consideration of dust as a obstacle to deployment and economics	M.S. Thesis Good discussions of issues in China relating to other parts of the world.
Shirakawa et al. (2015)	P, CM, A	São Paulo, Brazil [6-18 months]	Crystalline Si Modules	<i>Sub-aerial biofilm</i> (SAB) development on PV module surfaces (tropical conditions). Fungi were an important component of these biofilms; very few phototrophs were observed. Major microorganisms detected were melanised meristematic ascomycetes and pigmented bacterial genera <i>Arthrobacter</i> and <i>Tetracoccus</i> ; Some diverse algae, cyanobacteria and bacteria were identified in biofilms. Photovoltaic modules: significant power reductions after 6, 12 (both 7%) and 18 (11%) months.	No differences between 6- and 12-month power observations in modules attributed to dual nature of soiling. Soiling effects removed by light rain.

Sleiman et al. (2015)	TR	General	Solar Roofs	Primarily a “cool roof” study, but this paper also examines solar reflectivity. Accelerated aging method for solar is both repeatable and reproducible within an acceptable range of standard deviations: the repeatability standard deviation s_r ranged from 0.008 to 0.015 (relative standard deviation of 1.2–2.1%) and the reproducibility standard deviation s_R ranged from 0.022 to 0.036 (relative standard deviation of 3.2–5.8%).	The 3 rd in a series of 3 papers on “cool roof”. The other two are cited in the notable others section.
Spataru et al. (2015)	MS	Denmark	Crystalline Si PV Test System and Laboratory Modeling	Shading and soiling considerations. Proposes a complete diagnostic method for detecting shading, increased series-resistance losses, and potential-induced degradation of the PV generator by analyzing changes its current-voltage characteristics.	Practical application: the diagnostic parameters and rules applied “as is” to a field test setup consisting of a crystalline silicon based PV string and a commercial string inverter capable of measuring the I-V curve of the PV string, yielding a similar high-detection rate.
Sulaiman et al. (2015)	P	Malaysia	Crystalline Si Modules	Effects of dust accumulation on the performance of PV panels. Experiment; dust particles on solar panels with a constant-power light source, to determine the resulting electrical power generated and efficiency. Results: the accumulated dust on the surface of photovoltaic solar panel can reduce the system’s efficiency by up to 50%	Characterization of local Malaysia climate zone.
Tanesab et al. (2015)	P, MC, TR	Perth, Australia Temperate Climate Zones	PV Modules	Properties of dust: particles deposited on PV modules’ surface were dominated by fine particles built of large amounts of quartz (SiO_2), followed by calcium oxide (CaO) and some minors of feldspars minerals (KAlSi_3O_8), which are primarily responsible for transmittance losses. Module degradation for this 18+ year installation was mostly due to non-dust issues, but dust can be attributed to some levels in the range of 16%-29%.	Modules were in field for 18 years with no cleaning schedule
Verma and Singhal (2015)	P	Gujrat, India Plant commissioned in 2012	Grid-Connected PV Plant (20 MW) a-Si:H modules	Major causes of cells/modules operating outside standard conditions: Voltage drop in the dc cables and protection diodes; Dirt and dust, Shade; Dispersion of parameters among the PV modules; Operation voltage out of the maximum power point (MPP); Spectrum and angle of incidence. Bird droppings major cause of “shading” Always returned to within 1% of rating after cleaning	Consideration of all loss mechanisms for this large thin-film PV plant; detailed review of power plant operation/reliability.

Weber et al. (2015)	P	Worldwide overview of issues	Soiling and Cleaning of PV Modules; Potential effects on module abrasion	Importance of relationships among soiling, cleaning, and abrasion of module surfaces. Abrasion of coatings (e.g., ARCs) Climate zone informations requirements (wind speed/direction, dust compositions, moisture, natural cleaning, water availability) Power reduction (more severe in desert countries than Germany)	Discussion of PVQAT activities with dust/interactions Very good overviews of cleaning, indoor simulations, testing, standard procedures, abrasion, etc.)
Wu at al. (2015)	MC	Laboratory Study	Electrodynamic Coatings	Transparent ITO “fork electrodes” were configured on glass substrates with different widths and separations. The effects of the electrode width, the electrode spacing, voltage, frequency, waveform, and the duty ratio on the dust removal efficiency were investigated for artificial dust removal. Optimum conditions of dust removal: voltage - 1500 V, frequency - 15 Hz, square wave, 10% duty ratio, the electrode width - 0.5 mm, electrodes spacing -1.3 mm; dust removal with with 99% efficiency.	Follow up on previous work in 2014
Xu et al. (2015)	TR	Laboratory and New York City	Glass Covers	Development and testing of high-performance polymeric coating on glass with a nano-scale surface roughness: both anti-reflective (ARC) as well as superhydrophobic properties.	Mechanical and chemical durability investigated and reported (suggests 30-year lifetime in NYC).
Yang et al. (2015)	ME	Acceptance procedures	Utility-Scale	Methodology for performance acceptance testing of solar boilers using Linear Fresnel Reflectors (LFR) with Direct Steam Generation (DSG). Proposed methodology is based on relevant ISO and American standards applying an adapted parameter identification technique. Discussions regarding soiling and measurement requirements and uncertainty analysis are also provided.	Methodology anticipated to improvement in the operation of next LFR power plants.
Yilbas et al. (2015)	P, TR, CM	Laboratory Measurements	PV Glass Surfaces (Chemical/compositional properties of dust & adhesion to surfaces)	Effects of soiling and mud on the optical, chemical, and mechanical properties of PV module glass. The characteristics of the dust and the mud (cementitious layers) formed from this dust examined by analytical techniques (optical & scanning electron microscopy, AFM, XRD, energy spectroscopy, FTIR). Microtribometer used to measure adhesion, cohesion and frictional forces required for the removal of dry mud from the glass surfaces.	Extensive chemical and physical measurements of dust partial properties. Interesting and useful investigations of adhesive forces holding dust and “mud” to the module glass surfaces (macroscale determinations of force)

Zell et al. (2015)	P, A, S	Saudi Arabia	Solar Resource Assessment	<p>In-depth and comprehensive discussion/analysis of solar resource assessment (results for Saudi Arabia) Stresses that accurate measurements of the solar Resource depend critically on environmental conditions such as ambient air temperature and dust levels that affect/control project output, and are critical to project deployment.</p> <p>Affect of dust on solar spectra—and on the output from the PV system in these desert regions because of dust adhesion.</p>	<p>Excellent discussion and analysis of the solar resource in the desert regions-especially Saudi Arabia. Studies tied with the important KACARE program for solar deployment and research in KSA See website for detailed info on solar resources: https://rratlas.kacare.gov.sa/RRMMPublicPortal/)</p>
-----------------------	---------	--------------	---------------------------	---	--

*P=Performance, *MS=Modeling/Simulation; *CM=Composition/Morphology; *TR=Transmission/Reflection; *CE=Cost/Economics; *MC=Mitigation/Cleaning;

*A=ambient conditions/effects; *I=Instrumentation; *S=Spectral Effects; TO=Tilt/Orientation