

2003

Effect of carbon nanotube doping on critical current density of MgB₂ superconductor

S X. Dou

University of Wollongong, shi@uow.edu.au

W. K. Yeoh

University of Wollongong

J. Horvat

University of Wollongong, jhorvat@uow.edu.au

M. Ionescu

University of Wollongong, mionescu@uow.edu.au

Follow this and additional works at: <https://ro.uow.edu.au/engpapers>



Part of the [Engineering Commons](#)

<https://ro.uow.edu.au/engpapers/98>

Recommended Citation

Dou, S X.; Yeoh, W. K.; Horvat, J.; and Ionescu, M.: Effect of carbon nanotube doping on critical current density of MgB₂ superconductor 2003.

<https://ro.uow.edu.au/engpapers/98>

Effect of carbon nanotube doping on critical current density of MgB₂ superconductor

S. X. Dou, W. K. Yeoh, J. Horvat,^{a)} and M. Ionescu

Institute for Superconducting and Electronic Materials, University of Wollongong, Northfields Avenue, Wollongong, New South Wales 2522, Australia

(Received 8 August 2003; accepted 23 October 2003)

The effect of doping MgB₂ with carbon nanotubes on transition temperature, lattice parameters, critical current density and flux pinning was studied for MgB_{2-x}C_x with $x=0, 0.05, 0.1, 0.2,$ and 0.3 . The carbon substitution for B was found to enhance J_c in magnetic fields but depress T_c . The depression of T_c , which is caused by the carbon substitution for B, increases with an increasing doping level, sintering temperature, and duration. By controlling the extent of the substitution and addition of carbon nanotubes we can achieve the optimal improvement on critical current density and flux pinning in magnetic fields while maintaining the minimum reduction in T_c . Under these conditions, J_c was enhanced by two orders of magnitude at 8 T and 5 K and 7 T and 10 K. J_c was more than 10 000 A/cm² at 20 K and 4 T and 5 K and 8.5 T, respectively. © 2003 American Institute of Physics. [DOI: 10.1063/1.1634378]

The effect of C-doping on superconductivity in a MgB₂ compound has been studied by several groups.^{1–8} The results on C solubility and the effect of C-doping on T_c reported so far vary significantly due to the precursor materials, fabrication techniques, and processing conditions used. It appears that lower sintering temperatures and short sintering times result in an incomplete reaction and hence lower C solubility in MgB₂. Ribeiro *et al.* used Mg and B₄C as precursors to synthesize C-doped MgB₂ by sintering at 1200 °C for 24 h.⁹ A neutron diffraction study confirmed that the most likely solubility of C in MgB₂ is up to around 10% of C in the boron sites, resulting in a large drop of both T_c and the a -axis lattice parameter.¹⁰ Recently, Lee *et al.* synthesised C-doped single crystalline MgB₂ at high pressure (5 GPa) and high temperature (1600 °C), obtaining the C solubility of 15% at the boron sites and T_c depression to below 3 K.¹¹ All these studies on C doping into MgB₂ have only focused on the effect on superconductivity. From the applications point of view, the effect of C doping on the flux pinning properties is crucially important. The author's group has reported a significant improvement in $J_c(H)$ and H_{irr} in MgB₂ through nano-SiC doping.¹² Recently, the effects of C doping on the flux pinning and critical current density in MgB₂ has been studied using amorphous carbon¹³ and diamond,¹⁴ both showing improvement of J_c at elevated magnetic fields. Wei *et al.* have studied the superconductivity of MgB₂-carbon nanotube composites.¹⁵ However, the effect of carbon nanotube doping on critical current density and flux pinning has not been reported. Among various carbon precursors, carbon nanotubes are particularly interesting as their special geometry (high aspect ratio and nanometer diameter) may induce more effective pinning centers compared to other carbon-containing precursors. In this letter we report the results on control of the extent of carbon nanotube substitution and addition to achieve an enhancement of critical current density and flux pinning by two orders of magnitude in magnetic fields.

Polycrystalline samples of MgB_{2-x}C_x were prepared through a reaction *in-situ* process.^{16,17} High purity powders of magnesium (99%), amorphous boron (99%) and multi-walled carbon nanotubes of 20–30 nm diameter were weighed out according to the nominal atomic ratio of MgB_{2-x}C_x with $x=0, 0.05, 0.1, 0.2, 0.3,$ and well-mixed through grinding. We stress that the values for x are the nominal values throughout the paper, and the actual substitution of C for B will be shown to be less than these values. The powders were pressed into pellets of 10 mm in diameter and 3 mm in thickness using a hydraulic press. The pellets were sealed in Fe tubes, then heat treated at 700 to 1000 °C for 10–120 min in flowing high purity Ar. This was followed by a furnace cooling to room temperature. An undoped sample was also made under the same conditions for use as a reference sample. The phase and crystal structure of all the samples was obtained from x-ray diffraction (XRD) patterns using a MAC Science MX03 diffractometer with Cu $K\alpha$ radiation. Si powder was used as an internal standard to calculate the lattice parameters. The grain morphology and microstructure were also examined by a scanning electron microscope (SEM) and a transmission electron microscope (TEM).

The magnetization was measured over a temperature range of 5–30 K using a Physical Property Measurement System (PPMS, Quantum Design) in a time-varying magnetic field with sweep rate 50 Oe/s and amplitude 8.5 T. Bar-shaped samples with a size of $4 \times 3 \times 0.5$ mm³ were cut from each pellet for magnetic measurements. The magnetic measurements were performed by applying the magnetic field parallel to the longest sample axis. The magnetic J_c was calculated from the height of the magnetization loop ΔM using the Bean model: $J_c = 20 \Delta M / [a(1 - a/3b)]$, with a and b as the dimensions of the sample perpendicular to the direction of applied magnetic field and $a < b$. J_c versus the magnetic field has been measured up to 8.5 T. The low field J_c below 10 K could not be measured due to flux jumping. The T_c was determined by measuring the real part of the ac susceptibility at a frequency of 117 Hz and an external mag-

^{a)}Electronic mail: jhorvat@uow.edu.au

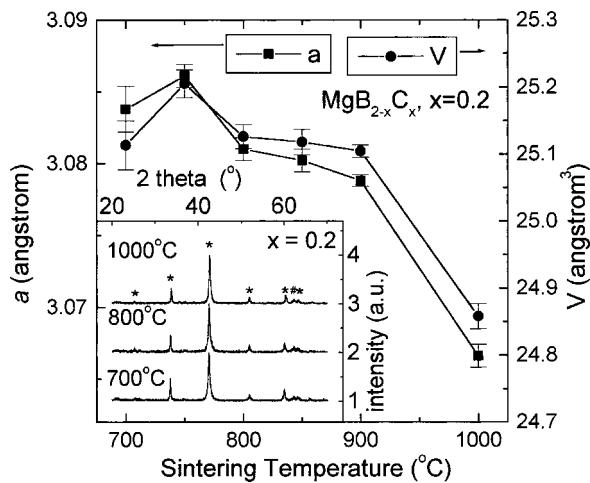


FIG. 1. The variation of lattice parameter a and the unit cell volume of $\text{MgB}_{2-x}\text{C}_x$, with nominal $x=0.2$, with sintering temperature. The carbon was in the form of multiwalled carbon nanotubes. Inset: an XRD pattern for carbon nanotube doped MgB_2 , sintered at temperatures as indicated in the figure. Symbols* and # indicate the XRD peaks for MgB_2 and MgO , respectively.

netic field of 0.1 Oe. T_c was defined as the onset of the diamagnetism.

Figure 1 shows lattice parameter a , and unit cell volume versus sintering temperature for the sample doped at $x=0.2$. The a axis decreases monotonically with increasing sintering temperature. The c axis varies very little with the sintering temperature and consequently the volume changes in a similar manner as a (Fig. 1). The decrease of the a -axis is an indication of the boron substitution for carbon. The decrease of the a axis is more pronounced at temperatures above 900 °C, because of the enhanced carbon substitution at these temperatures, which is consistent with several recent papers.^{10,11} However, the substitution reaction in the present work is far from completion, even at sintering temperature of 1000 °C, in comparison with those treated at a higher temperature (1600 °C) and high pressure.¹¹ Thus, we achieved a condition of partial substitution of C for B and the addition of a majority of C, which may react with B to form BC, as detected using EELS,¹⁸ or stay as carbon nanotubes. The inset to Fig. 1 shows the XRD data for carbon nanotube doped samples, sintered at three different temperatures. The sample was a well-developed MgB_2 phase, with only a small amount of MgO present, similar to other high-quality MgB_2 samples.^{12,13,17}

Figure 2 shows the transition temperature (T_c) for the doped and undoped samples determined by ac susceptibility measurements. The T_c onset for the undoped sample is ~ 38 K. For the sample doped at $x=0.2$ (10% of B) and sintered for a fixed period of 30 min, the T_c decreases with increasing sintering temperature. T_c reaches 31 K for the sintering temperature of 1000 °C. This indicates that the extent of the C substitution reaction increases with increasing sintering temperature, resulting in T_c depression, which is consistent with the recent reports.^{10,11} The effect of doping level on T_c was also studied at a fixed sintering temperature of 800 °C for 30 min. For this sintering temperature, T_c only drops slightly, 2.0 K at a C doping level of $x=0.3$ (15% C doping). These results suggest that only a small amount of C nanotube powder was substituted in the B position in the samples sintered

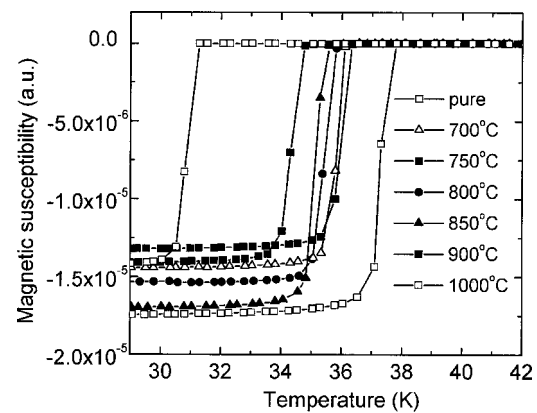


FIG. 2. Magnetic ac susceptibility as a function of temperature for $\text{MgB}_{2-x}\text{C}_x$ sintered at different temperatures for 30 min. Carbon added was in the form of multiwalled carbon nanotubes.

at low temperature and a short period, consistent with small crystal lattice contraction. In order to improve the J_c at higher temperature, such as 20 K, it is essential to maintain high T_c . The above results indicate that by manipulating the processing parameters we could control the T_c while achieving a high level of C inclusion into MgB_2 sample, up to 10% of B. Because such C inclusion has little effect on T_c , the partial substitution of boron for carbon and the partial addition of nanocarbon particles into a MgB_2 matrix may enhance flux pinning within a wide range of temperatures.

Figure 3 shows the $J_c(H)$ curves at 5 and 20 K for the samples of $\text{MgB}_{2-x}\text{C}_x$, where $x=0, 0.05, 0.1, 0.2$, and 0.3 are the nominal values for C content, with all the samples sintered at 800 °C for 30 min. All the $J_c(H)$ curves for doped samples have a higher J_c than the undoped sample at high fields. The sample doped with 10% of carbon nanotubes ($x=0.2$) gives the best J_c at high fields: J_c increases by a factor of 45 at 5 K for the field of 8 T, and at 20 K for the field of 5 T, as compared to the undoped sample. At a higher doping level ($x=0.3$), although the J_c in low-field regime was depressed, the rate of J_c drop is much slower than for all other samples, clearly indicating strong flux pinning induced by the C nanotube doping.

Figure 4 shows the $J_c(H)$ curves at 5 and 20 K for the $\text{MgB}_{1.8}\text{C}_{0.2}$ sample sintered at temperatures from 700 °C–

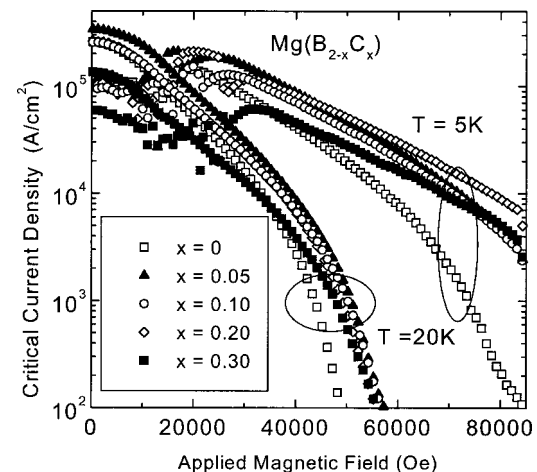


FIG. 3. Critical current density as a function of the magnetic field at 5 and 20 K for a different doping level of multi-walled carbon nanotubes.

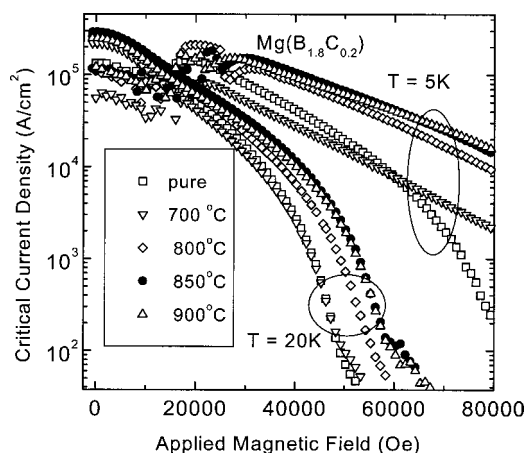


FIG. 4. The critical current density as a function of magnetic field at 5 and 20 K for $\text{MgB}_{1.8}\text{C}_{0.2}$, sintered at different temperatures for 30 min. The carbon was in the form of multiwalled carbon nanotubes.

1000 °C for 30 min. For comparison, the $J_c(H)$ curve for the undoped sample, MgB_2 sintered at 800 °C is included. It is noted that the sintering temperature has a significant effect on the J_c performance in the field. A general trend is such that the $J_c(H)$ characteristic is improved with increasing sintering temperature. Although the sample sintered at 1000 °C has lower J_c values in the low-field regime, its $J_c(H)$ curve crosses over the $J_c(H)$ for the other samples in higher fields. As a higher sintering temperature promotes the C substitution reaction for B, the improved field dependence of J_c measured at lower temperatures is clearly attributable to the C substitution. However, because C substitution depresses T_c , the $J_c(H)$ behavior for samples processed at high temperatures deteriorates above 20 K. Thus, it is important to control the extent of C nanotube substitution and addition to achieve the best combination of the substitution-induced flux pinning and C nanotube additive pinning.

Figure 5 compares the $J_c(H)$ for carbon nanotubes and nano-C particle¹³ doped MgB_2 at 5 and 20 K. It is noted that

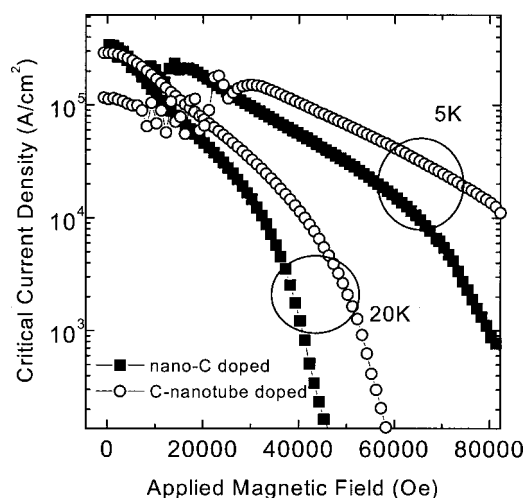


FIG. 5. The field dependence of J_c for 10% nano-C doped (solid symbols) and 10% carbon nanotube doped (open symbols) MgB_2 at 5 and 20 K. This doping level corresponds to the nominal $x=0.2$. The sweep rate of the field was 50 Oe/s.

the carbon nanotubes produced a stronger enhancement of J_c than the nano-C particles. The reasons for C nanotube doping being far better than C nanoparticle doping can be explained as follows. The optimum doping level for nano-C particles is $x=0.05$ (2.5% of B) while this level increases to $x=0.2$ (10% of B) for C nanotube doping. This indicates that the superconductivity of MgB_2 shows a higher tolerance to C nanotubes than C nanoparticles. Consequently, there can be a higher concentration of nanoinclusions in the C nanotube doped sample than in the C nanoparticle doped ones, for the same value of T_c . Furthermore, the special geometry of C nanotubes is desirable for effective pinning.

In summary, the effect of C nanotube doping on lattice parameters, T_c , J_c and flux pinning in MgB_2 was investigated under a wide range of processing conditions. It was found that the substitution of the C nanotube for B enhances the flux pinning but depresses T_c . By controlling the processing parameters an optimized $J_c(H)$ performance is achieved under a partial C substitution and C nanoaddition. Under these conditions, J_c was enhanced by two orders of magnitude at 8 T and 5 K, and at 7 T and 10 K. The J_c was more than 10 000 A/cm² at 20 K in the field of 4 T and at 5 K in the field of 8.5 T, respectively. Carbon nanotube inclusions and C substitution for B are proposed to be responsible for the enhancement of flux pinning in high fields.

The authors thank S. Soltanian and S. H. Zhou for their help in the experiment. This work was supported by the Australian Research Council, Hyper Tech Research Inc. OH USA, Alphatech International Ltd., NZ and the University of Wollongong. W.K.Y. received an Australia-Asia Award funded by the Australian Government.

- ¹T. Takenobu, T. Ito, Dam Hieu Chi, K. Prassides, and Y. Iwasa, *Phys. Rev. B* **64**, 134513 (2001).
- ²M. Paranthaman, J. F. Thompson, D. K. Christen, *Physica C* **355**, 1 (2001).
- ³A. Bharathi, S. Jemina Balaselvi, S. Kalavathi, G. L. N. Reddy, V. Sankara Sastry, Y. Haritharan, and T. S. Radhakrishnan, *Physica C* **370**, 211 (2002).
- ⁴J. S. Ahn and E. J. Choi, *cond-mat/0103169*.
- ⁵I. Maurin, S. Margadonna, K. Prassides, T. Takenobu, T. Ito, D. H. Chi, Y. Iwasa, and A. Fitch, *Physica B* **318**, 392 (2002).
- ⁶I. Maurin, S. Margadonna, K. Prassides, T. Takenobu, Y. Iwasa, and A. N. Fitch, *Chem. Mater.* **14**, 3894 (2002).
- ⁷W. Mickelson, J. Cumings, W. Q. Han, and A. Zettl, *Phys. Rev. B* **65**, 052505 (2002).
- ⁸Zhao-hua Cheng, Bao-gen Shen, Jian Zhang, Shao-ying Zhang, Tong-yun Zhao, and Hong-Wu Zhao, *J. Appl. Phys.* **91**, 7125 (2002).
- ⁹R. A. Ribeiro, S. Bud'ko, C. Petrovic, and P. C. Canfield, *Physica C* **382**, 166 (2002).
- ¹⁰M. Avdeev, J. D. Jorgensen, R. A. Ribeiro, S. L. Bud'ko, and P. C. Canfield, *Physica C* **387**, 301 (2003).
- ¹¹S. Lee, T. Masui, A. Yamamoto, H. Uchiyama, and S. Tajima, *cond-mat/0305485*.
- ¹²S. X. Dou, S. Soltanian, J. Horvat, X. L. Wang, P. Munroe, S. H. Zhou, M. Ionescu, H. K. Liu, and M. Tomsic, *Appl. Phys. Lett.* **81**, 3419 (2002).
- ¹³S. Soltanian, J. Horvat, X. L. Wang, P. Munroe, and S. X. Dou, *Physica C* **390**, 185 (2003).
- ¹⁴C. H. Cheng, H. Zhang, Y. Zhao, Y. Feng, X. F. Rui, P. Munroe, H. M. Zeng, N. Koshizuka, and M. Murakami, *cond-mat/0302202*.
- ¹⁵J. Wei, Y. Li, C. Xu, B. Wei, and D. Wu, *Chem. Phys.* **78**, 785 (2003).
- ¹⁶S. X. Dou, X. L. Wang, J. Horvat, D. Milliken, A. H. Li, K. Konstantinov, E. W. Collings, M. D. Sumption, and H. K. Liu, *Physica C* **361**, 79 (2001).
- ¹⁷X. L. Wang, S. Soltanian, J. Horvat, A. H. Li, M. J. Qin, H. K. Liu, and S. X. Dou, *Physica C* **361**, 149 (2001).
- ¹⁸S. X. Dou, V. Braccini, S. Soltanian, R. Klie, Y. Zhu, S. Li, X. L. Wang, and D. Larbaestier (unpublished).