



ARTICLE

DOI: 10.1038/s41467-017-02629-3

OPEN

Electric-field control of anomalous and topological Hall effects in oxide bilayer thin films

Yuki Ohuchi¹, Jobu Matsuno ², Naoki Ogawa², Yusuke Kozuka¹, Masaki Uchida ¹, Yoshinori Tokura^{1,2} & Masashi Kawasaki^{1,2}

One of the key goals in spintronics is to tame the spin-orbit coupling (SOC) that links spin and motion of electrons, giving rise to intriguing magneto-transport properties in itinerant magnets. Prominent examples of such SOC-based phenomena are the anomalous and topological Hall effects. However, controlling them with electric fields has remained unachieved since an electric field tends to be screened in itinerant magnets. Here we demonstrate that both anomalous and topological Hall effects can be modulated by electric fields in oxide heterostructures consisting of ferromagnetic SrRuO₃ and nonmagnetic SrIrO₃. We observe a clear electric field effect only when SrIrO₃ is inserted between SrRuO₃ and a gate dielectric. Our results establish that strong SOC of nonmagnetic materials such as SrIrO₃ is essential in electrical tuning of these Hall effects and possibly other SOC-related phenomena.

¹Department of Applied Physics and Quantum-Phase Electronics Center (QPEC), University of Tokyo, Tokyo 113-8656, Japan. ²RIKEN Center for Emergent Matter Science (CEMS), Wako, Saitama 351-0198, Japan. Correspondence and requests for materials should be addressed to J.M. (email: matsuno@riken.jp)

Profound implications for the electric field control of spin states have been revealed through magneto-transport properties arising from the spin-orbit coupling (SOC)¹. Such properties have been attracting great interest as foundations for high-density and low-power-consumption spintronic devices because the properties coupled to the spin states enable spin manipulation without magnetic field variation or large current injection. Among the magneto-transport processes, of interest here is the intrinsic anomalous Hall effect² (AHE), which is related to magnetization (M) in Hall resistivity ($\rho_{\text{AHE}} = R_S M$). In some itinerant ferromagnets such as SrRuO₃^{3, 4}, the proportionality factor (R_S) is governed by k -space monopoles, i.e., singularities originating from band-crossings gapped by SOC; not M but R_S is potentially tuneable by electric field there. Another intriguing example is the topological Hall effect (THE) originating from scalar spin chirality concomitant with non-coplanar spin structures such as in a frustrated pyrochlore magnet⁵ and in metallic magnets characterized by a non-zero skyrmion number (N_{sk})^{6–9}. In the case of $N_{\text{sk}} = 1$, the topologically protected spin swirling texture is called magnetic skyrmion^{6, 10, 11}. Despite mounting interest in electrical control of these Hall effects, however, their control in itinerant magnets has been elusive in conventional field-effect structures, that is, magnetic materials adjacent to gate dielectrics. Recent discovery of the THE in an oxide heterostructure composed of SrRuO₃ and SrIrO₃¹² brings an opportunity to develop electrical control because the strong SOC in SrIrO₃¹³ induces a SOC-related phenomenon in neighboring ferromagnetic SrRuO₃. In addition to the intrinsic AHE inherent to SrRuO₃³, the combination of the strong SOC and the broken inversion symmetry gives rise to substantial Dzyaloshinskii–Moriya interaction (DMI)^{6, 14} and the concomitant THE; the underlying spin texture has been deduced to be the interface-driven skyrmion¹². In view of the fact that ultrathin films of itinerant magnets have been a playground for electrical manipulation of spin states^{1, 15–19}, an electric field applied to the ultrathin heterostructure may provoke effective manipulation of the spin state contending with screening effects by itinerant electrons of SrRuO₃. Furthermore, we can expect that the strong SOC in SrIrO₃ plays a positive role at the interface as well because both AHE and THE are magneto-transport phenomena driven by SOC.

Here, we show the clear modulation of both AHE and THE by an electric field in the heterostructure of SrRuO₃/SrIrO₃/SrTiO₃ from magneto-transport and magneto-optic Kerr effect (MOKE) measurements. The electrical modulation is effective only when SrIrO₃ is inserted between SrRuO₃ and a gate dielectric, i.e., SrTiO₃. This indicates the essential role of the strong SOC in nonmagnetic materials for the electrical tuning of these Hall effects and possibly other SOC-related phenomena.

Results

Stacking-order dependent electric field control. Five-unit-cell SrRuO₃ thin films were epitaxially grown on SrTiO₃(001) substrates by pulsed laser deposition in three stacking orders with SrIrO₃ (see Methods): a single layer of SrRuO₃ (SRO5/Sub), a bilayer of SrRuO₃ and 2-unit-cell SrIrO₃ (SIO2/SRO5/Sub), and that with the inverted deposition order (SRO5/SIO2/Sub, Fig. 1a). We first take a look at basic transport and magnetic properties before we go into the Hall effects under an applied electric field (Fig. 1b). In Fig. 1c, d, we show the temperature dependence of longitudinal resistivity (ρ_{xx}) and magnetization perpendicular to the film plane in the three samples. All of them show metallic conduction and ferromagnetic magnetization whose Curie temperatures (T_C) are lower than the bulk value (160 K)³. These transport and magnetic properties are consistent with previously

reported ultrathin SrRuO₃ films²⁰. Figure 1e shows anomalous Hall conductivity (σ_{AHE}) as a function of magnetization with temperature as a control parameter. The σ_{AHE} of the three samples behave the same way; when the magnetization gets larger, the sign of σ_{AHE} is inverted from positive to negative. This sign inversion is consistent with the previous experiments^{4, 12}, manifesting the above-mentioned band anti-crossing singularities of SrRuO₃. Conversely, such temperature dependence in AHE implies the potential for electrical control of AHE through the modification of the SOC-induced band.

In contrast to the similarities of the basic transport and magnetic properties among the three samples, a clear difference emerges in electric field effect (see Methods). The sums of anomalous and topological Hall resistivities ($\rho_{\text{AHE}} + \rho_{\text{THE}}$) under applied electric fields are shown in Figs. 1f–h as a function of external magnetic field (B). The B dependence of ρ_{AHE} corresponds to that of magnetization normal to the film plane, whereas ρ_{THE} shows up with the formation of the topological spin texture as exemplified by the peak at around 3 T in Fig. 1h. The sum of these Hall components is obtained by subtracting the B -linear ordinary Hall term ($R_{\text{H}}B$) from the Hall resistivity (ρ_{yx}). Both in SRO5/Sub (Fig. 1f) and in SIO2/SRO5/Sub (Fig. 1g), $\rho_{\text{AHE}} + \rho_{\text{THE}}$ is almost unchanged by the applied electric field. However, $\rho_{\text{AHE}} + \rho_{\text{THE}}$ is obviously changed in SRO5/SIO2/Sub (Fig. 1h). This striking stacking-order dependence suggests that the electric field to the SrRuO₃-SrIrO₃ interface causes the noticeable modulation. The thinness of the SrIrO₃ layer compared with the SrRuO₃ layer contributes to the preferable modulation in SRO5/SIO2/Sub because the interface in SRO5/SIO2/Sub is closer to the gate dielectric than that in SIO2/SRO5/Sub (see Supplementary Figure 1 and Supplementary Note 1). Hereafter, we focus on the control in the SRO5/SIO2/Sub sample.

Electric-field modulation of AHE. In the structure of SRO5/SIO2/Sub, the large electric field modulation gives rise to the sign inversion of AHE without changing temperature. Magnetic-field dependences of $\rho_{\text{AHE}} + \rho_{\text{THE}}$ under different electric fields at 30 K are shown in Fig. 2a–c. Except for the topological Hall term that shows a peak at around 0.8 T, the data are dominated by the anomalous Hall contribution. In particular, we can consider the value at high magnetic field such as 2 T to be totally derived from ρ_{AHE} since all the spins are ferromagnetically aligned without forming any topological spin textures. The sign of ρ_{AHE} above the saturation field is inverted from negative to positive when the gate voltage is varied from negative (–180 V) to positive (200 V), while ρ_{AHE} is close to vanish under zero bias. This sign inversion indicates the sign reversal of the proportionality factor R_S because MOKE measurements reveal that only a minor fraction of M , <10% of the magnetization, is electrically modulated (see Supplementary Figure 2 and Supplementary Note 2). Such electrical sign inversion has never been observed in plain films of itinerant magnets including SrRuO₃.

As shown in Fig. 2d, the tendency of AHE change is nearly temperature independent; the positive (negative) bias voltage increases (decreases) ρ_{AHE} regardless of the sign of AHE. Since singularities in the band structure of SrRuO₃ originate from band anti-crossings gapped by SOC, we speculate that the electric field control of AHE is ascribed to the redistribution of the singularities caused by the variation of SOC. The pronounced controllability in SRO5/SIO2/Sub compared with its absence in SIO2/SRO5/Sub suggests that the electric field from SrIrO₃ side induces certain modification of SOC in the bilayer even if it has itinerant carrier density as high as 10^{22} cm^{-3} in the magnetic SrRuO₃ layer. This is in sharp contrast to the case of chemically doped EuTiO₃²¹, where carrier-density variation inverts the sign

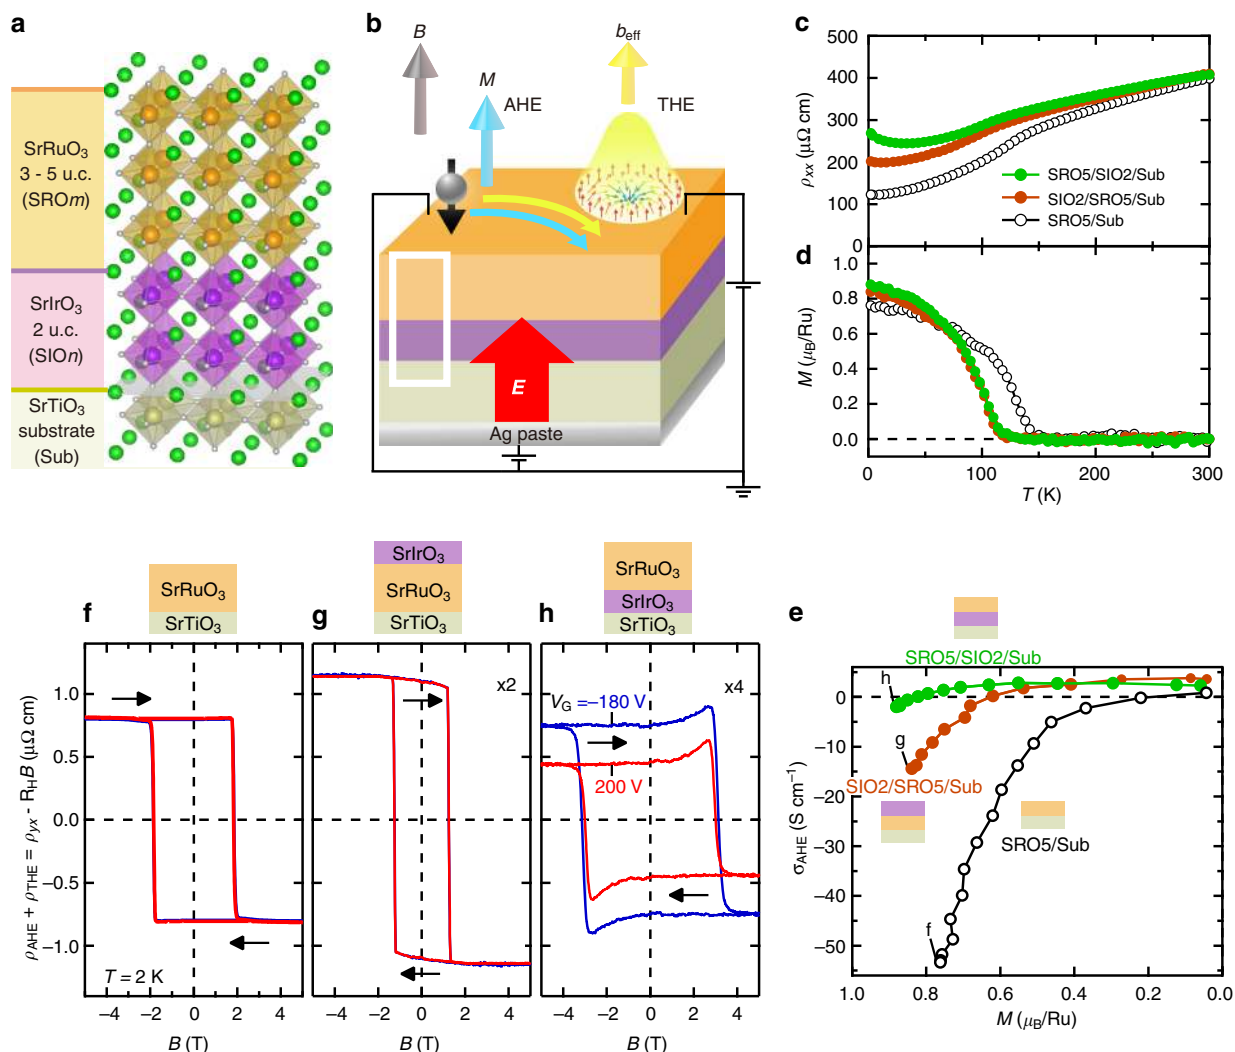


Fig. 1 Structure and basic physical properties of samples. **a** Schematics of the SrRuO₃-SrIrO₃ bilayer film, where SrIrO₃ is inserted between SrRuO₃ and SrTiO₃ substrate (SROM/SiO₂/Sub, $m = 3-5$ unit cells). Green, orange, purple, beige, and gray atoms represent Sr, Ru, Ir, Ti, and O, respectively, in the crystal structure, which is drawn using VESTA³⁸. **b** Schematics of the magneto-transport properties observed in SROM/SiO₂/Sub under the application of a gate electric field (E): Anomalous Hall effect (AHE) generated by magnetization (M) and topological Hall effect (THE) driven by fictitious magnetic field (b_{eff}) in the case of skyrmion formation. White box corresponds to the schematics in **a**. Temperature (T) dependence of longitudinal resistivity (ρ_{xx} , **c**) and out-of-plane magnetization measured at 0.1 T (M , **d**) for SRO5/Sub, SIO2/SRO5/Sub, and SRO5/SiO2/Sub. **e** Anomalous Hall conductivity (σ_{AHE}) as a function of magnetization (M). **f-h** The sum of anomalous and topological Hall resistivity ($\rho_{\text{AHE}} + \rho_{\text{THE}}$) at 2 K as a function of external magnetic field (B) under application of gate bias $V_G = -180$ V (blue lines) and 200 V (red lines). At the lowest temperature ($T = 2$ K), the largest modulation of carrier density can be realized due to the quantum paraelectric nature of SrTiO₃ substrates. On top, respective sample structure is shown. $\rho_{\text{AHE}} + \rho_{\text{THE}}$ is deduced by subtracting a B -linear ordinary Hall component ($R_H B$) from the Hall resistivity (ρ_{yx}). Black arrows indicate the sweep direction of B

of AHE accompanied by the shift of Fermi energy (E_F). The insertion of the SrIrO₃ layer makes a more important contribution to the AHE modulation than the E_F shift in SrRuO₃ does. The controllability may partly rely on the lower carrier density of inserted semimetallic SrIrO₃, the order of 10^{19} cm^{-3} ²².

In order to clarify the effectiveness of the heterointerface close to the gate dielectric, we also fabricate the heterostructure with thicker (5 unit cells) SrIrO₃ (SRO5/SiO5/Sub, see Supplementary Figures 3–5 and Supplementary Notes 3 and 4). Figure 2e shows magnetic field dependences of $\rho_{\text{AHE}} + \rho_{\text{THE}}$ under different electric fields at 30 K in SRO5/SiO5/Sub, where the change of ρ_{AHE} is apparently suppressed. In Fig. 2f, we compare the variation of ρ_{AHE} ($\Delta\rho_{\text{AHE}} = \rho_{\text{AHE}}(V_G = 200 \text{ V}) - \rho_{\text{AHE}}(V_G = -180 \text{ V})$) in SRO5/SiO5/Sub with that in SRO5/SiO2/Sub, where we can clearly see the suppression of the modulation in the thicker SrIrO₃ sample within all the measured temperatures. We attribute

this suppression to the significant screening of the electric field within the thicker SrIrO₃ layer.

Electric-field modulation of THE. THE is also modulated by electric field in the structure of SRO5/SiO2/Sub. In order to evaluate ρ_{THE} from magneto-transport measurement, ρ_{AHE} has to be subtracted from $\rho_{\text{AHE}} + \rho_{\text{THE}}$. Since MOKE is proportional to magnetization as anticipated from its perturbative nature and also as experimentally verified in the previous report¹², MOKE under applied electric field can be utilized as the reference of ρ_{AHE} , which is also proportional to magnetization at a constant temperature. The magnetic field dependences of Kerr rotation are shown by the broken lines in Fig. 2a–c. Each Kerr rotation is normalized by ρ_{AHE} at high magnetic field under each applied electric field; the normalized curves represent the B dependence of ρ_{AHE} . By subtracting them from $\rho_{\text{AHE}} + \rho_{\text{THE}}$, we deduced ρ_{THE}

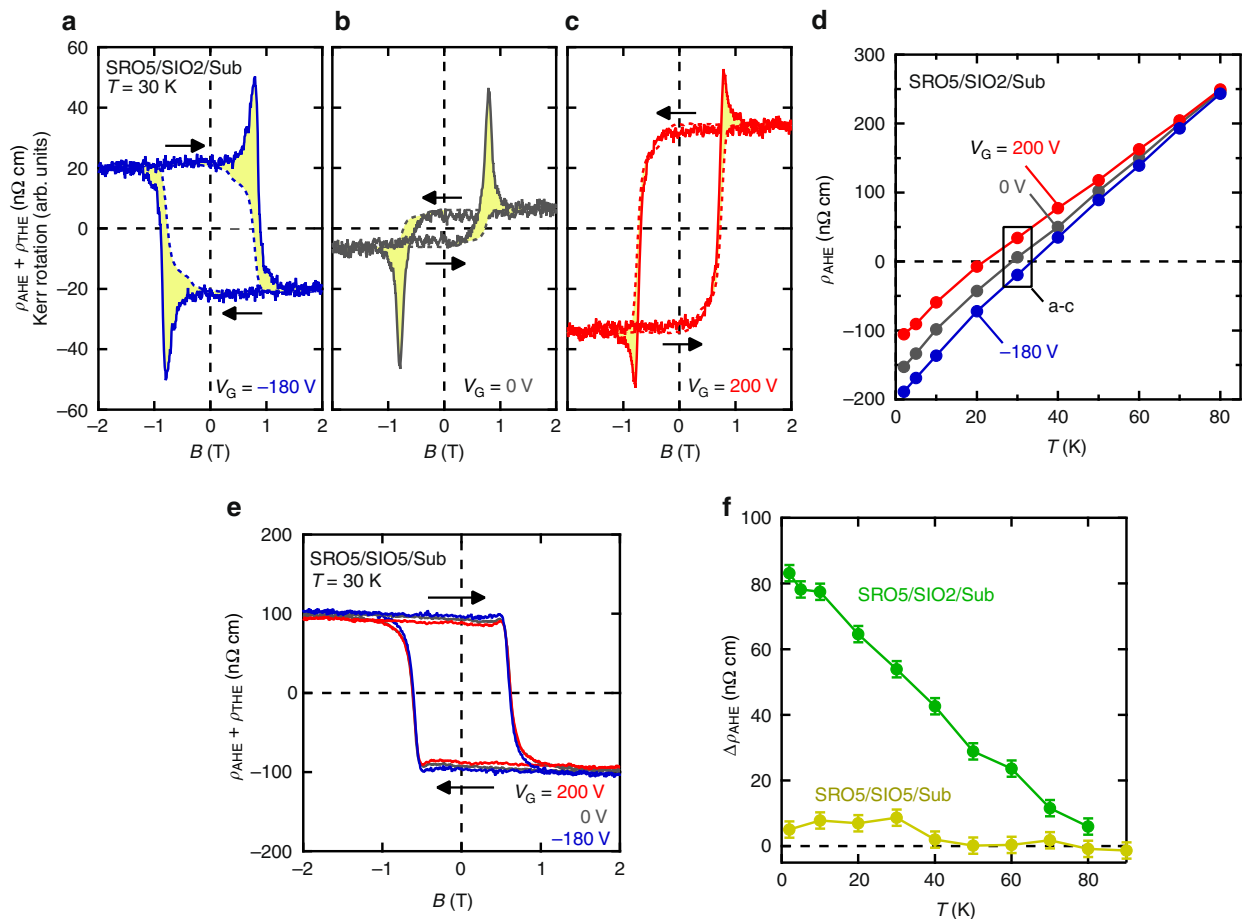


Fig. 2 Electric-field control of anomalous Hall effect. Magnetic-field (B) dependence of anomalous and topological Hall resistivities ($\rho_{\text{AHE}} + \rho_{\text{THE}}$, solid lines) at 30 K under gate voltage $V_G = -180$ V (**a**), 0 V (**b**), and 200 V (**c**) for SRO5/SiO2/Sub. Magneto-optic Kerr rotation as a function of B under the same gate bias is also shown by broken lines in each panel. Yellow colored regions correspond to ρ_{THE} . Black arrows indicate the sweep direction of B . **d** Temperature (T) dependence of ρ_{AHE} under $V_G = -180$ V (blue), 0 V (gray) and 200 V (red). The black box corresponds to the data in **a-c**. **e** B dependence of $\rho_{\text{AHE}} + \rho_{\text{THE}}$ at 30 K under $V_G = -180$ V (blue), 0 V (gray), and 200 V (red) for SRO5/SiO5/Sub. **f** T dependence of variation in anomalous Hall resistivity ($\Delta\rho_{\text{AHE}}$) between $V_G = 200$ V and $V_G = -180$ V for SRO5/SiO5/Sub (yellow) and SRO5/SiO2/Sub (green). Error bars include the uncertainty of the sample thickness and of electrical measurement

(yellow colored regions in Fig. 2a–c). Figure 3a shows the electric field-controlled peak of ρ_{THE} around $B = 0.8$ T. The electric field also tunes the range of magnetic field where finite ρ_{THE} appears; when the positive (negative) gate voltage is applied, ρ_{THE} gets smaller (larger) and the magnetic field region gets shrunk (enlarged). The variation in peak of ρ_{THE} ($\Delta\rho_{\text{THE}} = \rho_{\text{THE}}(V_G = 200 \text{ V}) - \rho_{\text{THE}}(V_G = -180 \text{ V})$) normalized by zero-bias value ($\Delta\rho_{\text{THE}}/\rho_{\text{THE}}(0 \text{ V})$) is as large as 55%. The sign of THE remains the same during the sign inversion of AHE by electric field, supporting that the origins of AHE and THE are clearly distinct from each other as previously indicated¹².

Assuming the skyrmion formation in this heterostructure, we discuss the relation of this THE modulation with skyrmion length scale. ρ_{THE} is an outgrowth of ordinary Hall effect under fictitious magnetic field (b_{eff}) caused by the non-coplanar spin texture of skyrmion⁶. Since one skyrmion generates one flux quantum ($\Phi_0 = h/e$), ρ_{THE} is described as a function of skyrmion density (n_{sk}):

$$\rho_{\text{THE}} = PR_{\text{H}}b_{\text{eff}} = PR_{\text{H}}n_{\text{sk}}\Phi_0 \quad (1)$$

where P is spin polarization of conduction electrons in SrRuO₃. Ordinary Hall coefficient R_{H} is inversely proportional to carrier density. The change of P or R_{H} is negligible because E_{F} in SrRuO₃ remains almost unchanged judging from the variation of ρ_{xx} as

small as the order of 1% as discussed later. Therefore, the modulation of ρ_{THE} indicates the change of n_{sk} . The skyrmion size, estimated by $r_{\text{sk}} \cong 1/\sqrt{n_{\text{sk}}}$, is varied from 15 nm ($V_G = 200$ V) to 12 nm ($V_G = -180$ V) adopting $P = -9.5\%$ as a typical value of SrRuO₃²³ and R_{H} evaluated from the B -linear component of Hall resistivity under $V_G = 0$ V at 30 K. Since r_{sk} is proportional to the ratio of ferromagnetic interaction J to DMI D , or J/D ⁶, the positive (negative) gate voltage should increase (decrease) J/D . The controlling knob of ρ_{THE} is thought to be D rather than J ; the variation of J is negligible because the applied electric field hardly varies T_{C} , which can be evaluated by a kink structure in ρ_{xx} ³ (see Supplementary Figure 6 and Supplementary Note 5). The real-space observation of such electrical control of skyrmion size would be one of the future challenges.

We examine the other possibilities of the underlying spin texture. One of the candidates is the conical spin structure, which is topologically trivial and is reported to give rise to THE-like signal²⁴. In our case, this can be excluded since the spin structure is dominated by conventional ferromagnetic phase with finite anisotropy as exemplified by open hysteresis loops in magnetization (see Supplementary Figure 2). The possibility of non-coplanar spin structures stabilized only under geometrical frustration^{5, 25} can also be excluded because such frustration is apparently absent in our heterostructure. We then focus on a

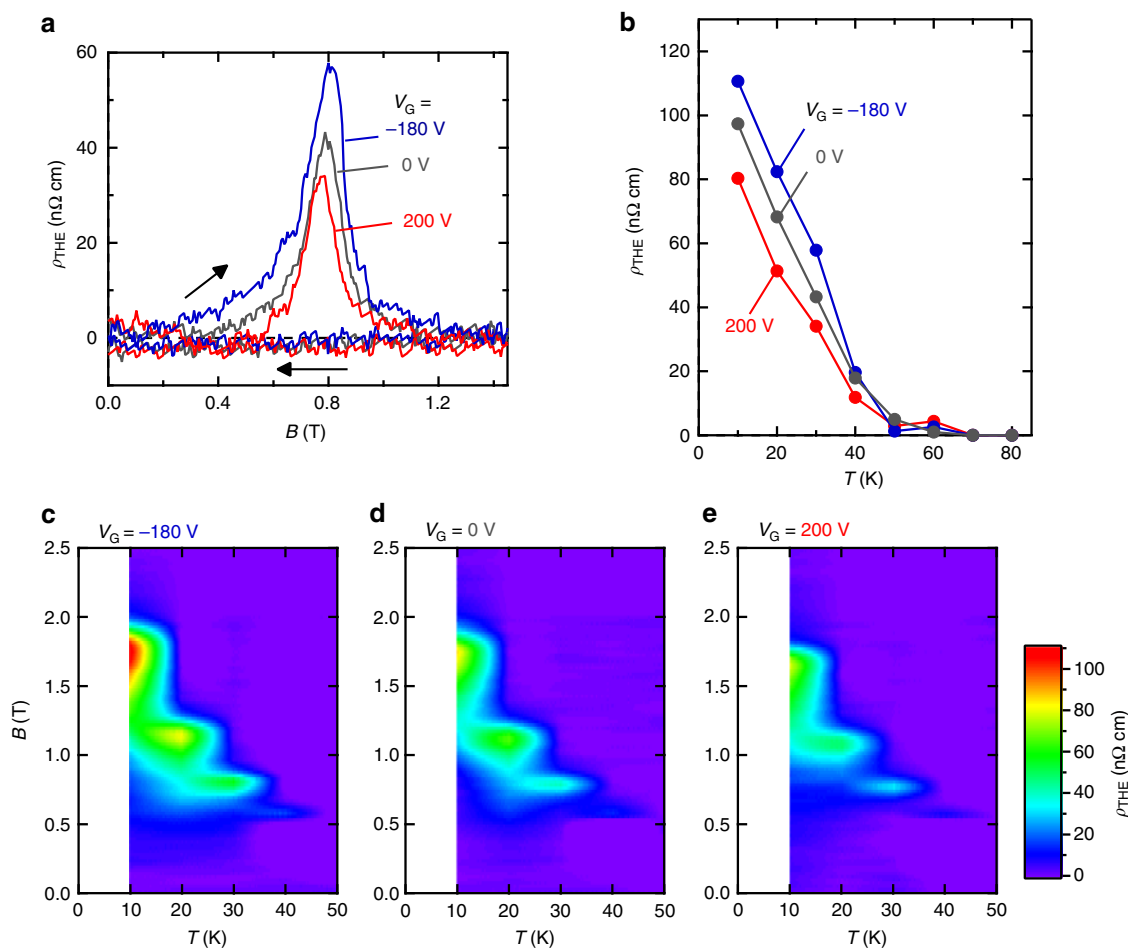


Fig. 3 Electric-field control of topological Hall effect. **a** Topological Hall resistivity (ρ_{THE}) at 30 K as a function of external magnetic field (B) under $V_G = -180$ V (blue line), 0 V (gray line) and 200 V (red line) for SRO5/SiO₂/Sub. Black arrows indicate the sweep direction of B . **b** Temperature (T) dependence of ρ_{THE} under gate bias. Color map of ρ_{THE} in the T - B plane under $V_G = -180$ V (**c**), 0 V (**d**) and 200 V (**e**)

topological spin texture other than skyrmion e.g., biskyrmion or meron, of which topological number (N_{sk}) is not unity^{9,26,27}. The emergent fictitious magnetic field can thus be generalized as $n_{\text{topo}}N_{\text{sk}}\Phi_0$, where n_{topo} is the density of the topological spin texture. Since N_{sk} is constant inherent in the topological spin structures and hence independent of the gate bias, the electric field modulation of ρ_{THE} is attributed to the modulation of n_{topo} . In order to realize topologically nontrivial spin structures in SrRuO₃, the interface-driven DMI is required as discussed in the above-mentioned skyrmion case. The ratio of J/D is inversely correlated with n_{topo} for any type of topological spin textures. The consequence therefore remains the same; positive (negative) gate voltage should increase (decrease) J/D .

Considering that the variation of DMI is attributed to the modification of SOC at the interface, both modulations of AHE and THE are brought about by the same origin; this appears in the temperature dependence. The tendency of ρ_{THE} change is independent of temperature as shown in Fig. 3b. The expansion of the observable magnetic field region under negative electric field is discerned at every temperature below 40 K (Fig. 3c–e). These indicate that the obtained modulation of THE is independent of the sign of AHE, which is inverted at 30 K. The temperature independent trend of the electric field effect on THE is in accord with that on AHE (Fig. 2d), implying the common origin of SOC variation. In fact, the MOKE measurements indicate that the coercive force (H_C) is shifted from 0.73 T ($V_G = 200$ V) to 0.76 T ($V_G = -180$ V) at 30 K (see Supplementary

Figure 2 and Supplementary Note 2). This shift of H_C also supports the modification of SOC because the magnetic anisotropy originates from SOC.

Discussion

The observed modulations of the AHE and THE are not simply explained by the variation of carrier density. In order to show this clearly, the variations of AHE ($\Delta\rho_{\text{AHE}}$) and THE ($\Delta\rho_{\text{THE}}/\rho_{\text{THE}}(0\text{ V})$) with different thickness of SrRuO₃ films are shown in Fig. 4a, b, respectively, as a function of ρ_{xx} variation normalized by zero-bias value ($\Delta\rho_{xx}/\rho_{xx}(0\text{ V})$) at various temperatures (see Supplementary Figures 7–9 and Supplementary Notes 6–8 for detailed transport and magnetic properties). $\Delta\rho_{xx}/\rho_{xx}(0\text{ V})$ ranges from 1.2% in SRO5/SiO₂/Sub to 6.6% in SRO3/SiO₂/Sub at 10 K. Since ρ_{xx} is inversely proportional to carrier density (n), the order of magnitude is consistent with the expected electron accumulation by a SrTiO₃-back-gate transistor (Supplementary Note 8). $\Delta\rho_{\text{AHE}}$ in bilayers indicates that the gate-bias control of AHE has the specific tendency regardless of the film thickness. The same plots of SrRuO₃ single layers (SROm/Sub) are also depicted for comparison. They have negligible change in AHE, while their ρ_{xx} variation is in the same range with that in bilayers with the same SrRuO₃ thickness. As already pointed out, these results demonstrate the importance of inserting the SrIrO₃ layer rather than the E_F shift in SrRuO₃. According to the equation (1), ρ_{THE} is proportional not only to n_{sk} (or $n_{\text{topo}}N_{\text{sk}}$) but also to R_H . We show the calculated variation of ρ_{THE} contributed from R_H , i.e., n

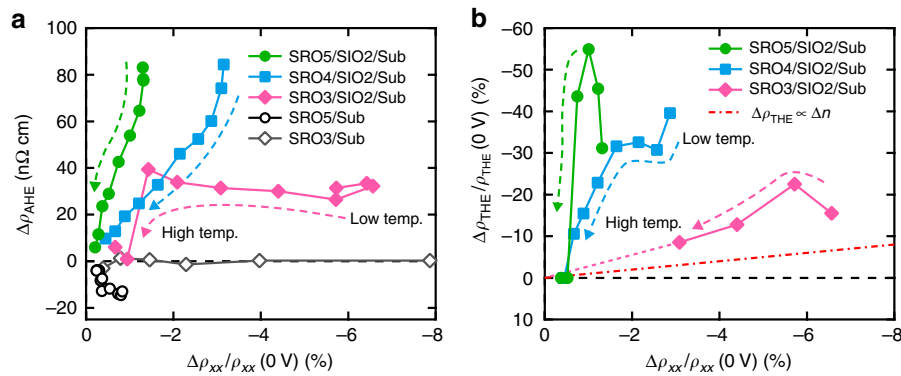


Fig. 4 Qualitative analyses of modulations in AHE and THE. **a** Difference in anomalous Hall resistivity ($\Delta\rho_{\text{AHE}}$) between $V_G = 200$ V and $V_G = -180$ V as a function of longitudinal resistivity variation ratio ($\Delta\rho_{xx}/\rho_{xx}$ (0 V) (%)) at temperatures ranging from 2 K to 80 K. **b** Modulation ratio of topological Hall resistivity ($\Delta\rho_{\text{THE}}/\rho_{\text{THE}}$ (0 V) (%)) as a function of $\Delta\rho_{xx}/\rho_{xx}$ (0 V) (%). Red dash-dotted line is the calculated variation where gate bias only changes carrier density (Δn). Pink dotted line is the guide to the eyes. Broken arrows indicate temperature variation

variation (ΔR_H i.e. $\Delta n = n(V_G = 200 \text{ V}) - n(V_G = -180 \text{ V})$) with the red dash-dotted line in Fig. 4b, assuming small Δn ($\Delta R_H \propto \Delta n/n^2$, i.e., $\Delta\rho_{\text{THE}} \propto \Delta n$) and V_G -independent electron mobility. All the modulations in heterostructures are located far above the red dash-dotted line. Therefore, most of the observed $\Delta\rho_{\text{THE}}$ is attributed to the change in size of the topological spin texture, i.e., DMI. These pronounced modulations of the AHE and THE are both achieved not by carrier-density variation in SrRuO₃ but by modification of SOC at the interface of SrRuO₃ and SrIrO₃.

Recent theoretical calculations^{28, 29} have revealed that the DMI is enormously affected by the singularities in band structures as well as the AHE, although the precise dependencies differ between them. This has been confirmed in itinerant chiral magnets³⁰ and a semiconducting Dirac electron system³¹. We speculate that our bilayers have some band deformation when applying an electric field to the interface. In both plots in Fig. 4, thinner SrRuO₃ films exhibit smaller variation in spite of the larger $\Delta\rho_{xx}/\rho_{xx}$ (0 V). This thickness dependence is probably attributed to band structure deformation as observed in the thin limit of SrRuO₃³²; the density of states near E_F shrinks as SrRuO₃ gets thinner.

One of the plausible pathways in the electric field-induced change of SOC is through the interface potential gradient, which is observed as the electrical control of Rashba-type band splitting in a semiconductor quantum well³³. In contrast to the conventional Rashba systems, however, we have to take into account of the strong SOC of SrIrO₃, the magnetic properties of SrRuO₃, and their strong hybridization. Furthermore, since the itinerant-electron systems including SrRuO₃ and SrIrO₃ have complicated distribution of band-anti-crossings in their band structures^{22, 34, 35}, the quantitative evaluation of the electric field-induced modulation in the heterostructures requires elaborate theoretical investigation. Nevertheless, the present observations clearly indicate that the electric field applied to the thin SrIrO₃ plays the crucial role in SOC at the interface and even brings about the significant modification of magnetic properties in the neighboring itinerant ferromagnet. The method of inserting a thin nonmagnetic material with strong SOC between a ferromagnet and a gate dielectric may be applicable to tuning many intriguing spin-orbit coupled phenomena such as magnetic anisotropy¹⁵, domain wall motion³⁶ and the DMI itself³⁷.

Methods

Sample preparation. The epitaxial bilayers composed of SrIrO₃ and SrRuO₃, and single layer films of SrRuO₃ were deposited on SrTiO₃(001) substrates by pulsed laser deposition using a KrF excimer laser ($\lambda = 248$ nm). The substrate temperatures during the growth of SrRuO₃ and SrIrO₃ were 730 °C and 600 °C, respectively,

where oxygen partial pressure was 120 mTorr. The laser fluence was 1.2 J/cm² for SrRuO₃ and 2.6 J/cm² for SrIrO₃.

Measurement of magnetic and transport properties. The magnetization data were recorded by a SQUID magnetometer with a magnetic field applied perpendicularly to the film plane and along the magnetic easy axis grown on SrTiO₃(001). Magneto-optic Kerr effect was measured with a laser at 690 nm wavelength in polar geometry by using a photoelastic modulator.

Transport properties were measured in Hall bars cut by a diamond wheel saw (1 mm × 2.5 mm) and ultrasonically bonded with Al wires. The applied current was 10 μA , which corresponds to 3.6×10^6 A/m² for SRO5/SiO2/Sub. Back-gate transistors were fabricated using 0.5-mm-thick SrTiO₃ substrates as a gate dielectric and silver paste as a gate electrode at the opposite side of the deposited films. Antisymmetrizations were performed for both the Hall resistivity and the Kerr rotation angle. Ordinary Hall term was subtracted from the Hall resistivity by linear fitting in a higher magnetic field region.

Data availability. The data that support the findings of this study are available from the corresponding author upon request.

Received: 22 April 2017 Accepted: 14 December 2017

Published online: 15 January 2018

References

- Matsukura, F., Tokura, Y. & Ohno, H. Control of magnetism by electric fields. *Nat. Nanotechnol.* **10**, 209–220 (2015).
- Nagaosa, N., Sinova, J., Onoda, S., MacDonald, A. H. & Ong, N. P. Anomalous Hall effect. *Rev. Mod. Phys.* **82**, 1539–1592 (2010).
- Koster, G. et al. Structure, physical properties, and applications of SrRuO₃ thin films. *Rev. Mod. Phys.* **84**, 253–298 (2012).
- Fang, Z. et al. The anomalous Hall effect and magnetic monopoles in momentum space. *Science* **302**, 92–95 (2003).
- Taguchi, Y., Oohara, Y., Yoshizawa, H., Nagaosa, N. & Tokura, Y. Spin chirality, berry phase, and anomalous Hall effect in a frustrated ferromagnet. *Science* **291**, 2573 (2001).
- Nagaosa, N. & Tokura, Y. Topological properties and dynamics of magnetic skyrmions. *Nat. Nanotechnol.* **8**, 899–911 (2013).
- Lee, M., Kang, W., Onose, Y., Tokura, Y. & Ong, N. P. Unusual Hall effect anomaly in MnSi under pressure. *Phys. Rev. Lett.* **102**, 186601 (2009).
- Neubauer, A. et al. Topological Hall effect in the A phase of MnSi. *Phys. Rev. Lett.* **102**, 186602 (2009).
- Wang, W. et al. A centrosymmetric hexagonal magnet with superstable biskyrmion magnetic nanodomains in a wide temperature range of 100–340 K. *Adv. Mater.* **28**, 6887–6893 (2016).
- Mühlbauer, S. et al. Skyrmion lattice in a chiral magnet. *Science* **323**, 915–919 (2009).
- Yu, X. Z. et al. Real-space observation of a two-dimensional skyrmion crystal. *Nature* **465**, 901–904 (2010).
- Matsuno, J. et al. Interface-driven topological Hall effect in SrRuO₃-SrIrO₃ bilayer. *Sci. Adv.* **2**, e1600304 (2016).
- Matsuno, J. et al. Engineering a spin-orbital magnetic insulator by tailoring superlattices. *Phys. Rev. Lett.* **114**, 247209 (2015).

14. Fert, A., Cros, V. & Sampaio, J. Skyrmions on the track. *Nat. Nanotechnol.* **8**, 152–156 (2013).
15. Weisheit, M. et al. Electric field-induced modification of magnetism in thin-film ferromagnets. *Science* **315**, 349–351 (2007).
16. Chu, Y.-H. et al. Electric-field control of local ferromagnetism using a magnetoelectric multiferroic. *Nat. Mater.* **7**, 478–482 (2008).
17. Chiba, D. et al. Electrical control of the ferromagnetic phase transition in cobalt at room temperature. *Nat. Mater.* **10**, 853–856 (2011).
18. Valencia, S. et al. Interface-induced room-temperature multiferroicity in BaTiO₃. *Nat. Mater.* **10**, 753–758 (2011).
19. Shimizu, S. et al. Gate tuning of anomalous Hall effect in ferromagnetic metal SrRuO₃. *Appl. Phys. Lett.* **105**, 163509 (2014).
20. Xia, J., Siemons, W., Koster, G., Beasley, M. R. & Kapitulnik, A. Critical thickness for itinerant ferromagnetism in ultrathin films of SrRuO₃. *Phys. Rev. B* **79**, 140407(R) (2009).
21. Takahashi, K. S., Onoda, M., Kawasaki, M., Nagaosa, N. & Tokura, Y. Control of the anomalous Hall effect by doping in Eu_{1-x}La_xTiO₃ thin films. *Phys. Rev. Lett.* **103**, 057204 (2009).
22. Nie, Y. F. et al. Interplay of spin-orbit interactions, dimensionality, and octahedral rotations in semimetallic SrIrO₃. *Phys. Rev. Lett.* **114**, 016401 (2015).
23. Worledge, D. C. & Geballe, T. H. Negative spin-polarization of SrRuO₃. *Phys. Rev. Lett.* **85**, 5182–5185 (2000).
24. Meynell, S. A. et al. Hall effect and transmission electron microscopy of epitaxial MnSi thin films. *Phys. Rev. B* **90**, 224419 (2014).
25. Machida, Y., Nakatsuji, S., Onoda, S., Tayama, T. & Sakakibara, T. Time-reversal symmetry breaking and spontaneous Hall effect without magnetic dipole order. *Nature* **463**, 210–213 (2010).
26. Ezawa, M. Compact merons and skyrmions in thin chiral magnetic films. *Phys. Rev. B* **83**, 100408(R) (2011).
27. Yu, X. Z. et al. Biskyrmion states and their current-driven motion in a layered manganite. *Nat. Commun.* **5**, 3198 (2014).
28. Koretsune, T., Nagaosa, N. & Arita, R. Control of Dzyaloshinskii-Moriya interaction in Mn_{1-x}Fe_xGe: a first-principles study. *Sci. Rep.* **5**, 13302 (2015).
29. Wakatsuki, R., Ezawa, M. & Nagaosa, N. Domain wall of a ferromagnet on a three-dimensional topological insulator. *Sci. Rep.* **5**, 13638 (2015).
30. Shibata, K. et al. Towards control of the size and helicity of skyrmions in helimagnetic alloys by spin-orbit coupling. *Nat. Nanotechnol.* **8**, 723–728 (2013).
31. Yasuda, K. et al. Geometric Hall effects in topological insulator heterostructures. *Nat. Phys.* **12**, 555–559 (2016).
32. Toyota, D. et al. Thickness-dependent electronic structure of ultrathin SrRuO₃ films studied by *in situ* photoemission spectroscopy. *Appl. Phys. Lett.* **87**, 162508 (2005).
33. Nitta, J., Akazaki, T., Takayanagi, H. & Enoki, T. Gate control of spin-orbit interaction in an inverted In_{0.53}Ga_{0.47}As/In_{0.52}Al_{0.48}As heterostructure. *Phys. Rev. Lett.* **78**, 1335–1338 (1997).
34. Chen, Y., Bergman, D. L. & Burkov, A. A. Weyl fermions and the anomalous Hall effect in metallic ferromagnets. *Phys. Rev. B* **88**, 125110 (2013).
35. Zeb, M. A. & Kee, H.-Y. Interplay between spin-orbit coupling and Hubbard interaction in SrIrO₃ and related *Pbnm* perovskite oxides. *Phys. Rev. B* **86**, 085149 (2012).
36. Chiba, D. et al. Electric-field control of magnetic domain-wall velocity in ultrathin cobalt with perpendicular magnetization. *Nat. Commun.* **3**, 888 (2012).
37. Nawaoka, K., Miwa, S., Shiota, Y., Mizuochi, N. & Suzuki, Y. Voltage induction of interfacial Dzyaloshinskii-Moriya interaction in Au/Fe/MgO artificial multilayer. *Appl. Phys. Express* **8**, 063004 (2015).
38. Momma, K. & Izumi, F. VESTA 3 for three-dimensional visualization of crystal, volumetric and morphology data. *J. Appl. Crystallogr.* **44**, 1272–1276 (2011).

Acknowledgements

We thank N. Nagaosa, R. Arita, T. Koretsune, and Y. Kaneko for fruitful discussions. This work was partly supported by JSPS KAKENHI Grant Numbers JP24226002, JP17H02791, and JP16J06170 (Y.O.) and by Japan Society for the Promotion of Science through Program for Leading Graduate Schools (MERIT) (Y.O.).

Author contributions

Y.O., J.M., and M.K. designed the experiments. Y.O. fabricated films, measured transport properties, and analyzed the data. N.O. measured magneto-optic Kerr effect. M.U. and Y. K. contributed to the film fabrication and the transport measurements. Y.O. and J.M. wrote the manuscript. Y.T. and M.K. coordinated the projects. All authors discussed the results.

Additional information

Supplementary Information accompanies this paper at <https://doi.org/10.1038/s41467-017-02629-3>.

Competing interests: The authors declare no competing financial interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2018