

Emergence of Rigidity at the Structural Glass Transition: A First-Principles Computation

Hajime Yoshino¹ and Marc Mézard²

¹*Department of Earth and Space Science, Faculty of Science, Osaka University, Toyonaka 560-0043, Japan*

²*Laboratoire de Physique Théorique et Modèles Statistiques, CNRS-Université Paris Sud, Bâtiment 100, 91405 Orsay Cedex, France*

(Received 15 March 2010; published 1 July 2010)

We compute the shear modulus of structural glasses from a first-principles approach based on the cloned liquid theory. We find that the intrastate shear modulus, which corresponds to the plateau modulus measured in linear viscoelastic measurements, strongly depends on temperature and vanishes continuously when the temperature is increased beyond the glass temperature.

DOI: 10.1103/PhysRevLett.105.015504

PACS numbers: 61.43.Fs, 64.70.pm, 64.70.Q–

The shear modulus is an unambiguous measure of the mechanical stability of materials. When one cools a glass former below its glass transition, a nonzero shear modulus appears on laboratory-accessible time scales. The understanding of the mechanism through which this rigidity emerges at the glass transition is a basic problem in condensed matter physics.

A standard view on glasses is to regard them as very slow liquids with extremely high shear viscosity [1]. Viscoelastic measurements show that supercooled liquids and various soft-glassy materials behave as solids: The elastic modulus develops a plateau at low frequencies, which extends to lower and lower frequencies by lowering the temperature or increasing the density (see [2,3] and references therein). Thus glasses acquire rigidity progressively. This feature is remarkably different from ordinary transitions from liquid to crystal, where the rigidity appears abruptly at the first-order phase transition.

Among various theoretical attempts, the so-called random first-order theory (RFOT) [4] provides a useful working ground to study the supercooled liquids and glasses in a unified manner [5]. At the mean-field level it is backed up by some microscopic approaches. On the one hand, it is intimately related to the mode-coupling theory (MCT) concerning the dynamics at relatively high temperatures [6]. On the other hand, the so-called cloned liquid approach, which combines the traditional liquid theory and the replica method, allows one to compute thermodynamic static quantities at lower temperatures [7–9]. This approach is currently the main first-principles approach to studying properties of the glass phase. So far, it has been limited to computing thermodynamic properties, in particular, the “complexity” giving the entropy associated with the number of glass states. One of the major challenges at present is to understand how the nucleation processes allowing the jumps between glass states, which are not taken into account in the simplest RFOT scenario, can be included in this scheme. These processes are, in particular, crucial for explaining why the mean-field prediction of a dynamical transition at the dynamical (MCT) temperature T_c breaks down, and is replaced by a rapid increase of the relaxation

time when the temperature gets close to T_c . Attempts in this direction include the mosaic theory of [5] and the study of long-range interactions [10].

We shall extend the cloned liquid approach in order to compute the static shear response of glasses. We identify the plateau modulus mentioned above by distinguishing intrastate and interstate stress fluctuations. When applied to mesoscopic samples, this approach predicts that the stress vs strain curve should have an intermittent behavior.

Models.—We consider a system of N particles ($i = 1, 2, \dots, N$) at position $\mathbf{r}_i = (x_i, y_i, z_i)$ in the laboratory frame, which are interacting with each other via two-body potentials, $H(\{\mathbf{r}_{ij}\}) = \sum_{i<j} v_{ij}(r_{ij})$, where $\mathbf{r}_{ij} = \mathbf{r}_i - \mathbf{r}_j$ and $r_{ij} = |\mathbf{r}_{ij}|$. In order to study the rigidity against simple shear deformation, we consider a system of particles in a container with two boundary walls which are normal to the z axis and separated from each other by distance L_z as shown in Fig. 1. To impose a shear strain γ on the system, we simply displace the top wall by an amount γL_z into the x direction. Then it is convenient to introduce a sheared frame with x' , y' , and z' , which are related to the laboratory frame as $(x, y, z) = (x' + z'\gamma, y', z')$. The volume of the system, V , and the number density $\rho = N/V$ remain constant under this shear.

Shear modulus.—The total free-energy $F(\gamma)$ of the system can be written as

$$-\beta F(\gamma) = \ln \int_{\gamma} \frac{\prod_i d^3 r_i}{V^N} e^{-\beta H(\{r_{ij}(\gamma)\})}, \quad (1)$$

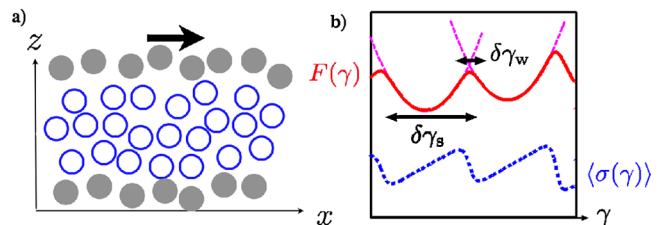


FIG. 1 (color online). Schematic picture of the system under static shear. (a) Mobile particles (open circles) bounded by “random walls” (filled circle). (b) Schematic mean-field picture of the energy landscape and stress-strain curve.

with $\beta^{-1} = k_B T$ being the inverse temperature. The ideal gas part of the free energy is omitted because it does not change. Note that the integration over the interior volume of the container is taken using the sheared frame $\mathbf{r}' = (x', y', z')$ for which the integration range \mathcal{V} is independent of the shear γ .

Taking the infinitesimal shear, the free energy can be expanded formally as $F(\gamma) = F(0) + N\langle\sigma\rangle\gamma + \frac{N}{2}\mu\gamma^2 + O(\gamma^3)$, where the shear stress σ and the shear modulus μ are

$$\mu = d\langle\sigma\rangle/d\gamma = \langle b \rangle - N\beta[\langle\sigma^2\rangle - \langle\sigma\rangle^2], \quad (2)$$

with

$$N\sigma = \frac{dH}{d\gamma} = \sum_{i<j} r v'(r)|_{r=r_{ij}} \hat{x}_{ij} \hat{z}_{ij}, \quad (3)$$

$$Nb = \frac{d^2H}{d\gamma^2} = \sum_{i<j} \hat{z}_{ij}^2 [r^2 v''(r) \hat{x}_{ij}^2 + r v'(r)(1 - \hat{x}_{ij}^2)]|_{r=r_{ij}},$$

where $\langle \dots \rangle$ denotes a thermal average evaluated with zero strain $\gamma = 0$. We have introduced shorthand notations like $\hat{x}_{ij} = (x_i - x_j)/r_{ij}$, and the prime stands for differentiation. The first term $\langle b \rangle$ in the definition of μ in Eq. (2) is called the Born term. It represents the instantaneous response of the system against shear $G(\tau = 0)$ (see below), which is finite even in liquids. The second term is the correction term due to thermal fluctuations of the shear stress.

This type of fluctuation formula for the static elastic constants is well known [11, 12]. In liquids, it is equivalent to the static limit of the Green-Kubo formula which relates the dynamic linear response against shear $\delta\sigma(t) = \int_{-\infty}^t dt' G(t-t') \dot{\gamma}(t')$ to the shear-stress autocorrelation function $\langle\sigma(t)\sigma(t')\rangle$ by $G(\tau) = \beta\langle\sigma(\tau)\sigma(0)\rangle$. Linear viscoelastic measurements give access to the complex dynamical modulus $G(\omega) = \omega G^*(\omega)$.

Boundary condition to shear.—Let us pause here to discuss more explicitly the boundary condition. First of all, it is obvious that the boundary walls should *not* be strictly translationally invariant to exert shear on the system. On the other hand, we want the system to maintain translational invariance at least on *macroscopic* scales. We thus assume that the walls are built from a quenched *random* configuration of particles, as shown in Fig. 1, so that the system keeps translational invariance in a *statistical* sense.

Because of the translational invariance at macroscopic scales, the thermodynamic free-energy density $\lim_{V \rightarrow \infty} F(\gamma)/V$ is independent of γ . This also happens in crystals, as discussed recently [13]. However, the definition of the shear modulus (and of the solid state) is through the linear response to a shear: The shear modulus in solids is nonzero because of the noncommutation of the small shear limit $\delta\gamma \rightarrow 0$ and thermodynamic limit $V \rightarrow \infty$. The same phenomenon happens in glasses. This discussion has interesting consequences if one studies the deformation of

mesoscopic samples on very small scales. We expect that the stress $\langle\sigma\rangle$ and shear modulus μ of a *single* realization of the random walls will be nonzero even after the thermal averaging, but will fluctuate along the γ axis (see Fig. 1). Only if one performs an average along the γ axis will one recover the zero average value. Physically, the breakdown of the commutation of the two limits means that the elasticity theory fails. Thus elasticity and plasticity must emerge simultaneously in solids. We will argue that the plastic events can be viewed as changes of the relevant metastable states when one varies γ (see Fig. 1).

Shear on a cloned system.—Let us now analyze the static response of glasses to shear. Taking the view of the RFOT, we suppose that there exist exponentially many metastable states $\alpha = 1, 2, \dots$ with free energies per particle f_α .

Our strategy is to consider a cloned system: m replicas ($a = 1, 2, \dots, m$) are forced to stay in the same metastable state, and we examine how the system responds to a generalized shear such that each replica a is submitted to a different strain γ_a . The total free energy F_m of such a cloned system can be written formally as

$$F_m(\gamma) = F_m(0) + N \sum_{a=1}^m \langle\sigma_a\rangle \gamma_a + \frac{N}{2} \sum_{a,b=1}^m \mu_{ab} \gamma_a \gamma_b + O(\gamma^3). \quad (4)$$

By clone symmetry the generalized shear modulus μ_{ab} can be written as

$$\mu_{ab} = \hat{\mu} \delta_{a,b} + \tilde{\mu} \quad (5)$$

with $\hat{\mu} = \langle b \rangle - N\beta \sum_{\alpha} [\langle\sigma^2\rangle_{\alpha} - \langle\sigma\rangle_{\alpha}^2] P_{\alpha}$ and $\tilde{\mu} = -N\beta [\sum_{\alpha} \langle\sigma\rangle_{\alpha}^2 P_{\alpha} - (\sum_{\alpha} \langle\sigma\rangle_{\alpha} P_{\alpha})^2]$, where $P_{\alpha} = e^{-m\beta[Nf_{\alpha} - F_m(0)]}$ is the thermal weight of the α th metastable state at temperature T/m and $\langle \dots \rangle_{\alpha}$ stands for a thermal average within the α th metastable state. $\hat{\mu}$ can be naturally interpreted as the intrastate shear modulus and $\tilde{\mu}$ as the negative correction due to *interstate* thermal fluctuations. It is easy to see that the physical shear modulus μ of a single system at temperature T/m can be obtained as $\mu = \sum_{b=1}^m \mu_{ab} = \hat{\mu} + m\tilde{\mu}$.

Physically, the intrastate shear modulus $\hat{\mu}$ should be interpreted as the plateau modulus measured in linear viscoelastic measurements [3]. We expect it not to fluctuate between different metastable states. On the other hand, $\tilde{\mu}$, which is due to the interstate fluctuations, should be different on different realizations of the random walls. As we discussed before, the statistical translational symmetry of the random walls requires the total modulus μ to vanish on average; this imposes that, on average over the realizations of random walls, $\tilde{\mu} = -\hat{\mu}/m$.

Within the RFOT [4], the metastable states disappear at a dynamical transition temperature $T_c (> T_K)$ predicted by the MCT [6]. Thus the plateau modulus $\hat{\mu}$ is positive only below T_c .

Cage expansion of the shear modulus.—Within the cloned liquid theory (see details in [7]) one assumes that

particles in different replicas form molecules with a certain “cage” size A , which plays the role of an order parameter that distinguishes the liquid phase $A = \infty$ from the glass phase $A < \infty$. The system is considered as a liquid at an effective temperature $T^* = T/m^*$, where $m^* = m^*(T)$ is determined for each temperature T by the stationarity condition of the free energy. One finds that $m^* < 1$ when $T < T_K$, where T_K is the Kauzmann temperature [14], while m^* sticks to the value 1 for larger temperatures. In many cases the behavior of m^* is well approximated by $m^* \approx T/T_K$ [7,8]. It is convenient to label the molecules as $i = 1, 2, \dots, N$ and to write the position of a particle as $\mathbf{r}_i^a = \mathbf{r}_i + \mathbf{u}_i^a$, where \mathbf{r}_i is the center-of-mass position of the molecule and \mathbf{u}_i^a describes the displacement of the particle in replica a within the molecule ($\sum_a \mathbf{u}_i^a = 0$). The cage size $A \equiv [Nm(m-1)]^{-1} \sum_i \sum_{a < b} \langle (u_i^a - u_i^b)^2 \rangle$ is assumed to be small enough to allow a small cage expansion. Then the fluctuation within the cage is characterized by $\langle u_i^a u_j^b \rangle_{\text{cage}} = -2(1 - m\delta_{ab}) \frac{A}{m} \delta_{ij}$, where u is a component of \mathbf{u} . If the cage size A changes discontinuously from a finite value to ∞ at T_c , as predicted by the MCT [6], the cage expansion can work, in principle, right up to T_c [9].

Using the above prescription, we have computed the shear modulus up to first order in the cage expansion [15]. The intrastate (or plateau) modulus is obtained as

$$\hat{\mu} = \langle b \rangle_* - J_1 + (J_2 + J_3)(1 - m), \quad (6)$$

where $\langle \dots \rangle_*$ is a thermal average at temperature T^* and

$$\begin{aligned} J_1 &= 2 \frac{A}{m} \frac{1}{N} \sum_i \sum_{j_1 (\neq i)} \sum_{j_2 (\neq i)} \beta^* \langle \nabla_{i j_1} \sigma_{i j_1} \cdot \nabla_{i j_2} \sigma_{i j_2} \rangle_*, \\ J_2 &= -2 \frac{A}{m} \frac{1}{N} \sum_{i < j} \langle \nabla_{ij}^2 b_{ij} \rangle_*, \\ J_3 &= 2 \frac{A}{m} \frac{1}{N} \sum_{i < j} \sum_{k < l} \beta^* \langle b_{ij} \nabla_{kl}^2 v(r_{kl}) \rangle_{c^*}, \end{aligned} \quad (7)$$

where σ_{ij} and b_{ij} are the summands in Eq. (3) and $\langle \dots \rangle_{c^*}$ stands for a connected correlation function at T^* . In the derivation of the above result, we used the fact that the shear modulus is zero in the liquid $\langle b \rangle_* - \beta^* \langle \sigma^2 \rangle_{c^*} = 0$.

The remarkable fact is that we can compute the plateau modulus at temperatures between T_K and T_c . From Eq. (6), one finds that in this regime (where $m^* = 1$), it takes the simple and suggestive form $\hat{\mu} = \langle b \rangle - J_1$. The physical interpretation of this result is very simple. On time scales shorter than the α -relaxation time, the stress field is essentially frozen in time. There, the only appreciable fluctuations are those associated with the β relaxation. The term J_1 represents the strength of the stress fluctuations due to these processes.

A test case: a binary soft-sphere system.—To test our scheme we performed an explicit computation of the shear modulus of the standard binary mixture of particles with soft-core interactions [16]. The Kauzmann temperature of

this system is $T_K \approx 0.14$ [8], while the dynamical (MCT) transition temperature is $T_c \approx 0.22$ [17]. In Fig. 2 we show the result for the case of density $\rho = 1$. To evaluate m^* and the radial distribution function $g_*(r)$ at T^* , we performed the cloned liquid computation using the binary hypernetted chain approximation [8].

The evaluation of various terms in Eq. (6) is done as follows. The Born term and J_2 involve only two-point functions so that they can be evaluated easily using $g_*(r)$. We evaluate J_1 by $J_1 = -2 \frac{A}{m} \int d^3 r g_*(r) \beta^* |\nabla \sigma|^2(r) - 2 \frac{A}{m} \int d^3 r_1 d^3 r_2 g(\mathbf{r}_1) g(\mathbf{r}_2) g(\mathbf{r}_{12}) \beta^* \nabla \sigma(\mathbf{r}_1) \cdot \nabla \sigma(\mathbf{r}_2)$, where we made a chain approximation in order to approximate the three-point correlation function by a product of two-point terms, an approximation which is reasonable at high densities. The evaluation of J_3 involves a connected four-point function which is expected to be smaller than the other terms, and we have neglected it at present.

As shown in Fig. 2, the plateau modulus $\hat{\mu}$ strongly depends on the temperature. Remarkably, it continuously crosses zero at a temperature very close to T_c determined by direct numerical simulations [17]. Furthermore, the cage size A is found to still be very small (10^{-2}) at this temperature, which justifies our use of the first-order small cage expansion. Our result of a plateau shear modulus emerging continuously below T_c disagrees with the conventional MCT [6], which predicts that the shear modulus jumps discontinuously to a finite value at T_c from the liquid side. Our result means that the density field is frozen at T_c as the MCT predicted, but the system is just marginally stable there [18], a picture which is consistent with the energy landscape picture of the RFOT [19–23]. For the viscoelastic measurements, this continuous transition suggests a power-law behavior $G'(\omega)$, $G''(\omega) \propto \omega^\lambda$.

Intermittency of static shear response.—Our results have a natural interpretation within a mean-field picture. They suggest the following “intermittent” nature of static shear response below T_K at *mesoscopic scales* such that the

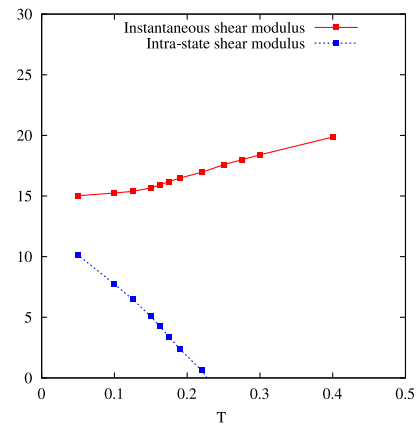


FIG. 2 (color online). Shear modulus of a binary soft-sphere system, computed from the cloned liquid approach. The bottom curve gives the plateau shear modulus; it is positive below $T_c \approx 0.22$.

system size N is *large but finite*. Within the mean field, the parameter $m = m^*(T) \simeq T/T_K$ obtained in the cloned liquid approach is naturally interpreted as the Parisi parameter of the one-step replica symmetry breaking ansatz for the glass phase.

As shown in Fig. 1, the interpretation at the mean-field level is that of a free-energy landscape $F(\gamma)$ which may be viewed as a sequence of parabolas with curvature $\hat{\mu}$ (plateau modulus) along the γ axis, matching with each other at yield points [24]. Below T_K , the static response to the shear is dominated by an intrastate response with an occasional interstate response when passing the yield points.

This picture is analogous to the mesoscopic response in mean-field spin-glass models [25]. Here γ plays the role of the external magnetic field h in spin glasses, which exhibit a stepwise increase of magnetization $m(h)$ along the h axis. The drops of the stress passing the yield points corresponds to steps of the magnetization. At a given γ , each metastable state has a random free energy f_α and a random stress $\langle \sigma \rangle_\alpha$ so that the increase of γ induces level crossings between low-lying states.

The distribution of the stress may be modeled by a Gaussian distribution with zero average and variance Δ/\sqrt{N} . From the correspondence with the spin-glass problem [25], we expect the typical spacing between the yield points to scale as $\delta\gamma_s \sim T_K/(\Delta\sqrt{N})$ and the width of thermal rounding of the yield points to scale as $\delta\gamma_w \sim T/(\Delta\sqrt{N})$. Here the parameter Δ is fixed as $\beta\Delta^2 = \hat{\mu}/m$ in order to satisfy the condition that the total shear modulus, including the interstate shear modulus, becomes zero on average. At low temperatures, if we choose a value of γ randomly, most of the time we will observe the plateau modulus $\hat{\mu}$, which is positive; occasionally, with probability $\delta\gamma_w/\delta\gamma_s \sim T/T_K$, we will find a negative shear modulus.

Discussion.—Our computations predict a nonzero plateau modulus $\hat{\mu}$ at all temperatures below the dynamical transition temperature T_c , including the low temperature regime [12]. They also give a natural way to compute this dynamical transition temperature within the cloned liquid theory, offering an alternative to the MCT computation. This plateau modulus should be observable dynamically on time scales smaller than the α relaxation time τ_α . Therefore one expects it to be seen, on all laboratory time scales, at all temperatures below the glass transition temperature (where the α relaxation time becomes larger than 10^3 s).

The prediction of intermittent shear response in mesoscopic samples should also be amenable to experimental tests. It is supposed to take place even at temperatures higher than T_K at the length and time scales of the so-called mosaic states proposed by the RFOT [4,5], because

each mosaic is subjected to a random pinning field provided by the surrounding mosaics.

We thank Giulio Biroli, Jean-Philippe Bouchaud, Song-Ho Chong, Silvio Franz, Jorge Kurchan, Anael Lemaître, Kunimasa Miyazaki, Michio Otsuki, and Tommaso Rizzo for useful discussions. This work is supported by *Triangle de la physique* Grant No. 117.

-
- [1] C. A. Angell, *Science* **267**, 1924 (1995).
 - [2] C. Maggi, B. Jakobsen, T. Christensen, N. B. Olsen, and J. C. Dyre, *J. Phys. Chem. B* **112**, 16320 (2008).
 - [3] T. G. Mason, Martin-D. Lacasse, G. S. Grest, D. Levine, J. Bibette, and D. A. Weitz, *Phys. Rev. E* **56**, 3150 (1997).
 - [4] T. R. Kirkpatrick, D. Thirumalai, and P. G. Wolynes, *Phys. Rev. A* **40**, 1045 (1989).
 - [5] M. P. Eastwood and P. G. Wolynes, *Europhys. Lett.* **60**, 587 (2002); J.-P. Bouchaud and G. Biroli, *J. Chem. Phys.* **121**, 7347 (2004); G. Biroli, J. P. Bouchaud, A. Cavagna, T. S. Grigera, and P. Verrocchio, *Nature Phys.* **4**, 771 (2008).
 - [6] W. Götze, in *Liquids, Freezing and Glass Transition*, edited by J. P. Hansen, D. Levesque, and J. Zinn-Justin (North Holland, Amsterdam, 1991), p. 287.
 - [7] M. Mézard and G. Parisi, *Phys. Rev. Lett.* **82**, 747 (1999); *J. Chem. Phys.* **111**, 1076 (1999).
 - [8] B. Coluzzi, M. Mézard, G. Parisi, and P. Verrocchio, *J. Chem. Phys.* **111**, 9039 (1999).
 - [9] G. Parisi and F. Zamponi, *Rev. Mod. Phys.* **82**, 789 (2010).
 - [10] S. Franz, *J. Stat. Mech.* (2005) P04001.
 - [11] D. R. Squire, A. C. Holt, and W. G. Hoover, *Physica (Amsterdam)* **42**, 388 (1969).
 - [12] C. Maloney and A. Lemaître, *Phys. Rev. Lett.* **93**, 195501 (2004); F. Leonforte, R. Boissière, A. Tanguy, J. P. Wittmer, and J.-L. Barrat, *Phys. Rev. B* **72**, 224206 (2005).
 - [13] F. Sausset, G. Biroli, and J. Kurchan, arXiv:1001.0918.
 - [14] A. W. Kauzmann, *Chem. Rev.* **43**, 219 (1948).
 - [15] Details of the derivations will be published elsewhere.
 - [16] B. Bernu, J. P. Hansen, Y. Hiwatari, and G. Pastore, *Phys. Rev. A* **36**, 4891 (1987).
 - [17] J. N. Roux, J. L. Barrat, and J.-P. Hansen, *J. Phys. Condens. Matter* **1**, 7171 (1989).
 - [18] M. Otsuki and S.-i. Sasa, *J. Stat. Mech.* (2006) L10004.
 - [19] J. Kurchan and L. Laloux, *J. Phys. A* **29**, 1929 (1996).
 - [20] S. Franz and G. Parisi, *Phys. Rev. Lett.* **79**, 2486 (1997).
 - [21] S. Franz and G. Parisi, *J. Phys. Condens. Matter* **12**, 6335 (2000).
 - [22] T. S. Grigera, A. Cavagna, I. Giardina, and G. Parisi, *Phys. Rev. Lett.* **88**, 055502 (2002).
 - [23] L. Berthier, J.-L. Barrat, and J. Kurchan, *Phys. Rev. E* **61**, 5464 (2000).
 - [24] J.-P. Bouchaud and M. Mézard, *J. Phys. A* **30**, 7997 (1997).
 - [25] H. Yoshino and T. Rizzo, *Phys. Rev. B* **77**, 104429 (2008).