

 Open access • Journal Article • DOI:10.1007/BF02644080

## Evaluation of Toughness in AISI 4340 Alloy Steel Austenitized at Low and High Temperatures — [Source link](#)

Robert O. Ritchie, Benjamin Francis, William L. Server

**Institutions:** Lawrence Berkeley National Laboratory, Harvey Mudd College

**Published on:** 01 Jun 1976 - Metallurgical and Materials Transactions A-physical Metallurgy and Materials Science (Springer-Verlag)

**Topics:** Charpy impact test, Toughness, Fracture toughness and Alloy steel

Related papers:

- [Further considerations on the inconsistency in toughness evaluation of AISI 4340 steel austenitized at increasing temperatures](#)
- [The effect of austenitizing temperature on the microstructure and mechanical properties of as-quenched 4340 steel](#)
- [On the relationship between critical tensile stress and fracture toughness in mild steel](#)
- [Effect of heat treatment on the fracture toughness of low alloy steels](#)
- [A general model to predict the elastic-plastic stress distribution and fracture strength of notched bars in plane strain bending](#)☆

Share this paper:    

View more about this paper here: <https://typeset.io/papers/evaluation-of-toughness-in-aisi-4340-alloy-steel-45sdfs91wm>

# Lawrence Berkeley National Laboratory

## Recent Work

**Title**

EVALUATION OF TOUGHNESS IN AISI 4340 ALLOY STEEL AUSTENITIZED AT LOW and HIGH TEMPERATURES

**Permalink**

<https://escholarship.org/uc/item/50s3t51d>

**Author**

Ritchie, R.O.

**Publication Date**

1975-09-01

Submitted to Metallurgical Transactions

RECEIVED  
LIBRARY  
BERKELEY CALIFORNIA

LBL-4125  
Preprint c.1

NOV 15 1975

LIBRARY  
OF THE UNIVERSITY OF CALIFORNIA

EVALUATION OF TOUGHNESS IN AISI 4340 ALLOY STEEL  
AUSTENITIZED AT LOW AND HIGH TEMPERATURES


R. O. Ritchie, B. Francis and W. L. Server

September 1975

Prepared for the U. S. Energy Research and  
Development Administration under Contract W-7405-ENG-48

**For Reference**

Not to be taken from this room

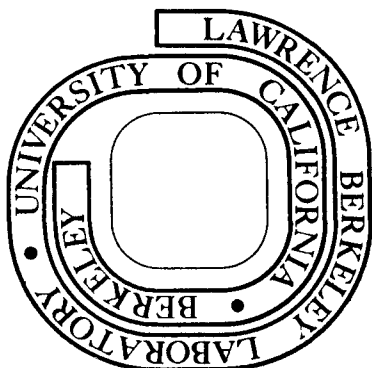

LBL-4125  
c.1

0 0 0 0 0 0 0 0 0 0

## **DISCLAIMER**

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

EVALUATION OF TOUGHNESS IN AISI 4340 ALLOY STEEL  
AUSTENITIZED AT LOW AND HIGH TEMPERATURES

R. O. Ritchie, B. Francis, and W. L. Server

Inorganic Materials Research Division, Lawrence Berkeley Laboratory and  
Department of Materials Science and Engineering, College of Engineering;  
University of California, Berkeley, California

ABSTRACT

It has been reported for as-quenched AISI 4340 steel that high temperature austenitizing treatments at 1200°C, instead of conventional heat-treatment at 870°C, result in a two-fold increase in fracture toughness,  $K_{Ic}$ , but a decrease in Charpy impact energy. This paper seeks to find an explanation for this discrepancy in Charpy and fracture toughness data in terms of the difference between  $K_{Ic}$  and impact tests. It is shown that the observed behavior is independent of shear lip energy and strain rate effects, but can be rationalized in terms of the differing response of the structure produced by each austenitizing treatment to the influence of notch root radius on toughness. The microstructural factors which affect this behavior are discussed. Based on these and other observations, it is considered that the use of high temperature austenitizing be questioned as a practical heat-treatment procedure for ultra-high strength, low alloy steels. Finally, it is suggested that evaluation of material toughness should not be based solely on  $K_{Ic}$  or Charpy impact energy values alone; both sharp crack fracture toughness and rounded notch impact energy tests are required.

---

R. O. Ritchie is Miller Research Fellow and Visiting Lecturer, Department of Materials Science and Engineering, College of Engineering, University of California, Berkeley, California 94720; B. Francis is Assistant Professor, Harvey Mudd College, Claremont, California 91711; and W. L. Server is Director of Materials Testing Laboratory, Effects Technology, Inc., Santa Barbara, California 93105.

## INTRODUCTION

Recent research<sup>1</sup> into the influence of austenitizing treatment on the mechanical properties of as-quenched AISI 4340 steel has shown that compared to conventional austenitizing at 870°C, increasing the austenitizing temperature to 1200°C can raise the plane strain fracture toughness ( $K_{Ic}$ ) by a factor of 2 (without reduction in yield strength). However, concurrent with this improvement in  $K_{Ic}$  there is an unexplained and perplexing reduction in the Charpy impact energy. The same effect has been reported for British Ni-Cr-Mo and Ni-Cr-Mo-V steels,<sup>2</sup> 4340<sup>3,4</sup> and 300M<sup>3</sup> steels, in both as-quenched and quenched and tempered (<350°C) conditions. Since  $K_{Ic}$  and the Charpy impact energy are both measures of material toughness, it appears paradoxical that high temperature austenitizing gives the greater toughness when rated by  $K_{Ic}$ , while low temperature austenitizing gives the greater toughness when rated by Charpy impact energy. In the face of this conflicting evaluation of toughness, it is tempting for the scientist to simply adopt the results of the  $K_{Ic}$  test and disregard the results of the Charpy test as "inadequate", since it is no doubt true that the  $K_{Ic}$  test is based on a theoretical foundation of greater solidity than is the Charpy impact test. In reality, however, the contradictory results of the two techniques for measuring toughness appear to be a real phenomenon and are indeed an indication of important differences between fracture induced by sharp ( $K_{Ic}$ ) and blunt (Charpy) notches. These differences may be summarized as follows: (1) the Charpy test measures the energy required to cause complete failure of the specimen and therefore will include a contribution from plane stress, shear lip formation. The fracture toughness test, on the other hand, measures a critical value of

the stress intensity ( $K$ ) at the crack tip necessary to cause plane strain unstable fracture. In a test-piece of valid thickness<sup>5</sup>, this value will be virtually independent of shear lip formation. (2) The strain rate in an impact test is several orders of magnitude greater than in a  $K_{Ic}$  test. In fact, when expressed in terms of rate of increase in stress intensity at the notch tip ( $\dot{K}$ ),  $\dot{K}$  for impact ('dynamic') testing is of the order of  $10^5$ - $10^6$  MPa/m/s compared with  $<3$  MPa/m/s for ('static')  $K_{Ic}$  tests. (3) There is a marked difference in the root radius ( $\rho$ ) of the stress concentrator in the two tests. Charpy test-pieces contain a V-notch ( $\rho \approx 0.25$  mm), whereas  $K_{Ic}$  test-pieces contain a fatigue pre-crack ( $\rho \rightarrow 0$ ).

It is the purpose of this paper to offer an explanation of the contradictory toughness results reported for the 4340 alloy, in the light of these basic differences, with the belief that this explanation may have considerably broader application.

## EXPERIMENTAL PROCEDURE

The material used in the investigation was aircraft quality (vacuum-arc remelted) AISI 4340 hot-rolled bar, received in the fully annealed condition, and having the following composition (wt pct):

C	Mn	Cr	Ni	Mo	Si	S	P	Cu
0.41	0.80	0.79	1.75	0.23	0.26	0.004	0.006	0.06

Two heat-treatments were studied: (1) the conventional austenitizing treatment of 1 hr at 870°C, followed by an oil quench and (2) the heat-treatment, recommended by Lai et al,<sup>1</sup> of 1 hr at 1200°C, followed by a salt quench to 870°C for 1/2 hr, then oil quenching to room temperature. The structures obtained by these heat-treatments are hereafter referred to as the 870°C and the 1200-870°C structures respectively.

The ambient temperature (22°C) uniaxial tensile properties and prior austenite grain sizes for these structures are shown in Table 1. Toughness properties were measured using Charpy V-notch impact tests, plane strain ('static') fracture toughness ( $K_{IC}$ ) tests, and dynamic fracture toughness ( $K_{Id}$ ) tests. Charpy impact energies were determined using standard sized (10 mm sq) ASTM Charpy V-notch specimens,<sup>6</sup> broken in a pendulum type impact machine of hammer velocity 3.3 m/s.  $K_{IC}$  values were determined in accordance with ASTM specifications,<sup>5</sup> using 15.4 mm thick C.T.S. test-pieces. All  $K_{IC}$  values were found to be 'valid' according to this specification.  $K_{Id}$  data were determined using fatigue pre-cracked standard Charpy specimens<sup>7</sup> broken using an instrumented (Dynatup) Charpy impact machine at a hammer velocity of 1.36 m/s. The complete experimental procedure for dynamic  $K_{Id}$  testing has been described elsewhere.<sup>8</sup> Test-pieces for all experiments were machined in the longitudinal (L-T) orientation.



## RESULTS

The ambient temperature (22°C) toughness properties for both structures are shown in Table 2. Two important features are shown by this data:

(1) As originally reported by Lai et al,<sup>1</sup> the 1200-870°C structure has superior  $K_{Ic}$  but inferior Charpy values, with respect to the 870°C structure. The difference in Charpy values is, however, small. (2) Both  $K_{Ic}$  and  $K_{Id}$  results show the 1200-870°C structure to be the tougher, although there is some reduction in the dynamic values due to the higher strain rate.

In the following paragraphs we now consider these results in terms of the basic differences between the Charpy and fracture toughness tests, as summarized above.

### (1) Shear Lip Effects

It is well known that the shear lip portion of the fractured surface of a Charpy test-piece requires more energy per unit area to fracture than does the flat portion. Therefore, a significant increase in the proportion of plane stress shear lips in the 870°C structure, over that of the 1200-870°C structure, could possibly account for the small improvement in Charpy energy of the 870°C structure.\* Examination of the broken Charpy test-pieces, however, confirmed that there was no measurable difference in the shear lip area for the two structures. In fact, the proportion of shear lip area for both structures was always less than 4%. It is concluded that fractures in both Charpy and  $K_{Ic}$  tests occurred under fully plane strain conditions, and therefore the contribution from shear lip formation can be eliminated as an explanation for the difference in Charpy and  $K_{Ic}$  test results.

---

\* In view of the fact that the yield strengths of the two structures were identical, and that the  $K_{Ic}$  for the 870°C structure was less than for the 1200-870°C structure, one would not expect such an increase. 0

## (2) Strain Rate Effects

There is always a possibility when comparing Charpy impact and  $K_{Ic}$  values that the higher strain rate of the impact test ( $\sim 10^1 - 10^2 \text{ sec}^{-1}$  compared to  $\sim 10^{-4} \text{ sec}^{-1}$  in static tests) may induce a change in fracture mechanism through an increase in the ductile/brittle transition temperature.

In the present results, it might be expected that the transition temperature would be higher for the 1200-870°C structure because of the larger grain size. Thus, increased strain rate may shift the transition temperature of the 1200-870°C structure above room temperature in the Charpy test, whilst leaving the transition temperature of the 870°C structure below room temperature. This would result in a low Charpy impact energy for the 1200-870°C structure.

Scanning electron microscopy of fracture surfaces of both Charpy and  $K_{Ic}$  test-pieces, however, showed that the fracture mechanisms were identical in both tests for a given structure. Failure in both Charpy and  $K_{Ic}$  test-pieces occurred by quasi-cleavage and fibrous rupture in the 870°C structure, and by intergranular and fibrous fracture in the 1200-870°C structure (Fig. 1). Since for a given heat-treatment the fracture mechanisms, at both high and low strain rates, are the same, change of mechanism can be eliminated as an explanation for the contradictory toughness results.

There is an additional possibility that a strain rate effect could occur without change in fracture mechanism, through, for example, an effect on deformation flow properties. To test this possibility dynamic fracture toughness ( $K_{Id}$ ) tests were conducted on pre-cracked test-pieces. The results are listed in Table 2, where it can be seen that, although there was some reduction in toughness for the higher austenitizing treatment,

the 1200-870°C structure still shows superior fracture toughness compared to the 870°C structure. Since this result occurs at the same strain rate as in standard Charpy tests, which show the opposite result in terms of which structure is tougher, it is clear that strain rate sensitivity does not provide an explanation for the contradictory toughness results.

### (3) Notch Root Radius Effects

A significant difference between Charpy and fracture toughness testing is the radius of the stress concentrator introduced into the test-pieces. Charpy test-pieces contain a V-notch ( $\rho=0.25$  mm) whereas  $K_{Ic}$  test-pieces contain a fatigue pre-crack ( $\rho \rightarrow 0$ ). To determine how measured toughness varies with notch root radius for each austenitizing treatment, a series of Charpy test-pieces was prepared with notch root radii ranging from a fatigue pre-crack to a 0.58 mm radius V-notch. The specimens were broken at room temperature (22°C) in an instrumented Charpy machine, and impact energy and "apparent" dynamic fracture toughness,  $K_A^*$ , measured in each case (Table 3). In Fig. 2 the apparent fracture toughness,  $K_A$ , is shown as a function of the square root of the notch radius,  $\rho^{1/2}$ , for both microstructures. The important feature of this figure is that for small root radii ( $\rho < 0.05$  mm) the toughness of the 1200-870°C structure exceeds that of the 870°C structure, whereas at larger radii ( $\rho > 0.05$  mm) the reverse is the case. A similar effect has been observed for fine and coarse grained 4340 tested at liquid nitrogen temperatures.<sup>12</sup> Thus, it can be seen that in fracture toughness tests, where  $\rho \rightarrow 0$ , the 1200-870°C structure will have the higher  $K_{Ic}$  value; but for Charpy tests, where  $\rho=0.25$  mm, the 870°C structure will fracture at the larger  $K_A$  value, and thus show the larger impact energy. This is precisely the behavior

\* "Apparent" fracture toughness refers to the value of  $K_{Ic}$  (or  $K_{Id}$ ) measured ahead of a rounded notch of radius  $\rho$ , and is generally used as a means of estimating the fracture toughness without recourse to fatigue pre-cracking.<sup>9-11</sup>

reported previously.<sup>1-4</sup>

An explanation for this effect can be deduced by examining the simple theory, developed by Tetelman and co-workers,<sup>9,10</sup> to account for the influence of notch root radius ( $\rho$ ) on fracture toughness. For constant stress-controlled fracture, it was proposed that failure occurs when the maximum tensile stress,  $\sigma_{yy}^{\max}$ , located at the plastic-elastic interface exceeds a critical fracture stress,  $\sigma_F$ , for failure. Thus if

$$\sigma_{yy}^{\max} = \sigma_y [1 + \ln(1 + r/\rho)] \dots \dots \dots (1)$$

from slip-line field theory, where  $\sigma_y$  is the uniaxial yield stress in tension and  $r$  is the distance from the notch tip; and

$$r_c \approx 0.12 (K_A/\sigma_y)^2 \dots \dots \dots (2)$$

from linear elastic theory, where  $r_c$  is the radius of the critical plastic zone size, then at failure, when  $\sigma_{yy}^{\max} = \sigma_F$ , and  $r = r_c$ ,

$$K_A \approx 2.9 \sigma_y [\exp (\sigma_F/\sigma_y - 1) - 1]^{1/2} \rho^{1/2} \dots \dots \dots (3)$$

Equation 3 shows that the apparent fracture toughness ( $K_A$ ) varies with  $\rho$ , as found experimentally and shown in Fig. 2. However, for some radius ( $\rho < \rho_o$ ),  $K_A$  is independent of  $\rho$  and has the same value as  $K_{Ic}$ , measured in standard ASTM specimens<sup>5</sup> which have been fatigue pre-cracked before testing. Consequently, Tetelman and co-workers<sup>9,10</sup> proposed that

$$K_{Ic} \text{ (or } K_{Id}) \approx 2.9 \sigma_y [\exp (\sigma_F/\sigma_y - 1) - 1]^{1/2} \rho_o^{1/2} \dots (4)$$

The parameter  $\rho_o$ , the "effective" or limiting root radius, is a measure of the extent of the process zone ahead of the crack (the

"characteristic distance") over which the critical stress  $\sigma_F$  must exist to cause failure, and is related to the microstructural feature which controls fracture (such as slip or twin band spacings, grain size or inclusion spacing).<sup>13-15</sup> The characteristic distance ( $l$ ) represents the minimum distance from the notch where the critical fracture event can occur (i.e., where  $\sigma_{yy} > \sigma_F$ ), and is only important where the maximum tensile stress ( $\sigma_{yy}^{max}$ ) is very close to the notch tip.<sup>14,15</sup> This is the case ahead of sharp cracks,<sup>16</sup> where  $\sigma_{yy}^{max}$  at fracture is located at a distance ahead of the crack tip which is generally smaller than the characteristic distance. Ahead of rounded notches ( $\rho > \rho_o$ ), however,  $\sigma_{yy}^{max}$  is located at, or just behind,<sup>17</sup> the plastic-elastic interface, and thus at failure the critical fracture event is occurring at a distance from the crack tip which is large compared with the characteristic distance.\* A schematic representation of these fracture events is shown in Fig. 3.

The application of this model to the present results is complicated by the fact that it is only strictly valid for stress-controlled fracture, and was derived from data on cleavage in mild steel.<sup>9</sup> The failure mechanisms in 4340 steel are far more complex (see Fig. 1), but at least the dominant fracture mechanism for both structures can be considered to be largely stress-controlled (i.e. quasi-cleavage and intergranular cracking). In addition, the general form of the relationship between toughness and root radius shown in Fig. 2, and the existence of a limiting root radius would appear to be unchanged even for strain-controlled ductile fracture.<sup>18</sup>

Examination of Fig. 2 in the light of the above theory reveals (i) the critical fracture stress,  $\sigma_F$ , is smaller in the 1200-870°C

---

\*A fuller explanation of how the stress distribution ahead of sharp and rounded notches can influence fracture behavior can be found in references 14 and 15.

structure compared to the 870°C structure, as indicated by the differing slopes of the curves (see Eqn. 3). (ii) The limiting root radius,  $\rho_0$ , is larger for the 1200-870°C structure compared to the 870°C structure. (iii) For both structures, the value of  $\rho_0$  is of the same order as the prior austenite grain size. These observations indicate that the higher austenitizing treatment has caused a reduction in critical fracture stress, but increased the critical distance over which it must be exceeded for failure. The increase in characteristic distance appears to be associated with the larger grain size. The decrease in  $\sigma_F$  is probably the result of segregation of impurity elements to the smaller grain boundary surface area of the larger grain-sized material - typically, segregation of phosphorous leading to intergranular cracking,<sup>19,20</sup> and segregation and precipitation of sulfur leading to intergranular fibrous rupture.<sup>21,22</sup>

Thus,  $K_{Id}$  (and  $K_{Ic}$ ) will be increased in the larger grained 1200-870°C structure because the fracture stress ahead of the sharp crack must be exceeded over a much larger distance (Fig. 3a and b). In Charpy tests, however, where the larger root radius causes the critical fracture event to occur much further away from the notch tip, the lower fracture stress of the 1200-870°C structure leads to an inferior  $K_A$  and thus lower impact energy with respect to the 870°C condition (Fig. 3c and d).

## DISCUSSION

It can be seen from this work that the explanation for the differences in toughness, as evaluated by fracture toughness and Charpy tests, may be attributed to the differing response of each structure to the influence of notch root radius on toughness. An explanation of this effect in terms of microstructure is more complex. It has been suggested that the improvement in  $K_{Ic}$  from high temperature austenitizing can be attributed to (a) dissolution of carbides at the high solution temperatures;<sup>1,23</sup> (b) retention of austenite films around martensite plates;<sup>1,23</sup> (c) elimination of proeutectoid ferrite<sup>24</sup> and upper bainite<sup>23-25</sup> due to increased hardenability from the larger grain size; or (d) lack of twinned martensite plates in the as-quenched structure.<sup>26,27</sup> Such microstructural modifications, however, should also lead to increased impact energies, which are not observed. The present analysis indicates that the increase in  $K_{Ic}$  (and  $K_{Id}$ ), following high temperature austenitizing, results merely from a significant increase in effective root radius  $\rho_o$ .

The magnitude of  $\rho_o$  should relate to the particle spacing or grain size, depending upon the mechanism of failure. For particle-controlled fracture (e.g. fully fibrous rupture) the increase in  $\rho_o$  could be attributed to increased carbide spacings, although, in the present case, these particle spacings do not relate numerically to the values of  $\rho_o$  obtained. For cleavage and intergranular fracture, on the other hand, it has been shown<sup>15,28</sup> that the magnitude of  $\rho_o$  is of the order of the grain size (i.e. approximately equal to 2 grain diameters for cleavage in mild steel,<sup>15</sup> and 1-1½ grain diameters for intergranular failure in low alloy, En30A steel<sup>28</sup>). Since

in the present results, the principal fracture modes are either cleavage or intergranular cracking, and the numerical values of  $\rho_o$  are of the same order as the grain diameters, it must be concluded (although tentatively) that the increase in  $\rho_o$ , and hence  $K_{Ic}$ , for the high temperature austenitizing treatment, is a result of the order of magnitude increase in grain size.

It is clear that the use of high temperature austenitizing, instead of conventional heat-treatment, can result in steels of much improved fracture toughness ( $K_{Ic}$ ), but the accompanying low Charpy impact energies must limit the practical usefulness of such procedures. Other results<sup>1-4,29</sup> in the literature substantiate this claim.\* For example, it has been reported<sup>29</sup> that an Fe/3.85% Mo/0.18%C steel has a  $K_{Ic} = 93$  ksi/in (103 MPa $\sqrt{m}$ ) after oil quenching from 1200°C, and yet the Charpy impact energy for this condition is a mere 11 ft.lb. (15J). It should also be noted that the tensile ductility properties of low alloy steels austenitized at high temperatures can be greatly reduced. This can be seen from results<sup>3</sup> obtained for AISI 4130, 4330, 4140, 4340, 300M and D6-AC steels in both as-quenched and quenched and tempered conditions. In the present results, for instance, the reduction in area for as-quenched 4340 is only 8% in the 1200-870°C structure, compared to 31% in the 870°C structure (Table 1). The percentage elongation is similarly reduced (by a factor of 3), and this is consistent with a lower 'true' fracture stress in the 1200-870°C structure. Furthermore, the considerably larger prior austenite grain size of steels austenitized at higher temperature

---

\*AISI 4130 and 4330 steels appear to be exceptions, although even these steels, when tempered above 300°C, show superior Charpy impact energies after austenitizing at 870°C, compared to the high temperature austenitized treatments.<sup>3</sup>



can lead to increased dangers from temper embrittlement<sup>19</sup> and tempered martensite embrittlement,<sup>30</sup> if the steel is subsequently tempered. The smaller grain boundary area associated with large grain sizes implies that segregation of impurity elements, should it occur, will be more effective in producing subsequent embrittlement because the relative degree of grain boundary coverage produced by a given amount of solute can be correspondingly greater.<sup>28</sup> Thus, although there is evidence,<sup>31,32</sup> in certain molybdenum-containing secondary hardening steels, that austenitizing at 1200°C can be beneficial to strength as well as fracture toughness (no Charpy impact values were reported), it is felt that, in general, the use of high temperature austenitizing treatments for ultra-high strength, low alloy steels, in place of conventional low temperature treatments, should be regarded with extreme caution.

Finally, it is considered that the phenomenon described in this paper has an important bearing on what procedures should be carried out in alloy design to evaluate material toughness. Although  $K_{Ic}$  (and  $K_{Id}$ ) measurements are obviously necessary, it appears no longer sufficient to grade toughness solely in terms of these parameters, since they only indicate material resistance to fracture ahead of sharp cracks. For the present steel, for example, grading material toughness by  $K_{Ic}$  (or  $K_{Id}$ ) alone would lead to the conclusion that the steel austenitized at 1200°C was tougher. Yet, if in service the steel contained a blunt indentation, the structure resulting from the conventional 870°C heat-treatment would show superior resistance to fracture for all notch root radii greater than 0.002 in (0.05 mm). Thus, it is suggested that the toughness evaluation of a material must include a measure of resistance to fracture ahead of both

sharp and rounded notches. It appears insufficient to grade material toughness solely on the basis of  $K_{Ic}$  or Charpy impact energy values alone. An assessment from both sharp crack fracture toughness and rounded notch impact energy testing is required.

### CONCLUSIONS

(1) It has been verified that a high temperature austenitizing treatment of 1200° (followed by a step quench to 870°C) improves the fracture toughness of as-quenched AISI 4340, but gives rise to inferior Charpy impact energies compared to conventional 870°C austenitizing.

(2) This effect was shown to be independent of shear lip energy differences, and to be independent of variation in strain rate imposed by  $K_{Ic}$  and impact tests.

(3) The effect was found to result from the differing behavior of each structure to the influence of notch root radius on toughness.

(4) The structure obtained after austenitizing at 1200°C was found to show superior toughness for failure ahead of sharp cracks (i.e. in  $K_{Ic}$  and  $K_{Id}$  tests) due to its larger "effective" root radius for fracture. This was tentatively associated with the larger prior austenite grain size.

(5) The structure obtained after conventional austenitizing at 870°C was found to show superior toughness for fracture ahead of rounded notches (i.e. in Charpy impact tests) due to its larger critical fracture stress for failure.

(6) The use of high temperature austenitizing treatments, in place of conventional heat-treatments, for ultra-high strength, low alloy steels is questioned, because the structures which result appear to show low Charpy impact energies and much lower ductility, and may give rise to increased susceptibility to embrittlement during tempering.

(7) It is suggested that evaluation of material toughness must include a measure of resistance to fracture ahead of both sharp and rounded notches. It appears insufficient to grade material toughness solely on the basis of  $K_{Ic}$  or Charpy impact energy values alone. Both sharp crack  $K_{Ic}$  and rounded notch impact energy values are required.

#### ACKNOWLEDGEMENTS

The authors would like to thank Dr. T. R. Wilshaw of Effects Technology, Inc. for helpful discussions, Dr. N. F. Kennon and Mr. R. M. Horn for their critical review of the manuscript, and Mr. J. W. Scheckherd for assistance in performing the instrumented Charpy tests. The continued support of Professors E. R. Parker and V. F. Zackay of the University of California in Berkeley is also appreciated. The research was conducted partially under the auspices of U. S. Energy Research and Development Administration through the Inorganic Materials Research Division of the Lawrence Berkeley Laboratory, and partially through Dynatup Services, Effects Technology, Inc., Santa Barbara.

REFERENCES

1. G. Y. Lai, W. E. Wood, R. A. Clark, V. F. Zackay and E. R. Parker: Met. Trans., 1974, vol. 5, p. 1663.
2. D. Dulieu: Discussion to paper by V. F. Zackay, E. R. Parker and W. E. Wood; "The Microstructure and Design of Alloys," Proc. Third Intl. Conf. on the Strength of Metals & Alloys, Cambridge, England, Aug. 1973, vol. 2, p. 383. (Institute of Metals/Iron and Steel Institute).
3. W. E. Wood, E. R. Parker and V. F. Zackay: "An Investigation of Metallurgical Factors which Affect the Fracture Toughness of Ultra High Strength Steels," Report No. LBL-1474, May 1973. (Lawrence Berkeley Laboratory, University of California, Berkeley, California 94720).
4. A. A. Anctil and E. B. Kula: unpublished research, 1975 (Army Materials and Mechanics Research Center, Watertown, Mass.).
5. Annual Book of ASTM Standards (American Society for Testing and Materials), ASTM Standards E399-74, Philadelphia, 1974.
6. Annual Book of ASTM Standards (American Society for Testing and Materials), ASTM Standards E23-72, Philadelphia, 1972, p. 276.
7. W. L. Server and A. S. Tetelman: Eng. Fract. Mech., 1972, vol. 4, p. 367.
8. W. L. Server, D. R. Ireland and R. A. Wullaert: "Strength and Toughness Evaluations from an Instrumented Impact Test", Dynatup Technical Report No TR 74-29R, November 1974. (Effects Technology, Inc., Santa Barbara, California 93105).
9. T. R. Wilshaw, C. A. Rau and A. S. Tetelman: Eng. Fract. Mech., 1968, vol. 1, p. 191.

10. J. Malkin and A. S. Tetelman: *ibid.*, 1971, vol. 3, p. 151.
11. P. T. Heald, G. M. Spink and P. J. Worthington: *Mater. Sci. Eng.*, 1972, vol. 10, p. 129.
12. S. Ensha and A.S. Tetelman: "The Effect of Microstructure on the Fracture Toughness of Low-Alloy Steels", UCLA Technical Report No. 14, UCLA-ENG-7435, May 1974. (School of Engineering and Applied Science, University of California, Los Angeles, California 90024).
13. A. H. Cottrell: "The Mechanical Properties of Matter," p.365 John Wiley, New York, 1964.
14. A. S. Tetelman, T. R. Wilshaw and C. A. Rau: *Int. J. Fract. Mech.*, 1968, vol. 4, p. 147.
15. R. O. Ritchie, J. F. Knott and J. R. Rice: *J. Mech. Phys. Solids*, 1973, vol. 21, p. 395.
16. J. R. Rice and M. A. Johnson: "Inelastic Behavior of Solids," edited by M. F. Kanninen et al., p. 641, McGraw Hill, New York, 1970.
17. J. R. Griffiths and D. R. J. Owen: *J. Mech. Phys. Solids*, 1971, vol. 19, p. 149.
18. C. G. Chipperfield and J. F. Knott: *Metals Technology*, 1975, vol. 2, p. 45.
19. B. J. Schulz and C. J. McMahon, Jr.: *ASTM Special Technical Publ.* No. 499, 1972, p. 104. (American Society for Testing and Materials).
20. G. Clark, R. O. Ritchie and J. F. Knott: *Nature Phys. Sci.*, 1972, vol. 239, p. 104.
21. B. J. Schulz and C. J. McMahon, Jr.: *Met. Trans.*, 1973, vol. 4, p. 2485.
22. R. O. Ritchie and J. F. Knott: *ibid.*, 1974, vol. 5, p. 782.

23. G. Thomas: Iron and Steel International, 1973, vol. 46, p. 451.
24. G. Y. Lai: Mater. Sci. Eng., 1975, vol. 19, p. 153.
25. W. E. Wood: Eng. Fract. Mech., 1975, vol. 7, p. 219.
26. S. K. Das and G. Thomas: Trans. ASM, 1969, vol. 62, p. 659.
27. J. A. McMahon and G. Thomas: "The Microstructure and Design of Alloys", Proc. Third Intl. Conf. on the Strength of Metals and Alloys, Cambridge, England, Aug. 1973, vol. 1, p. 180. (Institute of Metals/Iron and Steel Institute).
28. R. O. Ritchie, L. C. E. Geniets and J. F. Knott: ibid., p. 124.
29. R. A. Clark and G. Thomas: Met. Trans.A, 1975, vol. 6A, p. 969.
30. J. R. Rellick and C. J. McMahon, Jr.: Met. Trans., 1974, vol. 5, p. 2439.
31. V. F. Zackay, E. R. Parker, R. D. Goolsby and W. E. Wood: Nature Phys. Sci., 1972, vol. 236, p. 108.
32. T. Tom: "Microstructural Variables and Fracture Toughness of High Strength Mo and Mo-Ni Steels," (D. Eng. Thesis), Report No. LBL-1856, Sept. 1973. (Lawrence Berkeley Laboratory, University of California, Berkeley, California 94720).

TABLE CAPTIONS

- Table 1. Ambient Temperature Longitudinal Tensile Properties for Alloy AISI 4340 in the Oil Quenched Condition (after Lai et al<sup>1</sup>).
- Table 2. Ambient Temperature Longitudinal Toughness Properties for Alloy AISI 4340 in the Oil Quenched Condition.
- Table 3. Ambient Temperature Instrumented Charpy Results for Alloy AISI 4340 in the Oil Quenched Condition, showing the Variation of Charpy Impact Energy and Apparent Fracture Toughness ( $K_A$ ) with Notch Root Radius ( $\rho$ ).



Table 1. Ambient Temperature Longitudinal Tensile Properties for Alloy AISI 4340 in the Oil Quenched Condition (after Lai et al<sup>1</sup>)

Austenitizing Temperature °C	0.2 pct Proof Stress		Ultimate Tensile Strength		Elongation  pct	Reduction in area  pct	True Fracture Strain pct	Prior Austenite grain size, μm
	ksi	MPa	ksi	MPa				
1200-870	231	1593	318	2193	3.2	7.8	0.07	254-360
870	231	1593	322	2217	9.0	30.8	0.18	24-32

00004308494

Table 2. Ambient Temperature Longitudinal Toughness Properties for Alloy AISI 4340 in the Oil Quenched Condition.

Austenitizing Temperature, °C	Charpy V-notch Impact Energy		Plane Strain Fracture Toughness, $K_{Ic}$		Dynamic Fracture Toughness, $K_{Id}$	
	ft.lb.	J	ksi√in	MPa√m	ksi√in	MPa√m
1200-870	5.4*	7.32	63.8*	70.1	54.2	59.6
	6.0*	8.13	66.6*	73.2	48.8	53.7
	5.0	6.78	61.2*	67.2		
	2.0	2.71				
	6.0	8.13				
870	7.5*	10.20	31.1*	34.2	36.6	40.3
	6.1*	8.27	39.0*	42.9	30.0	33.0
	7.5	10.20	32.3*	35.5	33.3	36.6

\*after Lai et al<sup>1</sup>.

000004308495

The circuit of this unit in its gas-fired configuration is shown in Figure 4. The modifications that must be made to this unit to convert to solar operation are more drastic than would be the modifications of a water-lithium bromide unit. The gas-fired ammonia-water unit uses the high temperatures available with a gas flame to produce a temperature in the generator of about 325°F, which leads to a concentration of ammonia in the solution leaving the generator (the strong absorbent) of about 12%. Because of this very low concentration (relative to that produced in the solar driven unit), the gas-driven unit can use a solution-cooled absorber to preheat the solution (weak absorbent) entering the generator. This is not possible in the solar driven configuration.

Three major modifications were necessary to the gas-driven unit. Most obviously, the gas-fired generator had to be replaced by a water heated generator. This required replacement of the generator rather than just modification. Second, because the temperatures available in the generator do not allow large changes in the ammonia concentration of the solution passing through the generator, more solution must be pumped for each pound of refrigerant that is to be generated. Thus the solution pump in the unit must be replaced by a pump with three to five times the original capacity. Third, because the solution-cooled absorber will no longer be effective in preheating the solution entering the generator, a liquid-liquid heat exchanger must be added. When these modifications are made to the gas-fired unit, the unit shown in Figure 5 is obtained.

The state points shown for the solar-driven unit in Figure 5 have been calculated by a rather naive program that does not carefully treat all the temperature, pressure, and concentration drops that occur in the system. However, the values shown do indicate the regime of operation under which our experiments will be conducted. The solution-cooled absorber will be retained in the unit, even though we expect it will be rather ineffective. The use of the

Table 3. Ambient Temperature Instrumented Charpy Results for Alloy AISI 4340 in the Oil Quenched Condition, Showing the Variation of Charpy Impact Energy and Apparent Fracture Toughness ( $K_A$ ) with Notch Root Radius ( $\rho$ ).

Austenitizing Temperature, °C	Notch Root Radius $\rho$		Charpy Impact Energy		Apparent Dynamic Fracture Toughness $K_A$	
	in	$\mu\text{m}$	ft.lb.	J	ksi/in	MPa $\sqrt{\text{m}}$
1200-870	0	0	1.5	2.03	48.8	53.7
	0	0	2.4	3.25	54.2	59.6
	0.0011	27.9	2.3	3.12	46.4	51.0
	0.0038	96.5	2.3	3.12	45.3	49.8
	0.0094	238.8	2.0	2.71	48.7	53.5
	0.0094	238.8	6.0	8.13	54.8	60.2
	0.0115	292.1	5.0	6.78	52.9	58.1
	0.0171	434.3	3.0	4.07	62.0	68.1
	0.0230	584.2	3.0	4.07	69.2	76.1
870	0	0	1.0	1.36	30.0	33.0
	0	0	1.0	1.36	33.3	36.6
	0	0	1.0	1.36	36.6	40.3
	0.0012	30.5	2.3	3.12	48.7	53.5
	0.0027	68.6	3.0	4.07	63.4	69.7
	0.0033	83.8	4.5	6.10	78.2	85.9
	0.0084	213.4	5.7	7.73	95.5	105.0
	0.0100	254.0	7.5	10.2	105.7	116.2
	0.0133	337.8	9.5	12.9	126.4	138.9
	0.0175	444.5	12.3	16.7	132.5	145.6
	0.0220	558.8	13.5	18.3	137.1	150.7

FIGURE CAPTIONS

Fig. 1 Fractographs of as-quenched 4340; showing (a) in structure austenitized at 870°C, quasi-cleavage (~65%) linked by areas of fibrous rupture; and (b) and (c) in structure austenitized at 1200-870°C, intergranular cracking (~55%) and transgranular fibrous rupture. Several intergranular facets show evidence of microvoid coalescence on grain boundary surfaces (c).

NOTE: 1200-870°C structure fails partly by intergranular fracture, and not, as erroneously reported in ref. 1, by 100% fibrous rupture.

Fig. 2 The relationship between toughness, measured by the apparent dynamic fracture toughness, ( $K_A$ ) from instrumented Charpy tests, and notch root radius ( $\rho$ ) in oil quenched AISI 4340, for the 1200-870°C and 870°C structures.  $\rho_0$  is the 'limiting' root radius,  $K_{Id}$  the dynamic fracture toughness.

Fig. 3 Schematic representation of the distribution of tensile stress ( $\sigma_{yy}$ ) at distance ( $r$ ) ahead of stress concentrator at failure for (a) 870°C structure with sharp crack ( $\rho < \rho_0$ ), (b) 1200-870°C with sharp crack, (c) 870°C structure with rounded notch ( $\rho > \rho_0$ ), (d) 1200-870°C structure with rounded notch. Critical fracture event occurs when  $\sigma_{yy} > \sigma_F$  over characteristic distance ( $\ell$ ) ahead of sharp crack, or when  $\sigma_{yy}^{\max} \geq \sigma_F$  at the plastic-elastic interface ( $r_c \gg \ell$ ) ahead of rounded notch. Toughness of 1200-870°C structure is greater ahead of sharp crack because characteristic distance ( $\ell$ ) is larger, toughness of 870°C structure is greater ahead of rounded notch because fracture stress ( $\sigma_F$ ) is larger.


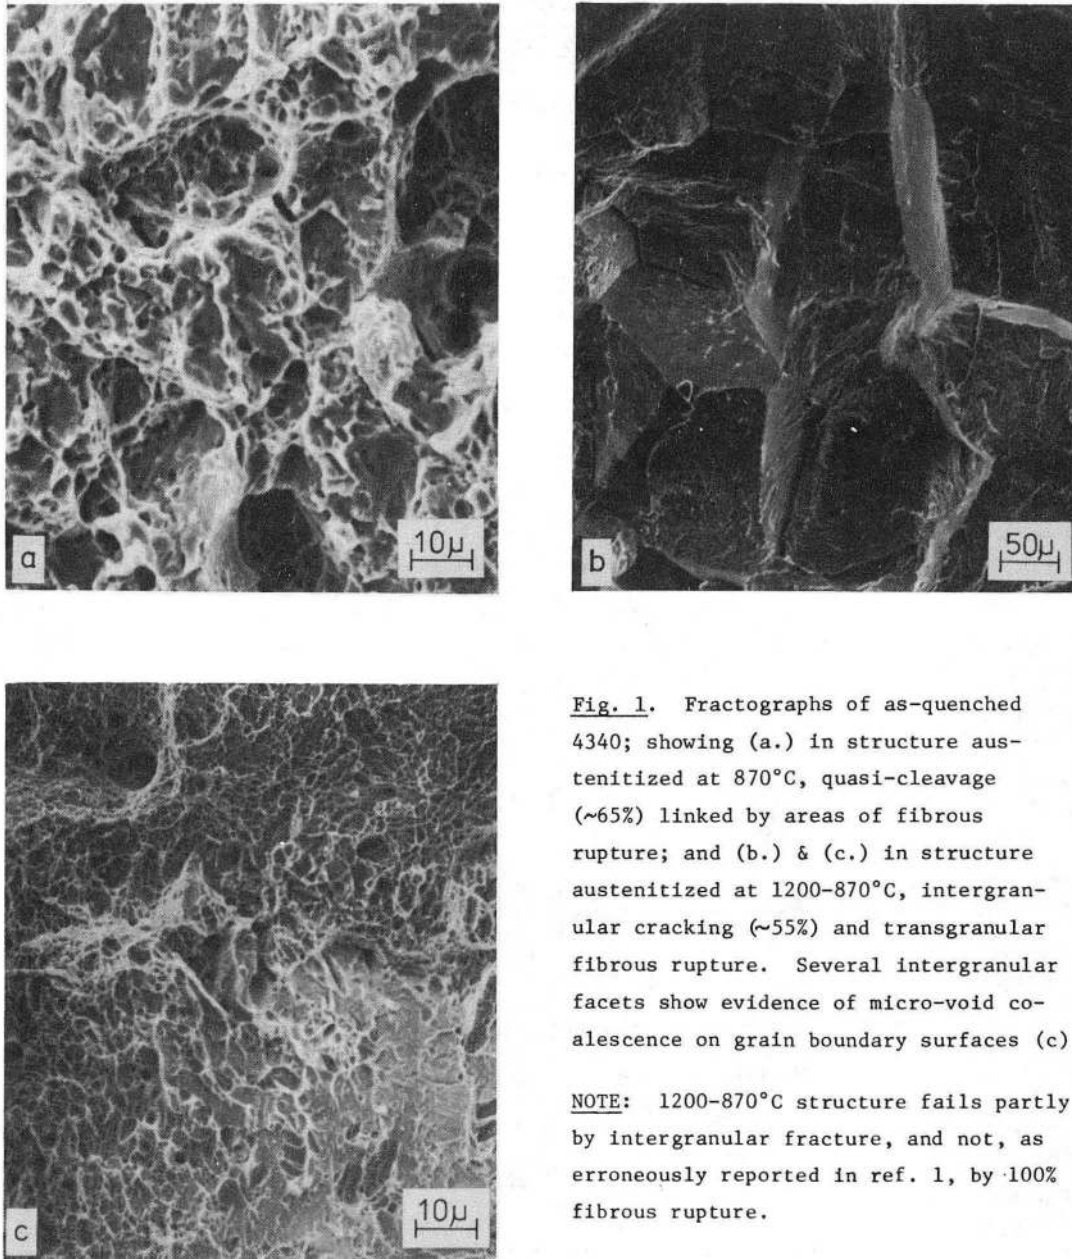


Fig. 1. Fractographs of as-quenched 4340; showing (a.) in structure austenitized at 870°C, quasi-cleavage (~65%) linked by areas of fibrous rupture; and (b.) & (c.) in structure austenitized at 1200-870°C, intergranular cracking (~55%) and transgranular fibrous rupture. Several intergranular facets show evidence of micro-void coalescence on grain boundary surfaces (c).

NOTE: 1200-870°C structure fails partly by intergranular fracture, and not, as erroneously reported in ref. 1, by 100% fibrous rupture.


XBB 758-6005

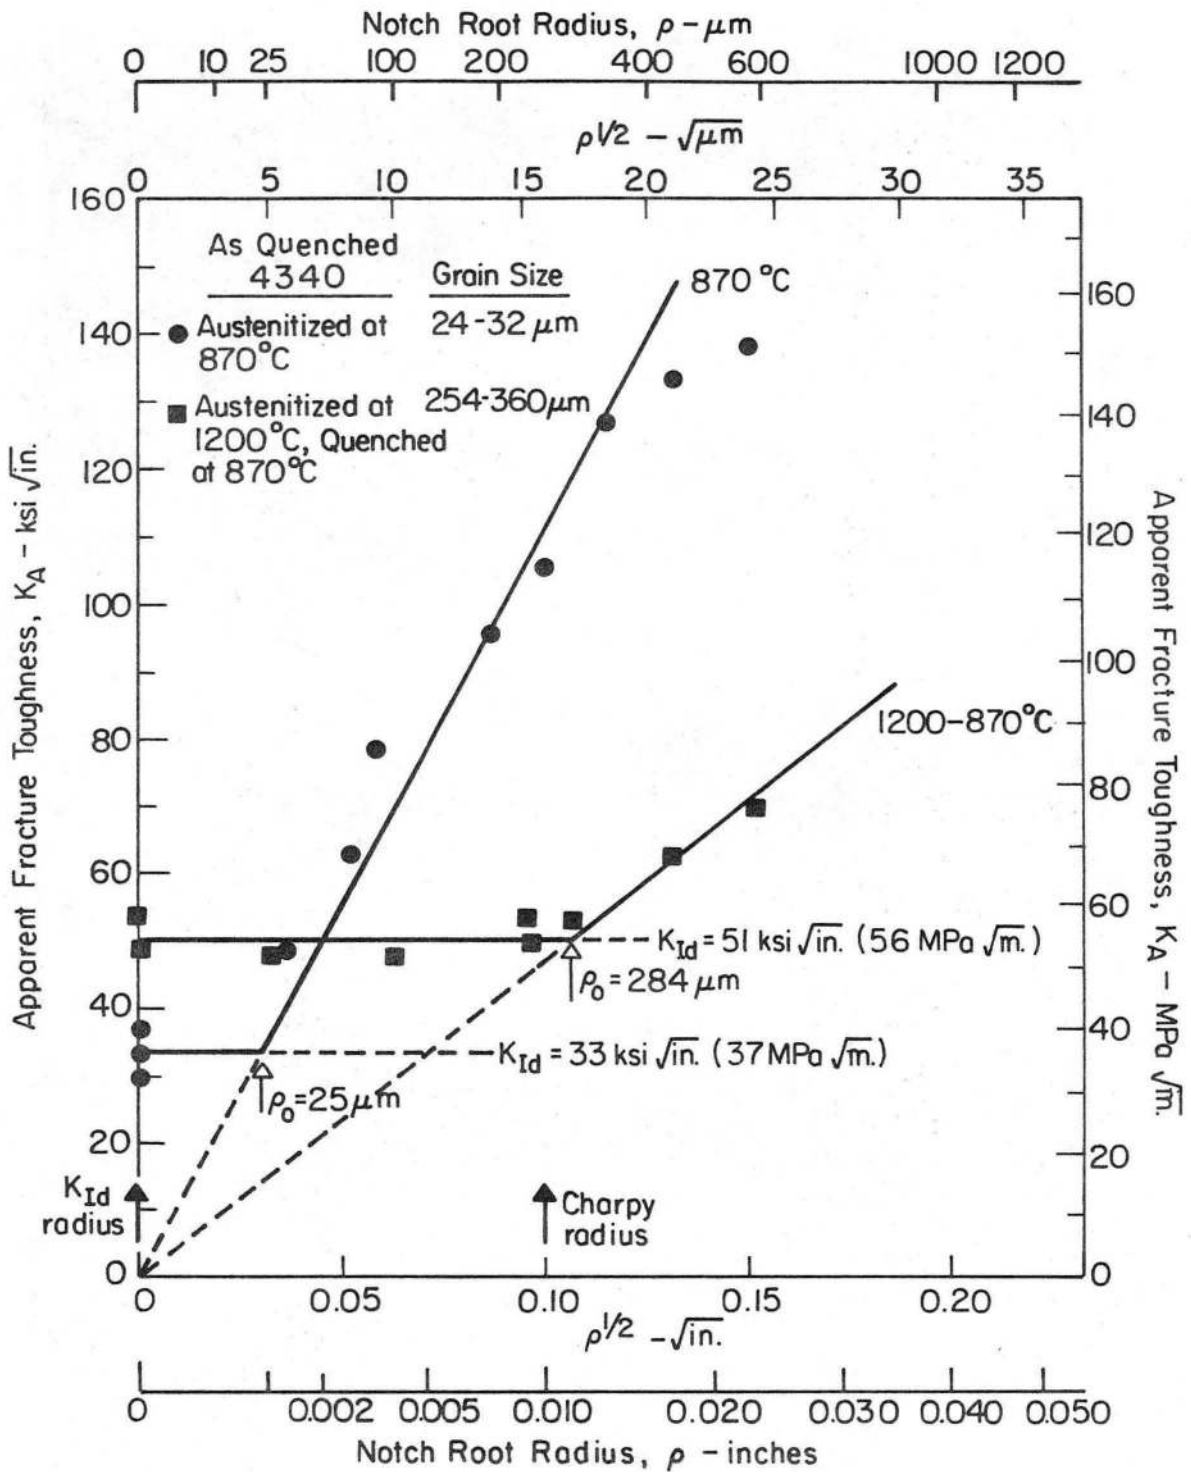


XBL 758-6995

Fig. 2. The relationship between toughness, measured by the apparent dynamic fracture toughness ( $K_A$ ) from instrumented Charpy tests, and notch root radius ( $\rho$ ) in oil quenched AISI 4340, for the 1200-870°C and 870°C structures.  $\rho_0$  is the "limiting" root radius,  $K_{Id}$  the dynamic fracture toughness.




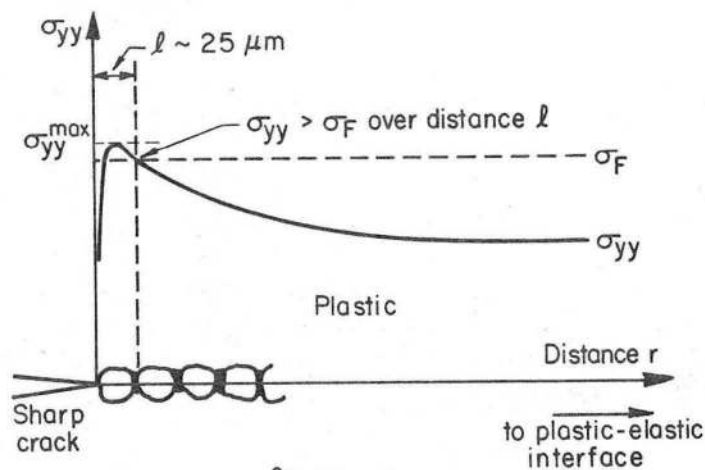


(a) 870°C Structure

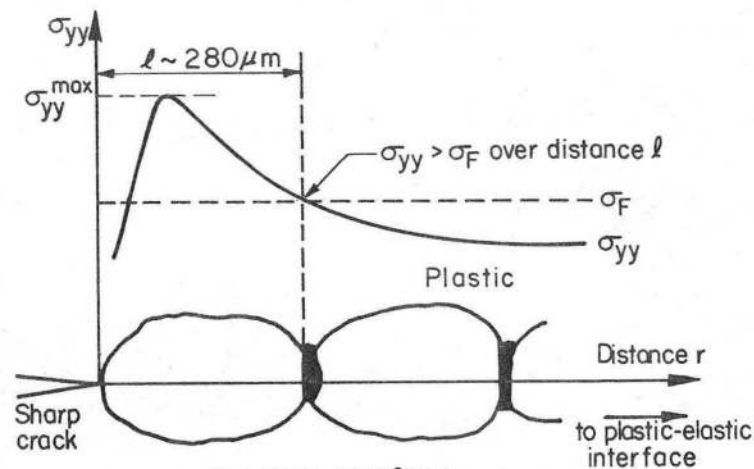

(b) 1200-870°C Structure

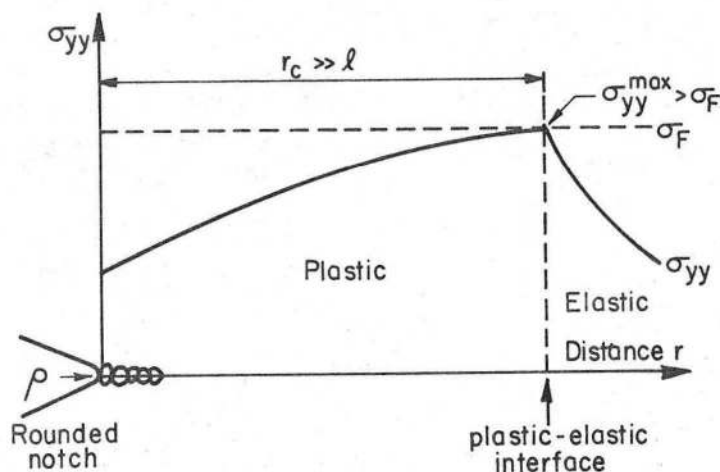

(c) 870°C Structure

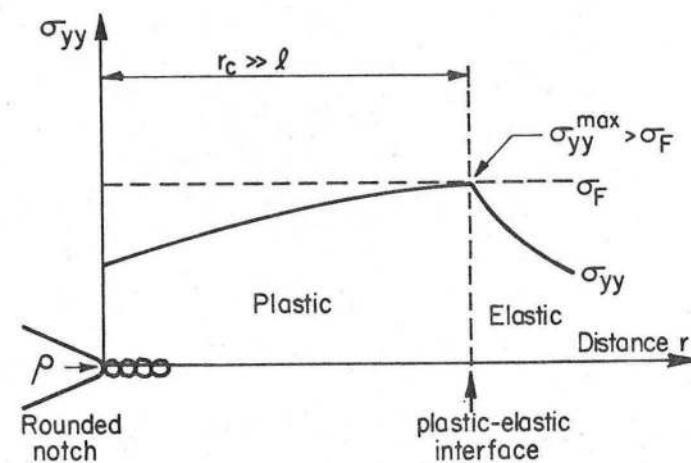

(d) 1200-870°C Structure

XBL758-6996

Fig. 3. Schematic representation of the distribution of tensile stress ( $\sigma_{yy}$ ) at distance ( $r$ ) ahead of stress concentrator at failure for (a) 870°C structure with sharp crack ( $\rho < \rho_o$ ), (b) 1200-870°C with sharp crack, (c) 870°C structure with rounded notch ( $\rho > \rho_o$ ), (d) 1200-870°C structure with rounded notch. Critical fracture event occurs when  $\sigma_{yy} > \sigma_F$  over characteristic distance ( $l$ ) ahead of sharp crack, or when  $\sigma_{yy}^{\max} \geq \sigma_F$  at the plastic-elastic interface ( $r_c \gg l$ ) ahead of rounded notch. Toughness of 1200-870°C structure is greater ahead of sharp crack because characteristic distance ( $l$ ) is larger, toughness of 870°C structure is greater ahead of rounded notch because fracture stress ( $\sigma_f$ ) is larger.

**LEGAL NOTICE**

*This report was prepared as an account of work sponsored by the United States Government. Neither the United States nor the United States Energy Research and Development Administration, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe privately owned rights.*

TECHNICAL INFORMATION DIVISION  
LAWRENCE BERKELEY LABORATORY  
UNIVERSITY OF CALIFORNIA  
BERKELEY, CALIFORNIA 94720