

Evidence for Activated Carrier Mobility in Organic Solids

STEADY state space charge limited currents (SCLC) were obtained at different temperatures for a series of dipyrindium model compounds (Fig. 1) into which one TCNQ molecule (tetracyanoquinodimethane), in the form of a radical ion, was introduced. Some compounds were produced containing two molecules of TCNQ, one associated with each ring. Polymers of these compounds were also produced and SCLC measured (details of preparation will be published elsewhere).

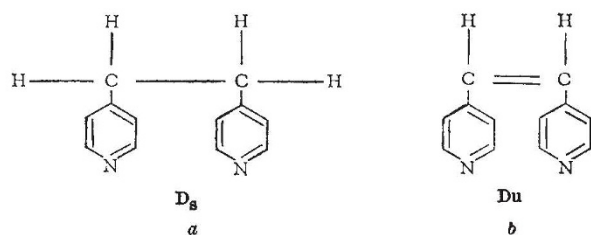


Fig. 1. Chemical structure of (a) 1,2-bis-(4-pyridyl)-ethane, D_s , and (b) 1,2-bis-(4-pyridyl)-ethylene, D_u .

The conductivity measurements were made on 0.5 inch diameter cylindrical pellets. Pellets prepared under pressures *in vacuo* between 20,000 and 100,000 pounds/inch had essentially identical conductivities. Electrical contact was made with vacuum-deposited gold electrodes or, in some cases, contacts were applied by covering the top and bottom surfaces with a thin layer of gold powder followed by recompression in the hydraulic press. Both processes resulted in firmly adherent, cohesive, contacts which were ohmic at voltages below those at which appreciable charge injection occurred. In one case only was it possible to carry out measurements on a single crystal; the resulting activation energy, 0.129 eV, was close to that obtained with the compactions, namely, 0.103 eV.

The concentrations of free carriers at thermal equilibrium, n_{co} , were obtained¹ from the transition voltage V_{tr} from ohmic to parabolic voltage dependence, evaluated graphically using the following equation

$$n_{co} = \frac{2\epsilon\epsilon_0 V_{tr}}{et^2} \quad (1)$$

where e is the charge of the electron, ϵ_0 the permittivity of free space, ϵ the relative permittivity and t is the inter-electrode spacing. With knowledge of the carrier concentration and the conductivity σ , the mobility may then be obtained from

$$\mu = \frac{\sigma}{en_{co}} \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1} \quad (2)$$

The results are summarized in Fig. 2. It is seen that the carrier concentration remains substantially constant, to within an order of magnitude, at about 10^{11} cm^{-3} , over a temperature range in which the resistivities, some of which are also shown, change by up to eight orders of magnitude. In view of the uncertainties involved in the graphical location of V_{tr} and the probable changes in the effective permittivity at low temperatures, the values of n_{co} are estimated to be accurate only to within a factor of five. The largest apparent change in n_{co} was found in the unsaturated D_u 1-TCNQ compound, which appeared to drop from 4.5×10^{11} at -187°C to 1.2×10^{10} at -78°C . In that temperature interval, the conductivity increased by five orders of magnitude.

The temperature dependence of the mobility deduced from SCLC data could be fitted to a shallow trap model², but this would require mobilities $\geq 40,000 \text{ cm}^2/\text{V s}$. Such values would be substantially larger than those shown in Fig. 2 or found from Hall mobility measurements (to be published elsewhere) and larger than those

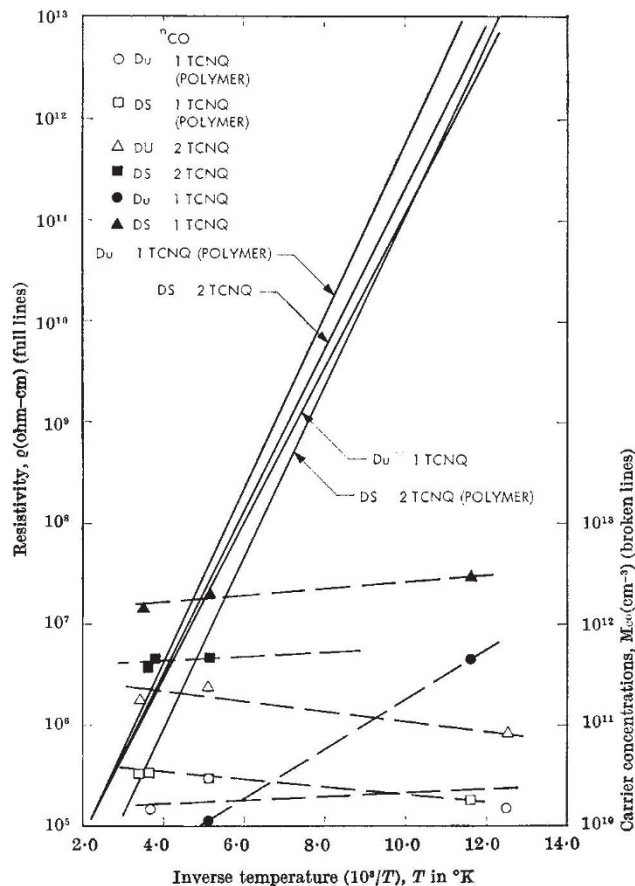


Fig. 2. Temperature dependence of resistivity, σ , and concentration of carriers, n_{co} .

found in most single crystal inorganic semiconductors. Mobilities as large as this are extremely unlikely in systems lacking long range order.

We are forced to the conclusion that the observed conductivity changes are caused by mobility changes. Such a thermally activated mobility in organic materials has been repeatedly proposed³, but to our knowledge this work presents the first evidence for its existence.

It is of interest that the carrier concentration values appear to be invariant—again to plus or minus an order of magnitude—with respect to saturation versus unsaturation, introduction of a second TCNQ molecule and polymerization. In fact, carrier concentrations of the order reported here have also been observed by other workers⁴.

This article presents the results of one phase of research carried out at the Jet Propulsion Laboratory, California Institute of Technology, sponsored by the US National Aeronautics and Space Administration.

F. GUTMANN
A. M. HERMANN
A. REMBAUM

Jet Propulsion Laboratory,
California Institute of Technology,
Pasadena, California.

Received November 29, 1968; revised January 28, 1969.

¹ Lampert, M. A., Rose, A., and Smith, R. W., *J. Phys. Chem. Solids*, **8**, 464 (1959).

² Rose, A., *Phys. Rev.*, **97**, 1538 (1955).

³ Frollich, H., and Sewell, G. L., *Proc. Phys. Soc.*, **74**, 643 (1959); Tredgold, R. H., *ibid.*, **80**, 807 (1962). Pohl, H. A., and Opp, D. A., *J. Phys. Chem.*, **66**, 2121 (1962). Hadek, V., and Ulbert, K., *Coll. Czech. Chem. Commun.*, **32**, 1118 (1967). Hermann, A. M., and Rembaum, A., *J. Polymer Sci., Part C, Polymer Symposia*, **17**, 120 (1967). Chery, R. J., *Quart. Rev.*, **22**, 162 (1968).

⁴ Gutmann, F., and Lyons, L. E., *Organic Semiconductors* (John Wiley and Sons, New York, 1967).