

SCIENTIFIC REPORTS

OPEN

Facile fabrication of one-dimensional Te/Cu₂Te nanorod composites with improved thermoelectric power factor and low thermal conductivity

Dabin Park, Hyun Ju, Taeseob Oh & Jooheon Kim

In this study, Te/Cu₂Te nanorod composites were synthesized using various properties of Cu₂Te, and their thermoelectric properties were investigated. The nanorods were synthesized through a solution phase mixing process, using polyvinylpyrrolidone (PVP). With increasing Cu₂Te content, the composites exhibited a reduced Seebeck coefficient and enhanced electrical conductivity. These characteristic changes were due to the high electrical conductivity and low Seebeck coefficient of Cu₂Te. The composite containing 30 wt.% of Cu₂Te nanorods showed the maximum power factor (524.6 μV/K at room temperature). The two types of nanorods were assembled into a 1D nanostructure, and with this structure, thermal conductivity decreased owing to the strong phonon scattering effect. This nanorod composite had a dramatically improved *ZT* value of 0.3, which was ~545 times larger than that of pristine Te nanorods.

The global energy crisis and environmental problems caused by burning fossil fuels have drawn much attention to alternative energy sources. Thermoelectric (TE) energy conversion is highly attractive as a promising energy-harvesting strategy because it can be used to, directly generate electrical energy from temperature gradients^{1–3}. The dimensionless figure of merit (*ZT*) is used to evaluate the performance of TE materials; a large *ZT* is required to achieve a high energy conversion efficiency. *ZT* can be expressed as shown in Equation 1.

$$ZT = S^2\sigma T/\kappa \quad (1)$$

In Equation 1, *S* is the Seebeck coefficient, σ is the electrical conductivity, κ is the total thermal conductivity, and *T* is the absolute temperature. The thermoelectric performance of a material can be enhanced by two simple strategies: reducing its thermal conductivity, or enhancing its power factor ($PF = S^2\sigma$), which can be accomplished by decoupling the relationship between *S* and σ .

An outstanding Seebeck coefficient is one of the most important prerequisites for obtaining a large power factor. The *S* value of a material is generally considered inversely proportional to its η (carrier concentration), as shown in the following relatively simple model of electron transport (Equation 2).

$$S = \frac{8 \cdot \pi^2 \cdot k_B^2}{3 \cdot e \cdot h^2} \cdot m^* \cdot T \cdot \left(\frac{\pi}{3 \cdot \eta} \right)^{\frac{2}{3}} \quad (2)$$

In Equation 2, *h* is the Planck constant, *k_B* is the Boltzmann constant, and *m** equals 0.58 *m_e*, where *m_e* is the electron resting mass. From this equation, it can be seen that the *S* value increases as η decreases. In recent studies, inorganic materials have mainly been used as thermoelectric devices, due to their high Seebeck coefficients, which are caused by their crystalline structures. In recent years, Te and its alloys have shown great potential as efficient thermoelectric materials, because of their unique characteristics^{4–6}. Te exhibits excellent thermoelectric performance, and has an extremely high Seebeck coefficient. (~400 μV/K at 300 K)⁷, which is higher than that

School of Chemical Engineering & Materials Science, Chung-Ang University, Seoul, 06974, Republic of Korea. Correspondence and requests for materials should be addressed to J.K. (email: jooheonkim@cau.ac.kr)

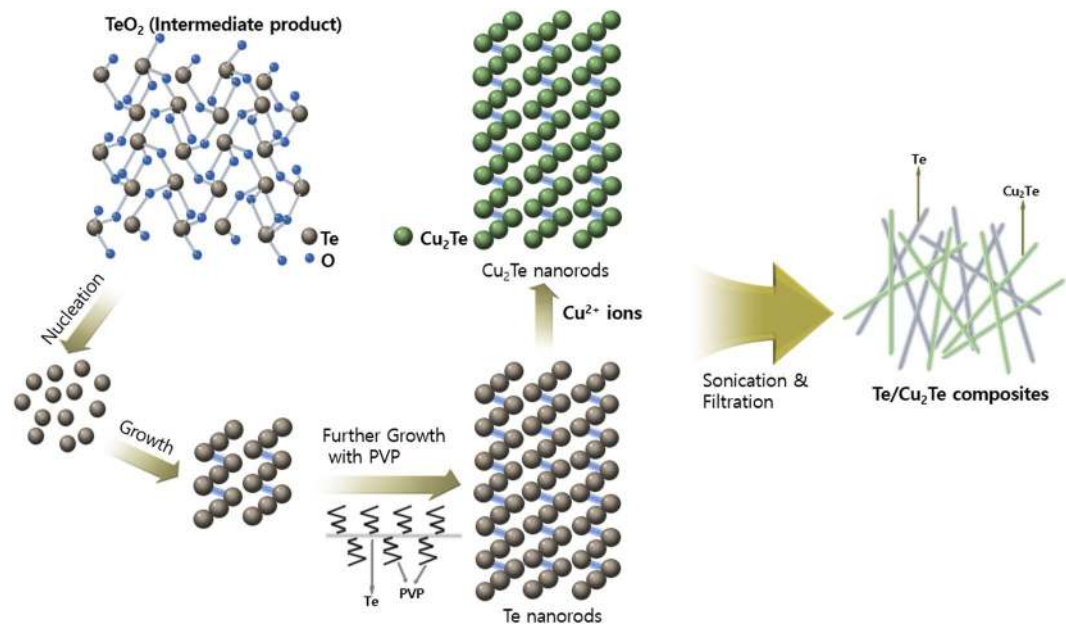


Figure 1. Schematic illustration of the fabrication of Te/Cu₂Te nanorod composite.

of Te alloys such as Bi₂Te₃ (~170 μV/K)⁸, PbTe (~200 μV/K)⁹, Sb₂Te₃ (~160 μV/K)¹⁰, or Ag₂Te (~90 μV/K)¹¹. Despite this advantage, Te is not a perfect high power factor material, due to its electrical conductivity (~12 S/m at 300 K)¹², which is lower than that of other Te alloys.

To solve this problem, some researchers have focused on improving the electrical conductivity of Te-based thermoelectric devices^{13–16}. Preparing composites of Te with other similar materials is a simple way to improve its thermoelectric properties. One example is the polymer-Te hybrid composite of PANI and Te nanorods, which are reported to have a high *ZT* value of 0.23 at 383 K¹⁷. Zhang *et al.*¹⁸ prepared Bi₂Te₃-Te heterophase nanoparticles, which also achieved an enhanced power factor.

Among the various Te alloys, copper (I) telluride (Cu₂Te) has shown relatively high electrical conductivity (~40,000 S/m at 300 K)¹⁹ when compared with other Te alloys - Ag₂Te (~20,000 S/m at 300 K)²⁰, Bi₂Te₃ (~22,000 S/m at 300 K)²¹, and pure Te - and was also reported to have an outstanding Seebeck coefficient. Additionally, reports of thermoelectric materials containing Cu₂Te have been published in recent years, and so Cu₂Te is considered to be an appropriate material for increasing the power factor of Te.


Low thermal conductivity is another important factor in achieving a high *ZT*. One-dimensional (1D) nanostructures have many unique physical and chemical properties, and are highly promising materials for various applications^{22,23}. 1D nanostructures can reduce thermal conductivity by increasing phonon scattering. Materials with 1D nanostructure generate many phonon scattering sites, and scatter phonons more efficiently than bulk materials^{24,25}, a phenomenon that reduces total thermal conductivity as a consequence. Nanostructured, Te-based thermoelectric materials, with lower thermal conductivity than the corresponding bulk counterparts, were discussed in our previous papers^{26,27}. In addition, Alam *et al.* reported an enhancement of *ZT* by reducing the thermal conductivity on the basis of the nanostructure of the material²⁸. Yang *et al.*²⁹ obtained significantly reduced thermal conductivity using nanostructured Bi₂Te₃.

In this study, Te/Cu₂Te nanorod composites made from Te and Cu₂Te nanorods were fabricated to achieve improved thermoelectric properties. The Te nanorods were prepared using a polyvinylpyrrolidone (PVP)-assisted, solution-phase synthetic process, from a Te precursor solution. The role of PVP in this study was to restrict the growth direction to one dimension, and to control the growth rate. Cu₂Te nanorods were synthesized from the fabricated Te nanorods by solution phase mixing. After the fabrication of both types of nanorods, the composites were fabricated via ultrasonication. The homogeneous dispersion of the two types of nanorods affected the intrinsic conduction of the composites and was thought to potentially enhance their thermoelectric properties.

On this basis, the thermoelectric properties of the Te/Cu₂Te nanorod composite samples, with varied Cu₂Te content, were investigated, and our hypothesis was that the combination of these two nanorods would affect each other and enhance their thermoelectric properties.

Results and Discussion

Figure 1 shows the overall synthesis of the Te/Cu₂Te nanorod composites. Both the Te and Cu₂Te nanorods were prepared using a PVP-assisted, solution-phase mixing process. In the first stage of the Te nanorod synthesis, TeO₂ was mixed with PVP and NaOH in ethylene glycol (EG). After the temperature was raised to 120 °C, N₂H₄·H₂O was injected into the solution. The reaction process during the Te synthesis steps is shown in Equations 3–5.




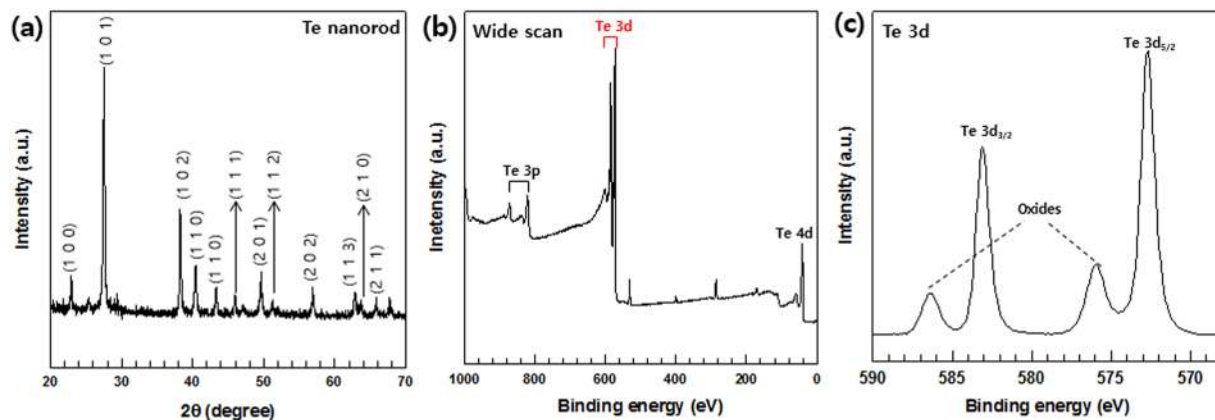


Figure 2. (a) XRD patterns, and (b,c) XPS spectra of Te nanorods: (b) Wide XPS scan for Te, (c) Te 3d spectrum.



The reaction process can be divided into two stages. First, tellurium dioxide reacts with NaOH to form TeO_3^{2-} (Equation 3). Then, the generated TeO_3^{2-} , and two Na^+ ions produce Na_2TeO_3 . (Equation 2). Subsequently, hydrazine monohydrate reduces the Na_2TeO_3 to elemental Te (Equation 3). During this stage, the nucleation of Te^{2-} ions occurs, the elemental Te is formed with reduction of the Te^{2-} ions, and a solid crystal nucleus is formed. The growth of the Te crystal nuclei into Te nanorods was accelerated by reduction, and the concentration of Te^{2-} ions in the solution was decreased.

PVP, used as the surfactant, played an important role in the Te nanorod synthesis. It has been reported that linear polymers can react with inorganic ions to form chain-shaped intermediates^{30,31}. In this study, PVP served as a directing template for the fabrication of the 1D nanostructure. In other words, PVP controlled the growth rate, and maintained the 1D growth direction, of the nanorods.

The Cu_2Te nanorods used in this study were fabricated from the synthesized Te nanorods. The Cu precursor ($\text{Cu}(\text{NO}_3)_2$) was reacted with the Te nanorods to generate Cu_2Te nanorods. The transformation of Te nanorods into Cu_2Te nanorods involved the following reactions: First, the Cu^{2+} ions released by $\text{Cu}(\text{NO}_3)_2$ are absorbed on the surface of the Te nanorods. After ascorbic acid (a weak reducing agent) is injected into the mixture with the Te and Cu^{2+} ions, the Cu^{2+} ions are reduced to Cu^+ . Second, the reduced Cu^+ ions induce an imbalanced response at the surface of the Te nanorods, by which $\text{Te} \rightarrow \text{Te}^{4+} + \text{Te}^{2-}$. Finally, the Cu^+ ions react with Te^{2-} , and Cu_2Te nanorods are formed.

XRD patterns of the two types of nanorods were measured to confirm their synthesis. The XRD patterns of the Te and Cu_2Te nanorods are shown in Figs 2a and 3a, respectively. This pattern indicated the hexagonal crystalline phase of the Te product and was in good agreement with the literature values (JCPDS no. 13-1452). In Fig. 3a, all diffraction peaks in the XRD pattern can be indexed to the hexagonal Cu_2Te phase and are consistent with those reported in the literature (JCPDS no. 10-0421). No other peaks were observed in either of the two patterns, indicating the successful fabrication of pristine Te and Cu_2Te nanorods.

The synthesis of the Te and Cu_2Te nanorods was further confirmed using XPS analysis. The resulting XPS survey spectra for the prepared Te and Cu_2Te nanorods are illustrated in Figs 2 and 3. A high-resolution spectrum of the Te 3d region (Fig. 2c) shows two peaks at approximately 572.5 and 582.9 eV: these two peaks correspond to the Te 3d_{5/2} and Te 3d_{3/2} binding energies of Te. Two relatively small peaks can be seen at 576.1 and 586.4 eV, which can be assigned as the Te(IV) 3d binding energy, indicating the oxidation of Te. These peaks are observed because the surface of Te nanorods is easily oxidized in air.

Nanostructured materials are more easily oxidized in air, as has been reported in previous studies³². The XPS data of the Cu_2Te nanorods are shown in Fig. 3b–d, in which the Cu 2p and Te 3d peaks are observed. The high-resolution spectra of the Te 3d and Cu 2p regions are shown in Fig. 3c,d, respectively. In the Cu 2p region, two peaks at 932.2 and 952.4 eV are observed, which correspond to Cu 2p_{3/2} and Cu 2p_{1/2}, and the two peaks located at 589.2 eV and 572.5 eV in Fig. 3d correspond to the Te 3d_{3/2} and 3d_{5/2} binding energies. The Cu_2Te nanorods are nanostructured materials, and thus are also easily oxidized in air. As a result, the oxidation peaks of Cu and Te are observed in Fig. 3c,d, respectively.

To confirm the 1D nanostructure, crystallinity, and the morphology of the synthesized nanorods, FE-SEM and EDS analyses were carried out. Low and high-resolution FE-SEM images of the fabricated Te nanorods are shown in Fig. 4a,b and demonstrate the existence of a large number of randomly dispersed wire-like structures. The obtained products consisted mainly of cylindrically shaped rods of a relatively uniform size. Each Te nanorod was ~15 nm in length, and ~600 nm in diameter. The images at Fig. 4c,d shows the presence of Cu_2Te nanorods, confirming the successful synthesis of Cu_2Te . These results were further verified using EDS mapping, Figs 5 and 6

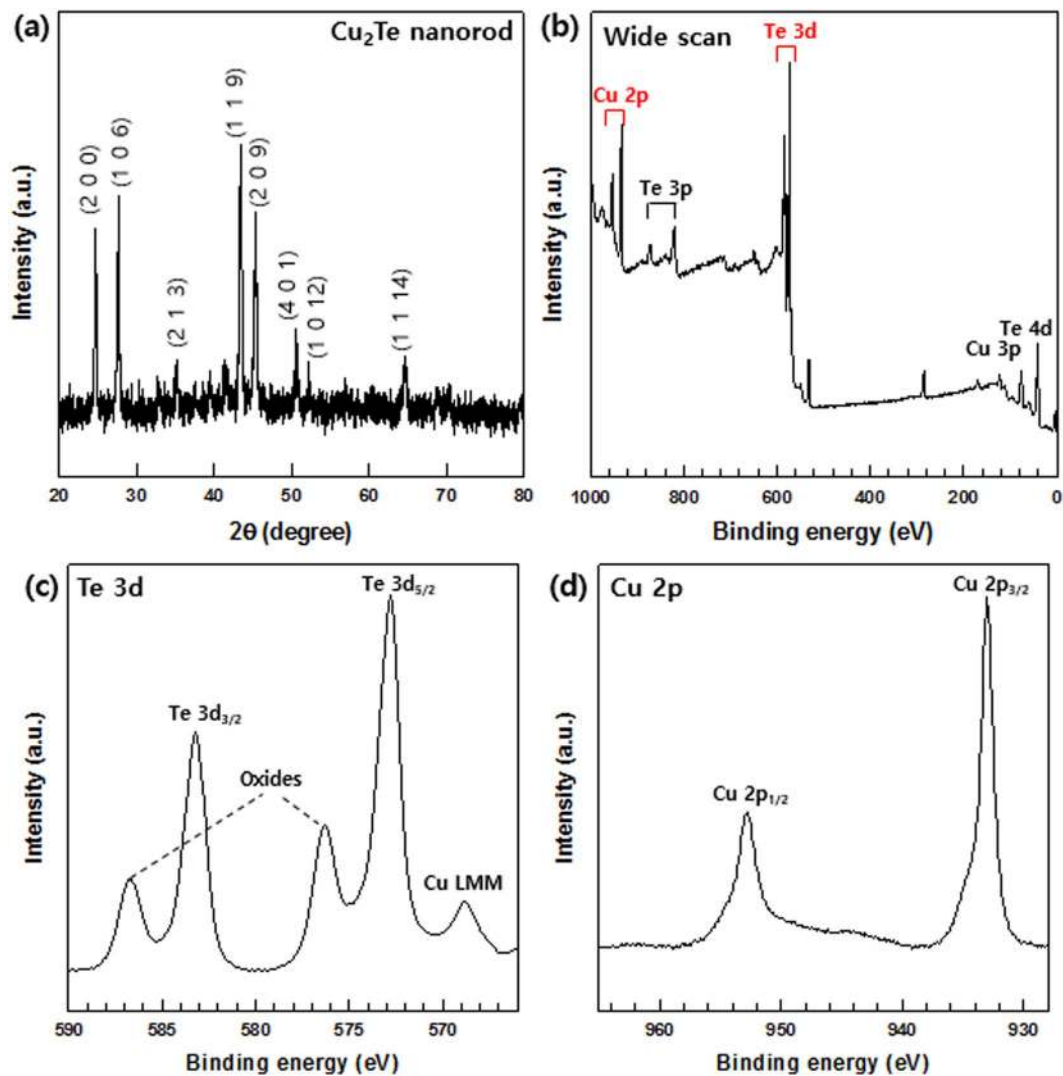


Figure 3. (a) XRD patterns, and (b–d) XPS spectra of Cu_2Te nanorods: (b) Wide XPS scan for Cu_2Te , (c) Te 3d spectrum, (d) Cu 2p spectrum.

illustrates the EDS atomic mapping of the Te and Cu_2Te nanorods, respectively. The EDS spectrum collected in the specific region highlighted in Fig. 6b,c indicates the presence of Cu and Te.

To verify the successful synthesis of the Te/ Cu_2Te composites, XRD analysis was performed on the composites with various Cu_2Te content. The XRD patterns of the Te/ Cu_2Te composites with different Cu_2Te content (10, 30, and 50 wt.%) are shown in Fig. 7. The profiles of the composites with low Cu_2Te content were similar to the XRD peaks of the Te. In contrast, as the Cu_2Te content increased, the peaks corresponding to Cu_2Te became more intense. The XRD peaks allowed confirmation that there was good dispersion of Te and Cu_2Te in the composite samples.

Before measurement of their TE characteristics, the Te/ Cu_2Te nanorod composite samples were compressed into disks with a diameter of 12.7 mm. Pristine Te and Cu_2Te nanorod disks were also fabricated, all the composite samples were hot-pressed, and then the FE-SEM and EDS analyses were carried out – with the resultant images shown in Figs S1–3.

The Seebeck coefficient S was measured for the composite samples with varied Cu_2Te content (10, 30, and 50 wt.%) at room temperature. The Seebeck coefficients were determined from the linear relationship between the temperature difference (ΔT), and electromotive force (ΔV). The measured S values of the composite samples are shown in Fig. 8, which also shows the S values of the pristine Te and Cu_2Te nanorods. The S values of the two pure nanorods were found to be $404 \mu\text{V/K}$ and $25 \mu\text{V/K}$, which were similar to those in previous reports^{7,19}. The Seebeck coefficients of the composite samples showed a decreasing trend with increasing Cu_2Te contents, which was due to the difference in the S values of Te and Cu_2Te nanorods. Additionally, the S values of the Te nanorods, Cu_2Te nanorods, and Te/ Cu_2Te nanorod composites were all positive, which indicated that Te and Cu_2Te exhibited p-type semiconductor behavior.

The electrical conductivity of the Te/ Cu_2Te nanorod composite samples with various Cu_2Te contents (10, 30, and 50 wt.%) are shown in Fig. 8. The electrical conductivity of the two pristine Te and Cu_2Te nanorod samples

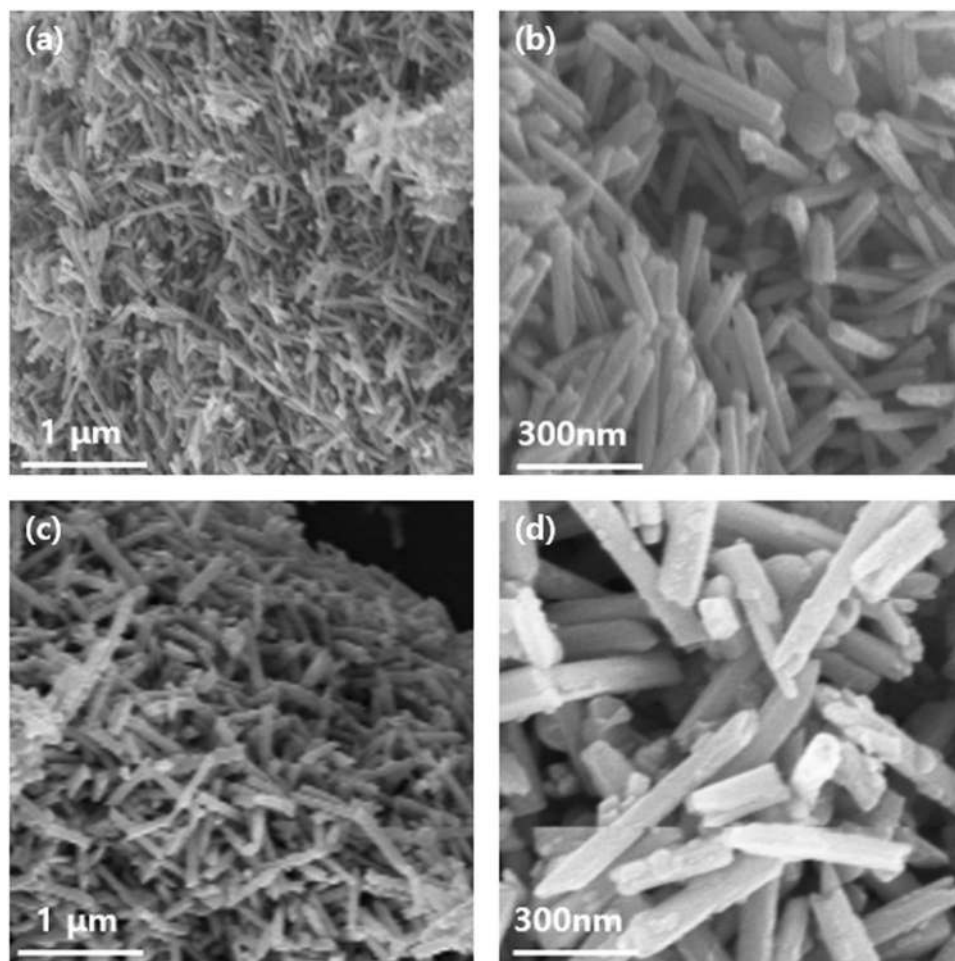


Figure 4. (a) Low and (b) high-magnification FE-SEM images of Te nanorods, (c) low and (d) high-magnification FE-SEM image of Cu_2Te nanorods.

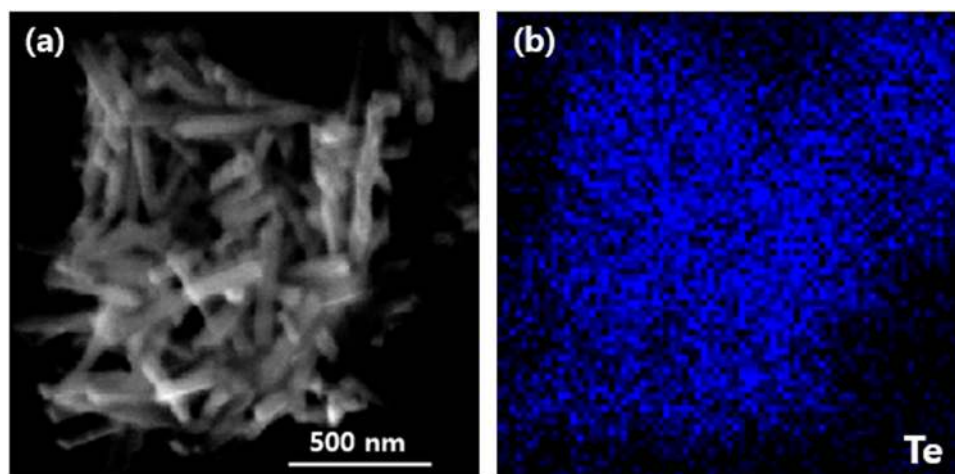


Figure 5. Particle surface morphology and atomic mapping of Te nanorods.

were found to be 0.22 S/cm and 454 S/cm, and these values were similar to those in previous reports that analyzed the thermoelectric properties of Te and Cu_2Te ^{7,19}. Compared to Te, Cu_2Te has a much higher electrical conductivity. In contrast to the Seebeck coefficient, as the contents of Cu_2Te increased, the electrical conductivity of the composite samples also increased. This tendency was due to the difference in electrical conductivity between the two materials.

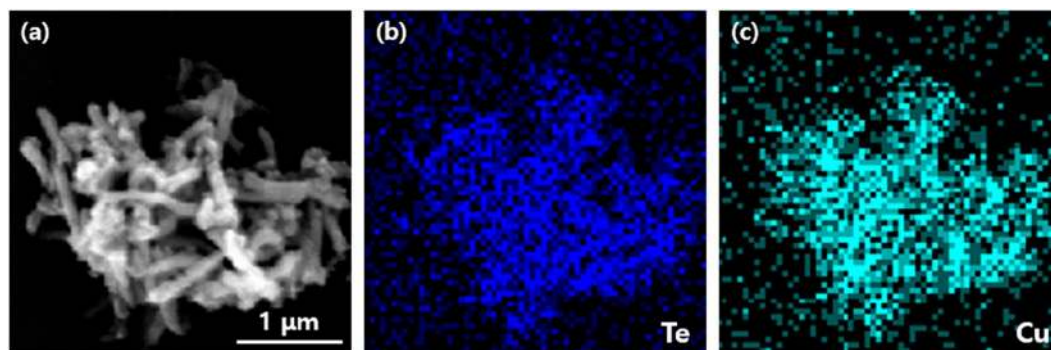


Figure 6. Particle surface morphology and atomic mapping of Cu_2Te nanorods.

The thermoelectric power factors of the $\text{Te}/\text{Cu}_2\text{Te}$ nanorod composites were analyzed, and are shown in Fig. 9. The composite containing 30 wt.% Cu_2Te nanorods showed the highest power factor ($524.6 \mu\text{W}/\text{mK}^2$), which was ~ 145.7 times larger than the PF of the pristine Te nanorods. However, for the Cu_2Te nanorods with content above 30 wt.%, the power factor showed as decreasing trend, and these changes in the power factors of the samples can be attributed to the reduction of the Seebeck coefficient, and the enhancement of the electrical conductivity.

Figure 10 shows the total thermal conductivity of the composites with different Cu_2Te nanorod content. The total thermal conductivity (κ) of composite materials is composed of a lattice contribution (κ_l) from phonons, and an electronic contribution (κ_e) from the charge carriers ($\kappa = \kappa_l + \kappa_e$). The electronic contribution, κ_e can be estimated from the Wiedemann-Franz law ($\kappa_e = L \cdot \sigma \cdot T$), where L is the Lorentz number ($L = 2.45 \times 10^{-8} \text{ W}\Omega/\text{K}^2$)^{33–36}. The total thermal conductivity was mainly dependent on the lattice term, κ_l , due to the relatively small contribution of the electronic term. Therefore, lattice phonon scattering was the key factor that determined the κ value of the composites. The charge carrier concentration and carrier mobility values of $\text{Te}/\text{Cu}_2\text{Te}$ composites with different amount of Cu_2Te are shown in Fig. S4 listed in Table S2.

The κ values of the pristine Te and Cu_2Te nanorods (1.94 and 0.67 $\text{W}/\text{m}\cdot\text{K}$) are also shown in Fig. 10. Specific thermal conductivity parameters for $\text{Te}/\text{Cu}_2\text{Te}$ nanorod composites, and for the two pristine nanorods, are listed in Table S1. These thermal conductivities were relatively lower than those of the corresponding bulk counterparts reported in a previous study^{7,19}. This difference between the κ values of the bulk and nanorod materials resulted from the decrease in κ_l , owing to phonon scattering. One-dimensional nanostructures increased phonon scattering, therefore reducing the contribution from κ_l . Hence, 1D nanomaterials have lower thermal conductivity than their corresponding bulk counterparts, and for this reason, the Te and Cu_2Te nanorod samples showed lower thermal conductivity than their bulk counterparts. Similar results have been reported in previous studies²⁶. The $\text{Te}/\text{Cu}_2\text{Te}$ nanorod composites showed lower κ values than the pristine samples.

The findings in this study showed that the incorporation of two nanorod matrices led to the formation of $\text{Te}/\text{Cu}_2\text{Te}$ nanorod interfaces, which created effective phonon-scattering centers. Due to this, the κ_l values of the composites were lower than those of the Te and Cu_2Te nanorods.

The value of ZT was determined for the composites, as shown in Fig. 11. The ZT values of the $\text{Te}/\text{Cu}_2\text{Te}$ nanorod composites were higher than those of the two pure nanorods due to their enhanced power factors and reduced κ . The maximum ZT of 0.30 was observed for the 30 wt.% composite sample, which was ~ 545 times larger than that of the pure Te nanorods.

The $\text{Te}/\text{Cu}_2\text{Te}$ composites reported in this study showed improved thermoelectric characteristics. The combination of the high electrical conductivity of Cu_2Te , and the high Seebeck coefficient of Te , was able to enhance the power factor of their composite materials. Additionally, the reduction of thermal conductivity due to the high level of phonon scattering of the nanostructure contributed to the achievement of a high ZT value. The present study has shown the synergetic effects of Te and Cu_2Te materials and highlights the enhanced thermoelectric properties of $\text{Te}/\text{Cu}_2\text{Te}$ composites.

Conclusion

$\text{Te}/\text{Cu}_2\text{Te}$ nanorod composites with various Cu_2Te contents were successfully fabricated, using a facile wet chemical synthesis and sintering process, and their thermoelectric properties were investigated. During the nanorod synthesis, PVP played an important role in forming the wire-like structure, by reacting with inorganic ions to form chain-shaped intermediates, causing the growth of a one-dimensional nanostructure. The two nanorods were uniformly distributed by ultrasonication and vacuum filtering, providing a well-dispersed solution. XRD, XPS, FE-SEM, and EDS analyses were carried out to confirm the morphology and nanostructure of the nanorod samples.

The main goal of this study was to enhance the electrical conductivity of the Te nanorods. The electrical conductivity of the composite samples showed an increasing trend with increasing Cu_2Te content, due to the high electrical conductivity of Cu_2Te . The Seebeck coefficient showed the opposite trend, as a result of the relatively low Seebeck coefficient of Cu_2Te . As a result, the maximum power factor of the composite sample ($524.6 \mu\text{W}/\text{m}\cdot\text{K}^2$ at 300 K) was observed for the 30 wt.% Cu_2Te nanorods. This value is ~ 145.7 times that of the pristine Te nanorods. The composite samples also showed reduced thermal conductivity, due to lattice phonon scattering. The rod-like, 1D nanostructure increased phonon scattering, resulting in decreased lattice thermal conductivity,

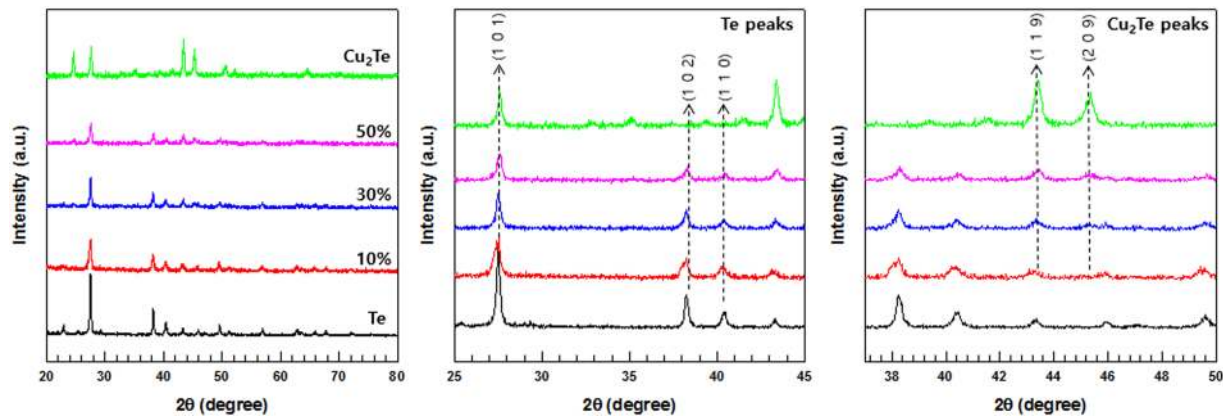


Figure 7. XRD pattern of Te/Cu₂Te nanorod composites with different Cu₂Te nanorod contents.

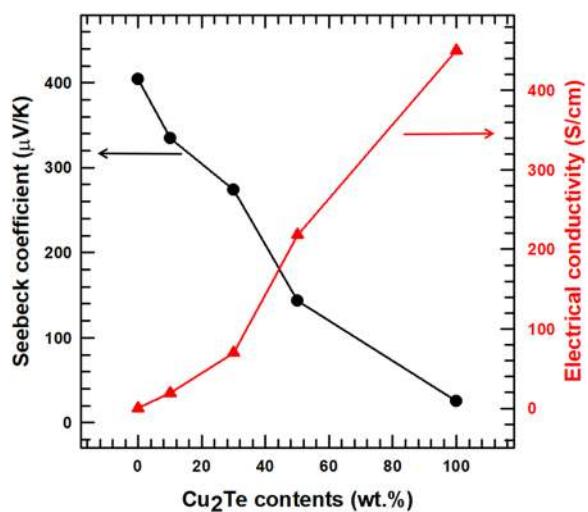


Figure 8. Seebeck coefficient and electrical conductivity of the Te/Cu₂Te nanorod composite with different Cu₂Te nanorod content.

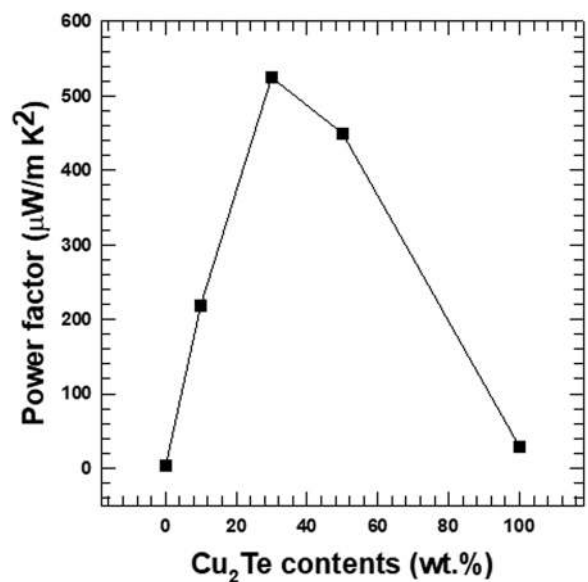


Figure 9. Power factor of the Te/Cu₂Te nanorod composites with different Cu₂Te nanorod content.

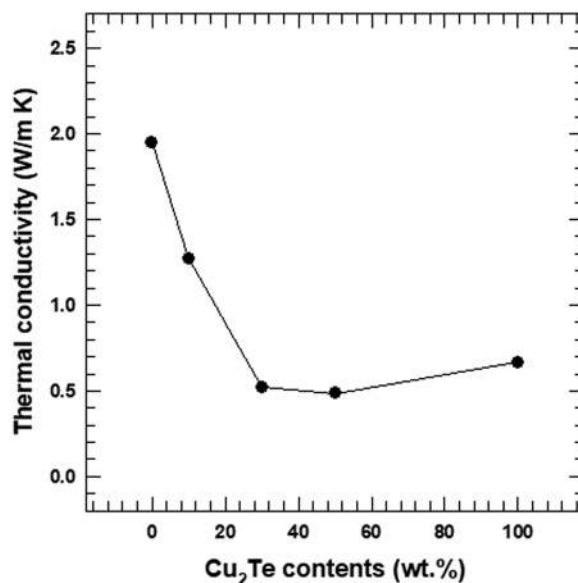


Figure 10. Total thermal conductivity of the Te/Cu₂Te nanorod composites with different Cu₂Te nanorod content.

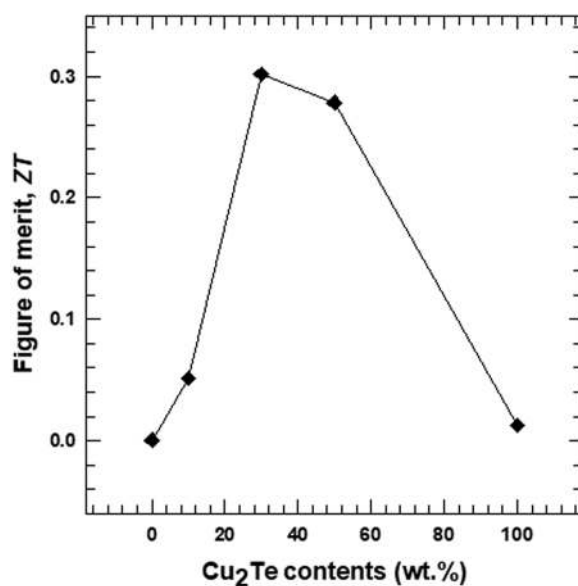


Figure 11. Figure of merit (ZT) of the Te/Cu₂Te nanorod composite with different Cu₂Te nanorod content.

and total thermal conductivity. The highest thermoelectric figure of merit (ZT) was obtained for the 30 wt.% composite sample, and this value was ~545 times that of the pristine Te nanorods. Thus, this study has highlights the synergetic effect of the two nanorods on the thermoelectric properties of the composite.

Experimental

Materials. Tellurium (IV) dioxide (TeO₂, 99%), copper (II) nitrate trihydrate (Cu(NO₃)₂·3H₂O, 99%), L (+)-ascorbic acid (C₆H₈O₆, 99%), hydrazine monohydrate (N₂H₄·H₂O, 80%), and ethylene glycol (EG, C₂H₆O₂, 99.5%) were purchased from Daejung Chemicals & Metals Co (Seoul, Korea). Sodium hydroxide (NaOH, 98%), and PVP, [molecular weight (MW) = ~40,000] were purchased from Sigma Aldrich (St. Louis, USA).

Synthesis of Te nanorods. First, 2.88 g of TeO₂ (MW = 159.6), 3.6 g of NaOH (MW = 40), and 1.2 g of PVP were mixed with 120 mL of EG, in the presence of magnetic stirring. Then the solution was heated to 120 °C, after which, 7.35 mL of N₂H₄·H₂O was injected into the mixture. At first, the color of the mixture turned white, which indicated the presence of tellurium dioxide colloids, and then gradually turned dark gray, after the addition of

$\text{N}_2\text{H}_2\cdot\text{H}_2\text{O}$. The solution was allowed to react at 120°C for 90 min. The as-synthesized Te solution was then poured into 10 vol.% $\text{N}_2\text{H}_2\cdot\text{H}_2\text{O}$ in de-ionized (DI) water and stirred. Next, it was centrifuged, with the addition of volumetric water, and vacuum-filtered, and the resulting solution was then dried in a vacuum oven, for 24 h at 60°C .

Synthesis of Cu_2Te nanorods. The Cu_2Te nanorods were synthesized with as-prepared Te nanorods. For this, 1.53 g of the synthesized Te nanorods was dispersed in 60 mL EG. In a separate glass vial, 2.899 g of $\text{Cu}(\text{NO}_3)_2\cdot 3\text{H}_2\text{O}$ was dissolved in 20 mL EG. The copper precursor solution was then added to the Te nanorod solution, and the mixture was heated to 90°C , at which point, 12 mL of 1.89 M (+)-ascorbic acid aqueous solution was injected, to initiate the reaction. The reaction proceeded for two hours under stirring, after which, the solution was washed with DI water, and dried in a vacuum oven.

Fabrication of Te/ Cu_2Te nanorod composite. The Te/ Cu_2Te nanorod composites were fabricated by ultrasonication of the Te and Cu_2Te nanorods. Nanorod solutions containing various amounts of Cu_2Te nanorods (10, 30, and 50 wt.%) were poured into ethanol, and the mixtures were then subjected to ultrasonication for 10 min. The resulting products were washed and filtered, then dried in vacuum oven at 60°C for 24 h. The resulting composites were ground into a fine powder, and then loaded into a Fe mold and pressed at 200°C under a pressure of 50 MPa, for 5 min.

Sample characterization. X-ray photoelectron spectroscopy (XPS, VG-Microtech, ESCA2000) and X-ray diffraction (XRD) (New D8-Advance/Bruker-AXS) at 40 mA and 40 kV using a $\text{Cu K}\alpha$ radiation (0.154056 nm) source and a scan rate of $1^\circ/\text{s}$ in the 2θ range of 5 to 70° were employed to characterize the crystal structure of the materials. Field-emission scanning microscopy (FE-SEM, SIGMA) was used to determine the morphology and microstructure of the materials. Elemental maps of the sample were analyzed using energy-dispersive X-ray diffraction (EDS, NORAN system 7, Thermo Scientific).

The Seebeck coefficient, S , was then calculated as the ratio between ΔV and ΔT , given as $S = \Delta V/\Delta T$. The value was calculated from the slope of the line representing the linear relationship between the thermal electromotive force (ΔV), and the temperature difference (ΔT), between the two end points of the composite pellets. A four-point probe with a source meter (Keithley 2400) was used to measure the electrical conductivity, and a digital micrometer was used to measure the thickness of the sample. Charge carrier concentration and carrier mobility of the composite were determined by conducting Hall-effect measurements using a Van der Pauw four-point probe configuration (HMS-3000, Ecopia). The thermal conductivity of the sample was calculated using the equation $\kappa = \alpha \cdot \rho \cdot C_p$, where α , ρ , and C_p are the thermal diffusivity, bulk density, and specific heat of the material, respectively. The xenon flash method was conducted using NETZSCH, LFA 447 Nanoflash instrument to evaluate α , whereas C_p was measured by applying differential scanning calorimetry (DSC) (DSC 131 EVO, Setaram Instrumentation).

Data Availability

All data generated or analyzed during this study are included in this paper. Raw datasets are available from the corresponding author, upon receipt of a reasonable request.

References

- Zhu, T. *et al.* Compromise and Synergy in High-Efficiency Thermoelectric Materials. *Adv. Mater.* **29**, 1605884 (2017).
- Ju, H. & Kim, J. Chemically exfoliated SnSe nanosheets and their SnSe/poly (3,4-ethylenedioxythiophene): poly (styrenesulfonate) composite films for polymer based thermoelectric applications. *ACS nano* **10**, 5730–5739 (2016).
- Yu, J. *et al.* Unique Role of Refractory Ta Alloying in Enhancing the Figure of Merit of NbFeSb Thermoelectric Materials. *Adv. Energy Mater.* **8**, 1701313 (2018).
- Yang, M. *et al.* High-pressure synthesis and thermoelectric performance of tellurium doped with bismuth. *J. Mater. Sci.* **52**, 10526–10532 (2017).
- Bae, E. J., Kang, Y. H., Jang, K.-S. & Cho, S. Y. Enhancement of thermoelectric properties of PEDOT: PSS and tellurium-PEDOT: PSS hybrid composites by simple chemical treatment. *Sci. Rep.* **6**, 18805 (2016).
- Ju, H., Kim, M. & Kim, J. A facile fabrication of n-type Bi₂Te₃ nanowire/graphene layer-by-layer hybrid structures and their improved thermoelectric performance. *Chem. Eng. J.* **275**, 102–112 (2015).
- Shi, H., Parker, D., Du, M.-H. & Singh, D. J. Tellurium as a high-performance elemental thermoelectric. *Nat. Commun.* **7**, 10287 (2016).
- Shi, H., Parker, D., Du, M.-H. & Singh, D. J. Connecting thermoelectric performance and topological-insulator behavior: Bi₂Te₃ and Bi₂Te₃Se from first principles. *Phys. Rev. Appl.* **3**, 014004 (2015).
- Cao, Y., Zhu, T. & Zhao, X. Low thermal conductivity and improved figure of merit in fine-grained binary PbTe thermoelectric alloys. *J. Phys. D Appl. Phys.* **42**, 015406 (2008).
- Kim, J.-H., Choi, J.-Y., Bae, J.-M., Kim, M.-Y. & Oh, T.-S. Thermoelectric characteristics of n-type Bi₂Te₃ and p-type Sb₂Te₃ thin films prepared by co-evaporation and annealing for thermopile sensor applications. *Mater. Trans.* **54**, 618–625 (2013).
- Zhao, W. *et al.* n-Type Carbon Nanotubes/Silver telluride Nanohybrid Buckypaper with a High-Thermoelectric Figure of Merit. *ACS Appl. Mater. Interfaces* **6**, 4940–4946 (2014).
- Park, D., Ju, H. & Kim, J. Enhanced thermoelectric power factor and low thermal conductivity in one-dimensional Te/Ag₂Te composites. *Ceram. Inter.* **43**, 11156–11162 (2017).
- Park, D., Ju, H., Oh, T. & Kim, J. A p-type multi-wall carbon nanotube/Te nanorod composite with enhanced thermoelectric performance. *RSC Adv.* **8**, 8739–8746 (2018).
- Dun, C. *et al.* Flexible thermoelectric fabrics based on self-assembled tellurium nanorods with a large power factor. *Phys. Chem. Chem. Phys.* **17**, 8591–8595 (2015).
- Bae, E. J., Kang, Y. H., Jang, K.-S. & Cho, S. Y. Thermoelectric power factor optimization in PEDOT: PSS tellurium nanowire hybrid composites. *Phys. Chem. Chem. Phys.* **15**, 4024–4032 (2013).
- See, K. C. *et al.* Water-processable polymer–nanocrystal hybrids for thermoelectrics. *Nano let.* **10**, 4664–4667 (2010).
- Wang, Y., Zhang, S. & Deng, Y. Flexible low-grade energy utilization devices based on high-performance thermoelectric polyaniline/tellurium nanorod hybrid films. *J. Mater. Chem. A* **4**, 3554–3559 (2016).

18. Zhang, Y. *et al.* Surfactant-free synthesis of Bi₂Te₃-Te micro-nano heterostructure with enhanced thermoelectric figure of merit. *ACS Nano* **5**, 3158–3165 (2011).
19. Ballikaya, S., Chi, H., Salvador, J. R. & Uher, C. Thermoelectric properties of Ag-doped Cu₂Se and Cu₂Te. *J. Mater. Chem.* **1**, 12478 (2013).
20. Fujikane, M., Kurosaki, K., Muta, H. & Yamanaka, S. Thermoelectric properties of α - and β -Ag₂Te. *J. Alloys Compd.* **393**, 299–301 (2005).
21. Ju, H., Kim, M. & Kim, J. Preparation of graphene sheets into one-dimensionally nanostructured bulk bismuth telluride for enhancing thermoelectric power factor. *J. Mater. Sci-Mater. El.* **27**, 3427–3434 (2016).
22. Y Xia, Y. *et al.* One-dimensional nanostructures: synthesis, characterization, and applications. *Adv. Mater.* **15**, 353–389 (2003).
23. Bux, S. K. *et al.* Nanostructured bulk silicon as an effective thermoelectric material. *Adv. Funct. Mater.* **19**, 2445–2452 (2009).
24. Perez-Taborda, J. A. *et al.* Ultra-low thermal conductivities in large-area Si-Ge nanomeshes for thermoelectric applications. *Scientific reports* **6**, 32778 (2016).
25. Wu, H. *et al.* Strong enhancement of phonon scattering through nanoscale grains in lead sulfide thermoelectrics. *NPG Asia Materials* **6**, e108 (2014).
26. Ju, H. & Kim, J. Preparation and structure dependent thermoelectric properties of nanostructured bulk bismuth telluride with graphene. *J. Alloys Compd.* **664**, 639–647 (2016).
27. Park, D., Ju, H. & Kim, J. Preparation and thermoelectric properties of two types of nanostructured tellurium with multi-walled carbon nanotubes. *J Alloys Compd.* **748**, 305–313 (2018).
28. Alam, H. *et al.* A review on the enhancement of figure of merit from bulk to nano-thermoelectric materials. *Nano energy* **2**, 190–212 (2013).
29. Yang, L., Chen, Z.-G., Hong, M., Han, G. & Zou, J. Enhanced thermoelectric performance of nanostructured Bi₂Te₃ through significant phonon scattering. *ACS Appl. Mater. Interfaces* **7**, 23694–23699 (2015).
30. Qian, H.-S., Yu, S.-H., Gong, J.-Y., Luo, L.-B. & Fei, L.-f. High-quality luminescent tellurium nanowires of several nanometers in diameter and high aspect ratio synthesized by a poly (vinyl pyrrolidone)-assisted hydrothermal process. *Langmuir* **22**, 3830–3835 (2006).
31. Liu, Z. *et al.* Size-controlled synthesis and growth mechanism of monodisperse tellurium nanorods by a surfactant-assisted method. *Langmuir* **20**, 214–218 (2004).
32. Park, H. *et al.* Aqueous chemical synthesis of tellurium nanowires using a polymeric template for thermoelectric materials. *Cryst Eng Comm* **17**, 1092–1097 (2015).
33. Pettes, M. T., Maassen, J., Jo, I., Lundstrom, M. S. & Shi, L. Effects of surface band bending and scattering on thermoelectric transport in suspended bismuth telluride nanoplates. *Nano Lett.* **13**, 5316–5322 (2013).
34. Bubnova, O. & Crispin, X. Towards polymer-based organic thermoelectric generators. *Energy Environ. Sci.* **5** (2012).
35. Nethravathi, C. *et al.* Synthesis and thermoelectric behaviour of copper telluride nanosheets. *J. Mater. Chem. A* **2**, 985–990 (2014).
36. Kurosaki, K. *et al.* Thermoelectric and Thermophysical Characteristics of Cu₂Te-Tl₂Te Pseudo Binary System. *Mater. Trans.* **47**, 1432–1435 (2006).

Acknowledgements

This research was supported by the Human Resources Development (No. 20184030202070) of the Korea Institute of Energy Technology Evaluation and Planning (KETEP) grant funded by the Korea government Ministry of Trade, Industry and Energy and also supported by the Chung-Ang University Graduate Research Scholarship in 2017.

Author Contributions

D.P. designed the study. T.O. synthesized the sample. H.J. characterized the prepared samples and measured thermoelectric properties. D.P. analyzed the investigated thermoelectric properties and wrote the manuscript. J.K. supervised the project.

Additional Information

Supplementary information accompanies this paper at <https://doi.org/10.1038/s41598-018-35713-9>.

Competing Interests: The authors declare no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2018