

Giant Goos-Hänchen effect at the reflection from left-handed metamaterials

Ilya V. Shadrivov, Alexander A. Zharov, and Yuri S. Kivshar

Citation: *Applied Physics Letters* **83**, 2713 (2003); doi: 10.1063/1.1615678

View online: <http://dx.doi.org/10.1063/1.1615678>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/83/13?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Goos-Hänchen shift of the reflection from nonlinear nanocomposites with electric field tunability](#)

Appl. Phys. Lett. **97**, 041903 (2010); 10.1063/1.3470000

[Giant Goos-Hänchen displacement enhanced by dielectric film in frustrated total internal reflection configuration](#)

J. Appl. Phys. **101**, 013103 (2007); 10.1063/1.2405737

[Goos-Hänchen shift surface plasmon resonance sensor](#)

Appl. Phys. Lett. **89**, 261108 (2006); 10.1063/1.2424277

[Large positive and negative Goos-Hänchen shifts from a weakly absorbing left-handed slab](#)

J. Appl. Phys. **98**, 043522 (2005); 10.1063/1.2034084

[Reflection-type 2×2 optical waveguide switch using the Goos-Hänchen shift effect](#)

Appl. Phys. Lett. **76**, 2841 (2000); 10.1063/1.126491

The advertisement features a photograph of the Model PS-100 cryogenic probe station, which is a complex piece of scientific equipment with various lenses, mirrors, and mechanical components. The background is a gradient of blue and white.

Model PS-100
Tabletop Cryogenic
Probe Station

The logo for Lake Shore Cryotronics, consisting of a stylized blue and white square.

Lake Shore
CRYOTRONICS

*An affordable solution for
a wide range of research*

Giant Goos-Hänchen effect at the reflection from left-handed metamaterials

Ilya V. Shadrivov,^{a)} Alexander A. Zharov,^{b)} and Yuri S. Kivshar
*Nonlinear Physics Group, Research School of Physical Sciences and Engineering,
 Australian National University, Canberra ACT 0200, Australia*

(Received 12 May 2003; accepted 5 August 2003)

We study the beam reflection from a layered structure with a left-handed metamaterial. We predict a giant lateral (Goos-Hänchen) shift and splitting of the beam due to the resonant excitation of surface polaritons with a vortexlike energy flow between the right- and left-handed materials. © 2003 American Institute of Physics. [DOI: 10.1063/1.1615678]

As is known, a totally reflected beam experiences a lateral displacement from its position predicted by the geometric optics because each of its plane-wave components undergoes a different phase change.¹ For the beam reflected from an interface, the lateral beam shift (the so-called Goos-Hänchen effect) is usually much less than the beam width. However, larger beam shifts may occur in the layered systems supporting *surface waves*, which are able to transfer energy along the interface. Such surface waves are not excited at a single interface because the phase-matching condition between the incident and surface waves is not satisfied. However, a surface polariton can be excited in a layered structure, when the beam is incident at the angle larger than the angle of the total internal reflection. Excitations of polaritons take place in two well known geometries of the attenuated beam reflection (used e.g., for the measurements of the dielectric permittivity of solids): (i) Glass prism-air-silver structure (the so-called Otto configuration) and (ii) prism-silver film-air structure (the so-called Kretschmann configuration) (see, e.g., Ref. 2 and references therein).

The extensive study of microstructured materials with negative refraction recently fabricated experimentally,³ the so-called *left-handed metamaterials*, demonstrated that an interface between right- and left-handed material supports *surface polaritons* of transverse electric (TE) and transverse magnetic (TM) types,^{4,5} which can enhance dramatically the Goos-Hänchen effect because the excited surface waves can transfer the energy along the interface. In this letter, we predict and analyze the giant Goos-Hänchen effect in the structure (i) (the Otto configuration), where the third medium is substituted by a left-handed metamaterial.

We consider a two-dimensional geometry shown in Fig. 1(a), where the beam, incident from an optically dense medium ($\epsilon_1\mu_1 > \epsilon_2\mu_2$) at the angle larger than the angle of the total internal reflection, is reflected from the interface. We assume that the third medium is separated by a gap (which we call the second medium), and it is made of a left-handed metamaterial which possesses both negative real parts of dielectric permittivity ϵ_3 and magnetic permeability μ_3 . The interface between the second and third media supports surface waves which can be excited resonantly when the tan-

gential component of the wave vector of the incident beam coincides with the propagation constant of the surface polariton. In such a case, the surface wave can transfer energy along the interface leading to a great enhancement of the lateral beam shift.

The Goos-Hänchen shift Δ can be calculated analytically as $\Delta = -d\Phi/dk_x$,⁶ when the phase Φ of the reflection coefficient is a linear function of the wave vector component k_x along the interface, across the spectral width of the beam. The (standard) lateral beam shift has been calculated for the reflection from layered structures with left-handed materials, for the cases of a single interface⁷ and for a periodic structure of alternating right- and left-handed layers.⁸

In our geometry [see Fig. 1(a)], the reflection coefficient $R = R(k_x)$ for the TE-polarized plane monochromatic

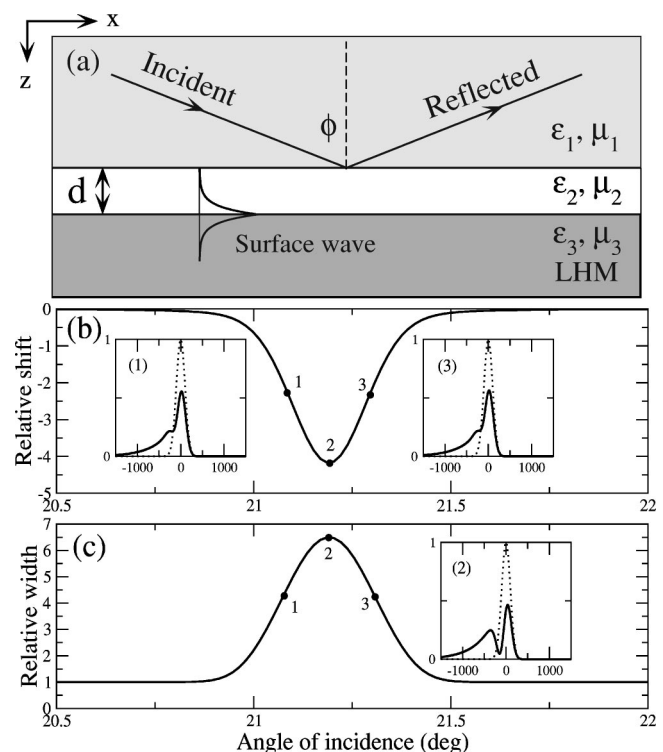


FIG. 1. (a) Geometry of the problem. (b) and (c) Relative beam shift and width vs incidence angle. Insets are the profiles of the reflected (solid) and incident (dotted) beams, shown as the field amplitude vs normalized coordinate x .

^{a)}Electronic mail: ivs124@rsphysse.anu.edu.au

^{b)}Permanent address: Institute for Physics of Microstructures, Russian Academy of Sciences, Nizhny Novgorod 603950, Russia.

$[\sim \exp(i\omega t)]$ wave can be found as

$$R = \frac{(\alpha_1 + 1)(\alpha_2 + 1) - (\alpha_1 - 1)(\alpha_2 - 1)e^{2ik_2d}}{(\alpha_1 - 1)(\alpha_2 + 1) - (\alpha_1 + 1)(\alpha_2 - 1)e^{2ik_2d}}, \quad (1)$$

where $\alpha_{1,2} = k_{z1,3}\mu_2/k_{z2}\mu_{1,3}$, $k_{zi} = (\omega^2\epsilon_i\mu_i/c^2 - k_x^2)^{1/2}$, where $i = 1, 2, 3$, d is the gap thickness, and c is the speed of light in a vacuum. Here, we consider the TE-polarized waves, but the results are qualitatively similar for the TM-polarized waves. One can show that the absolute value of the reflection coefficient has a deep minimum when k_x equals the wave vector of a surface wave excited at the interface between second and third media.

We consider an incident beam of the Gaussian shape, $E_i(x) = \exp(-x^2/4a^2 - ik_{x0}x)$, where a is the width of the beam, k_{x0} determines the angle of incidence ϕ , $k_{x0} = k_1 \sin \phi$, and k_1 is the propagation constant in the first medium, $k_1 = \omega\sqrt{(\epsilon_1\mu_1)}/c$. The reflected field is found in a standard way

$$E_r(x) = \frac{1}{2\pi} \int_{-\infty}^{\infty} R(k_x) \bar{E}_i(k_x) dk_x, \quad (2)$$

where \bar{E}_i is the Fourier spectrum of the incident beam.

Larger lateral beam shifts are expected at the angles of incidence such that the beam spectrum contains the components with the same k_x as the propagation constant of the surface waves. As has been shown recently, both *forward* and *backward* surface polaritons can exist at the left-handed interface,⁵ depending on the parameters $X = |\epsilon_3|/\epsilon_2$ and $Y = |\mu_3|/\mu_2$. Excitation of the forward surface waves results in the energy transfer in the direction of incidence. A negative shift of the beam is obtained when the backward surface waves are excited, this corresponds to the parameters $XY > 1$ and $Y < 1$.

We define the relative shift of the beam, Δ , as the normalized *first momentum* of the electric field of the reflected beam, $\Delta = \Delta_1$, where

$$\Delta_n = a^{-n} \int_{-\infty}^{\infty} x^n |E_r(x)|^2 dx \left(\int_{-\infty}^{\infty} |E_r(x)|^2 dx \right)^{-1}. \quad (3)$$

The values $\Delta \ll 1$ correspond to the beam shift much smaller than the beam width, while $\Delta \gg 1$ corresponds to a giant Goos-Hänchen shift. The second momentum Δ_2 [defined by Eq. (3) at $n = 2$] characterizes the relative width of the beam after the reflection, $W = \Delta_2^{1/2}$.

We chose the following parameters of the media: $\epsilon_1 = 12.8$, $\mu_1 = \epsilon_2 = \mu_2 = 1$, $\epsilon_3 = -3$, $\mu_3 = -0.5$. The propagation constant of surface polaritons can be found from the relation $h^2 = (\omega/c)^2 \epsilon_2 \mu_2 Y(Y - X)/(Y^2 - 1)$, and, for these parameters, the surface waves at the interface are backward propagating. Figures 1(b) and 1(c) show the dependence of Δ and W on the angle of incidence at $\omega a/c = 100$ and $\omega d/c = 3$, respectively. We observe a distinctive resonant dependence of the beam shift, and the maximum corresponds to the phase matching condition $k_{x0} = h$.

In the inset (2) of Fig. 1(c), two distinctive peaks in the reflected beam are observed. The first peak corresponds to a mirror reflection, while the second peak is shifted from the incident beam and it appears due to the excitation of surface waves. At the resonance, the lateral beam shift becomes larger than the beam width. The double-peak structure ap-

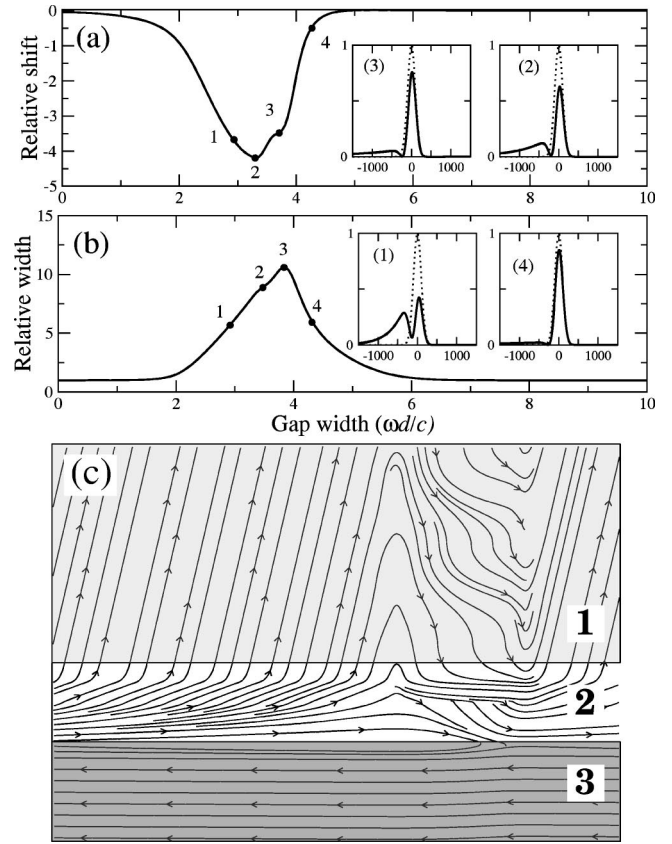


FIG. 2. (a) and (b) Relative shift and width of the reflected beam vs normalized gap $\omega d/c$ at $\omega a/c = 100$. (c) Energy flow, shown as a streamlines of the Poynting vector. In all plots, the angle of incidence corresponds to the point (2) in Figs. 1(b) and 1(c). Insets show the profiles of the reflected (solid) and incident (dotted) beams.

pears only for narrow beams, when the beam spectrum is wider than the spectrum width of the surface mode, the latter can be found as a width of the resonance shown in Fig. 1(b). The components of the beam spectrum outside this region are reflected in a mirrorlike fashion, while the spectrum components near the resonance transform into a surface wave, being responsible for the second peak in the shifted reflected beam. For wider beams, such that their spectrum completely falls into the surface mode excitation line, only the shifted peak appears. With an increase of the beam width, though, the relative beam shift decreases due to the fact that the absolute shift of the beam grows slower than the beam width.

Figures 2(a)–2(c) show the beam shift and width versus the normalized gap thickness and the structure of the energy flow. The resonances observed in Figs. 2(a) and 2(b) have a simple physical explanation. Indeed, when the gap is absent ($d = 0$) or small, no surface wave is excited, and the beam shift is negligible. By increasing the gap width, one increases the quality factor of the surface mode, thus increasing its propagation distance and the reflected beam shift. Similarly, for large d , the surface wave is not excited, and the reflected beam shift becomes small again.

To understand deeper the physical mechanism for the giant Goos-Hänchen shift, we calculate the energy flow for the beam reflection and compare it with the results for the right-handed media.⁹ Figure 2(c) shows the structure of the energy flow for the case of a negative lateral shift. The strongly curved flow lines in the upper medium correspond

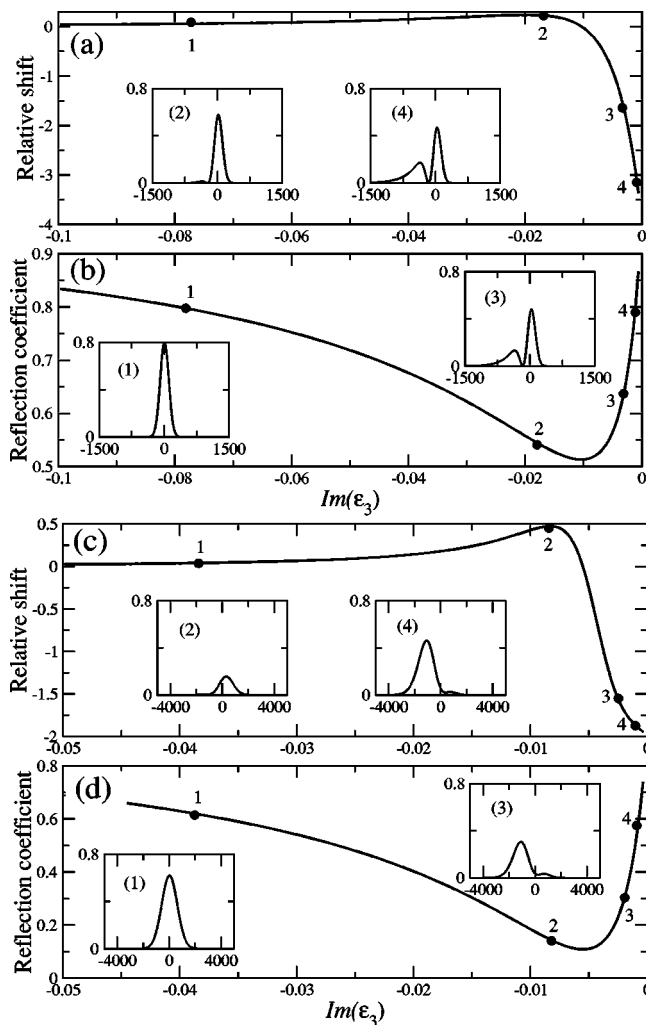


FIG. 3. (a) and (c) Relative beam shift and (b) and (d) reflection coefficient vs the imaginary part of the dielectric permittivity, for narrow $\omega a/c = 100$ [(a) and (b)] and wide $\omega a/c = 600$ [(c) and (d)] beams, for $\omega d/c = 3$. Insets show the profiles of the reflected beam.

to the interference of the incident and mirrorlike reflected beams. The finite-extension surface wave excited in a slab along the interface has a distinctive vortexlike structure.¹⁰ This surface wave transfers the energy in the negative direction, and then the energy is reflected from the interface as a shifted beam.

To make our predictions more realistic, we study the effect of losses always present in left-handed materials. We introduce losses by adding the imaginary parts to the dielectric permittivity ϵ_3 and magnetic permeability μ_3 . In particular, we take $\text{Im}(\mu_3) = -2 \times 10^{-5}$ and vary the imaginary

part of ϵ_3 . We notice that the losses in the left-handed medium affect mostly the surface waves and, therefore, the major effect produced by the losses is observed for the strongly shifted beam component.

We distinguish two limiting cases. When the beam is narrow, i.e., its spectral width is large, only a part of the beam energy is transferred to surface waves, while the other part is reflected. This case is shown in Figs. 3(a) and 3(b). In this case, the increase of losses, i.e., the increase of the absolute value of $\text{Im}(\epsilon_3)$, results in the suppression of the second peak in the reflected beam, which is due to the surface wave excitation. The growth of the amplitude of the mirrorlike reflected beam can be explained by a detuning from the resonance between the incident wave and the surface polariton.

For a wide beam with a narrow spectrum, almost all of the energy of the beam is transferred into a surface wave and, therefore, the lateral shift becomes strongly affected by the losses in the left-handed medium, as shown in Fig. 3(c). Figure 3(d) shows the dependence of the reflection coefficient on the imaginary part of the dielectric permittivity in the third medium.

In conclusion, we have described the Goos-Hänchen shift and splitting of a beam totally reflected from a layered structure with a left-handed metamaterial. The giant lateral shift of the beam is explained by the resonant excitation of surface vortexlike polaritons at the interface between the right- and left-handed materials. The beam shift can be both positive and negative, depending on the type of the surface waves excited at the interface. We believe that the giant enhancement of the lateral shift of the reflected beam can be employed for direct measurements of the parameters of left-handed materials.

¹F. Goos and H. Hänchen, *Ann. Phys. (Leipzig)* **1**, 333 (1947).

²S. Chuang, *J. Opt. Soc. Am. A* **3**, 593 (1986).

³R. A. Shelby, D. R. Smith, and S. Schultz, *Science* **292**, 77 (2001).

⁴R. Ruppin, *Phys. Lett. A* **277**, 61 (2000).

⁵I. V. Shadrivov, A. A. Sukhorukov, Y. S. Kivshar, A. A. Zharov, A. D. Boardman, and P. Egan, *arXiv:physics/0305126* (2003).

⁶See, e.g., L. Brekhovskikh, *Waves in Layered Media* (Academic, New York, 1980).

⁷P. Berman, *Physica E (Amsterdam)* **66**, 067603 (2002); A. Lakhtakia, *Electromagnetics* **23**, 71 (2003); R. W. Ziolkowski, *Opt. Express* **11**, 662 (2003).

⁸I. V. Shadrivov, A. A. Sukhorukov, and Y. S. Kivshar, *Appl. Phys. Lett.* **82**, 3820 (2003).

⁹See, e.g., H. Lai, C. Kwok, Y. Loo, and B. Xu, *Phys. Rev. E* **62**, 7330 (2000).

¹⁰I. V. Shadrivov, A. A. Sukhorukov, and Y. S. Kivshar, *Phys. Rev. E* **67**, 057602 (2003).