
Green Binders for Wood Adhesives

Emelie Norström, Deniz Demircan,
Linda Fogelström, Farideh Khabbaz and
Eva Malmström

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/intechopen.72072>

Abstract

Today's society relies heavily on glued wood products for constructions, furniture, and floorings, for example. Essentially, all adhesives on the market are based on fossil-based resources, and many also contain formaldehyde to yield sufficient reactivity and adhesive performance. Formaldehyde is soon to be banned from consumer goods in Europe, due to its carcinogenic and allergenic features. With the rapidly growing societal environmental awareness, it becomes evident that it is crucial to seek greener, more sustainable alternatives. There is nothing new to this idea; on the contrary, prior to the advent of synthetic polymers, a range of biopolymers such as proteins and starch, were successfully used. However, since adhesives based on synthetic polymers were found to perform better, especially regarding the water resistance, the naturally sourced adhesives have had a subordinate role up until recently. The growing interest for using bio-polymers from renewable resources, such as wood/forest, corn, and cereals have spurred significant R&D developments toward the use of bio-polymers in green wood adhesives. The scope of the present chapter is to summarize, in short, some of the most recent scientific literature regarding the development of green adhesives.

Keywords: wood adhesive, protein, polysaccharide, starch, chitosan, hemicellulose, tannin, lignin

1. Introduction

Wood adhesives are produced in large amounts and are used for many large-scale applications such as load-bearing constructions, flooring, furniture, doors, and windows. Today, wood adhesives are essentially solely prepared from fossil-derived polymers based on, for example, urea, melamine, formaldehyde, phenol, resorcinol, isocyanate, and vinyl acetate, but historically adhesives were prepared from various natural sources, such as proteins

from milk, blood, and soybean [1]. In 1928, Casco Adhesives (now AkzoNobel Adhesives) in Sweden, started their production of adhesives based on casein (Casein Company), a milk protein [2]. With the rapid and revolutionizing development of the “plastic era,” initialized during the 1940s with the launch of synthetic polymers such as acrylates and vinyl esters, it became apparent that the performance of bio-based adhesives could be widely exceeded. During the 1960s, the hitherto used natural binders were replaced by synthetic polymers derived from fossil-based resources, motivated both by insufficient properties and high cost [3, 4].

Fossil-derived adhesives are cost-effective and perform very well regarding bonding performance and water resistance. The oil-crisis during the 1970s brought about a realization that natural sources for fossil-based products are limited; however, this has not yet had a dramatic effect on the adhesive industry. A large share of the industrially viable wood adhesive systems also comprises formaldehyde which is a highly reactive compound, making it well suited for its intended use. For instance, particleboard products are almost exclusively bonded with formaldehyde, in combination with urea and/or melamine or phenol. However, formaldehyde has been identified as a very hazardous compound and will most likely be banned from use in many applications [5]. The formaldehyde ban, combined with the rapidly growing environmental awareness calls for the adhesive industry to become more sustainable, more benign, and less fossil-dependent. To replace fossil-based adhesives with sustainable counterparts successfully, the adhesive properties and bonding performance have to be very similar, or bring other added values, and very importantly, the cost performance has to be on par with existing, non-sustainable, adhesives.

The urge for developing green adhesives reawakens the interest for bio-based adhesives, even though it is not completely uncomplicated. Many natural resources such as starch and protein, potentially well-suited for adhesive applications, may also be used as food sources. This calls for careful consideration in a time where more than 800 million people suffer from starvation world-wide [6].

The development of bio-based adhesives also poses other challenges; adhesives prepared from bio-based polymers often exhibit poor water resistance and/or render too high cost to successfully compete with fossil-derived polymers [1]. Another challenge when utilizing bio-based polymers is the often large property variation, emanating from locus and constantly shifting growth-conditions such as type of source, growth season, access to nutrients, climate, etc. [7]. Also, the extraction and fractionation procedures required to isolate the bio-based polymers will influence the final properties of the adhesive, as well as the cost. Altogether, it is challenging to replace robust synthetic polymers, having well-known and reproducible characteristics, with bio-based polymers with a broader property window, in industrial applications. Today, the research in this area is mainly focused on proteins, starch and other polysaccharides, lignin, and tannin as raw materials (**Figure 1**).

1.1. Evaluation of bonded specimens

Wood adhesives can be applied on several different substrates such as veneers, plywoods, panels, beams, particleboards, etc., and are often subjected to elevated temperatures and high

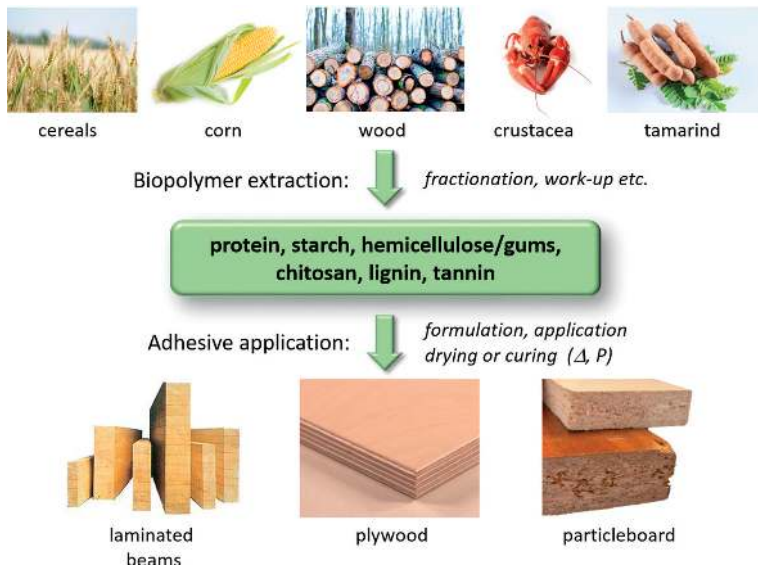


Figure 1. Green binders for wood adhesives. Photocredits for pictures of particleboard and plywood distributed by a CC-BY-SA 3.0 license [8].

pressure during cure depending on the application. Adhesives are evaluated by testing the bond strength of the bonded wood specimens; both dry and wet strength are crucial properties. The requirement of the adhesive depends on the application (e.g., interior or exterior use), type of adhesive (e.g., thermoplastic or thermosets), type of wood substrate, etc. Heat resistance is of particular interest for specimens glued with thermoplastic adhesives, since a thermoplastic material generally is more sensitive to heat than the thermosetting counterpart. There are many different national standardized evaluation procedures, such as ASTM, EN, Chinese industry standard, China National Standards, etc., with different criteria for fulfilling the requirements of a certain application. These standards often differ in the gluing procedure, sample preparation, pressing conditions, conditioning and performance evaluation. The use of slightly dissimilar standards and evaluation protocols make it difficult to compare different studies [9, 10]. The evaluation of mechanical properties of wood adhesives has been subject to substantial research [11].

The chemical composition of adhesives is often characterized with Fourier transform infrared spectroscopy (FTIR), nuclear magnetic resonance (NMR), and the relative average molecular weight is determined by size exclusion chromatography (SEC). Further characterization includes rheological studies (mainly the viscosity), thermal studies using differential scanning calorimetry (DSC) and thermogravimetric analysis (TGA), contact angle measurements, and storage stability measurements. The bond line and the adhesive's penetration into the wood in the bonded specimens can be studied with optical microscopy (OM), scanning electron microscopy (SEM), transmission electron microscopy (TEM), X-ray photoelectron spectroscopy (XPS), and energy dispersive X-ray spectroscopy (EDXS), etc.

The scope of this book chapter is to give a short overview of the most recent publications concerning the use of bio-polymers as promising sustainable resources for wood adhesives. Several extensive and in-depth reviews of the use of green wood adhesives are already published and these are referred to throughout the chapter, when appropriate. The chapter does not cover patents or scientific publications published in any other language than English.

2. Protein

Proteins are linear polyamides built up by amino acids, linked together with polypeptide bonds, and are, together with DNA, fat, and polysaccharides, the most important constituent in all living species. There are 20 different amino acids, either acidic, basic, or neutral depending on the structure of the side chain. The properties of a protein originates from its complex structure; the amino acid sequence (primary structure) is partly arranging into α -helices and β -sheets (secondary structure), side-chains interact to form a 3D-structure (tertiary structure), and the whole protein molecule interacts with other protein molecules to form a higher-order (quaternary) structure [12].

Proteins have a long history as binders in wood adhesives but were replaced by fossil-based polymers due to cost and insufficient properties, such as poor bond strength and water resistance [1]. The side-chains of the polypeptide chain contain functional groups that make the amino acid either hydrophilic or hydrophobic, and provide possibilities for interaction with hydroxyl or carboxyl groups in wood, and for crosslinking.

Generally, protein adhesives suffer from high viscosity, consequently demanding low solid content, and they commonly only meet the requirements for indoor applications due to poor water resistance [13]. Extensive research is being conducted to improve the bonding performance and water resistance of proteins to extend the applicability of wood-bonded protein adhesives, as previously reviewed in literature [13–15].

Soybean protein can be obtained from soybeans during the production of soy oil and soy meal. Soy oil is used in the food industry and soy meal as animal feed [16]. Soy protein is a promising alternative to fossil-based adhesives due to its availability, easy processing, and low cost, but the fact that it is a food source is debatable. Soybean protein-based adhesives have been suggested in a few applications today: particleboards, laminated plywood, and finger-joint lumber [13, 17]. So far, the use of soybean protein in adhesives has been limited due to low water resistance and high viscosity [13]. Adhesives containing soybean flour is commercially available [18].

Physical and chemical methods have been used to improve the properties of proteins. Denaturation of the native protein structure exposes functional groups buried within the 3D-structure of the protein, which may enable solubilization and bonding. The increased solubilization further makes it possible for the protein adhesive to flow better over the wood surface, forming hydrogen bonds with wood, and allows for subsequent chemical crosslinking. Denaturation can be triggered by increased temperature, pressure, and changes in pH, as well as the addition of denaturants, such as urea guanidine hydrochloride, enzymes, SDS or other detergents [13, 19].

It was shown that a combination of thermal alkali degradation, thermal acid treatment, and crosslinking of soybean protein can provide an adhesive with better applicability regarding viscosity and bonding performance. Thermal alkali degradation lowers the viscosity and improves the technological applicability. Thermal acid treatment allows for the formation of an intermolecular network which improves the water resistance. Glyoxal, epoxy latex, polyisocyanate, and polyamide were evaluated as crosslinkers. The type of crosslinker, amount of crosslinker, and ratio of thermal alkali-degraded soybean protein to thermal acid-treated soybean protein, had important effects on the final adhesive properties. Polyamide is the preferred crosslinker due to its good crosslinking efficiency, miscibility with soybean protein, and low viscosity [20].

Thermo-chemical treatment of soybean protein in the presence of sodium sulfide or sodium dodecyl sulfate, followed by crosslinking with epichlorohydrin-modified polyamide (EMPA) showed promising results. The adhesive could withstand recurring hygrothermal treatment after which the wet strength fulfilled the required value for structural use [21].

Proteins have also been combined with synthetic polymers and resins such as formaldehyde, urea formaldehyde (UF), melamine urea formaldehyde (MUF), and dispersion polymers, such as polyvinyl acetate (PVAc) [14, 22]. The water resistance of protein adhesives can be improved by the addition of crosslinkers such as polyamidoamine-epichlorohydrin (PAE) resin or polymeric diphenylmethane diisocyanate (pMDI) [14].

In a recent study, water was substituted with egg white in a soybean-meal adhesive which was subsequently crosslinked with triglycidyl amine in an attempt to increase the solid content and to improve the water resistance of soybean protein-based adhesives. As a result, the solid content was increased, the viscosity was kept low, and the bonding performance was improved. The wet strength of the adhesive was superior to that of conventional UF resin and PAE-crosslinked soybean protein-based adhesive, and was comparable to that of melamine-modified UF resin [23].

A green route to prepare a soybean protein-based adhesive has been demonstrated by utilizing the polysaccharides and proteins in soy meal. First, the polysaccharides and proteins were separated, whereafter the polysaccharides were crosslinked with a green crosslinker, sodium hexametaphosphate, and subsequently blended with the proteins to form an interpenetrating network. After hot pressing, a stable glue line was formed that fulfills the requirements for plywood in interior use [24]. In another study, the polysaccharides were hydrolyzed and then crosslinked with the proteins through a Maillard reaction. The bonding performance, rheological properties, and thermal stability were improved and the adhesive also met the requirements for plywood in indoor applications [25].

Magnesium oxide (MgO) has been added to soybean protein-based adhesives to improve the bonding performance. In a recent study, MgO was used together with different fractions from soybean. It is preferable to use soy flour or soy meal directly without purification steps which would increase the cost of the final product. However, the purified soybean protein gave better adhesive properties together with MgO, compared with the polysaccharide-containing soy flour [26].

The water resistance of a soybean protein-based adhesive can be improved with the addition of 5,5-dimethyl hydantoin polyepoxide (DMHP). DMHP acts as a crosslinker during cure

while at the same time decreasing the wet-adhesive viscosity, improving the wetting and penetration of the adhesive, yielding a smooth surface and bonding performance. DMHP made it possible to increase the solid content, decrease the viscosity, and improve both dry and wet strength [27].

A new type of soybean protein-based adhesive has been presented where a soybean protein-acrylate emulsion-based adhesive was synthesized by mini-emulsion polymerization. Methyl methacrylate and butyl acrylate were polymerized using soybean protein as the protective colloid, resulting in an adhesive evaluated for plywood preparation. The bonding performance was, however, only slightly improved [28].

Soybean protein has been blended with ethylene glycol, diethylene glycol, and polyethylene glycols with different molecular weights. Ethylene glycol improved the wet strength of the adhesive which was suggested to be due to improved wettability and hydrogen bonding. Higher molecular weight polyols, however, decreased the wet strength of the adhesives [29].

Soybean protein has also been blended with lignin to improve the water resistance of the adhesive [30]. The lignin-particle size and the protein-to-lignin ratio significantly affected the bonding performance. Lignin with smaller particle size increased the wet strength of the adhesive [31]. Lignin amine was prepared by Fenton oxidation and subsequent reductive amination [32]. Addition of lignin amine to soybean protein-based adhesives has also shown to improve the bonding performance and water resistance.

Soybean protein and cottonseed protein isolates were mixed in different ratios and used as wood adhesives. Increasing fraction of soybean protein was deteriorating the adhesive properties. However, formulations with addition of ca 50% xylan, starch, or cellulose exhibited a retained hot-water resistance [33].

Soy crops are unfortunately not widespread over the world; therefore, the possibility of using other types of proteins has also been explored. Wheat gluten is a by-product from the production of wheat starch and bioethanol, and has been studied as a binder for wood adhesives with promising results [34–44]. Other proteins that have been evaluated are, for example, zein protein [45], pea protein [45], canola protein [46, 47], cotton-seed protein [47], triticale protein [48], and lupine protein [49, 50].

3. Polysaccharides

Polysaccharides, built up by hydroxyl-functional monosaccharides joined together by glycosidic bonds, are an interesting group of polymers that have shown potential as binders for wood adhesives [51]. A polysaccharide with high molar mass will provide cohesive strength to the adhesive; however, a high molar mass will also give higher viscosity. The formation of hydrogen bonds between hydroxyl groups in the polysaccharide and the substrate allows for strong adhesion to wood. However, the hydroxyl groups also render the polysaccharide hydrophilic, which has a negative impact on the water resistance of the final adhesive. Improving the water resistance of polysaccharides is a challenge that is subject to much research.

3.1. Starch

Starch is a polysaccharide that has shown great potential as a binder for wood adhesives [14, 15, 52]. Starch has attracted much attention because of its abundance, renewability, and low price. Starch consists of amylose and amylopectin. Amylose is a long, linear polymer of α -1,4-linked D-glucopyranose, and amylopectin is a branched polymer, much larger than amylose, with α -1,4-linked glucose segments connected with α -1,6-linked branch points. The proportion of amylose to amylopectin affects the properties of the wood adhesive.

Native starch is a very good binder for wood, but it suffers from insufficient water resistance, when modifications are necessary. Many strategies have been employed to improve the properties of starch-based wood adhesives. Starch is often combined with another component, for example, polyvinyl alcohol, or polyvinyl acetate, to increase water resistance [53, 54]. There are several studies on graft polymerizations from starch, commonly using vinyl acetate as monomer and ammonium persulfate as initiator [54–56]. Confocal Raman Microscopy has been used to study the homogeneity of vinyl acetate-grafted starch. It was shown that the graft efficiency was important and had a large effect on the bonding performance of the starch adhesive [57].

One of the main challenges with starch-based wood adhesives is the storage stability; lately, several studies have demonstrated how this can be improved. The effect of emulsifiers in wood adhesives with high starch content has been studied, since the addition of emulsifiers can allow for good dispersion and storage stability. A combination of lauryl sodium sulfate (LSS) and alkylphenol ethoxylates (APEO) can improve the flowability and stability of the adhesive. However, a substitute for APEO is necessary since APEO has a negative impact on the environment [58]. Heat treatment of starch prior to the grafting reaction has been shown to enhance the grafting efficiency and the storage stability [59]. Sucrose-fatty acid esters, derived from renewable sources, have been used as surfactants added prior to grafting a high amylose-containing starch with vinyl acetate. The addition of surfactant resulted in excellent storage stability and improved bonding performance. The thermal stability increased and it was suggested that aggregation of particles was impeded by the surfactant [60]. Addition of SDS has been shown to improve the dispersibility and storage stability of starch grafted with vinyl acetate [61]. Unfortunately, the bonding performance was decreased with the addition of SDS. By adding Na-montmorillonite, a nano-layered silicate, the bonding performance was improved. An addition of 5% Na-montmorillonite enhanced the strength both in dry and wet state; the viscosity slightly increased but the dispersibility and stability were retained [62].

Acid hydrolysis of starch is a common method that can be used to modify starch and improve the solubility and the viscosity of the adhesive. Acid hydrolysis results in breakage of hydrogen bonds between starch molecules, facilitating starch molecules to react with crosslinkers or grafting monomers. Excessive acid hydrolysis may, however, damage the structure. More recently, studies have been performed to better understand how acid hydrolysis can be used to improve bonding performance, water resistance, heat resistance, and storage stability of the adhesive [63, 64].

A starch wood adhesive has been synthesized by oxidation of starch and subsequent attachment of a silane coupling agent, followed by polymerization of butyl acrylate and vinyl acetate. The bonding performance and the thermal stability of the adhesive were improved [65]. Butyl acrylate-grafted starch also resulted in an adhesive with good stability. The bonding

performance was similar to a commercial polyvinyl acetate adhesive even after storage for 3 months [65]. In another paper, oxidized starch was grafted with acrylamide and butyl acrylate and thereafter crosslinked with vinyltriisopropoxysilane to yield an adhesive with improved bonding performance [66]. A γ -methacryloxypropyl trimethoxy silane coupling agent was also studied for crosslinking starch grafted with vinyl acetate. The resulting adhesive showed improved bond strength, storage stability, and shear-thinning properties [67].

An isocyanate pre-polymer has been used to crosslink starch to enhance the water resistance. The starch was prepared by oxidation, or esterification, to reduce the crystallinity and increase the reactivity, and thereafter crosslinked with isocyanate [68–70]. Carboxymethyl cellulose (CMC) is another component that has been added to a starch/isocyanate adhesive together with polyvinyl alcohol and borax to tailor the viscosity, solids content, bonding performance, and the interface compatibility between starch and isocyanate pre-polymer [71].

3.2. Chitosan

Chitosan is deacetylated chitin, which is a polysaccharide that exists in crustaceans such as shrimp and crab, and insects. Naturally, chitosan only occurs in *Mucoraceae* fungi, but chitosan is also readily available and abundant by means of easy and facile derivatization from chitin. It is estimated that 10 billion tons of chitin are synthesized every year by the related organisms [72]. Chitosan is a polysaccharide consisting of β -(1,4)-linked 2-acetamido-2-deoxy-D-glucopyranose (N-acetyl glucosamine) and 2-amino-2-deoxy-D-glucopyranose (glucosamine). Besides being an economically feasible bioresource, chitosan has received great attention for a wide range of commercial applications [73–76] as it is biodegradable, biocompatible, non-toxic, antimicrobial and has reactive amino side groups which allow for chemical modification.

Besides the molecular weight, the degree of deacetylation is particularly important for the adhesion properties of chitosan. Chitosan is characterized by reactive amino groups and numerous hydroxyl groups that can interact with many different functional groups and high molar mass that provides cohesive strength, which makes it an interesting group of materials. Chitosan is insoluble in most organic solvents but soluble in water at acidic pH due to protonation of the amino groups. Combined, these characteristics open up the possibility for new applications in the adhesive and binder area [77].

Chitosan has shown great potential as a binder in adhesives, with or without additives or cross-linkers, as reviewed in literature [77, 78]. Chitosan formulations were prepared by dissolving chitosan in acetic acid solution, often used to dissolve chitosan. Double-lap wood specimens were bonded and dried for 24 h at 40°C with no applied pressure. The adhesive showed good bond strength that could be further improved with the addition of glycerol and trisodium citrate dehydrate [79]. It has been reported that citric acid reacts with chitosan amine groups to form amide bonds [80] and glycerol acts as a plasticizer which takes part in the curing process [81]. However, all formulations were found to have poor water resistance. The penetration of rhodamine-labeled chitosan in a pinewood matrix was investigated using a micro-imaging technique. No in-depth penetration of high molecular weight chitosan was observed [79].

Chitosan has been modified with glucose via the Maillard reaction [82, 83], aiming at improving bonding properties. The effect of glucose addition to chitosans of varying molecular

weight was evaluated with respect to bonding properties [84]. It was found that the dry and wet strengths were improved for low-molecular-weight chitosan. However, addition of glucose had a negative impact on bonding properties of high-molecular-weight chitosan.

Chitosan adhesives have also been prepared in combination with konjak glucomannan (KGM) [85]. Compared with casein and soybean protein references, the chitosan-KGM adhesive showed better bonding performance, but was inferior to a UF resin [85]. The bonding performance of chitosan-KGM-polyvinyl alcohol adhesive was also modeled using the Box-Behnken design for response surface methodology [86]. Polypeptides have been used to react with aldehyde and amine groups present in KGM and chitosan, respectively. The wet strength was improved, but the dry strength deteriorated [87].

3.3. Hemicelluloses/gums

Hemicelluloses can be found together with cellulose and lignin in biomass such as wood, grass, and cereals, while gums can be found in seeds, plants, seaweeds or microorganisms for example. Hemicelluloses and gums are heteropolysaccharides consisting of sugars such as xylose, arabinose, mannose, glucose, galactose, and sugar acids, and their chemical composition and structure varies with species [51, 88]. Hemicelluloses have low molecular weight, the average degree of polymerization (DP) is typically 80–200, compared with gums or cellulose with DP of several thousands [7]. Hemicelluloses and gums are among the most abundant biopolymers in nature. By-products from forestry and agriculture are good sources of hemicelluloses. With the growing environmental awareness, the traditional pulp mill is converted into a biorefinery to make efficient use of all possible side streams. Apart from power and fuel production, the possibilities for deriving value-added chemicals are also exploited. The hemicellulose-rich hydrolysates, emanating from the pulping process, can be explored as a constituent for wood adhesives. However, the hemicelluloses in the dilute hydrolysate have rather low-molecular weight and the liquor also contains salts and other by-products; therefore, further fractionation/purification is needed before evaluated in wood adhesives. Hemicelluloses are similar to starch structurally, thus holding promise for adhesive applications; yet, the challenges regarding water resistance remain. Moreover, hemicelluloses, unlike starch, have the advantage of not being a food source.

Locust bean gum (LBG), guar, tamarind, and xanthan gum have been evaluated as wood adhesives [89]. LBG, a galactomannan, obtained from seeds from the carob tree, has shown promising properties. A water dispersion of LBG exhibited very good bond strength, water resistance, and heat resistance [89]. A bacterial polysaccharide, FucoPol, has been tested as a binder for wood. The bond strength was fairly good, but the water resistance was very poor [90]. Another bacterial polysaccharide, xanthan gum, has been evaluated in wood adhesives [89, 91]. Xanthan gum by itself does not show any water resistance, but oxidized xanthan gum, on the other hand, show water resistance similar to polyurethane and chitosan adhesives. No significant improvement was observed by combining xanthan gum with chitosan [91]. Gum Arabic has been evaluated to produce particleboards that noticeably improved the overall panel properties. The particleboard had a smooth surface, and improved internal bond strength [92]. It has been reported that KGM can be used as a wood adhesive with good bond strength and stability [93]; however, low water resistance is limiting its applicability in wood adhesives [85]. The adhesion of KGM on plywood has been investigated and it was

found that the dry bond strength was relatively good despite the low solid content used [85]. However, the water resistance was found to be very poor. In several studies, KGM has been combined with chitosan, as reviewed in Section 3.2.

Xylan extracted from beech has been suggested as a binder in wood adhesives [94]. Xylan itself does not show sufficient bonding performance, especially regarding water resistance. A combination of xylan with dispersing agents with/without crosslinkers has been studied. The best combination was a water dispersion of xylan and polyvinyl amine that exhibited good bond strength, water resistance, and heat resistance [94].

4. Lignin

Lignin is the third most abundant biological macromolecule and exists in the complex and rigid structure of lignocelluloses [1, 95, 96]. It is present in lignocellulosics including wood, grass, agricultural residues, and other plants [97]. It is a high-molecular-weight aromatic polymer based on phenylpropane units in a densely crosslinked structure. Intimately interspersed in the lignocellulose structure, lignin acts as a “glue” binding cellulose and hemicellulose together, thus providing rigidity and microbial resistance to the cell wall [98].

Chemical modification of lignin has been extensively studied [99]. Lignin in adhesive applications has been actively researched and several papers have been published recently on this topic [14, 15, 100, 101]. The main interest in lignins as adhesives is due to its structural similarity to phenol, suggesting they can be used as substitutes for phenol-formaldehyde (PF) resins [102]. In adhesive research, lignin is often combined with synthetic resins such as PF and/or urea-formaldehyde (UF) resins [103] to decrease cost [104] and formaldehyde emission [105].

Lignin in adhesives have rendered limited commercial success mainly due to the low reactivity toward formaldehyde, or other aldehydes, as a result of its complexity and low number of reactive sites [101]. The low reactivity is a disadvantage in applications where short curing times are desired. To enable utilization in various material applications, the reactivity can be improved by modification [106–108]. Phenolic and aliphatic hydroxyl groups on lignin allow for chemical modifications including esterification, etherification, phenolation, oxidation, reduction, and amination.

Lignin was used without any chemical modifications as a phenol substitute in the synthesis of a resin evaluated for plywood applications [109]. This study involved the replacement of phenol with lignin in a PF resol resin. The effect of the formaldehyde ratio was studied, and the prepared plywoods were found to exhibit very low formaldehyde emissions. In terms of thermomechanical properties, the lignin-based resin was reported to be similar to the PF reference. Organosolv and sulphite lignin were phenolated and used as reactive precursors for wood veneers and particleboards [102]. Wet and dry internal bond strength fulfills European standards for load-bearing boards in humid environments. In a recent study, a lignin-urea-glyoxal (LUG) wood adhesive was prepared in attempt to eliminate the use of formaldehyde from wood-based panels such as plywood [95]. No significant decrease in mechanical strength was observed, when it was concluded that glyoxal is a suitable substitute for formaldehyde in wood adhesives. In the same study, further improvement of physical and mechanical

properties was obtained by adding nanoclay to the LUG resin. Lignin was modified by phenol and used in UF resins [110]. It was demonstrated that the formaldehyde emission from wood panels, bonded with modified lignin-UF resin, was lower compared with commercial UF adhesives. Wood panels were also prepared by using lignin in a UF resin [111, 112]. Prior to the resin preparation, lignin was modified by two different methods, either by a pretreatment with a green ionic liquid (IL), 1-ethyl-3-methylimidazolium acetate, or by glyoxalation, to increase the reactivity [111]. Both modifications resulted in UF resins with improved properties. Panels bonded with IL-modified lignin UF resins were superior, regarding mechanical strength, formaldehyde emission, and gel time. The effect of addition of polymeric 4,4-diphenylmethane diisocyanate (pMDI) liquid to (IL)-treated lignin-urea-formaldehyde resin on the physical and mechanical properties of plywood panels ionic have been investigated [112]. The addition of pMDI enhanced the performance of lignin-UF resins for wood-based panels.

Lignin-based adhesives have been formulated by substituting all phenols with unmodified lignin from corn stover in a PF resin. The mechanical strength of the evaluated adhesive system was similar to a commercial phenol-resorcinol-formaldehyde (PRF) adhesive reference [113]. Different industrial lignins, such as softwood Kraft lignins, have been evaluated in self-binding high-density fibreboards, of which some were found to perform well in dry conditions [114]. Lignin has also been blended with other bio-based polymers such as soybean protein and/or chitosan [32, 115]. Lignin amine was prepared by an efficient two-step process, in which lignin was oxidized through a Fenton oxidation reaction, followed by a reductive amination to yield lignin amine [32]. The soybean protein-lignin amine system exhibited high dry and wet strengths for plywood. The improved properties were attributed to the catechol-like functionalities in the system, mimicking marine adhesive proteins. Laccase-modified lignin, combined with either soybean protein or chitosan, followed by reduction with NaBH_4 was evaluated as cheap and safe adhesive systems [115]. The dry strength of the lignin-chitosan formulation was slightly improved when laccase-treated lignin was used, but the subsequent reduction drastically reduced the bonding strength. The laccase-treated and reduced lignin-soybean protein adhesive exhibited more than half the strength compared with a commercial polyurethane adhesive and showed good water resistance.

5. Tannin

Tannins are polyphenols that exist naturally in the bark of various trees such as mimosa, quebracho or pine [116–118]. Natural tannins are divided into two main classes: hydrolysable tannins and condensed polyflavonoid tannins. Condensed tannins constitute more than 90% of the total production of commercial tannins [119]. Tannins are water-soluble compounds [120], and similar to lignin [121], they are of particular interest in the replacement of phenolic resins owing to their chemical structure, similar to phenolic compounds, as well as the ability to react with formaldehyde [120].

The high reactivity toward aldehydes and other reagents renders tannins both chemically and economically interesting in the production of adhesives and resins [120]. However, the present use of commercial tannins for leather manufacturing [122], and beverages [123] limits their availability for other industrial resins. Despite this, tannins have been the subject of extensive

research, leading to the exploration of a wide range of adhesive applications [14, 101, 124]. Attempts have been made to commercialize tannin-based adhesives with limited success [125].

In a recent study, tannins have been suggested as scavengers for formaldehyde in MF resins. The formaldehyde emission was decreased with the addition of tannin [126]. The effect of addition of tannin in PF and MF resins was also studied, and the observed results were improved water resistance and decreased formaldehyde emission [127].

Tannins have also been used as a substitute for phenols in PF resins with promising results. Good characteristics and low formaldehyde emissions were obtained even though only a part of the phenol was replaced by tannin [116]. Noteworthy, curing agents used to prepare such adhesive systems, e.g., tris(hydroxymethyl)nitromethane, paraformaldehyde, hexamethylenetetramine, may cause formaldehyde emission [128, 129]. A hyperbranched polyamine ester was used as a curing agent together with tannin-glyoxalated Kraft lignin (TGKL) and evaluated as an adhesive [120]. The adhesive was evaluated on plywood and the results showed that the modification improved the water resistance strength of TGKL effectively. In another study, lignin-based aldehydes were combined with a reactive tannin from pine bark and evaluated as adhesive in wood panels. The performance was in accordance with relevant standards [130].

Boric acid (BA), a weak Lewis base, is known to induce tannin gelation [131]. Hexamine was used in tannin-BA adhesive systems to fixate BA through complexing onto the network, thus preventing leaching of BA. It is also reported that this treatment enhanced biological resistance [132]. Tannin has been explored for plywood applications by incorporating BA into the adhesive system to increase the hardening rate, thus decreasing press time [133]. The adhesive system was composed of quebracho tannin, NaOH, hexamine, BA, and polymeric isocyanate (pMDI). The results indicated that the addition of BA not only lowered time and temperature of hardening, which is of significant importance for the cost of production of wood composites, but also resulted in higher elastic modulus and good resistance to fungal attack.

Recently, tannin adhesives have also been studied in the preparation of particleboards [122, 134, 135]. Internal bond (IB) strengths of the particleboards were investigated with different tannin-based adhesive formulations [122]. It is reported that particleboards manufactured with the formulation containing paraformaldehyde powder as a hardener exhibited the best IB strength. A formaldehyde-free adhesive based on tannin for manufacturing of particleboards has also been developed [134]. The effect of type and concentration of hardeners was investigated. Tris(hydroxymethyl)nitromethane (TRIS), glyoxal (GLY), and hexamethylenetetramine (HEX) were used as hardener instead of formaldehyde. Condensed chestnut-shell tannins could be combined with low proportions of chestnut bur or eucalyptus bark without reducing board quality. The formaldehyde emission level was low.

Glulam from three layers of lamina has been manufactured by using a mahogany tannin-adhesive system, composed of tannin extract and formaldehyde [124]. The results showed that the adhesive was on par with the conventional adhesive for glulam manufacturing regarding mechanical and physical properties, and had low formaldehyde emission. In a more recent study [136], an adhesive of mimosa tannin, mixed with the *Eremurus* root (syrsh), was prepared to manufacture three-layer particleboards, yielding a fully green product. The addition of syrsh improved the overall performance of the mimosa tannin adhesive system.

6. Outlook

The industry's transition to fully green wood adhesives, i.e., based solely on sustainable bio-polymers, will most likely linger for quite some time. Still, substantial challenges remain to develop bio-based adhesives that fulfill all the prerequisites for both indoor and outdoor applications. Water resistance is one area that is particularly challenging; the general, inherent hydrophilic character of most bio-polymers has to be tampered in such a way that the final adhesive bond is able to withstand both humidity and water sufficiently. There are already promising solutions on how to tackle this, but so far it has almost only been demonstrated on a lab scale and not for large-scale productions. Bio-polymers are also encompassed with large natural variations (molecular weight, solubility, etc.) as an effect of shifting growth conditions which bring about a need for a greater flexibility in the production line, either when manufacturing the adhesive or when conducting the actual bonding. On a lab scale, this is usually manageable but it rapidly becomes a problem when targeting large-scale manufacturing. However, there is light in the tunnel. Hybrid adhesive systems, partly composed of bio-based polymers, already exist and suggest that the transition to greener adhesive systems will occur gradually. Stricter legislations and tougher social expectations are believed to accelerate this development. It is, however, challenged by manufacturers' and end-users' unwillingness to pay more for a greener adhesive, when the transition has to be justified by a neutral cost performance and/or improved final properties. For researchers around the world, the field of green adhesives is an exciting area to be active in. Fundamental research is still required in order to develop detailed understanding of the complex adhesion mechanisms that govern strong bonding between adhesive and substrates. A better understanding will propel the future design of green adhesive systems, and scientific breakthroughs may have a substantial impact on a large industrial sector.

Acknowledgements

This study was supported by VINNOVA VINN Excellence Centre BiMaC Innovation, and Wobama WoodWisdom –Net ERA-NET/Formas.

Author details

Emelie Norström¹, Deniz Demircan¹, Linda Fogelström¹, Farideh Khabbaz² and Eva Malmström^{1*}

*Address all correspondence to: mavem@kth.se

¹ Department of Fibre and Polymer Technology, School of Chemical Science and Engineering, KTH Royal Institute of Technology, Stockholm, Sweden

² AkzoNobel Adhesives AB, Årsta, Sweden

References

- [1] Frihart CR. Wood adhesion and adhesives. In: Rowell RM, editor. *Handbook of Wood Chemistry and Wood Composites*. Florida: CRS Press; 2005. pp. 215-278
- [2] Akzo Nobel Adhesives. History. 2017. Available from: <https://www.akzonobel.com/adhesives/aboutus/history/>
- [3] Lambuth AL. Protein adhesives for wood. In: Pizzi A, Mittal KL, editors. *Handbook of Adhesive Technology*. Second ed. New York: Marcel Dekker, Inc; 2003. pp. 457-477
- [4] Bye CN. Casein and mixed protein adhesives. In: Skeist I, editor. *Handbook of Adhesives*. New York: Van Nostrand Reinold; 1990. pp. 135-152
- [5] EPA United States Environmental Protection Agency. EPA Issues Final Rule to Protect the Public from Exposure to Formaldehyde, 2017. Available from: <https://www.epa.gov/newsreleases/epa-issues-final-rule-protect-public-exposure-formaldehyde>
- [6] WFP FN:s livsmedelsprogram. Hunger 2017. 2017. Available from: <http://sv.wfp.org/hunger/fr%C3%A5gor-om-hunger>
- [7] Teleman A. Hemicelluloses and pectins. In: Gellerstedt G, editor. *The Ljungberg Textbook Wood Chemistry and Wood Biotechnology*. Stockholm; 2009. pp. 87-108
- [8] Photocredits for pictures of particleboard and plywood distributed by a CC-BY-SA 3.0 license. 2017. Available from: https://commons.wikimedia.org/wiki/File%3ABirch_plywood.jpg; <https://commons.wikimedia.org/wiki/File%3AParticleboard.jpg>
- [9] Frihart CR. Adhesive bonding and performance testing of bonded wood products. *Journal of ASTM International*. 2005;**2**(7):1-1
- [10] Pizzi A, Mittal KL. *Wood Adhesives*. Boston: CRC Press; 2010
- [11] Stoeckel F, Konnerth J, Gindl-Altmutter W. Mechanical properties of adhesives for bonding wood—A review. *International Journal of Adhesion and Adhesives*. 2013;**45**:32-41
- [12] Nelson DL, Cox MM, Lehninger AL. *Lehninger's principles of biochemistry*. 4th ed. New York: Freeman WH; NY, USA, 2005. 75 p
- [13] Vnucic D, Kutnar A, Gorsek A. Soy-based adhesives for wood-bonding—A review. *Journal of Adhesion Science and Technology*. 2017;**31**(8):910-931
- [14] Hemmilä V, Adamopoulos S, Karlsson O, Kumar A. Development of sustainable bio-adhesives for engineered wood panels—A review. *RSC Advances*. 2017;**7**(61):38604-38630
- [15] Ferdosian F, Pan Z, Gao G, Zhao B. Bio-based adhesives and evaluation for wood composites application. *Polymers (Basel, Switz)*. 2017;**9**(2):70/1-/29
- [16] Kumar R, Choudhary V, Mishra S, Varma IK, Mattiason B. Adhesives and plastics based on soy protein products. *Industrial Crops and Products*. 2002;**16**(3):155-172

- [17] North Carolina Soybean Production Association. Uses of soybeans. 2017. Available from: <http://ncsoy.org/media-resources/uses-of-soybeans/>
- [18] Solenis. Soyad™ Adhesive Technology. 2017. Available from: <https://solenis.com/en/industries/specialties-wood-adhesives/innovations/soyad-adhesive-technology/>
- [19] Sun XS. Thermal and mechanical properties of soy proteins. In: Wool R, Sun XS, editors. *Bio-Based Polymers and Composites*. United States: Elsevier Inc; 2005. pp. 292-326
- [20] Fan B, Zhang LP, Gao ZH, Zhang Y, Shi J, Li J. Formulation of a novel soybean protein-based wood adhesive with desired water resistance and technological applicability. *Journal of Applied Polymer Science*. 2016;**133**(27) n/a
- [21] Zhang B, Fan B, Huo P, Gao Z-H. Improvement of the water resistance of soybean protein-based wood adhesive by a thermo-chemical treatment approach. *International Journal of Adhesion and Adhesives*. 2017;**78**:222-226
- [22] Zeng N, Xie J, Ding C. Properties of the soy protein isolate/PVAc latex blend adhesives. *Advanced Materials Research (Durnten-Zurich, Switzerland)*. 2012;**550-553**(Pt. 2, *Advances in Chemical Engineering II*):1103-7
- [23] Luo J, Li L, Luo J, Li X, Li K, Gao Q. A high solid content bioadhesive derived from soybean meal and egg white: Preparation and properties. *Journal of Polymers and the Environment*. 2017;**25**(3):948-959
- [24] Yuan C, Chen M, Luo J, Li X, Gao Q, Li J. A novel water-based process produces eco-friendly bio-adhesive made from green cross-linked soybean soluble polysaccharide and soy protein. *Carbohydrate Polymers*. 2017;**169**:417-425
- [25] Zheng P, Li Y, Li F, Ou Y, Lin Q, Chen N. Development of defatted soy flour-based adhesives by acid hydrolysis of carbohydrates. *Polymers (Basel, Switz)*. 2017;**9**(5):153/1-12
- [26] Jang Y, Li K. An all-natural adhesive for bonding wood. *Journal of the American Oil Chemists' Society*. 2015;**92**(3):431-438
- [27] Luo J, Li C, Li X, Luo J, Gao Q, Li J. A new soybean meal-based bioadhesive enhanced with 5,5-dimethyl hydantoin polyepoxide for the improved water resistance of plywood. *RSC Advances*. 2015;**5**(77):62957-62965
- [28] Wang F, Wang J, Wang C, Chu F, Liu X, Pang J. Fabrication of soybean protein-acrylate composite mini-emulsion toward wood adhesive. *European Journal of Wood and Wood Products*. 2017: Ahead of Print
- [29] Chen M, Chen Y, Zhou X, Lu B, He M, Sun S, et al. Improving water resistance of soy-protein wood adhesive by using hydrophilic additives. *BioResources*. 2015;**10**(1):41-54, 14 pp
- [30] Luo J, Luo J, Yuan C, Zhang W, Li J, Gao Q, et al. An eco-friendly wood adhesive from soy protein and lignin: Performance properties. *RSC Advances*. 2015;**5**(122):100849-100855
- [31] Pradyawong S, Qi G, Li N, Sun XS, Wang D. Adhesion properties of soy protein adhesives enhanced by biomass lignin. *International Journal of Adhesion and Adhesives*. 2017;**75**:66-73

- [32] Xin J, Zhang P, Wolcott MP, Zhang J, Hiscox WC, Zhang X. A novel and formaldehyde-free preparation method for lignin amine and its enhancement for soy protein adhesive. *Journal of Polymers and the Environment*. 2017;**25**(3):599-605
- [33] Cheng HN, Ford C, Dowd MK, He Z. Soy and cottonseed protein blends as wood adhesives. *Industrial Crops and Products*. 2016;**85**:324-330
- [34] D'Amico S, Mueller U, Berghofer E. Effect of hydrolysis and denaturation of wheat gluten on adhesive bond strength of wood joints. *Journal of Applied Polymer Science*. 2013;**129**:2429-2434
- [35] El-Wakil NA, Abou-Zeid RE, Fahmy Y, Mohamed AY. Modified wheat gluten as a binder in particleboard made from reed. *Journal of Applied Polymer Science*. 2007;**106**:3592-3599
- [36] Khosravi S, Nordqvist P, Khabbaz F, Oehman C, Bjurhager I, Johansson M. Wetting and film formation of wheat gluten dispersions applied to wood substrates as particle board adhesives. *European Polymer Journal*. 2015;**67**:476-482
- [37] Khosravi S, Khabbaz F, Nordqvist P, Johansson M. Wheat-gluten-based adhesives for particle boards: Effect of crosslinking agents. *Macromolecular Materials and Engineering*. 2014;**299**:116-124
- [38] Khosravi S, Khabbaz F, Nordqvist P, Johansson M. Protein-based adhesives for particleboards. *Industrial Crops and Products*. 2010;**32**:275-283
- [39] Khosravi S, Nordqvist P, Khabbaz F, Johansson M. Protein-based adhesives for particleboards-effect of application process. *Industrial Crops and Products*. 2011;**34**:1509-1515
- [40] Lei H, Pizzi A, Navarrete P, Rigolet S, Redl A, Wagner A. Gluten protein adhesives for wood panels. *Journal of Adhesion Science and Technology*. 2010;**24**:1583-1596
- [41] Nordqvist P, Khabbaz F, Malmström E. Comparing bond strength and water resistance of alkali-modified soy protein isolate and wheat gluten adhesives. *International Journal of Adhesion and Adhesives*. 2010;**30**:72-79
- [42] Nordqvist P, Lawther M, Malmström E, Khabbaz F. Adhesive properties of wheat gluten after enzymatic hydrolysis or heat treatment—A comparative study. *Industrial Crops and Products*. 2012;**38**:139-145
- [43] Nordqvist P, Nordgren N, Khabbaz F, Malmström E. Plant proteins as wood adhesives: Bonding performance at the macro- and nanoscale. *Industrial Crops and Products*. 2013;**44**:246-252
- [44] Nordqvist P, Thedjil D, Khosravi S, Lawther M, Malmström E, Khabbaz F. Wheat gluten fractions as wood adhesives-glutenins versus gliadins. *Journal of Applied Polymer Science*. 2012;**123**:1530-1538
- [45] Santoni I, Pizzo B. Evaluation of alternative vegetable proteins as wood adhesives. *Industrial Crops and Products*. 2013;**45**:148-154
- [46] Bandara N, Esparza Y, Wu J. Exfoliating nanomaterials in canola protein derived adhesive improves strength and water resistance. *RSC Advances*. 2017;**7**(11):6743-6752

- [47] He Z, Chapital DC, Cheng HN, Dowd MK. Comparison of adhesive properties of water- and phosphate buffer-washed cottonseed meals with cottonseed protein isolate on maple and poplar veneers. *International Journal of Adhesion and Adhesives*. 2014;**50**:102-106
- [48] Bandara N, Chen L, Wu J. Adhesive properties of modified triticale distillers grain proteins. *International Journal of Adhesion and Adhesives*. 2013;**44**:122-129
- [49] Khabbaz F, inventor; Akzo Nobel Coatings International B.V., Neth.. assignee. Aqueous adhesive compositions containing lupin proteins and polymers patent WO2012076566A2. 2012
- [50] Huang J, Li K. Development and characterization of a formaldehyde-free adhesive from lupine flour, glycerol, and a novel curing agent for particleboard (PB) production. *Holzforschung*. 2016;**70**(10):927-935
- [51] Patel AK, Mathias J-D, Michaud P. Polysaccharides as adhesives: a critical review. *Reviews of Adhesion and Adhesives*. 2013;**1**(3):312-345
- [52] Gadhave RV, Mahanwar PA, Gadekar PT. Starch-based adhesives for wood/wood composite bonding: Review. *Open Journal of Polymer Chemistry*. 2017;**7**(2):19-32
- [53] Imam SH, Gordon SH, Mao L, Chen L. Environmentally friendly wood adhesive from a renewable plant polymer: Characteristics and optimization. *Polymer Degradation and Stability*. 2001;**73**:529-533
- [54] Wang Z, Li Z, Gu Z, Hong Y, Cheng L. Preparation, characterization and properties of starch-based wood adhesive. *Carbohydrate Polymers*. 2012;**88**:699-706
- [55] Wang Z, Gu Z, Hong Y, Cheng L, Li Z. Bonding strength and water resistance of starch-based wood adhesive improved by silica nanoparticles. *Carbohydrate Polymers*. 2011;**86**:72-76
- [56] Wu Y, Lv C, Han M. Synthesis and performance study of polybasic starch graft copolymerization function materials. *Advanced Materials Research (Durnten-Zurich, Switzerland)*. 2009;**79-82**:43-46
- [57] Wang P, Cheng L, Gu Z, Li Z, Hong Y. Assessment of starch-based wood adhesive quality by confocal Raman microscopic detection of reaction homogeneity. *Carbohydrate Polymers*. 2015;**131**:75-79
- [58] Cheng L, Guo H, Gu Z, Li Z, Hong Y. Effects of compound emulsifiers on properties of wood adhesive with high starch content. *International Journal of Adhesion and Adhesives*. 2017;**72**:92-97
- [59] Zheng X, Cheng L, Gu Z, Hong Y, Li Z, Li C. Effects of heat pretreatment of starch on graft copolymerization reaction and performance of resulting starch-based wood adhesive. *International Journal of Biological Macromolecules*. 2017;**96**:11-18
- [60] Zia ud D, Xiong H, Wang Z, Fei P, Ullah I, Javaid AB, et al. Effects of sucrose fatty acid esters on the stability and bonding performance of high amylose starch-based wood adhesive. *International Journal of Biological Macromolecules*. 2017;**104**(Part_A):846-53

- [61] Li Z, Wang J, Cheng L, Gu Z, Hong Y, Kowalczyk A. Improving the performance of starch-based wood adhesive by using sodium dodecyl sulfate. *Carbohydrate Polymers*. 2014;**99**:579-583
- [62] Li Z, Wang J, Li C, Gu Z, Cheng L, Hong Y. Effects of montmorillonite addition on the performance of starch-based wood adhesive. *Carbohydrate Polymers*. 2015;**115**:394-400
- [63] Wang Y, Xiong H, Wang Z, Zia ud D, Chen L. Effects of different durations of acid hydrolysis on the properties of starch-based wood adhesive. *International Journal of Biological Macromolecules*. 2017;**103**:819-828
- [64] Yu H, Fang Q, Cao Y, Liu Z. Effect of HCl on starch structure and properties of starch-based wood adhesives. *BioResources*. 2016;**11**(1):1721-1728
- [65] Zhang Y, Ding L, Gu J, Tan H, Zhu L. Preparation and properties of a starch-based wood adhesive with high bonding strength and water resistance. *Carbohydrate Polymers*. 2015;**115**:32-37
- [66] Sun J, Li L, Cheng H, Huang W. Preparation, characterization and properties of an organic siloxane-modified cassava starch-based wood adhesive. *The Journal of Adhesion*. 2016:1-16
- [67] Chen L, Wang Y, Zia ud D, Fei P, Jin W, Xiong H, et al. Enhancing the performance of starch-based wood adhesive by silane coupling agent(KH570). *International Journal of Biological Macromolecules*. 2017;**104**(Part_A):137-144
- [68] Qiao Z, Gu J, Lv S, Cao J, Tan H, Zhang Y. Preparation and properties of isocyanate prepolymer/corn starch adhesive. *Journal of Adhesion Science and Technology*. 2015;**29**(13):1368-1381
- [69] Qiao Z, Gu J, Lv S, Cao J, Tan H, Zhang Y. Preparation and properties of normal temperature cured starch-based wood adhesive. *BioResources*. 2016;**11**(2):4839-4849
- [70] Wang S-M, Shi J-Y, Xu W. Synthesis and characterization of starch-based aqueous polymer isocyanate wood adhesive. *BioResources*. 2015;**10**(4):7653-7666
- [71] Qiao Z, Gu J, Zuo Y, Tan H, Zhang Y. The effect of carboxymethyl cellulose addition on the properties of starch-based wood adhesive. *BioResources*. 2014;**9**(4):6117-6129, 13 pp
- [72] Zargar V, Asghari M, Dashti A. A review on chitin and chitosan polymers: Structure, chemistry, solubility, derivatives, and applications. *ChemBioEng Reviews*. 2015;**2**(3):204-226
- [73] Pantaleone D, Yalpani M, Scollar M. Unusual susceptibility of chitosan to enzymic hydrolysis. *Carbohydrate Research*. 1992;**237**:325-332
- [74] Dodane V, Vilivalam VD. Pharmaceutical applications of chitosan. *Pharmaceutical Science & Technology Today*. 1998;**1**(6):246-253
- [75] Hirano S. Chitin biotechnology applications. *Biotechnology Annual Review*. 1996;**2**:237-258

- [76] Sechriest VF, Miao YJ, Niyibizi C, Westerhausen-Larson A, Matthew HW, Evans CH, et al. GAG-augmented polysaccharide hydrogel: A novel biocompatible and biodegradable material to support chondrogenesis. *Journal of Biomedical Materials Research*. 2000;**49**(4):534-541
- [77] Mati-Baouche N, Elchinger P-H, de Baynast H, Pierre G, Delattre C, Michaud P. Chitosan as an adhesive. *European Polymer Journal*. 2014;**60**:198-212
- [78] Patel AK. Chitosan: Emergence as potent candidate for green adhesive market. *Biochemical Engineering Journal*. 2015;**102**:74-81
- [79] Patel AK, Michaud P, Petit E, de Baynast H, Grediac M, Mathias J-D. Development of a chitosan-based adhesive. Application to wood bonding. *Journal of Applied Polymer Science*. 2013;**127**(6):5014-5021
- [80] Cui Z, Beach ES, Anastas PT. Modification of chitosan films with environmentally benign reagents for increased water resistance. *Green Chemistry Letters and Reviews*. 2011;**4**(1):35-40
- [81] Domjan A, Bajdik J, Pintye-Hodi K. Understanding of the plasticizing effects of glycerol and PEG 400 on chitosan films using solid-state NMR spectroscopy. *Macromolecules*. 2009;**42**(13):4667-4673
- [82] Umemura K, Kawai S. Preparation and characterization of Maillard reacted chitosan films with hemicellulose model compounds. *Journal of Applied Polymer Science*. 2008;**108**(4):2481-2487
- [83] Umemura K, Kawai S. Modification of chitosan by the Maillard reaction using cellulose model compounds. *Carbohydrate Polymers*. 2007;**68**(2):242-248
- [84] Umemura K, Mihara A, Kawai S. Development of new natural polymer-based wood adhesives III: Effects of glucose addition on properties of chitosan. *Journal of Wood Science*. 2010;**56**(5):387-394
- [85] Umemura K, Inoue A, Kawai S. Development of new natural polymer-based wood adhesives I: Dry bond strength and water resistance of konjac glucomannan, chitosan, and their composites. *Journal of Wood Science*. 2003;**49**(3):221-226
- [86] Gu R, Mu B, Yang Y. Bond performance and structural characterization of polysaccharide wood adhesive made from Konjac glucomannan/chitosan/polyvinyl alcohol. *BioResources*. 2016;**11**(4):8166-8177
- [87] Shang J, Liu H, Qi C, Guo K, Tran VC. Evaluation of curing and thermal behaviors of konjac glucomannan-chitosan-polypeptide adhesive blends. *Journal of Applied Polymer Science*. 2015;**132**(34):n/a
- [88] Salam A, Venditti RA, Pawlak JJ, El-Tahlawy K. Crosslinked hemicellulose citrate-chitosan aerogel foams. *Carbohydrate Polymers*. 2011;**84**:1221-1229
- [89] Norström E, Fogelström L, Nordqvist P, Khabbaz F, Malmström E. Gum dispersions as environmentally friendly wood adhesives. *Industrial Crops and Products*. 2014;**52**:736-744

- [90] Araujo D, Alves VD, Campos J, Coelho I, Sevrin C, Grandfils C, et al. Assessment of the adhesive properties of the bacterial polysaccharide FucoPol. *International Journal of Biological Macromolecules*. 2016;**92**:383-389
- [91] Paiva D, Goncalves C, Vale I, Bastos MMSM, Magalhaes FD. Oxidized xanthan gum and chitosan as natural adhesives for cork. *Polymers (Basel, Switz)*. 2016;**8**(7):259/1-/13
- [92] Abuarra A, Hashim R, Bauk S, Kandaiya S, Tousi ET. Fabrication and characterization of gum Arabic bonded *Rhizophora* spp. particleboards. *Materials and Design*. 2014;**60**:108-115
- [93] Wang Y, Guo K-Q, Li J-N, Duan X-F, Li Y-J. Konjac glucomannan/chitosan based adhesive for plywood production. *China Wood Industry*. 2009;**23**(2):13-15
- [94] Norstroem E, Fogelstroem L, Nordqvist P, Khabbaz F, Malmstroem E. Xylan—A green binder for wood adhesives. *European Polymer Journal*. 2015;**67**:483-493
- [95] Younesi-Kordkheili H. Improving physical and mechanical properties of new lignin-urea-glyoxal resin by nanoclay. *European Journal of Wood and Wood Products*. 2017:1-7
- [96] Fu D, Mazza G, Tamaki Y. Lignin extraction from straw by ionic liquids and enzymatic hydrolysis of the cellulosic residues. *Journal of Agricultural and Food Chemistry*. 2010;**58**(5):2915-2922
- [97] Khalil HSA, Alwani MS, Omar AKM. Chemical composition, anatomy, lignin distribution, and cell wall structure of Malaysian plant waste fibers. *BioResources*. 2007;**1**(2):220-232
- [98] Kirk TK a, Farrell RL. Enzymatic “combustion”: The microbial degradation of lignin. *Annual Review of Microbiology* 1987;**41**(1):465-501
- [99] Laurichesse S, Averous L. Chemical modification of lignins: Towards biobased polymers. *Progress in Polymer Science*. 2014;**39**(7):1266-1290
- [100] Ghaffar SH, Fan M. Lignin in straw and its applications as an adhesive. *International Journal of Adhesion and Adhesives*. 2014;**48**:92-101
- [101] Pizzi A. Recent developments in eco-efficient bio-based adhesives for wood bonding: Opportunities and issues. *Journal of Adhesion Science and Technology*. 2006;**20**:829-846
- [102] Ibrahim MNM, Zakaria N, Sipaut CS, Sulaiman O, Hashim R. Chemical and thermal properties of lignins from oil palm biomass as a substitute for phenol in a phenol formaldehyde resin production. *Carbohydrate Polymers*. 2011;**86**(1):112-119
- [103] Podschun J, Stücker A, Buchholz RI, Heitmann M, Schreiber A, Saake B, et al. Phenolated lignins as reactive precursors in wood veneer and particleboard adhesion. *Industrial and Engineering Chemistry Research*. 2016;**55**(18):5231-5237
- [104] Shimatani K, Sano Y, Sasaya T. Preparation of moderate-temperature setting adhesives from softwood Kraft lignin. Part 2. Effect of some factors on strength properties and characteristics of lignin-based adhesives. *Holzforschung*. 1994;**48**(4):337-342

- [105] Yang S, Zhang Y, Yuan TQ, Sun RC. Lignin–phenol–formaldehyde resin adhesives prepared with biorefinery technical lignins. *Journal of Applied Polymer Science*. 2015;**132**(36)
- [106] El Mansouri NE, Yuan Q, Huang F. Synthesis and characterization of kraft lignin-based epoxy resins. *BioResources*. 2011;**6**(3):2492-2503
- [107] Stewart D. Lignin as a base material for materials applications: Chemistry, application and economics. *Industrial Crops and Products*. 2008;**27**(2):202-207
- [108] Qin J, Wolcott M, Zhang J. Use of polycarboxylic acid derived from partially depolymerized lignin as a curing agent for epoxy application. *ACS Sustainable Chemistry & Engineering*. 2013;**2**(2):188-193
- [109] Tachon N, Benjelloun-Mlayah B, Delmas M. Organosolv wheat straw lignin as a phenol substitute for green phenolic resins. *BioResources*. 2016;**11**(3):5797-5815
- [110] Younesi-Kordkheili H, Pizzi A, Niyatzade G. Reduction of formaldehyde emission from particleboard by phenolated kraft lignin. *The Journal of Adhesion*. 2016;**92**(6):485-497
- [111] Younesi-Kordkheili H, Pizzi A. A comparison between lignin modified by ionic liquids and glyoxalated lignin as modifiers of urea-formaldehyde resin. *The Journal of Adhesion*. 2016:1-11
- [112] Younesi-Kordkheili H, Pizzi A, Mohammadghasemipour A. Improving the properties of ionic liquid-treated lignin-urea-formaldehyde resins by a small addition of isocyanate for wood adhesive. *The Journal of Adhesion*. 2017:1-14
- [113] Kalami S, Arefmanesh M, Master E, Nejad M. Replacing 100% of phenol in phenolic adhesive formulations with lignin. *Journal of Applied Polymer Science*. 2017;**134**(30):n/a
- [114] Tupciauskas R, Gravitis J, Abolins J, Veveris A, Andzs M, Liitia T, et al. Utilization of lignin powder for manufacturing self-binding HDF. *Holzforschung*. 2017;**71**(7-8):555-561
- [115] Ibrahim V, Mamo G, Gustafsson P-J, Hatti-Kaul R. Production and properties of adhesives formulated from laccase modified Kraft lignin. *Industrial Crops and Products*. 2013;**45**:343-348
- [116] Kim S. Environment-friendly adhesives for surface bonding of wood-based flooring using natural tannin to reduce formaldehyde and TVOC emission. *Bioresource Technology*. 2009;**100**(2):744-748
- [117] Pinto PC, Sousa G, Crispim F, Silvestre AJ, Neto CP. Eucalyptus globulus bark as source of tannin extracts for application in leather industry. *ACS Sustainable Chemistry & Engineering*. 2013;**1**(8):950-955
- [118] Fechtal M, Riedl B. Use of eucalyptus and Acacia mollissima bark extract-formaldehyde adhesives in particleboard manufacture. *Holzforschung*. 1993;**47**(4):349-357
- [119] Pizzi A. Types, processing and properties of bioadhesives for wood and fibers. In: Waldron KW, editor. *Advances in Biorefineries: Biomass and Waste Supply Chain Exploitation*. Amsterdam: Elsevier; 2014. pp. 736-771

- [120] Faris AH, Ibrahim MNM, Rahim AA. Preparation and characterization of green adhesives using modified tannin and hyperbranched poly(amine-ester). *International Journal of Adhesion and Adhesives*. 2016;**71**:39-47
- [121] Faris AH, Rahim AA, Ibrahim MNM, Hussin MH, Alkurdi AM, Salehabadi A. Investigation of oil palm based Kraft and auto-catalyzed organosolv lignin susceptibility as a green wood adhesives. *International Journal of Adhesion and Adhesives*. 2017;**74**:115-122
- [122] Konai N, Pizzi A, Raidandi D, Lagel M, L'Hostis C, Saidou C, et al. Aningre (*Aningeria* spp.) tannin extract characterization and performance as an adhesive resin. *Industrial Crops and Products*. 2015;**77**:225-231
- [123] Harbertson JF, Parpinello GP, Heymann H, Downey MO. Impact of exogenous tannin additions on wine chemistry and wine sensory character. *Food Chemistry*. 2012;**131**(3):999-1008
- [124] Lestari ASRD, Hadi YS, Hermawan D, Santoso A. Glulam properties of fast-growing species using mahogany tannin adhesive. *BioResources*. 2015;**10**(4):7419-7433
- [125] Pizzi A. Wood products and green chemistry. *Annals of Forest Science*. 2016;**73**(1):185-203
- [126] Kim S, Kim HJ, Kim HS, Lee HH. Effect of bio-scavengers on the curing behavior and bonding properties of melamine-formaldehyde resins. *Macromolecular Materials and Engineering*. 2006;**291**(9):1027-1034
- [127] Gangi M, Tabarsa T, Sepahvand S, Asghari J. Reduction of formaldehyde emission from plywood. *Journal of Adhesion Science and Technology*. 2013;**27**(13):1407-1417
- [128] Kim S, Kim H-J. Curing behavior and viscoelastic properties of pine and wattle tannin-based adhesives studied by dynamic mechanical thermal analysis and FT-IR-ATR spectroscopy. *Journal of Adhesion Science and Technology*. 2003;**17**(10):1369-1383
- [129] Trosa A, Pizzi A. A no-aldehyde emission hardener for tannin-based wood adhesives for exterior panels. *Holz als Roh- und Werkstoff*. 2001;**59**(4):266-271
- [130] Santiago-Medina F, Foyer G, Pizzi A, Caillol S, Delmotte L. Lignin-derived non-toxic aldehydes for ecofriendly tannin adhesives for wood panels. *International Journal of Adhesion and Adhesives*. 2016;**70**:239-248
- [131] Thevenon M-F, Tondi G, Pizzi A. High performance tannin resin-boron wood preservatives for outdoor end-uses. *European Journal of Wood and Wood Products*. 2009;**67**(1):89-93
- [132] Tondi G, Wieland S, Lemenager N, Petutschnigg A, Pizzi A, Thevenon M-F. Efficacy of tannin in fixing boron in wood. *BioResources*. 2012;**7**(1):1238-1252
- [133] Efhamisisi D, Thevenon M-F, Hamzeh Y, Karimi A-N, Pizzi A, Pourtahmasi K. Induced tannin adhesive by boric acid addition and its effect on bonding quality and biological performance of poplar plywood. *ACS Sustainable Chemistry & Engineering*. 2016;**4**(5):2734-2740

- [134] Santos J, Antorrena G, Freire MS, Pizzi A, González-Álvarez J. Environmentally friendly wood adhesives based on chestnut (*Castanea sativa*) shell tannins. *European Journal of Wood and Wood Products*. 2017;**75**(1):89-100
- [135] Fitzken Da Vinci M, Niro J, Kyriazopoulos M, Bianchi S, Mayer I, Eusebio DA, Arboleda JR, et al. Development of medium- and low-density fibreboards made of coconut husk and bound with tannin-based adhesives. *International Wood Products Journal*. 2016;**7**(4): 208-214
- [136] Eghtedarnejad N, Mansouri HR. Building wooden panels glued with a combination of natural adhesive of tannin/Eremurus root (syrish). *European Journal of Wood and Wood Products*. 2016;**74**(2):269-272

