

High Accuracy Dispersion Measurements of Chirped Fibre Gratings

S Barcelos, M N Zervas, R I Laming, D N Payne, L Reekie, J A Tucknott,

R Kashyap*, P F McKee*, F Sladen** and B Wojciechowicz**

Optoelectronics Research Centre, University of Southampton,

Southampton, SO17 1BJ, UK; Fax: +44 1703 593149; Email: sb2@orc.soton.ac.uk

* British Telecom Laboratories, Martlesham Heath, Ipswich, IP5 7RE, UK

** York Technology Inc., Research Park, 139 Wall Street, Princeton NJ 08540, USA

Abstract

A wavelength scanning interferometric technique has been used to provide phase dispersion and time delay measurements of photorefractive fibre gratings with sub-picosecond time-delay and 3pm wavelength resolutions for the first time. Chirped fibre grating filters for dispersion compensation in long fibre telecommunications links have been fully characterised.

1. Introduction

The development of chirped fibre gratings for dispersion compensation requires full and accurate amplitude and phase dispersion characterisation of these devices. We have recently demonstrated such a system based on an all-fibre Michelson interferometer [1]. The reference arm of the interferometer is phase-modulated with a saw-tooth function to generate an electric signal at the photodetector which carries the optical phase and amplitude information of the reflective fibre device under test, which is included in the other arm of the interferometer. The amplitude response of the interferometer is directly proportional to the field reflection coefficient. The time delay is given by the derivative of the relative phase with respect to wavelength. A high wavelength resolution tunable laser source (HP8168A/C) is used in conjunction with a fully automated set-up to provide sub-picosecond resolution. The interferometer is stabilised to

minimise temperature-dependent phase drifts [1]. Reflected and transmitted power are measured non-interferometrically, by blocking the reference arm of the interferometer. In this paper, we present measurements for different chirped fibre Bragg gratings, discuss the system resolution, and compare the results with an alternative direct group-delay measurement technique.

2. Experimental Results and Discussions

The set-up was used to measure the reflectivity/transmissivity and the phase-dispersion/time-delay characteristics of a wide-bandwidth step-chirped fibre grating fabricated at BT labs [2], as well as, a narrow-bandwidth externally-chirped fibre grating fabricated at Southampton. The first one was made using the phase-mask technique [2] and was 8mm long. Its 3dB reflection bandwidth was 14nm and the peak reflectivity 67%. The second was made using a holographic technique [3] and was 40mm long. At room temperature, its 3dB bandwidth and peak reflectivity were 0.09 nm and 31%, respectively. Variable amounts of chirp were externally induced in this grating by applying different temperature gradients to it.

Figure 1 shows the experimental results for the 8mm long chirped grating. Figure 1(a) shows the transmitted power and phase response of the reflected field. It clearly demonstrates that the relative phase varies parabolically with wavelength, corresponding on average to a quasi-linear decrease of the time delay (figure 1(b)) across the reflection bandwidth (i.e., negative dispersion). The wavelength instability of the tunable laser source combined with the wavelength dependent path imbalance of the interferometer contributes to the noise in the time delay curve, which obviously increases away from the centre of the grating. From these measurements, the rms frequency noise of the laser is estimated to be around a GHz. Lower noise lasers should improve this technique. An averaged version of this data is shown in figure 1(c). As predicted by theory [4], small ripples are observed at the edges of the time delay curve. By adjusting the optical path difference between the interferometer arms, we can accurately vary the DC offset of the time delay slope to within 0.5ps ($\sim 1^\circ$), which demonstrates the sub-

picosecond time delay resolution of our experimental set-up. Measurement of the grating in the reverse direction showed an identical dispersion characteristic but, as expected, of opposite sign. The dispersion of this grating was measured to be ± 4.35 ps/nm. A similar grating has been used for dispersion compensation of 400 fs pulses with recompression ratio greater than 0.98 [5], indicating the high quality of its linear dispersion characteristics and accuracy of our technique. The grating of figure 1 was also measured using an instrument designed for high-accuracy measurements of fibre chromatic dispersion (York S19). This instrument measures the group-delay directly, as compared to the interferometric technique, which measures the phase delay [6,7]. Figure 1(c) shows the results which are also in very good agreement with our interferometric measurements.

Figures 2-3 are related to the narrow-band 40mm long holographic grating. Different temperature gradients were applied to it in order to induce variable external chirp. The gradient was achieved by placing the grating in a 45mm long V-groove made on an aluminium slab, and heating its left and right sides with two separate peltier elements. Although, the grating was slightly pre-chirped in the fabrication process, we were able to cancel the built-in chirp and achieve the narrowest bandwidth with the temperature gradient of figure 2. Further increasing the temperature gradient (fig 3(a)), the grating spectrum broadens, its peak reflectivity reduces and a positive time delay slope of +1200 ps/nm is induced. Reversing the temperature gradient (fig 3(b)), the chirp is reversed and the delay slope changes sign. Spectral broadening and decrease in the peak reflectivity are also observed (c.f. fig 2). The measured dispersion in this case is -1100 ps/nm. The ripples in the delay slope edges are in good agreement with theoretical predictions [4].

3. Conclusions

We have demonstrated an interferometric technique capable of measuring the dispersion of fibre gratings with sub-picosecond time-delay and 3pm wavelength resolutions. Measurements of a

wide-bandwidth step-chirped fibre grating indicate its high quality linear dispersion characteristic. Measurements of a narrow-bandwidth externally-chirped fibre grating indicate that by applying variable temperature gradients to a 4 cm long grating, useful dispersion up to ± 2050 ps/nm (3-dB bandwidth = 0.08nm) can be induced, which is capable of compensating the dispersion of over 120 km of standard telecom fibre. Our results are very repeatable and have proved to be in very good agreement with other time delay measuring techniques, as well as with theory [4] and recent system measurements [8]. The wavelength resolution and instability of the tunable laser source are the main source of noise and major limitation in our measurements.

4. Acknowledgements

S Barcelos acknowledges the support of the Brazilian National Council for Science and Technology (CNPq) and R I Laming acknowledges the Royal Society for provision of a Research fellowship. This work has been supported by Pirelli Cavi SpA.

5. References

- [1] S Barcelos, M N Zervas, R I Laming and D N Payne; "Interferometric Fibre Grating Characterization"; IEE Colloquium on Fibre Gratings and their Applications, London, UK, 30 January 95.
- [2] R Kashyap, P F McKee, R J Campbell & D L Williams; "A novel method of writing photo-induced chirped Bragg gratings in optical fibres"; *Elect. Lett.* 30(12), 996, 1994.
- [3] G Meltz, W W Morey and W H Glenn; "Formation of Bragg gratings in optical fibres by a transverse holographic method", *Opt. Lett.*, 14 (15), pp. 823-825, 1989.
- [4] M N Zervas, D Taverner, S Barcelos and R I Laming; "Study of Linearly-Chirped Fibre Gratings"; National Quantum Electronics Conference, QE-12, Southampton, UK, 4-8 September 1995.
- [5] R Kashyap, S V Chernikov, P F McKee & J R Taylor; "30ps chromatic dispersion compensation of 400fs pulses at 100Gbit/s using an all fibre photoinduced chirped reflection grating"; *Elect. Lett.* 30(13), 1078, 1994.
- [6] R Kashyap & M H Reeve; "Single-ended fibre strain and length measurement in frequency domain"; *Elect. Lett* 16(18), 689, 1980.
- [7] S19 Chromatic Dispersion Measurement System, York Technology Inc., instrument specifications.
- [8] R I Laming, N Robinson, P L Scrivener, S Barcelos, M N Zervas; "A dispersion tunable grating in a 10Gbit/s 100-220km step index fibre link". European Conference on Optical Communications, ECOC'95, Brussels, Belgium, September 95.

Figure Captions

Figure 1: Experimental results for the 8mm long wide-bandwidth step-chirped fibre Bragg grating: (a) transmitted power (a.u. = arbitrary units) and interferometric phase response of the reflected field (reflection coefficient); (b) time delay response; (c) averaged time delay and measurement results using the York S19 instrument.

Figure 2: (a) Reflected power and (b) time delay response of the 40mm long fibre grating for a temperature gradient of $15^{\circ}\text{C}/45\text{mm}$.

Figure 3: Grating responses for two different temperature gradients; (a) $50^{\circ}\text{C}/45\text{mm}$ and (b) $-25^{\circ}\text{C}/45\text{mm}$. The 3dB bandwidth and dispersion are 0.216nm and $\sim -1200\text{ps}/\text{nm}$, and 0.228nm and $\sim -1100\text{ps}/\text{nm}$, respectively.

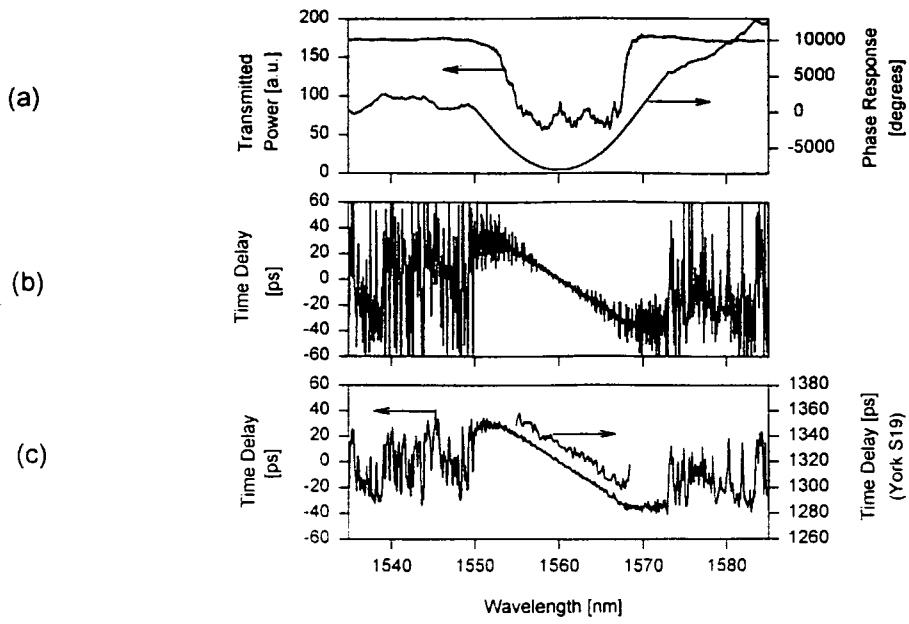


Figure 1

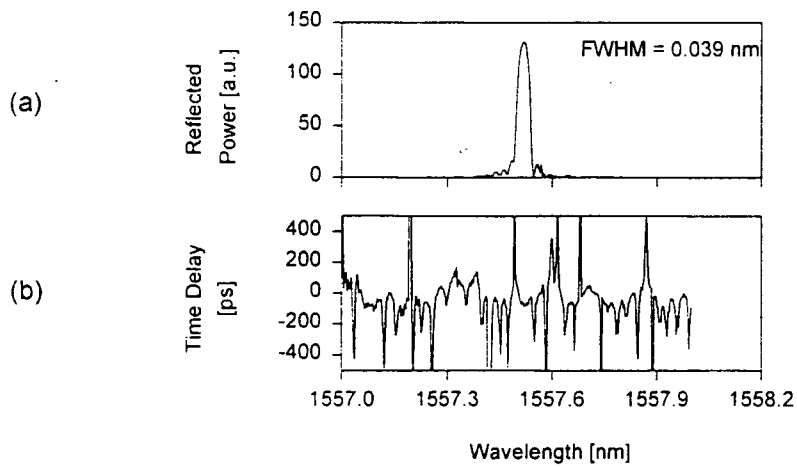


Figure 2

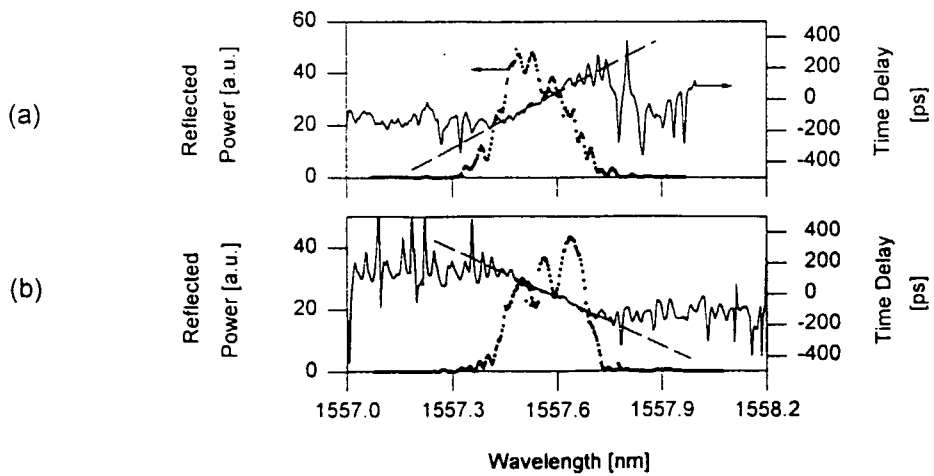


Figure 3