

## Hydrogen diffusivity in FeAl

**P BANERJEE and R BALASUBRAMANIAM\***

Department of Materials and Metallurgical Engineering, Indian Institute of Technology, Kanpur 208 016, India

MS received 11 February 1997

**Abstract.** The room temperature diffusivity of hydrogen in a fully B2 ordered iron aluminide of composition Fe–35.8 Al was estimated from the experimental hydrogen depth profile to be  $2.38 \times 10^{-15} \text{ m}^2/\text{s}$ . The mathematical procedure utilized for data analysis has been described. The estimated diffusivity is a lower bound value due to surface trapping effects.

**Keywords.** Hydrogen diffusivity; iron aluminide; FeAl; mathematical analysis.

### 1. Introduction

It is well known that iron aluminides exhibit poor room temperature ductilities due to hydrogen embrittlement (Liu *et al* 1989). Hydrogen is produced on the surface due to the reaction of moisture with the base iron aluminide and the nascent hydrogen enters the lattice to cause embrittlement (Agarwal and Balasubramaniam 1996). One of the important factors that needs to be understood is the diffusivity of hydrogen in iron aluminides.


Zhu *et al* (1996) recently provided direct evidence for the production of hydrogen by reaction of moisture with iron aluminide FeAl (Fe–35.8 at % Al) surfaces. Having provided heat treatments to obtain FeAl in a fully recrystallized ordered B2 structure, they used a laser desorption mass spectrometric method to detect the presence of hydrogen after contact of iron aluminide with water or after cathodic hydrogen charging. With the aid of pulsed-laser material removal, they were also able to obtain the three dimensional distribution of trapped hydrogen atoms as a function of depth from the surface after the iron aluminide was cathodically charged with hydrogen for one day in 1N H<sub>2</sub>SO<sub>4</sub>. They reported the strength of the hydrogen signal (in mV) that was obtained in their spectrometer as a function of depth in figure 3 of their paper. The aim of the present paper is to determine the diffusivity of hydrogen in FeAl using this published data.

### 2. Diffusivity estimation procedure

The experimental data of Zhu *et al* (1996) on hydrogen distribution as a function depth from the surface is provided in figure 1. The data exhibits a lot of scatter especially after a depth of 20 μm from the surface. The variation of H signal (denoted henceforth as H<sub>Y</sub>s) from surface to bulk is due to the diffusing species (hydrogen) as no hydrogen signal is detected for the uncharged specimens or for specimens not exposed to water (Zhu *et al* 1996). Assuming  $(C - C_b)$  to be proportional to increase in hydrogen signal over the bulk value, i.e.  $H_{Ys} - H_{Ys_b}$ , we obtain

$$\frac{C - C_b}{C_s - C_b} = \frac{H_{Ys} - H_{Ys_b}}{H_{Ys_s} - H_{Ys_b}} \quad (1)$$

\*Author for correspondence

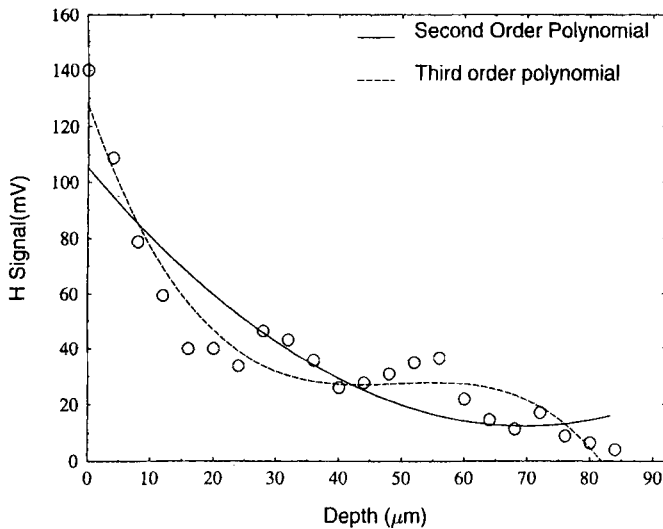

**Figure 1.** Data of Zhu *et al* (1996) showing experimental data of the strength of the hydrogen signal measured by laser desorption mass spectrometry as a function of depth in Fe-35.8 Al. The specimen was cathodically charged with hydrogen in 1N sulphuric acid for 1 day prior to the experiment.

where  $C_s$  is the surface concentration of diffusing species,  $C_b$  the bulk concentration of diffusing species and  $C$  the concentration of diffusing species at any point and subscripts b and s denote bulk and surface, respectively.

Since the specimen surfaces were flat and the depths of diffusion field were very small compared to thickness of samples (6350  $\mu\text{m}$  as provided by Zhu *et al* (1996)), the problem may be treated as unsteady diffusion through a semi-infinite flat specimen. By assuming that the diffusion occurred through a single phase, there was no internal phase formation in the diffusion field, the diffusion coefficient was constant in the entire diffusion zone, and the surface concentration is not a function of time, (1) can be combined with the standard diffusion equation to give

$$\frac{HY_s - HY_{s_b}}{HY_s - HY_{s_b}} = \frac{C - C_b}{C_s - C_b} = 1 - \operatorname{erf}\left(\frac{z}{2\sqrt{Dt}}\right) = \operatorname{erfc}\left(\frac{z}{2\sqrt{Dt}}\right). \quad (2)$$

The assumptions used in the above analysis are valid. First, it is known that the composition Fe-35.8 Al lies in the single phase region in the Fe-Al phase diagram and therefore the assumption of diffusion taking place in a single phase field is valid. Secondly, the heat treatments provided by Zhu *et al* (1996) resulted in a fully ordered B2 structure and therefore the presence of a second (disordered  $\alpha$  or ordered  $\text{DO}_3$ ) phase is also excluded. However, the assumption of constant surface concentration is not strictly valid because variations in the specimen potential generally occur during cathodic hydrogen charging. Therefore,  $C_s$  should be ideally eliminated from (2).  $C_s$  can be eliminated and the diffusion coefficient was determined using (2) by the following method (Roy *et al* 1996). A pair of points on the hydrogen signal vs depth curve was

chosen and the following parameter  $Y_{12}$  was obtained (for two given points 1 and 2) based on (2).

$$Y_{12} = \frac{(C_1 - C_b)/(C_s - C_b)}{(C_2 - C_b)/(C_s - C_b)} = \frac{C_1 - C_b}{C_2 - C_b} = \frac{\operatorname{erfc}(z_1/2\sqrt{Dt})}{\operatorname{erfc}(z_2/2\sqrt{Dt})} = \frac{(\text{HYS})_1 - (\text{HYS})_b}{(\text{HYS})_2 - (\text{HYS})_b}, \tag{3}$$

where  $(\text{HYS})_1$ ,  $(\text{HYS})_2$  and  $(\text{HYS})_b$  are the values of hydrogen signals and  $C_1$ ,  $C_2$  and  $C_b$  are the hydrogen concentrations at locations 1, 2 and in the bulk, respectively.  $D$  is the only unknown parameter in (3) for a given experiment. Equation (3) can be solved by using error function table and by trial and error solution.

As mentioned earlier, there is a lot of scatter in the experimental data after a depth of about 20  $\mu\text{m}$ . Therefore, the data was first mathematically analyzed. A quadratic fit of the data points provided a curve that could be drawn through the data points and this is shown in figure 1. The coefficient of fit in this case was 81% which does not indicate very good fit of the experimental data. This curve was first used to estimate the hydrogen diffusivity according to the procedure outlined above. The value of the bulk hydrogen signal  $(\text{HYS})_b$  was taken as 14 mV and the diffusivity values and average diffusivity calculated are provided in table 1.

A better fit of the experimental data, especially in the near-surface region, was obtained by a third order polynomial fit and this is also shown in figure 1. The correlation of fit in this case was 93%. Hydrogen diffusivity was estimated by the above procedure by using  $\text{HYS}_b$  from the first flat region of the curve (i.e. 28 mV) and the average diffusivity was found to be  $1.34 \times 10^{-15} \text{ m}^2/\text{s}$  (table 1). The same curve was also used to determine hydrogen diffusivity by using the lowest data point (i.e. 4 mV) as the bulk  $\text{HYS}_b$  value. This provided an average diffusivity value of  $2.35 \times 10^{-15} \text{ m}^2/\text{s}$  (table 1). It is seen that similar hydrogen diffusivities are obtained for slightly different  $\text{HYS}_b$  used. It is again noticed that the estimated average hydrogen diffusivity values are comparable to those obtained from the quadratically fit curve. Finally, it can also be observed from the data that the first five data points (i.e. from the surface) lie on a smooth curve and hydrogen diffusivity was again estimated using just the four data points. The data for  $z = 0$  was not used as it is not amenable for analysis by (3). The average diffusivity estimated by this procedure was  $1.41 \times 10^{-15} \text{ m}^2/\text{s}$ .

The average diffusivity value calculated from the individual average diffusivities obtained by the different methods of analysis is  $2.38 \times 10^{-15} \text{ m}^2/\text{s}$ . This could be taken

**Table 1.** Diffusivity values and average diffusivity of hydrogen in Fe-35.8%Al estimated in the present study.

Analysis method	Bulk HYS (mV)	$D_{\text{H}}$ ( $\text{m}^2/\text{s} \times 10^{15}$ )	$D_{\text{H, av}}$ ( $\text{m}^2/\text{s} \times 10^{15}$ )
Quadratic fit	14	5.84, 3.86, 3.83, 4.2	4.43
Third order Polynomial	28	1.3, 1.6, 1.01, 1.43	1.34
	4	3.04, 2.2, 1.18, 2.96	2.35
Actual data	4	1.28, 1.63, 1.31, 1.43	1.41
		Average	2.38

as the diffusivity of hydrogen in Fe–35.8 Al determined in the present analysis, because averaging a set of values is expected to diminish the estimation errors further. This is the first reported value of hydrogen diffusivity in Fe–35.8 Al.

### 3. Comparison with Literature

The diffusivity of hydrogen has been reported recently in iron aluminide of composition (in at %) Fe–28 Al–5.0 Cr–0.5 Nb–0.5 Mo–0.2 C–0.2 B–0.1 Zr (Chiu *et al* 1996). In a study on the environment sensitive cracking of this aluminide, they determined the room temperature diffusivity of hydrogen in the intermetallic by the time-lag technique (Devanathan and Stachurski 1962) to be  $1.6 \times 10^{-9} \text{ m}^2/\text{sec}$ . They concluded that the reported value of hydrogen diffusivity was reasonable as it was of the same order of magnitude as that for hydrogen diffusivity in BCC metals like  $\alpha$ -Fe, V and Nb (Völkl and Alefeld 1978). The estimated hydrogen diffusivity in FeAl is lower than that for the Fe<sub>3</sub>Al-based aluminide.

Limited data is available in the literature on the room temperature hydrogen diffusivity for Al and Al alloys and these have been summarized by Thakur and Balasubramaniam (1996). The estimated hydrogen diffusivity in FeAl is lower than that for hydrogen diffusion in aluminum. The hydrogen diffusivity in pure iron has been determined by several authors and the available data have been critically reviewed (Völkl and Alefeld 1975, 1978; Kiuchi and McLellan 1983). There is a large degree of discrepancy in the data obtained for well-annealed b.c.c. iron and the degree of discrepancy increases sharply with decreasing temperature (Kiuchi and McLellan 1983). The measured diffusivities of several investigators begin a sharp drop around 300 K. The reasons proposed to explain these discrepancies are the presence of intrinsic trapping sites in the structure of well annealed iron, differing states of surface oxidation and the presence of non-intrinsic defect sites in the bulk of the material (like impurity atoms, grain boundaries and dislocations) (Kiuchi and McLellan 1983). Kiuchi and McLellan (1983) also analyzed the available data on hydrogen diffusivity in well-annealed iron and concluded that the techniques that used electropolished and Pd-coated surfaces in the gas equilibration and electrochemical methods provided reliable diffusivities. The hydrogen diffusivity calculated from these reliable data at 300 K is about  $10^{-8} \text{ m}^2/\text{s}$ . This is higher than that calculated above for FeAl in the present study. One reason for the lower diffusivity measured could be the presence of a large atomic percent of Al which would act as blocking sites for hydrogen diffusion result in a lower diffusivity value. Secondly, it has been reported that data obtained from specimens containing bulk or surface trapping sites produce lower diffusivity values (Kiuchi and McLellan 1983). In the case of the experiments of Zhu *et al* (1996), the specimens were not coated with Pd before hydrogen charging and therefore the absence of surface trapping sites cannot be precluded. The low hydrogen diffusivity estimated in FeAl could be due to surface and bulk trapping effects and this may be taken as a lower bound value.

### 4. Conclusions

The diffusivity of hydrogen in Fe–35.8 Al was estimated by mathematical analysis of hydrogen concentration versus depth data of Zhu *et al* (1996) by applying the standard

diffusion equation. It was found to be  $2.38 \times 10^{-15} \text{ m}^2/\text{s}$  at room temperature. The estimated hydrogen diffusivity is a lower bound value due to surface trapping effects.

### References

- Agarwal A and Balasubramaniam R 1996 *Bull. Mater. Sci.* **19** 91  
Chiu H, Qiao L and Mao X 1996 *Scr. Mater.* **34** 963  
Devanathan M A V and Stachurski Z O 1962 *Proc. R. Soc.* **A270** 90  
Kiuchi K and McLellan R B 1983 *Acta Metall.* **31** 961  
Liu C T, Lee E H and McKamey C G 1989 *Scr. Metall. Mater.* **23** 875  
Roy T K, Balasubramaniam R and Ghosh A 1996 *Scr. Mater.* **34** 1425  
Thakur C and Balasubramaniam R 1996 *J. Mater. Sci. Lett.* **15** 1397  
Völkl J and Alefeld G 1975 in *Diffusion in solids* (eds) A S Nowick and J J Burton (New York: Academic Press) p. 231  
Völkl J and Alefeld G (eds) 1978 in *Hydrogen in metals I* (Berlin: Springer Verlag) p. 321  
Zhu Y F, Liu C T and Chen C H 1996 *Scr. Mater.* **35** 1435