

 Open access • Journal Article • DOI:10.1007/S10659-014-9508-Z

Hyperelastic Energy Densities for Soft Biological Tissues: A Review

— [Source link](#) 

Grégory Chagnon, Marie Rebouah, Denis Favier

Institutions: University of Grenoble

Published on: 01 Aug 2015 - Journal of Elasticity (Springer Netherlands)

Topics: Hyperelastic material, Cauchy elastic material, Polynomial (hyperelastic model), Ogden and Constitutive equation

Related papers:

- [A new constitutive framework for arterial wall mechanics and a comparative study of material models](#)
- [Hyperelastic modelling of arterial layers with distributed collagen fibre orientations](#)
- [A three-dimensional constitutive model for the large stretch behavior of rubber elastic materials](#)
- [Large Deformation Isotropic Elasticity—On the Correlation of Theory and Experiment for Incompressible Rubberlike Solids](#)
- [Fitting hyperelastic models to experimental data](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/hyperelastic-energy-densities-for-soft-biological-tissues-a-1u4x2ei9t0>



HAL
open science

Hyperelastic Energy Densities for Soft Biological Tissues: A Review

Grégory Chagnon, Marie Rebouah, Denis Favier

► **To cite this version:**

Grégory Chagnon, Marie Rebouah, Denis Favier. Hyperelastic Energy Densities for Soft Biological Tissues: A Review. *Journal of Elasticity*, Springer Verlag, 2015, 120 (2), pp.129-160. 10.1007/s10659-014-9508-z . hal-01480510

HAL Id: hal-01480510

<https://hal.archives-ouvertes.fr/hal-01480510>

Submitted on 5 Apr 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Hyperelastic Energy Densities for Soft Biological Tissues: A Review

G. Chagnon · M. Rebouah · D. Favier

Abstract Many soft tissues are naturally made of a matrix and fibres that present some privileged directions. They are known to support large reversible deformations. The mechanical behaviour of these tissues highlights different phenomena as hysteresis, stress softening or relaxation. A hyperelastic constitutive equation is typically the basis of the model that describes the behaviour of the material. The hyperelastic constitutive equation can be isotropic or anisotropic, it is generally expressed by means of strain components or strain invariants. This paper proposes a review of these constitutive equations.

1 Introduction

Soft tissues are composed of several layers, each one of these layers has different compositions. It is considered that four typical tissues exist: epithelial tissue, connective tissue, muscular tissue and neuronal tissue [156]. For the mechanical studies on soft tissues the connective tissues are often considered as the most important from a mechanical point of view [69, 156, 177]. They are composed of cells and of extra cellular matrix. The extra cellular matrix is composed of ground substance and of three types of fibres: collagen, reticular and elastic fibres. Collagen fibres are often considered as more important than others, particularly because of their large size, and represent most of the mechanical behaviour. The reticular fibres, which are thin collagen fibres with different chemical properties, allow creating ramifications with the collagen fibres. Finally the elastic fibres mainly composed of elastin present a purely elastic behaviour and are also linked to the collagen fibres. The elastic properties of soft tissues are mainly due to these fibres. Soft tissues are often able to support large deformations.

G. Chagnon (✉) · M. Rebouah · D. Favier
Université de Grenoble Alpes/CNRS/TIMC-IMAG UMR 5525, Grenoble 38041, France
e-mail: gregory.chagnon@imag.fr

The first mechanical study of soft tissues started in 1687 with Bernoulli experiments on gut. The first constitutive equation was proposed in 1690 by Leibniz, before Bernoulli and Riccati proposed other equations [22]. Since these works, many experimental studies have been performed. As an illustration, some experimental data can be found, not exhaustively, in the literature for arteries [209, 262], aortic valve tissues [162], veins [4], vaginal tissues [196], anterior malleolar ligament [47], muscles [89], human trachea [254], cornea [235], skin [90] or gallbladder walls [143]... Even if many soft tissues are studied, the largest database in the literature concerns arteries.

Soft tissues present a complex behaviour with many non-linear phenomena as explained by different authors [118, 124] as the time dependency [27, 202] or the stress softening phenomenon [154, 198], *i.e.*, their mechanical behaviour mainly depends on time and on the maximum deformation previously endured. Most of soft tissues dissipate energy when loading, nevertheless, the elastic behaviour generally dominates their behaviour and it represents the asymptotic behaviour when the dissipation diminishes to zero. In this way, in a first approach, most of the soft tissues are described in the context of hyperelasticity [94, 149, 246]. To take into account the fibrous structure of the soft tissues, anisotropic formalism is introduced. The diversity among the mechanical characteristics of soft tissues has motivated a great number of constitutive formulations for the different tissue types. For example, the reader is referred to [224], wherein the author treats the history of biaxial techniques for soft planar tissues and the associated constitutive equations.

Anisotropic hyperelasticity can be modeled by using the components of the strain tensor or by the use of strain invariants. The two formulations permit the development of different families of anisotropic strain energy densities. Soft tissues are numerous and present different tissue architectures that lead to various anisotropy degrees, *i.e.*, difference of mechanical behaviour in each direction, and different maximum admissible deformation. In this way, many constitutive equations are proposed to describe the tissues.

The aim of this paper is to propose a review of most of the hyperelastic strain energy densities commonly used to describe soft tissues. In a first part, the different formalisms that can be used are recalled. In a second part, the isotropic modelling is described. In a third part, the anisotropic modelling is presented. The deformation tensor component approach based on Fung's formulation is briefly presented, and invariant approaches are detailed. In a fourth part, the statistical approaches, considering the evolution of the collagen network, are described. Last, a discussion about the models closes the paper.

2 Mechanical Formulation

2.1 Description of the Deformation

Deformations of a material are classically characterised by right and left Cauchy–Green tensors defined as $\mathbf{C} = \mathbf{F}^T \mathbf{F}$ and $\mathbf{B} = \mathbf{F} \mathbf{F}^T$, where \mathbf{F} is the deformation gradient. In the polar decomposition of \mathbf{F} , the principle components of the right or left stretch tensors are called the stretches and are denoted as λ_i with $i = 1..3$. The Green–Lagrange tensor is defined as $\mathbf{E} = (\mathbf{C} - \mathbf{I})/2$, where \mathbf{I} is the identity tensor, and its components are denoted as E_{ij} with $i, j = 1..3$. Nevertheless, some prefer to use the logarithmic strains $e_i = \ln(\lambda_i)$, instead of a strain tensor, generalised strains as $e_i = \frac{1}{n}(\lambda_i^n - 1)$ [185], or others measures as, for example, $e_i = \frac{\lambda_i}{\lambda_j^2 \lambda_k^2}$ with $j \neq i$ and $k \neq i$ [86]; all these measures are written in their principal basis.

Instead of using directly the strain tensors, strain invariants are often preferred as they have the same values whatever the basis is. From an isotropic point of view, three principal strain invariants I_1 , I_2 and I_3 are defined by

$$I_1 = \text{tr}(\mathbf{C}), \quad (1)$$

$$I_2 = \frac{1}{2}[\text{tr}(\mathbf{C})^2 - \text{tr}(\mathbf{C}^2)], \quad (2)$$

$$I_3 = \det(\mathbf{C}), \quad (3)$$

where “tr” is the trace operator, and “det” the determinant operator.

Characteristic directions corresponding to the fibre orientations must be defined. For one material, one or many material directions (the number of directions is noted q) can be defined according to the architecture of the considered tissue. In the undeformed state, the i th direction is noted \mathbf{N}^i in the initial configuration. The norm of the vector \mathbf{N}^i is unit. Due to material deformation, the fibre orientations are evolving in the deformed state. The current orientation is defined by

$$\mathbf{n}^{(i)} = \mathbf{F}\mathbf{N}^{(i)}. \quad (4)$$

Note that $\mathbf{n}^{(i)}$ is not a unit vector. Two orientation tensors can be defined, one in the undeformed and another in the deformed state:

$$\mathbf{A}^{(i)} = \mathbf{N}^{(i)} \otimes \mathbf{N}^{(i)}, \quad \mathbf{a}^{(i)} = \mathbf{n}^{(i)} \otimes \mathbf{n}^{(i)}. \quad (5)$$

The introduction of such directions lead to the definition of new invariants related to each direction. The invariant formulation of anisotropic constitutive equations is based on the concept of structural tensors [29, 30, 238, 239, 241, 243].¹ The invariant I_4 and I_5 can be defined for one direction i as

$$I_4^{(i)} = \text{tr}(\mathbf{C}\mathbf{A}^{(i)}) = \mathbf{N}^{(i)} \cdot \mathbf{C}\mathbf{N}^{(i)}, \quad \text{and} \quad I_5^{(i)} = \text{tr}(\mathbf{C}^2\mathbf{A}^{(i)}) = \mathbf{N}^{(i)} \cdot \mathbf{C}^2\mathbf{N}^{(i)}. \quad (6)$$

In practice, some prefer to use the cofactor tensor of \mathbf{F} , i.e., $\text{Cof}(\mathbf{F})$, [120] and to define $J_5^{(i)} = \text{tr}(\text{Cof}(\mathbf{C})\mathbf{A}^{(i)})$, in order to easily ensure the polyconvexity of the strain energy (see Sect. 2.3). In the literature, in the case of two fibre directions (1) and (2), a notation I_4 and I_6 is often used for soft tissues [108] instead of $I_4^{(1)}$ and $I_4^{(2)}$ (or I_5 and I_7 instead of $I_5^{(1)}$ and $I_5^{(2)}$). In this paper, it is preferred to keep only $I_4^{(i)}$ notation and to generalise the notation to n directions. These invariants depend only on one direction but it is possible to take into account the interaction between different directions, by introducing a coupling between directions i and j by means of two other invariants:

$$I_8^{(i,j)} = (\mathbf{N}^{(i)} \cdot \mathbf{N}^{(j)})(\mathbf{N}^{(i)} \cdot \mathbf{C}\mathbf{N}^{(j)}), \quad \text{and} \quad I_9^{(i,j)} = (\mathbf{N}^{(i)} \cdot \mathbf{N}^{(j)})^2. \quad (7)$$

$I_9^{(i,j)}$ is constant during deformation, thus it is not adapted to describe the deformation of the material but it represents the value of $I_8^{(i,j)}$ for zero deformation. Let us denote I_k as the invariants family $(I_1, I_2, I_3, I_4^{(i)}, I_5^{(i)}, I_8^{(i,j)}, I_9^{(i,j)})$ and J_k as the invariants family

¹Details about the link between structural tensors and a method to link a fictitious isotropic configuration to render an anisotropic, undeformed reference configuration via an appropriate linear tangent map is given in [163].

$(I_1, I_2, I_3, I_4^{(i)}, J_5^{(i)})$. When only one direction is considered, the superscript (i) is omitted in the remainder of this paper.

The I_k invariants are the mostly used invariants in the literature, although other invariants have been proposed. Some authors [50] propose to use invariants that are zero at zero deformation. In this way, they introduce the tensor $\mathbf{G} = \mathbf{H}^T \mathbf{H}$, with $\mathbf{H} = \frac{1}{2}(\mathbf{F} - \mathbf{F}^T)$. This motivates the definition of a new class of invariants \tilde{I}_k :

$$\begin{cases} \tilde{I}_1 = \text{tr}(\mathbf{G}), \\ \tilde{I}_2 = \text{tr}(\mathbf{G}^2), \\ \tilde{I}_4 = \text{tr}(\mathbf{G}\mathbf{A}^{(i)}), \\ \tilde{I}_5 = \text{tr}(\mathbf{G}^2\mathbf{A}^{(i)}). \end{cases} \quad (8)$$

Ericksen and Rivlin [70] proposed another formulation, adapted to transversely isotropic materials only, characterised by a vector \mathbf{N} (*i.e.*, only one direction i). This direction often corresponds to a fibre reinforced direction. Their work was further used by different authors [3, 52, 54, 55] who proposed to define other invariants $(\lambda_p, \lambda_n, \gamma_n, \gamma_p, \psi_\gamma)$, denoted as Cr_k . They can be expressed as a function of the I_k invariants:

$$\begin{cases} \lambda_p^2 = \sqrt{\frac{I_3}{I_4}}, \\ \lambda_n^2 = I_4, \\ \gamma_n^2 = \frac{I_5}{I_4} - I_4, \\ \gamma_p^2 = I_1 - \frac{I_5}{I_4} - 2\sqrt{\frac{I_3}{I_4}}, \\ \tan 2\psi_\gamma = \frac{2\lambda_p H + / - \gamma_p \sqrt{\gamma_n^4 \gamma_p^2 (4\lambda_p^2 + \gamma_p^2) - H^2}}{\lambda_p H + / - 2\lambda_p \sqrt{\gamma_n^4 \gamma_p^2 (4\lambda_p^2 + \gamma_p^2) - H^2}}, \end{cases} \quad (9)$$

with $H = (2\lambda_n^2 + \gamma_n^2)(2\lambda_p^2 + \gamma_p^2) + 2\lambda_p^4 - 2I_2$. The advantage is that these invariants have a physical meaning. λ_n is the measure of stretch along \mathbf{N} , λ_p is a measure of the in-plane transverse dilatation, γ_n is a measure of the amount of out-of-plane shear, γ_p is the amount of shear in the transverse plane, and ψ_γ is a measure of the coupling among the other invariants. Criscione et al. [52] criticised these invariants for not being zero for zero deformation, as is the corresponding strain tensors. They proposed to use the β_k invariants:

$$\begin{cases} \beta_1 = \frac{\ln I_3}{2}, \\ \beta_2 = \frac{3 \ln I_4 - \ln I_3}{4}, \\ \beta_3 = \ln \left(\frac{I_1 I_4 - I_5}{2\sqrt{I_3 I_4}} + \sqrt{\left(\frac{I_1 I_4 - I_5}{2\sqrt{I_3 I_4}} \right)^2 - 1} \right), \\ \beta_4 = \sqrt{\frac{I_5}{I_4^2} - 1}, \\ \beta_5 = \frac{I_1 I_4 I_5 + I_1 I_4^3 + 2I_3 I_4 - I_5^2 - 2I_2 I_4^2 - I_5 I_4^2}{(I_5 - I_4^2) \sqrt{I_1^2 I_4^2 + I_5^2 - 2I_1 I_4 I_5 - 4I_3 I_4}}. \end{cases} \quad (10)$$

These invariants also have a physical meaning. β_1 is the logarithmic volume strain, β_2 specifies a fibre strain of distortion, β_3 specifies the magnitude of cross-fibre, *i.e.*, pure shear strain, β_4 specifies the magnitude of along fibre strain, *i.e.*, simple shear strain and β_5 specifies the orientation of the along fibre shear strain relative to the cross-fibre shear strain.

These last two families of invariants were developed for a one fibre direction material; it can easily be generalised to q directions but this has not yet been used yet in the literature. All these invariants are useful. In practice, the I_k are the most used and the other invariants are not often used for calculations in finite element software. But, as they can be written by means of the I_k invariants, all the expressions can be deduced from these invariants. As a consequence in this work, the theoretical development is only presented for the I_k formulation.

2.2 Strain-Stress Relationships

Living tissues are often considered as incompressible. To use constitutive equations in finite element codes, a volumetric/isochoric decomposition is used. All the equations are written using the pure incompressibility hypothesis in order to avoid any non-physical response of these equations [100], but some details about the consequences of the volumetric-isochoric choice split is detailed in [227]. Nevertheless, they can be written in a quasi-incompressible framework by means of the incompressible invariants \bar{I}_k :

$$\begin{cases} \bar{I}_1 = I_1 I_3^{-1/3}, \\ \bar{I}_2 = I_2 I_3^{-2/3}, \\ \bar{I}_4^{(i)} = I_4^{(i)} I_3^{-1/3}, \\ \bar{I}_5^{(i)} = I_5^{(i)} I_3^{-2/3}, \\ \bar{I}_8^{(i,j)} = I_8^{(i,j)} I_3^{-1/3}. \end{cases} \quad (11)$$

This formulation is particularly useful for finite element implementation. All the equations for the elasticity tensor can be seen in different papers [32, 133, 145, 152, 195, 271]. In this case, a penalty function depending on I_3 is used to ensure incompressibility. One can refer to [62] for a comparison of the different functions classically used. The choice of the penalty parameter to ensure incompressibility [253] is a critical issue. In this paper, all the constitutive equations are written in the purely incompressible framework, but all the models can be established in the quasi-incompressible framework as well.

The second Piola–Kirchhoff stress tensor can be directly calculated by derivation of the strain energy function $W(I_1, I_2, I_4^{(i)}, I_5^{(i)}, I_8^{(i,j)}, I_9^{(i,j)})$, with $i, j = 1..q$:

$$\begin{aligned} \mathbf{S} = & 2 \left[(W_{,1} + I_1 W_{,2}) \mathbf{I} - W_{,2} \mathbf{C} + \sum_i^q W_{,4}^{(i)} \mathbf{N}^{(i)} \otimes \mathbf{N}^{(i)} \right. \\ & + \sum_i^q W_{,5}^{(i)} (\mathbf{N}^{(i)} \otimes \mathbf{C} \mathbf{N}^{(i)} + \mathbf{N}^{(i)} \mathbf{C} \otimes \mathbf{N}^{(i)}) \\ & \left. + \sum_{i \neq j} W_{,8}^{(i,j)} (\mathbf{N}^{(i)} \cdot \mathbf{N}^{(j)}) (\mathbf{N}^{(i)} \otimes \mathbf{N}^{(j)} + \mathbf{N}^{(j)} \otimes \mathbf{N}^{(i)}) \right] + p \mathbf{C}^{-1} \quad (12) \end{aligned}$$

where $W_{,k} = \frac{\partial W}{\partial I_k}$, and p is the hydrostatic pressure. The Eulerian stress tensor, *i.e.*, the Cauchy stress tensor, is directly obtained by the push-forward operation. To ensure that the

stress is identically zero in the undeformed configuration, it is required that:

$$\forall i \quad W_{,4}^{(i)} + 2W_{,5}^{(i)} = 0, \quad (13)$$

for zero deformation [174]. The direct expressions that permit calculation of the stress with the other invariants basis can be found in [52, 53].

2.3 Stability

The strong ellipticity condition is a mathematical restriction on the constitutive functions. For three-dimensional problems [267], the strong ellipticity was characterised for compressible isotropic materials in [236], and for incompressible ones in [273]. In this context, the strong ellipticity was largely studied in the case of transverse isotropy for in plane strains in [165–168, 170, 240]. The generic condition to verify for the strain energy in the absence of body forces [150, 167, 168] can be written as:

$$\frac{1}{J} F_{pr} F_{qs} \frac{\partial^2 W}{\partial F_{ir} \partial F_{js}} n_p n_q m_i m_j > 0 \quad \text{with } \mathbf{m} \neq \mathbf{0} \text{ and } \mathbf{n} \neq \mathbf{0}, \quad (14)$$

where \mathbf{m} and \mathbf{n} are two non-zero vectors. Nevertheless, this condition is always difficult to verify. Thus, some have proposed another way to tackle the strong ellipticity condition. It is known that polyconvexity implies ellipticity [173, 228, 232]. As a consequence, the polyconvexity in the sense of Ball [14, 15] is used, even if it is more restrictive than strong ellipticity. Of course, some strain energies can be elliptic but not polyconvex. It is important to note that polyconvexity does not conflict with the possible non-uniqueness of equilibrium solutions, as it guarantees only the existence of at least one minimizing deformation. Hence, polyconvexity provides an excellent starting point to formulate strain energy functions that guarantees both ellipticity and existence of a global minimizer.

Polyconvexity has been studied within the framework of isotropy [23, 244], and the conditions to verify it are well known for every classical isotropic model from the literature (see for example [97, 98, 180, 204]). Many authors have extended their study to anisotropic materials [67, 121, 171, 206, 245, 257]. Some have studied the polyconvexity of existing constitutive equations [64, 104, 106, 186, 267], whereas others have attempted to directly develop polyconvex constitutive equations.

Some Conditions. In case of existing constitutive equations, Walton and Wilber [267] summarised conditions to ensure polyconvexity. For a strain energy depending on I_1 , I_2 and I_4 , $W(I_1, I_2, I_4^{(i)})$, the conditions are:

$$W_{,k} > 0 \quad \text{for } k = 1, 2, 4 \quad \text{and} \quad (15)$$

$$[W_{,kl}] \quad \text{is definite positive.} \quad (16)$$

If the strain energy also depends on $I_8^{(i,j)}$, the following condition should be added:

$$\frac{\partial W}{\partial I_8^{(i,j)}} \leq \frac{\partial W}{\partial I_1}. \quad (17)$$

The use of the fifth invariant $I_5^{(i)}$ introduces the need to change the other invariants, as I_5 is not a polyconvex function (when used alone). Walton and Wilber [267] used I_k^* :

$$\begin{cases} I_1^* = \frac{1}{2}I_1, \\ I_2^* = \frac{1}{2}I_1^2 - I_2, \\ I_4^{(i)*} = I_4^{(i)}, \\ I_5^{(i)*} = I_5^{(i)}. \end{cases} \quad (18)$$

Here, the condition to verify for I_k^* is:

$$\begin{cases} W_{,k} > 0 & \text{for } k = 1, 2, 4, 5, \\ W_{,1} + \kappa W_{,4} \geq 0 & \text{for some } \kappa > 4, \\ [W_{,kl}] & \text{is definite positive.} \end{cases} \quad (19)$$

As it will be described in next paragraph, many strain energies can be decomposed as $W = W_{iso}(I_1) + W_{aniso}(I_4)$. In this case, some sufficient conditions, but not necessary for polyconvexity, have been given in [106] for the anisotropic part:

$$\frac{\partial W_{aniso}}{\partial I_4} \geq 0 \quad \text{and} \quad (20)$$

$$\frac{\partial W_{aniso}}{\partial I_4} + 2I_4 \frac{\partial^2 W_{aniso}}{\partial I_4^2} \geq 0. \quad (21)$$

These two restrictive conditions mean that the considered directions cannot generate negative forces when submitted to compression whereas the strong ellipticity can also be verified in compression. This is an illustration of the constraints generated by the polyconvexity compared to strong ellipticity.

Development of Specific Constitutive Equations. Some authors have created elementary strain energies that satisfy polyconvexity. First, Schroder and Neff [228] worked on equations depending on I_1 and I_4 , and they proved that some functions are polyconvex:

$$W_1 = \beta_1 I_4, \quad W_2 = \beta_2 I_4^2, \quad W_3 = \beta_3 \frac{I_4}{I_3^{1/3}}, \quad \text{and} \quad W_4 = \beta_4 \frac{I_4^2}{I_3^{1/3}}, \quad (22)$$

where β_i are material parameters. Nevertheless, as I_5 is not a polyconvex function, some have proposed [228, 229] the construction of new combinations of invariants in the case of one reinforced direction that are polyconvex; these invariants are denoted as K_i :

$$\begin{cases} K_1 = I_5 - I_1 I_4 + I_2 (\text{tr}(\mathbf{A}))^{1/2}, \\ K_2 = I_1 - I_4, \\ K_3 = I_1 I_4 - I_5. \end{cases} \quad (23)$$

These invariants permitted the development of a list of elementary polyconvex energies [66, 231]. The different strain energies are listed in Table 1. Since a combination of polyconvex energy densities is also polyconvex, it is possible to develop many constitutive equations that can be adapted to different soft tissues.

Table 1 Elementary polyconvex functions [66, 231], where β_i with $i = 5 \dots 23$ are material parameters

Elementary polyconvex functions		
$W_5 = \beta_5 K_1$	$W_6 = \beta_6 K_1^2$	$W_7 = \beta_7 K_1^3$
$W_8 = \beta_8 \frac{K_1}{I_3^{1/3}}$	$W_9 = \beta_9 \frac{K_1^2}{I_3^{2/3}}$	$W_{10} = \beta_{10} K_2$
$W_{11} = \beta_{11} K_2^2$	$W_{12} = \beta_{12} \frac{K_2}{I_3^{1/3}}$	$W_{13} = \beta_{13} \frac{K_2^2}{I_3^{2/3}}$
$W_{14} = \beta_{14} K_3$	$W_{15} = \beta_{15} K_3^2$	$W_{16} = \beta_{16} \frac{K_3}{I_3^{1/3}}$
$W_{17} = \beta_{17} \frac{K_3^2}{I_3^{2/3}}$		
$W_{18} = \beta_{18} (I_1^2 + I_4 I_1)$	$W_{19} = \beta_{19} (2I_2^2 + I_2 I_5 - I_1 I_2 I_4)$	$W_{20} = \beta_{20} (3I_1^2 - I_4 I_1)$
$W_{21} = \beta_{21} (2I_2^2 + I_1 I_2 I_4 - I_2 I_5)$	$W_{22} = \beta_{22} (3I_1 - 2I_4)$	$W_{23} = \beta_{23} (I_2 - 2I_5 + 2I_1 I_4)$

3 Isotropic Hyperelastic Constitutive Equations

From a macroscopic point of view, soft tissues are an assembly of cells and fibres. According to the quantity and the orientation of the fibres, the behaviour of soft tissues can be supposed isotropic or not. According to the application, anisotropic behaviour can be neglected, and isotropic modelling can be efficient. In this way, many authors decide to use an isotropic approach to model soft tissues, as for example liver [149] kidney [113], bladder and rectum [33], pelvic floor [193], breast [12, 226], cartilage [144], meniscus [1], ligaments [80], eardrum [46], arteries [192], brain [127], lungs [234], uterus [95] or skin [142]... Many models that are used to describe an isotropic approach come from rubber like materials studies. Some literature reviews have been proposed [34, 258]. Constitutive equations for rubber like materials were created to represent a strain hardening for deformations of about hundreds of percent whereas soft tissues often strain harden after some tens of percent. Thus, the functions for rubber like materials may not necessarily apply. Other, more suitable constitutive equations have been developed especially for soft tissues. The main models are listed in Table 2. The main feature for the constitutive equations is the presence of an important change of slope in the strain-stress curve for moderate deformations. This explains why most of the equations include an exponential form which allows the description of strong slope changes. Nevertheless, all constitutive equations stay equivalent to the neo-Hookean model [255, 256] for small strains. Moreover, most of the constitutive equations are very similar for the I_1 part as it is the exponential form that dominates in the equations. While most of the constitutive equations are only expressed with the first invariant, the second invariant can be employed to capture the different states of loading [112]. There exists some limitations to use only the first invariant [110, 270]. Nevertheless, the choice of using I_1 , or (I_1, I_2) mainly depends on the available experimental data. When experiments are limited to one loading case, it can be difficult to correctly fit a constitutive equation expressed by means of the two invariants.

4 Anisotropic Hyperelastic Constitutive Equations

Different approaches have been used to describe the anisotropy of soft tissues. The first one is based on Green–Lagrange components and the second one is based on strain invariants.

Table 2 Principal isotropic hyperelastic constitutive equations developed for soft tissues, where c_1, c_2, c_3 and c_4 are material parameters. (*) The model is known as the generalised neo-Hookean model. (**) As pointed out by [109] is frequently mistakenly referred to Delfino et al. [56]

Polynomial models	
Raghavan and Vorp [210]	$W = c_1(I_1 - 3) + c_2(I_1 - 3)^2$
Knowles [131, 274] (*)	$W = \frac{c_1}{2c_2} \left[\left(1 + \frac{c_2}{c_3}(I_1 - 3)\right)^{c_3} - 1 \right]$
Exponential model	
Demiray [57] (**)	$W = \frac{c_1}{c_2} \left\{ \exp\left[\frac{c_2}{2}(I_1 - 3)\right] - 1 \right\}$
Demiray et al. [58]	$W = \frac{c_1}{c_2} \left\{ \exp\left[\frac{c_2}{2}(I_1 - 3)^2\right] - 1 \right\}$
Holmes and Wow [103]	$W = c_0(\exp(c_1(I_1 - 3)) + \exp(c_2(I_2 - 3))) - c_0$
Arnoux et al. [7, 8]	$W = c_1 \exp(c_2(I_1 - 3)) - \frac{c_1 c_2}{2}(I_2 - 3)$
Singh et al. [237]	$W = \frac{c_1}{2c_2} \exp(c_2(I_1 - 3) - 1) + \frac{c_3}{2}(I_2 - 3)^2$
Volokh and Vorp [266]	$W = c_1 - c_1 \exp\left[-\frac{c_2}{c_1}(I_1 - 3) - \frac{c_3}{c_1}(I_1 - 3)^2\right]$
Tang et al. [251]	$W = c_1(I_1 - 3) + c_2(I_2 - 3) + c_3(\exp(c_4(I_1 - 3)) - 1)$
Van Dam et al. [261]	$W = c_1 \left\{ -\frac{1-c_2}{c_3} \left[(c_3 x + 1) \exp(-c_3 x) - 1 \right] + \frac{1}{2} c_2 x^2 \right\}$ with $x = \sqrt{c_4 I_1 + (1 - c_4) I_2 - 3}$

4.1 Use of Green–Lagrange Tensor Components

The first model using the components of the Green–Lagrange strain tensor were developed in [118]. It consists in proposing strain energy densities that are summarily decomposed into contributions of each component with different weights; a review of these models is proposed in [116]. The first generic form was proposed by Tong and Fung [252]:

$$W = \frac{c}{2} (\exp(b_1 E_{11}^2 + b_2 E_{22}^2 + b_3 (E_{12}^2 + E_{21}^2) + 2b_4 E_{12} E_{21} + b_5 E_{11}^3 + b_6 E_{22}^3 + b_7 E_{11}^2 E_{22} + b_8 E_{11} E_{22}^2)^{-1}), \quad (24)$$

where c and $b_i, i = 1...8$ are material parameters. Three years later, Fung [77] developed a generic form in two dimensions, the model was next generalised to three dimensions [49]. Later, shear strains were introduced [128], and finally a global formulation was proposed [116]:

$$W = c(\exp(A_{ijkl} E_{ij} E_{kl}) - 1), \quad (25)$$

where c and A_{ijkl} are material parameters. Different constitutive equations were then developed and written in cylindrical coordinates (r, θ, z) often used for arteries [138]. Moreover, the strain energy function can be naturally uncoupled into a dilatational and a distortional part [11], to facilitate the computational implementation of incompressibility. In the same way, as in non-Gaussian theory [137], it is possible to take into account the limiting extensibility of the fibres [175]. This exposes the possibility of a constitutive equation that presents an asymptote even if constitutive equations that include an exponential or an asymptotic form can be very close [42]. The proposed models are listed in Table 3. The main difficulty of these constitutive equations is that they have a large number of material parameters.

Table 3 Anisotropic constitutive equations written with strain tensors components, where A_{ijkl} with $i, j, k, l = 1...3$, b_i , with $i = 1...12$, a_{ij} , b_{ij} , c_{ij} with $i, j = 1...3$ and c are material parameters

Generic Fung functions $W = \frac{C}{2}(\exp Q - 1)$	
Tong and Fung [252]	$Q = A_{ijkl}E_{ij}E_{kl}$
Fung et al. [77]	$Q = b_1 E_{\theta\theta}^2 + b_2 E_{zz}^2 + 2b_4 E_{\theta\theta} E_{zz}$
Chuong and Fung [49]	$Q = b_1 E_{\theta\theta}^2 + b_2 E_{zz}^2 + b_3 E_{rr}^2 + 2b_4 E_{\theta\theta} E_{zz} + 2b_5 E_{rr} E_{zz} + 2b_6 E_{\theta\theta} E_{rr}$
Humphrey [116]	$Q = b_1 E_{\theta\theta}^2 + b_2 E_{zz}^2 + b_3 E_{rr}^2 + 2b_4 E_{\theta\theta} E_{zz} + 2b_5 E_{rr} E_{zz}$ $+ 2b_6 E_{\theta\theta} E_{rr} + b_7 E_{\theta z}^2 + b_8 E_{r z}^2 + b_9 E_{r\theta}^2$
Costa et al. [51]	$Q = b_1 E_{ff}^2 + b_2 E_{ss}^2 + b_3 E_{nn}^2 + 2b_4 (\frac{1}{2}(E_{fn} + E_{nf}))^2$ $+ 2b_5 (\frac{1}{2}(E_{sn} + E_{ns}))^2 + 2b_6 (\frac{1}{2}(E_{fs} + E_{sf}))^2$
Rajagopal et al. [213]	$Q = b_1 E_{\theta\theta}^2 + b_2 E_{zz}^2 + b_3 E_{rr}^2 + 2b_4 E_{\theta\theta} E_{zz} + 2b_5 E_{rr} E_{zz} + 2b_6 E_{\theta\theta} E_{rr}$ $+ b_7 (E_{rr}^2 + E_{\theta\theta}^2) + b_8 (E_{\theta\theta}^2 + E_{zz}^2) + b_9 (E_{rr}^2 + E_{zz}^2)$
Other exponential functions	
Choi and Vito [48]	$W = b_0 [\exp(b_1 E_{11}^2) + \exp(b_2 E_{22}^2) + \exp(2b_3 E_{11} E_{22}) - 3]$
Kasyanov and Rachev [128]	$W = b_1 (\exp(b_2 E_{zz}^2 + b_3 E_{zz} E_{\theta\theta} + b_4 E_{\theta\theta}^2 + b_5 E_{zz}^2 E_{\theta\theta} + b_6 E_{zz} E_{\theta\theta}^2 - 1))$ $+ (b_7 E_{\theta\theta} \exp(b_8 E_{\theta\theta}) + b_9 E_{zz} + b_{10} E_{\theta z}^2)$
Other models	
Vaishnav et al. [259]	$W = b_1 E_{\theta\theta}^2 + b_2 E_{\theta\theta} E_{zz} + b_3 E_{zz}^2 + b_4 E_{\theta\theta}^3 + b_5 E_{\theta\theta}^2 E_{zz} + b_6 E_{\theta\theta} E_{zz}^2$ $+ b_7 E_{zz}^3$
Rajagopal et al. [213]	$W = b_1 E_{11} + b_2 E_{22} + b_3 E_{33} + b_4 E_{11} E_{22} + b_5 E_{11} E_{33} + b_6 E_{22} E_{33}$ $+ b_7 E_{11}^2 + b_8 E_{22}^2 + b_9 E_{33}^2 + b_{10} E_{12}^2 + b_{11} E_{13}^2 + b_{12} E_{23}^2$
Tong and Fung [252]	$W = \frac{1}{2}(b_1 E_{11}^2 + b_2 E_{22}^2 + b_3 (E_{12}^2 + E_{21}^2)) + 2b_4 E_{12} E_{21}$ $+ [\frac{b_5}{2} \exp(b_6 E_{11}^2 + b_7 E_{22}^2 + b_8 (E_{12}^2 + E_{21}^2)) + 2b_9 E_{12} E_{21}$ $+ b_{10} E_{11}^3 + b_{11} E_{22}^3 + b_{12} E_{11}^2 E_{22} + b_{13} E_{11} E_{22}^2]^{-1}$
Humphrey [117]	$W = b_1 E_{rr}^2 + b_2 E_{\theta\theta}^2 + b_3 E_{zz}^2 + 2b_4 E_{rr} E_{\theta\theta} + 2b_5 E_{\theta\theta} E_{zz} + 2b_6 E_{rr} E_{zz}$ $+ b_7 (E_{r\theta}^2 + E_{\theta r}^2) + b_8 (E_{z\theta}^2 + E_{\theta z}^2) + b_9 (E_{zr}^2 + E_{rz}^2)$
Takamizawa and Hayashi [249]	$W = -c \ln(1 - (\frac{1}{2}b_1 E_{\theta\theta}^2 + \frac{1}{2}b_2 E_{zz}^2 + b_3 E_{\theta\theta} E_{zz} + b_4 E_{\theta\theta} E_{zz}$ $+ b_5 E_{\theta\theta} E_{rr} + b_6 E_{rr} E_{zz}))$
Nash and Hunter [175]	$W = c_{11} \frac{E_{11}^2}{ a_{11} - E_{11} ^{b_{11}}} + c_{22} \frac{E_{22}^2}{ a_{22} - E_{22} ^{b_{22}}} + c_{33} \frac{E_{33}^2}{ a_{33} - E_{33} ^{b_{33}}}$ $+ c_{12} \frac{E_{12}^2}{ a_{12} - E_{12} ^{b_{12}}} + c_{13} \frac{E_{13}^2}{ a_{13} - E_{13} ^{b_{13}}} + c_{23} \frac{E_{23}^2}{ a_{23} - E_{23} ^{b_{23}}}$

Moreover, the parameters of these materials are often difficult to fit as they have no physical meaning. For example, the strain energy of [259] is discussed in [104] and is not convex, this can also be the case for Fung functions if the parameters are not well chosen [104]. The limitations in material parameters are discussed in [71, 269] with respect to polyconvexity. In this way, developments have been made to ensure polyconvexity with a physical meaning of the material response [247]. Other conditions also must be respected for viable functions.

For example, the function defined in [175] requires a limit for each component. As a consequence, the domain limits of the function are well established. The question is different for [249] as the function is written in terms of the sum of the components in a logarithmic form and the function can be undefined [104].

4.2 Use of Strain Invariants

Strain energy densities depend on isotropic and anisotropic strain invariants. The use of I_4 and I_5 is necessary to recover linear theory [174]. Different cases exist. In a first case, the strain energy can be split as a sum into different parts as an isotropic and anisotropic contribution:

$$W = W^{iso}(I_1, I_2) + \sum_i W^{aniso}(I_4^{(i)}, I_5^{(i)}), \quad (26)$$

or some coupling can be realised between the isotropic and anisotropic parts as $W^{aniso}(I_1, I_2, I_4^{(i)}, I_5^{(i)})$. But very few models present a non-additive decomposition between two directions i and j , *i.e.*, between $I_4^{(i)}, I_5^{(i)}, I_4^{(j)}$ and $I_5^{(j)}$. When W^{iso} is used, it is often represented by a classical energy function. We discuss W^{aniso} in the next paragraph. The use of only I_4 or I_5 , instead of the both of these invariants is questionable as it leads to the same shear modulus in the direction of and in the direction orthogonal to the reinforced direction [174].

Different model forms can be distinguished such as the polynomial, the power, the exponential and other constitutive equations not of these types.

4.2.1 Polynomial Development

The most known model for isotropic hyperelasticity is Rivlin's series [217] that describes a general form of constitutive equations depending on the first and second invariants. The generalisation of this model to an anisotropic formulation has been proposed in different ways. One consists in introducing the anisotropic invariants in the series. First a simple I_4 series [123] was proposed:

$$W^{aniso} = \sum_{k=2}^n c_k (I_4 - 1)^k, \quad (27)$$

where c_k are material parameters. A linear term cannot be used, *i.e.*, $k = 1$ in the previous equation, as it does not ensure zero stress for zero deformation. The term $k = 2$ corresponds to the standard reinforcing model [61, 182, 220, 257], not initially proposed for soft tissues. The complete generalisation of the Rivlin series was proposed in [222]:

$$W = \sum_{klmn} c_{klmn} (I_1 - 3)^k (I_2 - 3)^l (I_4 - 1)^m (I_5 - 1)^n, \quad (28)$$

where c_{klmn} are material parameters. A modified formulation was proposed in [111] to be more convenient for numerical use:

$$W = \sum_{klmn} c_{klmn} (I_1 - 3)^k [(I_2 - 3) - 3(I_1 - 3)]^l (I_4 - 1)^m (I_5 - 2I_4 + 1)^n. \quad (29)$$

Instead of using I_4 , one may use $\sqrt{I_4}$ which represents the elongation in the considered direction. This leads to a new series development [115]:

$$W = \sum_{kl} c_{kl} (I_1 - 3)^k (\sqrt{I_4} - 1)^l, \quad (30)$$

Table 4 Some constitutive equations based on truncations of the series developments where c_i with $i = 1 \dots 6$ are material parameters

I_4 forms	
Triantafyllidis and Abeyaratne [257]	$W^{aniso} = c_2(I_4 - 1)^2$
Peng et al. [199]	$W^{aniso} = c_2(I_4 - 1)^2 + c_4(I_4 - 1)^4$
Basciano and Kleinstreuer [19]	$W^{aniso} = c_2(I_4 - 1)^2 + c_3(I_4 - 1)^3 + c_4(I_4 - 1)^4$ $+ c_5(I_4 - 1)^5 + c_6(I_4 - 1)^6$
Basciano and Kleinstreuer [19]	$W^{aniso} = c_6(I_4 - 1)^6$
Lin and Yin [148]	$W = c_1(I_1 - 3)(I_4 - 1) + c_2(I_1 - 3)^2 + c_3(I_4 - 1)^2$ $+ c_4(I_1 - 3) + c_5(I_4 - 1)$
$\sqrt{I_4}$ forms	
Alastrue et al. [4, 6]	$W^{aniso} = c_2(\sqrt{I_4} - 1)^2$
Humphrey [115]	$W = c_1(\sqrt{I_4} - 1)^2 + c_2(\sqrt{I_4} - 1)^3 + c_3(I_1 - 3)$ $+ c_4(I_1 - 3)(\sqrt{I_4} - 1) + c_5(I_1 - 3)^2$
I_4, I_5 forms	
Park and Youn [194]	$W^{aniso} = c_3(I_4 - 1) + c_5(I_5 - 1)$
Bonet and Burton [31]	$W = [c_1 + c_2(I_1 - 3) + c_3(I_4 - 1)](I_4 - 1) - \frac{c_1}{2}(I_5 - 1)$
Bonet and Burton [31]	$W^{aniso} = [c_1 + c_3(I_4 - 1)](I_4 - 1) - \frac{c_1}{2}(I_5 - 1)$
Merodio and Ogden [111, 169, 170]	$W^{aniso} = c_2(I_5 - 1)^2$
Hollingsworth and Wagner [102]	$W^{aniso} = c_2(I_5 - I_4^2)$
Murphy [174]	$W = c_1(I_1 - 3) + c_2(2I_4 - I_5 - 1) + c_3(I_5 - 1)^2$
Murphy [174]	$W = c_1(I_1 - 3) + c_2(2I_4 - I_5 - 1) + c_3(I_4 - 1)(I_5 - 1)$
Murphy [174]	$W = c_1(I_1 - 3) + c_2(2I_4 - I_5 - 1) + c_3(I_4 - 1)^2$

where c_{kl} are material parameters. It is worth noting that the use of $\sqrt{I_4}$ includes, in the quadratic formulation [6, 35], a model that represents the behaviour of a linear spring.

As other invariants were proposed, a series development based on β_k invariants also has been considered [52]:

$$W = \sum_{klm} G_{klm} \beta_3^k \beta_4^l \beta_5^m, \quad (31)$$

where G_{klm} are material parameters.

As for rubber like materials with the Rivlin's series, the whole series is not used and a good truncation of the strain energy is essential. According to the considered material and to the loading states, different developments have been given in the literature. A list of resulting equations is included in Table 4. It is also important to note that the I_4 invariant is often used whereas the I_5 invariant is most often disregarded.

4.2.2 Power Development

Ogden's [184] isotropic constitutive equation has proved its efficiency to describe complex behaviour. It is based on elongations and a power law development. For a material with a

Table 5 Model based on a power development, where k_i , $i = 1..6$ are material parameters

Power developments	
Ghaemi et al. [85]	$W^{aniso} = C(I_4^{k_1/2} - 1)^{k_2}$
Schroder et al. [50, 228, 230]	$W^{aniso} = k_1 I_4^{k_2}$
Balzani et al. [16, 17]	$W = k_1 (I_1 I_4 - I_5 - 2)^{k_2}$
Schroder et al. [230]	$W = k_1 (I_5 - I_1 I_4 + I_2) + k_2 I_4^{k_3} + k_4 (I_1 I_4 - I_5) + k_5 I_4^{k_6}$
O'Connell et al. [183]	$W = k_6 I_4 ((I_5 - I_1 I_4 + I_2) - 1)^2$

single fibre direction, there is the following generic form [186]:

$$W^{aniso} = \frac{2\mu_1}{\beta^2} (I_4^{\beta/2} + 2I_4^{-\beta/4} - 3), \quad (32)$$

where μ_1 and β are material parameters. A generalised form was proposed by not imposing the same parameters for the two terms [264]

$$W^{aniso} = \sum_r (\alpha_r (I_4^{\beta_r} - 1) + \gamma_r (I_4^{-\delta_r} - 1)), \quad (33)$$

where α_r , β_r , γ_r , δ_r are material parameters. The same type of formulation is also proposed using the other invariants. Two general equations are of the form [122]:

$$W = \sum_{klmn} c_{klmn} (I_1 - 3)^{a_k} (I_2 - 3)^{b_l} (I_4 - 1)^{c_m} (I_5 - 1)^{d_n} \quad \text{and} \quad (34)$$

$$W = \sum_{klmn} c_{klmn} (I_1^{a_k} - 3^{a_k}) (I_2^{b_l} - 3^{b_l}) (I_4^{c_m} - 1) (I_5^{d_n} - 1), \quad (35)$$

where c_{klmn} , a_k , b_l , c_m and d_n are material parameters. In the same way, other power law constitutive equations were proposed and are listed in Table 5. Additional forms can be found in the polyconvex strain energies listed in Table 1. These models represent different forms that link different invariants.

4.2.3 Exponential Development

A key property of the constitutive equation for soft tissues is the inclusion of an important strain hardening. This is easily obtained by means of an exponential function of the I_4 invariant. This approach is largely used in the literature, the first models were proposed in the 1990s. In the beginning, two fibre directions were introduced to represent the mechanical behaviour of arteries [104]. This was extended to four directions [13, 159] and to n directions [82] and used for example with 8 directions for cerebral aneurysms [276]. These models may be used to model the behaviour of a complex tissue such as in different areas of a soft tissue (as for example the different layers of an artery) [18]. Various formulations are listed in Table 6.

In order to take into account the ratio of isotropic to anisotropic parts of a heterogeneous material, a weighting factor has been introduced based on the contributions of I_1 and I_4 [107]. This represents a measure of dispersion in the fibre orientation. This model leads to

Table 6 List of exponential constitutive equations, where c_1, c_2, c_3, c_4, c_5 and κ are material parameters

I_4 forms	
Humphrey and Yin [114]	$W^{aniso} = c_1 (\exp(c_2(\sqrt{I_4} - 1)^2) - 1)$
Weiss et al. [268]	$W^{aniso} = c_1 (\exp(I_4 - 1) - I_4)$
Ciarletta et al. [50]	$W^{aniso} = c_1 (\exp(c_2 I_4^{c_3}) - 1)$
Pinsky et al. [201]	$W^{aniso} = \frac{c_1}{c_2} (\exp(c_2(I_4 - 1)) - c_2 I_4)$
Natali et al. [176]	$W^{aniso} = \frac{c_1}{c_2} \{ \exp(c_2(I_4 - 1)) - c_2(I_4 - 1) - 1 \}$
Holzapfel et al. [104]	$W^{aniso} = \frac{c_1}{2c_2} [\exp(c_2(I_4 - 1)^2) - 1]$
Weiss et al. [268]	$W^{aniso} = c_1 (\exp(I_4 - 1)^2 - (I_4 - 1)^2 - 1)$
Peña et al. [196]	$W^{aniso} = \frac{c_1}{c_2} [\exp(c_2(I_4 - 1)) - c_2(I_4 - 1) - 1]$
I_1, I_4 forms	
Holzapfel et al. [105]	$W^{aniso} = c_1 (I_4 - 1) \exp(c_2(I_4 - 1)^2)$
Gasser et al. [83]	$W = \frac{c_1}{2c_2} [\exp\{c_2[\kappa I_1 + (1 - 3\kappa)I_4 - 1]^2\} - 1]$
Holzapfel et al. [107]	$W = \frac{c_1}{2c_2} \{ \exp(c_2((1 - \kappa)(I_1 - 3)^2 + \kappa(I_4 - 1)^2) - 1) \}$
May-Newman and Yin [161, 162]	$W = c_0 (\exp(c_1(I_1 - 3)^2 + c_2(\sqrt{I_4} - 1)^4) - 1)$
Rubin and Bodner [221]	$W = \frac{c_1}{2c_2} (\exp(c_2(c_5(I_1 - 3) + \frac{c_3}{c_4}(\sqrt{I_4} - 1)^{2c_4})) - 1)$
Lin and Yin [148]	$W = c_1 (\exp(c_2(I_1 - 3)^2 + c_3(I_1 - 3)(I_4 - 1) + c_4(I_4 - 1)^2) - 1)$
Doyle et al. [64]	$W = c_1 (\exp(c_2(I_1 - 3)^2 + c_3(I_1 - 3)(I_4 - 1) + c_4(I_4 - 1)^2$ $+ c_5(I_1 - 3) + c_6(I_4 - 1)) - 1)$
Fung et al. [78]	$W = c_1 (\exp(c_2(I_1 - 3)^2 + c_3(I_1 - 3)(I_4 - 1) + c_4(I_4 - 1)^2) - 1)$ $+ c_5(I_1 - 3)^2 + c_6(I_4 - 1)^2 + c_7(I_1 - 3)(I_4 - 1)$
I_4, I_5 forms	
Masson et al. [160]	$W^{aniso} = \frac{C_1}{2C_2} (\exp\{C_2(I_4 - 1)^2\} - 1) + \frac{C_3}{2C_4} (\exp\{C_4(I_5 - 1)^2\} - 1)$

the creation of different constitutive equations which are also listed in Table 6. Recently, a general form of an energy function was devised [197] in order to summarise a large number of constitutive equations:

$$W = \frac{\gamma}{a\eta} [\exp(\eta(I_1 - 3)^a) - f_1(I_1, a)] + \frac{c_i}{bd_i} [\exp(d_i(I_4^{(i)} - I_4^0)^b) - g(I_4^{(i)}, I_4^0, b)]. \quad (36)$$

The choice of the functions f_1 and g allows for the wide generalization of many different models. Also, $\gamma, \eta, a, b, c_i, d_i$ and I_4^0 are material parameters, and I_4^0 represents the threshold to reach for the fibre to become active. Some authors [68, 75] have proposed in a way similar as to what is done in the case of isotropy [96] a constitutive equation for the stress, the energy being obtained by integration:

$$\sigma(\lambda) = A \left(\exp \left(B \frac{\lambda^2 - 1}{2} \right) - 1 \right), \quad (37)$$

Table 7 Other models written in invariants, where c_i with $i = 1...7$ are material parameters

General forms	
Horgan and Saccomandi [111]	$W_{,4} = -\frac{c_1+c_2(I_4-1)}{c_3+c_4(I_4-1)+c_5(I_4-1)^2+c_6(I_5-2I_4+1)}$
Horgan and Saccomandi [111]	$W_{,4} = -\frac{c_1+c_2(I_4-1)}{c_3+c_4(I_4-1)}$
Ruter and Stein [222]	$W = c_2(\cosh(I_4 - 1) - 1)$
Horgan and Saccomandi [111]	$W = -c_2c_3(I_4 - 1 + c_3 \ln(1 - \frac{I_4-1}{c_3}))$
Ogden and Saccomandi [187]	$W = -\frac{c_2}{2}c_3 \ln(1 - \frac{(I_4-1)^2}{c_3})$
Horgan and Saccomandi [111]	$W = -\frac{c_2}{n}c_3 \ln(1 - \frac{(I_4-1)^n}{c_3})$
Dorfmann et al. [63]	$W^{an} = c_2[1 - c_3 \tanh(\frac{I_4-1}{c_4})][\exp(c_5(I_4 - 1)^2) - 1]$
Markert et al. [157]	$W = \frac{c_1}{c_2}(I_4^{c_2/2} - 1) - c_1 \ln(I_4^{1/2})$
Limbirt and Middleton [146]	$W = 2c_5\sqrt{I_4} + c_6 \ln(I_4)$
Calvo et al. [38]	$W = 2c_5\sqrt{I_4} + c_6 \ln(I_4) + c_7$
Demirkoparan et al. [59, 60]	$W = \frac{2}{3}(\frac{I_4}{c_1^2} + 2\frac{c_1}{\sqrt{I_4}} - 3)$
Horgan and Saccomandi [111]	$W = -c_1c_2 \log(1 - \frac{(I_5-1)^2}{c_2})$
Lurding et al. [153]	$W = c_1(I_1 - 3) + c_2(I_1 - 3)(I_4 - 1) + c_3(I_4^2 - I_5) \\ + c_4(\sqrt{I_4} - 1)^2 + c_5 \ln(I_4)$
Chui et al. [153]	$W = c_1 \ln(1 - T) + c_5(I_1 - 3)^2 + c_6(I_4 - 1)^2 + c_7(I_1 - 3)(I_4 - 1) \\ \text{with } T = c_2(I_1 - 3)^2 + c_3(I_4 - 1)^2 + c_4(I_1 - 3)(I_4 - 1)$
Other invariants	
Lu and Zhang [151]	$W = c_2 \exp(c_1(\sqrt{I_4} - 1)^2) + \frac{1}{2}c_3(\beta_1 - 1) + \frac{1}{2}c_4(\beta_2 - 2)$

where A and B are material parameters.

Even if this approach was initially developed and used for arteries [43, 205, 260], it is also often used for different living tissues, as for example human cornea [190], erythrocytes [130], the mitral valve [203], trachea [155, 254], cornea [139, 179], collagen [125], abdominal muscle [101].

4.2.4 Some Other Models

Other ideas have been developed for rubber like materials, as for example the Gent [84] model which presents a large strain hardening with only two parameters. Its specific form gives it a particular interest for some tissues. This model was generalised to anisotropy in two ways [111]. Other different forms can be proposed with a logarithmic or a tangent function. A list of constitutive equations is given in Table 7. There are two ideas in these models. One is to describe the behaviour at moderate deformation. Thus, functions that provide for a weak slope are used; these models are principally used before the activation of muscles, *i.e.*, when the material is very soft. When the material becomes stiffer, a function that models a large strain hardening is necessary. In this way, different functions were introduced to capture very important changes of slopes.

4.2.5 Coupling Influence

Different coupling can be taken into account in the constitutive equation, for example, the shear between the fibres and the matrix, and the interaction between the fibres.

Fibre Shear. In this case, the soft tissue is considered as a composite material, the strain energy is decomposed into three additive parts $W = W^m + W^f + W^{fm}$ [199], where the three terms are the strain energy of the matrix, of the fibres and of the interactions between fibres and matrix, respectively. Moreover, the deformation gradient of the fibres \mathbf{F} can be decomposed into a uniaxial extension tensor \mathbf{F}_f and a shear deformation \mathbf{F}_s , as $\mathbf{F} = \mathbf{F}_s \mathbf{F}_f$ [52]. The decomposition of the strain energy function into different parts allows, for different loading states, the consideration of constitutive equations which are specific for the strain endured by the fibre, the matrix and the interface. This leads to the construction of different function forms [92]:

$$\begin{cases} W^m = \frac{1}{2}c_1 f(I_4)(I_1 - 3), \\ W^f = c_1 g_1(I_4) \left(\frac{I_5 - I_4^2}{I_4} \right), \\ W^{fm} = c_1 g_2(I_4) \left(I_1 - \frac{I_5 + 2\sqrt{I_4}}{I_4} \right). \end{cases} \quad (38)$$

Another basic form also has been proposed [199]:

$$W^{fm} = g_2(I_4) \left[\frac{I_4}{I_3} (I_5 - I_1 I_4 + I_2) - 1 \right]^2, \quad (39)$$

where f , g_1 and g_2 are functions to define and c_1 is a material parameter. The first function corresponds a generalisation of the neo-Hookean model [93]. Few functions for f , g_1 and g_2 have so far been proposed, the first being based on exponential functions [40, 91, 92].

Interaction Between Fibres. Few models are proposed to take into account the influence of the coupling between different fibre directions. Different techniques can be used.

In order to take into account different directions and to not limit the problem to one direction fibre, it is also possible to couple invariants from different directions [228], the following invariant expression has been proposed:

$$\alpha^2 I_4^{(1)2} + 2\lambda(1 - \alpha) I_4^{(1)} I_4^{(2)} + (1 - \alpha)^2 I_4^{(2)2} \quad \text{with } \alpha \in [0, 1]. \quad (40)$$

α represents a material parameter. This expression takes into account the deformation in two directions with only one invariant. Nevertheless, this has not yet been used in constitutive equations.

Instead of employing an additive decomposition of the strain energy to account for the different directions, a function that represents a coupling between the invariants of different directions [102] can be used [242]:

$$W = \frac{c_1}{c_2} [\exp(c_2(I_4^{(1)} + I_4^{(2)} - 2)) - c_2(I_4^{(1)} + I_4^{(2)}) + 2c_2 - 1]. \quad (41)$$

A generalised weighted expression of the constitutive equation also has been developed [67, 121]:

$$W = \frac{1}{4} \sum_r \mu_r \left[\frac{1}{\alpha_r} \left(\exp \left(\alpha_r \left(\sum_i \gamma_i I_4^{(i)} - 1 \right) \right) - 1 \right) + \frac{1}{\beta_r} \left(\exp \left(\beta_r \left(\sum_i \gamma_i J_5^{(i)} - 1 \right) \right) - 1 \right) \right]. \quad (42)$$

Even if the model was developed for pneumatic membranes, such representations that have proposed multiplicative terms between the I_4 invariants of each direction instead of an additive decomposition can be used for soft tissues [215]:

$$W = c_1^{(1)} (I_4^{(1)} - 1)^{\beta_1} + c_2^{(1)} (I_5^{(1)} - 1)^{\beta_2} + c_1^{(2)} (I_4^{(2)} - 1)^{\gamma_1} + c_2^{(2)} (I_5^{(2)} - 1)^{\gamma_2} + c_c^{(1)} (I_1 - 3)^{\delta_1} (I_4^{(1)} - 1)^{\delta_1} + c_c^{(2)} (I_1 - 3)^{\delta_2} (I_4^{(2)} - 1)^{\delta_2} + c_c^{(1,2)} (I_4^{(1)} - 1)^\eta (I_4^{(2)} - 1)^\eta. \quad (43)$$

This strain energy introduces coupling between the different directions, but the additive decomposition of the constitutive equation allows one to fit separately the different parameters $c_i^{(j)}$, δ_i and β_i .

Use of I_8 and I_9 . As proposed in the first part of this paper, coupling terms including $I_8^{(i,j)}$ and $I_9^{(i,j)}$ can be used. Thus such terms have been added to the strain energy in order to model esophageal tissues [177]:

$$W = \frac{c_1}{c_3} \exp[c_3(I_1 - 3)] + \frac{c_2}{c_5} \exp[c_5(I_2 - 3)] + \frac{c_4}{c_7^2} \{ \exp[c_7(I_4^{(1)} - 1)] - c_7(I_4^{(1)} - 1) - 1 \} + \frac{c_6}{c_8^2} \{ \exp[c_8(I_4^{(2)} - 1)] - c_8(I_4^{(2)} - 1) - 1 \} + c_9 [I_8^{(1,2)} - I_9^{(1,2)}]^2, \quad (44)$$

where c_i with $i = 1 \dots 9$ are material parameters. For annulus fibrous tissues, the influence of the interaction between the layers has been modelled [178] with an energy term taking into account $I_4^{(1)}$, $I_4^{(2)}$ and $I_8^{(1,2)}$:

$$W = \frac{c_1}{2c_2} \left(\exp \left(c_2 \left(\frac{I_8^{(1,2)}}{(I_4^{(1)} I_4^{(2)} I_9^{(1,2)})^{1/2}} - \sqrt{I_9^{(1,2)}} \right)^2 \right) - 1 \right). \quad (45)$$

A similar form of exponential model (cf. Table 6) has been proposed to include the effect of I_8 [88]:

$$W = \frac{c_1}{c_2} \left[\exp \left(c_2 \frac{(I_8^{(1,2)})^2}{I_9^{(1,2)}} \right) - 1 \right]. \quad (46)$$

These models are not often employed, but there exist some for composite materials that can be used [200, 214]. In comparison with other models, these approaches take into account the shear strain in the material whereas the first models couple the deformations of the different fibres.

5 Statistical Approaches

In this part, some statistical approaches that tend to encompass the physics of soft tissues physics are detailed. They come from the study of the collagen network and use a change of scale method [45, 181]. A collagen molecule is defined by its length, its stiffness and its helical structure. Some studies are motivated by approaches developed for rubber like material [21, 73, 129]. Unlike polymer chains in rubber which are uncorrelated in nature, collagen chains in biological tissues are classified as correlated chains from a statistical point of view. Rubber chains resemble a random walk whereas biological chains often present privileged oriented directions. In this way, different theories are considered to represent the chains, as for example wormlike chains with a slight varying curvature [132], or sinusoidal, zig-zag or circular helix representations [75, 126, 140].

Nevertheless, to develop models which rest on statistical approaches, some hypotheses are needed. A distribution function f of the orientation of the fibres is used to represent the material. The unit vector \mathbf{a}_0 oriented in the direction of a certain amount of fibres having a spatial orientation distribution f is defined in terms of two spherical angles, denoted as ϕ and ψ :

$$\mathbf{a}_0 = \sin \phi \cos \psi \mathbf{e}_1 + \sin \phi \sin \psi \mathbf{e}_2 + \sin \phi \mathbf{e}_3, \quad (47)$$

with $\phi \in [0, \pi]$ and $\psi \in [0, 2\pi]$ and \mathbf{e}_i is the usual rectangular Cartesian basis. The distribution function is required to satisfy some elementary properties [191]. By symmetry requirements $f(\mathbf{a}_0) = f(-\mathbf{a}_0)$. The quantity $f(\mathbf{a}_0) \sin \phi d\phi d\psi$ represents the number of fibres with an orientation in the range $[(\phi, \phi + d\phi), (\psi, \psi + d\psi)]$. By considering the unit sphere S around a material point, the following property is deduced:

$$\frac{1}{4\pi} \int_S f(\mathbf{a}_0) dS = \frac{1}{4\pi} \int_0^\pi \int_0^{2\pi} f(\mathbf{a}_0) \sin \phi d\phi d\psi = 1. \quad (48)$$

A constant distribution leads to isotropy [10].

The strain energy of the soft tissue can then be deduced by integration of the elementary fibre energy in each direction $w(I_4(\mathbf{a}_0))$ by:

$$W = \frac{1}{4\pi} \int_S f(\mathbf{a}_0) w(I_4(\mathbf{a}_0)) dS. \quad (49)$$

Finally, the stress is determined by derivation:

$$\mathbf{S} = \frac{1}{2\pi} \int_S f(\mathbf{a}_0) \frac{\partial w(I_4(\mathbf{a}_0))}{\partial \mathbf{C}} dS. \quad (50)$$

The evaluation of the stress depends on different parameters: the distribution function and the energy of a single fibre. Different considerations have been proposed in the literature. For the distribution function, the principal propositions are: beta distribution [2, 37, 218, 225], log-logistic distribution [277], Gaussian distribution [24, 44, 65, 141, 223, 272], von Mises distribution [5, 83, 87, 191, 211, 263] or the Bingham distribution [6]. The forms of the distribution are listed in Table 8. The choice of the functions is also a key point. Different functions can be chosen to describe the mechanical behaviour of a collagen fibre; the simple linear behaviour [10], or the phenomenological laws of the exponential Fung type [5, 24, 125, 211, 225, 263] or a logarithmic function [277] or a polynomial function [74, 248], other functions [119, 207] or worm-like chain forms [5, 6, 25, 26, 36, 81, 135, 136,

Table 8 Some distribution functions used in statistical approaches, where ε_0 , b , σ , M and I are statistical parameters

Distribution functions	
Beta distribution	$\beta(\eta, \gamma) = \frac{\Gamma(\eta)\Gamma(\gamma)}{\Gamma(\eta+\gamma)}$ with $\Gamma(x) = \int_0^\infty t^{x-1} \exp(-t) dt$
Log-logistic distribution	$f(\varepsilon) = \frac{k}{b} \frac{(\varepsilon-\varepsilon_0/b)^{k-1}}{[1+(\varepsilon-\varepsilon_0/b)^k]^2}$ with $\varepsilon = \sqrt{I_4} - 1$
Gaussian distribution	$f(\phi) = \frac{1}{\sigma\sqrt{2\pi}} \exp\left(-\frac{(\phi-M)^2}{2\sigma^2}\right)$
Normalized von Mises distribution	$f(\phi) = \frac{4}{I} \sqrt{\frac{b}{2\pi}} \exp[b(\cos 2\phi + 1)]$ with $I = \frac{2}{\sqrt{\pi}} \int_0^{\sqrt{2b}} \exp(-t^2) dt$
Bingham distribution	$f(\mathbf{r}, \mathbf{A}) = [K(\mathbf{A})]^{-1} \exp(\mathbf{r}^T \cdot \mathbf{A} \mathbf{r})$ \mathbf{A} is a symmetric matrix, \mathbf{r} a vector and $K(\mathbf{A})$ a normalized constant

Table 9 Some fibre functions used in statistical approaches where k_1 , k_2 , r_0 , L , K , W_r , γ_m and m are material parameters

Energy functions	
Holzappel et al. function	$w = \frac{k_1}{k_2} [\exp(k_2(I_4 - 1)^2) - 1]$
Logarithmic function	$w = c(\varepsilon - \log(\varepsilon + 1))$ for $\varepsilon > 0$ with $\varepsilon = \sqrt{I_4} - 1$
Polynomial function	$w = \frac{1}{2} K [\gamma + \sum_{m=2}^M \frac{\gamma_m}{m} (\frac{\gamma}{\gamma_m})^m]$
Worm-like chain	$w = \frac{nk\theta L}{4A} [2\frac{r_1^2}{L^2} + \frac{1}{1-r_1/L} - \frac{r_1}{L} - \frac{\ln(I_4^2 r_0^2)}{4r_0 L} [4\frac{r_0}{L} + \frac{1}{[1-r_0/L]^2} - 1] - W_r]$ with $r_i = \sqrt{I_4} r_0$ and $W_r = 2\frac{r_0^2}{L^2} + \frac{1}{1-r_0/L} - \frac{r_0}{L}$

164, 216, 218] which are a particularisation of the eight-chain model [9] to the transversely isotropic case. For some models, a parameter should be introduced in the fibre concentration factor to control collagen fibre alignment along a preferred orientation [87]. The different constitutive equations are listed in Table 9. The reader can refer to [28] to determine which strain energy is used for each tissue.

The main difficulty of the different constitutive equations is that they need a numerical integration that is always time consuming [28, 211]. The integration of the fibre contribution is mainly realised over a referential unit sphere [134, 172]. Some prefer to use a finite number of directions, the constitutive equation is thus modified as follows:

$$\frac{1}{4\pi} \int_S (\cdot) dS = \sum_{i=1}^m w^i (\cdot)^i. \quad (51)$$

Different choices exist, as the 42 directions of Bazant and Oh [20] and by Menzel [164], or the 184 directions of Alastrue *et al.* [5], for example. The only different approach to those mentioned above is that proposed by [74] who used only six initial directions without employing an integration. Even if statistical approaches have more complex equations than phenomenological ones, some of these models have been implemented in finite element codes [5, 81, 135, 136, 164, 275].

6 Discussion


The main difficulty is not to find the better constitutive equation but to have suitable experimental data. In fact, the difficulty is often that there is a large dispersion in experimental data due to the dispersion between the different specimens. Moreover, it is often difficult to impose different loading conditions on similar specimens. Thus the errors are often large and the number of loading conditions is often limited. As a consequence, one can wonder if the key point is to obtain the best fit for a very specific experimental database, or if the most important point is to represent globally the mechanical behaviour keeping in mind the physics of soft tissues.

As it was shown in the previous paragraphs, the number of constitutive equations that can be used to describe soft tissues non-linear elasticity is very impressive. Moreover, there exist other approaches, not presented in this paper, which involve a new class of elastic solids with implicit elasticity [212] that can also describe the strain limiting characteristics of soft tissues [76]. These theories are also elastic as they do not dissipate energies even though they are written in terms of strain rate and stress rate. But in this paper, we only focus on hyperelastic energy functions. These functions are expressed in terms of strain tensor components or strain invariants. The main difference between the two approaches discussed here is that the invariants formulation permits one to split the energy function into additive isotropic and anisotropic parts, even if, some constitutive equations written in invariants also link these two parts. The first constitutive equations introduced for soft tissues were isotropic. Although, for some applications, an isotropic constitutive equation is used to describe the mechanical behaviour for different soft tissues, the use of such simplified models is, in many cases, misleading and inappropriate as most soft tissues have a fibre structure that must be taken into account. To represent this structure, many constitutive equations are based on privileged directions that correspond to physical fibre orientations. In the modelling, characteristic directions are defined and they are represented by an angle that defines the orientation of the fibre compared to a specific direction. This angle can be considered as a parameter that is used to fit as well as possible the experimental data. Thus, the model is not used to mimic the physical soft tissue but it is used as a phenomenological equation to describe properly experimental data. This is not, in our opinion, a good choice, and it may mean that the energy function is not well chosen. The angle between the fibres should not be an adjustable parameter but must be imposed by the soft tissue structure.

An important issue in modelling concerns the stretching resistance of fibres. Many authors consider that the fibre must reach a threshold before opposing a stress. In this way, a threshold parameter can be introduced in all the suitable constitutive equations presented in this review. For the phenomenological model, it consist in replacing $(I_4 - 1)$ by $(I_4 - I_4^0)$, or $(\sqrt{I_4} - 1)$ by $(\sqrt{I_4} - \sqrt{I_4^0})$ in the constitutive equations. I_4^0 corresponds to the needed deformation to generate stress, see for example [38, 107, 197, 219]. The advantage of such approaches is that there is a material parameter that controls the beginning of material stiffening. Nevertheless, a main difficulty is that it strongly depends on the zero state of the experimental data. Moreover, this zero state is often different between post-mortem and in-vivo specimens, and can depend on the experimenter.

Anisotropic strain energy functions are difficult to fit, as it is difficult to separate the contribution between the matrix and the fibres, and to distinguish the different parts of the strain energy. Nevertheless, some strategies based on dissociating isotropic and anisotropic parts can be used [94]. To avoid such representations, physical approaches attempt to represent the repartition of fibres in space, but two difficulties must be considered; the knowledge of the distribution function of the fibres in space and the mechanical properties of a single fibre.

Fig. 1 Organisation of the constitutive equations in the paper

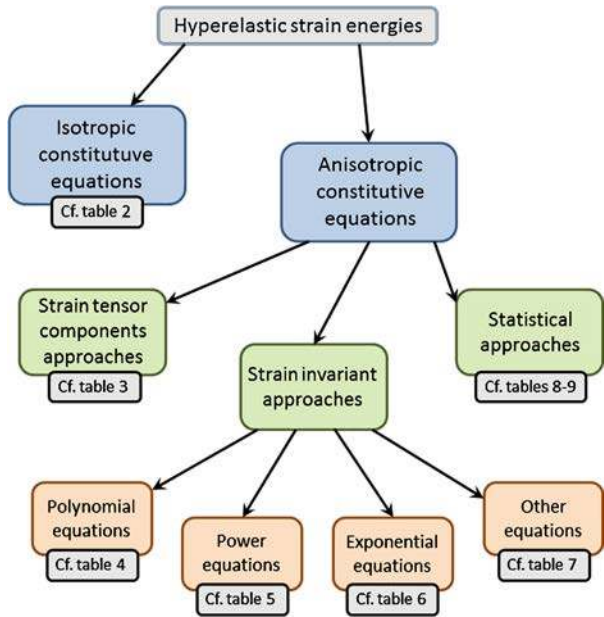

The choice of the best strain energy function is always a difficult point in the modelling process. A summary of the constitutive equations is presented in Fig. 1. In practise, the invariants I_2 and I_5 are often neglected. Their contribution is always difficult to determine [115] but it can be useful [72]. Moreover, these invariants are not independent from I_1 and I_4 in uniaxial loading tests. In this case, it is important to have also biaxial loadings to fit constitutive equations [224]. Moreover, in vivo experimental data [233] would be a benefit to obtain a good experimental fit, but there is little such data in the literature as compared to post-mortem experimental data. The constitutive equation choice will depend on the particular soft tissues under study and the conclusions will strongly depend on the experimental data that is chosen. Nevertheless, some comparisons between anisotropic strain energies have been realised in particular cases, see, for example, [41, 79, 104, 116, 117, 265].

In practice, a strategic point is the choice of a constitutive equation that is implemented in a finite element code to describe loading conditions that are very far from uniaxial or biaxial loadings. In this case, it is important to choose a constitutive equation that can be fitted with few experimental data that do not simulate non-physical response for any loading. Generally, it is better to limit the number of invariants and material parameters. Moreover, the simplest functions are often the best as they stand the least probability of creating non-physical responses even if their fitting is not the best.

7 Conclusion

This paper has listed many different constitutive equations that have been developed for soft tissues. The number of constitutive equations to represent the contribution due to hyperelasticity is extensive due to the number of soft tissues and the experimental data dispersion. The paper has listed first, isotropic constitutive equations, and next anisotropic ones, and these were classed in different categories; those written with strain tensor components, those written in terms of the invariants, and those based on statistical modelling.

Despite all the difficulties encountered in the modelling of the isotropic or anisotropic hyperelastic behaviour of soft tissue, these constitutive equations must be considered as only the basis of a more complex constitutive equation. Generalized equations should take into account other phenomena such as the activation of muscle [39, 158, 188, 189, 250] or the viscoelasticity of the tissues [27, 99, 105, 147, 208] or stress softening [154, 195], for example. Nevertheless, the hyperelasticity representation should remain as the starting point in a modelling program and should be described as well as possible before introducing other effects.

Acknowledgements The authors thank Prof. Roger Fosdick for his valuable comments. This work is supported by the French National Research Agency Program ANR-12-BS09-0008-01 SAMBA (Silicone Architected Membranes for Biomedical Applications).

References

1. Abraham, A.C., Moyer, J.T., Villegas, D.F., Odegard, G.M., Haut Donahue, T.L.: Hyperelastic properties of human meniscal attachments. *J. Biomech.* **44**, 413–418 (2011)
2. Abramowitz, M., Stegun, I.A.: *Handbook of Mathematical Functions with Formulas, Graphs, and Mathematical Tables*. National Bureau of Standards, Applied Mathematics Series vol. 55 (1964)
3. Agoras, M., Lopez-Pamies, O., Ponte Castañeda, P.: A general hyperelastic model for incompressible fiber-reinforced elastomers. *J. Mech. Phys. Solids* **57**, 268–286 (2009)
4. Alastrué, V., Peña, E., Martínez, M.A., Doblaré, M.: Experimental study and constitutive modelling of the passive mechanical properties of the ovine infrarenal vena cava tissue. *J. Biomech.* **41**, 3038–3045 (2008)
5. Alastrué, V., Martínez, M.A., Doblaré, M., Menzel, A.: Anisotropic microsphere-based finite elasticity applied to blood vessel modelling. *J. Mech. Phys. Solids* **57**, 178–203 (2009)
6. Alastrué, V., Martínez, M.A., Doblaré, M., Menzel, A.: On the use of the bingham statistical distribution in microsphere-based constitutive models for arterial tissue. *Mech. Res. Commun.* **37**, 700–706 (2010)
7. Arnoux, P.J.: *Modélisation des ligaments des membres porteurs*. Ph.D. thesis, Université de la Méditerranée (2000)
8. Arnoux, P.J., Chabrand, P., Jean, M., Bonnoit, J.: A viscohyperelastic model with damage for the knee ligaments under dynamic constraints. *Comput. Methods Biomech. Biomed. Eng.* **5**, 167–174 (2002)
9. Arruda, E.M., Boyce, M.C.: A three dimensional constitutive model for the large stretch behavior of rubber elastic materials. *J. Mech. Phys. Solids* **41**(2), 389–412 (1993)
10. Ateshian, G.A.: Anisotropy of fibrous tissues in relation to the distribution of tensed and buckled fibers. *J. Biomech. Eng.* **129**, 240–249 (2007)
11. Ateshian, G.A., Costa, K.D.: A frame-invariant formulation of fung elasticity. *J. Biomech.* **42**, 781–785 (2009)
12. Azar, F.S., Metaxas, D.N., Schnall, M.D.: A deformable finite element model of the breast for predicting mechanical deformations under external perturbations. *Acad. Radiol.* **8**, 965–975 (2001)
13. Baek, S., Gleason, R.L., Rajagopal, K.R., Humphrey, J.D.: Theory of small on large: potential utility in computations of fluid-solid interactions in arteries. *Comput. Methods Appl. Mech. Eng.* **196**, 3070–3078 (2007)
14. Ball, J.M.: Convexity conditions and existence theorems in non-linear elasticity. *Arch. Ration. Mech. Anal.* **63**, 557–611 (1977)
15. Ball, J.M.: Constitutive equalities and existence theorems in elasticity. In: Knops, R.J. (ed.) *Symposium on Non-well Posed Problems and Logarithmic Convexity*. Lecture Notes in Math., vol. 316. Springer, Berlin (1977)
16. Balzani, D., Neff, P., Schröder, J., Holzapfel, G.A.: A polyconvex framework for soft biological tissues. Adjustment to experimental data. *Int. J. Solids Struct.* **43**, 6052–6070 (2006)
17. Balzani, D., Schröder, J., Gross, D.: Simulation of discontinuous damage incorporating residual stresses in circumferentially overstretched atherosclerotic arteries. *Acta Biomater.* **2**, 609–618 (2006)
18. Balzani, D., Brands, D., Klawonn, A., Rheinbach, O., Schröder, J.: On the mechanical modeling of anisotropic biological soft tissue and iterative parallel solution strategies. *Arch. Appl. Mech.* **80**, 479–488 (2010)
19. Basciano, C.A., Kleinstreuer, C.: Invariant-based anisotropic constitutive models of the healthy and aneurysmal abdominal aortic wall. *J. Biomech. Eng.* **131**, 1–11 (2009)

20. Bažant, Z.P., Oh, B.H.: Efficient numerical integration on the surface of a sphere. *Z. Angew. Math. Mech.* **66**, 37–49 (1986)
21. Beatty, M.F.: An average-stretch full-network model for rubber elasticity. *J. Elast.* **70**, 65–86 (2004)
22. Bell, J.: *The Experimental Foundations of Solid Mechanics, Mechanics of Solids.* Springer, Berlin (1984)
23. Bilgili, E.: Restricting the hyperelastic models for elastomers based on some thermodynamical, mechanical and empirical criteria. *J. Elastomers Plast.* **36**, 159–175 (2004)
24. Billar, K.L., Sacks, M.S.: Biaxial mechanical properties of the native and glutaraldehyde-treated aortic valve cusp: Part II—a structural constitutive model. *J. Biomech. Eng.* **122**, 327–335 (2000)
25. Bischoff, J.E., Arruda, E.M., Grosh, K.: A microstructurally based orthotropic hyperelastic constitutive law. *J. Appl. Mech.* **69**, 570–579 (2002)
26. Bischoff, J.E., Arruda, E.M., Grosh, K.: Orthotropic hyperelasticity in terms of an arbitrary molecular chain model. *J. Appl. Mech.* **69**, 198–201 (2002)
27. Bischoff, J.E., Arruda, E.M., Grosh, K.: A rheological network model for the continuum anisotropic and viscoelastic behavior of soft tissue. *Biomech. Model. Mechanobiol.* **3**, 56–65 (2004)
28. Bischoff, J.E.: Continuous versus discrete (invariant) representations of fibrous structure for modeling non-linear anisotropic soft tissue behavior. *Int. J. Non-Linear Mech.* **41**, 167–179 (2006)
29. Boehler, J.: *Applications of Tensor Functions in Solid Mechanics.* CISM Courses and Lectures, vol. 292, pp. 13–30. Springer, Berlin (1987)
30. Boehler, J.: A simple derivation of representations for non-polynomial constitutive equations in some cases of anisotropy. *J. Appl. Math. Mech.* **59**, 157–167 (1979)
31. Bonet, J., Burton, A.J.: A simple orthotropic, transversely isotropic hyperelastic constitutive equation for large strain computations. *Comput. Methods Appl. Mech. Eng.* **162**, 151–164 (1998)
32. Bose, K., Dorfmann, A.: Computational aspects of a pseudo-elastic constitutive model for muscle properties in a soft-bodied arthropod. *Int. J. Non-Linear Mech.* **44**, 42–50 (2009)
33. Boubaker, M.B., Haboussi, M., Ganghoffer, J.F., Aletti, P.: Finite element simulation of interactions between pelvic organs: predictive model of the prostate motion in the context of radiotherapy. *J. Biomech.* **42**, 1862–1868 (2009)
34. Boyce, M.C., Arruda, E.M.: Constitutive models of rubber elasticity: a review. *Rubber Chem. Technol.* **73**, 504–523 (2000)
35. Brown, L.W., Smith, L.M.: A simple transversely isotropic hyperelastic constitutive model suitable for finite element analysis of fiber reinforced elastomers. *J. Eng. Mater. Technol.* **133**, 1–13 (2011)
36. Bustamante, C., Bryant, Z., Smith, S.B.: Ten years of tension: single-molecule DNA mechanics. *Nature* **421**, 423–427 (2003)
37. Cacho, F., Elbischger, P., Rodriguez, J., Doblaré, M., Holzapfel, G.: A constitutive model for fibrous tissue sconsidering collagen fiber crimp. *Int. J. Non-Linear Mech.* **42**, 391–402 (2007)
38. Calvo, B., Peña, E., Martins, P., Mascarenhas, T., Doblaré, M., Natal Jorge, R.M., Ferreira, A.: On modelling damage process in vaginal tissue. *J. Biomech.* **42**, 642–651 (2009)
39. Calvo, B., Ramirez, A., Alonso, A., Grasa, J., Soteras, F., Osta, R., Muñoz, M.J.: Passive non linear elastic behaviour of skeletal muscle: experimental results and model formulation. *J. Biomech.* **43**, 318–325 (2010)
40. Caner, F.C., Guo, Z., Moran, B., Bazant, Z.P., Carol, I.: Hyperelastic anisotropic microplane constitutive model for annulus fibrosus. *Trans. Am. Soc. Mech. Eng.* **129**, 1–10 (2007)
41. Carboni, M., Desch, G.W., Weizsacker, H.W.: Passive mechanical properties of porcine left circumflex artery and its mathematical description. *Med. Eng. Phys.* **29**, 8–16 (2007)
42. Chagnon, G., Marckmann, G., Verron, E.: A comparison of the physical model of Arruda–Boyce with the empirical Hart–Smith model and the Gent model. *Rubber Chem. Technol.* **77**, 724–735 (2004)
43. Chagnon, G., Gaudin, V., Favier, D., Orgeas, L., Cinquin, P.: An osmotically inflatable seal to treat endoleaks of type I. *J. Mech. Med. Biol.* **12**, 1250070 (2012)
44. Chen, L., Yin, F.C.P., May-Newman, K.: The structure and mechanical properties of the mitral valve leaflet-strut chordae transition zone. *J. Biomech. Eng.* **126**, 244–251 (2004)
45. Chen, H., Zhao, X., Lu, X., Kassab, G.: Nonlinear micromechanics of soft tissues. *Int. J. Non-Linear Mech.* **56**, 79–85 (2013)
46. Cheng, T., Dai, C., Gan, R.Z.: Viscoelastic properties of human tympanic membrane. *Ann. Biomed. Eng.* **35**, 305–314 (2007)
47. Cheng, T., Gan, R.Z.: Mechanical properties of anterior malleolar ligament from experimental measurement and material modeling analysis. *Biomech. Model. Mechanobiol.* **7**, 387–394 (2008)
48. Choi, H.S., Vito, R.P.: Two-dimensional stress-strain relationship for canine pericardium. *J. Biomech. Eng.* **112**, 153–159 (1990)
49. Chuong, C.J., Fung, Y.C.: Three-dimensional stress distribution in arteries. *J. Biomech. Eng.* **105**(3), 268–274 (1983)

50. Ciarletta, P., Izzo, I., Micera, S., Tendick, F.: Stiffening by fiber reinforcement in soft materials: a hyperelastic theory at large strains and its application. *J. Mech. Behav. Biomed. Mater.* **4**, 1359–1368 (2011)
51. Costa, K.D., Hunter, P.J., Waldman, L.K., Guccione, J.M., McCulloch, A.: A three-dimensional finite element method for large elastic deformations of ventricular myocardium: Part II—prolate-spherical coordinates. *J. Biomech. Eng.* **118**, 464–472 (1996)
52. Criscione, J.C., Douglas, A.S., Hunter, W.C.: Physically based strain invariants set for materials exhibiting transversely isotropic behavior. *J. Mech. Phys. Solids* **49**, 871–891 (2001)
53. Criscione, J.C., McCulloch, A.D., Hunter, W.C.: Constitutive framework optimized for myocardium and other high-strain, laminar materials with one fiber family. *J. Mech. Phys. Solids* **50**, 1691–1702 (2002)
54. deBotton, G., Hariton, I., Socolsky, E.A.: Neo-Hookean fiber-reinforced composites in finite elasticity. *J. Mech. Phys. Solids* **54**, 533–559 (2006)
55. deBotton, G., Shmuel, G.: Mechanics of composites with two families of finitely extensible fibers undergoing large deformations. *J. Mech. Phys. Solids* **57**, 1165–1181 (2009)
56. Delfino, A., Stergiopoulos, N., Moore, J.E. Jr, Meister, J.J.: Residual strain effects on the stress field in a thick wall finite element model of the human carotid bifurcation. *J. Biomech.* **30**(8), 777–786 (1997)
57. Demiray, H.: A note on the elasticity of soft biological tissues. *J. Biomech.* **5**, 309–311 (1972)
58. Demiray, H., Weizsacker, H.W., Pascale, K., Erbay, H.: A stress strain relation for a rat abdominal aorta. *J. Biomech.* **21**, 369–374 (1988)
59. Demirkoparan, H., Pence, T.: Swelling of an internally pressurized nonlinearly elastic tube with fiber reinforcing. *Int. J. Solids Struct.* **44**, 4009–4029 (2007)
60. Demirkoparan, H., Ansari, T.J.P., Wineman, A.: On dissolution and reassembly of filamentary reinforcing networks in hyperelastic materials. *Proc. R. Soc. A* **465**, 867–894 (2009)
61. Destrade, M., Gilchrist, M.D., Prikazhnikov, D.A., Saccomandi, G.: Surface instability of sheared soft tissues. *J. Biomech. Eng.* **130**, 1–6 (2008). 061007
62. Doll, S., Schweizerhof, K.: On the development of volumetric strain energy functions. *J. Appl. Mech.* **67**, 17–21 (2000)
63. Dorfmann, A.L., Woods, W.A. Jr., Trimmer, B.A.: Muscle performance in a soft-bodied terrestrial crawler: constitutive modeling of strain-rate dependency. *J. R. Soc. Interface* **5**, 349–362 (2008)
64. Doyle, M.G., Tavoularis, S., Bourgault, Y.: Adaptation of a rabbit myocardium material model for use in a canine left ventricle simulation study. *J. Biomech. Eng.* **132**, 041006 (2010)
65. Driessen, N.J.B., Bouten, C.V.C., Baaijens, F.P.T.: A structural constitutive model for collagenous cardiovascular tissues incorporating the angular fiber distribution. *J. Biomed. Eng.* **124**, 494–503 (2005)
66. Ebbling, V., Schröder, J., Neff, P.: Approximation of anisotropic elasticity tensors at the reference state with polyconvex energies. *Arch. Appl. Mech.* **79**, 651–657 (2009)
67. Ehret, A.E., Itskov, M.: A polyconvex hyperelastic model for fiber-reinforced materials in application to soft tissues. *J. Mater. Sci.* **42**, 8853–8863 (2007)
68. Einstein, D.R., Freed, A.D., Standar, N., Fata, B., Vesel, I.: Inverse parameter fitting of biological tissues: a response surface approach. *Ann. Biomed. Eng.* **33**, 1819–1830 (2005)
69. Epstein, E.H., Munderloh, N.H.: Isolation and characterisation of c-nbr peptides of human $[\alpha_1(iii)]_3$ collagen and tissue distribution $[\alpha_1(i)]_2\alpha_2$ and $[\alpha_1(iii)]_3$ collagen. *J. Biol. Chem.* **250**, 9304–9312 (1975)
70. Ericksen, J.L., Rivlin, R.S.: Large elastic deformations of homogeneous anisotropic materials. *Arch. Ration. Mech. Anal.* **3**, 281–301 (1954)
71. Federico, S., Grillo, A., Imatani, S., Giaquinta, G., Herzog, W.: An energetic approach to the analysis of anisotropic hyperelastic materials. *Int. J. Eng. Sci.* **46**, 164–181 (2008)
72. Feng, Y., Okamoto, R.J., Namani, R., Genin, G.M., Bayly, P.V.: Measurements of mechanical anisotropy in brain tissue and implications for transversely isotropic material models of white matter. *J. Mech. Behav. Biomed. Mater.* **23**, 117–132 (2013)
73. Flory, P.J.: *Statistical Mechanics of Chain Molecules* (1969)
74. Flynn, C., Rubin, M.B.: An anisotropic discrete fibre model based on a generalised strain invariant with application to soft biological tissues. *Int. J. Eng. Sci.* **60**, 66–76 (2012)
75. Freed, A.D., Einstein, D.R., Vesely, I.: Invariant formulation for dispersed transverse isotropy in aortic heart valves. *Biomech. Model. Mechanobiol.* **4**, 100–117 (2005)
76. Freed, A.D., Einstein, D.R.: An implicit elastic theory for lung parenchyma. *Int. J. Eng. Sci.* **62**, 31–47 (2013)
77. Fung, Y.C., Fronek, K., Patitucci, P.: Pseudoelasticity of arteries and the choice of its mathematical expression. *Am. J. Physiol.* **237**, H620–H631 (1979)
78. Fung, Y.C., Liu, S., Zhou, J.: Remodeling of the constitutive equation while a blood vessel remodels itself under stress. *J. Biomech. Eng.* **115**, 453–459 (1993)

79. Galle, B., Ouyang, H., Shi, R., Nauman, E.: A transversely isotropic constitutive model of excised guinea pig spinal cord white matter. *J. Biomech.* **43**, 2839–2843 (2010)
80. Garcia, J.J., Cortes, D.H.: A nonlinear biphasic viscohyperelastic model for articular cartilage. *J. Biomech.* **39**, 2991–2998 (2006)
81. Garikipati, K., Arruda, E.M., Grosh, K., Narayanan, H., Calve, S.: A continuum treatment of growth in biological tissue: the coupling of mass transport and mechanics. *J. Mech. Phys. Solids* **52**, 1595–1625 (2004)
82. Gasser, T.C., Holzapfel, G.A.: A rate-independent elastoplastic constitutive model for biological fiber-reinforced composites at finite strains: continuum basis, algorithmic formulation and finite element implementation. *Comput. Mech.* **29**, 340–360 (2002)
83. Gasser, T.C., Ogden, R.W., Holzapfel, G.A.: Hyperelastic modelling of arterial layers with distributed collagen fibre orientations. *J. R. Soc. Interface* **3**, 15–35 (2006)
84. Gent, A.N.: A new constitutive relation for rubber. *Rubber Chem. Technol.* **69**, 59–61 (1996)
85. Ghaemi, H., Behdinin, K., Spence, A.D.: In vitro technique in estimation of passive mechanical properties of bovine heart. Part II. Constitutive relation and finite element analysis. *Med. Eng. Phys.* **31**, 83–91 (2009)
86. Gilchrist, M.D., Murphy, J.G., Rashid, B.: Generalisations of the strain-energy function of linear elasticity to model biological soft tissue. *Int. J. Non-Linear Mech.* **47**, 268–272 (2012)
87. Girard, M.J.A., Downs, J.C., Burgoyne, C.F., Francis Suh, J.-K.: Peripapillary and posterior scleral mechanics—Part I: development of an anisotropic hyperelastic constitutive model. *J. Biomech. Eng.* **131**, 051011 (2009)
88. Göktepe, S., Acharya, S.N.S., Wong, J., Kuhl, E.: Computational modeling of passive myocardium. *Int. J. Numer. Methods Biomed. Eng.* **27**, 1–12 (2011)
89. Gras, L.L., Mitton, D., Viot, P., Laporte, S.: Hyper-elastic properties of the human sternocleidomastoideus muscle in tension. *J. Mech. Behav. Biomed. Mater.* **15**, 131–140 (2012)
90. Groves, R.B., Coulman, S.A., Birchall, J.C., Evans, S.L.: An anisotropic, hyperelastic model for skin: experimental measurements, finite element modelling and identification of parameters for human and murine skin. *J. Mech. Behav. Biomed. Mater.* **18**, 167–180 (2013)
91. Guo, Z.Y., Peng, X.Q., Moran, B.: A composites-based hyperelastic constitutive model for soft tissue with application to the human annulus fibrosus. *J. Mech. Phys. Solids* **54**, 1952–1971 (2006)
92. Guo, Z.Y., Peng, X.Q., Moran, B.: Large deformation response of a hyperelastic fibre reinforced composite: theoretical model and numerical validation. *Composites, Part A, Appl. Sci. Manuf.* **38**, 1842–1851 (2007)
93. Guo, Z.Y., Peng, X.Q., Moran, B.: Mechanical response of neo-Hookean fiber reinforced incompressible nonlinearly elastic solids. *Int. J. Solids Struct.* **44**, 1949–1969 (2007)
94. Harb, N., Labed, N., Domaszewski, M., Peyraut, F.: A new parameter identification method of soft biological tissue combining genetic algorithm with analytical optimization. *Comput. Methods Appl. Mech. Eng.* **200**, 208–215 (2011)
95. Harrison, S., Bush, M., Petros, P.: Towards a novel tensile elastometer for soft tissue. *Int. J. Mech. Sci.* **50**, 626–640 (2008)
96. Hart-Smith, L.J.: Elasticity parameters for finite deformations of rubber-like materials. *Z. Angew. Math. Phys.* **17**, 608–626 (1966)
97. Hartmann, S.: Parameter estimation of hyperelasticity relations of generalized polynomial-type with constraint conditions. *Int. J. Solids Struct.* **38**, 7999–8018 (2001)
98. Hartmann, S., Neff, P.: Polyconvexity of generalized polynomial-type hyperelastic strain energy functions for near-incompressibility. *Int. J. Solids Struct.* **40**, 2767–2791 (2003)
99. Haslach, H.W.: Nonlinear viscoelastic, thermodynamically consistent, models for biological soft tissue. *Biomech. Model. Mechanobiol.* **3**, 172–189 (2005)
100. Helfenstein, J., Jabareen, M., Mazza, E., Govindjee, S.: On non-physical response in models for fiber-reinforced hyperelastic materials. *Int. J. Solids Struct.* **47**, 2056–2061 (2010)
101. Hernandez, B., Peña, E., Pascual, G., Rodriguez, M., Calvo, B., Doblaré, M., Bellón, J.M.: Mechanical and histological characterization of the abdominal muscle. a previous step to modelling hernia surgery. *J. Mech. Behav. Biomed. Mater.* **4**, 392–404 (2011)
102. Hollingsworth, N.T., Wagner, D.R.: Modeling shear behavior of the annulus fibrosus. *J. Mech. Behav. Biomed. Mater.* **4**, 1103–1114 (2011)
103. Holmes, M., Mow, V.C.: The non-linear characteristics of soft gels and hydrated connective tissues in ultrafiltration. *J. Biomech.* **23**, 1145–1156 (1990)
104. Holzapfel, G.A., Gasser, T.C., Ogden, R.W.: A new constitutive framework for arterial wall mechanics and a comparative study of material models. *J. Elast.* **61**, 1–48 (2000)
105. Holzapfel, G.A., Gasser, T.C., Stadler, M.: A structural model for the viscoelastic behavior of arterial walls: continuum formulation and finite element analysis. *Eur. J. Mech. A, Solids* **21**, 441–463 (2002)

106. Holzapfel, G.A., Gasser, T.C., Ogden, R.W.: Comparison of multi-layer structural model for arterial walls with a Fung-type model, and issues of material stability. *J. Biomech. Eng.* **126**, 264–275 (2004)
107. Holzapfel, G.A., Sommer, G., Gasser, C.T., Regitnig, P.: Determination of the layer-specific mechanical properties of human coronary arteries with non-atherosclerotic intimal thickening, and related constitutive modelling. *Am. J. Physiol., Heart Circ. Physiol.* **289**, 2048–2058 (2005)
108. Holzapfel, G.A., Stadler, M., Gasser, T.C.: Changes in the mechanical environment of stenotic arteries during interaction with stents: computational assessment of parametric stent design. *J. Biomech. Eng.* **127**, 166–180 (2005)
109. Holzapfel, G.A., Mulvihill, J.J., Cunnane, E.M., Walsh, M.T.: Computational approaches for analyzing the mechanics of atherosclerotic plaques: a review. *J. Biomath.* **47**, 859–869 (2014)
110. Horgan, C.O., Saccomandi, G.: Simple torsion of isotropic, hyperelastic, incompressible materials with limiting chain extensibility. *J. Elast.* **56**, 159–170 (1999)
111. Horgan, C.O., Saccomandi, G.: A new constitutive theory for fiber-reinforced incompressible nonlinearly elastic solids. *J. Mech. Phys. Solids* **53**, 1985–2015 (2005)
112. Horgan, C.O., Smayda, M.G.: The importance of the second strain invariant in the constitutive modeling of elastomers and soft biomaterials. *Mech. Mater.* **51**, 43–52 (2012)
113. Hostettler, A., George, D., Rémond, Y., Nicolau, S.A., Soler, L., Marescaux, J.: Bulk modulus and volume variation measurement of the liver and the kidneys in vivo using abdominal kinetics during free breathing. *Comput. Methods Programs Biomed.* **100**, 149–157 (2010)
114. Humphrey, J.D., Yin, F.C.P.: On constitutive relations and finite deformations of passive cardiac tissue: I. A pseudo strain-energy approach. *J. Biomech. Eng.* **109**, 298–304 (1987)
115. Humphrey, J.D., Strumpf, R.K., Yin, F.C.P.: Determination of a constitutive relation for passive myocardium: I. A new functional form. *J. Biomech. Eng.* **15**, 1413–1418 (1990)
116. Humphrey, J.D.: Mechanics of arterial wall: review and directions. *Crit. Rev. Biomed. Eng.* **23**, 1–162 (1995)
117. Humphrey, J.D.: *Cardiovascular Solid Mechanics. Cells, Tissues and Organs.* Springer, New York (2002)
118. Humphrey, J.D.: Continuum biomechanics of soft biological tissues. *Proc. R. Soc. Lond. A* **459**, 3–46 (2003)
119. Hurschler, C., Loitz-Ramage, B., Vanderby, R. Jr: A structurally based stress-stretch relationship for tendon and ligament. *J. Biomech. Eng.* **119**, 392–399 (1997)
120. Itskov, M., Aksel, N.: A class of orthotropic and transversely isotropic hyperelastic constitutive models based on a polyconvex strain energy function. *Int. J. Solids Struct.* **41**, 3833–3848 (2004)
121. Itskov, M., Ehret, A.E., Mavrilas, D.: A polyconvex anisotropic strain energy function for soft collagenous tissues. *Biomech. Model. Mechanobiol.* **5**, 17–26 (2006)
122. Jemiolo, S., Telega, J.J.: Transversely isotropic materials undergoing large deformations and application to modelling soft tissues. *Mech. Res. Commun.* **28**, 397–404 (2001)
123. Kaliske, M.: A formulation of elasticity and viscoelasticity for fibre reinforced material at small and finite strains. *Comput. Methods Appl. Mech. Eng.* **185**, 225–243 (2000)
124. Kalita, P., Schaefer, R.: Mechanical models of artery walls. *Arch. Comput. Methods Eng.* **15**, 1–36 (2008)
125. Karsaj, I., Sansour, C., Soric, J.: The modelling of fibre reorientation in soft tissue. *Biomech. Model. Mechanobiol.* **8**, 359–370 (2009)
126. Kastelic, J., Palley, I., Baer, E.: A structural mechanical model for tendon crimping. *J. Biomech.* **13**, 887 (1980)
127. Kaster, T., Sack, I., Samani, A.: Measurement of the hyperelastic properties of ex vivo brain tissue slices. *J. Biomech.* **44**, 1158–1163 (2011)
128. Kas'yanov, V.A., Rachev, A.I.: Deformation of blood vessels upon stretching, internal pressure, and torsion. *Mech. Compos. Mater.* **16**, 76–80 (1990)
129. Kloczkowski, A.: Application of statistical mechanics to the analysis of various physical properties of elastomeric networks—a review. *Polymer* **43**, 1503–1525 (2002)
130. Kloppel, T., Wall, W.A.: A novel two-layer, coupled finite element approach for modeling the nonlinear elastic and viscoelastic behavior of human erythrocytes. *Biomech. Model. Mechanobiol.* **10**, 445–459 (2011)
131. Knowles, J.K.: The finite anti-plane shear field near the tip of a crack for a class of incompressible elastic solid. *Int. J. Fract.* **13**, 611–639 (1977)
132. Kratky, O., Porod, G.: Röntgenuntersuchungen gelöster fadenmoleküle. *Recl. Trav. Chim.* **68**, 1106–1122 (1949)
133. Kroon, M., Holzapfel, G.A.: A new constitutive model for multilayered collagenous tissues. *J. Biomech.* **41**, 2766–2771 (2008)

134. Kuhl, E., Ramm, E.: Microplane modelling of cohesive frictional materials. *Eur. J. Mech. A, Solids* **19**, S121–S143 (2000)
135. Kuhl, E., Garikipati, K., Arruda, E.M., Grosh, K.: Remodeling of biological tissue: mechanically induced reorientation of a transversely isotropic chain network. *J. Mech. Phys. Solids* **53**, 1552–1573 (2005)
136. Kuhl, E., Menzel, A., Garikipati, K.: On the convexity of transversely isotropic chain network models. *Philos. Mag.* **86**, 3241–3258 (2006)
137. Kuhn, W., Grün, F.: Beziehung zwischen elastischen konstanten und dehnungsdoppelbrechung hochelastischerstoffe. *Kolloideitschrift* **101**, 248–271 (1942)
138. Labrosse, M.R., Beller, C.J., Mesana, T., Veinot, J.P.: Mechanical behavior of human aortas: experiments, material constants and 3-D finite element modeling including residual stress. *J. Biomech.* **42**, 996–1004 (2009)
139. Lanchares, E., Calvo, B., Cristobal, J.A., Doblaré, M.: Finite element simulation of arcuates for astigmatism correction. *J. Biomech.* **41**, 797–805 (2008)
140. Lanir, Y.: Structure-strength relations in mammalian tendon. *Biophys. J.* **24**, 541–554 (1978)
141. Lanir, Y.: A structural theory for the homogeneous biaxial stress-strain relationship in flat collagenous tissues. *J. Biomech.* **12**, 423–436 (1979)
142. Lapeer, R.J., Gasson, P.D., Karri, V.: Simulating plastic surgery: from human skin tensile tests, through hyperelastic finite element models to real-time haptics. *Prog. Biophys. Mol. Biol.* **103**, 208–216 (2010)
143. Li, W.G., Hill, N.A., Ogden, R.W., Smythe, A., Majeed, A.W., Bird, N., Luo, X.Y.: Anisotropic behaviour of human gallbladder walls. *J. Mech. Behav. Biomed. Mater.* **20**, 363–375 (2013)
144. Li, Z., Alonso, J.E., Kim, J.-E., Davidson, J., Etheridge, B.S., Eberhardt, A.W.: Three-dimensional finite element models of the human pubic symphysis with viscohyperelastic soft tissues. *Ann. Biomed. Eng.* **34**, 1452–1462 (2006)
145. Limbert, G., Taylor, M.: On the constitutive modeling of biological soft connective tissues. A general theoretical framework and explicit forms of the tensors of elasticity for strongly anisotropic continuum fiber-reinforced composites at finite strain. *Int. J. Solids Struct.* **39**, 2343–2358 (2002)
146. Limbert, G., Middleton, J.: A transversely isotropic viscohyperelastic material application to the modeling of biological soft connective tissues. *Int. J. Solids Struct.* **41**, 4237–4260 (2004)
147. Limbert, G., Middleton, J.: A constitutive model of the posterior cruciate ligament. *Med. Eng. Phys.* **28**, 99–113 (2006)
148. Lin, D.H.S., Yin, F.C.P.: A multi-axial constitutive law for mammalian left ventricular myocardium in steady-state barium contracture or tetanus. *J. Biomech. Eng.* **120**, 504–517 (1998)
149. Lister, K., Gao, Z., Desai, J.P.: Development of in vivo constitutive models for liver: application to surgical simulation. *Ann. Biomed. Eng.* **39**, 1060–1073 (2011)
150. Lopez-Pamies, O., Idiart, M.I.: Fiber-reinforced hyperelastic solids: a realizable homogenization constitutive theory. *J. Eng. Math.* **68**, 57–83 (2010)
151. Lu, J., Zhang, L.: Physically motivated invariant formulation for transversely isotropic hyperelasticity. *Int. J. Solids Struct.* **42**, 6015–6031 (2005)
152. Lu, J., Zhou, X., Raghavan, M.L.: Computational method of inverse elastostatics for anisotropic hyperelastic solids. *Int. J. Numer. Methods Eng.* **69**, 1239–1261 (2007)
153. Lurding, D., Basar, Y., Hanskotter, U.: Application of transversely isotropic materials to multi-layer shell elements undergoing finite rotations and large strains. *Int. J. Solids Struct.* **38**, 9493–9503 (2001)
154. Maher, E., Creane, A., Lally, C., Kelly, D.J.: An anisotropic inelastic constitutive model to describe stress softening and permanent deformation in arterial tissue. *J. Mech. Behav. Biomed.* **12**, 9–19 (2012)
155. Malvé, M., Pérez del Palomar, A., Trabelsi, O., Lopez-Villalobos, J.L., Ginel, A., Doblaré, M.: Modeling of the fluid structure interaction of a human trachea under different ventilation conditions. *Int. Commun. Heat Mass Transf.* **38**, 10–15 (2011)
156. Marieb, E., Hoehn, K.: *Human Anatomy & Physiology*. Pearson Education, Upper Saddle River (2010)
157. Markert, B., Ehlers, W., Karajan, N.: A general polyconvex strain-energy function for fiber-reinforced materials. *Proc. Appl. Math. Mech.* **5**, 245–246 (2005)
158. Martins, J.A.C., Pires, E.B., Salvador, R., Dinis, P.B.: A numerical model of passive and active behaviour of skeletal muscles. *Comput. Methods Appl. Mech. Eng.* **151**, 419–433 (1998)
159. Masson, I., Boutouyrie, P., Laurent, S., Humphrey, J.D., Zidi, M.: Characterization of arterial wall mechanical behavior and stresses from human clinical data. *J. Biomech.* **41**, 2618–2627 (2008)
160. Masson, I., Fassot, C., Zidi, M.: Finite dynamic deformations of a hyperelastic, anisotropic, incompressible and prestressed tube. Applications to in vivo arteries. *Eur. J. Mech. A, Solids* **29**, 523–529 (2010)
161. May-Newman, K., Yin, F.C.P.: A constitutive law for mitral valve tissue. *Am. J. Physiol.* **269**, 1319–1327 (1998)

162. May-Newman, K., Lam, C., Yin, F.C.P.: A hyperelastic constitutive law for aortic valve tissue. *J. Biomech. Eng.* **131**, 1–7 (2009)
163. Menzel, A., Steinmann, P.: On the comparison of two strategies to formulate orthotropic hyperelasticity. *J. Elast.* **62**, 171–201 (2001)
164. Menzel, A., Waffenschmidt, T.: A microsphere-based remodelling formulation for anisotropic biological tissues. *Philos. Trans. R. Soc. A* **367**, 3499–3523 (2009)
165. Merodio, J., Pence, T.J.: Kink surfaces in a directionally reinforced neo-Hookean material under plane deformation: I. Mechanical equilibrium. *J. Elast.* **62**, 119–144 (2001)
166. Merodio, J., Pence, T.J.: Kink surfaces in a directionally reinforced neo-Hookean material under plane deformation: II. Kink band stability and maximally dissipative band broadening. *J. Elast.* **62**, 145–170 (2001)
167. Merodio, J., Ogden, R.W.: Material instabilities in fiber-reinforced nonlinearly elastic solids under plane deformation. *Arch. Mech.* **54**, 525–552 (2002)
168. Merodio, J., Ogden, R.W.: Instabilities and loss of ellipticity in fiber-reinforced compressible nonlinearly elastic solids under plane deformation. *Int. J. Solids Struct.* **30**, 4707–4727 (2003)
169. Merodio, J., Ogden, R.W.: Mechanical response of fiber-reinforced incompressible non-linearly elastic solids. *Int. J. Non-Linear Mech.* **40**, 213–227 (2005)
170. Merodio, J., Ogden, R.W.: On tensile instabilities and ellipticity loss in fiber-reinforced incompressible non-linearly elastic solids. *Mech. Res. Commun.* **32**, 290–299 (2005)
171. Merodio, J.: A note on tensile instabilities and loss of ellipticity for a fiber-reinforced nonlinearly elastic solid. *Arch. Mech.* **58**, 293–303 (2006)
172. Miehe, C., Göktepe, S., Lulei, F.: A micro-macro approach to rubber-like materials—Part I: the non-affine micro-sphere model of rubber elasticity. *J. Mech. Phys. Solids* **52**, 2617–2660 (2004)
173. Mielke, A.: Necessary and sufficient conditions for polyconvexity of isotropic functions. *J. Convex Anal.* **12**, 291–314 (2005)
174. Murphy, J.: Transversely isotropic biological, soft tissue must be modelled using both anisotropic invariants. *Eur. J. Mech. A, Solids* **42**, 90–96 (2013)
175. Nash, M.P., Hunter, P.J.: Computational mechanics of the heart: from tissue structure to ventricular function. *J. Elast.* **61**, 113–141 (2000)
176. Natali, A.N., Pavan, P.G., Carniel, E.L., Dorow, C.: A transversally isotropic elasto-damage constitutive model for the periodontal ligament. *Comput. Methods Biomech. Biomed. Eng.* **6**, 329–336 (2003)
177. Natali, A.N., Carniel, E.L., Gregersen, H.: Biomechanical behaviour of oesophageal tissues: material and structural configuration, experimental data and constitutive analysis. *Med. Eng. Phys.* **31**, 1056–1062 (2009)
178. Nerurkar, N.L., Mauck, R.L., Elliott, D.M.: Modeling interlamellar interactions in angle-ply biologic laminates for annulus fibrosus tissue engineering. *Biomech. Model. Mechanobiol.* **10**, 973–984 (2011)
179. Nguyen, T.D., Boyce, B.L.: An inverse finite element method for determining the anisotropic properties of the cornea. *Biomech. Model. Mechanobiol.* **10**, 323–337 (2011)
180. Nicholson, D.W.: Tangent modulus matrix for finite element analysis of hyperelastic materials. *Acta Mech.* **112**, 187–201 (1995)
181. Nierenberger, M., Rémond, Y., Ahzi, S.: A new multiscale model for the mechanical behavior of vein walls. *J. Mech. Behav. Biomed. Mater.* **23**, 32–43 (2013)
182. Ning, X., Zhu, Q., Lanir, Y., Margulies, S.S.: A transversely isotropic viscoelastic constitutive equation for brainstem undergoing finite deformation. *J. Biomech. Eng.* **128**, 925–933 (2006)
183. O’Connell, G.D., Guerin, H.L., Elliott, D.M.: Theoretical and uniaxial experimental evaluation of human annulus fibrosus degeneration. *J. Biomech. Eng.* **131**, 111007 (2009)
184. Ogden, R.W.: Large deformation isotropic elasticity—on the correlation of theory and experiment for incompressible rubber like solids. *Proc. R. Soc. Lond. A* **326**, 565–584 (1972)
185. Ogden, R.W.: *Non-linear Elastic Deformations*. Dover, New York (1997)
186. Ogden, R.W.: Nonlinear elasticity, anisotropy, material stability and residual stresses in soft tissue. In: Holzappel, G.A., Ogden, R.W. (eds.) *Biomechanics of Soft Tissue in Cardiovascular System*. CISM Courses and Lecture, vol. 441. Springer, New York (2003)
187. Ogden, R.W., Saccomandi, G.: Introducing mesoscopic information into constitutive equations for arterial walls. *Biomech. Model. Mechanobiol.* **6**, 333–344 (2007)
188. Paetsch, C., Trimmer, B.A., Dorfmann, A.: A constitutive model for active–passive transition of muscle fibers. *Int. J. Non-Linear Mech.* **47**, 377–387 (2012)
189. Paetsch, C., Dorfmann, A.: Non-linear modeling of active biohybrid materials. *Int. J. Non-Linear Mech.* **56**, 105–114 (2013)
190. Pandolfi, A., Maganiello, F.: A model for the human cornea: constitutive formulation and numerical analysis. *Biomech. Model. Mechanobiol.* **5**, 237–246 (2006)

191. Pandolfi, A., Vasta, M.: Fiber distributed hyperelastic modeling of biological tissues. *Mech. Mater.* **44**, 151–162 (2012)
192. Papaharilaou, Y., Ekaterinaris, J.A., Manousakid, E., Katsamouris, A.N.: A decoupled fluid structure approach for estimating wall stress in abdominal aortic aneurysms. *J. Biomech.* **40**, 367–377 (2007)
193. Parente, M.P.L., Natal Jorge, R.M., Mascarenhas, T., Fernandes, A.A., Martins, J.A.C.: The influence of the material properties on the biomechanical behavior of the pelvic floor muscles during vaginal delivery. *J. Biomech.* **42**, 1301–1306 (2009)
194. Park, H.C., Youn, S.K.: Finite element analysis and constitutive modelling of anisotropic nonlinear hyperelastic bodies with convected frames. *Comput. Methods Appl. Mech. Eng.* **151**, 605–618 (1998)
195. Peña, E., Peña, J.A., Doblaré, M.: On the Mullins effect and hysteresis of fibered biological materials: a comparison between continuous and discontinuous damage models. *Int. J. Solids Struct.* **46**, 1727–1735 (2009)
196. Peña, E., Calvo, B., Martínez, M.A., Martins, P., Mascarenhas, T., Jorge, R.M.N., Ferreira, A., Doblaré, M.: Experimental study and constitutive modeling of the viscoelastic mechanical properties of the human prolapsed vaginal tissue. *Biomech. Model. Mechanobiol.* **9**, 35–44 (2010)
197. Peña, E.: Prediction of the softening and damage effects with permanent set in fibrous biological materials. *J. Mech. Phys. Solids* **59**, 1808–1822 (2011)
198. Peña, E., Martins, P., Mascarenhas, T., Natal Jorge, R.M., Ferreira, A., Doblaré, M., Calvo, B.: Mechanical characterization of the softening behavior of human vaginal tissue. *J. Mech. Behav. Biomed. Mater.* **4**, 275–283 (2011)
199. Peng, X.Q., Guo, Z.Y., Roman, B.: An anisotropic hyperelastic constitutive model with fiber-matrix shear interaction for the human annulus fibrosus. *J. Appl. Mech.* **73**, 815–824 (2006)
200. Peng, X., Guo, Z., Du, T., Yu, W.R.: A simple anisotropic hyperelastic constitutive model for textile fabrics with application to forming simulation. *Composites, Part B, Eng.* **52**, 275–281 (2013)
201. Pinsky, P.M., van der Heide, D., Chernyak, D.: Computational modeling of mechanical anisotropy in the cornea and sclera. *J. Cataract Refract. Surg.* **31**, 136–145 (2005)
202. Prevost, T.P., Balakrishnan, A., Suresh, S., Socrate, S.: Biomechanics of brain tissue. *Acta Biomater.* **7**, 83–95 (2011)
203. Prot, V., Haaverstad, R., Skallerud, B.: Finite element analysis of the mitral apparatus: annulus shape effect and chordal force distribution. *Biomech. Model. Mechanobiol.* **8**, 43–55 (2009)
204. Przybylo, P.A., Arruda, E.M.: Experimental investigations and numerical modeling of incompressible elastomers during non-homogeneous deformations. *Rubber Chem. Technol.* **71**, 730–749 (1998)
205. Qian, M., Wells, D.M., Jones, A., Becker, A.: Finite element modelling of cell wall properties for onion epidermis using a fibre-reinforced hyperelastic model. *J. Struct. Biol.* **172**, 300–304 (2010)
206. Qiu, G.Y., Pence, T.: Remarks on the behaviour of a simple directionally reinforced incompressible non linearly elastic solids. *J. Elast.* **49**, 1–30 (1997)
207. Quapp, K.M., Weiss, J.A.: Material characterization of human medical collateral ligament. *J. Biomech. Eng.* **124**, 757–763 (1998)
208. Quaglini, V., Vena, P., Contro, R.: A discrete-time approach to the formulation of constitutive models for viscoelastic soft tissues. *Biomech. Model. Mechanobiol.* **3**, 85–97 (2004)
209. Raghavan, M., Webster, M.W., Vorp, D.A.: Ex vivo biomechanical behavior of abdominal aortic aneurysm: assessment using a new mathematical model. *Ann. Biomed. Eng.* **24**, 573–582 (1996)
210. Raghavan, M., Vorp, D.A.: Toward a biomechanical tool to evaluate rupture potential of abdominal aortic aneurysm: identification of a finite strain constitutive model and evaluation of its applicability. *J. Biomech.* **33**, 475–482 (2000)
211. Raghupathy, R., Barocas, V.H.: A closed-form structural model of planar fibrous tissue mechanics. *J. Biomech.* **42**, 1424–1428 (2009)
212. Rajagopal, K.: On implicit constitutive theories. *Appl. Math.* **48**, 279–319 (2003)
213. Rajagopal, K., Bridges, C., Rajagopal, K.R.: Towards an understanding of the mechanics underlying aortic dissection. *Biomech. Model. Mechanobiol.* **6**, 345–359 (2007)
214. Rebouah, M., Chagnon, G., Favier, D.: Development and modeling of filled silicone architected membranes. *Meccanica* (2014). doi:10.1007/s11012-014-0065-0
215. Reese, S., Raible, T., Wriggers, P.: Finite element modelling of orthotropic material behaviour in pneumatic membranes. *Int. J. Solids Struct.* **38**, 9525–9544 (2001)
216. Rief, M., Oesterhelt, F., Heymann, B., Gaub, H.H.E.: Single molecule force spectroscopy on polysaccharides by atomic force microscopy. *Science* **275**, 1295–1297 (1997)
217. Rivlin, R.S., Saunders, D.W.: Large elastic deformations of isotropic materials—VII. Experiments on the deformation of rubber. *Philos. Trans. R. Soc. A* **243**, 251–288 (1951)
218. Rodriguez, J.F., Cacho, F., Bea, J.A., Doblaré, M.: A stochastic-structurally based three dimensional finite-strain damage model for fibrous soft tissue. *J. Mech. Phys. Solids* **54**, 864–886 (2006)

219. Rodriguez, J.F., Ruiz, C., Doblaré, M., Holzapfel, G.A.: Mechanical stresses in abdominal aortic aneurysms: influence of diameter, asymmetry, and material anisotropy. *J. Biomech. Eng.* **130**(2), 021023 (2008)
220. Rohrlé, O., Pullan, A.J.: Three-dimensional finite element modelling of muscle forces during mastication. *J. Biomech.* **40**, 3363–3372 (2007)
221. Rubin, M.B., Bodner, S.R.: A three-dimensional nonlinear model for dissipative response of soft tissue. *Int. J. Solids Struct.* **39**, 5081–5099 (2002)
222. Ruter, M., Stein, E.: Analysis, finite element computation and error estimation in transversely isotropic nearly incompressible finite elasticity. *Comput. Methods Appl. Mech. Eng.* **190**, 519–541 (2000)
223. Sacks, M.S., Gloeckner, D.: Quantification of the fiber architecture and biaxial mechanical behavior of porcine intestinal submucosa. *J. Biomed. Mater. Res.* **46**, 1–10 (1999)
224. Sacks, M.S.: Biaxial mechanical evaluation of planar biological materials. *J. Elast.* **61**, 199–246 (2000)
225. Sacks, M.S.: Incorporation of experimentally-derived fiber orientation into a structural constitutive model for planar collagenous tissues. *J. Biomech. Eng.* **125**, 280–287 (2003)
226. Samani, A., Plewes, D.: A method to measure the hyperelastic parameters of ex vivo breast tissue samples. *Phys. Med. Biol.* **49**, 4395–4405 (2004)
227. Sansour, C.: On the physical assumptions underlying the volumetric-isochoric split and the case of anisotropy. *Eur. J. Mech. A, Solids* **27**, 28–39 (2008)
228. Schröder, J., Neff, P.: Invariant formulation of hyperelastic transverse isotropy based on polyconvex free energy functions. *Int. J. Solids Struct.* **40**, 401–445 (2003)
229. Schröder, J., Neff, P.: On the construction of polyconvex transversely isotropic free energy functions. In: Miehe, C. (ed.) *Proceedings of the IUTAM Symposium on Computational Mechanics of Solids Materials at Large Strains*, pp. 171–180. Kluwer Academic, Norwell (2003)
230. Schröder, J., Neff, P., Balzani, D.: A variational approach for materially stable anisotropic hyperelasticity. *Int. J. Solids Struct.* **42**, 4352–4371 (2005)
231. Schröder, J., Neff, P., Ebbing, V.: Anisotropic polyconvex energies on the basis of crystallographic motivated structural tensors. *J. Mech. Phys. Solids* **56**, 3486–3506 (2008)
232. Schröder, J., Neff, P.: Poly-, quasi- and rank-one convexity in applied mechanics. In: *CISM International Centre for Mechanical Sciences*, vol. 516 (2010)
233. Schulze-Bauer, C.A.J., Holzapfel, G.A.: Determination of constitutive equations for human arteries from clinical data. *J. Biomech.* **36**, 165–169 (2003)
234. Schwenninger, D., Schumann, S., Guttman, J.: In vivo characterization of mechanical tissue properties of internal organs using endoscopic microscopy and inverse finite element analysis. *J. Biomech.* **44**, 487–493 (2011)
235. Shin, T.J., Vito, R.P., Johnson, L.W., McCarey, B.E.: The distribution of strain in the human cornea. *J. Biomech.* **30**, 497–503 (1997)
236. Simpson, H.C., Spector, S.J.: On copositive matrices and strong ellipticity for isotropic elastic materials. *Arch. Ration. Mech. Anal.* **84**, 55–68 (1983)
237. Singh, F., Katiyar, V.K., Singh, B.P.: A new strain energy function to characterize apple and potato tissues. *J. Food Eng.* **118**(2), 178–187 (2013)
238. Smith, G.F., Rivlin, R.S.: The anisotropic tensors. *Q. Appl. Math.* **15**, 309–314 (1957)
239. Smith, G.F., Rivlin, R.S.: The strain energy function for anisotropic elastic materials. *Trans. Am. Math. Soc.* **88**, 175–193 (1958)
240. Soldatos, K.P.: On loss of ellipticity in second-gradient hyper-elasticity of fibre-reinforced materials. *Int. J. Non-Linear Mech.* **47**, 117–127 (2012)
241. Spencer, A.J.M.: Theory of invariants. In: Eringen, A.C. (ed.) *Continuum Physics*. Academic Press, San Diego (1971)
242. Spencer, A.J.M.: *Continuum Theory of the Mechanics of Fibre-Reinforced Composites*. Springer, New York (1984)
243. Spencer, A.J.M.: Isotropic polynomial invariants and tensor functions. In: *CISM Courses and Lectures*, vol. 292, pp. 141–169. Springer, Berlin (1987)
244. Steigmann, D.: On isotropic, frame-invariant, polyconvex strain-energy functions. *Q. J. Mech. Appl. Math.* **56**, 483–491 (2003)
245. Steinmann, D.: Frame-invariant polyconvex strain-energy functions for some anisotropic solids. *Math. Mech. Solids* **8**, 496–506 (2003)
246. Stewart, M.L., Smith, L.M., Hall, N.: A numerical investigation of breast compression: a computer-aided design approach for prescribing boundary conditions. *IEEE Trans. Biomed. Eng.* **58**(10), 2876–2884 (2011)
247. Sun, W., Sacks, M.S.: Finite element implementation of a generalized Fung-elastic constitutive model for planar soft tissues. *Biomech. Model. Mechanobiol.* **4**, 190–199 (2005)

248. Sverdlík, A., Lanir, Y.: Time-dependent mechanical behavior of sheep digital tendons, including the effects of preconditioning. *J. Biomech. Eng.* **124**, 78–84 (2002)
249. Takamizawa, K., Hayashi, K.: Strain energy density function and uniform strain hypothesis for arterial mechanics. *J. Biomech.* **20**, 7–17 (1987)
250. Tang, C.Y., Zhang, G., Tsui, C.P.: A 3D skeletal muscle model coupled with active contraction of muscle fibres and hyperelastic behaviour. *J. Biomech.* **42**, 865–872 (2009)
251. Tang, D., Yang, C., Kobayashi, S., Zheng, J., Woodard, P.K., Teng, Z., Billiar, K., Bach, K., Ku, R.: 3D MRI-based anisotropic FSI models with cyclic bending for human coronary atherosclerotic plaque mechanical analysis. *J. Biomech. Eng.* **131**, 061010 (2009)
252. Tong, P., Fung, Y.C.: The stress-strain relationship for the skin. *J. Biomech.* **9**, 649–657 (1976)
253. Toungara, M., Chagnon, G., Geindreau, C.: Numerical analysis of the wall stress in abdominal aortic aneurysm: influence of the material model near-incompressibility. *J. Mech. Med. Biol.* **12**, 1250005 (2012)
254. Trabelsi, O., Pérez del Palomar, A., Lopez-Villalobos, J.L., Ginel, A., Doblaré, M.: Experimental characterization and constitutive modeling of the mechanical behavior of the human trachea. *Med. Eng. Phys.* **32**, 76–82 (2010)
255. Treloar, L.R.G.: The elasticity of a network of long chains molecules 1. *Trans. Faraday Soc.* **39**, 36–41 (1943)
256. Treloar, L.R.G.: The elasticity of a network of long chains molecules 2. *Trans. Faraday Soc.* **39**, 241–246 (1943)
257. Triantafyllidis, N., Abeyaratne, R.C.: Instability of a finitely deformed fiber-reinforced elastic material. *J. Appl. Mech.* **50**, 149–156 (1983)
258. Vahapoglu, V., Karadeniz, S.: Constitutive equations for isotropic rubber-like materials using phenomenological approach: a bibliography (1930–2003). *Rubber Chem. Technol.* **79**, 489–499 (2006)
259. Vaishnav, R.N., Young, J.T., Patel, D.J.: Distribution of stresses and of strain-energy density through the wall thickness in a canine aortic segment. *Circ. Res.* **32**, 577–583 (1973)
260. Valencia, A., Baeza, F.: Numerical simulation of fluid–structure interaction in stenotic arteries considering two layer nonlinear anisotropic structural model. *Int. Commun. Heat Mass Transf.* **36**, 137–142 (2009)
261. van Dam, E.A., Dams, S.D., Peters, G.W.M., Rutten, M.C.M., Schurink, G.W.H., Buth, J., van de Vosse, F.N.: Non-linear viscoelastic behavior of abdominal aortic aneurysm thrombus. *Biomech. Model. Mechanobiol.* **7**, 127–137 (2008)
262. Vande Geest, J.P., Sacks, M.S., Vorp, D.A.: The effects of aneurysm on the biaxial mechanical behavior of human abdominal aorta. *J. Biomech.* **39**, 1324–1334 (2006)
263. Vasta, M., Pandolfi, A., Gizzi, A.: A fiber distributed model of biological tissues. *Proc. IUTAM* **6**, 79–86 (2013)
264. Velardi, F., Fraternali, F., Angelillo, M.: Anisotropic constitutive equations and experimental tensile behavior of brain tissue. *Biomech. Model. Mechanobiol.* **5**, 53–61 (2006)
265. Vito, R.P., Dixon, S.A.: Blood vessel constitutive models 1995–2002. *Annu. Rev. Biomed. Eng.* **5**, 413–439 (2003)
266. Volokh, K.Y., Vorp, D.A.: A model of growth and rupture of abdominal aortic aneurysm. *J. Biomech.* **41**, 1015–1021 (2008)
267. Walton, J.R., Wilber, J.P.: Sufficient conditions for strong ellipticity for a class of anisotropic materials. *Int. J. Non-Linear Mech.* **38**, 441–455 (2003)
268. Weiss, J.A., Maker, B.N., Govindjee, S.: Finite implementation of incompressible, transversely isotropic hyperelasticity. *Comput. Methods Appl. Mech. Eng.* **135**, 107–128 (1996)
269. Wilber, J.P., Walton, J.R.: The convexity properties of a class of constitutive models for biological soft tissues. *Math. Mech. Solids* **7**, 217–235 (2002)
270. Wineman, A.: Some results for generalized neo-Hookean elastic materials. *Int. J. Non-Linear Mech.* **40**, 271–279 (2005)
271. Yosibash, Z., Priel, E.: p-fems for hyperelastic anisotropic nearly incompressible materials under finite deformations with applications to arteries simulation. *Int. J. Numer. Methods Eng.* **88**, 1152–1174 (2011)
272. Yu, J., Zeng, Y., Zhao, J., Liao, D., Gregersen, H.: Quantitative analysis of collagen fiber angle in the submucosa of small intestine. *Comput. Biol. Med.* **34**(34), 539–550 (2004)
273. Zee, L., Sternberg, E.: Ordinary and strong ellipticity in the equilibrium theory of incompressible hyperelastic solids. *Arch. Ration. Mech. Anal.* **83**, 53–90 (1983)
274. Zhang, J.P., Rajagopal, K.R.: Some inhomogeneous motions and deformations within the context of a non-linear elastic solid. *Int. J. Eng. Sci.* **30**, 919–938 (1992)

275. Zhang, Y., Dunn, M.L., Drexler, E.S., McCowan, C.N., Slifka, A.J., Ivy, D.D., Shandas, R.: A microstructural hyperelastic model of pulmonary arteries under normo- and hypertensive conditions. *Ann. Biomed. Eng.* **33**, 1042–1052 (2005)
276. Zhao, X., Raghavan, M.L., Lu, J.: Identifying heterogeneous anisotropic properties in cerebral aneurysms: a point wise approach. *Biomech. Model. Mechanobiol.* **10**, 177–189 (2011)
277. Zulliger, M.A., Fridez, P., Hayashi, K., Stergiopoulos, N.: A strain energy function for arteries accounting for wall composition and structure. *J. Biomech.* **37**, 989–1000 (2004)