

University of Groningen

Interaction between lattice dislocations and grain boundaries in f.c.c. and ordered compounds

Pestman, B.J.; Hosson, J.Th.M. De; Vitek, V.; Schapink, F.W.

Published in:
Philosophical Magazine A

DOI:
[10.1080/01418619108213958](https://doi.org/10.1080/01418619108213958)

IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.

Document Version
Publisher's PDF, also known as Version of record

Publication date:
1991

[Link to publication in University of Groningen/UMCG research database](#)

Citation for published version (APA):

Pestman, B. J., Hosson, J. T. M. D., Vitek, V., & Schapink, F. W. (1991). Interaction between lattice dislocations and grain boundaries in f.c.c. and ordered compounds: a computer simulation. *Philosophical Magazine A*, 64(4). <https://doi.org/10.1080/01418619108213958>

Copyright

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

Take-down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.

Interaction between lattice dislocations and grain boundaries in f.c.c. and ordered compounds: a computer simulation

By B. J. PESTMAN†, J. TH. M. DE HOSSON†, V. VITEK‡
and F. W. SCHAPINK§

† Department of Applied Physics, Materials Science Centre, University of Groningen,
Nijenborgh 18, 9747 AG Groningen, The Netherlands

‡ Department of Materials Science and Engineering, University of Pennsylvania,
Philadelphia, PA 19104, USA

§ Laboratory of Metallurgy, Delft University of Technology,
Rotterdamseweg 137, 2628 AL Delft, The Netherlands

[Received 3 October 1990 and accepted 12 December 1990]

ABSTRACT

The interaction of $1/2\langle 110 \rangle$ screw- and 60° dislocations with symmetric $[110]$ tilt boundaries was investigated by atomistic simulations using many-body potentials representing a pure f.c.c. metal and ordered intermetallic compounds. The calculations were performed with and without an applied shear stress. The observations were: absorption into the grain boundary, attraction of a lattice Shockley partial dislocation towards the grain boundary and transmission through the grain boundary under the influence of a shear stress. It was found that the structural unit model may help to predict the interaction mechanism for long period boundaries and that the interaction in ordered compounds shows similarities to the interaction in f.c.c. metals. Some comparisons with experimental observations have been made.

§ 1. INTRODUCTION

The structure of grain boundaries determines a number of important properties of polycrystalline materials, among which the mechanical strength is the most affected. Already in the late thirties it was proposed that grain boundaries affect glide of dislocations, i.e. the mechanical properties of polycrystalline materials (Chalmers 1937). A more recent example can be found in a number of ordered compounds, which are very attractive materials for high temperature applications because of their chemical resistivity and their mechanical strength at high temperatures. These materials are generally ductile as single crystals but show intergranular fracture in their polycrystalline form. This hampers their application, and therefore the physical reason for this intergranular brittleness needs to be scrutinized. A possible answer can be found in the low cohesion of grain boundaries in these materials. However, there is also experimental evidence that the dislocation mobility in the vicinity of grain boundaries may be strongly enhanced when ductilization takes place (Baker, Schulson and Horton 1987). The opposite has been suggested by Chaki (1990). This leads to the conclusion that it is necessary to consider the interaction between dislocations and grain boundaries in detail.

There has been a variety of experimental approaches to the study of dislocation-grain boundary interaction. They include etch-pitting, slip line analysis, and transmission electron microscopy (TEM) (Dingley and Pond 1979). *In situ* deformation in the electron microscope has provided detailed insight in the process of the interaction (Shen, Wagoner and Clark 1988), and additional information on an atomic level has

been provided by high resolution transmission electron microscopy (HRTEM) (Elkajbaji and Thibault-Desseaux 1989). A number of theoretical concepts which help the understanding of the processes at grain boundaries have also been developed, namely the coincidence site lattice (CSL) and displacement-shift-complete lattice (DSC) models (Bollmann 1970, Balluffi, Brokman and King 1982) and the structural unit model (Sutton and Vitek 1983, De Hosson and Vitek 1990).

When a lattice dislocation impinges on a grain boundary, there are various possibilities for the interaction mechanism (Shen, Wagoner and Clark 1988):

- (1) The lattice dislocation can dissociate into grain boundary dislocations. A grain boundary dislocation (g.b.d.) can only exist in a grain boundary and a perfect g.b.d. (or DSC dislocation) has a Burgers vector that belongs to the DSC lattice. This mechanism is referred to as absorption.
- (2) The lattice dislocation moves into the grain boundary, while another lattice dislocation emerges from the grain boundary into the other grain. A residue with a Burgers vector that is equal to the difference of the two lattice dislocations remains in the boundary. This residue is a DSC dislocation. This mechanism is referred to as transmission.
- (3) In addition, there are more complex mechanisms, like absorption and re-emission, at another site in the boundary.

In addition, a grain boundary can be the nucleation site of dislocations.

The selection of the actual interaction mechanism depends on the energetics. In this paper, we focus on the interaction, at the atomic level, between dislocation core and boundary core. The interaction between a number of periodic, symmetric [110] tilt boundaries and dislocations of screw and 60° character with their line direction parallel to [110] was studied by atomistic simulation using two approaches: static simulations (energy minimalization of the combined dislocation and grain boundary system) and kinematical simulations, in which a shear stress is applied in such a way that the dislocation is 'pushed' towards the grain boundary. Two aspects of interest are the application of the structural unit mode to the dislocation-grain boundary interaction and the influence of a high ordering energy on the interaction mechanism.

The simulations were carried out using many-body potentials describing three materials: Cu, Cu_3Au and Ni_3Al . Cu represents a model f.c.c. material, and also can formally be regarded as 'fully disordered' L1_2 , whereas Cu_3Au represents moderately ordered L1_2 (T_c below T_m , the melting temperature) and Ni_3Al represents highly ordered L1_2 (T_c above T_m). In this way, the effect of increasing ordering tendency can be studied. The computational procedure is simplified by limiting the choice of systems that are studied to those systems with the dislocation line parallel to the boundary plane, so as to be able to apply periodic boundary conditions along the dislocation line. In this way, little restriction is imposed on small displacements of the dislocation core. Another limitation of the computer simulations is that there is no possibility of simulating climb of the dislocation. It must be noted that the observations in HRTEM are usually limited to projections of the dislocation line and grain boundary end-on, and a one-to-one comparison with the results of atomistic simulations is possible and will be made.

§2. METHOD OF CALCULATION

For the description of interatomic forces, Finnis-Sinclair potentials representing Cu (Ackland, Tichy, Vitek and Finnis 1987), Cu_3Au (Ackland and Vitek 1989) and

Ni_3Al (Vitek, Ackland and Cserti 1990) were used. For the static simulations, the following procedure was used. First, the grain boundary was relaxed, using a standard gradient method; details are described elsewhere (Sutton and Vitek 1983). In the case of the ordered compounds, different ordering configurations of the grain boundary were considered (see for instance Frost 1987) and the ordering configuration with lowest energy was chosen as a starting point for the dislocation–grain boundary relaxation. Secondly, a computational block for the relaxation of the dislocation near the grain boundary was constructed. The computational block of the grain boundary was extended, according to the periodicity of the CSL, to form a block of $40 \mathbf{b} \times 40 \mathbf{b}$ (\mathbf{b} is the magnitude of the Burgers vector) perpendicular to the tilt axis. Along the tilt axis, periodic boundary conditions were applied. Next, the displacement field of a $1/2\langle 110 \rangle$ type dislocation was imposed with its elastic centre near the grain boundary. The anisotropic elastic solution (as if only the upper grain was present) was used for the (fixed) boundary conditions perpendicular to the dislocation line. Of course, the neglect of the presence of the lower grain will introduce a small error in the boundary conditions. The dislocation was introduced in the upper grain at different positions along the grain boundary period, a few lattice parameters away from the grain boundary plane. In the ordered alloys, the displacement field of a $1/2\langle 110 \rangle$ type superpartial was imposed with its elastic centre near the boundary plane, connected by a ribbon of anti phase boundary (APB) to another superpartial at elastic equilibrium distance, according to the APB energy. In the case of Cu_3Au the other superpartial was imposed with its elastic centre outside the computational block. Since the elastic equilibrium distance between the two superpartials in Ni_3Al was not as large, the computational block was extended to include both. The dislocation–grain boundary relaxation was carried out in the usual way for dislocation relaxation (Basinski, Duesbery, and Taylor 1970).

For the kinematical simulations, a similar procedure was used, but now the elastic centre of the dislocation was initially positioned at such a distance from the grain boundary that there was no strong effect of the grain boundary on the relaxation of the dislocation core. The initial position of the core was always chosen such that dissociation would occur on the glide plane. After relaxation of the dislocation core, a homogeneous shear strain was imposed on the computational block, corresponding to a shear stress as prescribed by anisotropic elasticity theory (as if only the grain initially containing the dislocation was present). The shear stress was applied in the direction of the Burgers vector, such that the dislocation would move towards the grain boundary plane. The kinematical simulations started with imposing a shear strain corresponding to a small stress. Larger stresses were built up by repeating this process.

§ 3. RESULTS

Most of the symmetric $[110]$ tilt boundaries studied have (001) as the mean boundary plane. Only the interaction of a $1/2[110]$ dislocation of pure screw character with these boundaries was simulated. In this set-up, transmission of the dislocation through the grain boundary is relatively easy, as no residue is left behind in the grain boundary plane. In the following, all Miller indices are in the coordinate system of the upper grain, unless indicated otherwise. The $\Sigma = 3$ ($\bar{1}11$) ($\Theta = 109.47^\circ$) coherent twin boundary and a number of boundaries in the misorientation range 31.59° to 50.48° were relaxed: the $\Sigma = 27$ ($\bar{1}15$) ($\Theta = 31.59^\circ$); the $\Sigma = 9$ ($\bar{1}14$) ($\Theta = 38.94^\circ$) (Cu only); the $\Sigma = 57$ ($\bar{2}27$) ($\Theta = 44.0^\circ$) (Cu only) and the $\Sigma = 11$ ($\bar{1}13$) ($\Theta = 50.48^\circ$). For Cu, a periodic

pattern of structural units was found: $\Sigma = 3$: C.C; $\Sigma = 27$: A.A; $\Sigma = 9$: AB; $\Sigma = 57$: ABBB; $\Sigma = 11$: B.B, where the . indicates a translation of $1/4 [110]$ along the tilt axis. For the ordered structure a topologically similar pattern was found, but with two units that differ in the occupation of atom sites by A- and B-atoms. For all materials, the $\Sigma = 27$ and the $\Sigma = 11$ boundaries are favoured boundaries in the misorientation range mentioned, i.e. the boundaries in the intermediate misorientations are composed of the structural units of these boundaries. In the kinematical simulations, the shear stress was applied on the $(1\bar{1}1)$ plane.

The energies of the different ordering states of the boundaries in Cu_3Au and Ni_3Al are given in table 1. The energies of the A_2 and A_3 (and for the $\Sigma = 3$ the A_1 , A_2 and A_3) structures should be identical on the basis of symmetry arguments.

Next, the $\Sigma = 9$ ($2\bar{2}1$) ($\Theta = 38.94^\circ$) boundary with mean plane $(1\bar{1}0)$ was studied (for Cu only). The relaxed boundary has a skew symmetric structure. Simulations were done of the dislocation-grain boundary interaction between this boundary and two types of 60° dislocations, the $1/2[10\bar{1}]$ on the $(1\bar{1}1)$ plane and the $1/2[01\bar{1}]$ on the $(1\bar{1}\bar{1})$ plane. A comparison will be made later with experimental results for Si (Elkajbaji and Thibault-Desseaux 1988).

For a number of boundaries, all low-energy dislocation configurations that have been found for that boundary are represented schematically in figures showing the relaxed boundary structure. It has to be emphasized that the symbols indicating the atom positions are drawn as if there is no dislocation present. Some examples of dislocation structures and the results for the kinematical simulations are depicted using the differential displacement method (Vitek, Perrin and Bowen 1970). This method indicates the relative displacement of each atom with respect to its neighbours in a certain crystallographic direction (usually the direction of the Burgers vector). If the absolute value of the relative displacement exceeds half of the periodicity of the lattice in that direction, an integer number times the period is added or subtracted. In the case of the ordered structure, the periodicity of the f.c.c. structure was used to facilitate the comparison. The position of the APB is indicated by a line. The relative displacements are indicated by arrows drawn between the atoms. In the figures, the regions where the differential displacements have a size between $0.30 a_0$ and $0.354 a_0$ (half the periodicity along the tilt axis, where a_0 is the lattice constant) are indicated by lines; the regions where the differential displacements are between $0.15 a_0$ and $0.30 a_0$ are indicated by lobes (two lines parallel).

Table 1. Grain boundary energies in mJ/m^2 for different ordering states. The cubic sublattices containing the B-atoms are indicated by their relative translation vector (in the coordinate system of the upper grain). The *relaxed* configuration with full symmetry is indicated by S.

Ordering state	S	A1	A2	A3
Translation vector	[000]	$1/2[110]$	$1/2[101]$	$1/2[011]$
$\Sigma = 3$ Cu_3Au	7	47	47	47
Ni_3Al	6	208	208	208
$\Sigma = 11$ Cu_3Au	363	344	358	359
Ni_3Al	506	490	605	606
$\Sigma = 27$ Cu_3Au	697	701	737	737
Ni_3Al	996	994	1105	1105

3.1. FCC (Cu)


In the kinematical simulations, the screw dislocation started to move in the lattice at an applied shear stress of 500 MPa. The screw dislocation was dissociated initially into two Shockley partials in the $(1\bar{1}1)$ plane. Their separation distance was $4 a_0$, and they remained separated during the movement.

In the static simulations of the interaction between the screw dislocation and the $\Sigma=3$ boundary one low energy configuration was found: absorption of the screw dislocation and splitting in the boundary plane into two Shockley partial dislocations, the $1/6[12\bar{1}]$ and the $1/6[211]$, which are DSC dislocations of the $\Sigma=3$ boundary, causing a step of $+1$ and -1 interplanar spacing, respectively. See fig. 1.

In the kinematical simulations, the $\Sigma=3$ boundary acted as an obstacle to the motion of the screw dislocation. At a stress level of 500 MPa the screw dislocation started to move towards the boundary plane from its initial position. The leading Shockley partial was halted at the boundary plane and the trailing one remained separated from it by approximately $2 a_0$. Upon further increase of the shear stress, this separation distance decreased, and eventually, at 1500 MPa, there was transmission of the screw dislocation through the boundary to the symmetric slip plane in the other grain. See fig. 2. After transmission, the separation of the Shockley's increased again.


For the $\Sigma=27$ boundary, four low energy configurations were found, all showing splitting into two lattice Shockley partial dislocations, on different $\{111\}$ planes, namely the $(\bar{1}11)$ and the $(1\bar{1}1)$ plane. See fig. 3. One of the Shockley partials was always attracted to the boundary and merged into the boundary plane. In most configurations, there was some spreading of the core into the other grain. Some local relaxation effects could be observed. For the kinematical simulations of the $\Sigma=27$ boundary, two

Fig. 1

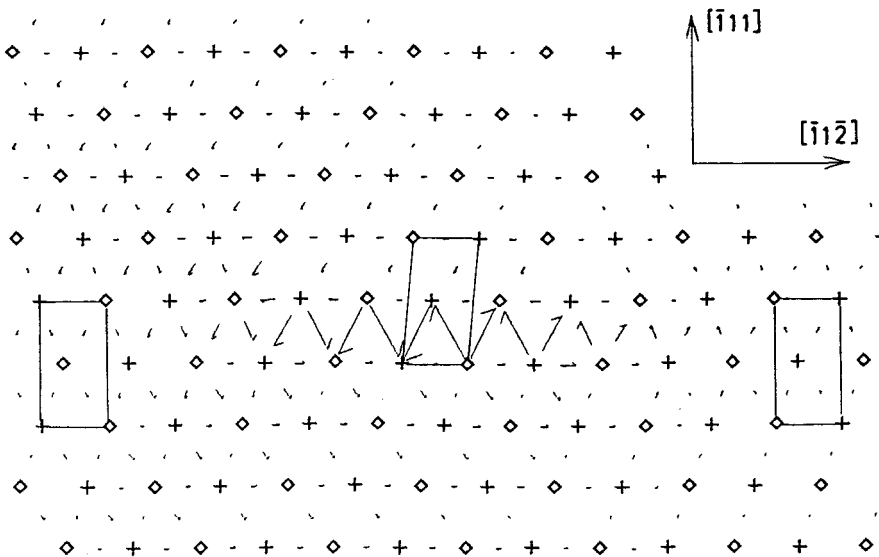

The configuration found for the $\Sigma=3$ boundary in Cu, showing absorption of the screw dislocation in the boundary plane into two g.b.d.s. In this and the following figures, a projection along $[110]$ is shown. The different symbols indicate different heights. Structural units in a boundary are indicated and if a new boundary is formed between the g.b.d.s, structural units in this new boundary are also indicated. The heights indicated by the symbols are heights before the dislocation was imposed.


Fig. 2

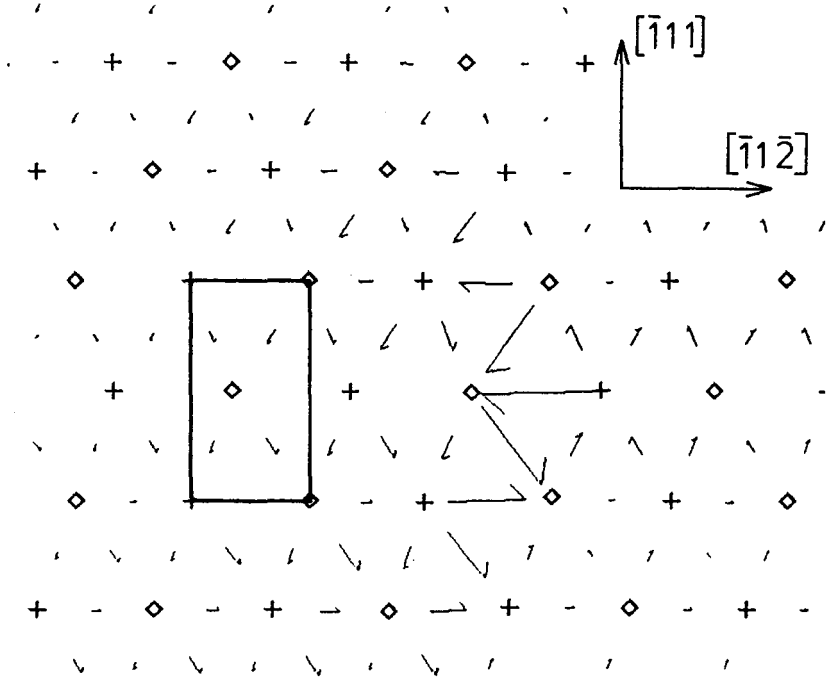Transmission of the screw dislocation through the $\Sigma=3$ boundary in Cu.

different initial configurations, corresponding to two different $(\bar{1}\bar{1}1)$ slip planes, ending at different locations in the structural unit, were chosen. In the first case, the screw dislocation reached the boundary in the middle part of the structural unit. Transmission to the $(\bar{1}\bar{1}\bar{1})_{II}$ plane (the $_{II}$ indicates the coordinate system of the lower grain) occurred at 1300 MPa. Contraction of the two Shockley partials during transmission through the boundary plane was not as pronounced as in the transmission through the $\Sigma=3$ boundary. Strong local relaxation effects could be observed. See fig. 4. In the second case, the $(\bar{1}\bar{1}1)$ slip plane ended in the left part of the structural unit. The movement of the screw dislocation again started at 500 MPa. Very close to the boundary plane, cross slip to the $(\bar{1}\bar{1}1)$ slip plane occurred and the screw dislocation moved to the right part of the $\Sigma=27$ structural unit. The leading Shockley was absorbed in the grain boundary plane with the trailing Shockley very close behind. When the applied shear stress was increased gradually, the trailing Shockley merged into the boundary plane and the leading one spread its core into the other grain onto the $(\bar{1}\bar{1}\bar{1})_{II}$ plane. No transmission occurred as the simulation continued (the final stress level was 3000 MPa).

The $\Sigma=11$ boundary showed only one low energy configuration: the screw dislocation was absorbed in the boundary and split into two DSC dislocations, the $1/22 [47\bar{1}]$ and the $1/22 [741]$. These DSC dislocations are both glissile in the $(\bar{1}13)$ plane of $\Sigma=11$ boundary. See fig. 5. The two DSCs cause a step of $+1$ and -1 interplanar spacing in the boundary plane respectively. Exactly the same dissociation was found in the kinematical simulations. The screw dislocation started to move towards the boundary at 500 MPa shear stress. At the boundary plane, it dissociated into the two

Fig. 3

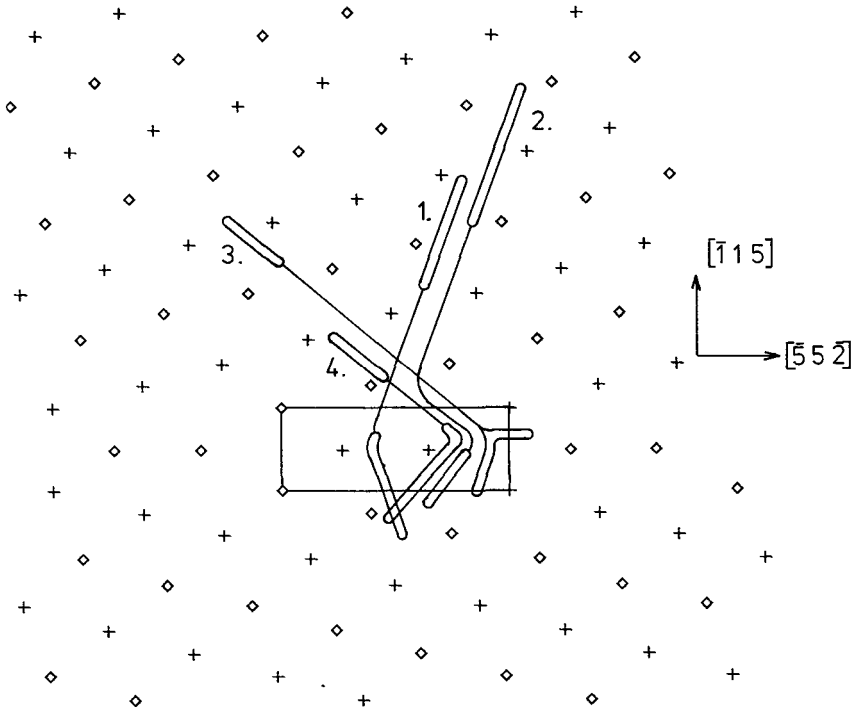

Schematic representation of the configurations found for the $\Sigma=27$ boundary in Cu. All configurations show a Shockley partial dislocation merged in the boundary, connected by a stacking fault to a Shockley in the lattice.

DSC dislocations mentioned above. After the dissociation, the $1/22[741]$ DSC dislocation moved to the right, to a position close to the border of the computational block.


3.2. Ordered compounds

3.2.1. Cu_3Au

In the static simulations for the $\Sigma=3$ boundary two different low energy configurations were found, corresponding to two different types of interaction: one configuration shows absorption into the boundary plane and dissociation into two DSC dislocations of the disordered boundary, the $1/6[12\bar{1}]$ and the $1/6[211]$, causing a step of one interplanar spacing in the grain boundary plane. The separation between the g.b.d.s was much smaller than the separation in Cu. The part of the new boundary between the g.b.d.s corresponds to a different ordering state of the $\Sigma=3$ boundary. It has to be noted that if the g.b.d.s are moving to different sides of the intersection between APB and boundary plane, two different ordering states of the original boundary are created at the two sides of the APB. These two states differ by the translation vector of the APB. For the boundaries studied in this paper, these have equal energy. The other configuration shows dissociation into two lattice Shockley partial dislocations, one of which was attracted to the boundary. See fig. 6.


The $\Sigma=27$ boundary showed two different types of interaction, with very little energy difference. A number of configurations, which are all examples of the first type of

Fig. 4

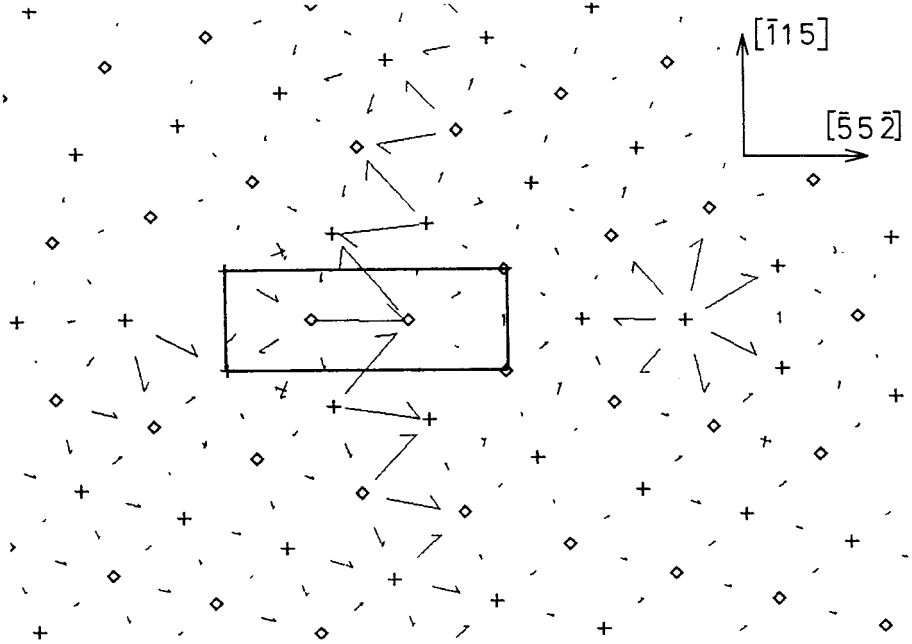


Transmission of the screw dislocation through the middle part of the structural unit of the $\Sigma=27$ boundary in Cu. Note the strong relaxations in the neighbouring structural units.

Fig. 5

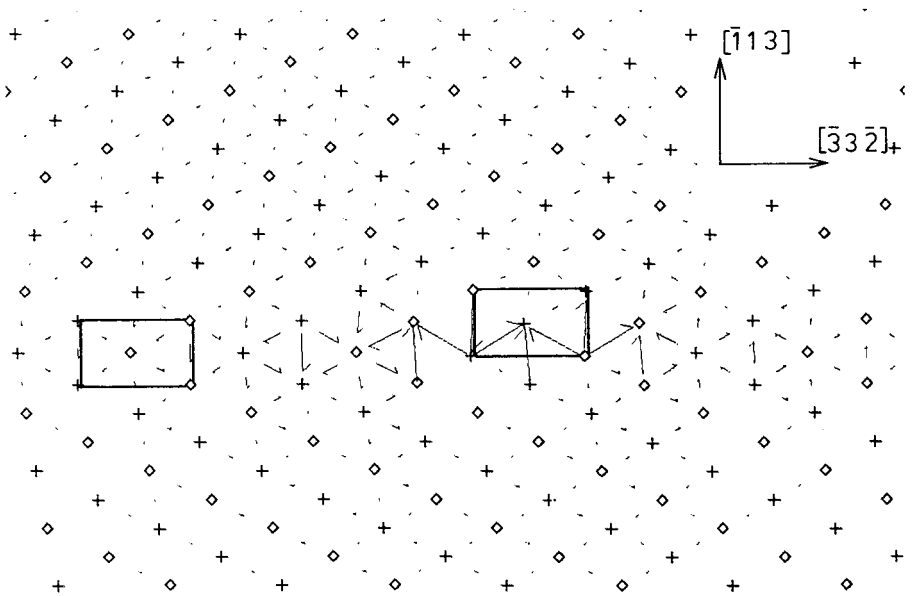

The configuration found for the $\Sigma=11$ boundary in Cu, showing absorption of the screw dislocation in the boundary plane into two g.b.d.s.

Fig. 6

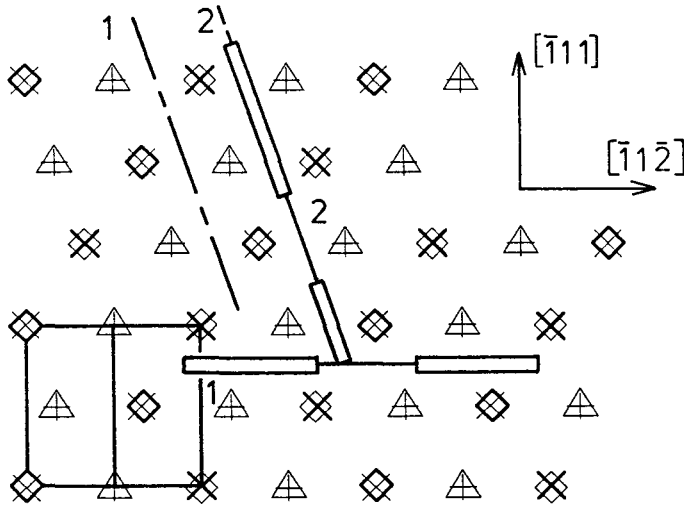

The configurations found for the $\Sigma = 3$ boundary in Cu_3Au (A_3B). For Cu_3Au , absorption in the boundary plane as well as attraction of one Shockley partial dislocation to the boundary plane were found. In this and the following figures, the B-atoms are indicated by thicker lines, with the following order of the symbols: \diamond , $+$, \times , \triangle . The different positions of the APB attached to a configuration are indicated by dashed lines and the number of the configuration.


interaction, showed dissociation into lattice Shockley partial dislocations, one of which was attracted to the boundary. These configurations compare well to the configuration no. 3 of fig. 3 for Cu. In two other configurations (fig. 7), absorption into the boundary plane and dissociation into two DSC dislocations of the disordered boundary, the $1/54[16\ 11\ 1]$ and the $1/54[11\ 16\ \bar{1}]$, was found. The g.b.d.s cause a step in the boundary plane of $+4$ and -4 interplanar spacings, respectively. The boundary formed between the two cores corresponds to a different ordering state of the original boundary; because of the step in the boundary, some shuffling of atoms has occurred and anti-site defects have been created because of the shuffling.

In the $\Sigma = 11$ boundary, a similar configuration to that in Cu was found again. As the g.b.d.s do not belong to the DSC lattice of the ordered boundary, the part of the boundary between the two g.b.d.s again has an ordering configuration which is different from the original boundary. The separation of the g.b.d.s was smaller than in Cu.

3.2.2. Ni_3Al

The relaxation in the perfect lattice of the core of a $1/2[110]$ superpartial dislocation without an applied shear stress revealed that there were two stable core configurations with very similar energies, depending on the initial position of the core. The first configuration ('glissile') showed spreading of the core on the $(1\bar{1}1)$ plane of the APB. The other configuration ('sessile') showed spreading of the core on the $(\bar{1}11)$ plane. This result compares well to other simulations in L1_2 ordered materials (Yamaguchi, Paidar, Pope, and Vitek 1982, Farkas and Savino 1988). In the kinematical simulations of the interaction with grain boundaries, the initial position of the dislocation was always chosen in such a way, that after the dislocation-grain boundary relaxation the

Fig. 7

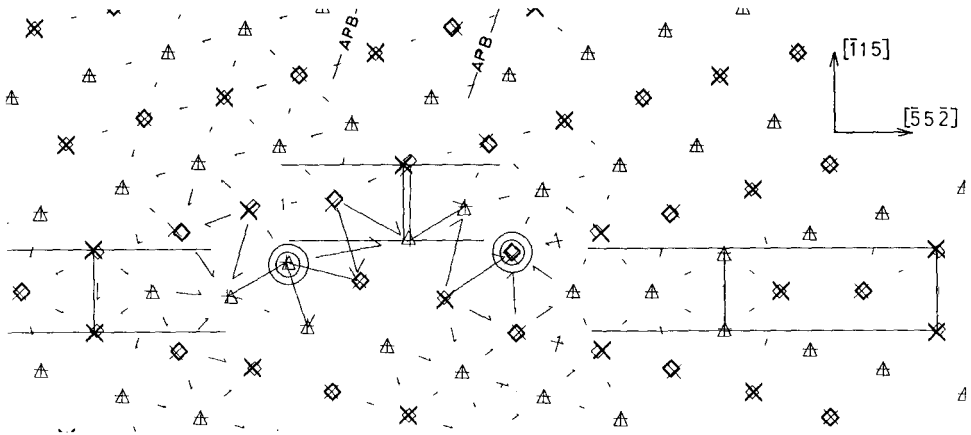

The configuration showing absorption in the boundary plane for the $\Sigma=27$ boundary in Cu_3Au . The double circles indicate anti-site defects.


glissile core configuration would be attained. In the kinematical simulations in the perfect lattice, the movement of the superpartial screw dislocations started at 700–800 MPa.

In the $\Sigma=3$ boundary, two different configurations, both similar to the two configurations in Cu_3Au , were found. The separation of the two g.b.d.s in the case of absorption was much smaller than in Cu and this configuration had a slightly higher energy than the configuration showing dissociation into two lattice Shockley partials. The interaction of the $1/2[110]$ superpartial screw dislocation with the $\Sigma=3$ boundary in the kinematical simulations showed a similar mechanism to Cu. The leading superpartial was dissociated into two Shockley partials with very small separation. Upon arrival at the boundary plane, the leading Shockley partial was stopped and a slight decrease of the separation of the Shockleys could be observed. When the shear stress reached a level of 2900 MPa, transmission occurred across the boundary into the symmetric slip plane in the other grain.

For the $\Sigma=27$ boundary only one type of interaction was found: dissociation into lattice Shockley partials, with one partial merged into the boundary. Most of the configurations that were found compare well with the configurations nos. 1, 3 and 4 of fig. 3 for Cu. One new configuration (no. 3 of fig. 8) was found for Ni_3Al ; this configuration had a slightly higher energy. See fig. 8.

For the study of the interaction with the $\Sigma=27$ boundary in the kinematical simulations, two different initial configurations were chosen. In the first configuration, the $(\bar{1}\bar{1}1)$ slip plane of the superpartial ended in the middle of structural unit no. 1. See fig. 9(a). When the leading $1/2[110]$ superpartial reached the boundary, it was halted, with one Shockley merged into the boundary plane and the other in the lattice, very close to the boundary plane. When the stress level increased, the Shockley partial in the lattice gradually spread its core onto the $(\bar{1}\bar{1}1)$ plane. At a stress level of 3400 MPa, the Shockley partial (originally $1/6[121]$) had dissociated into a $1/6[\bar{1}10]$ stair rod dislocation, located approximately at the original position of the Shockley, and a new Shockley partial, $1/6[211]$, which had merged into the right part of structural unit no. 2.


Fig. 8

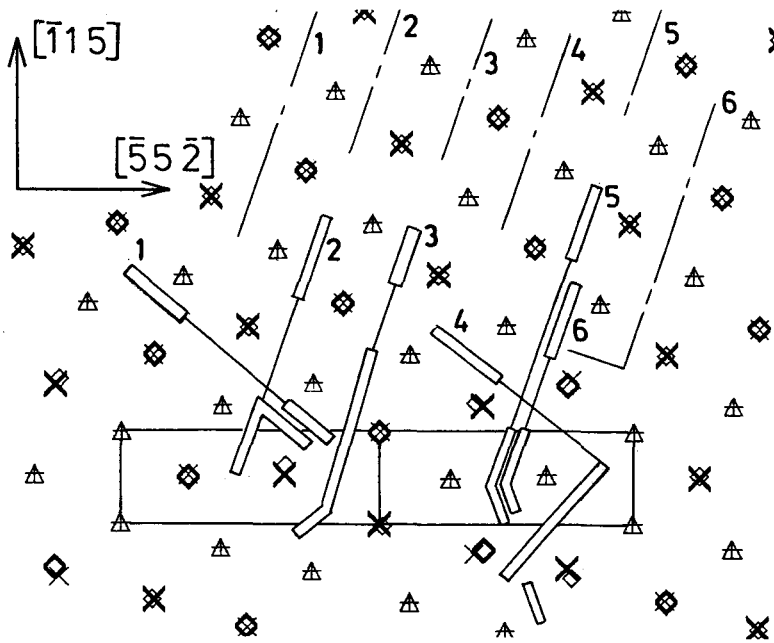The configurations found for the $\Sigma=27$ boundary in Ni_3Al .

In this way, a new, second region of complex stacking fault (CSF) had formed on the $(\bar{1}11)$ plane, connecting the stair rod dislocation and the newly formed Shockley partial. See fig. 9(a). At a stress level of 3900 MPa, the trailing $1/2[110]$ superpartial approached the configuration and a reaction between the stair rod dislocation and the leading Shockley of this superpartial took place, in which the $1/6[12\bar{1}]$ Shockley partial was created. The $1/6[12\bar{1}]$ Shockley partial cross-slipped away along the $(\bar{1}11)$ plane, thus creating an APB on the $(\bar{1}11)$ plane. Finally, at a stress level of 4200 MPa, a CSF was formed on a $(1\bar{1}\bar{1})_{\text{II}}$ plane in the other grain. See fig. 9(b). In the second configuration, the slip plane of the superpartial ended in the left part of structural unit no. 2. The superpartial cross slipped onto the $(\bar{1}11)$ plane and merged into the right part of the structural unit, analogous to the second mechanism described for the interaction with the $\Sigma=27$ boundary in Cu. At an applied shear stress of 3100 MPa, the superpartial was transmitted into the other grain onto a $(1\bar{1}\bar{1})_{\text{II}}$ plane. See fig. 10.


The $\Sigma=11$ boundary again showed the same configuration as was found in Cu_3Au . The separation between the g.b.d.s was smaller than the separations in Cu and Cu_3Au . In the kinematical simulations, one Shockley partial was initially attracted to the boundary while the other remained in the lattice at $3 a_0$ from the boundary plane. Thus, a relatively large area of CSF was created. When the stress level was increased further, this configuration remained the same, with only a slight decrease in the separation of the Shockley partials, until a stress level of 1900 MPa was reached. At this level, the superpartial was absorbed in the boundary and split into two g.b.d.s belonging to the DSC lattice of the disordered boundary, analogous to the mechanism in Cu.

Fig. 9

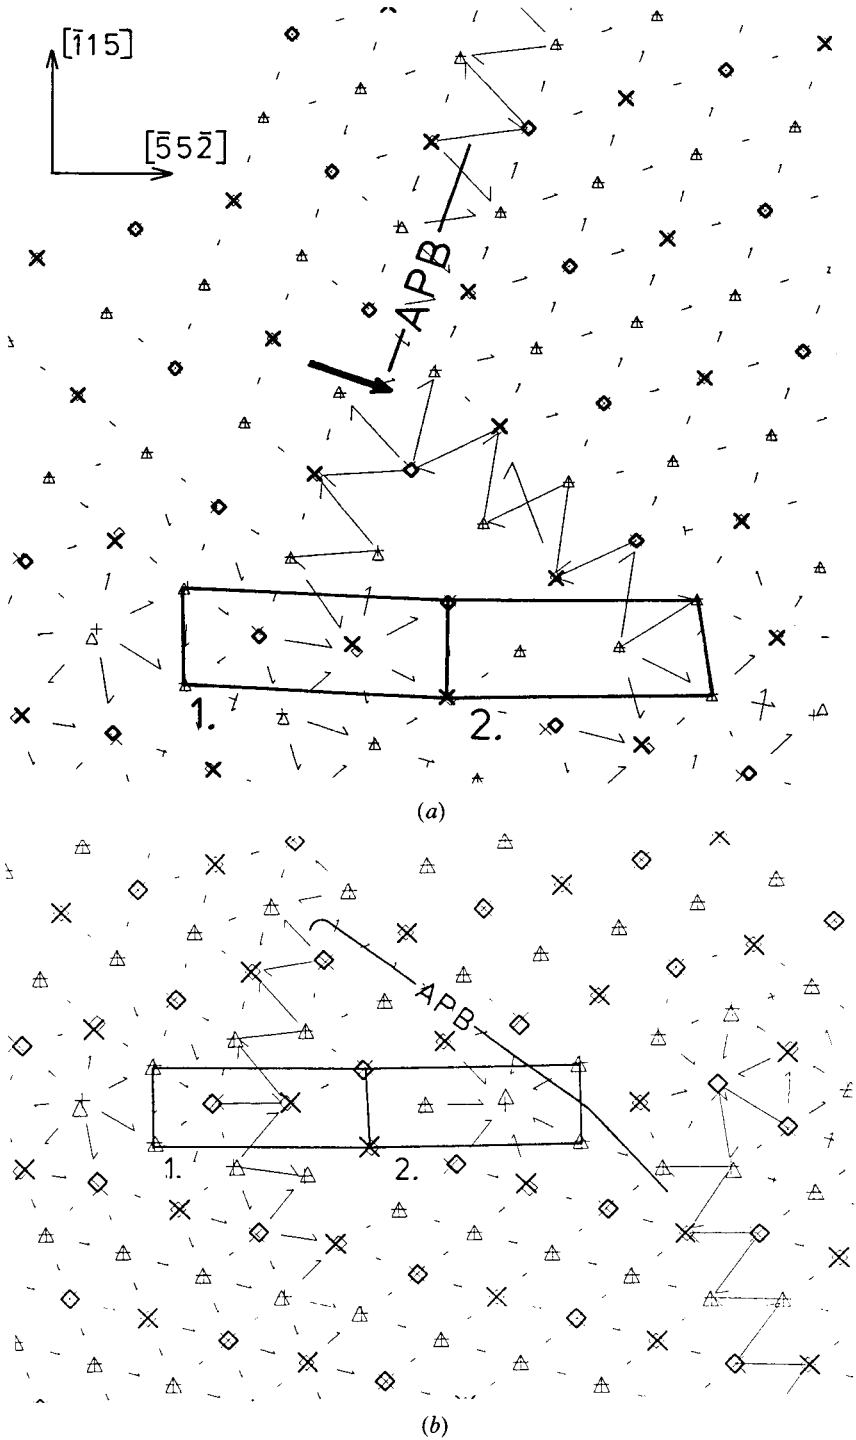

(a) First stage of the interaction with the $\Sigma=27$ boundary in Ni_3Al in the kinematical simulations. Both the leading and the trailing superpartial dislocations are visible. The arrow indicates the position of the stair rod dislocation. (b) Final configuration. The trailing superpartial has cross-slipped to the right and a CSF has been created in the lower grain.

Fig. 10

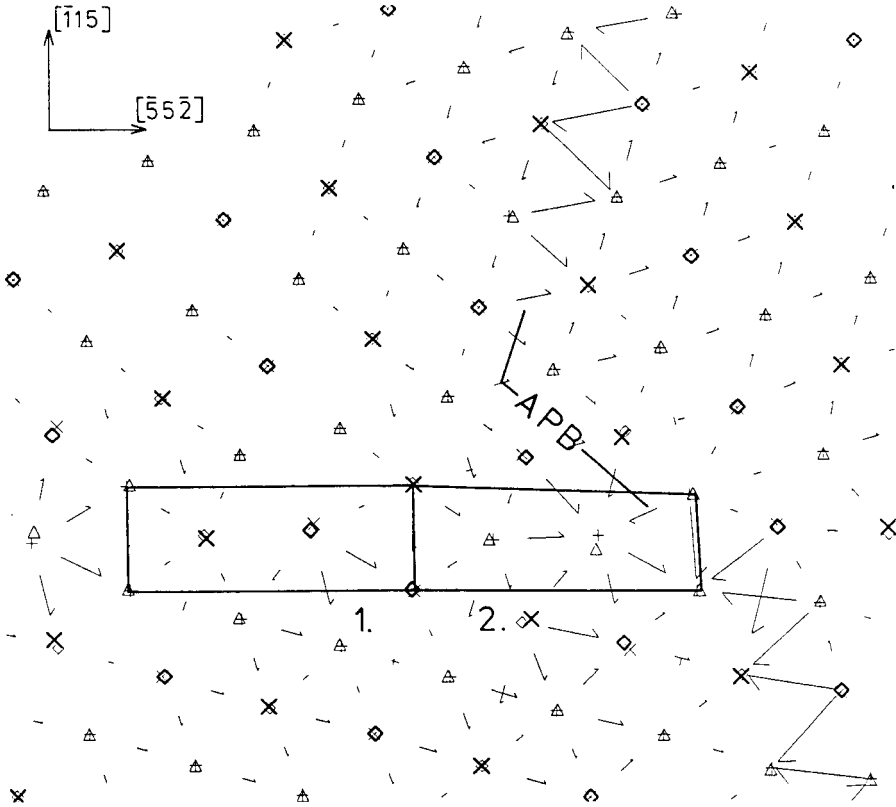


Transmission of the leading superpartial through the $\Sigma=27$ boundary in Ni_3Al . The trailing superpartial is visible in the upper grain.

3.3. Structural unit model and comparison with experiment

In the structural unit model, the structure of grain boundaries in the misorientation range between two low energy boundaries can be described as composed of a sequence of building blocks or 'structural units' of these two 'favoured' boundaries. In our case, the $\Sigma=27$ and the $\Sigma=11$ boundary are the favoured boundaries and the $\Sigma=57$ and $\Sigma=9$ ($\bar{1}14$) boundary are composed of units of the $\Sigma=27$ and $\Sigma=11$ boundaries. The interaction of a $1/2[110]$ screw dislocation with the $\Sigma=57$ and $\Sigma=9$ boundaries was studied in Cu.


The low energy configurations for the $\Sigma=57$ boundary are very similar to those found for the two delimiting favoured boundaries. In the parts of the boundary that can be described by $\Sigma=11$ units, the mechanism of absorption in the boundary was observed again. The splitting was never beyond the two $\Sigma=27$ units on both sides of the $\Sigma=11$ region. For the $\Sigma=27$ units, three of the four configurations that had been found for the $\Sigma=27$ boundary were found here again. See fig. 11. The $\Sigma=9$ ($\bar{1}14$) boundary again showed configurations that were similar to the $\Sigma=11$ and $\Sigma=27$ boundaries. Although the boundary consists of a repeating sequence of only one $\Sigma=11$ and one $\Sigma=27$ structural unit, the mechanism of absorption into the $\Sigma=11$ unit was observed here again; the splitting in the boundary plane was limited to the very narrow region of

Fig. 11

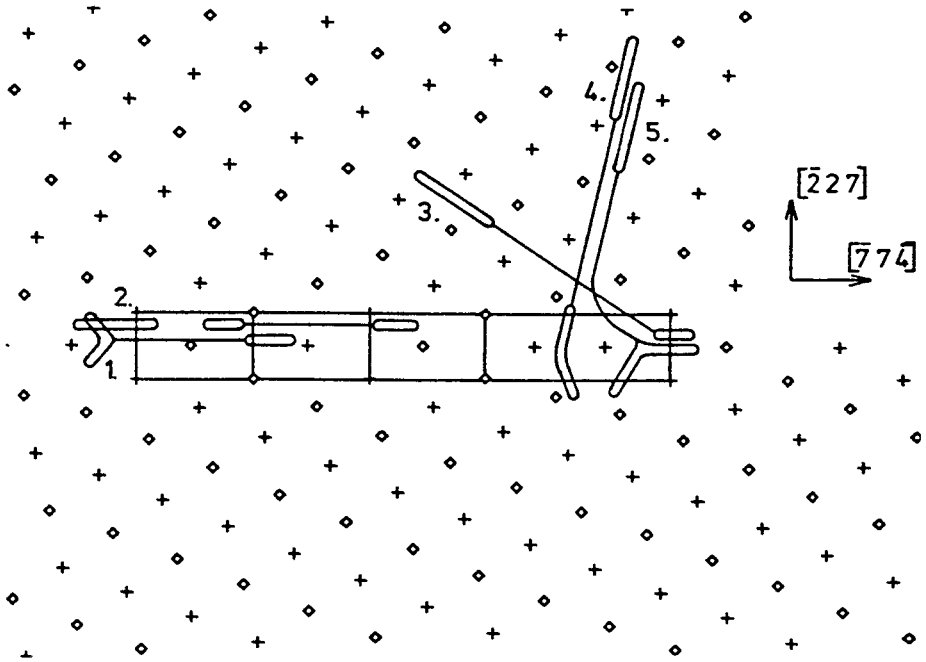


The configurations found for the $\Sigma=57$ boundary in Cu, showing similarity to the configurations found for the $\Sigma=27$ and $\Sigma=11$ delimiting favoured boundaries.

Fig. 12

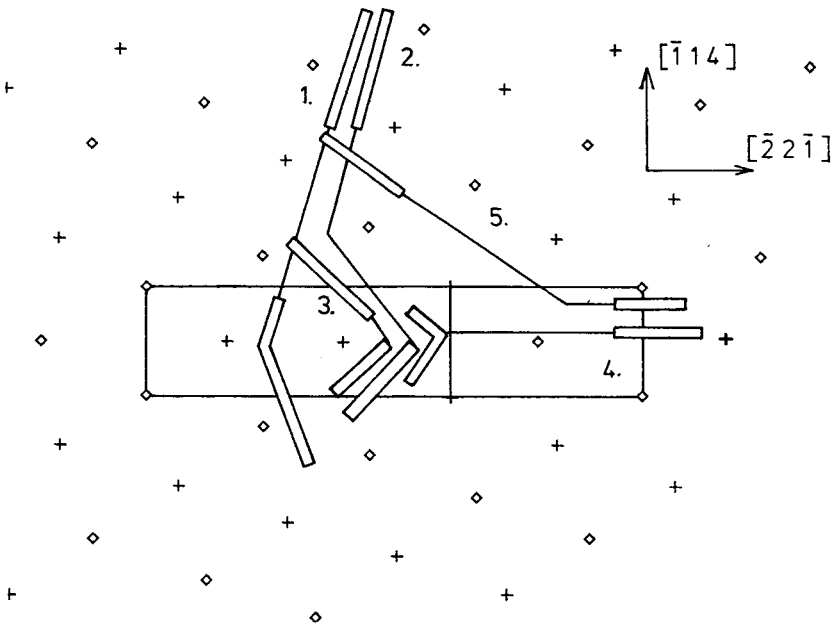

Schematic figure of the configurations found for the $\Sigma=9(\bar{1}14)$ boundary in Cu, showing mostly similarities to the configurations found for the $\Sigma=27$ and $\Sigma=11$ delimiting favoured boundaries.

Fig. 13

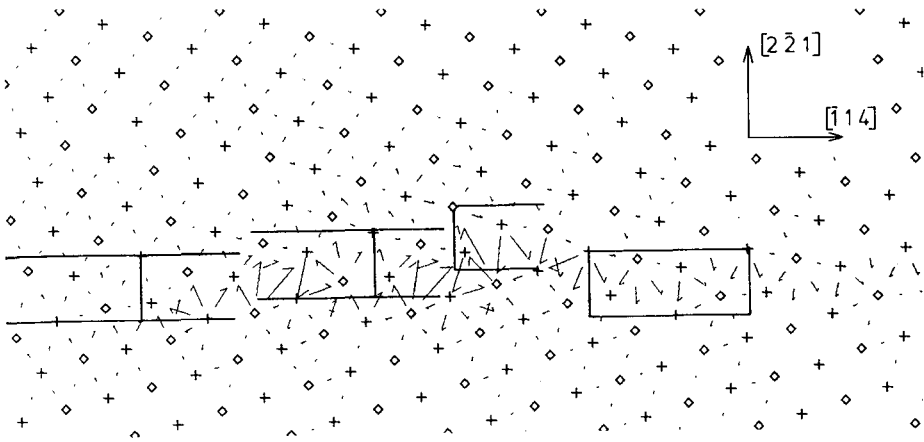

Absorption of the $1/2[10\bar{1}]$ 60° dislocation in the $\Sigma=9$ ($2\bar{2}1$) boundary into two $1/18[1\bar{1}\bar{4}]$ and one $1/18[72\bar{1}]$ g.b.d.s in Cu. In this figure, the displacements parallel to the $1/18[1\bar{1}\bar{4}]$ DSC dislocation are indicated.

one $\Sigma=11$ unit. The occurrence of one extra configuration (no. 5 of fig. 12) shows that there was some interference between the $\Sigma=11$ and the $\Sigma=27$ units. See fig. 12.

A number of simulations of the interaction of 60° dislocations with the $\Sigma=9$ ($2\bar{2}1$) boundary were performed to be able to compare with experimental observations. The simulations for the interaction between the $\Sigma=9$ ($2\bar{2}1$) boundary and the $1/2[10\bar{1}]$ 60° dislocation on the $(1\bar{1}1)$ plane show absorption of the dislocation and splitting into the $1/18[2\bar{2}\bar{8}]$ and $1/18[72\bar{1}]$ DSC dislocations, causing an effective step (King and Smith 1980) in the boundary plane of $+4$ and -3.5 interplanar layers, respectively. The $1/18[2\bar{2}\bar{8}]$ DSC is not an elementary DSC dislocation and it is glissile in the boundary plane, so it could be expected to split into two $1/18[1\bar{1}\bar{4}]$ dislocations. If the initial configuration before relaxation was altered in such a way that the position of the boundary plane was displaced by 4 interplanar spacings over a length of 2 boundary periods by shuffling of the atoms in these planes, a different configuration with lower energy was observed, showing splitting into two separate $1/18[1\bar{1}\bar{4}]$ dislocations and the $1/18[72\bar{1}]$. See fig. 13. For the interaction with the $1/2[01\bar{1}]$ dislocation on the $(1\bar{1}\bar{1})$ plane, splitting into lattice Shockley partials was observed and the leading (pure edge) partial was attracted to the boundary plane.

§ 4. DISCUSSION

In all the examples studied so far, there was an attractive force between the boundary and the (partial) dislocation core. First, we will discuss the results of the static simulations for the $\Sigma=3$, the $\Sigma=27$ and the $\Sigma=11$ boundaries and we will consider the effect of increasing ordering tendency.

For the $\Sigma=3$ and the $\Sigma=11$ boundaries, the absorption in the boundary plane and splitting into DSC dislocations can be understood using the \mathbf{b}^2 criterion, the fact that both dislocations are glissile in the boundary plane, the small step height associated with these dislocations and the conservation of step height (King and Smith 1980). In Cu, the new boundary that is formed between the two g.b.d.s is exactly the same as the original boundary, and therefore, from an elastic point of view, the g.b.d.s would be

expected to move apart as far as possible. Recent simulations using Finnis–Sinclair potentials (Pestman, De Hosson, Vitek, Tichelaar and Schapink 1990) show that the friction stress for screw dislocations is high in perfect crystal. An estimate of the elastic repulsion (using bulk elastic constants and isotropic elastic theory) in equilibrium with the friction stress yields a separation distance which is comparable to the actual separation that was found in the simulations described in this paper. As the Burgers vectors of the DSC dislocations in the $\Sigma = 11$ boundary are more parallel than those in the $\Sigma = 3$ boundary, a stronger elastic repulsion between them, and hence a large separation distance between the $\Sigma = 11$ g.b.d.s, would be expected. A possible reason why this is not so, might be found in a higher friction stress for glide in the $(\bar{1}13)$ boundary plane of the $\Sigma = 11$ boundary than for the $(\bar{1}11)$ boundary plane of the $\Sigma = 3$. The results for the $\Sigma = 3$ and $\Sigma = 11$ boundaries are confirmed by experimental observations using TEM of widely dissociated pairs of the same DSC dislocations in austenitic stainless steel for $\Sigma = 3$ (Pumphrey and Bowkett 1971) and for $\Sigma = 11$ by *in situ* observations of DSC dislocations, to which the same Burgers vectors are attributed as in our case, gliding on the $(\bar{1}13)$ boundary plane in Al (Mori and Tangri 1979).

The decrease in separation of the g.b.d.s when we go from 'disordered' Cu via Cu_3Au to strongly ordered Ni_3Al can be explained by the differences in the energy of the new grain boundary segment that is created between the g.b.d.s. The energy difference between the original boundary and the boundary created between the g.b.d.s is zero for disordered material and increases with increasing ordering tendency. See also table 1. In Cu_3Au and in Ni_3Al , a stable configuration showing splitting into two lattice Shockley partials occurred for the $\Sigma = 3$ boundaries in contrast to Cu where this did not occur. This can be explained by the small differences between the energy of the CSF, which is created between the two lattice Shockley partials, and the ordering fault energy of the boundary that is created between the g.b.d.s in the case of absorption. If we assume bulk elastic constants and only take the energy of the fault that is created between the two g.b.d.s into account, the equilibrium separation using isotropic elastic theory of the two g.b.d.s in the $\Sigma = 11$ in Ni_3Al , for example, would be expected to be $5.1 a_0$. The high friction force again could be the reason for the smaller splitting distances that are observed in the simulations.

In the $\Sigma = 27$ case, the attraction without splitting into g.b.d.s in the boundary plane shows that the (partial) dislocation core can lower its energy by merging into the boundary core. Absorption into DSC dislocations, as occurred in Cu_3Au structure, causes a larger step in the grain boundary plane than in the $\Sigma = 11$ or $\Sigma = 3$ boundary and glide of the two DSC dislocations will be associated with shuffling of atoms. Also, in the $L1_2$ structure, depending on the way the shuffling takes place, anti-site defects can be created in the shuffled region (i.e. the region between the positions of the boundary plane before and after migration). This will limit the separation of DSC dislocations. This argument can be applied in general to boundaries in the ordered structure. Even for another grain boundary-dislocation system, if there is dissociation into g.b.d.s that belong to the DSC lattice of the ordered grain boundary and no fault in the new boundary structure between the g.b.d.s is created, the creation of anti-site defects will limit the separation of the g.b.d.s. The reason why the splitting into g.b.d.s only occurred in Cu_3Au , might be found in the differences in the interatomic interactions between the three materials.

Now we turn to the results of the kinematical simulations. The applied shear stresses necessary to start the movement of the screw dislocations in perfect lattice are

0.009 μ for Cu (μ is the shear modulus) and 0.007 μ for Ni₃Al. These values are high in comparison to experimental values of the friction stress, even if we take into account the fact that the simulations are done at 0 K and that the friction stress for a screw dislocation is higher than for an edge. Of course, it should be noted that, because of the periodic boundary conditions along the dislocation line, motion of the screw dislocation through the formation of kinks is prohibited.

The transmission through the $\Sigma = 3$ boundary in both materials can be explained by the small angle between the symmetric slip plane in the other grain and the original slip plane, and consequently a high resolved shear stress on this slip plane. Transmission occurred at three times the friction stress for Cu and four times the friction stress for Ni₃Al, indicating that the $\Sigma = 3$ boundary is a stronger obstacle to dislocation movement in Ni₃Al.

From the study of the interaction with the $\Sigma = 27$ boundary in Cu, it can be concluded that the interaction with a boundary can show large differences, depending on where the dislocation arrives in the boundary. The resistance against shear seems to depend on the local atomic configuration and the differences within a structural unit can be large. When we compare the results for Cu and Ni₃Al, there are large differences between the interaction of the screw dislocation with the middle part of the structural unit in Cu and the interaction of the superpartial with the middle part of structural unit no. 1 in Ni₃Al. In Cu, transmission is observed at a stress level of less than three times the friction stress, while in Ni₃Al at more than five times the friction stress a complicated reaction takes place and transmission occurs at a different location in the grain boundary. When we compare the interaction of the screw dislocation gliding towards the left part of the structural unit in Cu with the interaction of the superpartial gliding towards the left part of structural unit no. 2 in Ni₃Al, we observe the same mechanism of cross slip towards the right part of the structural unit.

Both the $\Sigma = 3$ and the $\Sigma = 27$ boundaries show a tendency to transmission under an applied shear stress. In Ni₃Al, however, the stress level at which transmission occurs is clearly higher, even in terms of the friction stress, and the boundaries prove to be strong obstacles against passage of dislocations. It could be reasoned that a superdislocation arriving at a grain boundary in Cu₃Au and especially in Ni₃Al with its high APB energy first responds to an applied shear stress by decreasing the width of the APB separating the two superpartials. As a matter of course this phenomenon does not occur in f.c.c. Cu and, consequently, the boundaries are more transparent for moving dislocations. In Ni₃Al in particular, the close approach of the trailing superpartial to the leading one causes a stress concentration at the boundary plane. It might be envisaged that in reality in Ni₃Al, other processes like intergranular fracture will occur in response to the applied stress at lower stress levels than those necessary for transmission.

The absorption in the $\Sigma = 11$ boundary compares well to the static simulations, for in those the tendency of absorption and splitting into DSC dislocations was observed in both materials. This tendency is presumably so strong that transmission onto the $(1\bar{1}\bar{1})_{II}$ plane does not occur, in spite of the small deviation angle with respect to the original slip plane.

The results for the $\Sigma = 57$ and the $\Sigma = 9$ ($\bar{1}14$) boundaries show that the structural unit model may help us to predict the interaction between the screw dislocation and a long period boundary, if we know the interaction between the dislocation and the delimiting favoured boundaries. The results of a previous pair potential study of the $\Sigma = 57$ boundary in L1₂ ordered structure (Pestman, De Hosson, Vitek and Schapink 1990) support this conclusion for ordered alloys. However, there are two consider-

ations that have to be kept in mind: first, in the case of absorption in the boundary and splitting into DSC dislocations, the distance of splitting is limited to one type of structural unit; second, the minority units can be thought to contain a dislocation core and there can be elastic interaction with the lattice dislocation. In our case, the core of the $1/22[\bar{2}26]$ DSC that can be considered to be located in the $\Sigma=27$ unit in the $\Sigma=57$ boundary has elastic interaction with the edge components of the Shockley partials in the $(1\bar{1}1)$ plane of the screw dislocation. The leading partial is attracted whereas the trailing one is repelled. This might be an explanation for the slightly larger stacking fault of configurations no. 4 and 5 of fig. 11 for $\Sigma=57$ with respect to the configurations no. 1 and 2 of fig. 3 for $\Sigma=27$.

The simulations for the $\Sigma=9(2\bar{2}1)$ boundary in Cu can be compared with HRTEM observations of Elkajbaji and Thibault-Desseaux (1988) of the same system in Si. Since Si can be regarded as an f.c.c. lattice with a basis consisting of two atoms, the geometry of the system is the same. The splitting of the $1/2[10\bar{1}]$ dislocation into the $1/18[72\bar{1}]$ (which is the $1/6[21\bar{1}]_{II}$ in the notation as used by Elkajbaji and Thibault) and two $1/18[1\bar{1}\bar{4}]$ g.b.d.s compares very well with fig. 9 of their paper. In our simulations the splitting distances are much lower, as the friction stress in the simulations is relatively high. The attraction to the grain boundary plane of the leading 90° Shockley partial of the $1/2[011]$ lattice dislocation compares well with fig. 8(a) of their paper. Splitting of the leading Shockley partial into two g.b.d.s, as was observed experimentally, would not be expected to occur in the simulations: there is no driving force for this dissociation, because the Burgers vectors of the two g.b.d.s are perpendicular and in the simulations there are no external stresses.

The simulations have been done for configurations at 0 K. It could be reasoned that the mechanisms of the interactions, which are mostly derived from calculations of energy differences, will probably remain the same at higher temperatures, whereas the motion of the g.b.d.s, especially if associated with shuffling atoms or with climb, will be easier. Further, the concept of structural multiplicity has been found to be very common within the structural unit model, with alternative structures frequently possessing very similar energies. The existence of these alternative structures suggests that at high temperatures transformations of the boundary structures could occur. These transformations may either be of the order-disorder type involving transition from a periodic to a non-periodic multiple structure, or the transitions from one alternative structure to another (Vitek, Minonishi, Wang 1985, Vitek and De Hosson 1986).

§ 5. CONCLUSIONS

- (1) A number of experimental observations of dislocation-grain boundary interaction can be reproduced in computer simulation.
- (2) The structural unit model may be used to predict the interaction of a lattice dislocation with boundaries in a certain misorientation range if the interaction of the lattice dislocation with the favoured boundaries delimiting the misorientation range is known.
- (3) The mechanism of the interaction between lattice dislocations and grain boundaries is similar for boundaries in ordered and disordered (or f.c.c.) materials. In the case of absorption into g.b.d.s in ordered material, an ordering fault is left behind in the boundary plane and anti-site defects may be created during movement of the g.b.d. Because of these phenomena, movement of g.b.d.s in ordered material is hindered and, in the case of extended slip, stress

concentrations will develop at the boundary upon arrival of more lattice dislocations. In the case of transmission, the simulations show that transmission through an ordered boundary occurs at high stress levels and the superpartials constituting the arriving dislocation will decrease their separation in response to the applied stress. In this way, stress concentrations near the boundary will be generated. These considerations suggest that the interaction between lattice dislocations and grain boundaries may be of importance for the explanation of the intergranular fracture occurring in a number of ordered compounds, particularly those with a high ordering energy.

ACKNOWLEDGMENTS

This work is part of the research program of the Foundation for Fundamental Research on Matter (F.O.M.-Utrecht) and has been made possible by financial support from the Netherlands Organization for Research (N.W.O.-The Hague). A support of the National Science Foundation, MRL Program under Grant no. DMR88-19885 (VV) is acknowledged.

REFERENCES

- ACKLAND, G. J., TICHY, G., VITEK, V., and FINNIS, M. W., 1987, *Phil. Mag. A*, **56**, 735.
 ACKLAND, G. J., and VITEK, V., 1989, *High Temperature Ordered Intermetallic Alloys*, edited by C. C. Koch, C. T. Liu and A. I. Taub (Mater. Res. Soc. Symp. Proc. 133), p. 105.
 BAKER, I., SCHULSON, E. M. and HORTON, J. A., 1987, *Acta Metall.*, **35**, 1533.
 BALLUFFI, R. W., BROKMAN, A., and KING, A. H., 1982, *Acta Metall.*, **30**, 1453.
 BASINSKI, Z. S., DUESBERY, M. S., and TAYLOR, R., 1970, *Phil. Mag.*, **21**, 1201.
 BOLLMANN, W., 1970, *Crystal Defects and Crystalline Interfaces* (Berlin: Springer).
 CHAKI, T. K., 1990, *Phil. Mag. Lett.*, **61**, 5.
 CHALMERS, B., 1937, *Proc. R. Soc. London. A*, **162**, 120.
 DE HOSSON, J. TH. M., and VITEK, V., 1990, *Phil. Mag. A*, **61**, 305.
 DINGLEY, D. J., and POND, R. C., 1977, *Acta Metall.*, **27**, 667.
 ELKAJBAJI, M., and THIBAUT-DESSEAUX, J., 1988, *Phil. Mag. A*, **58**, 325.
 FARKAS, D., and SAVINO, E. J., 1988, *Scripta Metall.*, **22**, 557.
 FROST, H., 1987, *Acta Metall.*, **35**, 519.
 KING, A. H., and SMITH, D. A., 1980, *Acta Crystallogr. A*, **36**, 335.
 MORI, T., and TANGRI, K., 1979, *Metall. Trans. A*, **10**, 733.
 PESTMAN, B. J., DE HOSSON, J. TH. M., VITEK, V., and SCHAPINK, F. W., 1990, *J. de Phys. Paris*, **51**, C1-311.
 PESTMAN, B. J., DE HOSSON, J. TH. M., VITEK, V., TICHELAR, F. D., and SCHAPINK, F. W., 1990, *Alloy Phase Stability and Design*, edited by G. M. Stocks, D. P. Pope and A. F. Giamei (Mater. Res. Soc. Symp. Proc., MRS 186).
 PUMPHREY, P. H., and BOWKETT, K. M., 1971, *Phil. Mag. A*, **24**, 225.
 SHEN, Z., WAGONER, R. H., and CLARK, W. A. T., 1988, *Acta Metall.*, **36**, 3231.
 SUTTON, A. P., and VITEK, V., 1983, *Philos. Trans. R. Soc. London A*, **309**, 37.
 VITEK, V., ACKLAND, G. J., and CSERTI, J., 1990, *Alloy Phase Stability and Design*, edited by G. M. Stocks, D. P. Pope and A. F. Giamei (Mater. Res. Soc. Symp. Proc., MRS 186).
 VITEK, V., and DE HOSSON, J. TH. M., 1986, *Computer-based Microscopic Description of the Structure and Properties of Materials*, edited by J. Broughton, W. Krakow and S. T. Pantelides, MRS 63, 137.
 VITEK, V., MINONISHI, Y., WANG, G.-J., 1985, *J. Physique*, **46**, C4-171.
 VITEK, V., PERRIN, R. C., and BOWEN, D. K., 1970, *Phil. Mag.*, **21**, 1049.
 YAMAGUCHI, M., PAIDAR, V., POPE, D. P., and VITEK, V., 1982, *Phil. Mag. A*, **45**, 867.