

University of Nebraska - Lincoln

DigitalCommons@University of Nebraska - Lincoln

Diandra Leslie-Pelecky Publications

Research Papers in Physics and Astronomy

April 2005

Iron Oxide Nanoparticles for Sustained Delivery of Anticancer Agents

Tapan K. Jain

Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025

Marco Morales Torres

University of Nebraska - Lincoln, mmorales_torres2@unl.edu

Sanjeeb K. Sahoo

Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025

Diandra Leslie-Pelecky

University of Nebraska -- Lincoln, diandra2@unl.edu

Vinod Labhassetwar

*Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025 and Department of Biochemistry and Molecular Biology, University of Nebraska Medical Center, Omaha, Nebraska 68198-4525; * Author for correspondence. Mailing address: 986025; Nebraska Medical Center, Omaha, NE 68198-6025, vlabhase@unmc.edu*

Follow this and additional works at: <https://digitalcommons.unl.edu/physicslesliepelecky>

 Part of the [Physics Commons](#)

Jain, Tapan K.; Morales Torres, Marco; Sahoo, Sanjeeb K.; Leslie-Pelecky, Diandra; and Labhassetwar, Vinod, "Iron Oxide Nanoparticles for Sustained Delivery of Anticancer Agents" (2005). *Diandra Leslie-Pelecky Publications*. 2.

<https://digitalcommons.unl.edu/physicslesliepelecky/2>

This Article is brought to you for free and open access by the Research Papers in Physics and Astronomy at DigitalCommons@University of Nebraska - Lincoln. It has been accepted for inclusion in Diandra Leslie-Pelecky Publications by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.

Copyright © 2005 American Chemical Society

Iron Oxide Nanoparticles for Sustained Delivery of Anticancer Agents

Tapan K. Jain, *Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025*

Marco A. Morales, *Department of Physics & Astronomy and Center for Materials Research & Analysis, University of Nebraska-Lincoln, Lincoln, Nebraska 68588-0111*

Sanjeeb K. Sahoo, *Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025*

Diandra L. Leslie-Pelecky, *Department of Physics & Astronomy and Center for Materials Research & Analysis, University of Nebraska-Lincoln, Lincoln, Nebraska 68588-0111*

Vinod Labhassetwar, *Department of Pharmaceutical Sciences, College of Pharmacy, Nebraska Medical Center, Omaha, Nebraska 68198-6025 and Department of Biochemistry and Molecular Biology, University of Nebraska Medical Center, Omaha, Nebraska 68198-4525; * Author for correspondence. Mailing address: 986025 Nebraska Medical Center, Omaha, NE 68198-6025. Tel: (402) 559-9021. Fax: (402) 559-9543. E-mail: vlabhase@unmc.edu*

Received January 18, 2005

Abstract:

We have developed a novel water-dispersible oleic acid (OA)-Pluronic-coated iron oxide magnetic nanoparticle formulation that can be loaded easily with high doses of water-insoluble anticancer agents. Drug partitions into the OA shell surrounding iron oxide nanoparticles, and the Pluronic that anchors at the OA-water interface confers aqueous dispersity to the formulation. Neither the formulation components nor the drug loading affected the magnetic properties of the core iron oxide nanoparticles. Sustained release of the incorporated drug is observed over 2 weeks under in vitro conditions. The nanoparticles further demonstrated sustained intracellular drug retention relative to drug in solution and a dose-dependent antiproliferative effect in breast and prostate cancer cell lines. This nanoparticle formulation can be used as a universal drug carrier system for systemic administration of water-insoluble drugs while simultaneously allowing magnetic targeting and/or imaging.

Keywords: Sustained release; water-insoluble drugs; cellular uptake; breast cancer; targeting; tumor therapy; magnetic nanoparticles

<http://pubs.acs.org/cgi-bin/sample.cgi/mpohbp/2005/2/i03/html/mp0500014.html>

In accordance with ACS policy, only the abstract, figures, and tables are presented here.

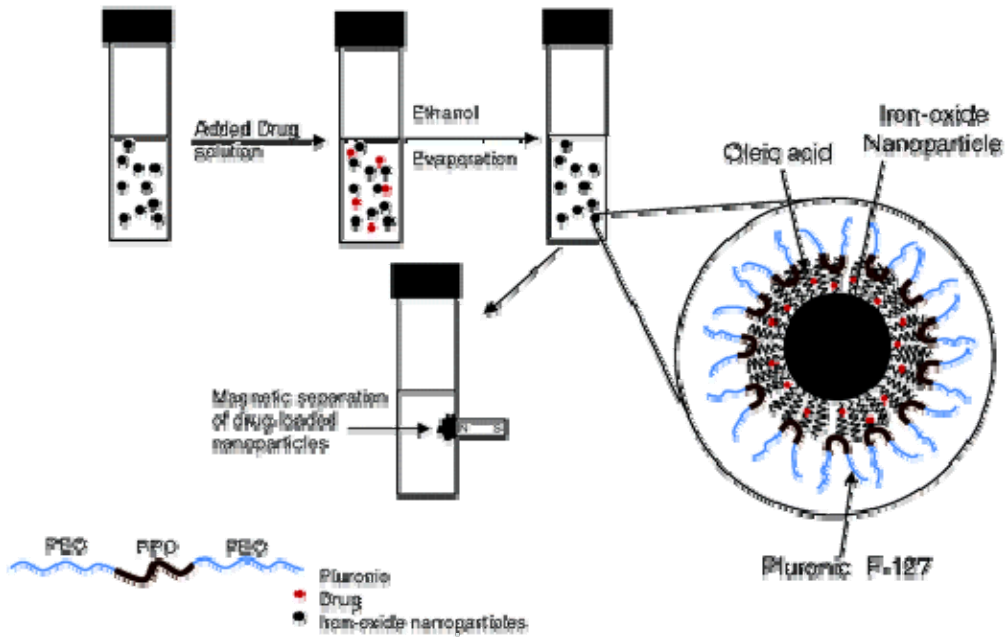


Figure 1 Schematic representing formulation of iron oxide nanoparticles and the process for drug loading.

Copyright © 2007 American Chemical Society

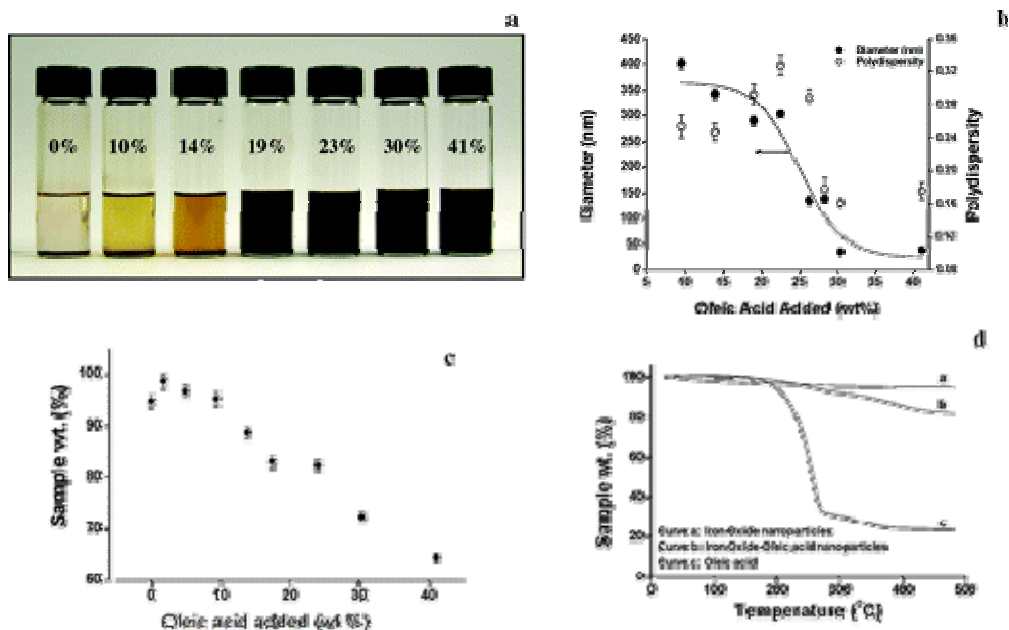


Figure 2 Effect of OA concentration on (a) sedimentation of iron oxide nanoparticles in hexane after 2 days; (b) mean particle size and polydispersity index of OA-coated iron oxide nanoparticles in hexane (data as mean \pm SEM, $n = 10$, a nonlinear square fitting was used to connect data points); (c) mass loss by thermogravimetric analysis of different formulations of OA-coated iron oxide nanoparticles (data as mean \pm SEM, $n = 3$; and (d) typical thermograms of iron oxide nanoparticles, OA, and OA-coated iron oxide nanoparticles (a representative from three different runs).

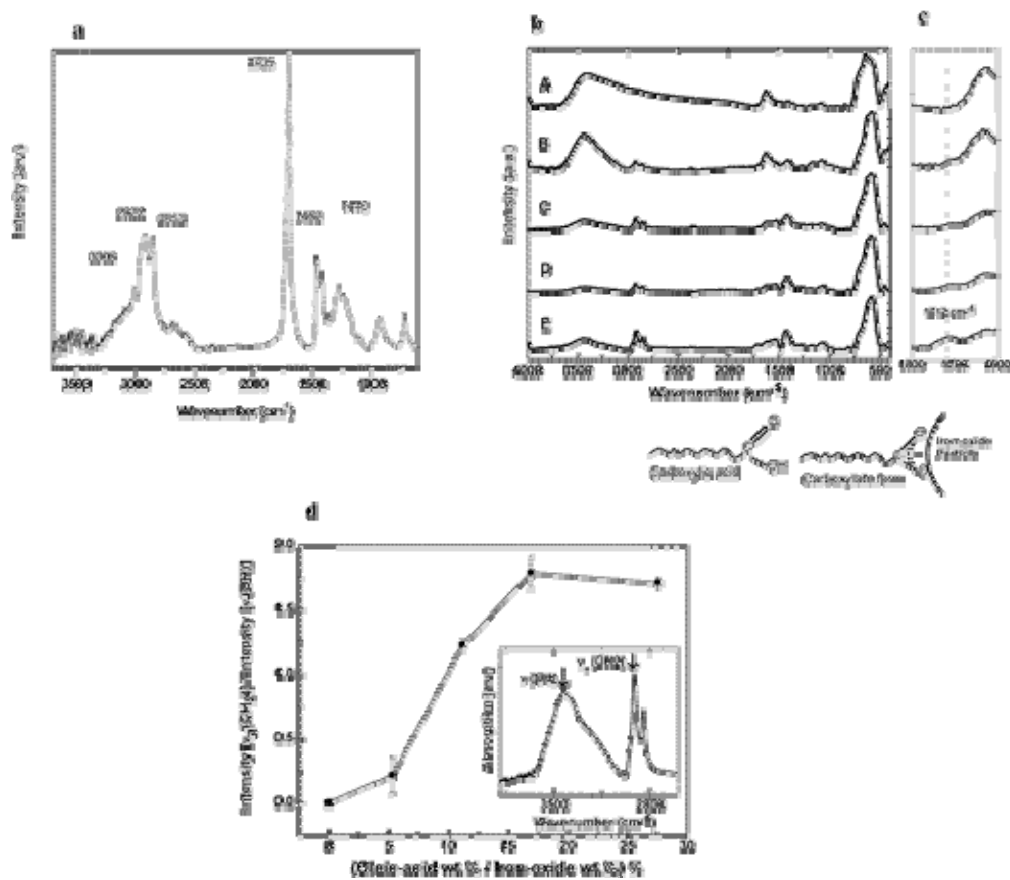


Figure 3 (a) FT-IR spectrum of pure OA. (b) FT-IR spectra of OA-coated iron oxide nanoparticles: (A) pure iron oxide; (B) 5 wt % OA relative to iron oxide; (C) 11 wt % OA relative to iron oxide; (D) 17 wt % OA relative to iron oxide; and (E) 23 wt % OA relative to iron oxide. (c) Zoom of the FT-IR spectra in the range of 1800-1600 cm⁻¹. (d) Relative intensities of the CH₂ symmetric stretch mode to the OH stretch mode versus the relative concentration of OA to the iron oxide (data as mean ± SEM from 32 spectral scans).

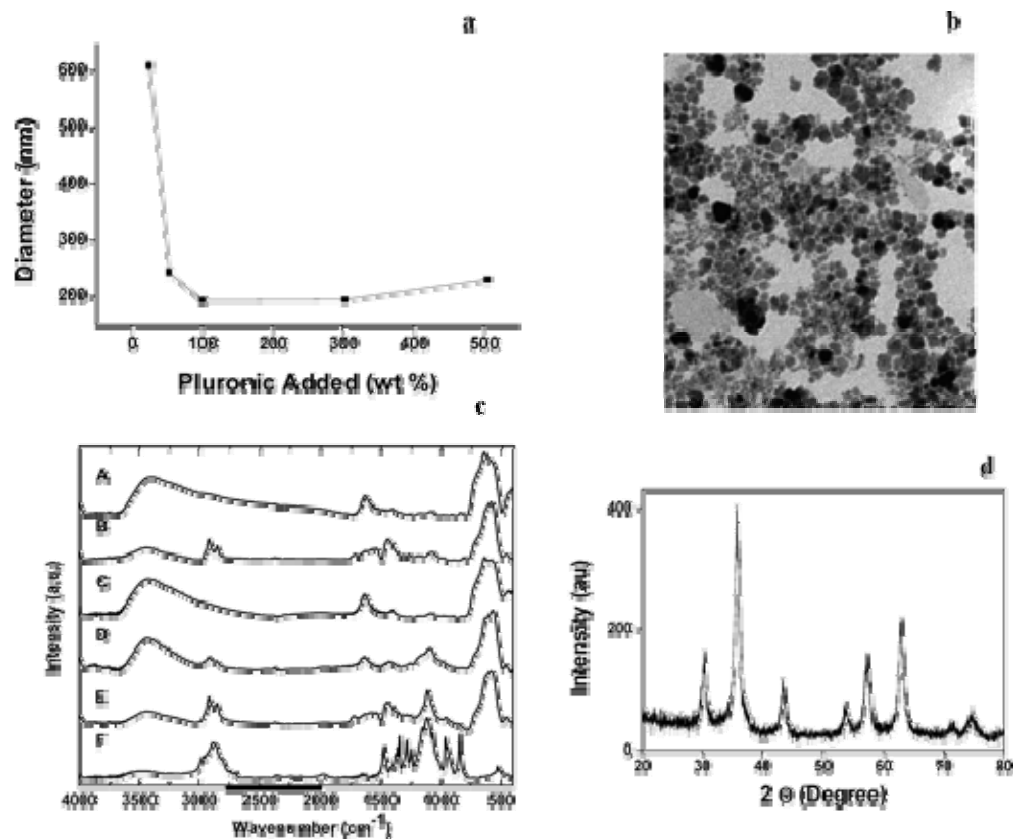


Figure 4 (a) Effect of different concentration of Pluronic on particle size of OA-coated iron oxide nanoparticles in water as measured by laser light scattering method (data as mean \pm SEM, $n = 10$). (b) TEM of OA-Pluronic stabilized iron oxide nanoparticles. (c) FT-IR spectra: (A) pure iron oxide; (B) 78.4 wt % iron oxide, 21.6 wt % OA; (C) 40.4 wt % iron oxide, 0.0 wt % OA, 59.6 wt % Pluronic F127; (D) 54.8 wt % iron oxide, 2.7 wt % OA, 42.5 wt % Pluronic F127; (E) 70.1 wt % iron oxide, 15.4 wt % OA, 14.5 wt % Pluronic F127; and (F) pure Pluronic F127. (d) XRD powder pattern of OA-Pluronic stabilized iron oxide nanoparticles.

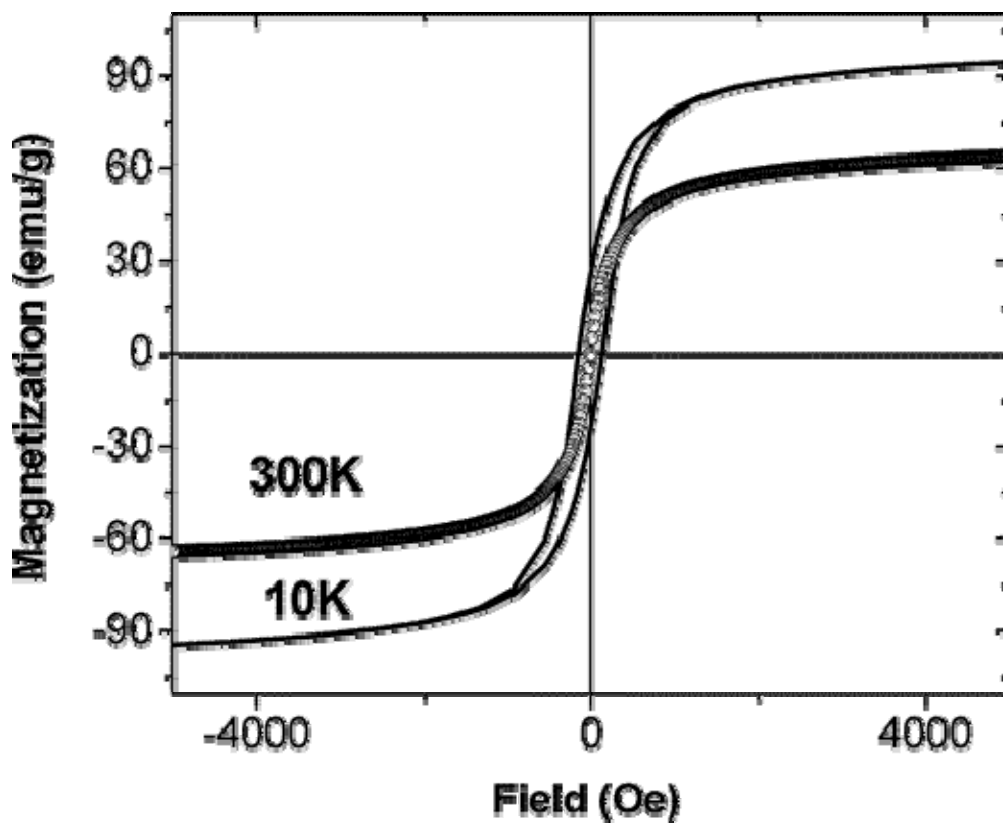


Figure 5 Magnetization as a function of field OA-Pluronic-stabilized iron oxide nanoparticles, measured at 10 K (solid line) and 300 K (circles).

Copyright © 2007 American Chemical Society

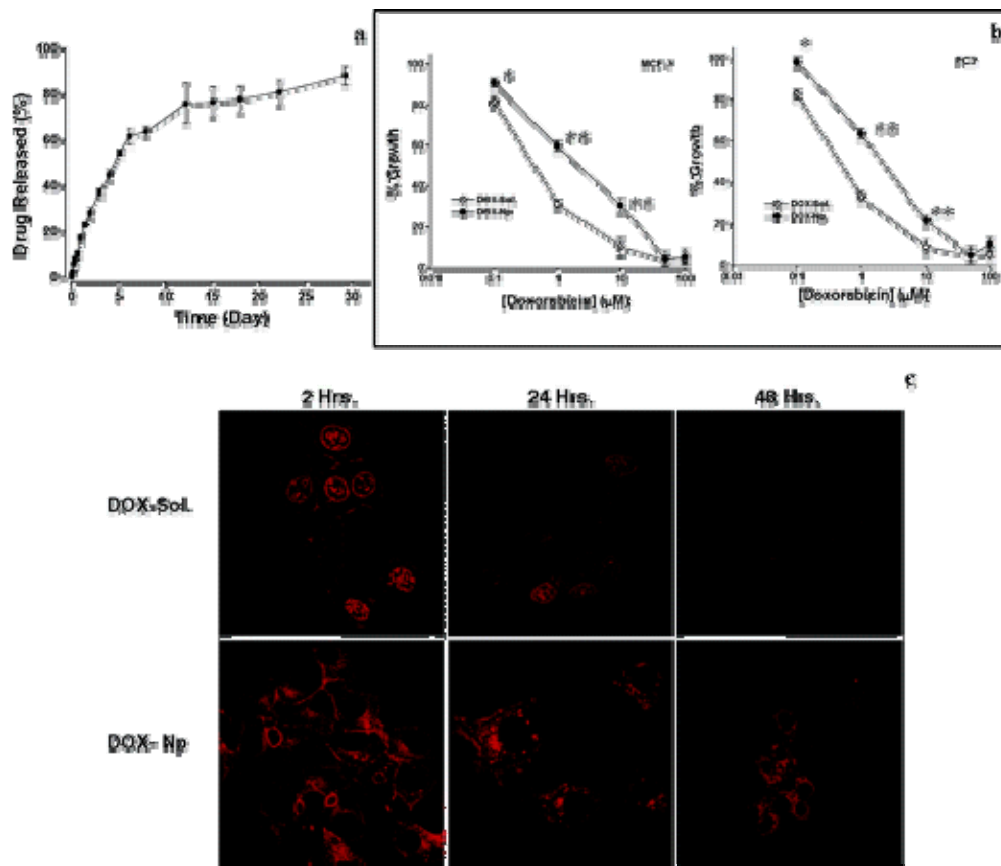


Figure 6 (a) Release of doxorubicin in vitro from drug-loaded OA-Pluronic-stabilized iron oxide nanoparticles. (b) Antiproliferative activity of drug-loaded nanoparticles and drug in solution in MCF-7 and PC3 cells. Data as mean \pm SEM ($n = 6$). * = $p < 0.05$, ** = $p < 0.005$, *** = $p < 0.001$. p values calculated for DOX-Np vs DOX-Sol. (c) Confocal laser scanning microscopic images of MCF-7 cells incubated for 2, 24, and 48 h with drug-loaded nanoparticles or drug in solution. Original magnification, 100 \times .

samples	saturation magnetization M_S (emu/g)	T_{max} (K)	coercive field H_C (Oe)
iron oxide nanoparticles	66.1 ± 0.1	215 ± 7	201 ± 11
OA-Pluronic-stabilized iron oxide nanoparticles	86.1 ± 0.5	170 ± 5	158 ± 05
drug-loaded OA-Pluronic- stabilized iron oxide nanoparticles	88.8 ± 0.5	160 ± 5	151 ± 06

^a Saturation magnetization is normalized to the weight of magnetite.