

# Light Induced Green Synthesis of Silver Nanoparticles Using Aqueous Extract of *Prunus amygdalus*

Sista Kameswara Srikar<sup>1,2</sup>, Deen Dayal Giri<sup>1,3</sup>, Dan Bahadur Pal<sup>1</sup>, Pradeep Kumar Mishra<sup>1</sup>, Siddh Nath Upadhyay<sup>1\*</sup>

<sup>1</sup>Department of Chemical Engineering & Technology, Indian Institute of Technology (BHU) Varanasi, Varanasi, Uttar Pradesh, India

<sup>2</sup>Tata Steel, Jamshedpur, Jharkhand, India

<sup>3</sup>Department of Botany, IFTM University, Moradabad, Uttar Pradesh, India  
Email: sista.sri@gmail.com, ddgiri1@gmail.com, danbahadur.chem@gmail.com, pkmishra.che@itbhu.ac.in, snupadyay.che@itbhu.ac.in

Received 2 November 2015; accepted 22 February 2016; published 25 February 2016

Copyright © 2016 by authors and Scientific Research Publishing Inc.

This work is licensed under the Creative Commons Attribution International License (CC BY).

<http://creativecommons.org/licenses/by/4.0/>



Open Access

---

## Abstract

Light driven, photon mediated green synthesis of silver nano-particles (AgNPs) was carried out using aqueous silver nitrate solution (1 mM) and aqueous extract of almond (*Prunus amugdalus*). Experiments were carried out in dark, diffused sunlight and direct sunlight to study the influence of light intensity as well as by wrapping the reaction tubes with colored cellophane filters (violet, green, yellow and red) to investigate the effect of light color on AgNP synthesis. It was observed that the violet filter enhanced the AgNPs synthesis appreciably. The FTIR spectroscopic analysis confirmed participation of bio-molecules with hydroxyl and amide groups present in the almond extract as reducing and capping or stabilizing agents, respectively. Dynamic light scattering (DLS) studies revealed the particle size distribution of nano-particles as 2 – 400 nm, and scanning electron microscopy (SEM) confirmed their spherical shape with an average size of about 20 nm. Growth analysis of AgNPs revealed an increase in number of nano-particles with time, whereas their rate of growth decreased gradually. The AgNP suspension was stable even beyond 3 weeks.

## Keywords

AgNPs, Nano-Particles, Green Synthesis, *Prunus amulgdalus*

---

\*Corresponding author.

## 1. Introduction

The most commonly used methods for nano-particle synthesis such as chemical reduction [1], gamma-ray irradiation [2], micro-emulsion [3], laser ablation [4], electrochemical reduction [5], autoclaving [6], microwave irradiation [7] and photochemical reduction [8] are associated with one or the other disadvantages like toxicity, high operation cost and energy inefficiency, and thus raising many environmental concerns. The quest for environmental friendly and sustainable methods to synthesize AgNPs has gained momentum during the past decade and shifted the interest of the researchers towards the bio-reduction potential of microorganisms [9]-[12], and plant extracts [13]-[20]. Natural polymers have also been used as reducing and capping agents in the synthesis of nano-particles [21]-[24]. The eco-friendly green synthesis methods suffer from the drawback of longer synthesis period for generation of AgNPs [25]. The vital need for efficient and cost effective supplementary methods to reduce the reaction time lag has attracted the interest of the researchers on light driven plasmon mediated reactions [26]. The photon induced methods are gaining increasing interest due to their advantages like controlled reducing action and generation of uniform AgNPs, capability to get absorbed by molecules without any additional absorption promoters and their low cost [27].

In the present work, aqueous extract of *Prunus amygdalus* was used to produce AgNPs, whose synthesis is mediated by the photons present in the sunlight. To the best of our knowledge, this is the first report regarding synthesis of AgNPs using aqueous almond extract.

## 2. Materials and Methods

### 2.1. Materials

Silver nitrate of 99.8% purity (Ranbaxy Industries Limited, India), fresh almonds (obtained from the local market of Varanasi, U.P) and distilled water was used in the experiments. Colored cellophane papers were purchased from the stationery market and all glass wares used in the experiments were purchased from Borosil (ISO 9001) Company, India.

### 2.2. Preparation of AgNPs

Almond extract was prepared by soaking 20 g of washed almonds in 100 ml distilled water for a period of 24 hr at 20°C followed by filtration using a Whatman's filter paper. This filtered aqueous extract (30 ml) was added to 30 ml aqueous AgNO<sub>3</sub> solution (2 mM) in a volumetric flask (250 ml) for a final concentration of 1mM (AgNO<sub>3</sub>). The above experiment was carried out in triplicate and the reaction mixtures were kept under dark (no light), dispersed sunlight and direct sunlight conditions. The above samples were stored and subjected to optical characterization studies.

In another set of experiments, AgNPs using similar reaction mixtures were synthesized in test tubes wrapped with violet, green, yellow and red colored cellophane papers, with 3 min exposure to direct sunlight. These samples were subjected to optical characterization study and results were recorded.

A typical sample of AgNPs of similar proportion was also synthesized with 3 min exposure to sunlight and was stored for optical, functional and morphological analyses. In order to carry out SEM analysis, the sample was centrifuged at 10,000 rpm for 10 min and the particles settled at the bottom of the tube were collected.

### 2.3. Characterizations

Synthesized AgNPs were subjected to optical analysis using PC based double beam UV-Visible spectrophotometer (Model-2202, Systronics) operated at a bandwidth of 2 nm in the wavelength range of 200 - 800 nm. Functional group analysis was carried out with a FTIR spectrophotometer (NICOLET-5700-Thermo Electron Corporation, USA) and morphological analysis was done using DLS (Delsa Nano C-Beckmann Coulter Company, Germany) instrument and SEM analysis performed using Supra-40, Carl Zeiss Oxford Instruments, Germany.

## 3. Results and Discussion

### 3.1. Effect of Light


UV-Vis spectral analysis of the samples grown under dark (no light) dispersed light and direct sunlight conditions

were carried out. Results (**Figure 1**) depict a remarkable difference in the absorbance patterns of the three cases, which reveals that no formation of AgNPs takes place under completely dark (no light) condition and the rate of formation of AgNPs gets accelerated by around 60 times in presence of direct sunlight compared to synthesis in dispersed light. The possible reason behind this behavior might be the presence of greater number of photons of certain wavelength in direct sunlight which catalyzed the reducing action, thus promoting the formation of AgNPs.


UV-Vis spectral analysis of AgNPs synthesized in color wrapped reaction tubes (**Figure 2(a)**), to predict the effect of the wavelength of light promoting the AgNPs synthesis, revealed the highest absorbance for violet color (380 - 450 nm) wrapped tube (**Figure 2(b)**), proving that this portion of the visible spectrum promotes the AgNPs synthesis.

### 3.2. Surface Plasmon Resonance


The AgNPs formation was accompanied by the appearance of yellowish-brown color from colorless sample (**Figure 3(a)**). Optical analysis of the sample revealed a Surface Plasmon Resonance (SPR) peak at ~420 nm (**Figure 3(b)**) due to the interaction of the electromagnetic radiation with the conduction band electrons around the nano-particles [28]. Sastry and coworkers also reported most of the SPR peaks of the AgNPs in the range of 400 - 450 nm [29].

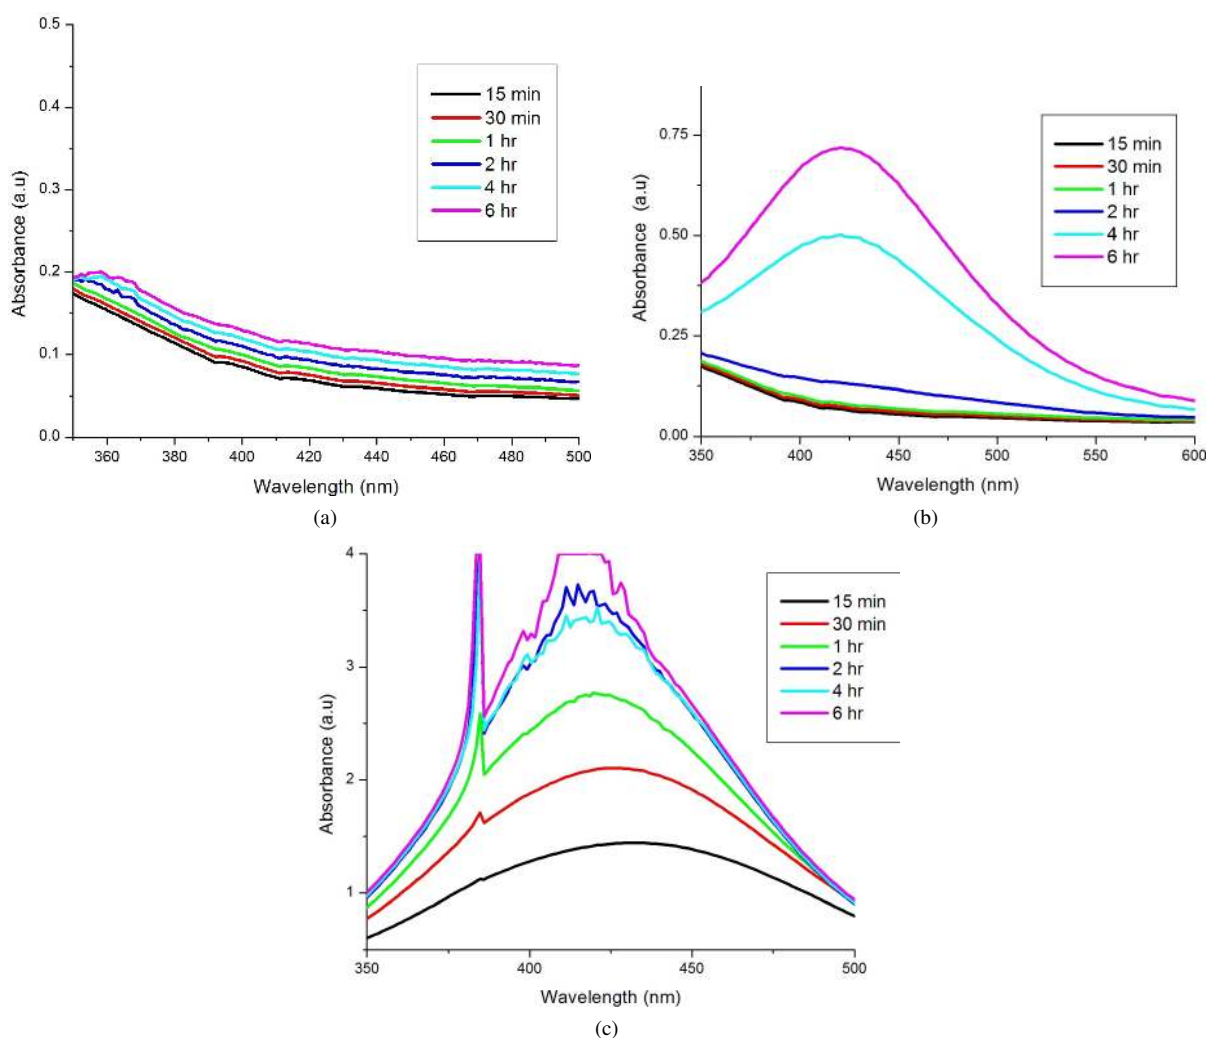

**Figure 1.** UV-Vis spectral analysis of AgNPs suspension samples (a) No light, (b) Exposed to dispersed sunlight (normal room light), (c) Exposed to direct sunlight.

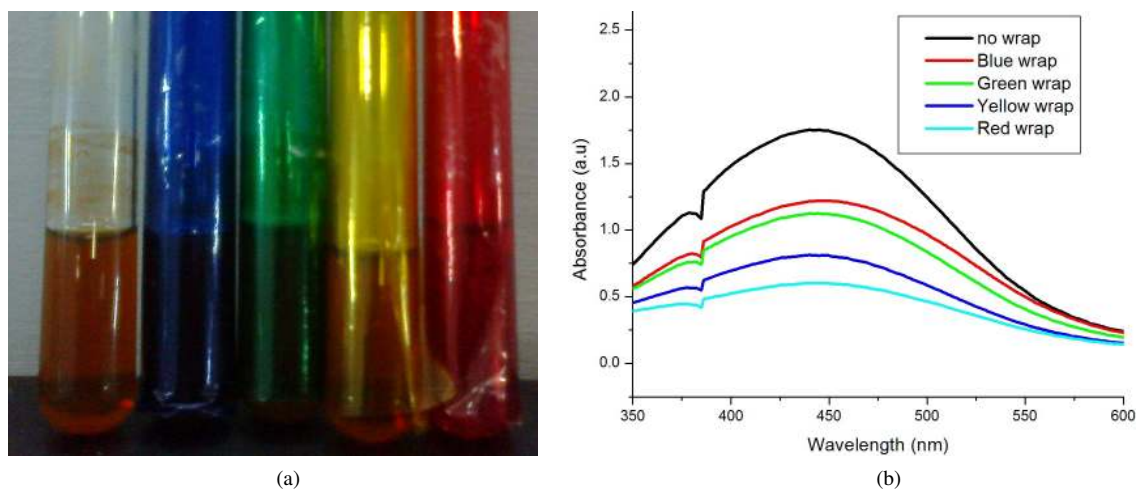

**Figure 2.** Effect of light wavelength on AgNPs synthesis: a) Reaction tubes wrapped with colored cellophane papers, b) UV-Vis spectra of AgNPs suspensions at different wavelengths.

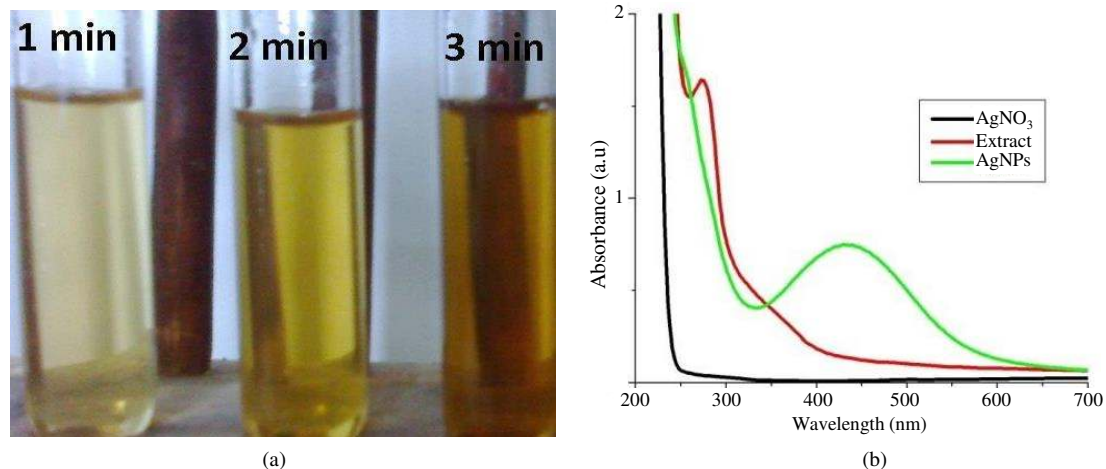

**Figure 3.** (a) Visible color change of the aqueous extract due to AgNP formation after exposure to the sun light for various durations due to AgNPs formation and (b) change in their SPR Peak.

### 3.3. Functional and Morphological Analysis

The FTIR spectral results (**Figure 4**) revealed significant peaks for almond extract at  $1636.4\text{ cm}^{-1}$  (amide-I and C = O),  $3301.7\text{ cm}^{-1}$  (OH-stretch) and for AgNPs at  $1636.3\text{ cm}^{-1}$  (amide-I and C = O),  $3286.8\text{ cm}^{-1}$  (OH-stretch). Decrease in the wave number from  $3301.7$  to  $3286.8\text{ cm}^{-1}$  after formation of AgNPs proved the consumption of OH groups for the synthesis, whereas no change in the wave number of amide group confirms their role in the stabilization of AgNP's. No significant change in the transmittance might be due to very low change in the concentration of active ingredient which is involved in changing  $\text{Ag}^+$  ions to AgNP and might also imply the presence of numerous number of reducing groups available in the biological extract ( $1636.4\text{ cm}^{-1}$ ). The results are in agreement with observations made by other researchers [30]-[32].

The SEM and DLS analyses revealed that the AgNP's are  $\sim 20\text{ nm}$  spheres and the particle size varied in between  $5 - 400\text{ nm}$ , with an average diameter of  $\sim 100\text{ nm}$  (**Figure 5**). Variation in the size estimate between the above two methods is due to the fact that the later method also measures the layer of water molecules associated with the AgNPs [33].

### 3.4. Growth Analysis

Change in absorbance of synthesized AgNPs suspension was analyzed for a period of 20 days. An increase in

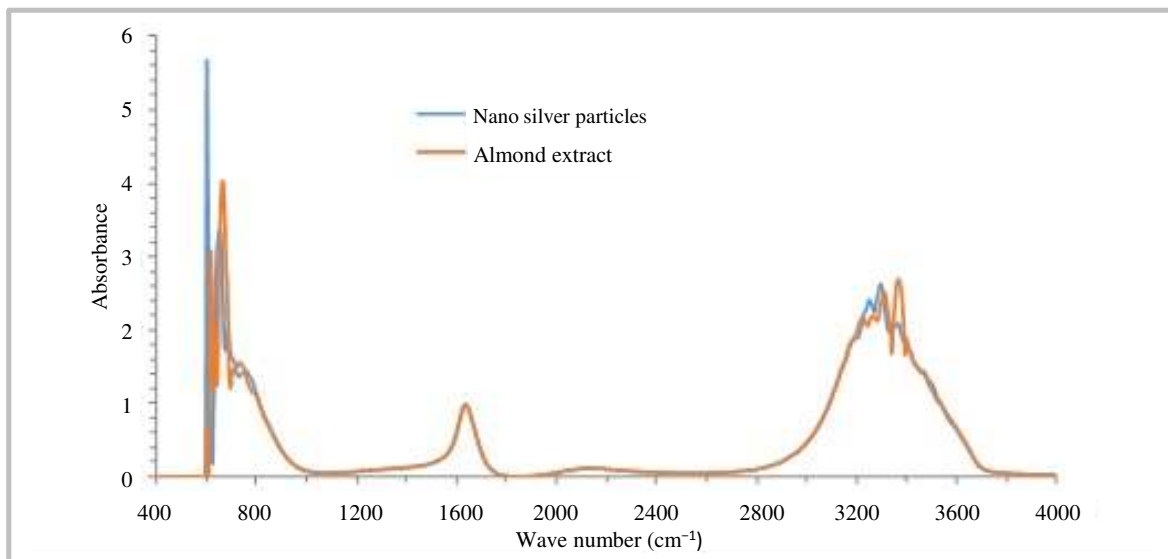


Figure 4. FTIR spectra of almond extract and AgNPs suspension.



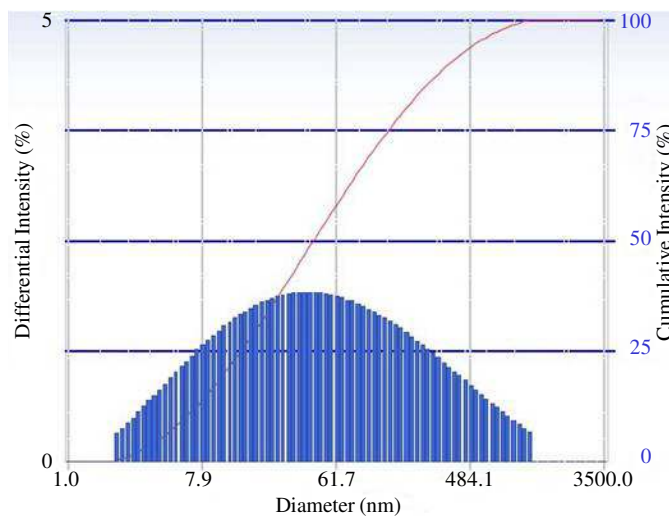


Figure 5. DLS spectra and SEM photomicrograph of AgNPs particles.

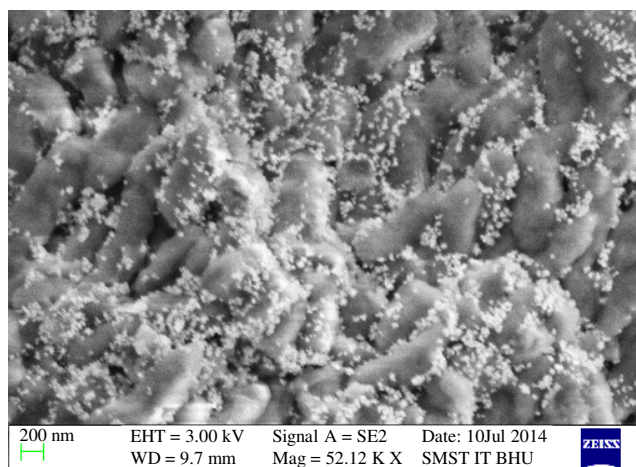

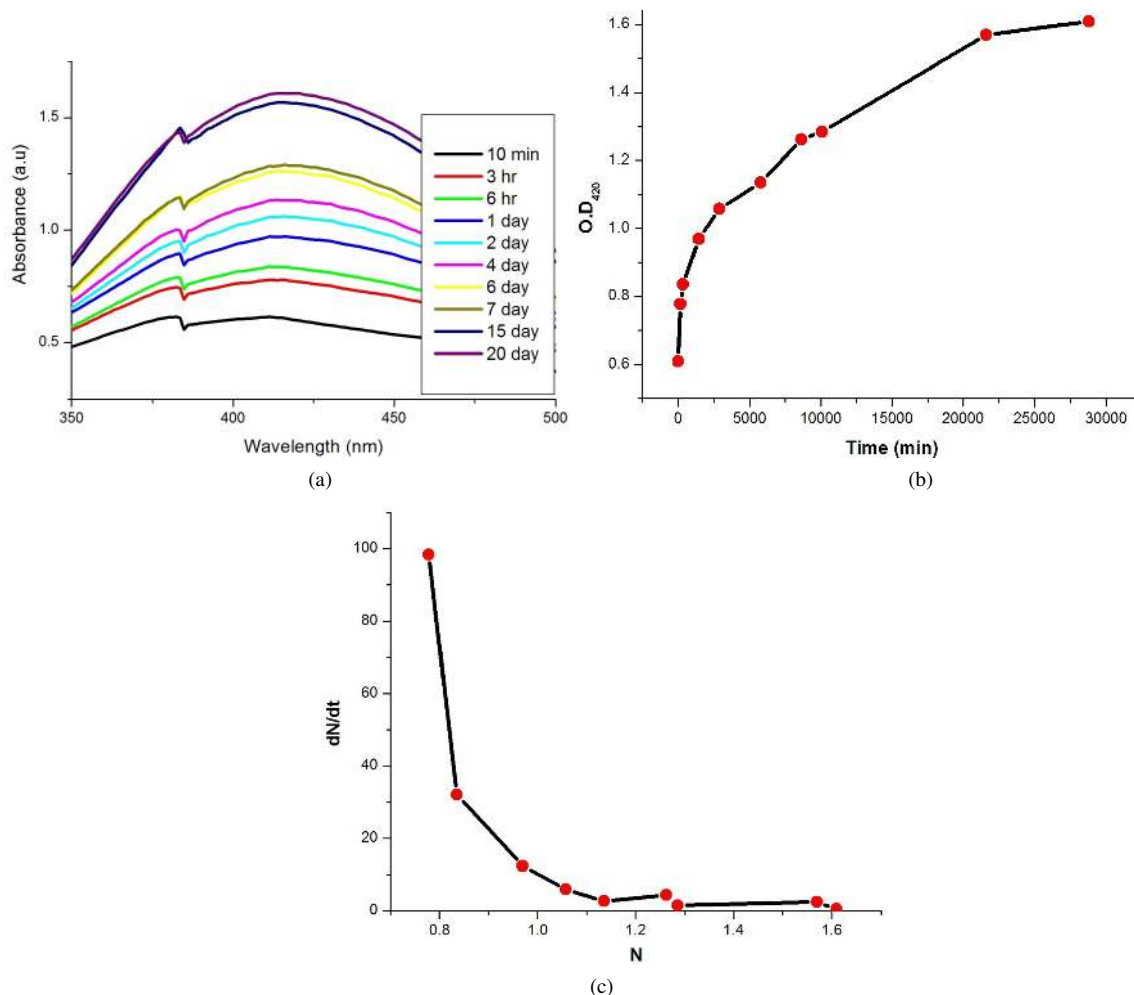

**Figure 6.** Growth Analysis for a period of 20 days, a) UV-Vis spectral analysis, b) Growth in number of AgNPs, c) Rate of formation of AgNPs.

absorbance ( $O. D_{420}$ ) with increase in time period signifies the growth in the number of AgNPs ( $N$ ). It is also observed that the rate at which the number of AgNPs being synthesized ( $dN/dt$ ) was high during the initial days and a gradual decrease in this rate was observed leading to a constant rate or no new growth zone after 18 days (Figure 6). This behavior might be due to the limited availability of extract molecules for the reduction of silver ions or due to the limited availability of  $Ag^+$  ions for the extract molecules.

Aging of nano-particles causes a red shift in the wavelength of SPR peak thereby proving their instability [34]. The synthesized AgNPs reported no wavelength shift in the SPR peak for a period of 20 days, proving their stability.

#### 4. Conclusion

Aqueous extract of *Prunus amygdalus* is an effective biological agent for synthesizing stable (20 days) and spherical AgNPs (~20 nm). Alcoholic groups presented in the extract promote the AgNPs synthesis and amide groups promote the stabilizing action. Violet portion of visible light supports the synthesis of AgNPs. Sunlight, photo catalyzed the reducing action of biological agent and accelerated the synthesis rate by about 60 times. Growth analysis of AgNPs revealed that the rate of formation of nano-particles decreases gradually with time.

#### Acknowledgements

The authors are thankful to by Dr. Chandan Upadhyay (Department of Materials Science and Engineering) for

SEM analysis, Prof. Sanjay Singh (Department of Pharmaceutics) for DLS analysis and the Head, Department of Chemical Engineering and Technology, IIT-BHU for encouragement and providing necessary facilities. DDG is thankful to UGC, New Delhi for grant in form of DS Kothari Postdoc Fellowship. SNU is grateful to the Department of Atomic Energy, Government of India, Mumbai for the award of Raja Ramanna Emeritus Fellowship

## References

- [1] Khan, Z., Al-Thabaiti, S.A., Obadi, A.Y. and Al-Youbi, A.O. (2011) Preparation and Characterization of Silver Nanoparticles by Chemical Reduction Method. *Colloids and Surfaces B*, **82**, 513-517. <http://dx.doi.org/10.1016/j.colsurfb.2010.10.008>
- [2] Chen, P., Song, L.Y. and Liu, Y.K. (2007) Synthesis of Silver Nanoparticles by Gamma-Ray Irradiation in Acetic Water Solution Containing Chitosan. *Radiation Physics and Chemistry*, **76**, 1165-1168. <http://dx.doi.org/10.1016/j.radphyschem.2006.11.012>
- [3] Zhang, W.Z., Qiao, X.L. and Chen, J.G. (2006) Synthesis and Characterization of Silver Nanoparticles in AOT Micro-Emulsion System. *Chemical Physics*, **300**, 495-500. <http://dx.doi.org/10.1016/j.chemphys.2006.09.029>
- [4] Abid, J.P., Wark, A.W., Brevetm, P.F. and Giarult, H.H. (2002) Preparation of Silver Nanoparticles in Solution from a Silver Salt by Laser Irradiation. *Chemical Communications*, **7**, 792-793. <http://dx.doi.org/10.1039/b200272h>
- [5] Reicha, F.M., Sarhan, A., Abdel-Hamid, M.I. and El-Sherbiny, I.M. (2012) Preparation of Silver Nanoparticles in the Presence of Chitosan by Electrochemical Method. *Carbohydrate Polymers*, **89**, 236-244. <http://dx.doi.org/10.1016/j.carbpol.2012.03.002>
- [6] Yang, J. and Pan, J. (2012) Hydrothermal Synthesis of Silver Nanoparticles by Sodium Alginate and Their Applications in Surface-Enhanced Raman Scattering and Catalysis. *Acta Materialia*, **60**, 4753-4758. <http://dx.doi.org/10.1016/j.actamat.2012.05.037>
- [7] Khan, A., El-Toni, A.M., Alrokayan, S., Alsalmi, M., Alhoshan, M. and Aldwayyan, A.S. (2011) Microwave-Assisted Synthesis of Silver Nanoparticles Using Poly-N Isopropyl Acrylamide/Acrylic Acid Microgel Particles. *Colloids and Surfaces A*, **377**, 356-360. <http://dx.doi.org/10.1016/j.colsurfa.2011.01.042>
- [8] Alarcon, E.I., Udekwu, K., Skog, M., Pacioni, N.L., Stamplecoskie, K.G., Gonzalez-Bejar, M., Poliseti, N., Wickham, A., Richter-Dahlfors, A., Griffith, M. and Scaiano, J. (2012) The Biocompatibility and Antibacterial Properties of Collagen-Stabilized, Photochemically Prepared Silver Nanoparticles. *Biomaterials*, **33**, 4947-4956. <http://dx.doi.org/10.1016/j.biomaterials.2012.03.033>
- [9] Das, S.K., Khan, Md.M.R., Guha, A.K., Das, A.K. and Mandal, A.B. (2012) Silver-Nanobiohybrid Material: Synthesis, Characterization and Application in Water Purification. *Bioresource Technology*, **124**, 495-499. <http://dx.doi.org/10.1016/j.biortech.2012.08.071>
- [10] Fayaz, A.M., Balaji, K., Kalaichelvan, P.T. and Venkatesan, R. (2009) Fungal Based Synthesis of Silver Nanoparticles—An Effect of Temperature on the Size of Particles. *Colloids and Surfaces B*, **74**, 123-126. <http://dx.doi.org/10.1016/j.colsurfb.2009.07.002>
- [11] Zhang, M., Zhang, K., Gussemme, B.D., Verstraete, W. and Field, R. (2014) The Antibacterial and Anti-Biofouling Performance of Biogenic Silver Nanoparticles by *Lactobacillus fermentum*. *Biofouling: The Journal of Bioadhesion and Biofilm Research*, **30**, 347-357. <http://dx.doi.org/10.1080/08927014.2013.873419>
- [12] Juibari, M.M., Abbasalizadeh, S., Jouzani, G.S. and Noruzi, M. (2011) Intensified Biosynthesis of Silver Nanoparticles Using a Native Extremophilic *Ureibacillus thermosphaerius* Strain. *Materials Letters*, **65**, 1014-1017. <http://dx.doi.org/10.1016/j.matlet.2010.12.056>
- [13] Kathiraven, T., Sundaramanickam, A., Shanmugam, N. and Balasubramanian, T. (2014) Green Synthesis of Silver Nanoparticles Using Marine Algae *Caulerpa resmosa* and Their Anti-Bacterial Activity against Some Human Pathogens. *Applied Nanoscience*, **5**, 499-504. <http://dx.doi.org/10.1007/s13204-014-0341-2>
- [14] Kulkarni, A.P., Srivastava, A.A., Nagalgaon, R.K. and Zunjarrao, R.S. (2012) Phytofabrication of Silver Nanoparticle from a Novel Plant Source and Its Application. *International Journal of Biological & Pharmaceutical Research*, **3**, 417-421.
- [15] Bhor, G., Maskare, S., Hinge, S., Singh, L. and Nalwade, A. (2014) Synthesis of Silver Nanoparticles Using Leaflet Extract of *Nephrolepis sexaltata* L. and Evaluation Antibacterial Activity against Human and Plant Pathogenic Bacteria. *Asian Journal of Pharmaceutical Technology and Innovation*, **2**.
- [16] Jha, A.K. and Prasad, K. (2010) Green Synthesis of Silver Nanoparticles Using *Cycas* Leaf. *International Journal of Green Nanotechnology: Physics and Chemistry*, **1**, 110-117.
- [17] Ashokkumar, S., Ravi, S., Kathiravan, V. and Velmurugan, S. (2015) Synthesis of Silver Nanoparticles Using *A. indicum* Leaf Extract and Their Antibacterial Activity. *Spectrochimica Acta Part A: Molecular and Biomolecular Spec-*

- troscopy*, **134**, 34-39. <http://dx.doi.org/10.1016/j.saa.2014.05.076>
- [18] Suresh, P., Gunasekar, P.H., Kokila, D., Prabhu, D., Dinesh, D., Ravichandran, N., Ramesh, B., Koodalingam, A. and Siva, G.V. (2014) Green Synthesis of Silver Nanoparticles Using *Delphinium denundatum* Root Extract Exhibits Antibacterial and Mosquito Larvicidal Activities. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, **127**, 61-66. <http://dx.doi.org/10.1016/j.saa.2014.02.030>
- [19] Yasin, S., Liu, L. and Yao, J. (2013) Biosynthesis of Silver Nanoparticles by Bamboo Leaves Extract and Their Antimicrobial Activity. *Journal of Fiber Bioengineering and Informatics*, **6**, 77-84. <http://dx.doi.org/10.3993/jfbi03201307>
- [20] Veerasamy, R., Xin, T.Z., Gunasagaran, S., Xiang, T.F.W., Yang, E.F.C., Jeyakumar, N. and Dhanaraj, S.A. (2011) Biosynthesis of Silver Nanoparticles Using Mangosteen Leaf Extract and Evaluation of Their Antimicrobial Activities. *Journal of Saudi Chemical Society*, **15**, 113-120. <http://dx.doi.org/10.1016/j.jscs.2010.06.004>
- [21] Chen, Q., Jiang, H., Ye, H., Li, J. and Huang, J. (2014) Preparation, Antibacterial, and Antioxidant Activities of Silver/Chitosan Composites. *Journal of Carbohydrate Chemistry*, **33**, 298-312.
- [22] Ashraf, S., Abbasi, A.Z., Pfeiffer, C., Hussain, S.Z., Khalid, Z.M., Gil, P.R., Parak, W.J. and Hussain, I. (2013) Protein-Mediated Synthesis, pH-Induced Reversible Agglomeration, Toxicity and Cellular Interaction of Silver Nanoparticles. *Colloids and Surfaces B: Biointerfaces*, **102**, 511-518. <http://dx.doi.org/10.1016/j.colsurfb.2012.09.032>
- [23] Sasikala, D., Govindaraju, K., Tamilselvan, K. and Singaravelu, G. (2012) Soyabean Protein: A Natural Source for the Production of Green Silver Nanoparticles. *Biotechnology and Bioprocess Engineering*, **17**, 1176-1181. <http://dx.doi.org/10.1007/s12257-012-0021-6>
- [24] Kora, A.J., Sashidhar, R.B. and Arunachalam, J. (2010) Gum Kondagogu (*Cochlospermum gossypium*): A Template for Green Synthesis and Stabilization of Silver Nanoparticles with Antibacterial Application. *Carbohydrate Polymers*, **82**, 670-679. <http://dx.doi.org/10.1016/j.carbpol.2010.05.034>
- [25] Shankar, S.S., Ahmad, A. and Sastry, M. (2003) Geranium Leaf Assisted Biosynthesis of Silver Nanoparticles. *Biotechnology Progress*, **19**, 1627-1631. <http://dx.doi.org/10.1021/bp034070w>
- [26] Zhang, J., Langille, M.R. and Mirkin, C.A. (2010) Photomediated Synthesis of Silver Triangular Bipyramids and Prisms: The Effect of pH and BSPP. *Journal of the American Chemical Society*, **132**, 12502-12510. <http://dx.doi.org/10.1021/ja106008b>
- [27] Dong, S., Tang, C., Zhou, H. and Zhao, H. (2004) Photochemical Synthesis of Gold Nanoparticles by the Sunlight Radiation Using a Seeding Approach. *Gold Bulletin*, **37**, 187-195. <http://dx.doi.org/10.1007/BF03215212>
- [28] Park, J. and Kim, Y. (2008) Effect of Shape of Silver Nanoplates on the Enhancement of Surface Plasmon Resonance (SPR) Signals. *Journal of Nanoscience and Nanotechnology*, **8**, 5026-5029. <http://dx.doi.org/10.1166/jnn.2008.1018>
- [29] Sastry, M., Mayya, K.S. and Bandyopadhyay, K. (1997) pH Dependent Changes in the Optical Properties of Carboxylic Acid Derivatized Silver Colloid Particles. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, **127**, 221-228. [http://dx.doi.org/10.1016/S0927-7757\(97\)00087-3](http://dx.doi.org/10.1016/S0927-7757(97)00087-3)
- [30] Sadeghi, B. and Gholamhoseinpoor, F. (2015) A Study on Stability and Green Synthesis of Silver Nanoparticles Using *Ziziphora tenuior* (Zt) Extract at Room Temperature. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, **134**, 310-315. <http://dx.doi.org/10.1016/j.saa.2014.06.046>
- [31] Vijaykumar, P.P.N., Pammi, S.V.N., Kollu, P., Satyanarayana, K.V.V. and Shameem, U. (2014) Green Synthesis and Characterization of Silver Nanoparticles Using *Boerhaavia diffusa* Plant Extract and Their Antibacterial Activity. *Industrial Crops and Products*, **52**, 562-566. <http://dx.doi.org/10.1016/j.indcrop.2013.10.050>
- [32] Logeswari, P., Silambarasan, S. and Abraham, J. (2013) Ecofriendly Synthesis of Silver Nanoparticles from Commercially Available Plant Powders and Their Antibacterial Properties. *Scientia Iranica*, **20**, 1049-1054.
- [33] Lu, R., Yang, D., Cui, D., Wang, Z. and Guo, L. (2012) Egg White-Mediated Green Synthesis of Silver Nanoparticles with Excellent Biocompatibility and Enhanced Radiation Effects on Cancer Cells. *International Journal of Nanomedicine*, **7**, 2101-2107. <http://dx.doi.org/10.2147/IJN.S29762>
- [34] Tripathi, A., Chandrasekaran, N., Raichur, A.M. and Mukherjee, A. (2009) Antibacterial Applications of Silver Nanoparticles Synthesized by Aqueous Extract of *Azadirachta indica* (Neem) Leaves. *Journal of Biomedical Nanotechnology*, **5**, 93-98.