

 Open access • Journal Article • DOI:10.1103/PHYSREVB.25.2920

Magneto-Hall and Magnetoresistance Coefficients in Semiconductors with Mixed Conductivity — [Source link](#)

David C. Look

Institutions: Wright State University

Published on: 15 Feb 1982 - Physical Review B

Topics: Magnetoresistance and Magneto

Related papers:

- [Review of Magnetoresistance and Hall Effect in Metals and Semiconductors](#)
- [Calculation of kinetic coefficients for some organic semiconductors: Part II. Magnetoresistance and Hall constant](#)
- [The Hall Coefficient of Semiconductors](#)
- [Hall and magnetoresistance factors of a Bi_{0.88}Sb_{0.12} single crystal doped with Te](#)
- [Dynamics of simultaneous measurements of hall and magnetoresistance effects in liquid metals and semiconductors](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/magneto-hall-and-magnetoresistance-coefficients-in-1aocdm52p1>

2-1-1982

Magneto-Hall and Magnetoresistance Coefficients in Semiconductors with Mixed Conductivity

David C. Look

Wright State University - Main Campus, david.look@wright.edu

Follow this and additional works at: <https://corescholar.libraries.wright.edu/physics>



Part of the [Physics Commons](#)

Repository Citation

Look, D. C. (1982). Magneto-Hall and Magnetoresistance Coefficients in Semiconductors with Mixed Conductivity. *Physical Review B*, 25 (4), 2920-2922.

<https://corescholar.libraries.wright.edu/physics/187>

This Article is brought to you for free and open access by the Physics at CORE Scholar. It has been accepted for inclusion in Physics Faculty Publications by an authorized administrator of CORE Scholar. For more information, please contact library-corescholar@wright.edu.

Magneto-Hall and magnetoresistance coefficients in semiconductors with mixed conductivity

D. C. Look

University Research Center, Wright State University, Dayton, Ohio 45435

(Received 1 September 1981; revised manuscript received 2 November 1981)

Magneto-Hall and magnetoresistance formulas, correct to order B^2 , are derived for the case in which both single-carrier and mixed-carrier effects are important. Also, a new magneto-Hall coefficient is presented: $\beta = \langle \tau^4 \rangle \langle \tau \rangle^2 / \langle \tau^2 \rangle^3 - 1$. Values of β for various scattering mechanisms are calculated and compared with experiment.

The electron and hole currents in an isotropic semiconductor with spherical equal-energy surfaces can be written as¹

$$j_{nx} = \bar{\sigma}_{1n} E_x - \bar{\sigma}_{2n} E_y, \tag{1a}$$

$$j_{ny} = \bar{\sigma}_{2n} E_x + \bar{\sigma}_{1n} E_y, \tag{1b}$$

$$j_{px} = \bar{\sigma}_{1p} E_x + \bar{\sigma}_{2p} E_y, \tag{1c}$$

$$j_{py} = -\bar{\sigma}_{2p} E_x + \bar{\sigma}_{1p} E_y, \tag{1d}$$

where the magnetic field \vec{B} is in the z direction and

$$\bar{\sigma}_{1n} = \frac{ne^2}{m_n^*} \left\langle \frac{\tau_n}{1 + \omega_{cn}^2 \tau_n^2} \right\rangle, \tag{2a}$$

$$\bar{\sigma}_{2n} = \frac{ne^2}{m_n^*} \left\langle \frac{\omega_{cn} \tau_n^2}{1 + \omega_{cn}^2 \tau_n^2} \right\rangle. \tag{2b}$$

Similar equations for $\bar{\sigma}_{1p}$ and $\bar{\sigma}_{2p}$ follow by letting $n \rightarrow p$. Here $\omega_{cn} = eB/m_n^*$, all other symbols have their usual meanings, and the angular brackets denote averages over energy.

Consider first current in a single band, for example, the conduction band ($n \gg p$). Then, in accordance with the boundary condition $j_{ny} = 0$, we get

$$\sigma_n \equiv \frac{j_{nx}}{E_x} = \frac{\bar{\sigma}_{1n}^2 + \bar{\sigma}_{2n}^2}{\bar{\sigma}_{1n}} \tag{3}$$

and

$$R_n \equiv \frac{E_y}{j_{nx} B} = -\frac{1}{B} \frac{\bar{\sigma}_{2n}}{\bar{\sigma}_{1n}^2 + \bar{\sigma}_{2n}^2}, \tag{4}$$

where R_n is the Hall coefficient. To order $\omega_{cn}^2 \tau_n^2$ it can be shown¹ that Eq. (3) yields

$$\frac{\sigma_{n0} - \sigma_n}{\sigma_{n0}} = -\frac{\Delta\sigma_n}{\sigma_{n0}} \simeq \frac{\Delta\rho_n}{\rho_{n0}} = \xi_n R_{n0}^2 \sigma_{n0}^2 B^2, \tag{5}$$

where the subscript zero denotes measurement at zero magnetic field, $R_{n0} = \langle \tau^2 \rangle / \langle \tau \rangle^2 ne$, and

$$\xi_n = \frac{\langle \tau_n^3 \rangle \langle \tau_n \rangle}{\langle \tau_n^2 \rangle^2} - 1. \tag{6}$$

Here

$$\langle \tau_n^q \rangle = \frac{\int_0^\infty \tau_n^q \epsilon^{3/2} e^{-\epsilon/kT} d\epsilon}{\int_0^\infty \epsilon^{3/2} e^{-\epsilon/kT} d\epsilon} \tag{7}$$

in the Boltzmann approximation.

Equation (5) is a well-known result. However, it has evidently also been commonly accepted that, to the same order of approximation ($\omega_{cn}^2 \tau_n^2$), R_n is independent of magnetic field.² While this is true, strictly speaking, it is easily seen from Eq. (4) that a term of order $\omega_{cn}^3 \tau_n^3$ (i.e., $\sim B^3$) in $\bar{\sigma}_{2n} / (\bar{\sigma}_{1n}^2 + \bar{\sigma}_{2n}^2)$ will fall to order B^2 in R_n because of the B term in the denominator of Eq. (4). Thus, if we insert Eqs. 2(a) and 2(b) into Eq. (4), and carry out the averages to order $\omega_{cn}^3 \tau_n^3$, the result is

$$\frac{R_{n0} - R_n}{R_{n0}} = \frac{-\Delta R_n}{R_{n0}} = (\beta_n - 2\xi_n) R_{n0}^2 \sigma_{n0}^2 B^2, \tag{8}$$

where

$$\beta_n = \frac{\langle \tau_n^4 \rangle \langle \tau_n \rangle^2}{\langle \tau_n^2 \rangle^3} - 1. \tag{9}$$

Some typical values of ξ_n , β_n , and $r_n \equiv \langle \tau_n^2 \rangle / \langle \tau_n \rangle^2$ are shown in Table I. Here the usual

TABLE I. Theoretical values of r_n , ξ_n , and β_n for several scattering mechanisms ($\tau_n = a_n \epsilon^{-s}$), and experimental values for an O-doped GaAs crystal.

Type of scattering	s	r_n	ξ_n	β_n	$\beta_n - 2\xi_n$
Acoustic deformation potential	$\frac{1}{2}$	1.18	0.273	1.546	1.00
Acoustic piezoelectric potential	$-\frac{1}{2}$	1.10	0.0865	0.268	0.0950
Ionized impurity	$-\frac{3}{2}$	1.93	0.577	2.52	1.37
Experimental (Fig. 1)			0.79	1.94	0.36

power-law energy dependence for τ_n is assumed; i.e., $\tau_n = a_n \epsilon^{-s}$.

We now examine the case for mixed conductivity. Here¹

$$j_x = j_{nx} + j_{px} = (\bar{\sigma}_{1n} + \bar{\sigma}_{1p})E_x - (\bar{\sigma}_{2n} - \bar{\sigma}_{2p})E_y, \quad (10a)$$

$$j_y = j_{ny} + j_{py} = (\bar{\sigma}_{2n} - \bar{\sigma}_{2p})E_x + (\bar{\sigma}_{1n} + \bar{\sigma}_{1p})E_y. \quad (10b)$$

Again by setting $j_y = 0$ we get

$$\sigma \equiv \frac{j_x}{E_x} = \frac{(\bar{\sigma}_{1n} + \bar{\sigma}_{1p})^2 + (\bar{\sigma}_{2n} - \bar{\sigma}_{2p})^2}{(\bar{\sigma}_{1n} + \bar{\sigma}_{1p})} \quad (11)$$

and

$$R \equiv \frac{E_y}{j_x B} = -\frac{1}{B} \frac{\bar{\sigma}_{2n} - \bar{\sigma}_{2p}}{(\bar{\sigma}_{1n} + \bar{\sigma}_{1p})^2 + (\bar{\sigma}_{2n} - \bar{\sigma}_{2p})^2} \quad (12)$$

For τ_n, τ_p independent of energy, well-known equations can be derived^{2,3} which are valid for arbitrary field strength, as long as $kT \gg h\omega_c$. When τ_n and τ_p are energy dependent, however, we must again restrict ourselves to solving Eqs. (11) and (12) only to order $\omega_c^2 \tau^2$. The results are

$$-\frac{\Delta\sigma}{\sigma_0} \approx \frac{\Delta\rho}{\rho_0} = \left[\frac{\sigma_n \sigma_p (R_n \sigma_n - R_p \sigma_p)^2}{(\sigma_n + \sigma_p)^2} + \frac{\xi_n R_n^2 \sigma_n^3 + \xi_p R_p^2 \sigma_p^3}{(\sigma_n + \sigma_p)} \right]_0 B^2$$

$$= \left[\frac{c(ab+1)^2}{\alpha^2 b(1+bc)^2} + \frac{\xi_n bc}{1+bc} + \frac{\xi_p}{\alpha^2 b^2(1+bc)} \right]_0 r_{n0}^2 \mu_n^2 B^2, \quad (13)$$

$$-\frac{\Delta R}{R_0} = \left[\frac{\sigma_n^2 \sigma_p^2 (R_n + R_p)(R_n \sigma_n - R_p \sigma_p)^2}{(\sigma_n + \sigma_p)^2 (R_n \sigma_n^2 + R_p \sigma_p^2)} + \frac{\beta_n R_n^3 \sigma_n^4 + \beta_p R_p^3 \sigma_p^4}{R_n \sigma_n^2 + R_p \sigma_p^2} - \frac{(2\xi_n R_n^2 \sigma_n^3 + 2\xi_p R_p^2 \sigma_p^3)}{\sigma_n + \sigma_p} \right]_0 B^2$$

$$= \left[\frac{c(1-\alpha c)(1+ab)^2}{\alpha^2(1+bc)^2(ab^2c-1)} + \frac{\beta_n \alpha b^2 c}{(ab^2c-1)} - \frac{\beta_p}{\alpha^2 b^2(ab^2c-1)} - \frac{2\xi_n bc}{(1+bc)} - \frac{2\xi_p}{\alpha^2 b^2(1+bc)} \right]_0 r_{n0}^2 \mu_n^2 B^2, \quad (14)$$

where $c = n/p$, $b = \mu_n/\mu_p$, $\alpha = r_n/r_p$, $\sigma_n = en\mu_n$, $\sigma_p = ep\mu_p$, $R_n = -r_n/ne$, and $R_p = r_p/pe$. The subscript "0" on the large parentheses denotes that all quantities inside are to be evaluated at $B=0$. The first term in each of Eqs. (13) and (14) is clearly due to mixed-carrier effects alone, while the other terms involve single-carrier contributions.

Some data on a semi-insulating, O-doped GaAs crystal are presented in Fig. 1. For this sample $\rho_0 = 4.5 \times 10^7 \Omega \text{ cm}$, $n_H \equiv 1/R_0 e = 3.2 \times 10^7 \text{ cm}^{-3}$, and $R_0/\rho_0 = 4.3 \times 10^3 \text{ cm}^2/V \text{ sec}$. Two-carrier effects are not expected to be important since bc , $b^2c \gg 1$. Thus, Eqs. (5) and (8) should apply. Rather than plot $\Delta\rho/\rho_0$ and $-\Delta R/R_0$ vs B^2 , we

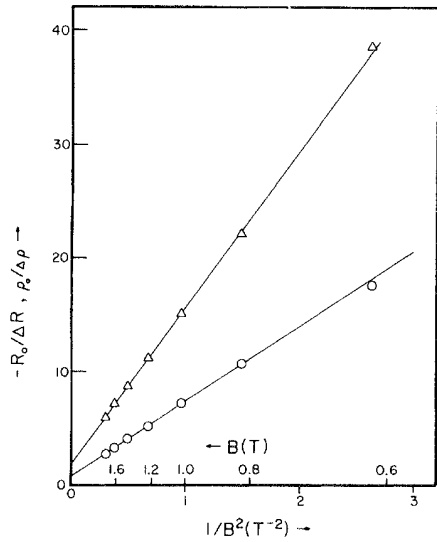


FIG. 1. Plots of $\rho_0/\Delta\rho$ (circles) and $-R_0/\Delta R$ (triangles) vs $1/B^2$ for an O-doped, semi-insulating GaAs crystal at 296 K.

have plotted $\rho_0/\Delta\rho$ and $-R_0/\Delta R$ vs $1/B^2$ because the curves are then more linear. From such plots it is seen that the data seem to obey the relationships

$$\frac{\rho_0}{\Delta\rho} = A_p + \frac{C_p}{B^2}, \quad (15)$$

$$-\frac{R_0}{\Delta R} = A_R + \frac{C_R}{B^2}, \quad (16)$$

over the magnetic field range 6–18 kG. Here we would identify $C_p^{-1} = \xi_n R_{n0}^2 \sigma_{n0}^2$ and $C_R^{-1} = (\beta_n - 2\xi_n) R_{n0}^2 \sigma_{n0}^2$. In fact, the slopes of the curves in Fig. 1 are the same as the initial slopes of $\Delta\rho/\rho_0$ and $-\Delta R/R_0$ vs B^2 plots, respectively, as they should be. Although it is not surprising that finite intercepts (A_p and A_R) exist at $1/B^2=0$, the functional form represented by Eqs. (15) and (16) would not be expected to hold as this value were approached, i.e., as $B \rightarrow \infty$. That is, we cannot obviously identify A_p and A_R with the expected high-field values of $\rho_0/\Delta\rho$ and $-R_0/\Delta R$, respectively. Interestingly enough, the forms of Eqs. (15)

and (16) hold exactly, for arbitrary B (in the non-quantum limit, $kT \gg \hbar\omega_c$), if single-carrier effects are totally absent.³ However, an analysis from this (mixed-carrier) point of view³ gives values of μ_p and n_i (intrinsic concentration) which are much too high. In fact, GaAs samples with $\rho_0 \leq 5 \times 10^8 \Omega \text{ cm}$ are not expected to have strong mixed-carrier effects.⁴ Thus, it appears that single-carrier (electron) effects dominate in this sample and that we can therefore obtain ξ_n and $\beta_n - 2\xi_n$ from the slopes of the curves in Fig. 1.

The values obtained are listed in Table I. Although β_n appears reasonable with respect to the calculated “pure-scattering” values, ξ_n seems to be too high. It would be interesting to carry out a proper “mixed-scattering” energy averaging [Eq. (7)] of the various quantities in Eqs. (6) and (9). It would also be interesting to know how such factors as inhomogeneous compensation would affect the results.

For completeness, we also calculate the high-field ($kT \gg \hbar\omega_c \gg \hbar/\tau$) limits of Eqs. (11) and (12), respectively:

$$\sigma_\infty = \frac{e\mu_n\mu_p(n-p)^2}{n\mu_p\langle\tau_n\rangle\langle\tau_n^{-1}\rangle + p\mu_n\langle\tau_p\rangle\langle\tau_p^{-1}\rangle}, \quad (17)$$

$$R = \frac{1}{e(p-n)}. \quad (18)$$

The low-field limits, on the other hand, are

$$\sigma_0 = e(n\mu_n + p\mu_p), \quad (19)$$

$$R_0 = \frac{r_p p \mu_p^2 - r_n n \mu_n^2}{e(n\mu_n + p\mu_p)^2}, \quad (20)$$

where r_n and r_p were defined previously. It is tempting to associate the intercept A_p with $\sigma_0/(\sigma_0 - \sigma_\infty)$, and A_R with $R_0/(R_0 - R_\infty)$, but it must be remembered that Eqs. (15) and (16) do not hold theoretically over the entire range of B .

We would like to thank R. S. Allgaier for a helpful discussion.

¹See, for example, R. H. Bube, *Electronic Properties of Crystalline Solids* (Academic, New York, 1974), Chap. 10.

²See, for example, E. H. Putley, *The Hall Effect and Semiconductor Physics* (Dover, New York, 1968), p.

96.

³D. C. Look, *J. Phys. Chem. Solids* **36**, 1311 (1975).

⁴D. C. Look, in *Semi-Insulating III-V Materials*, edited by G. J. Rees (Shiva, Orpington, 1980), p. 183.