

 Open access • Journal Article • DOI:10.1063/1.1695203

Metal-nanoparticle single-electron transistors fabricated using electromigration

— [Source link](#) 

[Kirill I. Bolotin](#), [Ferdinand Kuemmeth](#), [Abhay Pasupathy](#), [Daniel C. Ralph](#)

Published on: 13 Apr 2004 - [Applied Physics Letters](#) (American Institute of Physics)

Topics: [Electromigration](#), [Nanoparticle](#) and [Electrode](#)

Related papers:

- [Fabrication of metallic electrodes with nanometer separation by electromigration](#)
- [Coulomb blockade and the Kondo effect in single-atom transistors](#)
- [Controlled fabrication of nanogaps in ambient environment for molecular electronics](#)
- [Kondo resonance in a single-molecule transistor](#)
- [Single-electron devices and their applications](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/metal-nanoparticle-single-electron-transistors-fabricated-1zqxpeytjg>



Metal-nanoparticle single-electron transistors fabricated using electromigration

Bolotin, K I; Kuemmeth, Ferdinand; Pasupathy, A N; Ralph, D C

Published in:
Applied Physics Letters

DOI:
[doi: 10.1063/1.1695203](https://doi.org/10.1063/1.1695203)

Publication date:
2004

Document version
Publisher's PDF, also known as Version of record

Citation for published version (APA):
Bolotin, K. I., Kuemmeth, F., Pasupathy, A. N., & Ralph, D. C. (2004). Metal-nanoparticle single-electron transistors fabricated using electromigration. *Applied Physics Letters*, 84(16), 3154-3156. <https://doi.org/doi:10.1063/1.1695203>

Metal-nanoparticle single-electron transistors fabricated using electromigration

K. I. Bolotin, F. Kuemmeth, A. N. Pasupathy, and D. C. Ralph

Citation: *Appl. Phys. Lett.* **84**, 3154 (2004); doi: 10.1063/1.1695203

View online: <http://dx.doi.org/10.1063/1.1695203>

View Table of Contents: <http://apl.aip.org/resource/1/APPLAB/v84/i16>

Published by the [American Institute of Physics](http://www.aip.org/).

Related Articles

A programmable ferroelectric single electron transistor

Appl. Phys. Lett. **102**, 053505 (2013)

Universal scaling of resistivity in bilayer graphene

Appl. Phys. Lett. **101**, 223111 (2012)

Voltage-sustained self-oscillation of a nano-mechanical electron shuttle

Appl. Phys. Lett. **101**, 213111 (2012)

One electron-based smallest flexible logic cell

Appl. Phys. Lett. **101**, 183101 (2012)

Charge sensing in a Si/SiGe quantum dot with a radio frequency superconducting single-electron transistor

Appl. Phys. Lett. **101**, 142103 (2012)

Additional information on *Appl. Phys. Lett.*

Journal Homepage: <http://apl.aip.org/>

Journal Information: http://apl.aip.org/about/about_the_journal

Top downloads: http://apl.aip.org/features/most_downloaded

Information for Authors: <http://apl.aip.org/authors>

ADVERTISEMENT

AIP | Applied Physics
Letters

SURFACES AND INTERFACES
Focusing on physical, chemical, biological, structural, optical, magnetic and electrical properties of surfaces and interfaces, and more...

ENERGY CONVERSION AND STORAGE
Focusing on all aspects of static and dynamic energy conversion, energy storage, photovoltaics, solar fuels, batteries, capacitors, thermoelectrics, and more...

EXPLORE WHAT'S NEW IN APL

SUBMIT YOUR PAPER NOW!

Metal-nanoparticle single-electron transistors fabricated using electromigration

K. I. Bolotin, F. Kuemmeth, A. N. Pasupathy, and D. C. Ralph^{a)}

Laboratory of Atomic and Solid State Physics, Cornell University, Ithaca, New York 14853

(Received 14 October 2003; accepted 9 February 2004)

We have fabricated single-electron transistors from individual metal nanoparticles using a geometry that provides improved coupling between the particle and the gate electrode. This is accomplished by incorporating a nanoparticle into a gap created between two electrodes using electromigration, all on top of an oxidized aluminum gate. We achieve sufficient gate coupling to access more than ten charge states of individual gold nanoparticles (5–15 nm in diameter). The devices are sufficiently stable to permit spectroscopic studies of the electron-in-a-box level spectra within the nanoparticle as its charge state is varied. © 2004 American Institute of Physics. [DOI: 10.1063/1.1695203]

Single-electron transistors (SETs) made from metals are important for their use as electrometers, and also because they enable fundamental studies of charge transport in metals.^{1–8} For many applications, it is desirable to minimize the size of the central metal island within the SET, so as to increase the charging energy, optimize the electrometer sensitivity or spatial resolution, or raise the maximum operating temperature. If the island is made smaller than about 10 nm diameter, it is also possible to use such SETs to probe individual “electron-in-a-box” quantum states within the metal nanoparticle.⁸ SETs with metal islands smaller than 10 nm have been fabricated previously,^{9,10} but the gate capacitances were so small (10^{-19} F in Ref. 9 and $<10^{-20}$ F in Ref. 10) that it was difficult to adjust the charge on the island by more than one electron. Here we describe a technique to make metal-nanoparticle SETs with gate capacitances of order 10^{-18} F, sufficient to tune the number of electrons in a nanoparticle by more than ten. We use these devices to study the evolution of the electron-in-a-box level spectrum in gold nanoparticles as the electron number is changed one by one.

Our fabrication technique builds upon work in which electrical contact was made to single nanoparticles without a gate electrode^{10–13} and to networks of particles in the presence of a gate.¹⁴ We start by using photolithography to define a 16-nm-thick Al gate electrode with 2 nm of Ti as a sticking layer, on top of an oxidized Si substrate. The gate electrode is deposited with the substrate at liquid nitrogen temperature. The Al is warmed overnight to room temperature while in 50 mTorr of O₂ and then exposed to air.¹⁵ Next we use electron-beam lithography and liftoff to fabricate Au wires with a thickness of 16 nm and a minimum width of 100 nm on top of the gate [Fig. 1(a)]. After cleaning the Au wires in oxygen plasma, we submerge the chip in liquid helium and break the wires using electromigration;¹⁶ a source-drain bias is slowly ramped up until the wire breaks and the conductance drops suddenly.¹⁷ In most cases this happens at a bias of ~ 1 V and results in a gap about 5–10 nm wide after the sample is warmed to room temperature [Fig. 1(b)]. A similar process of electromigration has been used recently to make single-

molecule transistors.^{18,19} Then we create nanoparticles, formed by self-assembly, by evaporating Au on top of the broken lines and into the gap with the substrate at room temperature. For most samples we evaporate 20 Å of gold at 0.6 Å/s, which produces particle diameters of 5–15 nm as measured with a scanning electron microscope (SEM) [Fig. 1(b)]. When measured immediately after the evaporation, approximately 25% of the junctions show a drop of resistance into the MΩ range, indicating that a nanoparticle may be bridging the gap. This procedure has the virtue of producing nanoparticles separated from the gate electrode by only 2–3 nm of aluminum oxide, giving excellent coupling between the particle and the gate. Finally the devices are protected by evaporating 100 nm of aluminum oxide prior to air exposure.

We cool the finished devices to 4.2 K and measure their current–voltage (I – V) curves as a function of gate voltage (V_G) [see Fig. 1(c) for circuit conventions]. More than 50% of the devices that show a decrease in resistance during the nanoparticle deposition step exhibit Coulomb-blockade characteristics [Figs. 2(a) and 2(b)]. Fits to the orthodox theory of Coulomb blockade²⁰ yield good agreement [Fig. 2(a)]. The variation of dI/dV as a function of V_G and V is shown in Fig. 2(c), for a range of V_G large enough to span several “Coulomb diamonds.” The presence of only one positive

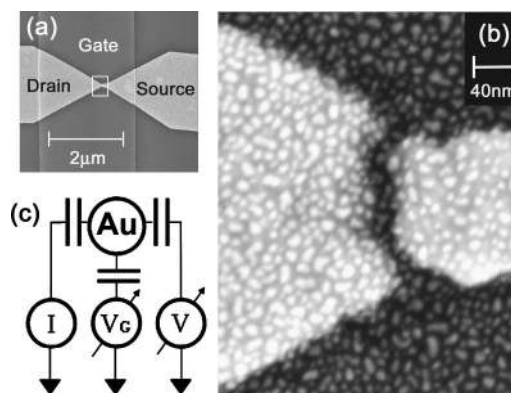


FIG. 1. (a) Top-view SEM image of the device geometry, with gold source and drain electrodes on top of an oxidized aluminum gate. (b) Expanded view of the region outlined with a white rectangle in (a). A 10 nm gap made by electromigration is visible, along with deposited gold nanoparticles. (c) Circuit schematic for the Au-nanoparticle SET.

^{a)}Electronic mail: ralph@ccmr.cornell.edu

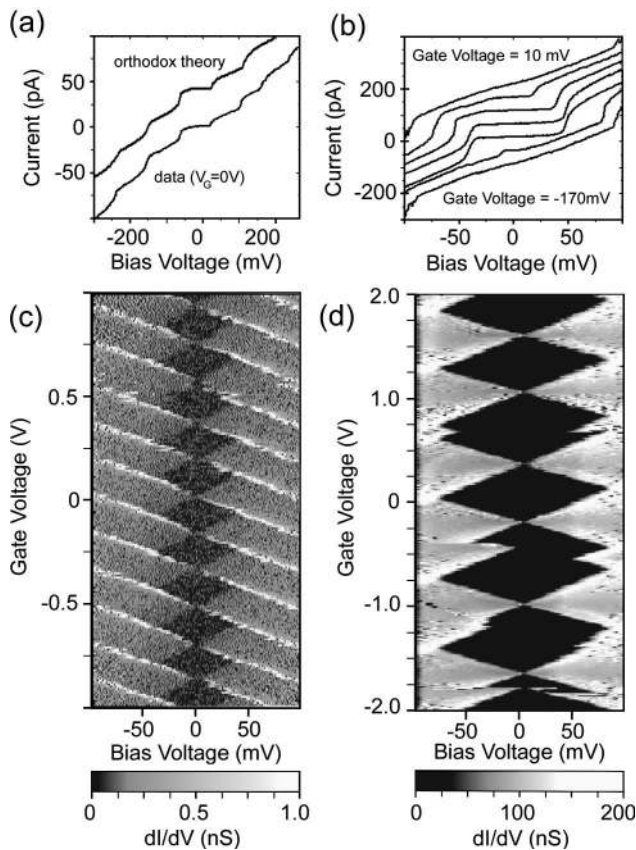


FIG. 2. (a) Coulomb staircase I - V curve for a gold nanoparticle SET (device 1) at 4.2 K, along with an orthodox model fit (offset for clarity). (b) I - V curves for device 1 at 4.2 K, for equally spaced values of V_G . (c) Gray-scale plot of dI/dV as a function of V_G and V for device 1 at 4.2 K. Eleven degeneracy points separating twelve different charge states are visible within a 2 V range of V_G . (d) Gray-scale plot of dI/dV as a function of V_G and V for device 2 at 4.2 K, showing “Coulomb diamonds” as well as several abrupt changes in the background charge of the SET island as V_G is swept.

and one negative slope for the tunneling thresholds versus V_G indicates that transport is indeed occurring through a single nanoparticle.²¹ The gate capacitance C_G is determined from the spacing in V_G between the degeneracy points where dI/dV is nonzero at $V=0$. For device 1 [Figs. 2(a)–2(c)], the spacing between neighboring degeneracy points is 180 mV, so $C_G=e/(180 \text{ mV})=0.89 \text{ aF}$ ($\pm 5\%$). This is an order of magnitude greater than gate capacitances achieved previously in metal nanoparticle transistors.⁹ The ratios C_D/C_G and C_S/C_G for the drain and source capacitances are then determined from the slopes of the tunneling thresholds versus V_G ,²² yielding for device 1 $C_D=2.4 \text{ aF}$ and $C_S=1.3 \text{ aF}$ ($\pm 10\%$). Figure 2(c) demonstrates that 12 different charge states within this nanoparticle can be accessed by varying V_G within the range $\pm 1 \text{ V}$. We should note that the scan in Fig. 2(c) is somewhat atypical in that there are very few discontinuities in the gate-voltage dependence, corresponding to sudden rearrangements in the background charge near the particle. The diamond plot in Fig. 2(d), from device 2, is more typical.

The yield given by our fabrication process is that 15%–20% of all devices exhibit gate-dependent Coulomb blockade. The gate capacitances are typically 0.3–2.0 aF and the source and drain capacitances are 1–10 times larger, yielding charging energies between 15 and 50 meV. As a control ex-

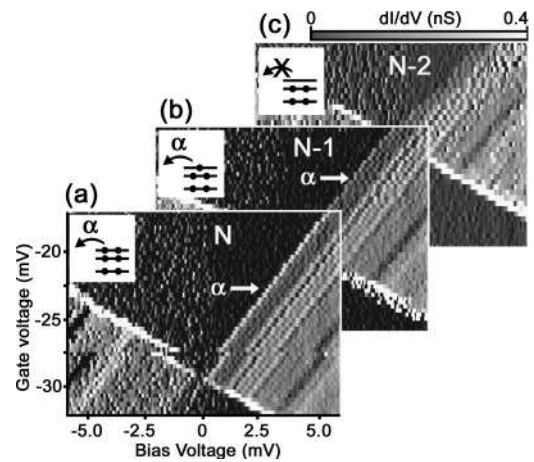


FIG. 3. Gray-scale plots of dI/dV as a function of V_G and V , displaying the discrete electron-in-a-box level spectra within a gold nanoparticle (device 3), measured with an electron temperature less than 150 mK and zero magnetic field. Panels (a), (b), and (c) represent spectra for different gate numbers of electrons in the same nanoparticle. Panel (b) covers the gate voltage range from -95 to -110 mV and (c) the range from -180 to -195 mV . Insets: Energy-level diagrams illustrating the tunneling transitions that contribute to line α for different numbers of electrons on the particle.

periment, we took 24 devices through the full fabrication process except for the step in which the nanoparticles are deposited. These samples never showed Coulomb-blockade characteristics.

In prior work, tunnel junctions containing individual metal nanoparticles have been used to measure the “electron-in-a-box” states inside the nanoparticle, and these experiments have been a rich source of information about electronic interactions within metals.^{8,9} Having a more effective gate would contribute greatly to these types of studies, by enabling investigations of how the spectra change as electrons are added to a nanoparticle, and also by giving increased control over nonequilibrium excitations.²² Next we demonstrate that our SETs are sufficiently stable to allow measurements of the electron-in-a-box spectra, and we present initial studies of how these spectra depend on the electron number.

In order to resolve electron-in-a-box quantum states, we cool samples in a dilution refrigerator with filtered electrical lines so that the electron temperature is less than 150 mK. In Fig. 3 we examine a device with parameters $C_G=2.0 \text{ aF}$, $C_S=1.9 \text{ aF}$, and $C_D=2.2 \text{ aF}$. Low-temperature plots of dI/dV versus V_G and V reveal a fine structure of lines beyond the tunneling threshold that correspond to tunneling via excited quantum states within the nanoparticle. Figure 3 shows three sets of spectra. In panel (a), the lines running parallel to the line labeled α correspond to transitions in which an electron tunnels off the nanoparticle to decrease the total number of electrons from some value N to $N-1$. Panel (b) displays a more negative range of V_G where transitions from $N-1$ electrons to $N-2$ are visible. Finally, the levels in panel (c) correspond to $N-2$ to $N-3$ transitions. The most striking aspect of these three plots is that the pattern of excited states is extremely similar. The only significant difference can be seen in the line labeled α at the threshold for tunneling. In panel (a) line α is strong, in panel (b) it is present but its conductance is decreased by approximately 45% and in (c) the line is absent. This behavior can be un-

derstood in a simple way by assuming that the energy levels in the nanoparticle are spin-degenerate, and that N corresponds to an even number of electrons. In this case, line α in panel (a) corresponds to transitions in which either one of the two (spin-degenerate) electrons in the highest occupied energy level for N electrons tunnels off of the particle into the source. For $N-1$ electrons in panel (b), one of these two electrons is already gone, so line α corresponds to having just the one remaining electron in that same energy level tunnel off of the particle. Because the source-particle interface is the rate limiting barrier in this device, the tunneling rate is reduced by approximately a factor of 2. Finally, in panel (c), no electrons are left to tunnel out of the state corresponding to line α , so the line is no longer present.

The strong similarities that we observe in the excited state spectra for different numbers of electrons on a gold nanoparticle are in striking contrast to analogous studies of GaAs quantum dots.²³ In GaAs dots, spin degeneracy is not generally observed and excited-state levels are shifted relative to one another when the electron number is changed. These spectral rearrangements in GaAs have been explained as due to exchange interactions between the added electron and quantum-dot states with different total spins. The similarity of the excited-state spectra that we observe for different numbers of electrons in gold is therefore evidence that exchange interactions are sufficiently weak that the energy levels are filled as in a noninteracting model, with each energy level spin-degenerate and with the energy-level spacings not sensitive to the electron number. This simple outcome is highly nontrivial for an interacting-electron system, but it is consistent with expectations for the strength of exchange interactions in gold.²⁴

In summary, we have fabricated single-electron transistors by depositing metal nanoparticles within break junctions made using electromigration. This method provides strong coupling between the nanoparticle and the gate electrode, thereby enabling experiments in which the number of electrons on the particle is varied over a wide range. We have demonstrated that this device geometry permits detailed measurements of electron-in-a-box level spectra in metals as a function of the electron number.

The authors thank A. R. Champagne and J. E. Grose for helpful discussions. This work was funded by the NSF (DMR-0244713 and through use of the Cornell Nanoscale Facility/NNUN) and by the ARO (DAAD19-01-1-0541).

- ¹D. V. Averin and K. K. Likharev, *J. Low Temp. Phys.* **62**, 345 (1986).
- ²T. A. Fulton and G. J. Dolan, *Phys. Rev. Lett.* **59**, 109 (1987).
- ³P. Lafarge, H. Pothier, E. R. Williams, D. Esteve, C. Urbina, and M. H. Devoret, *Z. Phys. B: Condens. Matter* **85**, 327 (1991).
- ⁴M. J. Yoo, T. A. Fulton, H. F. Hess, R. L. Willett, L. N. Dunkleberger, R. J. Chichester, L. N. Pfeiffer, and K. W. West, *Science* **276**, 579 (1997).
- ⁵R. J. Schoelkopf, P. Wahlgren, A. A. Kozhevnikov, P. Delsing, and D. E. Prober, *Science* **280**, 1238 (1998).
- ⁶M. H. Devoret and R. J. Schoelkopf *Nature (London)* **406**, 1039 (2000).
- ⁷R. G. Knobel and A. N. Cleland, *Nature (London)* **424**, 291 (2003).
- ⁸J. von Delft and D. C. Ralph, *Phys. Rep.* **345**, 61 (2001).
- ⁹D. C. Ralph, C. T. Black, and M. Tinkham, *Phys. Rev. Lett.* **78**, 4087 (1997).
- ¹⁰Y. A. Pashkin, Y. Nakamura, and J. S. Tsai, *Appl. Phys. Lett.* **76**, 2256 (2000).
- ¹¹D. Davidovic and M. Tinkham, *Appl. Phys. Lett.* **73**, 3959 (1998); *Phys. Rev. Lett.* **83**, 1644 (1999).
- ¹²S. I. Khondaker and Z. Yao, *Appl. Phys. Lett.* **81**, 4613 (2002).
- ¹³M. F. Lambert, M. F. Goffman, J. P. Bourgoin, and P. Hesto, *Nanotechnology* **14**, 772 (2003).
- ¹⁴S. E. Kubatkin, A. V. Danilov, A. L. Bogdanov, H. Olin, and T. Claeson, *Appl. Phys. Lett.* **73**, 3604 (1998); *J. Low Temp. Phys.* **118**, 307 (2000).
- ¹⁵A. Bachtold, P. Hadley, T. Nakanishi, and C. Dekker, *Science* **294**, 1317 (2001).
- ¹⁶H. Park, A. K. L. Lim, A. P. Alivisatos, J. Park, and P. L. McEuen, *Appl. Phys. Lett.* **75**, 301 (1999).
- ¹⁷As an alternative, we have also tried breaking the wires at room temperature inside the evaporator (instead of at liquid helium temperature) but this generally produced gaps too wide to make SETs with good yield.
- ¹⁸J. Park, A. N. Pasupathy, J. I. Goldsmith, C. Chang, Y. Yaish, J. R. Petta, M. Rinkoski, J. P. Sethna, H. D. Abruña, P. L. McEuen, and D. C. Ralph, *Nature (London)* **417**, 722 (2002).
- ¹⁹W. Liang, M. P. Shores, M. Bockrath, J. R. Long, and H. Park, *Nature (London)* **417**, 725 (2002).
- ²⁰D. V. Averin and K. K. Likharev, in *Mesoscopic Phenomena in Solids*, edited by B. L. Altshuler, P. A. Lee, and R. A. Webb (Elsevier, New York 1991), p. 173.
- ²¹A. V. Danilov, D. S. Golubev, and S. E. Kubatkin, *Phys. Rev. B* **65**, 125312 (2002).
- ²²M. M. Deshmukh, E. Bonet, A. N. Pasupathy, and D. C. Ralph, *Phys. Rev. B* **65**, 073301 (2002).
- ²³D. R. Stewart, D. Sprinzak, C. M. Marcus, C. I. Duruöz, and J. S. Harris, Jr., *Science* **278**, 1784 (1997).
- ²⁴D. A. Gorokhov and P. W. Brouwer, *Phys. Rev. Lett.* **91**, 186602 (2003).