

ORIGINAL RESEARCH

Open Access

# Methanolysis optimization of sesame (*Sesamum indicum*) oil to biodiesel and fuel quality characterization

Eriola Betiku<sup>1\*</sup> and Tunde Folorunsho Adepoju<sup>2</sup>

## Abstract

Statistical approach was employed to optimize biodiesel production from sesame oil in this work. Precisely, response surface methodology was applied, and the effects of four variables, viz. reaction temperature, catalyst amount, reaction time, and methanol/oil molar ratio, and their reciprocal interactions were determined. Central composite rotatable design was used to generate a total of 30 individual experiments, which were designed to study the effects of these variables during alkali-catalyzed methanolysis of sesame oil. A statistical model predicted the highest conversion yield of sesame biodiesel to be 99.71% at the following optimized variable conditions: reaction temperature of 63°C, catalyst amount of 1.04 wt.%, and methanol/oil molar ratio of 6.24, with a reaction time of 51.09 min. Using these variables under experimental condition in four independent replicates, an actual biodiesel yield of 98.36% was accomplished. The fuel properties of biodiesel produced were found to be within the ASTM D6751 and DIN EN 14214 biodiesel specifications.

**Keywords:** Biodiesel, Sesame oil, Methanolysis, Optimization, Response surface methodology

## Background

The need for alternative fuel, which can solve the problems of finite nature of fossil fuels and their environmental concerns, is imperative. About 98% of carbon emissions result from fossil fuel combustion [1]. The continued and increasing use of diesel derived from fossil oil intensifies air pollution and magnifies the global warming problem caused by CO<sub>2</sub> and other particulate matters [2]. Biodiesel, which is renewable in nature, non-toxic, and environmentally friendly with higher octane number than diesel, is the most promising candidate. It can be defined as the alkyl esters of long-chain fatty acids derived from renewable feedstock like vegetable oils or animal fats, obtained by transesterifying oil or fat with an alcohol [3].

Despite the food vs. fuel challenge facing the world, both edible and non-edible vegetable oil have been successfully used to produce biodiesel with superior qualities to diesel. These feedstocks include soybean oil [4], moringa oil [5], sunflower oil [6], rapeseed oil [7], palm

oil [8], jatropha oil [9], camelina oil [10], neem oil [11,12], karanja oil [13], and sesame oil [14]. The ideal vegetable oil for biodiesel must be readily available, its plant should be easy to cultivate, and its composition must include a high percentage of monounsaturated fatty acids (C16:1, C18:1), a low proportion of polyunsaturated acids (C18:2, C18:3) and a controlled amount of saturated fatty acids (C16:0, C18:0) [15].

Transesterification of oil or fat to produce a high yield of biodiesel is typically investigated by optimizing the following reaction variables: alcohol/oil molar ratio, catalyst concentration, reaction temperature, and reaction time involved in the process. Both the effects of the variables and their reciprocal interactions have been evaluated using response surface methodology (RSM). RSM is a useful statistical tool, which has been applied in research for optimizing various processes including pretreatment of the *Jatropha curcas* fruit hull for enzymatic hydrolysis [16], bioremediation of contaminated soil [17], and transesterification reaction of vegetable oils. Transesterification of *Moringa oleifera* oil to biodiesel was optimized via RSM by Rashid et al. [5], whereas Tiwari et al. [9] optimized biodiesel production from

\* Correspondence: ebetiku@oauife.edu.ng

<sup>1</sup>Biochemical Engineering Laboratory, Department of Chemical Engineering, Obafemi Awolowo University, Ile-Ife, Osun State 220005, Nigeria  
Full list of author information is available at the end of the article

**Table 1 Factors and their levels for composite central design**

Variable	Symbol	Coded factor levels				
		-2	-1	0	1	2
Reaction temperature (°C)	$X_1$	50	55	60	65	70
Catalyst amount (wt.%)	$X_2$	0.7	0.8	0.9	1.0	1.1
Reaction time (min)	$X_3$	40	45	50	55	60
Methanol/oil molar ratio	$X_4$	4	5	6	7	8


jatropha oil with high free fatty acids using RSM. Jeong et al. [18] optimized the transesterification process of animal fat ester, while Yuan et al. [7] used RSM for optimization of waste rapeseed oil with high FFA to biodiesel. Also, Zhang et al. [19] applied RSM for the

optimization of *Zanthoxylum bungeanum* seed oil transesterification to biodiesel using CaO as catalyst. Optimization of transesterification variables for biodiesel production from cottonseed oil using RSM has also been reported [20].

*Sesamum indicum*, commonly called beniseed in Africa but globally known as sesame, is a fast-growing crop whose oilseed can be utilized for biodiesel production through transesterification process. It is an important oilseed crop cultivated in many parts of the world. Its seed is composed of 50% to 52% oil, 17% to 19% protein, and 16% to 18% carbohydrate [21]. Fatty acid compositions of the oil are mostly oleic (32.7% to 53.9%), linoleic (39.3% to 59%), palmitic (8.3% to 10.9%), and stearic (3.4% to 6.0%) acids [22]. However, the fatty acid composition of this oil varies considerably among the

**Table 2 CCRD and experimental, predicted, and residual values for five-level four-factor response surface analysis**

Standard order	$X_1$ (°C)	$X_2$ (wt.%)	$X_3$ (min)	$X_4$	Experimental value % (w/w)	Predicted value % (w/w)	Residual values % (w/w)%
1	-1	-1	-1	-1	56.68	56.80	-0.12
2	1	-1	-1	-1	66.05	65.73	0.32
3	-1	1	-1	-1	79.06	79.08	-0.02
4	1	1	-1	-1	82.77	82.50	0.27
5	-1	-1	1	-1	63.86	64.05	-0.19
6	1	-1	1	-1	77.67	77.56	0.11
7	-1	1	1	-1	80.44	80.67	-0.23
8	1	1	1	-1	88.78	88.66	0.12
9	-1	-1	-1	1	83.55	83.57	-0.02
10	1	-1	-1	1	85.56	85.28	0.28
11	-1	1	-1	1	88.72	88.78	-0.06
12	1	1	-1	1	85.26	84.97	0.29
13	-1	-1	1	1	89.23	89.45	-0.22
14	1	-1	1	1	95.86	95.74	0.12
15	-1	1	1	1	88.78	89.00	-0.22
16	1	1	1	1	89.94	89.77	0.17
17	-2	0	0	0	77.75	77.14	0.61
18	2	0	0	0	86.10	86.86	-0.76
19	0	-2	0	0	65.13	65.19	-0.06
20	0	2	0	0	81.42	81.51	-0.09
21	0	0	-2	0	82.53	82.93	-0.40
22	0	0	2	0	95.22	94.97	0.25
23	0	0	0	-2	67.10	67.16	-0.06
24	0	0	0	2	94.95	95.04	-0.09
25	0	0	0	0	92.87	92.87	0.00
26	0	0	0	0	92.87	92.87	0.00
27	0	0	0	0	92.87	92.87	0.00
28	0	0	0	0	92.87	92.87	0.00
29	0	0	0	0	92.87	92.87	0.00
30	0	0	0	0	92.87	92.87	0.00

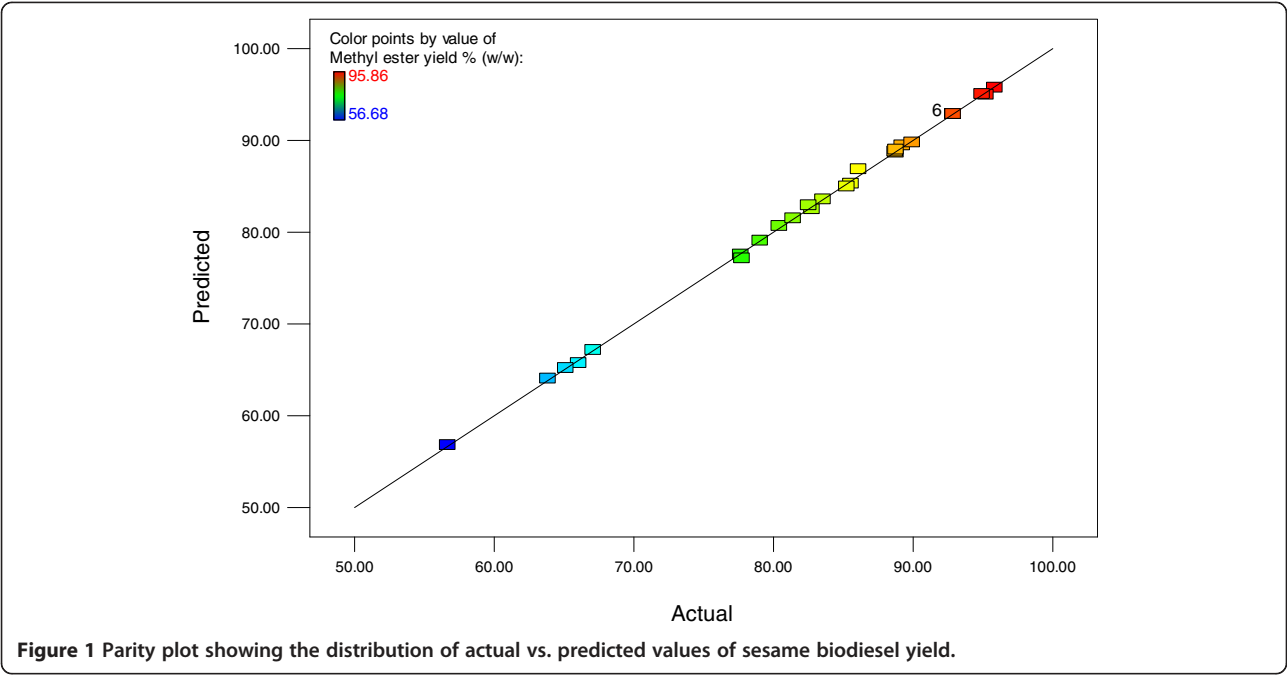

different varieties worldwide [22,23]. Sesame oil has emerged as a potential feedstock for biodiesel production. Although the transesterification of this seed oil from Turkey and Pakistan cultivars to biodiesel has been reported [14,24,25], the process has not yet been optimized using a statistical approach such as response surface methodology, and the maximum yield reported was 92% [24].

In this present study, an effort was made to optimize the process conditions for transesterification of sesame oil from a Nigeria cultivar to biodiesel. RSM with central composite rotatable design (CCRD) was applied, and the effect of four variables (reaction temperature, catalyst amount, reaction time, and methanol/oil molar ratio) at five levels and their reciprocal interactions were evaluated.

temperature of 70°C. The excess solvent in the oil was recovered by distillation.

**Experimental design of biodiesel production**

In this work, the central composite experimental design was employed to optimize the transesterification of sesame oil to biodiesel. A five-level-four-factor design was applied, which generated 30 experimental runs. These included 16 factorial points, 8 axial points, and 6 central points to provide information regarding the interior of the experimental region, making it possible to evaluate

Methods

Materials

*S. indicum* samples were collected from Lokoja, Nigeria. Chaffs were separated from the oilseeds by winnowing. The cleaned oilseeds were milled to powder by grinding with a plate machine. All chemicals and reagents used for this work were of analytical grades.

Extraction of sesame oil

Soxhlet apparatus and *n*-hexane as solvent were used for the oil extraction. Initially, the apparatus was charged with a known weight of the oilseed powder in a muslin cloth placed in a thimble of the apparatus. A round bottom flask containing a known volume of *n*-hexane was fixed to the end of the apparatus, and a condenser was tightly fixed at the bottom end of the extractor. The whole setup was heated up in a heating mantle at a

Table 3 Test of significance for every regression coefficient of CCRD

Source	Sum of squares	df	Mean square	F value	p value
$X_1$	141.17	1	141.17	1,192.78	<0.0001
$X_2$	399.11	1	399.11	3,364.87	<0.0001
$X_3$	217.74	1	217.74	1,835.80	<0.0001
$X_4$	1,166.08	1	1,166.08	9,831.27	<0.0001
$X_1X_2$	30.44	1	30.44	256.66	<0.0001
$X_1X_3$	20.95	1	20.95	176.66	<0.0001
$X_1X_4$	52.16	1	52.16	439.80	<0.0001
$X_2X_3$	32.06	1	32.06	270.33	<0.0001
$X_2X_4$	291.47	1	291.47	2,457.40	<0.0001
$X_3X_4$	1.87	1	1.87	15.77	0.0012
$X_1^2$	202.54	1	202.54	1,707.61	<0.0001
$X_2^2$	653.17	1	653.17	5,506.87	<0.0001
$X_3^2$	26.34	1	26.34	222.05	<0.0001
$X_4^2$	237.47	1	237.47	2,002.10	<0.0001

the curvature effect. Selected variables for the transesterification process from the sesame oil were reaction temperature ( $X_1$ ), catalyst amount ( $X_2$ ), reaction time ( $X_3$ ), and methanol/oil molar ratio ( $X_4$ ). The coded levels of the independent variables are given in Table 1. The experiments were randomized to minimize the effects of unexplained variability in the observed response due to extraneous factors.

#### Sesame biodiesel production procedure

The base-catalyzed reaction was carried out according to the work of Schinas et al. [26]. The transesterification reaction of sesame oil was carried out in a glass reactor (1-L capacity). The reactor was charged with a known weight of the oil sample, which was preheated to the desired temperature. A known weight of NaOH pellet (catalyst) was dissolved in a specific volume of methanol and was transferred into the preheated oil on the hot plate with a magnetic stirrer. The resulting mixture was transferred into a separating funnel for glycerol and methyl ester separation. The glycerol was allowed to separate by gravity for 24 h. Two phases separated clearly, the less dense methyl ester at the top and the denser phase of glycerol at the bottom. The glycerol was tapped off the bottom of the separating funnel, leaving behind methyl ester in the separating funnel. The methyl ester was washed with distilled water to remove residual catalyst, glycerol, methanol, and soap. The methyl ester was further dried over a heated  $\text{CaCl}_2$  powder. The final product was the sesame biodiesel, and the yield was calculated gravimetrically as described in Equation 1:

$$\text{Beniseed biodisel yield \% (w/w)} = \frac{\text{Weight of biodiesel produced}}{\text{Weight of Beniseed oil used}} \quad (1)$$

#### Statistical data analysis

Sesame biodiesel production data were analyzed statistically using response surface methodology, in order to fit the quadratic polynomial equation generated by the Design Expert software version 8.0.3.1 (Stat-Ease Inc., Minneapolis, MN, USA). To correlate the response variable to the independent variables, multiple regressions were used to fit the coefficient of the polynomial model of the response. The quality of the fit of the model was evaluated using a test of significance and analysis of variance (ANOVA). The fitted quadratic response model is described by

$$Y = b_0 + \sum_{i=1}^k b_i X_i + \sum_{i=1}^k b_{ii} X_i^2 + \sum_{i < j}^k b_{ij} X_i X_j + e, \quad (2)$$

where  $Y$  is the response variable (sesame biodiesel yield),  $b_0$  is the intercept value,  $b_i$  ( $i = 1, 2, \dots, k$ ) is the

**Table 4 ANOVA of regression equation**

Source	Sum of squares	df	Mean square	F value	p value
Model	3,234.82	14	231.06	1,948.06	< 0.0001
Residual	1.78	15	0.12		
Lack of fit	1.78	10	0.18	0.28	0.9589
Pure error	0.000	5	0.000		
Totals corrected for the mean	3,236.60	29			

For the mean square and  $F$  and  $p$  values,  $R^2 = 99.95\%$  and  $R^2(\text{adj}) = 99.89\%$ .

first-order model coefficient,  $b_{ij}$  is the interaction effect, and  $b_{ii}$  represents the quadratic coefficients of  $X_i$ , and  $e$  is the random error.

#### Oil and fuel properties

Fuel properties, namely, moisture content, density at  $15^\circ\text{C}$ , kinematic viscosity at  $40^\circ\text{C}$ , iodine value, acid value, higher heating value, flash point, pour point, cloud point, cetane number, diesel index, API, and aniline point of both sesame oil and biodiesel, were determined following standard methods and compared with American and European standards (ASTM D 6751 and DIN EN 14214).

#### Analysis of fatty acid compositions of sesame biodiesel

Fatty acid profile of the sesame biodiesel was determined using gas chromatography (HP 6890 powered with HP ChemStation Rev. A 09.01 (1206) software, Agilent Technologies Inc., Santa Clara, CA, USA). The sesame biodiesel sample (50 mg) was esterified for 5 min at  $95^\circ\text{C}$

**Table 5 ANOVA for response surface quadratic model for intercept**

Factors	Coefficient estimate	df	Standard error	95% CI low	95% CI high	VIF
Intercept	92.87	1	0.14	92.57	93.16	-
$X_1$	2.43	1	0.070	2.28	2.58	1.00
$X_2$	4.08	1	0.070	3.93	4.23	1.00
$X_3$	3.01	1	0.070	2.86	3.16	1.00
$X_4$	6.97	1	0.070	6.82	7.12	1.00
$X_1 X_2$	-1.38	1	0.086	-1.56	-1.20	1.00
$X_1 X_3$	1.14	1	0.086	0.96	1.33	1.00
$X_1 X_4$	-1.81	1	0.086	-1.99	-1.62	1.00
$X_2 X_3$	-1.42	1	0.086	-1.60	-1.23	1.00
$X_2 X_4$	-4.27	1	0.086	-4.45	-4.08	1.00
$X_3 X_4$	-0.34	1	0.086	-0.53	-0.16	1.00
$X_1^2$	-2.72	1	0.066	-2.86	-2.58	1.05
$X_2^2$	-4.88	1	0.066	-5.02	-4.74	1.05
$X_3^2$	-0.98	1	0.066	-1.22	-0.84	1.05
$X_4^2$	-2.94	1	0.066	-3.08	-2.80	1.05


with 3.4 mL of the 0.5 M KOH in dry methanol. The mixture was neutralized using 0.7 M HCl, and 3 mL of 14% boron trifluoride in methanol was added. The mixture was heated for 5 min at a temperature of 90°C to achieve complete methylation process. The fatty acids were thrice extracted from the mixture with redistilled *n*-hexane. The content was concentrated to 1  $\mu$ L for gas

chromatography analysis, and 1  $\mu$ L was injected into the injection port of gas chromatography (GC).

## Results and discussion

### Properties of the sesame seed oil used as feedstock

The analysis of the seed oil showed that it has a moisture content of 0.09%, specific gravity of 0.88, and

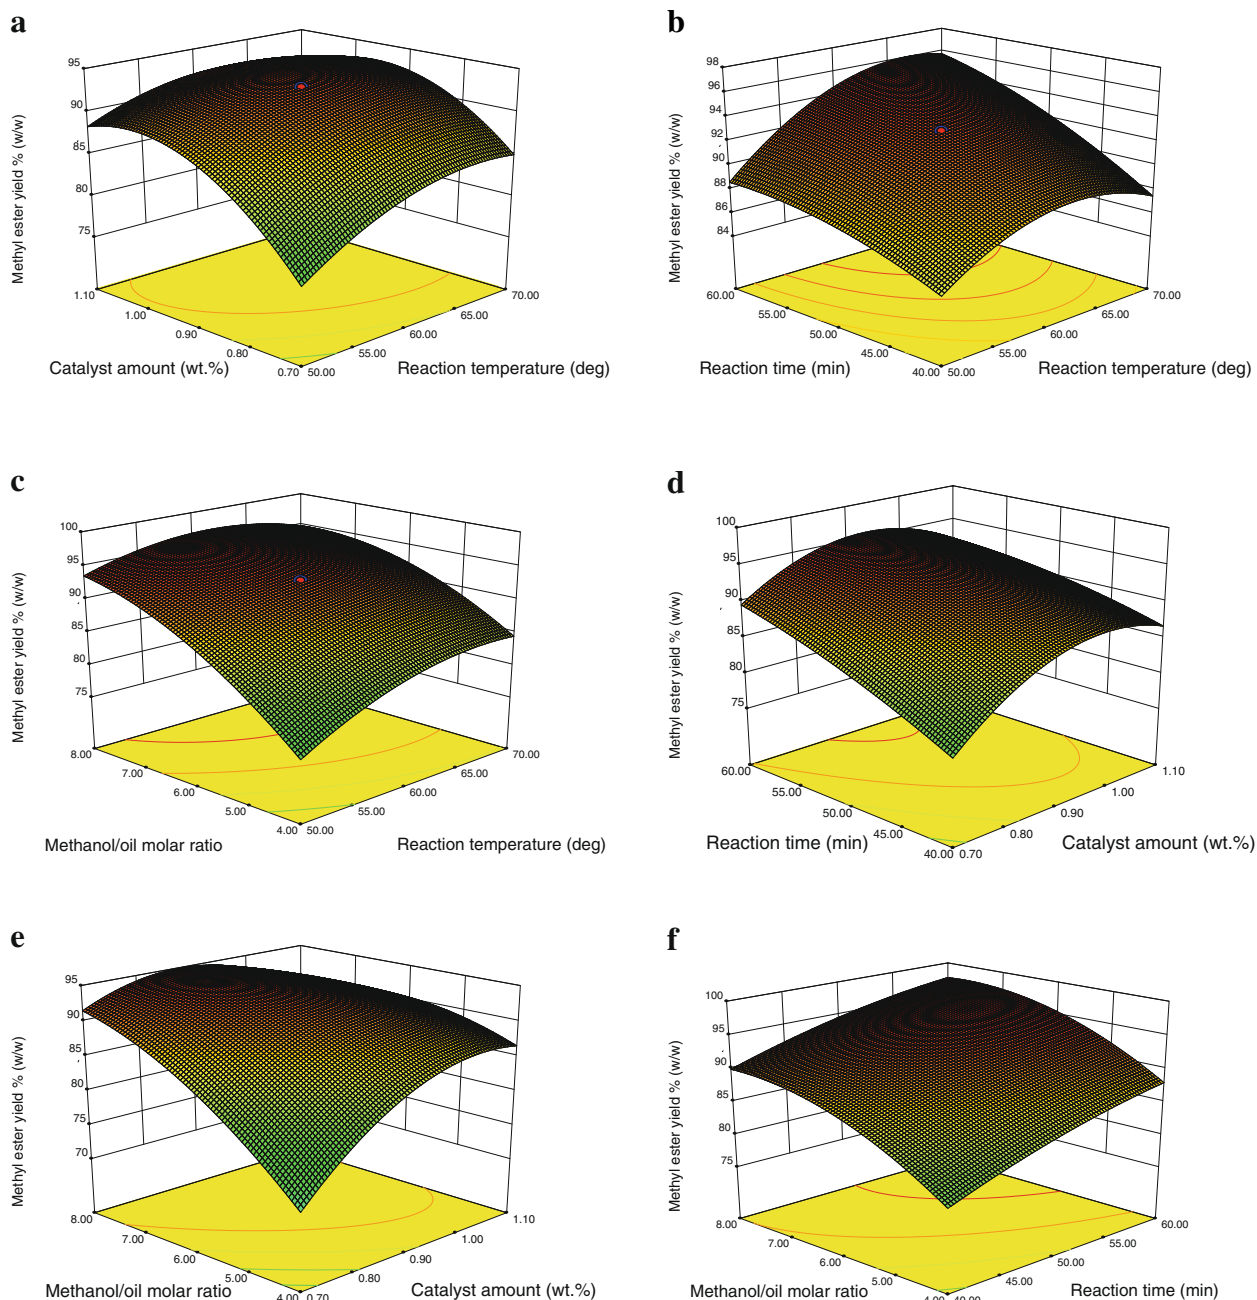

**Figure 2** Surface plots for conversion of sesame seed oil to biodiesel. (a) catalyst amount and reaction temperature, (b) reaction time and reaction temperature, (c) methanol/oil molar ratio and reaction temperature, (d) reaction time with catalyst amount, (e) methanol/oil molar ratio and catalyst amount, and (f) methanol/oil molar ratio and reaction time.



kinematic viscosity of 31.39 mm<sup>2</sup>/s. The acid value of the oil was 0.50 mg KOH/g oil, while the iodine value was 108 g I<sub>2</sub>/100 g oil. Whereas the saponification value and the peroxide value of the oil were 190 mg KOH/g oil and 7.80 meq O<sub>2</sub>/kg oil, respectively, its higher heating value and cetane number were 40.02 MJ/kg and 50.73, respectively. These results are within earlier reported values in the literature [14,27].

#### Optimization of sesame biodiesel production

The coded factors considered in this work with experimental results, predicted values, as well as the residual values obtained, are shown in Table 2. The parity plot showed a satisfactory correlation between the actual and predicted values of sesame biodiesel yield (Figure 1). Table 3 showed the results of the test of significance for every regression coefficient. The results revealed that the *p* value of the model terms was significant, i.e., *p* < 0.05. In this particular case, the four linear terms (*X*<sub>1</sub>, *X*<sub>2</sub>, *X*<sub>3</sub>, *X*<sub>4</sub>), six cross products (*X*<sub>1</sub>*X*<sub>2</sub>, *X*<sub>1</sub>*X*<sub>3</sub>, *X*<sub>1</sub>*X*<sub>4</sub>, *X*<sub>2</sub>*X*<sub>3</sub>, *X*<sub>2</sub>*X*<sub>4</sub>, *X*<sub>3</sub>*X*<sub>4</sub>), and the four quadratic terms (*X*<sub>1</sub><sup>2</sup>, *X*<sub>2</sub><sup>2</sup>, *X*<sub>3</sub><sup>2</sup>, and *X*<sub>4</sub><sup>2</sup>) were all remarkably significant model terms at 95% confidence level. Based on the large *F* values and low corresponding *p* values, all the linear terms had very strong effects on the biodiesel yield. However, methanol/oil molar ratio *X*<sub>4</sub> (*F* value = 9831.27) was the most significant variable followed by the catalyst amount *X*<sub>2</sub> (*F* value = 3364.87), followed by reaction time *X*<sub>3</sub> (*F* value = 1835.80), and lastly, reaction temperature *X*<sub>1</sub> (*F* value = 1192.78). In order to minimize error, all the coefficients were considered in the design. The model coefficients and probability values, i.e., coded values, are shown in Table 4. The model also proved suitable for adequate representation of the real relationship among the selected independent variables (*X*<sub>1</sub>, *X*<sub>2</sub>, *X*<sub>3</sub>, *X*<sub>4</sub>). Results of the ANOVA of the regression equation are presented in Table 5. The model *F* value of 3,234.83 with a low probability value (*p* < 0.0001) implied a high significance for the regression model [7]. The goodness of fit of the model was checked by the coefficient of determination (*R*<sup>2</sup>), which should be at least 0.80 for the good fit of a model [28]. The *R*<sup>2</sup> value of 0.9995 indicated that the sample variation of 99.95% for biodiesel was attributed to the independent variables, and only 0.05% of the total variations are not explained by the model. The value of the adjusted determination coefficient (adjusted *R*<sup>2</sup> of 0.9989) was also very high, supporting a high significance of the model [29,30], and all *p* values were less than 0.0001 except for *X*<sub>3</sub>*X*<sub>4</sub> with a *p* value of 0.0012, which indicated the model proved suitable for the adequate representation of the actual relationship among the selected variables. The lack-of-fit term of 0.9589 was not significant relative to the pure error. The final equation in terms of coded

factors for the central composite response surface quadratic model is expressed in Equation 3.

$$Y(w/w \%) = 92.87 + 2.43X_1 + 4.08X_2 + 3.01X_3 + 6.97X_4 - 1.38X_1X_2 + 1.14X_1X_3 - 1.81X_1X_4 - 1.42X_2X_3 - 4.27X_2X_4 - 0.34X_3X_4 - 2.72X_1^2 - 4.88X_2^2 - 0.98X_3^2 - 2.94X_4^2 \quad (3)$$

All the linear terms and cross-product term *X*<sub>1</sub>*X*<sub>3</sub> had a positive effect on the sesame biodiesel yield, while the rest of the surface quadratic model terms had negative effects on the yield. The low values of standard error observed in the intercept and all the model terms demonstrated that the regression model fits the data well, and the prediction was good (Table 5). The variance inflation factor (VIF) obtained in this study showed that the center points are orthogonal to all other factors in the model.

Generally, the 3D response surface plots are graphical representations of the regression equation for the optimization of the reaction variables, and they are presented in Figure 2. The curvatures' nature of the three-dimensional surfaces in Figure 2a,c,f suggested mutual interaction of catalyst amount with reaction temperature, methanol/oil molar ratio with reaction temperature, and methanol/oil molar ratio with reaction time, respectively. On the other hand, the curvatures' nature of the three-dimensional surfaces in Figure 2b,d,e indicated

**Table 6 Properties of sesame biodiesel in comparison to biodiesel standards**

Parameters	Sesame oil	Sesame biodiesel	ASTM D6751	EN 14214
Moisture content %	0.09	0.014	<0.03	0.02
Kinematic viscosity (mm <sup>2</sup> /s) at 40°C	31.39	4.03	1.9 to 6.0	3.5 to 5.0
Iodine value (g I <sub>2</sub> /100 g)	108	86.72	-	120 max
Acid value (mg KOH/g)	0.50	0.25	0.50 max	0.5 max
Density (kg/m <sup>3</sup> ) at 25°C	833	873	-	860 to 900
Higher heating value (MJ/kg)	40.20	41.35	-	-
Flash point (°C)	-	180	>130	>120
Pour point (°C)	-	6	-	-
Cloud point (°C)	-	18	-	-
Diesel index	55.80	69.17	50.40	-
API	29.30	30.03	36.95	-
Cetane number	50.73	59.80	47 min	51 min
Aniline point (°F)	190.42	230.33	331.00	-

moderate interactions of reaction time with reaction temperature, reaction time with catalyst amount, and methanol/oil molar ratio with catalyst amount, respectively.

The optimal values of the independent variables selected for the transesterification of sesame biodiesel were obtained by solving the regression equation (Equation 2) using the Design Expert software. The optimal conditions for this process were statistically predicted as  $X_1 = 63^\circ\text{C}$ ,  $X_2 = 1.04$  wt.%,  $X_3 = 51.09$  min, and  $X_4 = 6.24$ . The predicted sesame biodiesel yield under the above set of conditions was  $Y = 99.71\%$ . In order to verify the prediction of the model, the optimal conditions were applied to three independent replicates, and the average biodiesel yield obtained was 98.63%, which is well within the predicted value for the model equation.

### Sesame biodiesel quality characterization and fuel properties

The results of GC analysis revealed that sesame biodiesel is mainly composed of methyl esters of linoleic acid (45.17%) and oleic acid (39.02%), palmitic acid (8.47%) followed by 5.15% stearic acid, 0.93% behenic acid, 0.77% arachidic acid, 0.15% linolenic acid, 0.09% myristic acid, 0.04% palmitoleic acid, 0.03% arachidonic acid, and 0.01% erucic acid. These observations further showed that the sesame biodiesel produced under the optimal condition was within ASTM D 6751 specifications for free and total glycerol contents. In addition, Table 6 shows the results of the evaluation of sesame seed oil and fuel properties of the sesame biodiesel. Most of the fuel properties of sesame biodiesel from this study compared well with ASTM D6751 and EN 14214 biodiesel specifications.

### Conclusions

The results obtained in this study using response surface methodology to determine the effects of four reaction variables, namely, oil/methanol molar ratio, reaction temperature, catalyst concentration, and reaction time on sesame biodiesel yield via methanolysis, indicate that the biodiesel produced had fuel properties that satisfied both the ASTM D 6751 and EN 1424 standards. The statistical model predicted the optimal conditions for the selected transesterification variables as reaction temperature of  $63^\circ\text{C}$ , catalyst amount of 1.04 wt.%, reaction time of 51.09 min, and methanol/oil molar ratio of 6.24 with an actual sesame biodiesel yield of 98.63%. Hence, the work established the usefulness of RSM for optimum conversion of sesame (*S. indicum*) seed oil to biodiesel and also suggests that sesame oil could be effectively used as feedstock for biodiesel production.

### Competing interests

Authors declare that they have no competing interests.

### Authors' contributions

EB conceived and designed the research work. He is the major contributor in the preparation of the manuscript. TFA was involved in the laboratory work, and he drafted the manuscript. Both authors read and approved the final manuscript.

### Authors' information

EB is a senior lecturer in the Department of Chemical Engineering, Obafemi Awolowo University, Ile-Ife, Nigeria. He holds B.Sc. and M.Sc. degrees in Chemical Engineering from Obafemi Awolowo University. He also received a Ph.D. degree in Biotechnology from Technical University Carolo-Wilhelmina, Braunschweig, Germany in 2005. He was a DAAD scholar and a guest scientist at the National Research Centre for Biotechnology, Germany between April 2001 and December 2004, respectively. His research focus is in the area of biofuel development and bioconversion of agricultural crops and wastes to useful products. TFA is a lecturer in the Department of Chemical Engineering, Landmark University, Nigeria. He holds a M.Sc. degree in Chemical Engineering from Obafemi Awolowo University, Ile-Ife, Nigeria.

### Acknowledgments

E. Betiku gratefully acknowledged the equipment donation by the World University Service, Germany and provision of relevant literature by the DAAD. The authors also thank A.K. Omole and O.E. Aluko for their technical support.

### Author details

<sup>1</sup>Biochemical Engineering Laboratory, Department of Chemical Engineering, Obafemi Awolowo University, Ile-Ife, Osun State 220005, Nigeria.

<sup>2</sup>Department of Chemical Engineering, Landmark University, P.M.B 1001, Omu-Aran, Kwara State, Nigeria.

Received: 19 October 2012 Accepted: 22 January 2013

Published: 12 February 2013

### References

1. Balat, M: Potential alternatives to edible oils for biodiesel production - a review of current work. *Energ. Convers. Manage.* **52**, 1479–1492 (2010)
2. Shay, EG: Diesel fuel from vegetable oils: status and opportunities. *Biomass Bioenerg.* **4**(4), 227–242 (1993)
3. Knothe, G: Biodiesel and renewable diesel: a comparison. *Prog. Energ. Combust.* **36**, 364–373 (2010)
4. Aransiola, EF, Betiku, E, Layokun, SK, Solomon, BO: Production of biodiesel by transesterification of refined soybean oil. *Int. J. Biol. Chem. Sci.* **4**, 391–399 (2010)
5. Rashid, U, Anwar, F, Ashraf, M, Saleem, M, Yusup, S: Application of response surface methodology for optimizing transesterification of *Moringa oleifera* oil: biodiesel production. *Energ. Convers. Manage.* **52**, 3034–3042 (2011)
6. Berrios, M, Siles, J, Martin, M, Martin, A: A kinetic study of the esterification of free fatty acids (FFA) in sunflower oil. *Fuel* **86**, 2383–2388 (2007)
7. Yuan, X, Liu, J, Zeng, G, Shi, J, Tong, J, Huang, G: Optimization of conversion of waste rapeseed oil with high FFA to biodiesel using response surface methodology. *Renew. Energ.* **33**, 1678–1684 (2008)
8. Margaretha, YY, Prastyo, HS, Ayucitra, A, Ismadij, S: Calcium oxide from *Pomacea* sp. shell as a catalyst for biodiesel production. *Int. J. Energy Env. Eng.* **3**, 33 (2012)
9. Tiwari, AK, Kumar, A, Raheman, H: Biodiesel production from *Jatropha* oil (*Jatropha curcas*) with high free fatty acids: an optimized process. *Biomass Bioenerg.* **31**, 569–575 (2007)
10. Wu, X, Leung, DY: Optimization of biodiesel production from camelina oil using orthogonal experiment. *Appl. Energy* **88**(11), 3615–3624 (2011)
11. Muthu, H, SathyaSelvabala, V, Varathachary, T, Kirupha Selvaraj, D, Nandagopal, J, Subramanian, S: Synthesis of biodiesel from neem oil using sulfated zirconia via transesterification. *Braz J Chem Eng* **27**(4), 601–608 (2010)
12. Aransiola, EF, Betiku, E, Ikhuomogbe, DIO, Ojumu, TV: Production of biodiesel from crude neem oil feedstock and its emissions from internal combustion engines. *Afr. J. Biotech.* **11**(22), 6178–6186 (2012)
13. Meher, LC, Dharmagadda, VSS, Naik, SN: Optimization of alkali-catalyzed transesterification of *Pongamia pinnata* oil for production of biodiesel. *Bioresour Technol* **97**(12), 1392–1397 (2006)
14. Saydut, A, Duz, MZ, Kaya, C, Kafadar, AB, Hamamci, C: Transesterified sesame (*Sesamum indicum* L.) seed oil as a biodiesel fuel. *Bioresour. Technol* **99**(14), 6656–6660 (2008)

15. Wang, R, Hanna, MA, Zhou, W-W, Bhadury, PS, Chen, Q, Song, B-A, Yang, S: Production and selected fuel properties of biodiesel from promising non-edible oils: *Euphorbia lathyris* L., *Sapium sebiferum* L. and *Jatropha curcas* L. *Bioresour. Technol.* **102**(2), 1194–1199 (2011)
16. Marasabessy, A, Kootstra, AMJ, Sanders, JPM, Weusthuis, RA: Dilute H<sub>2</sub>SO<sub>4</sub>-catalyzed hydrothermal pretreatment to enhance enzymatic digestibility of *Jatropha curcas* fruit hull for ethanol fermentation. *Int. J. Energy Env. Eng.* **3**, 15 (2012)
17. Agarry, SE, Ogunleye, OO: Box-Behnken design application to study enhanced bioremediation of soil artificially contaminated with spent engine oil using biostimulation strategy. *Int. J. Energy. Env. Eng.* **3**, 31 (2012)
18. Jeong, GT, Yang, H-S, Park, DH: Optimization of transesterification of animal fat ester using response surface methodology. *Bioresour Technol* **100**, 25–30 (2009)
19. Zhang, J, Chen, S, Yang, R, Yan, Y: Biodiesel production from vegetable oil using heterogenous acid and alkali catalyst. *Fuel* **89**(10), 2939–2944 (2010)
20. Fan, X, Wang, X, Chen, F: Biodiesel production from crude cottonseed oil: an optimization process using response surface methodology. *The Open Fuels Energy Sci. J.* **4**, 1–8 (2011)
21. Ustimenko-Bakumovsky, GV: *Plant Growing in the Tropics and Subtropics*. Mir Publishers, Moscow (1983)
22. Yeramanos, DM, Hemstreet, S, Saleeb, W, Huszar, CK: Oil content and composition of the seed in the world collection of sesame introductions. *J. Am. Oil Chem. Soc.* **49**, 20–23 (1972)
23. Brar, GS: Variations and correlations in oil content and fatty acid composition of sesame. *Ind. J. Agric. Sci.* **52**, 434–439 (1982)
24. Ahmad, M, Khan, MA, Zafar, M, Sultana, S: Environment-friendly renewable energy from sesame biodiesel. *Energy Sources, Part A* **32**(2), 189–196 (2010)
25. Ahmad, M, Ullah, K, Khan, MA, Ali, S, Zafar, M, Sultana, S: Quantitative and qualitative analysis of sesame oil biodiesel, *Energy Sources. Part A.* **33**(13), 1239–1249 (2011)
26. Schinas, P, Karavalakis, G, Davaris, C, Anastopoulos, G, Karonis, D, Zannikos, F, Stournas, S, Lois, E: Pumpkin (*Cucurbita pepo* L.) seed oil as an alternative feedstock for the production of biodiesel in Greece. *Biomass Bioenergy* **33**, 44–49 (2009)
27. Elleuch, M, Besbes, S, Roiseux, O, Blecker, C, Attia, H: Quality characteristics of sesame seeds and by-products. *Food Chem* **103**(2), 641–650 (2007)
28. Guan, X, Yao, H: Optimization of viscozyme L-assisted extraction of oat bran protein using response surface methodology. *Food Chem* **106**, 345–351 (2008)
29. Akhnazarova, S, Kefarov, V: *Experiment Optimization in Chemistry and Chemical Engineering*. Mir Publishers, Moscow (1982)
30. Khuri, AI, Cornell, JA: *Response Surfaces: Design and Analysis*. Marcel Dekker, New York (1987)

doi:10.1186/2251-6832-4-9

**Cite this article as:** Betiku and Adepoju: Methanolysis optimization of sesame (*Sesamum indicum*) oil to biodiesel and fuel quality characterization. *International Journal of Energy and Environmental Engineering* 2013 **4**:9.

**Submit your manuscript to a SpringerOpen<sup>®</sup> journal and benefit from:**

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

---

Submit your next manuscript at ► [springeropen.com](http://springeropen.com)