



Migration of nanosized layered double hydroxide platelets from polylactide nanocomposite films

Journal:	<i>Food Additives and Contaminants</i>
Manuscript ID:	TFAC-2010-417.R1
Manuscript Type:	Original Research Paper
Date Submitted by the Author:	08-Mar-2011
Complete List of Authors:	Schmidt, Bjørn; Technical University of Denmark, National Food Institute; University of Copenhagen, Department of Basic Sciences and Environment Katiyar, Vimal; Technical University of Denmark, National Laboratory for Sustainable Energy Plackett, David; Technical University of Denmark, National Laboratory for Sustainable Energy Larsen, Erik; Technical University of Denmark, National Food Institute Gerds, Nathalie; University of Copenhagen, Department of Food Science Koch, Christian; University of Copenhagen, Department of Basic Sciences and Environment Petersen, Jens; Technical University of Denmark, National Food Institute
Methods/Techniques:	ICP/MS, Chromatography - GC, Chromatography, Metals analysis - ICP/MS
Additives/Contaminants:	Food contact materials, Food simulants, Migration
Food Types:	Meat

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

SCHOLARONE™
Manuscripts

For Peer Review Only

1
2
3
4
5 **Migration of nanosized layered double hydroxide platelets from polylactide**
6
7 **nanocomposite films**
8
9

10
11
12 B. Schmidt^{a,b}, V. Katiyar^c, D. Plackett^c, E. H. Larsen^b, N. Gerds^d, C. Bender Koch^a &
13
14 J. H. Petersen^{b,1}
15
16

17
18
19
20 ^a*Department of Basic Sciences and Environment, University of Copenhagen, Frederiksberg,*
21
22 *Denmark;* ^b*The National Food Institute, Technical University of Denmark, Søborg, Denmark;* ^c*Risø*
23
24 *National Laboratory for Sustainable Energy, Technical University of Denmark, Roskilde, Denmark;*
25
26
27 ^d*Department of Food Science, University of Copenhagen, Frederiksberg, Denmark.*
28
29
30
31

32 **Abstract**
33

34 Melt-extruded L-polylactide (PLA) nanocomposite films were prepared from commercially
35 available PLA and laurate-modified Mg-Al layered double hydroxide (LDH-C₁₂) and three films
36 with different LDH-C₁₂ loadings. These materials were tested for total migration as well as specific
37 migration of LDH, tin, laurate and low molecular weight PLA oligomers (OLLA). This is the first
38 reported investigation on the migration properties of PLA-LDH nanocomposite films. The tests
39 were carried out as part of an overall assessment of the suitability of such films for use as food
40 contact materials. Total migration was determined according to a European standard method. All
41 three films showed migration of nanosized LDH which was quantified using acid digestion
42 followed by inductively coupled plasma mass spectrometric (ICP-MS) detection of ²⁶Mg. Migration
43 of LDH from the films was also confirmed by examining migrates using transmission electron
44 microscopy (TEM) and was attributed indirectly to the significant PLA molecular weight reduction
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

¹J. H. Petersen. Email: jhpe@food.dtu.dk

1
2
3
4 observed in extruded PLA-LDH-C₁₂ films. Migration of tin was detected in two of the film samples
5
6 prepared by dispersion of LDH-C₁₂ using a masterbatch technique and migration of the laurate
7
8 organomodifier took place from all three film types. The results indicate that the material properties
9
10 are in compliance with the migration limits for total migration and specific lauric acid migration as
11
12 set down by the EU-legislation for Food Contact Materials (FCM), at least if a reduction factor for
13
14 fresh meat is taken into consideration. The tin detected arises from the use of organotin catalysts in
15
16 the manufacture of PLA.
17
18
19
20
21
22

23 **Keywords:** migration; nanoparticle; layered double hydroxides; nanocomposite; polylactide;
24
25 laurate organomodifier
26
27
28
29
30

31 **Introduction**

32
33 Almost half the global plastic production is currently used in packaging materials and almost half of
34
35 this amount is used in food packaging (Fomin and Guzeev 2001; Ray and Bousmina 2005). Most of
36
37 the plastics used in food packaging at present originate from fossil fuels (Lim et al. 2008; Ray and
38
39 Bousmina 2005; Sorrentino et al. 2007). However, consumer demands call for sustainability and
40
41 environmental safety and therefore research within *green* plastics is of great interest (Bordes et al.
42
43 2009; Ray and Bousmina 2005; Fomin and Guzeev 2001). Biopolymers derived from renewable
44
45 resources such as agricultural crops or crop residues meet the demands of sustainability and are
46
47 environmentally friendly (Garlotta 2001; Ray and Bousmina 2005; Auras et al. 2004; Martin and
48
49 Averous 2001; Lunt 1998; Sinclair 1996). Unfortunately, in comparison with conventional plastics
50
51 used in packaging, biopolymers can suffer from reduced thermal stability, poor gas barrier
52
53 properties, low strength, and low melt viscosity (Fomin and Guzeev 2001; Ray and Bousmina 2005;
54
55 Sorrentino et al. 2007). These inherent properties can in principle be improved by incorporation of
56
57
58
59
60

1
2
3
4 engineered or natural nanoparticles (NPs), resulting in biopolymer nanocomposite materials
5
6
7 (Bordes et al. 2009; Chang et al. 2003; Ray and Bousmina 2005; Sorrentino et al. 2007; Pluta et al.
8
9 2006; Ray et al. 2002; Arora and Padua 2010). Biopolymer nanocomposites have potential as food
10
11 contact materials (FCM) and can roughly be divided into four categories (Chaudhry et al. 2008): 1)
12
13 FCM with improved physical properties through incorporation of NPs, 2) active FCM where the
14
15 incorporated NPs provide antimicrobial activity, 3) intelligent FCM in which the NPs can act as a
16
17 sensor monitoring the condition of food during transport and storage, and 4) degradable or
18
19 compostable biopolymer nanocomposites. Research on biopolymer nanocomposites as FCM has
20
21 mainly focused on categories 1 and 4. In particular, degradable or compostable biopolymers with
22
23 layered silicate clay minerals as fillers, aiming at enhanced barrier properties, have received
24
25 attention because of the possibility to prolong the shelf life of foodstuffs packed under modified
26
27 atmosphere (MAP)(Arora and Padua 2010; Bordes et al. 2009; Ray and Bousmina 2005; Sorrentino
28
29 et al. 2007). One of the promising biopolymers in this respect is the aliphatic polyester L-
30
31 polylactide (PLA). L-lactic acid, typically obtained from starch, is the building block for PLA and a
32
33 frequently used industrial production route involves conversion to the L-lactide dimer followed by
34
35 ring-opening polymerization (ROP) in the presence of an organotin catalyst. PLA is considered to
36
37 be compostable and degrades via initial chain scission of the ester linkages (Garlotta 2001). Reports
38
39 indicate that PLA can degrade in the environment in a matter of months, whereas conventional
40
41 plastics such as polystyrene and polyethylene may persist for hundreds of years (Sinclair 1996). In
42
43 addition to silicate clay minerals as fillers in nanocomposites, layered double hydroxides (LDHs)
44
45 have attracted interest during the last few years. LDHs are synthesised in the laboratory under
46
47 controlled conditions, and the presence of trace metals which occur in natural clays can therefore be
48
49 controlled. Only a limited number of publications exist on the preparation and characterization of
50
51 PLA-LDH nanocomposites (Chiang and Wub 2008; Chiang and Wu 2010; Chiang et al., 2011;
52
53
54
55
56
57
58
59
60

1
2
3
4 Dagnon et al. 2009; Katiyar et al. 2010; Pan et al. 2008; Mahboobeh et al. 2010). In order to ensure
5
6 compatibility with and good dispersion in bioplastics such as PLA, treatment of LDHs with
7
8 organomodifiers is generally necessary.
9

10
11 A food safety concern exists when using nanocomposites as food packaging materials because the
12
13 consumer might be exposed to NPs through their migration into foodstuffs and drinks (Simon et al.
14
15 2008). Only a few studies on this issue have yet been published (Schmidt et al. 2009; Avella et al.
16
17 2005; Avella et al. 2007) and it is generally concluded that little or no migration of inorganic NPs
18
19 can be detected from the nanocomposites. This finding is in general agreement, although not
20
21 directly comparable, with a theoretical assessment of NP migration rates from polymer
22
23 nanocomposite food packaging materials based on physicochemical considerations (Simon et al.
24
25 2008). According to the current EU regulation on food contact materials “substances deliberately
26
27 engineered to particle size which exhibit functional physical and chemical properties that
28
29 significantly differ from those at a larger scale” should be risk assessed on a case-by-case basis until
30
31 more information is available about such new technology (European Commission 2009). The
32
33 European Food Safety Authority (EFSA) is empowered to make such assessments and to provide an
34
35 opinion for the European Commission. Until now only titanium nitride (TiN) NPs, intended to be
36
37 used as an additive in polyethylene terephthalate (PET) bottles, has been allowed in the EU for use
38
39 in amounts up to 20 mg kg⁻¹ plastic. TiN NPs with a diameter of 20 nm have been incorporated in
40
41 PET and tests have shown no sign of migration into food simulants down to the detection limit of
42
43 five µg kg⁻¹. EFSA opinions are usually based on data from toxicological testing, physical/chemical
44
45 data and results of migration tests. The evaluation of TiN NPs was based on physical/chemical data
46
47 and migration tests only and no toxicological data were needed in the evaluation since no NP
48
49 migrated (EFSA 2008).
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4 The aim of the study described here was to determine the total and specific migration of all major
5 constituents in the various prepared PLA/laurate-modified Mg-Al layered double hydroxide (PLA-
6 LDH-C₁₂) non-commercial nanocomposite films. LDH-C₁₂ was added with the purpose of reducing
7 gas permeability in order for the films to be used for meat packaging in modified atmospheres.
8
9 Specific migration tests focused on the detection of LDH, the laurate organomodifier, the organotin
10 catalyst applied and low molecular weight PLA oligomers (OLLA). In parallel with these studies,
11 chemical and physical characterization of melt-extruded PLA- LDH-C₁₂ films, including thermal
12 stability and barrier properties, has been undertaken and is the subject of another publication
13
14 (Katiyar et al. 2011).
15
16
17
18
19
20
21
22
23
24
25
26
27
28

29 **Materials and methods**

30 *Synthesis of LDH-C₁₂*

31 LDH-C₁₂ was synthesized using a reconstruction method for the intercalation of laurate anions.
32
33 LDH-CO₃, Al(NO₃)₃·9H₂O, Mg(NO₃)₂·6H₂O, Na₂CO₃, NaNO₃ (Merck KGaA, Darmstadt,
34 Germany) and NaOH (Mallinckrodt Baker B.V., Deventer, Netherlands) were used for the synthesis
35 of the LDH-CO₃. Ethanol (96%, Kemertyl A/S, Køge, Denmark) and Decanoic acid (lauric acid)
36 (Sigma-Aldrich Chemie GmbH, Munich, Germany) were used for the modification of the
37 synthesised LDH.
38
39
40
41
42
43
44
45
46

47 The precursor LDH-CO₃ was prepared by a constant pH-stat co-precipitation method similar to
48 Miyata (1975). 1.5 Liter of a 1 mol Al(NO₃)₃·9 H₂O solution was slowly transferred to a 15 Liter
49 bucket containing 5 Liter of 3 mole Mg(NO₃)₂·6 H₂O) solution over a period of 8 h. The pH of the
50 reaction mixture was adjusted to 9 by addition of 2 M NaOH and 0.2 M Na₂CO₃ solution. The
51 synthesis was carried out at room temperature and the suspension was constantly stirred during
52
53
54
55
56
57
58
59
60

1
2
3
4 synthesis over a 12-hour period. The precipitate was isolated by repeated centrifugation, washed
5 three times using double-deionised water and freeze dried. LDH-C₁₂ was prepared as followed:
6
7

8
9 The synthesized LDH-CO₃ was first calcined to form a metal oxide (MMO) by heating in a muffle
10 furnace at a temperature of 500°C for 5h. 10 Liter of an 30:70 ethanol-water (v/v) sodium laurate
11 solution was prepared by neutralization of lauric acid (0.1 M) solution with sodium hydroxide to pH
12 9. Subsequently, the MMO (150g) was dispersed into the sodium laurate solution under an Argon
13 atmosphere and stirred at room temperature overnight. After repeated centrifuging and washing
14 with ethanol the sample was freeze dried. The solid was further dried in a vacuum oven at 110°C to
15 minimize contamination by carbon dioxide during the drying process.
16
17
18
19
20
21
22
23
24
25
26
27

28 ***Processing of PLA and PLA-LDH-lauric acid nanocomposite films (PLA-LDH-C₁₂)***

29
30 PLA-film and PLA-LDH-C₁₂ nanocomposite films were processed using PLA (Grade 2003D) from
31 NatureWorks® LLC (Minnetonka, MN, USA) which was dried at 100°C for four hours prior to
32 processing into films. Neat PLA or PLA with LDH-C₁₂ was compounded into pellets using a twin-
33 screw co-rotating extruder (Jiangyu Xinhua Plastics Machinery Co. Ltd., Wuxi, Shanghai, China)
34 with an attached three-hole strand die (three mm), cooling bath and pelletizer. LDH-C₁₂ was
35 introduced into PLA either by direct compounding with PLA or by addition of 10% previously
36 prepared PLA-50% LDH-C₁₂ masterbatch. In short, the masterbatch was prepared by an *in situ*
37 intercalative ROP method in which an LDH-C₁₂ and L-lactide mixture (1:1 weight ratio) was first
38 prepared using dichloromethane as solvent. The dried mixture was then polymerized in the presence
39 of tin(II) 2-ethyl hexanoate as catalyst (~95%, Sigma Aldrich, Brøndby, Denmark), yielding the
40 aforementioned PLA-LDH-C₁₂ masterbatch with 5% nanofiller loading. Neat PLA pellets were
41 processed under the same conditions so the reference pellets would have the same thermal history
42 as the nanocomposite pellets. Dry PLA and PLA-LDH-C₁₂ pellets were then converted into films
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4 using a single screw extruder (Labotech Engineering Company Ltd., Bangkok, Thailand). A
5
6 detailed description of the film processing can be found elsewhere (Katiyar et al. 2010).
7
8

9 Nomenclature and a description of the materials are presented in Table 1.
10
11

12 13 14 *Migration studies*

15 16 *Migration test procedure*

17
18 The migration test procedure used 95% ethanol (HPLC grade $\geq 99.9\%$, Merck, Darmstadt,
19
20 Germany) and 5% water (glass-distilled) as a simulant substituting fatty foods in accordance with
21
22 European Union legislation (Comité Européen de Normalisation (CEN) 2002; Comité Européen de
23
24 Normalisation (CEN) 2004; European Commission 2002). One dm^2 from each type of PLA and
25
26 PLA-LDH- C_{12} film was fully immersed into 100 ml of simulant and both sides were exposed at
27
28 40°C for 10 days. Simulant blanks, simulant spiked with LDH- C_{12} and simulant spiked with lauric
29
30 acid ($\geq 99\%$ for synthesis, Merck, Hohenbrunn, Germany) were included. All migrates were
31
32 analysed in triplicate except for the blank, which was analysed in duplicate. Three series of tests
33
34 were performed for the purpose of determining total migration and specific migration of LDH, tin,
35
36 laurate and low molecular weight PLA oligomers (OLLA).
37
38
39
40
41
42
43
44

45 46 *Analysis of total migration*

47
48 Total migration from the nanocomposites (mass of migrant per dm^2) was determined
49
50 gravimetrically using a modification of the laboratory-accredited CEN-procedure in which the film
51
52 samples were removed after exposure and the simulant evaporated to dryness (Comité Européen de
53
54 Normalisation (CEN) 2002). The rather volatile laurate constitutes in some samples a significant
55
56 part of the total migration and was to some extent lost during the prescribed repeated heating,
57
58 drying, and weighing cycle prescribed by the migration test method. This was investigated by
59
60

1
2
3
4 experiments using known amounts (50 mg portions) of pure lauric acid. The final result was
5
6 corrected for evaporative loss of laurate by adjusting its contribution to the total migration result by
7
8 the experimentally determined loss of laurate (23% during four heating cycles at 105°C). The
9
10 method was otherwise as detailed by the CEN standard in respect to simulant blank, detection limit
11
12 and precision.
13
14
15

16 17 18 19 *Analysis of specific migration of laurate*

20
21 From each 100 ml food simulant migrate, 20 ml was removed for laurate analysis. Migrates were
22
23 evaporated almost to dryness and the residue was then resuspended in refluxing cyclohexane. An
24
25 internal standard (heptadecanoic acid, >99%, Fluka, Steinheim, Germany) was added, followed by
26
27 10 ml KOH (11 mg ml⁻¹, Pro Analysis, Merck KGaA, Darmstadt, Germany) and then five ml
28
29 boron-trifluoride-methanol complex (150 mg BF₃ ml⁻¹, Merck, Hohenbrunn, Germany). Finally, 15-
30
31 20 ml deionised water saturated with Na₂SO₄ was added to give a two-phase system. The upper
32
33 organic phase contained lauric acid methyl esters, which were quantified using gas chromatography
34
35 (GC) with flame ionization detection (FID). The GC was an Agilent 6890A (Agilent Technologies,
36
37 Santa Clara, CA, USA). Raw data were collected using Agilent Chemstation Software (ver. A10-
38
39 02). The GC column was a non-polar Agilent J&W DB1 (30 m, i.d. 0.25 mm, film thickness 0.25
40
41 µm) kept at 80°C for one minute, ramping with 15°C min⁻¹ to 300°C, which was maintained for five
42
43 minutes. The carrier gas was helium (column flow about 40 cm sec⁻¹). A one µl split injection at
44
45 250°C was used in the analyses (split 1:100). Lauric acid standards were included in the
46
47 derivatisation process in a range of concentrations corresponding to a migration of laurate from 0
48
49 mg dm⁻² to 10.6 mg dm⁻². The linearity of the laurate standard curve was reflected by a correlation
50
51 coefficient (R²) exceeding 0.996 and the limit of detection was 0.2 mg dm⁻².
52
53
54
55
56
57
58
59
60

1
2
3
4
5 *Analysis of the specific migration of LDH and tin*
6

7 From each of the 100 ml food simulant migrates the remaining 80 ml served as samples for analysis
8
9 of migrated LDH-C₁₂ and tin. The samples were reduced to 20 ml by evaporation, from which 12
10
11 ml was transferred to Teflon inserts for further acid digestion following method 3052 of the US
12
13 Environmental Protection Agency (USEPA) (United States Environmental Protection Agency
14
15 1996). These aliquots were then evaporated almost to dryness in a heated water bath and the
16
17 following were added to all inserts in the order mentioned: two ml H₂O₂ (Suprapur 30%, Merck,
18
19 Darmstadt, Germany), nine ml HNO₃ (PlasmaPURE 67-69%, SCP Science, Champlain, NY, USA),
20
21 two ml HCl (PlasmaPURE 34-37%, SCP Science, Champlain, NY, USA) and three ml HF
22
23 (Suprapur 40%, Merck, Darmstadt, Germany). In the next step, the Teflon inserts were enclosed in
24
25 steel bombs and placed in an oven at 180°C for six hours and the contents transferred quantitatively
26
27 to 50 ml conical polypropylene tubes (Sarstedt AG & Co. Nümbrecht, Germany) containing 20 ml
28
29 of 6% boric acid (Puratronic 99.9995% from Alfa Aesar GmbH & Co KG, Karlsruhe, Germany).
30
31 Milli-Q water was added to a final volume of 45 ml. The acid-digested samples were analysed for
32
33 tin and magnesium (Mg) in two different sequences by inductively coupled plasma mass
34
35 spectrometry (ICP-MS, Agilent 7500ce system, Agilent Technologies, Santa Clara, CA, USA)
36
37 equipped with a cooled Scott-type spray chamber and an Agilent micro flow nebulizer (model no.
38
39 G3139A-100). The ICP-MS was run in spectrum analysis acquisition mode with an uptake flow rate
40
41 of 0.33 ml min⁻¹ and the RF power set to 1550 W. Raw data were collected on Agilent Chemstation
42
43 Software (version B.03.05).
44
45
46
47
48
49
50

51 The LDH analyses were conducted by measuring the isotope ²⁶Mg with ¹⁰³Rh (rhodium standard for
52
53 ICP-MS, PlasmaCAL, SCP Science) as an internal standard. Non-cell mode was applied with an
54
55 integration time per mass set to 0.3 s with three repetitions. The acid-digested samples were diluted
56
57 before analysis by adding one ml acid-digested sample to 25.1 ml of 2% HNO₃ containing 10 µg Rh
58
59
60

1
2
3
4 l^{-1} . Quantification was performed by an external standard curve ranging from 0 to 10 mg Mg l^{-1}
5
6 using 10 μ g Rh l^{-1} as internal standard. The standard curve was linear with a correlation coefficient
7
8 (R^2) equal to 0.9996. The limit of detection was 20 μ g Mg dm^{-2} film which was equal to 0.1 mg
9
10 LDH per dm^2 of film surface.
11

12
13
14 Three inserts spiked with about 25.0 mg LDH-C₁₂ were included in order to correlate ²⁶Mg and the
15
16 amount of spiked LDH-C₁₂. Quantification of migrating LDH from all films was based on this
17
18 correlation and reported as LDH-C₁₂. The correlation between ²⁶Mg and pure LDH-C₁₂ was linear
19
20 with a correlation coefficient (R^2) equal to 0.9997.
21

22
23 For tin analysis the isotope ¹¹⁸Sn was used with ¹⁰³Rh as internal standard. Non-cell mode was
24
25 applied with an integration time of 0.9 s per mass using three repetitions. Before analyses, samples
26
27 were diluted by adding two ml sample to nine ml 1.7% HNO₃ and 2.7% HCl in Milli-Q water
28
29 containing 10 μ g Rh l^{-1} . Quantification was performed using an external ¹¹⁸Sn/¹⁰³Rh standard curve
30
31 in the range 0 to 50 μ g Sn l^{-1} and constant 10 μ g Rh l^{-1} . The standard curve was linear with a
32
33 correlation coefficient (R^2) equal to 1.000.
34
35
36
37
38
39

40 *Analysis of specific migration of low molecular weight PLA oligomers*

41
42 In order to qualitatively determine the specific OLLA migration, each 100 ml portion of food
43
44 simulatant was evaporated to dryness under reduced pressure at room temperature. An OLLA residue
45
46 was visible in the case of the neat PLA sample (PLA-PF) and particulate matter was also visible in
47
48 the residues after evaporation in the PLA-LDH-C₁₂ film samples (PLA-PF1, PLA-PF2 and PLA-
49
50 PF3). The residues were redissolved in two ml CHCl₃ (>99.8%, Sigma Aldrich, Brøndby,
51
52 Denmark). In order to avoid gel permeation chromatography (GPC) column contamination or
53
54 clogging by large particles, the redissolved migrates were filtered through a 0.20 μ m Whatman[®]
55
56 filter before analysis. 100 μ l of each sample was injected into the GPC system (model LC-10AD,
57
58
59
60

1
2
3
4 Shimadzu Europa GmbH, Duisburg, Germany) equipped with a refractive index detector (Model
5
6 200, Viscotek Corporation, Houston, TX, USA) and with 5 μ Mixed-C and a 5 μ Mixed-D PLgel
7
8 columns (300 mm, i.d. 7.5 mm, Polymer laboratories Ltd (through Scantec Lab AB, Sävedalen,
9
10 Sweden) in series, with tetrahydrofuran (THF) (HPLC grade, Sigma Aldrich, Brøndby, Denmark)
11
12 as eluent at a flow rate of 0.5 ml min⁻¹. The GPC system was calibrated using polystyrene standards
13
14 dissolved in THF in a range between 1.2 kDa and 680 kDa. PLA molecular weights (MW) and a
15
16 relative concentration factor (CF) for OLLA in migrant samples were calculated. PLA molecular
17
18 weights were expressed in terms of number average molecular weights (M_n).
19
20
21
22
23
24
25

26 *Film characterization before and after migration study*

27
28 Neat PLA and PLA-LDH-C₁₂ nanocomposite films were characterized with respect to number-
29
30 average molecular weight (M_n), weight-average molecular weight (M_w), and polydispersity index
31
32 ($PDI = M_w/M_n$) before and after exposure to the food simulant using the GPC system described
33
34 above. The procedure used for the molecular weight analysis of these films was similar to that for
35
36 OLLA. In order to avoid LDH or larger particles plugging the GPC column, the PLA-LDH-C₁₂
37
38 nanocomposite solutions in chloroform were kept for 24 hours at room temperature for particles to
39
40 settle and the supernatant was filtered through a 0.45 μ m Whatman[®] filter.
41
42
43
44
45
46

47 *Electron microscopy*

48
49 Scanning electron micrographs (SEM) on LDH-C₁₂ powder samples were obtained using a FEI
50
51 Quanta 200F field emission gun microscope (FEI Company, Hillsboro, OR, USA) operated at an
52
53 accelerating voltage of 5 kV. The powder samples were placed on carbon tape and coated with a 20
54
55 nm thick layer of carbon using a vacuum sputtering technique.
56
57
58
59
60

1
2
3
4 The migrates from neat PLA and PLA-LDH-C₁₂ films were examined by bright field imaging using
5 a Tecnai G² 12 twin transmission electron microscope (TEM) (FEI Company, Hillsboro, OR, USA)
6 equipped with an INCA energy-dispersive x-ray analysis (EDAX) system (Oxford Instruments,
7 Abingdon, Oxfordshire, UK). The microscope was operated at an accelerating voltage of 200 kV.
8
9 The samples for the TEM analyses were prepared by depositing a small droplet of food simulant
10 (directly from the migration studies) on a copper grid. The solvent was evaporated using a 100 watt
11 lamp for one hour before samples were examined in the TEM.
12
13
14
15
16
17
18
19
20
21
22

23 **Results and discussion**

24 *Migration studies*

25 *Total migration*

26
27
28
29
30
31 The results obtained for total migration measurements are reported in Table 4. It is apparent that
32 LDH-C₁₂ loading may influence total migration since the lowest total migration is found for the
33 neat PLA film (PLA-PF) and total migration values increase with increasing LDH-C₁₂ loading
34 (PLA-PF1 (1.8%), PLA-PF3 (1.8%) and PLA-PF2 (5.5%)). The migration limit for overall
35 migration is 10 mg dm⁻² and only the migration from PLA-PF2 is higher, at about 32 mg dm⁻².
36
37

38
39
40
41
42 However, the films produced in this project are intended for the packaging of fresh meat in which
43 case a reduction factor of four should be applied to the migration test result with a fatty food
44 simulant before comparing with the legislative limit (European Commission 2010). The corrected
45 result for PLA-PF2 was therefore 8 mg dm⁻², which is well below the total migration limit.
46
47

48
49
50
51
52 The recovered content of LDH-C₁₂ in spiked simulants was 5.2 mg and, compared to the 5.0 mg of
53 LDH-C₁₂ originally spiked to the simulant corresponds to a recovery of 104% which supports the
54 accuracy of the total migration study.
55
56
57
58
59
60

Specific migration of tin

Tin migration was only detected in the case of the PLA-PF2 and PLA-PF3 nanocomposite films (Table 4). This was expected since these two films are the ones prepared from the PLA-50% LDH-C₁₂ masterbatch, which was made by *in situ* intercalative ROP using tin (II) 2-ethyl hexanoate catalyst. The tin (II) 2-ethyl hexanoate catalyst is not on the EU positive list, but is accepted by the US Food and Drug Administration for use only as a catalyst for polyurethane resins and in epoxy coatings (US Food and Drug Administration 2010). Although, it is not required that catalysts used for FCM are on the EU positive list, a limit for the sum of more toxic organotin substances (typically used as PVC-stabilisers) of 6 µg tin kg⁻¹ food or 1 µg tin dm⁻² exists (European Commission 2002). Both PLA-PF2 and PLA-PF3 show migration of tin at about this level.

Specific migration of LDH

LDH-C₁₂ content recovered in the spiked simulant was 4.0 mg (Table 4), which corresponds to a recovery of 80% as 5.0 mg was originally spiked to the food simulant. The stoichiometry between LDH and laurate was not known, and this is why it was chosen to express the migration of LDH from the films as LDH-C₁₂. However, this will overestimate the amount of LDH NPs migrating since we relate Mg measured by the ICP-MS to the weighed mass of LDH-C₁₂ and because LDH-C₁₂ is not completely free of water. The highest value of LDH-C₁₂ migration was detected in the sample with the highest clay loading (PLA-PF2). Migration from the two other nanocomposite films were in the same order of magnitude due to their similar LDH-C₁₂ loading. The decrease in PLA molecular weight during the migration study can perhaps explain LDH-C₁₂ migration from the films. A higher rate of platelet migration could reflect a general increase in diffusivity that might be expected in a polymer matrix with lower molecular weight and hence higher free volume. However,

1
2
3
4 it cannot be established whether migration take place from the surface and/or from the bulk of the
5
6 film.
7
8

9
10
11 *Specific migration of laurate*
12

13
14 The results of the specific migration measurements can be found in Table 4. An interesting finding
15
16 in the spike experiments was the very low amount of free laurate released from LDH-C₁₂ into the
17
18 simulant compared to the release from the nanocomposite films. This was most likely because
19
20 laurate anions are strongly bound by ionic forces within the LDH platelet galleries. However,
21
22 migration of laurate was observed and quantified in the case of PLA-LDH-C₁₂ nanocomposite
23
24 films, indicating that lauric acid was either liberated from LDH during processing of the PLA films
25
26 or during the migration study. Notably, there was no significant difference between specific laurate
27
28 migration from films PF-1 and PF-3 produced by different compounding methods but with similar
29
30 LDH-C₁₂ loadings.
31
32
33

34
35 In an earlier study, significant migration of the organomodifier from exfoliated Cloisite®30B was
36
37 seen in tests of PLA films containing this organomodified montmorillonite clay. Attention should
38
39 therefore be given to organomodifier migration and potential food safety issues (Sharma et al. 2010)
40
41 as well as to the NPs (Scientific Committee on Emerging and Newly Identified Health Risks
42
43 (SCENIHR) 2006). Arguably, greater migration of an organomodifier might be expected in cases
44
45 where a higher extent of clay exfoliation has been achieved. In the case of laurate migration studied
46
47 here, there should be no toxicity concerns given the low levels of migration detected. It should,
48
49 however, be mentioned that lauric acid had a noticeably unpleasant smell when heated. A
50
51 phenomenon, which was observed during the repeated heating, drying, and weighing cycles of the
52
53 migrates as well as during the extruding process. This would be of concern in the context of food
54
55 packaging since the EU framework directive (European Commission 2004) prescribes that FCM
56
57
58
59
60

1
2
3
4 should not transfer their constituents to food in quantities which could bring about a deterioration in
5
6
7 the organoleptic characteristics of the food.
8
9

10 11 ***Characterization of films before and after migration studies*** 12

13
14 Figure 1 shows the gel permeation chromatograms and Table 2 summarizes the molecular weights
15
16 and molecular weight distributions of the processed films before and after exposure to food
17
18 simulant. Clearly, PLA molecular weights decreased during migration testing in all films. The
19
20 decrease in M_n of PLA-PF was ~ 24% but was in the range 36-38% for samples PLA-PF1, PLA
21
22 PF2 and PLA-PF3 A greater decrease in polymer molecular weight attributed to hydrolysis in PLA-
23
24 LDH films may be associated with a catalytic effect introduced by the presence of nano-dispersed
25
26 LDH platelets with many available hydroxyl groups and metal sites on the platelet surfaces. As
27
28 noted by Zhang et al. (1997), encapsulated metal salts, including hydroxides, can have a significant
29
30 influence on water uptake and degradation in poly(D,L-lactide-co-glycolide) and reasons such as: 1)
31
32 changes in film porosity, 2) osmotic forces, 3) neutralization of protons released during hydrolysis
33
34 of ester linkages, and 4) chemical interactions between ions and functional groups on the polymer,
35
36 were suggested. In this work, the interaction between PLA and the inorganic additive (i.e., LDH) is
37
38 likely enhanced by its dispersion in nano-form. The PDI of the PLA films increased during the
39
40 migration test period along with decreasing M_n regardless of the film type, which could be
41
42 explained by the formation of low molecular weight PLA oligomers (OLLA). It is feasible that
43
44 OLLAs could migrate from PLA films into the food simulant during migration testing and this was
45
46 therefore investigated.
47
48
49
50
51
52
53

54 55 56 ***Specific Migration of OLLA*** 57 58 59 60

1
2
3
4 The GPC chromatograms of the migrate solutions are shown in Figure 2 and the M_n values
5
6 corresponding to peaks for OLLAs in each sample are presented in Table 3. Three resolved GPC
7
8 peaks (peaks 1-3) were identified in these samples, suggesting a wide range of OLLA chains
9
10 migrating into the food simulant. The longer OLLA chains ($M_n \geq 3000$ Da) corresponds to peak 1 in
11
12 Figure 2 and peaks 2 and 3 represent lower molecular weight OLLA. The presence of OLLA in
13
14 migrates from all film samples were further examined using $^1\text{H-NMR}$ analysis and the presence of
15
16 OLLA was confirmed (data not shown).
17
18
19

20
21 In order to provide an estimate for the increase in OLLA migrating from the PLA nanocomposite
22
23 films compared to the neat PLA film the areas under the three GPC peaks (Figure 3) were
24
25 integrated and compared. A relative OLLA concentration factor (CF) was calculated by taking the
26
27 sum of all three peak areas for each sample and relating the sum to the same value in the GPC
28
29 output from neat PLA (PLA-PF). The relative values can be found in Table 3. It is observed that the
30
31 CF is higher at the higher LDH- C_{12} loading (PLA-PF2) which may indicate a relationship between
32
33 LDH- C_{12} loading and migrating OLLA. However, interestingly, the OLLA CF is lower in the case
34
35 of PLA-LDH- C_{12} film based on the masterbatch (PLA-PF3) compared to the other 1.8% w/w LDH-
36
37 C_{12} loaded film (PLA-PF1). LDH surface modification by growing PLA chains during masterbatch
38
39 synthesis and reduced interaction between PLA chains and LDH surface hydroxyl groups as a
40
41 result, may provide a possible explanation.
42
43
44
45
46
47
48

49 ***Imaging of LDH by SEM***

50
51 The microstructure of the LDH- C_{12} powder sample show aggregates (diam. $\sim 1\mu\text{m}$) of sheet planar
52
53 single particles with sand-rose morphology and a diameter particle size $\sim 200\text{nm}$ and thickness of <
54
55
56
57
58
59
60
20nm.

Imaging of migrates by TEM

In the migrate from the PLA-PF sample a residue which may be OLLA was observed (Figure 3b). TEM photomicrographs of migrate samples from PLA-PF1, PLA-PF2 and PLA-PF3 films (Figures 3 c-f) show particles that are consistent with the appearance of LDH platelets. EDAX data obtained when focusing on these particles indicated the presence of Mg and Al, which is chemical evidence supporting this identification of the particles seen in Figures 3 b-e. In the case of the nanocomposite films, the size of the LDH platelets as measured by image analysis was less than 50 nm, which compares with a platelet size from 50 nm to 200 nm when LDH-C₁₂ was examined using TEM after synthesis (Katiyar et al. 2010). This finding may arise due to mechanical separation of the LDH platelets during the melt processing steps. Smaller nanoplatelets will be more likely to diffuse from the PLA film to the food simulant. The finding that 50 nm NPs migrate in this case is not consistent with the theoretical physicochemical point of view expressed by Simon et al (Simon et al. 2008) who calculated the migratability of 5 nm particles in plastics with high diffusivity such as low-density polyethylene. These authors concluded that any significant migration, even after a long time in contact with foodstuffs, could be expected solely in the case of very small NPs with a radius in the order of 1 nm. However, they also indicate that although their migration test results conform with theory, more testing on other types of materials would be needed to build a broader picture and to confirm the predicted migration patterns for other nanocomposites. Consequently, it is perhaps not surprising that there would be differences in the size of any migrating NPs as a function of NP type and polymer matrix chemistry. Interestingly, we can also observe LDH platelets mixed with OLLA chains in the migrate from PLA-PF3 (Figures 3d and 3e). The possibility that PLA grafted on to LDH surfaces during masterbatch synthesis also participates in migration cannot be discounted (Katiyar et al. 2010).

Conclusions

Total migration and specific migration of LDH, tin and laurate from extruded PLA-LDH-C₁₂ nanocomposite films was analysed. Total migration, as well as specific migration of LDH and laurate, was higher at higher LDH-C₁₂ loading in the films. Hydrolysis of PLA during migration testing and a consequent reduction in molecular weight may provide the explanation for these findings. Specific migration of tin was quantified and qualitative evidence for OLLA migration was also found. In addition to release of laurate during the migration tests, it is possible that release of laurate from the organomodified LDH may have occurred during melt processing of PLA and LDH-C₁₂ which would be another contributing factor. For the first time specific migration of LDH nanoplatelets from nanocomposite films was visualised and the nanoplatelet dimensions confirmed by TEM. This visualisation in combination with elemental analysis by EDAX complemented the quantitative determination by ICP-MS. The use of TEM to examine migrate residues also provided evidence which was consistent with the presence of migrating PLA oligomers.

This paper has focused on examining the migration of particular organomodified LDH NPs from melt-processed PLA films and has demonstrated how standard migration procedures in combination with advanced characterization methods have advanced our knowledge in this particular field. In addition to the findings from this study, there are still other factors to consider before such materials could be considered suitable for food packaging, such as the effect of LDH organomodifiers on organoleptic properties of packaged food, including possible consequences for film use, and which sort of food packaging might be appropriate given the migration properties of any particular PLA-LDH nanocomposite type.

Acknowledgements

1
2
3
4 The authors would like to express their thanks to The Danish Strategic Research Council for
5
6 supporting the NanoPack (Biopolymer Nanocomposite Films for use in Food Packaging
7
8 Applications) project (File .no. 2106-06-0061).
9
10

11 12 13 14 **Reference List**

- 15
16
17
18
19
20 Arora, A and Padua, GW. 2010. Review: Nanocomposites in food packaging. *J Food Sci.* 75:R43-
21
22 R49.
23
24
25
26 Auras, R, Harte, B, Selke, S. 2004. An overview of polylactides as packaging materials. *Macromol*
27
28 *Biosci.* 4:835-864.
29
30
31
32 Avella, M, Bruno, G, Errico, ME, Gentile, G, Piciocchi, N, Sorrentino, A, Volpe, MG. 2007.
33
34 Innovative packaging for minimally processed fruits. *Packag Technol Sci.* 20:325-335.
35
36
37
38 Avella, M, De Vlieger, JJ, Errico, ME, Fischer, S, Vacca, P, Volpe, MG. 2005. Biodegradable
39
40 starch/clay nanocomposite films for food packaging applications. *Food Chem.* 93:467-474.
41
42
43
44 Bordes, P, Pollet, E, Averous, L. 2009. Nano-biocomposites: Biodegradable polyester/nanoclay
45
46 systems. *Prog Polym Sci.* 34:125-155.
47
48
49
50 Chang, JH, An, YU, Sur, GS. 2003. Poly(lactic acid) nanocomposites with various organoclays. I.
51
52 Thermomechanical properties, morphology, and gas permeability. *J Polym Sci B Polym*
53
54 *Phys.* 41:94-103.
55
56
57
58
59
60

- 1
2
3
4 Chaudhry, Q, Scotter, M, Blackburn, J, Ross, B, Boxall, A, Castle, L, Aitken, R, Watkins, R. 2008.
5
6 Applications and implications of nanotechnologies for the food sector. *Food Addit Contam.*
7
8 25:241-258.
9
10
11
12 Chiang, MF and Wu, TM. 2010. Synthesis and characterization of biodegradable poly(L-
13
14 lactide)/layered double hydroxide nanocomposites. *Compos Sci Technol.* 70:110-115
15
16
17
18 Chiang, MF and Wu, TM. 2008. Thermal degradation of novel exfoliated PLLA/LDH
19
20 nanocomposites. *Adv Mat Res, Pts 1 and 2.* 47-50:415-418.
21
22
23
24 Chiang, MF, Chu MZ, Wu, TM. 2011. Effect of layered double hydroxides on the thermal
25
26 degradation behavior of biodegradable poly(L-lactide) nanocomposites. *Polym Degr Stab.*
27
28 96:60-66.
29
30
31 Comité Européen de Normalisation (CEN).2002. EN 1186: Materials and articles in contact with
32
33 foodstuffs - plastics. Part 1: Guide to the of conditions and test methods for overall
34
35 migration. Part 14: Test method for substitute test for overall migration into isooctane and
36
37 95% aqueous ethanol. Brussels:CEN.
38
39
40
41 Comité Européen de Normalisation (CEN). 2004. EN 13130-1: Materials and articles in contact
42
43 with foodstuffs - Plastic substances subject to limitation - Part 1: Guide to test methods for
44
45 the specific migration of substances from plastics to foods and food simulants and the
46
47 determination of substances in plastics and the selection of exposure to food simulants.
48
49 Brussels:CEN.
50
51
52
53
54 Dagnon, KL, Ambadapadi, S, Shaito, A, Ogbomo, SM, DeLeon, V, Golden, TD, Rahimi, M,
55
56 Nguyen, K, Braterman, PS, D'Souza, NA. 2009. Poly(L-lactic acid) nanocomposites with
57
58 layered double hydroxides functionalized with ibuprofen. *J Appl Polym Sci.* 113:1905-1915.
59
60

1
2
3
4 EFSA. 2008. Scientific opinion of the panel on food contact materials, enzymes, flavouring and
5 processing aids (CEF) on 21st list of substances for food contact materials. EFSA J. 888-
6 890:1-14.
7
8
9

10
11
12 European Commission. 2004. Regulation no 1935/2004 of the European parliament and of the
13 council of 27 October 2004 on materials and articles intended to come into contact with
14 food. Off J Eur Comm. L. 338:4-17.
15
16
17
18

19
20 European Commission. 2007. Commission Directive 2007/19/EC of 30 March 2007 amending
21 Directive 2002/72/EC relating to plastic materials and articles intended to come into contact
22 with food and Council Directive 85/572/EEC laying down the list of simulants to be used
23 for testing migration of constituents of plastic materials and articles intended to come into
24 contact with foodstuffs. Off J Eur Comm. L. 91:1-11.
25
26
27
28
29
30
31

32
33 European Commission. 2002. Commission Directive of 6 August 2002 relating to plastic materials
34 and articles intended to come into contact with foodstuffs. Off J Eur Comm. L. 220:18-58.
35
36
37

38
39 European Commission. 2009. Commission regulation (EC) No 450/2009 of 29 May 2009 on active
40 and intelligent materials and articles intended to come into contact with food. Off J Eur
41 Comm. L. 135:3-11.
42
43
44
45

46
47 Fomin, VA and Guzeev, VV. 2001. Biodegradable polymers, their present state and future
48 prospects. Prog Rub Plast Technol. 17:186-204.
49
50

51
52
53 Garlotta, D. 2001. A literature review of poly(lactic acid). J Polym Environ. 9:63-84.
54
55

56
57 Katiyar, V, Gerds, N, Koch, CB, Risbo, J, Hansen, HCB, Plackett, D. 2010. Poly L-lactide
58 nanocomposites via in situ polymerization of L-lactide. Polym Degr Stab. 95: 2563-2573.
59
60

- 1
2
3
4
5
6 Katiyar, V, Gerds, N, Koch, CB, Risbo, J, Hansen, HCB, Plackett, D. 2011. Melt processing of poly
7
8 (L-lactic acid) in the presence of organomodified anionic and cationic clays. *J. Appl. Polym.*
9
10 *Sci.*, accepted for publication. Lim, LT, Auras, R, Rubino, M. 2008. Processing technologies
11
12 for poly(lactic acid). *Prog Polym Sci.* 33:820-852.
13
14
15
16 Lunt, J. 1998. Large-scale production, properties and commercial applications of polylactic acid
17
18 polymers. *Polym Degrad Stab.* 59:145-152.
19
20
21
22 Mahboobeh, E, Yunus, WMZW, Hussein, Z, Ahmad, M, Ibrahim, NA. 2010. Flexibility
23
24 improvement of poly(lactic acid) by stearate-modified layered double hydroxide. *J Appl*
25
26 *Polym Sci.* 118:1077-1083.
27
28
29
30 Martin, O and Averous, L. 2001. Poly(lactic acid): plasticization and properties of biodegradable
31
32 multiphase systems. *Polym.* 42:6209-6219.
33
34
35
36 Pan, PJ, Zhu, B, Dong, T, Inoue, Y. 2008. Poly(L-lactide)/layered double hydroxides
37
38 nanocomposites: Preparation and crystallization behavior. *J Polym Sci B Polym Phys.*
39
40 46:2222-2233.
41
42
43
44 Pluta, M, Paul, MA, Alexandre, M, Dubois, P. 2006. Plasticized polylactide/clay nanocomposites. I.
45
46 The role of filler content and its surface organo-modification on the physico-chemical
47
48 properties. *J Polym Sci B Polym Phys.* 44:299-311.
49
50
51
52 Ray, SS and Bousmina, M. 2005. Biodegradable polymers and their layered silicate nano
53
54 composites: In greening the 21st century materials world. *Prog Mat Sci.* 50:962-1079.
55
56
57
58
59
60

- 1
2
3
4 Ray, SS, Maiti, P, Okamoto, M, Yamada, K, Ueda, K. 2002. New polylactide/layered silicate
5
6 nanocomposites. 1. Preparation, characterization, and properties. *Macromolecules*. 35:3104-
7
8 3110.
9
10
11
12 Schmidt, B, Petersen, JH, Bender Koch, C, Plackett, D, Johansen, NR, Katiyar, V, Larsen, EH.
13
14 2009. Combining asymmetrical flow field-flow fractionation with light-scattering and
15
16 inductively coupled plasma mass spectrometric detection for characterization of nanoclay
17
18 used in biopolymer nanocomposites. *Food Addit Contam Part A Chem Anal Control Expo*
19
20 *Risk Assess*. 26:1619-1627.
21
22
23
24
25 Scientific Committee on Emerging and Newly Identified Health Risks (SCENIHR). Modified
26
27 Opinion (after public consultation) on the appropriateness of existing methodologies to
28
29 assess the potential risks associated with engineered and adventitious products of
30
31 nanotechnologies [Internet]. 2006. Brussels: European Commission [cited 2010 Nov 17].
32
33 Available from: http://ec.europa.eu/health/ph_risk/documents/synth_report.pdf
34
35
36
37
38 Sharma, AK, Schmidt, B, Frandsen, H, Jacobsen, NR, Larsen, EH, Binderup, ML. 2010.
39
40 Genotoxicity of unmodified and organo-modified montmorillonite. *Mutat Res Genet*
41
42 *Toxicol Environ Mutagen*. 700:18-25.
43
44
45
46 Simon, P, Chaudhry, Q, Bakos, D. 2008. Migration of engineered nanoparticles from polymer
47
48 packaging to food - a physicochemical view. *J Food Nutr Res*. 47:105-113.
49
50
51
52 Sinclair, RG. 1996. The case for polylactic acid as a commodity packaging plastic. *J Macromol Sci-*
53
54 *Pure Appl Chem*. A33:585-597.
55
56
57
58 Sorrentino, A, Gorrasi, G, Vittoria, V. 2007. Potential perspectives of bio-nanocomposites for food
59
60 packaging applications. *Trends Food Sci Technol*. 18:84-95.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

United States Environmental Protection Agency. 1996. Method 3052 - Microwave assisted acid digestion of siliceous and organically based matrices. Washington (MD): USA.

US Food and Drug Administration. Title 21: Food and Drugs [Internet]. 2010. Silver Spring, (MD):US Food and Drug Administration; [Cited 2010 Nov 16] Available from: <http://www.accessdata.fda.gov/scripts/fcn/fcnDetailNavigation.cfm?rpt=iaListing&id=2751>

Zhang, Y, Zale, S, Sawyer, L, Bernstein, H. 1997. Effects of metal salts on poly(DL-lactide-co-glycolide) polymer hydrolysis. J Biomed Mat Res. 34:531-538.

List of Tables

Table 1. Description of L-poly lactide (PLA) and PLA/laurate-modified Mg-Al layered double hydroxide (PLA-LDH-C₁₂) based films.

Table 2. Molecular weights and polydispersity index (PDI) of L-poly lactide (PLA) films and PLA/laurate-modified Mg-Al layered double hydroxide (PLA-LDH-C₁₂) films before and after migration testing.

Table 3. Number-average molecular weight of each low molecular weight L-poly lactide oligomer (OLLA) peak and relative concentration factor of the combined oligomers (Peak 1 to Peak 3) in the migrates as determined by gel permeation chromatography analysis.

1
2
3
4
5 **Table 4.** Total migration and specific migration of components from PLA and PLA-LDH-C₁₂
6
7 nanocomposite materials
8
9

10
11 **List of figures:**
12

13
14
15
16 **Figure 1.** Gel permeation chromatograms of L-poly lactide (PLA) and PLA/laurate-modified
17
18 Mg-Al layered double hydroxide (PLA-LDH-C₁₂) films before (BM) and after (AM)
19
20 migration experiments: (a) PLA-PF, (b) PLA-PF1, (c) PLA-PF2, (d) PLA-PF3.
21
22

23
24
25
26 **Figure 2.** Gel permeation chromatography analyses of the raw migrates solutions. (a) Blank
27
28 food simulant, (b) PLA-PF, (c) PLA-PF1, (d) PLA-PF2 and (e) PLA-PF3.
29
30

31
32
33 **Figure 3:** Electron photomicrographs of: (a) LDH-C₁₂ in SEM and TEM photomicrographs of
34
35 migrates from (b) PLA-PF, (c) PLA-PF1, (d) PLA-PF2, (e) PLA-PF3 and (f) PLA-
36
37 PF3.
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

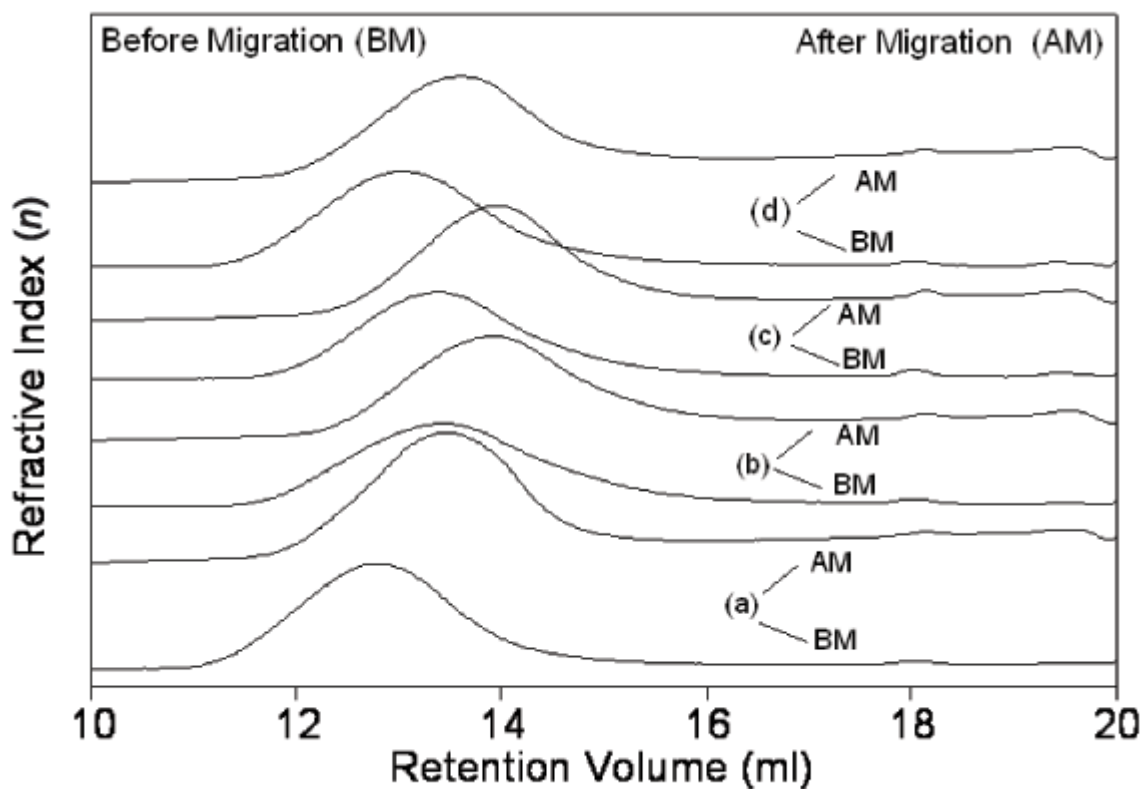


Figure 1. Gel permeation chromatograms of L-poly(lactide) (PLA) and PLA/laurate-modified Mg-Al layered double hydroxide (PLA-LDH-C₁₂) films before (BM) and after (AM) migration experiments: (a) PLA-PF, (b) PLA-PF1, (c) PLA-PF2, (d) PLA-PF3.







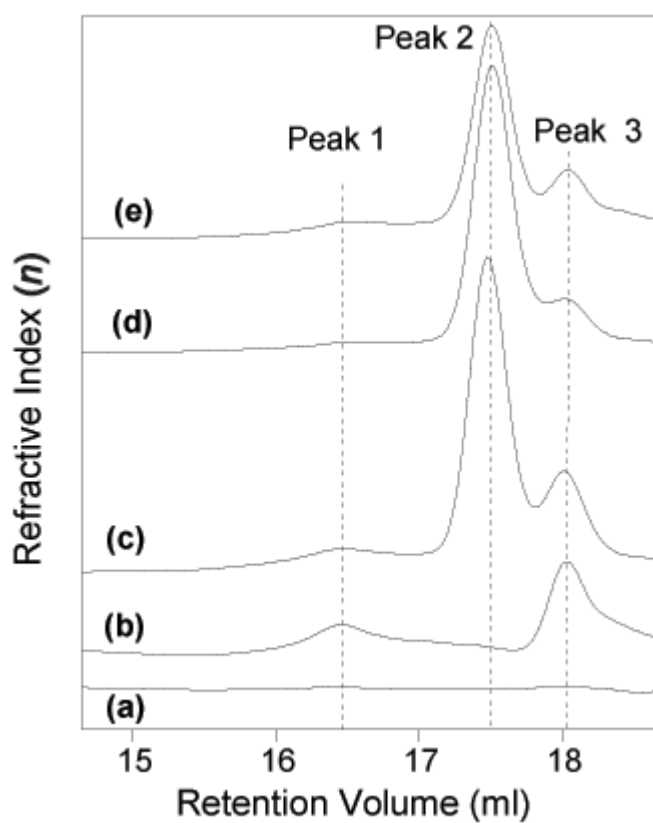


Figure 2. Gel permeation chromatography analyses of the raw migrates solutions. (a) Blank food simulant, (b) PLA-PF, (c) PLA-PF1, (d) PLA-PF2 and (e) PLA-PF3.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

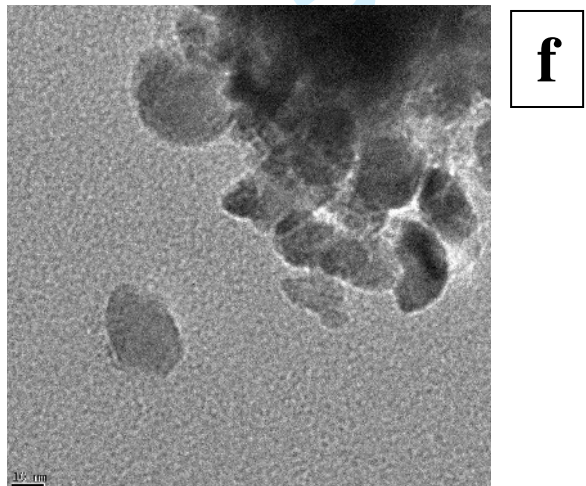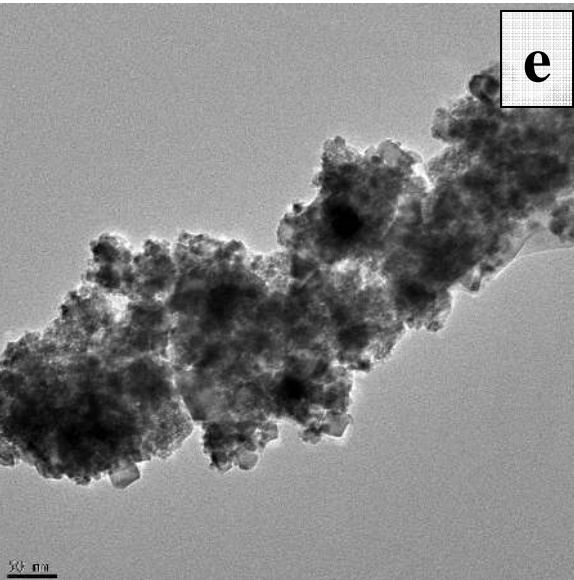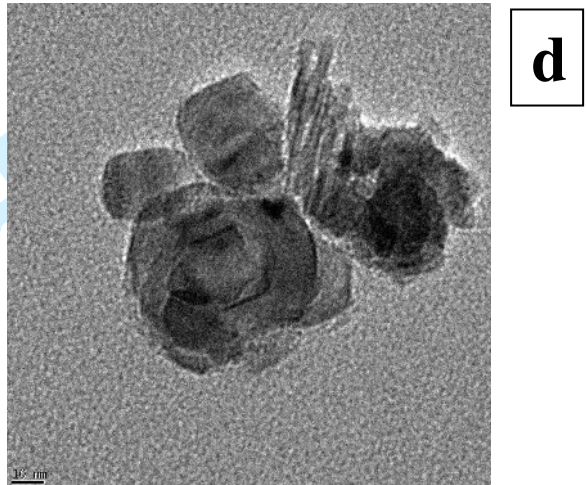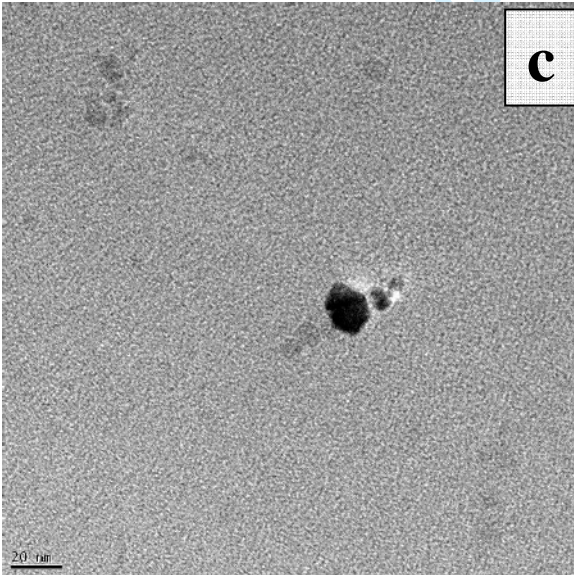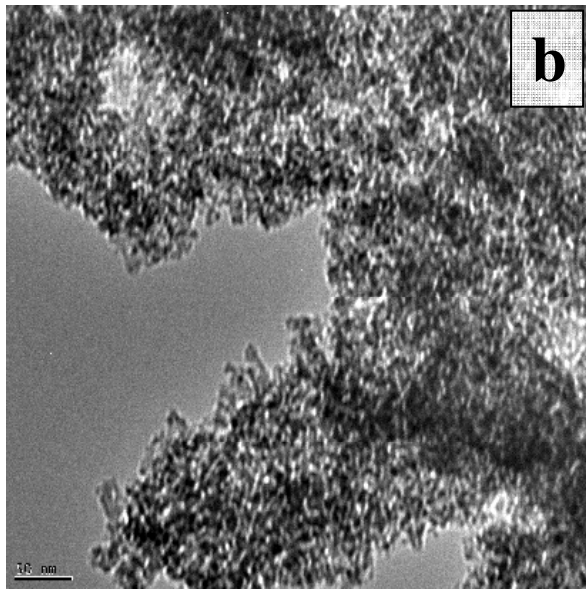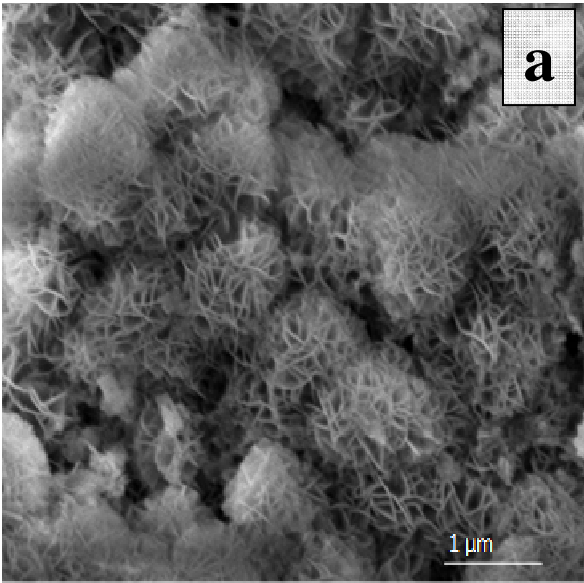

1
2
3
4
5
6
7 Figure 3. Electron photomicrographs of: (a) LDH-C₁₂ in SEM and TEM photomicrographs of
8
9 migrates from: (b) PLA-PF, (c) PLA-PF1, (d) PLA-PF2, (e) PLA-PF3 and (f) PLA-PF3.
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Peer Review Only

Table 1. Description of L-poly lactide (PLA) and PLA/laurate-modified Mg-Al layered double hydroxide (PLA-LDH-C₁₂) based films.

Film name	LDH-C ₁₂ loading in film	Description
PLA-PF	-	Film from pellets produced by extrusion of NatureWorks® PLA granulates
PLA-PF1	1.8 %	Film from extruded pellets, consisting of PLA granulates and 5.3 % LDH-C ₁₂ . Pellets were diluted x3 with PLA granulates to prepare final LDH-C ₁₂ 1.8 % loading.
PLA-PF2	5.5 %	Film from extruded pellets, consisting of PLA granulates and 10% of a 50%PLA/50% LDH-C ₁₂ masterbatch
PLA-PF3	1.8 %	Film from extruded pellets, consisting of PLA granulates and 10% of a 50%PLA/50% LDH-C ₁₂ masterbatch which was diluted 3 times with PLA granulates

Table 2. Molecular weights and polydispersity index (PDI) of L-poly lactide (PLA) films and PLA/laurate-modified Mg-Al layered double hydroxide (PLA-LDH-C₁₂) films before and after migration testing.

Film	M _w (Da)	M _n (Da)	PDI	M _w (Da)	M _n (Da)	PDI	% Change in M _n
	Films before migration test			Films after migration test			(during the test period)
PLA-PF	182,800	107,100	1.7	160,700	81,500	2.0	24
PLA-PF1	116,800	55,400	2.1	118,900	34,100	2.5	38
PLA-PF2	108,400	61,900	1.8	83,300	38,100	2.0	38
PLA-PF3	151,600	90,100	1.7	125,700	57,800	2.2	36

Table 3. Number-average molecular weight of each low molecular weight L-poly lactide oligomer (OLLA) peak and relative concentration factor of the combined oligomers (Peak 1 to Peak 3) in the migrates as determined by gel permeation chromatography analysis.

Film	Peak 1 M_n (Da)	Peak 2 M_n (Da)	Peak 3 M_n (Da)	Relative concentration factor of OLLA
PLA-PF	3,000	Not Detected	900	1
PLA-PF1	3,600	1,400	1,100	2.0
PLA-PF2	Not Detected	1,300	1,000	3.2
PLA-PF3	3,600	1,600	1,000	1.4

Table 4. Total migration and specific migration of components from PLA and PLA-LDH-C₁₂ nanocomposite materials

Sample	Total Migration (mg/dm ²)	Laurate Migration (mg/dm ²)	LDH Migration ^a (mg/dm ²)	Tin Migration (mg/dm ²)
PLA-PF	2.5±0.6	<0.2	<0.1	<0.0001
PLA-PF1	9.6±1.9	3.4±0.3	0.2±0.1	<0.0001
PLA-PF2	31.9±7.4	8.8±1.0	2.2±0.1	0.0025±0.0002
PLA-PF3	8.3±0.8	2.6±0.2	1.0±0.1	0.0008±0.0001
Spike	5.2±0.2	0.2	4.0±0.4	<0.0001

^aReported as LDH-C₁₂.