

MODELING OF MULTISCALE AND MULTIPHASE PHENOMENA IN MATERIAL PROCESSING

Andreas Ludwig, Abdellah Kharicha, Menghuai Wu

University of Leoben, Department Metallurgy,
Franz-Josef-Strasse 18, 8200 Leoben, Austria

Keywords: Material Processing, Modeling, Multiphase Phenomena

Abstract

In order to demonstrate how CFD can help scientists and engineers to better understand the fundamentals of engineering processes, a number of examples are shown and discussed. The paper will cover (i) special aspects of continuous casting of steel including turbulence, motion and entrapment of non-metallic inclusions, and impact of softreduction; (ii) multiple flow phenomena and multiscale aspects during casting of large ingots including flow induced columnar-to-equiaxed transition and 3D formation of channel segregation; (iii) multiphase magneto hydrodynamics during electro-slag remelting; and (iv) melt flow and solidification of thin but large centrifugal castings.

Introduction

Since the Bronze and the Iron Ages, material processing, and here especially metallurgy, has got a global importance for the economic well-being of the societies. It is thus understandable that metallurgy has changed from arts and crafts into an engineering specialty, where the knowledge of centuries has lead to an enormous commercial and technical efficiency. However, increasing competition and the necessitation of energy and CO₂ reduced manufacturing methods requires the improvement of existing techniques and even the development of new, alternative production technologies. On the other hand, the opacity of liquid and solid materials and the involved high temperatures makes the experimental penetration of metallurgical processes and with that the attainment of detailed process knowledge quite difficult.

Here, numerical process simulations put us in a position to zoom into process details and learn more about procedures that happens inside the product during its production. Since around four decades, numerical descriptions of nearly all production processes has come up and with time the impression is conveyed that nowadays the existing simulation tools are able to answer nearly all our questions. However, people who are dialing everyday with computer simulations know that the forecast ability of a numerical tool depends highly on the underlying physical model. If a certain phenomenon is not described properly in the program, the numerical tool can not give sound predictions on its consequences. Therefore, it is important to know the origin of the observation made in praxis and to create model descriptions capturing the involved physics.

In the present paper, we will take a look on four different metallurgical processes and discuss the present edge of ability of its numerical simulation, namely (i) Continuous and DC casting; (ii) ingot casting; (iii) eletro-slag remelting and (iv) centrifugal casting. We apologize of not being able to quote all groups who have contributed to the state of the art. The fact that the field is not easy to survey becomes obvious by taking a look on the program of the Int. Conf. METEC-

InSteelCon 2011 which comprises itself four different international conferences relevant for steelmaking [1] not to mention of corresponding conferences for Cu- and Al-based or other alloys.

Modeling Examples

Aspects of Continuous and DC Casting

After secondary metallurgical treatment in different aggregates (e.g. VD, VOD, AOD, and RH) the liquid metal is poured from the ladle into the tundish, from where it flows through the submerged entry nozzle into the casting mold. Here it starts to solidify most often in form of equiaxed and columnar dendritic crystals. During solidification and due to intensive cooling the strand (billet, bloom, or slab) contracts. The interplay of mechanical guidance, thermal contraction and metallostatic pressure leads to the typical deformation history which might often lead to unacceptable quality problems.

All of the process steps mentioned above are nowadays subject to numerical simulation, whereby pure flow simulation even when turbulence and temperature changes are considered must be seen as standard. Challenging topics arise when different phenomena interact as

- liquid metal flow and gas bubble motion especially in turbulent regimes;
- formation and motion of non-metallic inclusions and their interplay with refractory materials, gas bubbles, turbulent eddies and entrapment/engulfment into the solidifying shell;
- flow and solidification especially interdendritic flow and turbulence damping;
- microstructure formation and its dependence on grain motion and melt flow;
- natural buoyancy caused by cooling and solidification-induced compositional heterogeneity (segregation);
- flow, solidification and deformation which might cause the occurrence of hot cracking;
- creep and viscoplastic material behavior in the two-phase region.

Most advance research groups are currently working on the topics listed above [2]-[21]. Whereby, very often model formulations for simple academic case are suggested where measurements on an idealized system might exist. However, the application to real and complex industrial situations are much more challenging and fail often due to the lack of reasonable materials properties (as interface tensions, solutal expansion coefficients, melt viscosities especially in mushy regions etc.) or unknown intrinsic process details (as permeability of dendritic mushy zones; solid fraction evolution in the presence of local melt flow etc.). Also, available computer resources are often a hindrance to the application of suitable models to real process applications.

An example of a process where turbulent melt-flow, dendritic solidification and local contraction and deformation interact is thin slab casting of steel (see Fig. 1). In standard continuous casting of steel the turbulent melt flow from the SEN into the mold region is quite separated from the formation of the solid shell. Even isothermal flow studies of mold regions are often thought to represent the industrial reality and so water models are used to get experimental details. However, sophisticated modeling approaches have demonstrated that the existence of the solidifying shell may change the overall flow pattern in the mold region [6]. In the quoted work it was also shown that Argon gas which might be used to constantly purge the SEN and thus to prevent clogging may also affect the flow pattern in the mold region.

When it comes to the description of the interaction between turbulent melt-flow and dendritic solidification it has to be stated that no physically sound model has been suggested yet. Although the importance of melt flow for the formation of a dendritic mushy zone has been outlined [7] only oversimplified approaches are in use [8]. A similar statement must be made for the description of dendritic solidification and particle entrapment during continuous casting of steel [9]-[12]. Although turbulent particle dispersion in the mold region is accounted for [6] and a force balance at the dendrite tips decides on particle pushing or engulfment, the results are still questionable [9]. The reason for a necessary scepticism is the fact that the largest force in the model might exist for liquid inclusions only and not for the much more common solid inclusions.

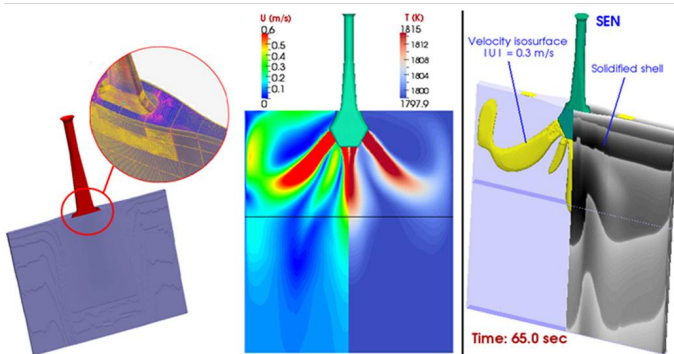


Figure 1. 3D modeling of thin slab casting (from left to right: solid shell and grid detail in the funnel area; flow and temperature fields in the mid plane; isosurface of velocity together with the solidified shell (taken from [11])

Another example for a complex interaction of different phenomena is the occurrence of centerline segregation in steel strands. While a strand solidifies from outside inwards its core remains liquid or at least mushy for quite a long time. As thermal and solidification-induced shrinkage has to be compensated by feeding with melt and as metallostatic pressure leads to bulging of the solidified outer shell, complex flow phenomena inside the strand leads to a macroscopic redistribution of alloying elements. In order to describe this phenomenon shell mechanics have to be combined with two phase flow descriptions inside the solidifying strand core. For this topic only simplifying descriptions exist. The authors' group studied the shrinkage flow induced macrosegregation in continuous casting of steel without considering of shell bulging [13]. They predicted negative centerline segregation. Then in a series of publication, it was demonstrated that with considering both shrinkage-induced feeding flow and bulging-induced core flow the centerline segregation will become positive [14]-[18]. Fig. 2 shows how the local flow field in the two-phase core of the solidifying strand may result in the formation of positive centreline segregation [19]-[21]. In [21] it is discussed how mechanical softreduction might be usable to reduce positive centreline segregation.

In DC casting of Cu- or Al-based alloys advanced simulation efforts focus on the prediction of macrosegregation in ternary systems for pure columnar solidifying strands [22]-[28]. The formation of macrosegregation in the mixed columnar and equiaxed solidifying case is still subject of future challenges. Another interesting fluid-structure interaction type topic is the interaction of a flexible combo bag with the flow in a DC Aluminium Casting [29].

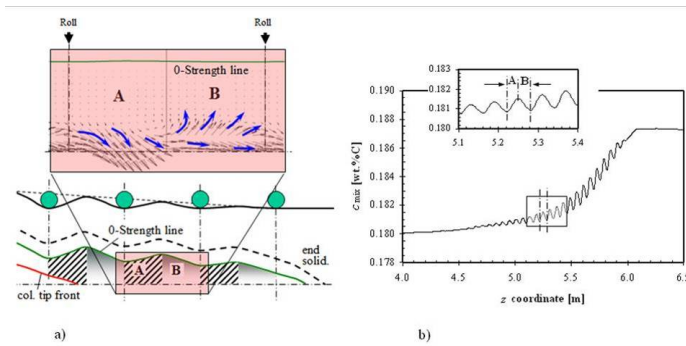


Figure 2. Local flow field in the two-phase core of a solidifying steel strand and the resulting formation of positive centerline segregation (taken from [19])

Aspects of Big Ingot Casting

Although most steel products were nowadays produced with continuous casting processes, large steel ingots are still required for manufacturing electric power plant turbine shafts, generator rotor shafts, nuclear pressure vessels, chemical pressure vessels, ship parts and other heavy machinery parts. Knowledge for producing steel ingots was mainly gained in last century [30]-[34], but the problems which haunted foundrymen for decades were still not be solved, even not fully understood, namely:

- formation of A- and V- macrosegregation;
- formation of the typical as-cast structure (columnar-to-equiaxed transition: CET);
- motion and engulfment of non-metallic inclusions;
- occurrence of hot tearing in extremely large ingots; etc.

The cost of full-scale trials was so high that people had to think of developing theoretical models of the formation of segregations in ingots [32]-[35]. Therefore, a series of modelling activities were carried out in the authors' group. A 3-phase model was developed for mixed columnar-equiaxed solidification in ingot casting [36]-[37]. A volume averaging concept was taken to allow the modelling approach to be applicable for the solidification of ingot casting at the process scale [37]-[40]. Thermodynamics was coupled with the solidification kinetics to consider the multi-component alloy system [41]-[47]. Very recently, the dendritic, multiscale feature of the solidifying crystals was also taken into account in the model [48]-[53]. In the mean time, the modelling approach was applied to study the formation mechanism of macrosegregation [54] and the as-cast structure including CET [55].

An example of 3-phase modeling result of a laboratory benchmark ingot is given in Fig. 3. It shows the solidification sequence, including sedimentation of the globular equiaxed grains, the sedimentation-induced and thermo-solutal buoyancy-induced melt convection. The columnar dendrites grow from the mold wall and the columnar tip front moves inwards. The equiaxed

grains nucleate near the mold walls and in the bulk melt. The columnar dendrites are stationary, whereas the equiaxed grains sink and settle in the base of the ingot. The accumulation of such grains at the base of the ingot has a characteristic cone-shape. The sedimentation of grains and the melt convection influence the macroscopic solidification sequence and thus, the final phase distribution. More equiaxed grains will be found at the bottom and in the base region, while columnar solidification will be predominant in the upper part of the ingot. As the columnar tip front is explicitly tracked, the simulation shows that the columnar tip fronts from both sides tend to meet in the casting center. However, in the lower part of the casting the large amount of equiaxed grains stops the propagation of the columnar tip front. Its final position indicates the CET position. The CET separates areas where only equiaxed grains appear from areas where both columnar dendrites and equiaxed grains might occur side-by-side.

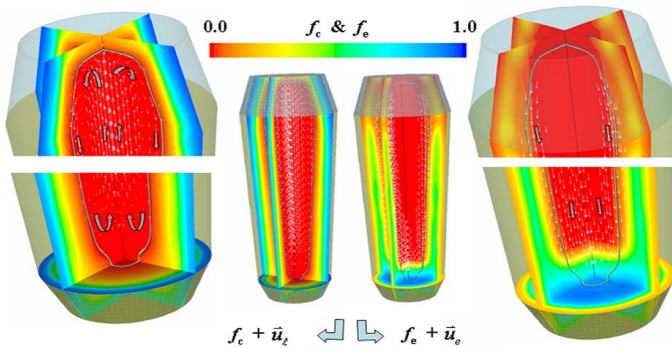


Figure 3. Simulated solidification sequence (at 20 s) of a laboratory steel ingot. The volume fraction of the columnar and equiaxed phases, f_c and f_e , are shown in color in two vertical and one horizontal sections, the velocity fields of the liquid melt and the settling equiaxed grains, \bar{u}_l and \bar{u}_g , are shown as vectors. The columnar tip front position is also shown.

A two-phase columnar solidification model was used to study the formation mechanism of the channel segregation in a Sn-10 wt.% Pb benchmark ingot, as shown in Fig. 4. The two phases considered in the current model are the melt and columnar phase. Transient development of flow channels during solidification can be numerically ‘visualized’. The iso-surface of liquid volume fraction $f_l = 0.35$ is plotted and reveal the 3D nature of the channels. They are discontinuous and lamellar-structured and originate from the region adjacent to the cooling wall, from which they develop with a certain angle (about 40 - 60 degrees to the horizontal plane). The channel spacing (distance between neighboring channels) is almost constant, or slightly adjusted with time during solidification. It is verified by the current model that remelting is not a necessary condition for the formation of channel segregation. Although remelting is not included in the current simulation benchmark, the channel segregation still appears.

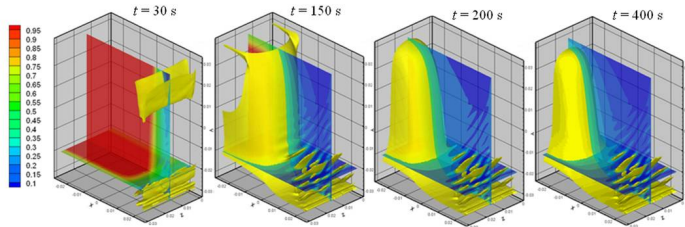


Figure 4. Predicted 3D solidification sequence in a Sn-10 wt.% Pb benchmark ingot, from (a) 30 s to (d) 400 s. The liquid volume fraction in two planes (a vertical central plane and a horizontal plane with a distance of 0.01 m from the bottom) is shown by using a color scale. In addition the iso-surface of liquid volume fraction $f_l = 0.35$ is shown to demonstrate the formation sequence of flow channels

Aspects of Electro-Slag Remelting

In the past few years, remelting technologies have taken an important role in the large field of special materials and the number of Electro-Slag Remelting (ESR) and Vacuum Arc Remelting (VAR) units is continuing to grow. In the ESR process an as-casted electrode is immersed into a hot slag such that droplets depart from the melting electrode, pass through the turbulently flowing slag and finally feed a liquid metal pool which then solidify directed. Hereby, a high electric current heats up the slag by Joule heating. In the VAR process the gap between electrode and the pool is put under metallurgical vacuum and the high current create one arc or several arcs between the electrode and the pool, which then cause a continuous melt flow to occur. Nowadays, ESR and VAR are commonly in use. However far-reaching investigations on an industrial scale in particular have rarely been published. There is still a great demand for more knowledge on these processes and how to optimize them for several alloys qualities, melting parameters and ingot sizes. To produce a high quality homogeneous ingot with good surface quality, the deviations in the process, such as melting rate or the immersion depth of the electrode need to be minimized.

During the process the electric parameters such as current, voltage and electric resistance are continuously recorded. The variation of the resistance, known as resistance swing, is often used for the control of the electrode position [56]. Higher level of resistance swing is interpreted as a low electrode immersion depth. However, the increase in resistance swing can be reliably, but not quantitatively, related with the immersion depth. This is why some efforts must be applied to the identification of the process state, solely through analysis of electric process parameters. To achieve this goal it is important to identify the phenomena that can generate these electric fluctuations. Assuming that most of the resistance is generated within the slag cap, our analysis focused on the possible paths that the electric current can take through this region. The slag region experiences strong flow turbulence that can induce locally strong temperature fluctuations. Large and fast fluctuations of the resistance can only be generated by modifying the shape of the slag cap. The solid slag that develops at the mould (referred as slag skin) is a boundary that was considered for a long time as an electric insulator [57]-[58]. Recent experimental and numerical investigations on static mould ESR have shown that typically 20% (but up to 80 %) of the total

current can cross the solid slag layer to enter directly into the mould [59]-[60]. The ratio mould current over the vertical current depends on two factors. First on the ratio between the electrode-mould radial distance and the slag cap height and second on the ratio between liquid slag and slag skin electric conductivities.

This process involves two liquids, a liquid metal and a liquid slag. Each liquid is subject to a phase change due to melting and/or solidification. From a fluid dynamic point of view, the ESR process is clearly a multiphase process, with free interfaces (slag/pool, gas/slag), and with a mixed area (slag and falling steel droplets) [59]-[67]. And, as the electric conductivity of the metal is known to be much higher than that of the slag, the distribution of the metallic phase within the slag will be a critical parameter to predict the distribution of the electric current density which in turn controls the Lorentz force magnitude. From these physical facts, one can expect in this nonlinear system a slight change in the position of the interfaces in the slag can result in totally different flow behavior. Physically, the development of the heat and mass transfer at the interfaces is important for the final ingot quality, composition and cleanliness. Unfortunately a visual observation of the droplet formation and interface movement is almost impossible.

To explore numerically the process, it is necessary to model the strong coupling between the flow and the electrodynamic phenomena. This typical Magnetohydrodynamic problem was tackled with the help of a 3D MHD-VOF model which is able to predict the electric and magnetic field distribution in function of the metallic distribution in the low electric conductivity slag. As shown in Fig. 5 and 6 it is nowadays possible to virtually see the melting phenomena for small and even for large scale ESR process.

In small scale the droplet formation occurs only at the center. At larger scale the liquid film that develops under the electrode allows droplets departure from many different positions. The way that the liquid metal droplets enter the liquid pool is one major factor which determines the liquid pool shape and depth. The reason why at small scale the dripping occurs in the middle lies on the ratio between the Lorentz force and the buoyancy forces. The Lorentz force acts mainly in the inward direction towards the center, while buoyancy results in a flow which is outwards towards the mould. The Lorentz force being larger in small ESR, the liquid metal film under the electrode has the tendency to accumulate at the center of the electrode. At larger scale, the Lorentz force is not strong enough to oppose the turbulent movement of the hot slag under the electrode. However the combined effects of the droplets impacts and Lorentz force is strong enough to generate a three dimensional wavy movement of the slag/pool interface. This movement generates a strong 3D movement of the flow in the liquid pool but also in the slag. This 3D movement was clearly observed on the surface of the exposed slag in industrial plant. Models that use 2D axisymmetric approximation can only predict radially inward or outward motion at the exposed slag surface. This first success in modeling is only a first step towards the full understanding of the multiphysics phenomena that occur in this process. In the future the following questions needs to be investigated:

- How axisymmetric is the system, especially the electric current and liquid flow? How does the symmetry affect the solidification? In previous 3D investigations the current was not allowed to cross the solid slag skin. Thus how will the system behave if the current is left free? A breaking of the global axial symmetry of the current path might occur at the lateral mold wall;
- Mechanisms of removal of non-metallic inclusion. How important is the effects of the electromagnetic Lorentz force?

- Melting tip of the electrode, flat or conical depends on the exact thermal and hydrodynamic conditions occurring in the slag;
- Development and evolution of the liquid film under the electrode and how it is related to the droplet transfer to the liquid pool;
- Formation of the solid shell just under the slag/pool interface, which can generate bad in-got surface quality.

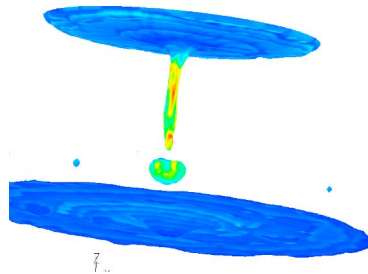


Figure 5. Electric current density in a small scale ESR color scaled from blue to red [10^5 - 10^{10} Amps/m²]. A current of 3000 Amps is passed through an electrode of 13 cm diameter.

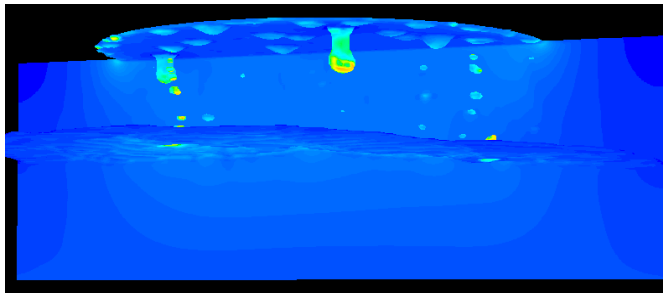


Figure 6. Electric current density in a large scale ESR color scaled from blue to red [10^4 - 10^8 Amps/m²]. A current of 13000 Amps is passed through an electrode of now 42 cm diameter. [67].

Aspects of Centrifugal Casting

The horizontal spin casting process (HSC) is a casting process that has generally several advantages above a traditional gravity casting process and also some other casting processes. The main profit is usually superior mechanical properties [68]-[72]. Centrifugally cast products have a high degree of metallurgical purity and homogeneous microstructure. A significant gain is observed for the rupture strength, the rupture strain, and for the Young modulus. These properties natu-

rally depend on the centrifugal force and thus, the higher the distance from the rotation center, the better the increase in mechanical properties.

Since the centrifugal force is defined as the product of the radius and the square of the angular frequency, the final mechanical properties mostly depend on the selection of the angular frequency. The proper selection of the angular frequency has to be done in order to prevent so-called raining on one hand i.e. metal droplets can fall down from the upper part of the inside surface of the casting product due to the low centrifugal acceleration and the winning counteracting action of the gravity. On the other hand, excessive speeds can, however, lead to the longitudinal cracks caused by the hoop stress in the initially solidified layer.

During horizontal spin casting of rolls, vibrations and mould deformations seems to have a significant effect on the final quality of the product [68]-[69]. There are several physical sources of vibrations that can be found. First, it is a poor roundness and a static imbalance of the chill itself. Secondly, those are free vibrations linked with natural frequencies of the rotating mould being subject to strong thermomechanical deformation, and to combined action of the centrifugal and Coriolis stresses.

In order to explore those effects, a 2D shallow layer model was built to simulate the hydrodynamic behaviour of a liquid metal layer over a inner surface of a rotating cylinder. A parabolic velocity profile is considered with maximum velocity on the free surface and zero velocity on the wall. Due to a high angular frequency Ω the liquid is mainly rotating with the mould; therefore, the model is defined in the rotating frame of reference. We introduce sine-like vibrations in the radial and tangential directions generated by a small default roundness of the mould. The possible occurrence of the bending of the mould axis is also considered. The introduction of bending and vibrations in the model induces a strong modification in the mathematical expression of the fictitious forces such as the centrifugal and the Coriolis forces. In opposite to a perfectly round and aligned mould, these forces are position and time dependant. They are able to generate unexpected flow movements and waves. Typical liquid flow velocities (relative to the rotating mould) reach values as large as 1 m/s. The waves dynamic was found to be very complex (Figure 7), it can take up to a minute before the bifurcation of the system to a steady chaotic state occurs. Although the vibrations were assumed to act only in the radial and tangential directions, the system gave rise to waves mainly propagating in the axial direction. The origin of this phenomenon is probably related to rotational property of the Coriolis force, the latest redirects the kinetic energy in a perpendicular direction. The velocity magnitude generated by these vibrations is strong enough to be able to fragment and transports relatively large solidified crystals far from the region where they originally nucleated [70].

In the future a 3 shallow layers approach will be used to simulate the solidification process. It will include the liquid region, a semi-liquid semi-solid granular layer, and a totally solidified layer. The equations of heat transfer, phase change, and the equation motion of the granular region will be added to the present model.

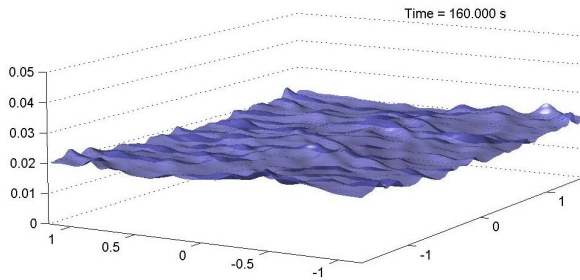


Figure 7. Developed flow regime for a liquid layer exposed to centrifugal force, Coriolis force, gravity, friction force, and vibrations for 20 mm liquid height and 30 rad/s angular frequency of the mould.

Conclusions

In material processing numerical modeling tools are more and more in use. Temperature and flow field predictions are nowadays quite reliable. However, the multiphase and multiscale nature of many industrial processes often limits the predictive efficiency even of the most sophisticated programs. With the help of four examples, we have demonstrated that sound predictions of important process details are only possible if the involved physics are modeled adequately. Especially when different phenomena interact, like e.g. flow, solidification, and stress-induced deformations or motion of dendritic crystal in a turbulent melt flow, our knowledge is still limited. Nowadays it is true that a successful extension of a numerical code is quite often accompanied by an increase of knowledge on important process details and vice versa.

Acknowledgements

The authors are grateful for financial support over the years by Böhler Edelstahl, Elektrowerke Sulzer Werfen, RHI Technologies, Siemens-VAI, Voestalpine Stahl Donawitz, Voestalpine Stahl Linz, Wieland Werke as well as the public agencies Christian-Doppler Society and FFG. We also acknowledge contributions from the present and former staff members Bohacek, Domitner, Eck, Grasser, Hao, Ishmurzin, Könözy, Li, Mayer, Nunner, Pfeiler, and Vakhrushev.

References

- [1] <http://www.metec-insteelcon2011.com/>
- [2] Thomas B.G., *Brimacombe Lecture, 59th Electric Furnace Conf., Phoenix, AZ, (2001)*, Iron & Steel Soc., pp.3.
- [3] Thomas B.G., *Chapter 15 - Continuous casting, in Modeling for Casting and Solidification Processes*, ed. Yu K-O., New York: Marcel Dekker, Inc., (2002), pp.499.
- [4] Thomas B.G., Yuan Q., Zhao B. and Vanka S., *JOM-e.*, 58, (2006), pp.16.
- [5] Koric S., Hibbeler L.C., Thomas B.G., *Int. J. Numer. Meth. Engng.*, 78, (2009), pp. 1.

- [6] C. Pfeiler, "Modeling of Turbulent Particle/Gas Dispersion in the Mold Region and Particle Entrapment into the Solid Shell of a Steel Continuous Caster" (Ph.D. thesis, University of Leoben, 2008).
- [7] M. Wu, A. Vakhrushev, G. Nunner, C. Pfeiler, A. Kharicha, A. Ludwig, *Open Transp. Phenomena J.*, 2 (2010), 16-23.
- [8] A. Vakhrushev, A. Ludwig, M. Wu, Y. Tang, G. Nitzl, G. Hackl, (4rd Int. Conf. Simulation and Modeling in Metallurgical Processes in Steelmaking, Düsseldorf, Germany, 2011), 17.1-8.
- [9] C. Pfeiler, B.G. Thomas, M. Wu, A. Ludwig, A. Kharicha, *Steel Research Int.*, 79(8) (2008), 599-607.
- [10] C. Pfeiler, B.G. Thomas, A. Ludwig, M. Wu, (2nd Int. Conf. on Simulation & Modeling of Metall. Processes in Steelmaking, Graz, Austria, 2007, Ed.: A. Ludwig), 247-52.
- [11] A. Vakhrushev, A. Ludwig, M. Wu, Y. Tang, G. Nitzl, G. Hackl, (European Continuous Casting Conference, Düsseldorf, Germany, 2011), 18.1-10.
- [12] A. Vakhrushev, A. Ludwig, M. Wu, Y. Tang, G. Nitzl, G. Hackl, (Open Source CFD Int. Conf. 2010, Munich, Germany, 2010), S:VI-B:T3:1-17.
- [13] F. Mayer, M. Gruber-Pretzler, M. Wu, A. Ludwig, (2nd Int. Conf. of Simulation & Modeling of Metall. Processes in Steelmaking, Graz, Austria, 2007, Ed.: A. Ludwig), 265-270.
- [14] F. Mayer, M. Wu, A. Ludwig, (12th Int. Conf. Modeling of Casting, Welding, Adv. Solidification Processes, Vancouver, Canada, Eds. S.L. Cockcroft et al 2009), 279-86.
- [15] F. Mayer, M. Wu, A. Ludwig, (3rd Int. Conf. Simulation and Modeling in Metallurgical Processes in Steelmaking, Leoben, Austria, 2009, Ed. A. Ludwig) 247-52.
- [16] F. Mayer, M. Wu, A. Ludwig, *Steel Research Int.* 81 (2010), 660-7.
- [17] M. Wu, A. Ludwig, C. Pfeiler, F. Mayer, (4th Int. Conf. on Continuous Casting of Steel in Developing Countries, Beijing, China, 2008), 30-7.
- [18] M. Wu, A. Ludwig, C. Pfeiler, F. Mayer, *J. of Iron and Steel Res. Int.* 15 (2008), 30-7.
- [19] M. Wu, J. Domitner, A. Ludwig, F. Mayer, (4rd Int. Conf. Simulation and Modeling in Metallurgical Processes in Steelmaking, Düsseldorf, Germany, 2011), S4.1-11.
- [20] J. Domitner, M. Wu, F. Mayer, A. Ludwig, B. Kaufmann, J. Reiter, T. Schaden, (7th European Continuous Casting Conference, Düsseldorf, Germany, 2011), S6.1-8.
- [21] M. Wu, J. Domitner, A. Ludwig, *Metall. Mater. Trans. A*, in press: DOI 10.1007/s11661-0940-4.
- [22] M. Gruber-Pretzler, M. Wu, A. Ludwig, J. Riedle, U. Hofmann, (Proc. COM/Cu2007, Canada, I, eds. J. Hugens et al, Canadian Inst. of Mining, Metallurgy and Petroleum 2007), .265-79.
- [23] M. Gruber-Pretzler, (Ph.D. thesis, University of Leoben, Austria, 2008).
- [24] M. Grasser, A. Ishmurzin, F. Mayer, M. Wu, A. Ludwig, U. Hofmann, J. Riedle, (12th Int. Conf. Modeling of Casting, Welding, Adv. Solidification Processes, Vancouver, Canada, 2009, Eds: S.L. Cockcroft et al), 221-8.
- [25] A. Eck, C. Pfeiler, A. Kharicha, A. Ludwig, J.W. Evans, (TMS Annual Meeting, proc. book "Materials Processing Fundamentals", 2009), 221-228.
- [26] J. Hao, M. Grasser, A. Ishmurzin, M. Wu, A. Ludwig, J. Riedle, R. Eberle, (Copper 2010, Hamburg, Germany 2010), 65-80.
- [27] J. Hao, M. Grasser, M. Wu, A. Ludwig, *Adv. Materials Research*, 154-5 (2011) 1401-4.
- [28] J. Hao, M. Wu, A. Ludwig, M. Grasser, *Adv. Materials Research*, 154-5 (2011), 1415-8.
- [29] A. Kharicha, A. Ludwig, M. Wu, (DGM Symposium Strangiessen 2010, ed. H.R. Müller) supplement
- [30] "Report on the heterogeneity of steel ingots", *J. Iron Steel Inst.*, 1003, (1926), pp.39.
- [31] J.J. Moore and N.A. Shah, *Int. Metals Rev.*, 28, (1983), pp.338.

- [32] M.C. Flemings, *ISIJ Int.*, 40, (2000), pp. 833.
- [33] C. Beckermann, *Int. Mater. Rev.*, 47, (2002), pp. 1.
- [34] G. Lesoult, *Mater. Sci. Eng. A*, 413-414 (2005), 19.
- [35] H. Combeau, M. Zaloznik, S. Hand, P.E. Richy, *Metall. Mater. Trans.* 40B (2009), 289-304.
- [36] M. Wu, A. Ludwig, *Metall. Mater. Trans.* 37A (2006), 1613-31.
- [37] M. Wu, A. Ludwig, *Metall. Mater. Trans.* 38A (2006), 1465-75.
- [38] M. Wu, A. Ludwig, (11th Int. Conf. on "Modeling of Casting, Welding and Advanced Solidification Processes, Opio, France, 2006, Eds. C.A. Gandin et al), 291-298.
- [39] M. Wu, L. Könözy, A. Fjeld, A. Ludwig: (7th Pacific Rim Int. Conf. Modeling of Casting & Solidification Processes, Dalian, China, 2007. Eds. J-Z. Jin et al), 379-87.
- [40] M. Wu, L. Könözy, A. Fjeld, A. Ludwig, (2nd Int. Conf. Simu & Mod. of Metall. Processes in Steelmaking, Graz, Austria, 2007. Ed. A. Ludwig), 114-9.
- [41] A. Ishmurzin, M. Gruber-Pretzler, F. Mayer, M. Wu, A. Ludwig, *Int. J. Mat. Res.* 99 (2008), 618-25.
- [42] A. Ludwig, A. Ishmurzin, M. Gruber-Pretzler, F. Mayer, M. Wu, R. Tanzer and W. Schützenhöfer, (5th Dec. Int. Conf. on Solidification Processing, Sheffield, UK. Ed.: H. Jones 2007), 493-6.
- [43] A. Ishmurzin, "Modeling and Simulation of Solidification of High Steel Ingot Castings" (Ph.D. thesis, University of Leoben, Austria, 2009).
- [44] L. Könözy, F. Mayer, A. Ishmurzin, M. Wu, A. Ludwig, R. Tanzer, W. Schützenhöfer, 2nd Int. Conf. Simu. & Mod. of Metall. Proc. in Steelmaking, Graz, Austria, 2007, Ed. A. Ludwig), 126-32.
- [45] L. Könözy, A. Ishmurzin, F. Mayer, M. Grasser, M. Wu, A. Ludwig, *Int. J. Cast Metals Research* 22 (2009) 175-8.
- [46] R. Tanzer, W. Schützenhöfer, G. Reiter, H.-P. Fauland, L. Könözy, A. Ishmurzin, M. Wu, A. Ludwig, (Int. Symp. Liquid Metal Processing and Casting, Nancy, France, 2007, Eds. P.D. Lee et al), 121-6.
- [47] R. Tanzer, W. Schützenhöfer, G. Reiter, H.P. Fauland, L. Könözy, A. Ishmurzin, M. Wu, A. Ludwig, *Metall. Mater. Trans.* 40B (2009), 305-11.
- [48] M. Wu, A. Ludwig, *Acta Mater.*, 57 (2009), 5621-31.
- [49] M. Wu, A. Ludwig, *Acta Mater.*, 57 (2009) 5632-44.
- [50] M. Wu, A. Ludwig, *Int. J. Cast Metals Research*, 22 (2009) 323-7.
- [51] M. Wu, A. Ludwig, (12th Int. Conf. Modeling of Casting, Welding, Adv. Solidification Processes, Vancouver, Canada, 2009, Eds S.L. Cockcroft et al), 537-44.
- [52] M. Wu, A. Fjeld, A. Ludwig, *Comp. Mater. Sci.*, 50 (2010), 32-42.
- [53] M. Wu, A. Ludwig, A. Fjeld, *Comp. Mater. Sci.*, 50 (2010) 43-58.
- [54] M. Wu, L. Könözy, A. Ludwig, W. Schützenhöfer, R. Tanzer, *Steel Research Int.*, 79 (2008), 637-44.
- [55] L. Könözy, A. Ishmurzin, M. Grasser, M. Wu, A. Ludwig, R. Tanzer, W. Schützenhöfer, *Mater. Sci. Forum*, 649 (2010), 349-54.
- [56] D.K. Melgaard, R.L. Williamson, and J.J. Beaman, *JOM* (1998), 13-17.
- [57] B. Hernandez-Morales and A. Mitchell, *Ironmaking & Steelmaking*, 26(6) (1999), 423-438.
- [58] V. Weber, A. Jardy et al., *Metall Mater Trans.B.* 14 (2009)
- [59] A. Kharicha, W. Schützenhöfer, A. Ludwig, R. Tanzer, Wu M., *Int. J. Cast Metals Research*, 22 (2009), 155-9.
- [60] A. Kharicha, W. Schützenhöfer, A. Ludwig, R. Tanzer. *Steel Research Int.* 79 (8) (2008), 632-6.

- [61] A. Kharicha, W. Schützenhöfer, A. Ludwig, R. Tanzer, M. Wu, (2nd Int. Conf. of Simulation & Modeling of Metallurgical Processes in Steelmaking, Graz, Austria, 2007. Ed.: A. Ludwig,), 105-10.
- [62] A. Kharicha, A. Mackenbrock, A. Ludwig, W. Schützenhöfer, V. Maronnier, M. Wu, O. Köser, (Int. Symp. Liquid Metal Processing and Casting, Nancy, France. 2007, Eds. P.D. Lee et al), 107-13.
- [63] A. Kharicha, A. Mackenbrock, A. Ludwig, W. Schützenhöfer, V. Maronnier, M. Wu, O. Köser, R. Tanzer, (Int. Symp. Liquid Metal Processing and Casting, Nancy, France. 2007, Eds. P.D. Lee et al), 113-9.
- [64] Kharicha A., Ludwig A., Wu M., *Mater. Sci. Eng. A*, 413, (2005), 129-134.
- [65] A. Kharicha, W. Schützenhöfer, A. Ludwig, G. Reiter, *Mater. Sci. Forum* 649 (2010), 229-36.
- [66] Kharicha A., Ludwig A., Int. Conf. on Multiphase Flows, ICMF 2010, June 2010, Tampa, Florida.
- [67] A. Kharicha, A. Ludwig, M. Wu, (4rd Int. Conf. Simulation and Modeling in Metallurgical Processes in Steelmaking, Düsseldorf, Germany, 2011), S19.1-5.
- [68] G. Chirita, I. Stefanescu, J. Barbosa, H. Puga, D. Soares, F.S. Silva, *Int. J. Cast Metals Research*, (2009), 382-9.
- [69] G. Chirita, I. Stefanescu, D. Soares, F.S. Silva, *Anales de Mecánica de la Fractura*, (2006), 317-22.
- [70] S.R. Chang, J.M. Kim, C.P. Hong, *ISIJ International* (2001), 738-47.
- [71] K.S. Keerthiprasad, M.S. Murali, P.G. Mukunda S. Majumdar, *Metall. Mater. Trans. B*, 42 (2010), 144-55.
- [72] P.S.S. Raju, S.P. Mehrotra, *JIM*, 41 ,(2000), 1626-35