

Multi-catalysis reactions: new prospects and challenges of biotechnology to valorize lignin

Christoph A. Gasser · Gregor Hommes ·
Andreas Schäffer · Philippe F.-X. Corvini

Received: 9 February 2012 / Revised: 15 May 2012 / Accepted: 15 May 2012 / Published online: 12 July 2012
© Springer-Verlag 2012

Abstract Considerable effort has been dedicated to the chemical depolymerization of lignin, a biopolymer constituting a possible renewable source for aromatic value-added chemicals. However, these efforts yielded limited success up until now. Efficient lignin conversion might necessitate novel catalysts enabling new types of reactions. The use of multiple catalysts, including a combination of biocatalysts, might be necessary. New perspectives for the combination of bio- and inorganic catalysts in one-pot reactions are emerging, thanks to green chemistry-driven advances in enzyme engineering and immobilization and new chemical catalyst design. Such combinations could offer several advantages, especially by reducing time and yield losses associated with the isolation and purification of the reaction products, but also represent a big challenge since the optimal reaction conditions of bio- and chemical catalysis reactions are often different. This mini-review gives an overview of bio- and inorganic catalysts having the potential to be used in combination for lignin depolymerization. We also discuss key aspects to consider when combining these catalysts in one-pot reactions.

Keywords Lignin · Homogeneous catalysis · Heterogeneous catalysis · Biocatalysis · Chemoenzymatic catalysis

Introduction

The depletion of fossil carbon reserves and concern about global warming calls for substitutes of fossil fuels and petrochemicals (Marquardt et al. 2010). For energy production, multiple alternatives are available, e.g., wind, sun, biomass, hydroelectricity, nuclear fission. However, biomass is the only known renewable resource that can be converted to both fuels and chemicals (Zhang 2008). Therefore, biorefineries using lignocellulosic feedstock have been proposed as alternatives to petroleum-based refineries (e.g., Wyman and Goodman 1993; Holladay et al. 2007; Kamm et al. 2007; Zhang 2008; Michels and Wagemann 2010). Recalcitrance to degradation of lignin is a major obstacle to harness lignocellulosic biomass efficiently (Mansfield et al. 1999; Achyuthan et al. 2010; Zakzeski et al. 2010a; Sanderson 2011).

Lignin, a complex three-dimensional amorphous polymer consisting of methoxylated phenylpropanoid units of various types (Achyuthan et al. 2010; Isroi et al. 2011), is the second most abundant constituent of plant biomass next to cellulose, accounting for approximately 20 % of carbon fixed in land ecosystems (Ruiz-Dueñas and Martínez 2009). Despite extensive research, lignin is mostly used in commercial applications of low value, for example, as concrete additive (Doherty et al. 2011) or as low-grade fuel. However, due to its structure, it constitutes a potential renewable source for aromatic added-value chemicals (Holladay et al. 2007).

Novel approaches using new catalytic systems seem necessary in order to exploit lignin as a resource for the production of fine chemicals (Vennestrøm et al. 2010a). The use of multiple catalysts (Marr and Liu 2011; Santacoloma et al.

C. A. Gasser · G. Hommes (✉) · P. F.-X. Corvini
Institute for Ecopreneurship, School of Life Sciences,
University of Applied Sciences and Arts Northwestern Switzerland,
Grüdenstrasse 40,
Muttenz 4132, Switzerland
e-mail: gregor.hommes@fhnw.ch

A. Schäffer
Institute for Environmental Research, RWTH Aachen,
Worringerweg 1,
52074, Aachen, Germany

P. F.-X. Corvini
School of the Environment, Nanjing University,
Hankou Road 22,
210093, Nanjing, China

2011) and the combination of bio- and inorganic catalysts in either sequential or one-pot cascade catalysis (Vennestrøm et al. 2010a) has not been investigated extensively and might be essential to achieve economically sustainable valorization of lignin. Furthermore, combining multiple catalysts in one-pot cascade catalysis would provide advantages over conventional processes focusing on single reactions, mainly by reducing time and yield losses associated with the isolation and purification of reaction products (Murzin and Leino 2008; Vennestrøm et al. 2010a). However, the combination especially of bio- and inorganic catalysts can be complex since enzymes and inorganic catalysts possess various optimal conditions regarding pH, temperature, pressure, and solvent (Marr and Liu 2011).

In this mini-review, we give an overview of various bio- and inorganic catalysts, having the potential to be used in combination for lignin depolymerization, a biopolymer constituting a possible renewable source for aromatic added-value chemicals. The first part focuses on the inorganic catalysts applied for the depolymerization of lignin, the second part deals with lignin degradation in nature and the enzymatic catalysts involved in this process, and the third part discusses aspects to consider when combining both types of catalysts. While several publications on the general combination of enzymatic with inorganic catalysts (e.g., Murzin and Leino 2008; Vennestrøm et al. 2010a; Marr and Liu 2011), lignin-degrading enzymes (e.g., Kersten and Cullen 2007; Hammel and Cullen 2008; Ruiz-Dueñas and Martínez 2009; Wong 2009), and inorganic catalysis for lignin conversion (Zakzeski et al. 2010a) exist, this mini-review combines all these aspects with a specific focus on the depolymerization of lignin for the production of added-value chemicals.

Inorganic catalysis

Depolymerization of lignin and lignin model compounds through inorganic catalysts has been attempted in a plethora of studies. Inorganic catalysts were usually used under harsh reaction conditions. Conversion of lignin depends not only on reaction conditions and catalysts but also on the pretreatment/extraction methods used to isolate the lignin fraction from lignocellulose. So far, the lignin polymer could not be isolated exhaustively due to its molecular association and potential covalent bonds with polysaccharides (Holtman et al. 2007). Depending on the pretreatment method used, undesired chemical transformations like the incorporation of sulfur can occur. Furthermore, the molecular weight of lignin can be reduced and the chemical bond linkages can be altered (Gluckstein et al. 2010). Pretreatment methods resulting in uniform types of lignin of high purity are most desirable. Several publications covering lignin pretreatment exist (e.g., da Costa Sousa et al. 2009; Gluckstein

et al. 2010; Zakzeski et al. 2010a). The variation between the lignin feedstocks used in the various studies on lignin transformation impedes the comparison of their performances because a benchmark substrate is lacking. Furthermore, comparability is complicated by the fact that different methods are used for product recovery and also because many studies solely dealt with lignin model compounds.

Chemical lignin transformation reactions can be divided into lignin cracking, hydrolysis, catalytic reduction, and catalytic oxidation reactions. Lignin catalytic cracking processes are adapted from petroleum refineries and work at harsh reaction conditions, especially high temperatures, usually above 300 °C. They can cleave lignin β -O-4 ether bonds as well as relatively unstable carbon-carbon bonds (Thring and Breau 1996) such as $C\alpha$ - $C\beta$ bonds. Lignin fragmentation by hydrolysis is also achieved at high temperatures, usually above 270 °C. Pandey and Kim (2011) recently reviewed the thermochemical depolymerization and conversion of lignin, including catalytic cracking and hydrolysis processes. These high-temperature processes lead to tar or char formation, volatile components, and complex mixtures of compounds (van Haveren et al. 2008; Zakzeski et al. 2010a; Pandey and Kim 2011).

Paralleling the emerging concept of green chemistry, more and more new chemical catalysts are designed to work in aqueous environments at milder reaction conditions (Hailes et al. 2007; Sheldon 2008). Since an extensive review on inorganic catalysis of lignin was published recently (Zakzeski et al. 2010a), the following section is restricted to a few selected studies where mild reaction conditions were used or that were published just recently.

Lignin reduction

Reductive lignin depolymerization usually removes alcohol, aldehyde, ether, and acid moieties. Therefore, it has the potential to produce simpler bulk aromatic compounds like benzene, toluene, and xylene (B, T, X) as well as phenol (van Haveren et al. 2008), which could be directly used by conventional petrochemical processes (Holladay et al. 2007). Furthermore, the removal of oxygen from lignin makes it a better working fuel (Sanderson 2011). Hydrogenation or hydrodeoxygenation of lignin and lignin model compounds with heterogeneous catalysts, performed at high temperatures and pressures, not only cleaved ether bonds but also hydrogenated aromatic rings, thereby producing an inefficient mixture of compounds (Sergeev and Hartwig 2011). Selective cleavage of lignin model compounds through electrocatalytic hydrogenation at relatively low temperatures (50 °C) was reported (Mahdavi et al. 1997; Dabo et al. 1999; Cyr et al. 2000). Few studies used homogenous catalysts to reduce lignin or lignin model compounds (e.g., Hu et al. 1997;

Plasseraud and Süss-Fink 1997; Schulz et al. 2000). A nickel catalyst was employed for hydrogenolysis of dimeric 4-O-5, α -O-4, and β -O-4 lignin model compounds and several alkyl-aryl and diaryl ethers at temperatures between 80 and 120 °C and pressure of 1 bar of hydrogen (Sergeev and Hartwig 2011). The aromatic C–O bonds of the ethers were selectively cleaved and produced exclusively alcohols and arenes. Furthermore, the ether linkages of the lignin model compounds were broken. Degradation of the α -O-4 model compound yielded 99 % 3,4-dimethoxytoluene and 2-methoxyphenol. Hydrogenation of the β -O-4 model yielded 89 % guaiacol. Thereby, it was demonstrated that the aromatic C–O bonds could be selectively cleaved in the presence of other C–O bonds, while leaving the arene units intact (Sergeev and Hartwig 2011). Whereas these results look promising, the effectiveness of the catalyst on different lignin feedstocks, not just lignin model compounds, has still to be demonstrated. A further issue is the soluble form of the catalyst, which makes separation from products difficult (Sanderson 2011).

Lignin oxidation

Oxidative lignin depolymerization requires catalysts that selectively disrupt the linkages in lignin in order to form specific aromatic alcohols, aldehydes, acids, or other specially functionalized aromatics like vanillin, syringaldehyde, or vanillic acid (Holladay et al. 2007; Zakzeski et al. 2010a). Many of the resulting chemicals might be used as platform chemicals for subsequent organic synthesis or are target fine chemicals (Zakzeski et al. 2010a). The oxidation of lignin and lignin model compounds was also briefly discussed in a recent review on biomass oxidation (Collinson and Thielemans 2010).

Heterogeneous catalysts, more specifically, TiO₂ and Pt/TiO₂, have been used for photocatalytic oxidation to process lignin from wastewater streams of the paper industry (Portjanskaja and Preis 2007; Ma et al. 2008; Portjanskaja et al. 2009). These processes were applied at relatively mild temperatures (~20 °C), but products and percentages of conversion were not specified.

Methyltrioxorhenium (MTO) has been used as a catalyst in the presence of H₂O₂ at 60 °C to cleave the CC double bond of isoeugenol and *trans*-ferulic acid, thereby producing vanillin (Herrmann et al. 2000). Further authors used the catalytic MTO/H₂O₂ system (homogeneous as well as heterogeneous) to oxidize technical lignins and lignin model compounds at 25 °C (Crestini et al. 2005, 2006). Phenolic, non-phenolic, and dimeric lignin model compounds were oxidized to a large extent. The oxidation of 18.2 g L⁻¹ sugar cane, red spruce kraft, and hardwood organosolv lignin at room temperature led to high degrees of degradation and produced lignin fragments of increased solubility.

Various studies investigated the electrochemical oxidation of lignin using different electrodes (e.g., Pardini et al. 1992;

Parpot et al. 2000; El-Ashtouky et al. 2009). Dominguez-Ramos et al. (2008, 2010a, b) used boron-doped diamond electrodes for the oxidation of lignosulfonates. They were able to oxidize approximately 90 % of the total organic carbon in a lignosulfonate solution. However, the structure of the degradation products was not elucidated. For the electrochemical oxidation of kraft lignin, different IrO₂-based electrodes were used (Tolba et al. 2010). Vanillin and vanillic acid were formed as primary intermediates. Apparent degradation rate constants were determined for temperatures ranging from 2 to 60 °C and were highest at 60 °C.

One commercial process for the oxidation of lignosulfonates exists (Faith et al. 1965). Lignosulfonates are produced through sulfite pulping in the pulp and paper industries. Their oxidation produces vanillin in a yield of 10–20 % (w/w based on the dry weight of lignosulfonates). The spent acid sulfite pulping liquors are oxidized with air at 160–170 °C at alkaline pH. After oxidation, the products are extracted using organic solvents and further purified (Hocking 1997; Ramachandra Rao and Ravishankar 2000).

Due to economic and environmental reasons, production of vanillin from lignosulfonates is a declining process (Sixta 2006). Therefore, Rudolf von Rohr and co-workers investigated an alternative process using kraft lignin as feedstock (Voitl et al. 2009; Voitl and Rudolf von Rohr 2010; Werhan et al. 2011). Kraft lignin is a by-product of the kraft process, which is presently the most prominent pulping process (Auhorn and Niemela 2007).

H₃PMo₁₂O₄₀ was used as homogeneous catalyst in an 80 % (v/v) methanol/water solvent at acidic pH at 170 °C under an atmosphere of 10.8 bar of oxygen containing 8.9 g L⁻¹ dry kraft lignin at the start of the oxidation process (Voitl and Rudolf von Rohr 2010). Monomeric products were extracted with chloroform. The process yielded 3.5 % (w/w) vanillin and 3.5 % (w/w) methyl vanillate. A total of 10 % (w/w) of monomers could be extracted, including further products like acetovanillone and methylparaben. Additionally, approximately 60 % (w/w) of oligomeric products with significantly lower molecular weight than kraft lignin were found in the extract (Voitl and Rudolf von Rohr 2010).

In a more recent study, different metal salt catalysts were tested as replacement for H₃PMo₁₂O₄₀ (Werhan et al. 2011). For all studied salts (CuSO₄, CoCl₂, FeCl₃, and CuCl₂), higher maximal vanillin concentrations were found than in the presence of H₃PMo₁₂O₄₀ or without catalyst. However, only experiments using CoCl₂ and CuSO₄ as catalyst reached similar concentrations of the valuable methyl vanillate as experiments using H₃PMo₁₂O₄₀. The average molecular weight of the product mixture was considerably lower in experiments using metal salts as catalysts compared to experiments using H₃PMo₁₂O₄₀. The treatment with FeCl₃

or CuCl_2 as catalyst led to the lowest average molecular weight (Werhan et al. 2011).

The oxidation of Alcell lignin, soda lignin, and several lignin model compounds was investigated using oxygen with $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$ as homogenous catalyst dissolved in an ionic liquid (1-ethyl-3-methylimidazolium diethyl phosphate, [EMIM] [DEP]) at 80 °C (Zakzeski et al. 2010b). Ionic liquids (ILs) are mixtures of cations and anions melting below 100 °C. Ethyl acetate extraction after lignin oxidation yielded no monomeric products. However, the difference between the attenuated total reflectance infrared spectra after various reaction times suggested a selective oxidation of the dissolved lignin (Zakzeski et al. 2010b). Treatment of lignin model compounds with the catalyst did not disrupt β -O-4, 5-5, and other linkages. Phenolic functional groups remained unchanged as well. However, alcohol moieties were oxidized to form aldehydes or, at high oxygen pressures or substrate loadings, to form acids (Zakzeski et al. 2010b). In a more recent study, the cobalt-catalyzed oxidation of lignin model compounds in [EMIM] [DEP] was further investigated (Zakzeski et al. 2011).

Further studies for the oxidation of lignin and lignin model compounds conducted at mild reaction conditions with homogeneous catalysts used metalloporphyrin, metallosalen, metallo-TAML, -DTNE, -TACN, polyoxometalate-based, simple metal salt-based, and miscellaneous catalyst systems and have been reviewed recently (Zakzeski et al. 2010a).

Many lignin oxidation studies have been carried out and several used mild reaction conditions to depolymerize lignin. These great efforts lead to processes where about 10 to 20 % (*w/w* based on lignin dry weight) of lignin could be converted to value-added monomers (Hocking 1997; Ramachandra Rao and Ravishankar 2000). Although this constitutes a considerable accomplishment, given the complexity of the task, higher product yields are necessary for the processes to become economically attractive. Therefore, new approaches seem indispensable to achieve efficient lignin depolymerization.

Enzymatic catalysis

While lignin depolymerization with inorganic catalysts has still limited success, lignin is efficiently degraded in nature by basidiomyceteous white-rot fungi through multiple enzymes (Levasseur et al. 2008; Ruiz-Dueñas and Martínez 2009; Sánchez 2009; Wong 2009; Collinson and Thielemans 2010; Hatakka and Hammel 2010). This illustrates the potential of biocatalysts for lignin depolymerization. In contrast to inorganic catalysts, biocatalysts can be much more selective and able to distinguish between functional groups (Vennestrøm et al. 2010a) but require mild reaction conditions and are often inactivated in non-aqueous solutions (Doukyu and Ogino

2010). The first part of this section covers the different enzymes involved in natural degradation processes of lignin.

Application of enzymes in industrial processes is challenging since they are usually less stable than inorganic catalysts, not easily recycled, and only work in a relatively narrow temperature window. The second part of this section discusses these challenges and presents ways to improve the biocatalyst properties.

Lignin degradation in nature

After extensive research, the mechanisms of fungal lignin degradation become gradually clearer (reviewed by, e.g., Kersten and Cullen 2007; Hammel and Cullen 2008; Ruiz-Dueñas and Martínez 2009; Wong 2009). Enzymes potentially involved in degrading lignin are divided into lignin oxidases and lignin-degrading auxiliary enzymes, corresponding to their direct or indirect participation to lignin degradation, respectively (Table 1). They have been described at length in previous studies and reviews (e.g., Henriksson et al. 2000; Ozimek et al. 2005; Whittaker 2005; Mayer 2006; Joosten and van Berkel 2007; Hammel and Cullen 2008; Ruiz-Dueñas and Martínez 2009; Wong 2009; Faulds 2010; Giardina et al. 2010; Lundell et al. 2010; Singh Arora and Kumar Sharma 2010). In addition, relevant information on these enzymes is collected in general databases (e.g., <http://www.brenda-enzymes.org>).

Lignin oxidases

Efficient lignin mineralization in nature is only achieved by basidiomyceteous white-rot fungi, which commonly inhabit forest litter and fallen trees (Kersten and Cullen 2007). Degradation of lignin is hindered by its non-phenolic aromatic nature, which prevents direct oxidation by low-redox-potential oxidoreductases (Ruiz-Dueñas and Martínez 2009). Moreover, bulky lignin polymers are often hardly accessible to enzymes. To overcome these limitations, white-rot fungi have developed highly specialized heme-containing ligninolytic peroxidases, i.e., lignin (LiP), manganese (MnP), and versatile (VP) peroxidases, which use H_2O_2 as oxidant (Ruiz-Dueñas and Martínez 2009).

It is assumed that LiPs are able to oxidize the aromatic rings of lignin via long-range electron transfer (Ruiz-Dueñas and Martínez 2009). The unspecific oxidation of the aromatic rings of lignin produces unstable cation radicals, which react further and undergo different non-enzymatic reactions like scission of $\text{C}\alpha$ – $\text{C}\beta$ and C4 –ether linkages (Martínez et al. 2005). The latter finally leads to the release of aromatic aldehydes, demethoxylation with subsequent methanol release, or aromatic ring cleavage prior to the formation of muconate-type structures (Martínez et al. 2005; Ruiz-Dueñas and Martínez 2009).

Table 1 Enzyme groups potentially involved in the degradation of lignin. The values given refer to the corresponding enzyme group as a whole and depict the temperature and pH ranges in which active enzymes of the associated group have been described. References were obtained from <http://www.brenda-enzymes.org>

Family	Enzyme group	pH optimum range	pH working Range ^a	Temperature optimum range, °C	Temperature working range, °C ^b	Reaction	References
Lignin oxidases family LO1	Laccase (EC 1.10.3.2)	2–9	0.5–11.5	20–85	0–100	4 benzenediol + O ₂ = 4 benzosemiquinone + 2 H ₂ O	Baldrian 2004; Dubé et al. 2008; Haibo et al. 2009; Pakhadnia et al. 2009; Shao et al. 2009; Wang et al. 2010; Wu et al. 2010
Lignin oxidases family LO2	Catechol oxidase (EC 1.10.3.1)	3.5–9	3–9.5	4–70	4–80	2 catechol + O ₂ = 2 1,2-benzoquinone + 2 H ₂ O	Doğan et al. 2005; Güleşin et al. 2005; Selinheimo et al. 2006; Sellés-Marchart et al. 2006; Kim et al. 2011
	Versatile peroxidase (EC 1.11.1.16)	3–5	No entries	No entries	No entries	Donor + H ₂ O ₂ = oxidized donor + 2 H ₂ O	Camarero et al. 1999
	Lignin peroxidase (EC 1.11.1.14)	1–6	1–7	23–70	10–80	(3,4-Dimethoxyphenyl)methanol + H ₂ O ₂ = 3,4-dimethoxybenzaldehyde + 2 H ₂ O	Aitken and Irvine 1989; Alam et al. 2009; Ghodake et al. 2009; Gomes et al. 2009
	Manganese peroxidase (EC 1.11.1.13)	2.5–6.8	2.5–11	22–60	10–75	2 Mn(II) + 2 H ⁺ + H ₂ O ₂ = 2 Mn(III) + 2 H ₂ O	Paszczyński et al. 1988; Giardina et al. 2000; Wang et al. 2002; Cheng et al. 2007; Gomes et al. 2009
	Genetic peroxidases (EC 1.11.1.7)	3–11.7	2–11.7	10–84	0–90	2 phenolic donor + H ₂ O ₂ = 2 phenoxy radical of the donor + 2 H ₂ O	Shin et al. 1997; Senczuk et al. 2003; Suzuki et al. 2006; Vermwal et al. 2006; Jeoung et al. 2007
Lignin oxidases family LO3	Chloroperoxidase (EC 1.11.1.10)	2.5–6	2–7	30–35	20–50	RH + chloride + H ₂ O ₂ = RCl + 2 H ₂ O	Petri et al. 2004; Bayramoğlu et al. 2008; Yadav et al. 2010
	Cellobiose dehydrogenase (EC 1.1.1.99.18)	2.7–9	2.5–10	20–75	10–80	Cellobiose + acceptor = cellobion-1,5-lactone + reduced acceptor	Schou et al. 1998; Baminger et al. 2001; Sigoillot et al. 2002; Zamocky et al. 2006
Lignin-degrading auxiliary enzymes family LDA1-8	Aryl-alcohol oxidase (EC 1.1.3.7)	5–8.5	2–10	30–55	20–60	An aromatic primary alcohol + O ₂ = an aromatic aldehyde + H ₂ O ₂	Guillén et al. 1992; Okamoto and Yanase 2002; Ferreira et al. 2005; Kumar and Goswami 2006
	Vanillyl-alcohol oxidase (EC 1.1.3.38)	7–10.5	6–12	38	No entries	Vanillyl alcohol + O ₂ = vanillin + H ₂ O ₂	de Jong et al. 1992; van den Heuvel et al. 2001
	Glyoxylate oxidase (EC 1.2.3.5)	8	6.5–8.5	40	No entries	Glyoxylate + H ₂ O + O ₂ = oxalate + H ₂ O ₂	Akamatsu and Shimada 1994
	Pyranose oxidase (EC 1.1.3.10)	4–8.5	2.5–11	35–65	25–70	D-Glucose + O ₂ = 2-dehydro-D-glucose + H ₂ O ₂	Schäfer et al. 1996; Artolozaga et al. 1997; Leimer et al. 2001; Takakura and Kuwata 2003; Odaci et al. 2010
	Galactose oxidase (EC 1.1.3.9)	5.5–8	5–9	30–50	20–60	D-Galactose + O ₂ = D-galacto-hexodialdose + H ₂ O ₂	Alberton et al. 2007; Isobe et al. 2007; Sasaki et al. 2010;
	Glucose oxidase (EC 1.1.3.4)	4–7	3–11	25–70	10–70	β-D-Glucose + O ₂ = D-glucono-1,5-lactone + H ₂ O ₂	Crognale et al. 2006; Simpson et al. 2007; Altikatoglu et al. 2010; Hashemifard et al. 2010; Courjean and Mano 2011

Table 1 (continued)

Family	Enzyme group	pH optimum range	pH working Range ^a	Temperature optimum range, °C	Temperature working range, °C ^b	Reaction	References
Lignin-degrading auxiliary esterases family EST	Benzoquinone reductase (EC 1.6.5.6)	6–7	5–9	40–45	15–50	NADPH + H ⁺ + <i>p</i> -benzoquinone = NADP ⁺ + hydroquinone	Shimizu et al. 1988
	Alcohol oxidase (EC 1.1.3.13)	3–9	3–10	30–65	18–65	A primary alcohol + O ₂ = an aldehyde + H ₂ O ₂	Couderc and Baratti 1980; Patel et al. 1981; Kumar and Goswami 2006; Jadhav et al. 2009; Gvozdev et al. 2010
Others	Feruloyl esterase (EC 3.1.1.73)	3–9	2.6–11	20–65	5–75	Feruloyl-polysaccharide + H ₂ O = ferulate + polysaccharide	García-Conesa et al. 2004; Wong 2006; Aurilia et al. 2007; Moukoulis et al. 2008; Hegde and Muralikrishna 2009
	Aryl-alcohol dehydrogenase (EC 1.1.1.91)	6.1–8.8	5–9.5	30	30–55	An aromatic alcohol + NADP ⁺ = an aromatic aldehyde + NADPH + H ⁺	Muheim et al. 1991; Gross and Zenk 1969

^a pH ranges in which enzymes of the corresponding group have been described as expressing at least 20 % of maximal activity

^b Temperature ranges in which enzymes of the corresponding group have been described as expressing at least 20 % of maximal activity

MnP oxidizes Mn²⁺ to Mn³⁺ (Gold et al. 1984). Mn³⁺ is subsequently stabilized by organic acids like oxalic acid, which results in Mn³⁺ chelates which act as redox mediators oxidizing phenolic lignin structures (Glenn and Gold 1985; Gold et al. 2000). Furthermore, it has been shown that lipid peroxidation by MnP might play an important role in lignin biodegradation. Mineralization of non-phenolic lignin model compounds as well as ¹⁴C-labeled synthetic lignin and ¹⁴C-labeled wheat straw was instigated by the presence of an unsaturated fatty acid, i.e., linoleic acid and a surfactant, i.e., Tween 20 or Tween 80 emulsifying water-insoluble components leading to a homogenous mixture of unsaturated fatty acids and water (Kapich et al. 1999a). Subsequently, it was shown that peroxidized unsaturated fatty acids are capable to oxidize non-phenolic β-O-4-linked lignin model compounds irrespective of MnP, indicating that direct contact between MnP and lignin is not necessary but, rather, that the formed peroxy radicals act as agents for lignin degradation (Kapich et al. 1999b). In nature, lipid substances might be produced by the fungus (Enoki et al. 1999) and are also already present in wood (Hofrichter et al. 2001). VP represents a hybrid of LiP and MnP and is able to directly oxidize non-phenolic lignin units as well as Mn²⁺ (Ruiz-Dueñas et al. 2009).

There are several white-rot fungi that exclusively produce MnP as extracellular peroxidase e.g., *Ceriporiopsis subvermispora* (Lobos et al. 1994), *Dichomitus squalens* (Périeri et al. 1996), *Lentinula (Lentinus) edodes* (Leatham 1986), *Phanerochaete sordida* (Rüttimann-Johnson et al. 1994), and *Pleurotus ostreatus* (Giardina et al. 2000), indicating that MnP might be essential for lignin biodegradation. Other white-rot basidiomycetes produce LiP alongside MnP, e.g., *Phanerochaete chryosporium* (Hatakka 1994), *Phlebia radiata* (Vares et al. 1995), and *Trametes versicolor* (Johansson and Nyman 1993), while VPs have been detected in *Pleurotus* (Camarero et al. 1999) and *Bjerkandera* (Mester and Field 1998) species.

Another group of enzymes potentially involved in the oxidation of lignin are laccases, copper-containing oxidases oxidizing phenolic rings to phenoxy radicals while using molecular oxygen as oxidant (Baldrian 2006). They usually have a low redox potential with few exceptions (Uzan et al. 2010). Therefore, they are unable to directly catalyze the oxidation of non-phenolic aromatic rings of lignin (Ruiz-Dueñas and Martínez 2009). However, they are able to degrade high-redox-potential substrates in the presence of small chemical oxidants acting as redox mediators (reviewed by, e.g., Morozova et al. 2007; Cañas and Camarero 2010; Kudanga et al. 2011). These mediators form radicals, which are able to penetrate the lignocellulose matrix (Ruiz-Dueñas and Martínez 2009). Nevertheless, the role of laccase in lignin biodegradation is still debated. While many white-rot fungi produce laccases, there are no laccase-encoding genes present in the whole genome of *P. chryosporium* (Martínez et al.

2004), a white-rot basidiomycete able to completely degrade all components of lignocellulose (Kersten and Cullen 2007). Furthermore, 17 laccase-encoding genes have been found in *Coprinopsis cinerea*, a basidiomycetous fungus unable to degrade lignin (Hatakka and Hammel 2010). Moreover, in the absence of suitable mediators, laccases oxidize the phenolic groups present in lignin, which results in polymerization (Rocheffort et al. 2004). Therefore, it remains unclear if laccases play a role in natural lignin degradation processes. However, since laccases can be produced in sufficient amounts for industrial applications (Hou et al. 2004), whereas this could not be achieved for ligninolytic peroxidases so far (Singh et al. 2011), their potential application for lignin depolymerization in industrial processes in combination with suitable mediators should not be disregarded.

Lignin-degrading auxiliary enzymes

The H_2O_2 needed by the ligninolytic peroxidases and possibly laccases is produced in situ by lignin-degrading auxiliary enzymes (LDA1–8) like, e.g., aryl-alcohol oxidase or glyoxal oxidase (Shah and Nerud 2002). It has been shown that aryl-alcohol oxidase is able to use the aromatic aldehydes produced by lignin breakdown or synthesized by fungi as substrate for H_2O_2 generation in cyclic redox reactions, which also involve aryl-alcohol dehydrogenase (Guillén et al. 2000). Furthermore, there is evidence that FAD oxidases like aryl-alcohol oxidase prevent the recondensation of intermediates during lignin degradation by reducing the de novo formed quinonoids and radical compounds (Marzullo et al. 1995). H_2O_2 has also been shown to be produced by oxidation of lignin-derived hydroquinones through laccases and VPs (Guillén et al. 2000; Gómez-Toribio et al. 2001, 2009) or Mn^{2+} oxidation through laccases (Schlosser and Höfer 2002).

Lignin-degrading auxiliary esterases, i.e., feruloyl esterases, have been shown to hydrolyze ferulate bridges between lignin and carbohydrates in monocotyledons and dicotyledons and to disrupt the cell wall structure in combination with xylanases and might, therefore, be involved in the initial stages of lignocellulose degradation (Topakas et al. 2007; Koseki et al. 2009).

Hydroxyl radical production

Hydroxyl radicals, which are the strongest oxidants in white-rot fungi cultures (Forney et al. 1982; Backa et al. 1992), can initiate the attack on lignocellulose and presumably cause hydroxylation, demethoxylation, and depolymerization of lignin (Evans et al. 1994; Joseleau et al. 1994). They can be produced by cellobiose dehydrogenase via Fenton reaction (Henriksson et al. 2000; Ludwig et al.

2010; Harreither et al. 2011). A further path leading to hydroxyl radical production involves *p*-quinones originating from lignin decomposition. They can be used by quinone reductases, laccases, and peroxidases in redox cycle reactions to activate oxygen (Guillén et al. 1997). This in turn reduces the ferric iron present in wood either by the superoxide radicals or semi-quinone radicals to ferrous iron (Guillén et al. 2000). Subsequent re-oxidation of the ferrous iron by H_2O_2 reduction produces hydroxyl radicals (Guillén et al. 2000).

Potential additional lignin-modifying enzymes

There are some reports of additional enzymes that might have the potential to act on lignin. Chloroperoxidases might contribute to lignin degradation since they have been shown to catalyze the cleavage of the β -O-4 bond of a dimeric lignin model compound (Ortiz-Bermúdez et al. 2003). Furthermore, they might chlorinate lignin and be partly responsible for the natural production of chloroaromatics (Ortiz-Bermúdez et al. 2003).

Two dye-decolorizing peroxidases (DyP) secreted by the jelly fungus *Auricularia auricular-judae* have been shown to oxidize non-phenolic lignin model compounds and high-redox-potential dyes, i.e., Reactive Blue 5 and Reactive Black 5 at acidic pH (activity maximum at pH 1.4), indicating the ligninolytic activity of these enzymes (Liers et al. 2010). The redox potential of five different DyPs has been calculated to be at least ~ 1.2 V and it has been suggested that this might be sufficient for the oxidation of non-phenolic lignin structures at low pH values between 1.5 and 3.0 (Hofrichter et al. 2010). However, not all DyPs are capable to oxidize non-phenolic lignin model compounds and whether certain DyPs can actually depolymerize lignin has still to be investigated (Hofrichter et al. 2010).

A further group of enzymes hypothesized to take part in the degradation of methoxylated compounds originating from lignin is aromatic peroxygenases (Kinne et al. 2011). Extracellular aromatic peroxygenase from the agaric fungus *Agrocybe aegerita* (*AaeAPO*) has been shown to cleave non-phenolic β -O-4 lignin model compounds as well as phenolic dimers but seems to be unable to oxidize polymeric lignin (Kinne et al. 2011). Therefore, *AaeAPO* seems not to be directly involved in lignin biodegradation but rather in the oxidation of compounds with low molecular masses such as lignin fragments or lignans (Kinne et al. 2011).

Lignin modification by brown-rot fungi

Besides white-rot basidiomycetes, brown-rot fungi are also capable to degrade lignocellulose in nature. While lignin is not significantly mineralized by brown-rot fungi, its structure is altered, i.e., its aromatic methoxyl content is lower and its

content of conjugated carbonyls and carboxyls as well as phenolic hydroxyls is higher (Yelle et al. 2008). While hydroxyl radicals seem to play a major role in lignocellulose degradation by brown-rot fungi (Hammel et al. 2002), there also appear to be hydrolytic enzymes involved in the process (Cohen et al. 2005). It has been argued that consequently some lignin degradation has to occur because otherwise these enzymes would be hindered to act on their target substrates, e.g., cellulose by the small pore sizes of intact wood (Yelle et al. 2008). Analysis of lignocellulose degraded by the brown-rot basidiomycete *Gloeophyllum trabeum* via two-dimensional solution-state nuclear magnetic resonance spectroscopy indicated degradation of lignin side chains during brown-rot (Yelle et al. 2008). However, brown-rotted lignin has been shown to be polymeric and to keep most of its aromatic residues (Jin et al. 1990). Therefore, it has been suggested that lignin is initially depolymerized by brown-rot fungi (Yelle et al. 2008). Subsequently, the content of phenolic units on lignin increases due to hydroxyl radicals reacting with the aromatic rings (Yelle et al. 2008). Thereafter, the lignin units get reconnected through radical coupling of the phenolic units (Yelle et al. 2008).

Lignin degradation by bacteria

Many bacteria have lignin-degrading ability (recently reviewed by Bugg et al. (2011)). They are able to solubilize lignin and modify the lignin structure (Buswell and Odier 1987; Ball et al. 1989; Godden et al. 1992). However, they do not mineralize lignin to a large extent (Buswell and Odier 1987). These bacteria produce several extracellular enzymes that are involved in the degradation of lignocellulosic biomass like peroxidases, cellulases, and esterases (Santhanam et al. 2012). However, at present, the enzymology of bacterial lignin degradation is not well understood (Bugg et al. 2011). Nevertheless, the results suggest that similar enzyme types as in fungi might be involved. It has been reported that *Streptomyces viridosporus* T7A, a lignin-degrading actinomycete, secretes several peroxidases able to catalyze the cleavage of lignin model compounds (Ramachandra et al. 1988). Subsequently, several actinomycetes exhibiting extracellular peroxidase activity have been identified (Mercer et al. 1996). More recently, a DyP has been identified and characterized in the actinomycete *Rhodococcus jostii* sp. RHA1 able to catalyze C α –C β bond cleavage of a lignin model compound (Ahmad et al. 2011). Production of laccases by bacteria has been reported as well (Miyazaki 2005; Kellner et al. 2008; Niladevi et al. 2008). This indicates that suitable enzymes produced by bacteria could potentially be used by themselves or in combination with enzymes from fungi in future conversion processes of lignin. Using bacteria instead of fungi for enzyme production would most likely reduce the practical challenges posed when working

with fungi concerning protein expression and genetic manipulation.

Enhancement of biocatalyst properties


The performance of one-pot multi-catalytic reactions with lignin-modifying enzymes (LMEs) can be limited by several reaction parameters, e.g., pH, temperature, and solvent. In general, pH is not a major constraint regarding activity as several LMEs active at rather high or low pH have been described (Table 1). Therefore, the right selection of enzymes allows for reaction conditions to be acidic as well as alkaline. However, enzyme stability might become an issue under extreme pH conditions, which are, e.g., associated to chemical oxidation processes. Temperature seems to be a major limitation as few enzymes are active at temperatures above 90 °C. Most LMEs show activity maxima between 20 and 70 °C. However, some overlap between the temperature ranges of LMEs and inorganic catalytic processes exists (Fig. 1). Moreover, enzymes are often inactivated or denatured in the presence of organic solvents (Ogino and Ishikawa 2001), further limiting their usability for the conversion of lignin in combination with chemical catalysis.

Improving enzyme stability and activity under harsh reaction conditions would lead to a broader application range, thereby increasing the possible combinations with other bio- or inorganic catalysts. In principle, there are three ways to obtain modified enzymes with improved properties. Enzymes can be isolated from extremophiles, obtained by classical protein engineering where stabilizing mutations can be predicted on the basis of the enzyme structure, and produced through directed evolution (Eijsink et al. 2005; Turner 2009). “Directed evolution is a widely-used engineering strategy for improving the stabilities or biochemical functions of proteins by repeated rounds of mutation and selection” (Bloom and Arnold 2009). These three strategies are also often used in combination. Additionally, enzyme immobilization often leads to the enhancement of enzyme stability and sometimes even of activity (Mateo et al. 2007). Furthermore, immobilization facilitates the recovery and reuse of enzymes (Sheldon 2007). In this section, we discuss several scientific and technological advances leading to the effective improvement of LME properties.

Thermostability

Increased enzymatic thermostability often goes along with a general stability increase of the enzyme, making it more tolerant to extreme pHs, high salt concentration, the presence of organic co-solvents, etc. (Arnold 1990; Ogino and Ishikawa 2001). High process temperatures confer advantages like low levels of microbial side-contamination, improved reaction yields, increased solubility of reaction substrate, and product

Fig. 1 Temperature ranges of the different enzyme families (gray background; data from Table 1) and in which the different types of chemical catalyses of lignin and lignin model compounds (white background) were performed (data from Zakzeski et al. (2010a)). Family LDA1-8 lignin-degrading auxiliary enzymes

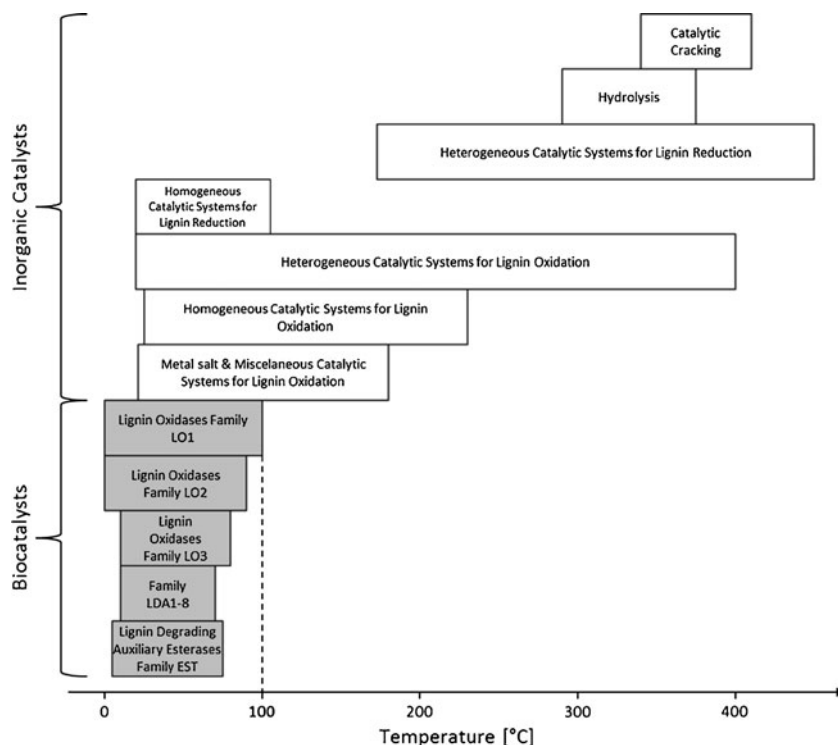

and time savings (Arnold 1990; Ogino and Ishikawa 2001; García-Ruiz et al. 2010).

However, increasing stability through point mutations often leads to a trade-off between stability and activity (García-Ruiz et al. 2010). Stability increases are mostly gained through mutations, which establish new interactions and thereby prevent unfolding and denaturation under harsh conditions (Reetz et al. 2006). At the opposite, activity increases are mostly achieved through destabilizing mutations that lead to better access for the substrates to the active sites of the enzymes (Bloom and Arnold 2009). Therefore, to produce enzymes with increased stability and activity, several mutations are often necessary. Several studies reported the increase of enzyme thermostabilities of LMEs through mutations, also often in combination with increased activities (Reading and Aust 2000; Morawski et al. 2001; Festa et al. 2008; García-Ruiz et al. 2010). For instance, a recombinant MnP had a higher activity than the native enzyme produced by *Phanerochaete chrysosporium* but was also more readily inactivated at temperatures of 37 °C and above (Reading and Aust 2000). The recombinant enzyme was modified by the insertion of a disulfide bond, which increased the enzyme's thermostability while retaining its enhanced activity. The newly built enzyme retained most of its activity up to a temperature of 52 °C, where it was inactivated at a similar rate as the native enzyme (Reading and Aust 2000). Other studies applied directed evolution to improve the thermostability of, e.g., a horseradish peroxidase (Morawski et al. 2001), laccase from *P. ostreatus* (Festa et al. 2008), and VP from *Pleurotus eryngii* together with high-redox-potential laccase from basidiomycete PM1

(García-Ruiz et al. 2010). The enzymes were expressed in *Saccharomyces cerevisiae* in all three studies. The half-life of the newly developed horseradish peroxidase was increased by a factor of 3 (Morawski et al. 2001) and that of laccase by a factor of 1.4 (Festa et al. 2008) in comparison to the native enzyme at 60 °C. The study aiming to improve the thermostability of VP and high-redox-potential laccase reported that the VP retained ~30 % of its maximal activity at 65 °C (three times more than the native enzyme) and the high-redox-potential laccase retained 40 % of its maximal activity at 72 °C (ten times more than the native enzyme) (García-Ruiz et al. 2010).

H₂O₂ tolerance of peroxidases

Peroxidases are inactivated by too high substrate, i.e., H₂O₂, concentrations. The oxidative damage of peroxidases has been referred to as suicide inactivation (Valderrama et al. 2002). Since H₂O₂ is needed by peroxidases to degrade lignin, either control of H₂O₂ concentrations or increased tolerance of peroxidases to higher H₂O₂ concentration levels is necessary to run continuous processes. Control of H₂O₂ concentrations could be achieved either by supplying H₂O₂ to fed batches (Mielgo et al. 2003) through electro-chemical methods (Lee and Moon 2003) or through the control of H₂O₂-producing enzymes (Lan et al. 2006). Some studies report on the operation of continuous processes with LiP from *Phanerochaete chrysosporium* whereby the enzymatic production of H₂O₂ was used as a mean to control the concentration of the latter (Lan et al. 2006; Qiu et al. 2009).

H₂O₂ was supplied by glucose oxidase from *Aspergillus niger*, which was in turn controlled through regulation of glucose concentration and pH. The effectiveness of this combination was demonstrated through the conversion of different dyes. In one study, 90.9 % of rhodamine B was converted over 1 h when H₂O₂ was produced enzymatically compared to only 41.0 % when H₂O₂ was supplied externally every 5 min (Lan et al. 2006). Total supplied H₂O₂ amounts over the course of the whole experiment were 300 μM in both cases (Lan et al. 2006). In another study, LiP and glucose oxidase were co-immobilized on nanoporous gold (Qiu et al. 2009). Some 87.2, 75.5, and 84.6 % of pyragallol red, rhodamine B, and fuchsine, respectively, were converted over 3 h when H₂O₂ was supplied enzymatically compared to only 55.6, 44.3 and 53.5 % when LiP was immobilized as a single enzyme and 1 μM H₂O₂ was supplied externally in one pulse at the beginning of the experiment (Qiu et al. 2009).

Gil-Rodríguez et al. (2008) reported the isolation of a peroxidase from daikon radish (*Raphanus sativus* L. cv. daikon) resistant to H₂O₂, named Zo peroxidase. Future detailed study of the enzyme structure of Zo peroxidase might reveal the properties responsible for its H₂O₂ tolerance and may help in the production of further H₂O₂-resistant peroxidases (Gil-Rodríguez et al. 2008). Several studies reported achieving enhanced H₂O₂ tolerance of ligninolytic peroxidases through mutagenesis. For example, MnP from *P. chrysosporium* with nine times higher H₂O₂ stability (Miyazaki-Imamura et al. 2003) and horseradish peroxidases with 25-, 18-, and 12-fold increased H₂O₂ stability (Ryan and Ó'Fágáin 2007) compared to the wild type were reported. Furthermore, increased H₂O₂ tolerance of a VP from *Bjerkandera adusta* was achieved by producing cross-linked enzyme aggregates of VP in combination with glucose oxidase from *A. niger* (Taboada-Puig et al. 2011).

Stability in non-aqueous solvents

Lignin can be dissolved in some organic solvents (Muurinen 2000; Zhao et al. 2009), making it more available for catalysts. However, enzymes are usually inactivated and denatured in the presence of organic solvents (Doukyu and Ogino 2010) since they generally require water to maintain their native structure by promoting non-covalent interactions like hydrogen bonds, and van der Waals, hydrophobic, and ionic interactions (Singer 1963). Furthermore, polar solvents are able to enter the protein's interior which might induce secondary and tertiary structural changes and are more able than apolar solvents to remove protein-bound water (Serdakowski and Dordick 2008). Additionally, the higher solubility of the substrate in organic solvents constitutes a thermodynamic stabilization of the substrate in its initial state, which leads to a decrease of the observed enzymatic activity (Serdakowski and

Dordick 2008). Changing solvent polarity can lead to a more stable transition state and therefore reduce the activation energy of the catalyzed reaction as shown, for example, for subtilisin-catalyzed transesterification reactions in organic solvents (Kim et al. 2000). Therefore, the addition of small amounts of water and the decrease of solvent polarity can lead to more enzymatic activity in organic solvents (Serdakowski and Dordick 2008). Another way to obtain active enzymes in non-aqueous solvents is protein engineering (Serdakowski and Dordick 2008). No LMEs are reported to be organic solvent tolerant by nature in a recent review on the subject (Doukyu and Ogino 2010). However, several studies successfully maintained the enzymatic activity of LMEs in organic solvents (e.g., Dai and Klivanov 1999; Ozawa and Klivanov 2000; van de Velde et al. 2001; Liu et al. 2006; Zumárraga et al. 2007).

Alternatively, biomass can be dissolved in ILs. Several ILs are able to dissolve lignocellulose and allow the separation and at least partial recovery of each fraction. The solubility of carbohydrates and lignin in ILs has been reviewed recently (Zakrzewska et al. 2010). The highest solubility of kraft lignin was achieved using 1,3-dimethylimidazolium methanesulfonate ([Mmim] [CH₃OSO₃]) or 1,3-dimethylimidazolium trifluoromethanesulfonate ([Bmim] [CF₃SO₃]) as solvent (Lee et al. 2009).

Several reviews discuss enzymatic reactions and enzyme stabilization in ILs (e.g., Cantone et al. 2007; van Rantwijk and Sheldon 2007; Gorke et al. 2010; Zhao 2010). Dissolution of lignocellulose in ILs and prospects on possible future uses of ILs in biorefineries are discussed in a recent feature article (Sun et al. 2011). The possibility to directly dissolve lignocellulose and separate lignin from cellulose and hemicellulose might allow an exhaustive utilization thereof and has the potential to facilitate the treatment of lignin with biocatalysts (Sun et al. 2011).

Enzyme immobilization

Enzyme immobilization can improve the properties of biocatalysts by increasing their stability and activity under various conditions (e.g., extreme pHs, organic solvents, elevated temperatures) (Bommarius and Riebel-Bommarius 2004) and allows enzyme reuse and biocatalysts separation from reaction products, thereby permitting the operation of continuous processes (Polizzi et al. 2007). Immobilization techniques have been the subject of several recently published reviews (e.g., Mateo et al. 2007; Brady and Jordaan 2009; Hartmann and Jung 2010; Jochems et al. 2011).

In a recent study, laccase from *T. versicolor* and horseradish peroxidase were co-immobilized on aluminum particles by cross-linking and layer-by-layer coating with alternatively charged polyelectrolytes (Crestini et al. 2011). The resulting multi-enzyme biocatalysts had increased stability compared to

the free enzymes. A total of 2 gL^{-1} milled wheat straw lignin was treated with the biocatalysts in water. Before the start of the experiment, the wheat straw lignin was completely insoluble. After treatment with the biocatalysts, 61.3 and 59.8 % (w/w) of milled wheat straw lignin were in solution with and without addition of a chemical laccase mediator, respectively. The water-soluble material consisted of polymers with significantly lower average molecular weight than the starting material, demonstrating that lignin depolymerization outweighed lignin solubilization. Control experiments with free enzymes and singly immobilized enzymes (used alone or in mixture, with or without laccase mediator) led to less efficient lignin conversion and depolymerization (Crestini et al. 2011). Furthermore, the immobilized catalysts could be recycled more than ten times. This study gives further indication that a multi-catalyst approach is expedient for lignin depolymerization and demonstrates the advantages of immobilized enzymes over free enzymes due to higher stability and recyclability.

Chemoenzymatic combination

The complex mechanism of lignin degradation in nature and the limited success of lignin depolymerization with single catalysts indicate that efficient lignin conversion to platform and fine chemicals might only be achieved by combining various catalysts. Making use of the unique properties of biocatalysts as well as of chemical catalysts represents a new approach (Vennestrøm et al. 2010a).

One possibility to treat lignin using chemical catalysts as well as biocatalysts would be a sequential treatment in several reactors, allowing optimal reaction conditions for each catalyst. While this might be necessary for certain reactions (especially reactions with chemical catalysts only working effectively at high temperatures), using multiple catalysts in one reactor would offer several advantages, such as process intensification, reduction of product separation and purification steps, material consumption, waste generation, and time and yield losses (Murzin and Leino 2008; Vennestrøm et al. 2010a). However, conducting such one-pot catalytic transformations is challenging. Temperature and reaction media (as already discussed in the previous chapter), pressure, compatibility, and reaction rates are key parameters to consider when combining enzymes and inorganic catalysts (Vennestrøm et al. 2010a). The highest pressure used in chemical catalysis as reported by a recent review (Zakzeski et al. 2010a) was 46 MPa (Kashima et al. 1964). However, these processes were conducted at temperatures between 250 and 450 °C and are therefore unsuitable for enzymatic reactions. The highest pressure for chemical catalysis conducted at 100 °C or below as reported by the same review was 18 MPa (Borthakur 2007). Pressures in this order of magnitude seem to have

only limited effects on enzyme stability as pressures of 100–200 MPa are required to dissociate oligomeric proteins (Silva and Weber 1993) and even higher pressures of 400–800 MPa are needed to denature small monomeric proteins (Heremans 1982).

Compatibility between reactants, intermediates, substrates, and bio- and inorganic catalysts that are employed in one-pot processes is more crucial and has to be ensured (Vennestrøm et al. 2010a). Furthermore, reaction rates have to be adjusted in order to avoid the formation of undesired compounds or substrate limitation for one of the catalysts (Murzin and Leino 2008; Vennestrøm et al. 2010a). Therefore, reliable kinetic models describing the transformation processes have to be developed, which is not an easy task because a lot of parameters and variables have to be considered and integrated together in the models, e.g., catalyst–catalyst interactions, mass transfer processes, feedback inhibition, etc. (Murzin and Leino 2008). Recently, processes relying on the chemo-enzymatic conversion of biomass were discussed in a further review, which however did not mention the use of lignin as feedstock (Marr and Liu 2011).

While chemo-enzymatic combinations for lignin transformation have not been extensively explored so far, several interactions between LMEs and chemical transformation processes can be envisioned (Fig. 2). Chemical transformation of lignin could provide compounds that can be used by laccases as mediators (Fig. 2, a). Phenol—a compound that has been shown to act as laccase mediator for the oxidation of, e.g., polycyclic aromatic hydrocarbons like anthracene (Johannes and Majcherczyk 2000)—has been produced by, e.g., hydrocracking of organocell lignin (Meier et al. 1994). Chemical oxidation of lignin has led to the formation of other compounds that have been reported to act as laccase mediators in a recent review (Cañas and Camarero 2010), e.g., vanillin (e.g., Badamali et al. 2009; Partenheimer 2009; Werhan et al. 2011) or aceto vanillone (e.g., Crestini et al. 2005, 2006; Badamali et al. 2009). Therefore, employing laccase in combination with certain chemical catalysts might lead to in situ production of laccase mediators, and consequently the addition of laccase mediators in advance might not be necessary.

Furthermore, the different oxidases can be employed for H_2O_2 production (Fig. 2, b). This has been demonstrated in a recent study (Vennestrøm et al. 2010b). Glucose oxidase from *A. niger* was immobilized on a titanium silicate catalyst. The H_2O_2 produced as a side-product by the glucose oxidase-catalyzed oxidation of one substrate (e.g., β -glucopyranose) was used as oxidizing agent by the chemical catalyst for the oxidation of another substrate (e.g., allyl alcohol, 2-butanol, 2-propanol, crotyl alcohol). A similar combination can be envisaged between FAD-oxidase enzymes and, for example, MTO catalysts that require H_2O_2 as primary oxidant for the oxidation of lignin (e.g.,

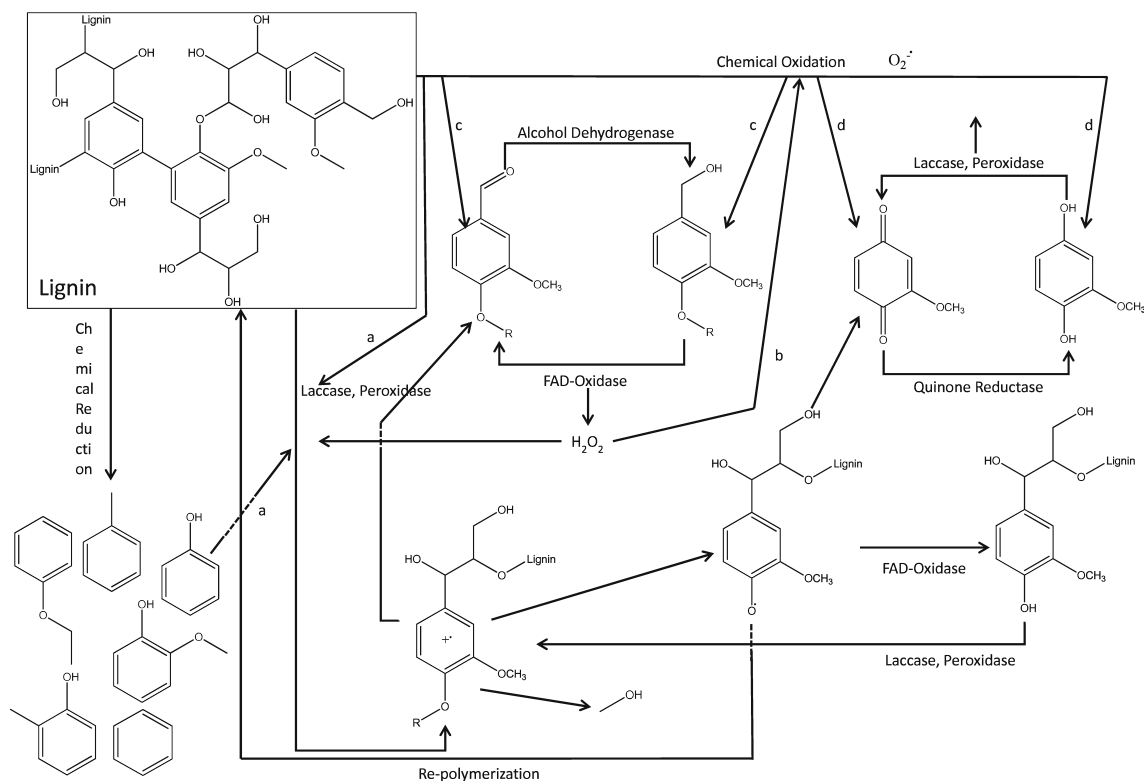


Fig. 2 Scheme depicting possible interactions between biological and chemical lignin degradation (for explanation, see text)

Herrmann et al. 2000; Crestini et al. 2005, 2006). The degradation of lignin or lignin model compounds by the MTO/H₂O₂ oxidation system has led to the formation of aromatic aldehydes (Herrmann et al. 2000; Crestini et al. 2005, 2006) as well as aromatic alcohols (Herrmann et al. 2000) (Fig. 2, c). These products could be directly used by FAD-oxidases and alcohol dehydrogenases in redox cycles for the further production of H₂O₂. Moreover, repolymerization of intermediates like quinonoids and radical compounds during lignin degradation might be prevented by employing FAD-oxidases.

Chemical oxidation of lignin by, e.g., polyoxometalate (POM) (Gaspar et al. 2007) or Co(salen) (Canevali et al. 2002) catalysts can result in quinones and hydroquinones that can be used by quinone reductases, laccases, and peroxidases in redox cycles for the production of superoxide radicals (Fig. 2, d). Furthermore, it has been shown that laccase can re-oxidize reduced POM catalysts. This has been used for the continuous delignification of eucalypt kraft pulp (Gamelas et al. 2007). The POM catalyst ([SiW₁₁V^VO₄₀]⁻⁵) was employed at around 90 °C in a batch reactor for pulp delignification. Laccase from *T. versicolor* was applied in a separate aerated batch reactor for the re-oxidation of the reduced POM catalysts at 45 °C. The re-oxidized chemical catalysts were separated from the enzymes via an ultrafiltration ceramic membrane and returned to the first reactor. By this continuous system,

nearly 70 % of pulp delignification was obtained (Gamelas et al. 2007).

Such possible interactions between catalysts show the large potential for new multi-catalyst processes for lignin transformation. Their development might be essential for a more efficient valorization of the biopolymer.

Conclusions

Lignin depolymerization using single inorganic catalysts had limited success. Advances in enzyme engineering and immobilization, emergence of new solvents, and new chemical catalyst design lead to an increasing degree of overlap of reaction conditions in which enzymes and inorganic catalysts can operate. These new possibilities for catalyst combinations open promising perspectives for novel technologies in the field of green chemistry. Sequential or one-pot multi-catalyst processes have the potential to play an important role in the conversion of the renewable feedstock lignin into value-added fine chemicals and should become the focus of future research.

Acknowledgments The support of the Swiss National Science Foundation, National Research Program 66 (Project 4066-136686), and the Commission for Technology and Innovation of the Swiss Federal Office for Professional Education and Technology (Grant PFNM-NM 12608.1) is gratefully acknowledged.

Conflict of interest The authors declare that they have no conflict of interest.

References

- Achyuthan KE, Achyuthan AM, Adams PD, Dirk SM, Harper JC, Simmons BA, Singh AK (2010) Supramolecular self-assembled chaos: polyphenolic lignin's barrier to cost-effective lignocellulosic biofuels. *Molecules* 15:8641–8688. doi:10.3390/molecules15118641
- Ahmad M, Roberts JN, Hardiman EM, Singh R, Eltis LD, Bugg TDH (2011) Identification of DypB from *Rhodococcus jostii* RHA1 as a lignin peroxidase. *Biochemistry-US* 50:5096–5107. doi:10.1021/bi101892z
- Aitken MD, Irvine RL (1989) Stability testing of ligninase and Mn-peroxidase from *Phanerochaete chrysosporium*. *Biotechnol Bioeng* 34:1251–1260. doi:10.1002/bit.260341003
- Akamatsu Y, Shimada M (1994) Partial purification and characterization of glyoxylate oxidase from the brown-rot basidiomycete *Tyromyces palustris*. *Phytochemistry* 37:649–653. doi:10.1016/s0031-9422(00)90332-7
- Alam MZ, Mansor MF, Jalal KCA (2009) Optimization of decolorization of methylene blue by lignin peroxidase enzyme produced from sewage sludge with *Phanerochaete chrysosporium*. *J Hazard Mater* 162:708–715. doi:10.1016/j.jhazmat.2008.05.085
- Alberton D, Silva de Oliveira L, Peralta RM, Barbosa-Tessmann IP (2007) Production, purification, and characterization of a novel galactose oxidase from *Fusarium acuminatum*. *J Basic Microb* 47:203–212. doi:10.1002/jobm.200610290
- Altikatoglu M, Basaran Y, Arioç C, Ogan A, Kuzu H (2010) Glucose oxidase–dextran conjugates with enhanced stabilities against temperature and pH. *Appl Biochem Biotechnol* 160:2187–2197. doi:10.1007/s12010-009-8812-8
- Arnold FH (1990) Engineering enzymes for non-aqueous solvents. *Trends Biotechnol* 8:244–249. doi:10.1016/0167-7799(90)90186-2
- Artolozaga MJ, Kubátová E, Volc J, Kalisz HM (1997) Pyranose 2-oxidase from *Phanerochaete chrysosporium*—further biochemical characterisation. *Appl Microbiol Biotechnol* 47:508–514. doi:10.1007/s002530050964
- Auhorn WJ, Niemela K (2007) Process chemicals for the production of chemical pulp. *Prof Papermak* 2:10–20
- Aurilia V, Parracino A, Saviano M, Rossi M, D'Auria S (2007) The psychrophilic bacterium *Pseudoalteromonas haloplanktis* TAC125 possesses a gene coding for a cold-adapted feruloyl esterase activity that shares homology with esterase enzymes from γ -proteobacteria and yeast. *Gene* 397:51–57. doi:10.1016/j.gene.2007.04.004
- Backa S, Gierer J, Reitberger T, Nilsson T (1992) Hydroxyl radical activity in brown-rot fungi studied by a new chemiluminescence method. *Holzforchung* 46:61–67. doi:10.1515/hfsg.1992.46.1.61
- Badamali SK, Luque R, Clark JH, Breeden SW (2009) Microwave assisted oxidation of a lignin model phenolic monomer using Co (salen)/SBA-15. *Catal Commun* 10:1010–1013. doi:10.1016/j.catcom.2008.12.051
- Baldrian P (2004) Purification and characterization of laccase from the white-rot fungus *Daedalea quercina* and decolorization of synthetic dyes by the enzyme. *Appl Microbiol Biotechnol* 63:560–563. doi:10.1007/s00253-003-1434-0
- Baldrian P (2006) Fungal laccases—occurrence and properties. *FEMS Microbiol Rev* 30:215–242. doi:10.1111/j.1574-4976.2005.00010.x
- Ball AS, Betts WB, McCarthy AJ (1989) Degradation of lignin-related compounds by actinomycetes. *Appl Environ Microbiol* 55:1642–1644
- Baminger U, Subramaniam SS, Renganathan V, Haltrich D (2001) Purification and characterization of cellobiose dehydrogenase from the plant pathogen *Sclerotium (Athelia) rolfsii*. *Appl Environ Microbiol* 67:1766–1774. doi:10.1128/aem.67.4.1766-1774.2001
- Bayramoğlu G, Kiralp S, Yilmaz M, Toppare L, Arica MY (2008) Covalent immobilization of chloroperoxidase onto magnetic beads: catalytic properties and stability. *Biochem Eng J* 38:180–188. doi:10.1016/j.bej.2007.06.018
- Bloom JD, Arnold FH (2009) In the light of directed evolution: pathways of adaptive protein evolution. *Proc Natl Acad Sci U S A* 106:9995–10000. doi:10.1073/pnas.0901522106
- Bommarius A, Riebel-Bommarius B (2004) *Biocatalysis: fundamentals and applications*. Wiley, New York
- Borthakur N (2007) World Intellectual Property Organization. WO 2007/094013 A1
- Brady D, Jordaan J (2009) Advances in enzyme immobilisation. *Biotechnol Lett* 31:1639–1650. doi:10.1007/s10529-009-0076-4
- Bugg TDH, Ahmad M, Hardiman EM, Singh R (2011) The emerging role for bacteria in lignin degradation and bio-product formation. *Curr Opin Biotechnol* 22:394–400. doi:10.1016/j.copbio.2010.10.009
- Buswell JA, Odier E (1987) Lignin biodegradation. *Crc Crit Rev Biotechnol* 6:1–60. doi:10.3109/07388558709086984
- Camarero S, Sarkar S, Ruiz-Dueñas FJ, Martínez MJ, Martínez ÁT (1999) Description of a versatile peroxidase involved in the natural degradation of lignin that has both manganese peroxidase and lignin peroxidase substrate interaction sites. *J Biol Chem* 274:10324–10330. doi:10.1074/jbc.274.15.10324
- Cañas AI, Camarero S (2010) Laccases and their natural mediators: biotechnological tools for sustainable eco-friendly processes. *Biotechnol Adv* 28:694–705. doi:10.1016/j.biotechadv.2010.05.002
- Canevali C, Orlandi M, Pardi L, Rindone B, Scotti R, Sipila J, Morazzoni F (2002) Oxidative degradation of monomeric and dimeric phenylpropanoids: reactivity and mechanistic investigation. *J Chem Soc Dalton* 15:3007–3014. doi:10.1039/B203386K
- Cantone S, Hanefeld U, Basso A (2007) Biocatalysis in non-conventional media-ionic liquids, supercritical fluids and the gas phase. *Green Chem* 9:954–971. doi:10.1039/B618893A
- Cheng X, Jia R, Li P, Tu S, Zhu Q, Tang W, Li X (2007) Purification of a new manganese peroxidase of the white-rot fungus *Schizophyllum* sp. F17, and decolorization of azo dyes by the enzyme. *Enzyme Microb Technol* 41:258–264. doi:10.1016/j.enzmictec.2007.01.020
- Cohen R, Suzuki MR, Hammel KE (2005) Processive endoglucanase active in crystalline cellulose hydrolysis by the brown rot basidiomycete *Gloeophyllum trabeum*. *Appl Environ Microbiol* 71:2412–2417. doi:10.1128/aem.71.5.2412-2417.2005
- Collinson SR, Thielemans W (2010) The catalytic oxidation of biomass to new materials focusing on starch, cellulose and lignin. *Coord Chem Rev* 254:1854–1870. doi:10.1016/j.ccr.2010.04.007
- Couderc R, Baratti J (1980) Oxidation of methanol by the yeast, *Pichia pastoris*. Purification and properties of the alcohol oxidase. *Agric Biol Chem* 44:2279–2289
- Courjean O, Mano N (2011) Recombinant glucose oxidase from *Penicillium amagasakiense* for efficient bioelectrochemical applications in physiological conditions. *J Biotechnol* 151:122–129. doi:10.1016/j.jbiotec.2010.10.077
- Crestini C, Pro P, Neri V, Saladino R (2005) Methyltrioxorhenium: a new catalyst for the activation of hydrogen peroxide to the oxidation of lignin and lignin model compounds. *Bioorg Med Chem* 13:2569–2578. doi:10.1016/j.bmc.2005.01.049
- Crestini C, Caponi MC, Argyropoulos DS, Saladino R (2006) Immobilized methyltrioxo rhenium (MTO)/H₂O₂ systems for the oxidation of lignin and lignin model compounds. *Bioorg Med Chem* 14:5292–5302. doi:10.1016/j.bmc.2006.03.046
- Crestini C, Melone F, Saladino R (2011) Novel multienzyme oxidative biocatalyst for lignin bioprocessing. *Bioorg Med Chem* 19:5071–5078. doi:10.1016/j.bmc.2011.05.058

- Crognale S, Pulci V, Brozzoli V, Petruccioli M, Federici F (2006) Expression of *Penicillium variabile* P16 glucose oxidase gene in *Pichia pastoris* and characterization of the recombinant enzyme. *Enzyme Microb Technol* 39:1230–1235. doi:10.1016/j.enzmictec.2006.03.005
- Cyr A, Chiltz F, Jeanson P, Martel A, Brossard L, Lessard J, Ménard H (2000) Electrocatalytic hydrogenation of lignin models at Raney nickel and palladium-based electrodes. *Can J Chem* 78:307–315. doi:10.1139/v00-009
- da Costa Sousa L, Chundawat SPS, Balan V, Dale BE (2009) ‘Cradle-to-grave’ assessment of existing lignocellulose pretreatment technologies. *Curr Opin Biotechnol* 20:339–347. doi:10.1016/j.copbio.2009.05.003
- Dabo P, Cyr A, Lessard J, Brossard L, Ménard H (1999) Electrocatalytic hydrogenation of 4-phenoxyphenol on active powders highly dispersed in a reticulated vitreous carbon electrode. *Can J Chem* 77:1225–1229. doi:10.1139/v99-120
- Dai L, Klibanov AM (1999) Striking activation of oxidative enzymes suspended in nonaqueous media. *Proc Natl Acad Sci U S A* 96:9475–9478. doi:10.1073/pnas.96.17.9475
- de Jong E, van Berkel WJH, van der Zwan RP, de Bont JAM (1992) Purification and characterization of vanillyl-alcohol oxidase from *Penicillium simplicissimum*. *Eur J Biochem* 208:651–657. doi:10.1111/j.1432-1033.1992.tb17231.x
- Doğan S, Turan P, Doğan M, Arslan O, Alkan M (2005) Purification and characterization of *Ocimum basilicum* L. polyphenol oxidase. *J Agric Food Chem* 53:10224–10230. doi:10.1021/jf051646j
- Doherty WOS, Mousavioun P, Fellows CM (2011) Value-adding to cellulosic ethanol: lignin polymers. *Ind Crop Prod* 33:259–276. doi:10.1016/j.indcrop.2010.10.022
- Dominguez-Ramos A, Aldaco R, Irabien A (2008) Electrochemical oxidation of lignosulfonate: total organic carbon oxidation kinetics. *Ind Eng Chem Res* 47:9848–9853. doi:10.1021/ie801109c
- Dominguez-Ramos A, Aldaco R, Irabien A (2010a) Photovoltaic solar electrochemical oxidation (PSEO) for lignosulphonate waste water treatment. *Chem Eng Trans* 21:379–384. doi:10.3303/CET1021064
- Dominguez-Ramos A, Aldaco R, Irabien A (2010b) Photovoltaic solar electrochemical oxidation (PSEO) for treatment of lignosulfonate wastewater. *J Chem Technol Biotechnol* 85:821–830. doi:10.1002/jctb.2370
- Doukyu N, Ogino H (2010) Organic solvent-tolerant enzymes. *Biochem Eng J* 48:270–282. doi:10.1016/j.bej.2009.09.009
- Dubé E, Shareck F, Hurtubise Y, Daneault C, Beaugregard M (2008) Homologous cloning, expression, and characterisation of a laccase from *Streptomyces coelicolor* and enzymatic decolorisation of an indigo dye. *Appl Microbiol Biotechnol* 79:597–603. doi:10.1007/s00253-008-1475-5
- Eijssink VGH, Gåseidnes S, Borchert TV, van den Burg B (2005) Directed evolution of enzyme stability. *Biomol Eng* 22:21–30. doi:10.1016/j.bioeng.2004.12.003
- El-Ashtouky ESZ, Amin NK, Abdelwahab O (2009) Treatment of paper mill effluents in a batch-stirred electrochemical tank reactor. *Chem Eng J* 146:205–210. doi:10.1016/j.cej.2008.05.037
- Enoki M, Watanabe T, Nakagame S, Koller K, Messner K, Honda Y, Kuwahara M (1999) Extracellular lipid peroxidation of selective white-rot fungus, *Ceriporiopsis subvermispora*. *FEMS Microbiol Lett* 180:205–211. doi:10.1111/j.1574-6968.1999.tb08797.x
- Evans CS, Dutton MV, Guillén F, Veness RG (1994) Enzymes and small molecular mass agents involved with lignocellulose degradation. *FEMS Microbiol Rev* 13:235–239. doi:10.1111/j.1574-6976.1994.tb00044.x
- Faith WL, Keyes DB, Clark DS (1965) *Industrial chemicals*. Wiley, New York
- Faulds C (2010) What can feruloyl esterases do for us? *Phytochem Rev* 9:121–132. doi:10.1007/s11101-009-9156-2
- Ferreira P, Medina M, Guillen F, Martinez MJ, Van Berkel WJ, Martinez AT (2005) Spectral and catalytic properties of aryl-alcohol oxidase, a fungal flavoenzyme acting on polyunsaturated alcohols. *Biochem J* 389:731–738. doi:10.1042/bj20041903
- Festa G, Autore F, Fraternali F, Giardina P, Sannia G (2008) Development of new laccases by directed evolution: functional and computational analyses. *Proteins* 72:25–34. doi:10.1002/prot.21889
- Forney LJ, Reddy CA, Tien M, Aust SD (1982) The involvement of hydroxyl radical derived from hydrogen peroxide in lignin degradation by the white rot fungus *Phanerochaete chrysosporium*. *J Biol Chem* 257:11455–11462
- Gamelas JAF, Pontes ASN, Evtuguin DV, Xavier AMRB, Esculcas AP (2007) New polyoxometalate-laccase integrated system for kraft pulp delignification. *Biochem Eng J* 33:141–147. doi:10.1016/j.bej.2006.10.014
- García-Conesa MT, Crepin VF, Goldson AJ, Williamson G, Cummings NJ, Connerton IF, Faulds CB, Kroon PA (2004) The feruloyl esterase system of *Talaromyces stipitatus*: production of three discrete feruloyl esterases, including a novel enzyme, TsFaeC, with a broad substrate specificity. *J Biotechnol* 108:227–241. doi:10.1016/j.jbiotec.2003.12.003
- García-Ruiz E, Maté D, Ballesteros A, Martínez ÁT, Alcalde M (2010) Evolving thermostability in mutant libraries of ligninolytic oxidoreductases expressed in yeast. *Microb Cell Fact* 9:1–13. doi:10.1186/1475-2859-9-17
- Gaspar AR, Gamelas JAF, Evtuguin DV, Pascoal Neto C (2007) Alternatives for lignocellulosic pulp delignification using polyoxometalates and oxygen: a review. *Green Chem* 9:717–730. doi:10.1039/B607824A
- Ghodake G, Kalme S, Jadhav J, Govindwar S (2009) Purification and partial characterization of lignin peroxidase from *Acinetobacter calcoaceticus* NCIM 2890 and its application in decolorization of textile dyes. *Appl Biochem Biotechnol* 152:6–14. doi:10.1007/s12010-008-8258-4
- Giardina P, Palmieri G, Fontanella B, Rivieccio V, Sannia G (2000) Manganese peroxidase isoenzymes produced by *Pleurotus ostreatus* grown on wood sawdust. *Arch Biochem Biophys* 376:171–179. doi:10.1006/abbi.1999.1691
- Giardina P, Faraco V, Pezzella C, Piscitelli A, Vanhulle S, Sannia G (2010) Laccases: a never-ending story. *Cell Mol Life Sci* 67:369–385. doi:10.1007/s00018-009-0169-1
- Gil-Rodríguez P, Ferreira-Batista C, Vázquez-Duhalt R, Valderrama B (2008) A novel heme peroxidase from *Raphanus sativus* intrinsically resistant to hydrogen peroxide. *Eng Life Sci* 8:286–296. doi:10.1002/elsc.200700073
- Glenn JK, Gold MH (1985) Purification and characterization of an extracellular Mn(II)-dependent peroxidase from the lignin-degrading basidiomycete, *Phanerochaete chrysosporium*. *Arch Biochem Biophys* 242:329–341. doi:10.1016/0003-9861(85)90217-6
- Gluckstein J, Hu M, Kidder M, McFarlane J, Narula C, Sturgeon M (2010) Final report: investigation of catalytic pathways for lignin breakdown into monomers and fuels (trans: Division EaTS). Oak Ridge National Laboratory, Oak Ridge
- Godden B, Ball AS, Helvenstein P, Mccarthy AJ, Penninckx MJ (1992) Towards elucidation of the lignin degradation pathway in actinomycetes. *J Gen Microbiol* 138:2441–2448. doi:10.1099/00221287-138-11-2441
- Gold MH, Kuwahara M, Chiu AA, Glenn JK (1984) Purification and characterization of an extracellular H₂O₂-requiring diarylpropane oxygenase from the white rot basidiomycete, *Phanerochaete chrysosporium*. *Arch Biochem Biophys* 234:353–362. doi:10.1016/0003-9861(84)90280-7
- Gold MH, Youngs HL, Gelpke MD (2000) Manganese peroxidase. *Met Ions Biol Syst* 37:559–586
- Gomes E, Aguiar AP, Carvalho CC, Bonfá MRB, da Silva R, Boscolo M (2009) Ligninases production by Basidiomycetes strains on

- lignocellulosic agricultural residues and their application in the decolorization of synthetic dyes. *Braz J Microbiol* 40:31–39. doi:10.1590/S1517-83822009000100005
- Gómez-Toribio V, Martínez AT, Martínez MJ, Guillén F (2001) Oxidation of hydroquinones by the versatile ligninolytic peroxidase from *Pleurotus eryngii*. *Eur J Biochem* 268:4787–4793. doi:10.1046/j.1432-1327.2001.02405.x
- Gómez-Toribio V, Garcia-Martin AB, Martinez MJ, Martinez ÁT, Guillen F (2009) Induction of extracellular hydroxyl radical production by white-rot fungi through quinone redox cycling. *Appl Environ Microbiol* 75:3944–3953. doi:10.1128/aem.02137-08
- Gorke J, Srienec F, Kazlauskas R (2010) Toward advanced ionic liquids. Polar, enzyme-friendly solvents for biocatalysis. *Biotechnol Bioproc Eng* 15:40–53. doi:10.1007/s12257-009-3079-z
- Gross GG, Zenk MH (1969) Reduktion aromatischer Säuren zu Aldehyden und Alkoholen im zellfreien System. *Eur J Biochem* 8:420–425. doi:10.1111/j.1432-1033.1969.tb00544.x
- Guillén F, Martínez ÁT, Martínez MJ (1992) Substrate specificity and properties of the aryl–alcohol oxidase from the ligninolytic fungus *Pleurotus eryngii*. *Eur J Biochem* 209:603–611. doi:10.1111/j.1432-1033.1992.tb17326.x
- Guillén F, Martínez MJ, Muñoz C, Martínez ÁT (1997) Quinone redox cycling in the ligninolytic fungus *Pleurotus eryngii* leading to extracellular production of superoxide anion radical. *Arch Biochem Biophys* 339:190–199. doi:10.1006/abbi.1996.9834
- Guillén F, Gómez-Toribio V, Martínez MJ, Martínez ÁT (2000) Production of hydroxyl radical by the synergistic action of fungal laccase and aryl alcohol oxidase. *Arch Biochem Biophys* 383:142–147. doi:10.1006/abbi.2000.2053
- Gülçin İ, İrfan Küfrevioğlu Ö, Oktay M (2005) Purification and characterization of polyphenol oxidase from nettle (*Urtica dioica* L.) and inhibitory effects of some chemicals on enzyme activity. *J Enzym Inhib Med Chem* 20:297–302. doi:10.1080/1475636032000141890
- Gvozdev A, Tuhvatullin I, Gvozdev R (2010) Purification and properties of alcohol oxidase from *Pichia putida*. *Biochem Mosc* 75:242–248. doi:10.1134/s000629791002015x
- Haibo Z, Yinglong Z, Feng H, Peiji G, Jiachuan C (2009) Purification and characterization of a thermostable laccase with unique oxidative characteristics from *Trametes hirsuta*. *Biotechnol Lett* 31:837–843. doi:10.1007/s10529-009-9945-0
- Hailes HC, Dalby PA, Woodley JM (2007) Integration of biocatalytic conversions into chemical syntheses. *J Chem Technol Biotechnol* 82:1063–1066. doi:10.1002/jctb.1763
- Hammel KE, Cullen D (2008) Role of fungal peroxidases in biological ligninolysis. *Curr Opin Plant Biol* 11:349–355. doi:10.1016/j.pbi.2008.02.003
- Hammel KE, Kapich AN, Jensen JKA, Ryan ZC (2002) Reactive oxygen species as agents of wood decay by fungi. *Enzyme Microb Technol* 30:445–453. doi:10.1016/s0141-0229(02)00011-x
- Harreither W, Sygmund C, Augustin M, Narciso M, Rabinovich ML, Gorton L, Haltrich D, Ludwig R (2011) Catalytic properties and classification of cellobiose dehydrogenases from ascomycetes. *Appl Environ Microbiol* 77:1804–1815. doi:10.1128/aem.02052-10
- Hartmann M, Jung D (2010) Biocatalysis with enzymes immobilized on mesoporous hosts: the status quo and future trends. *J Mater Chem* 20:844–857. doi:10.1039/B907869J
- Hashemifard N, Mohsenifar A, Ranjbar B, Allameh A, Lotfi AS, Etemadikia B (2010) Fabrication and kinetic studies of a novel silver nanoparticles–glucose oxidase bioconjugate. *Anal Chim Acta* 675:181–184. doi:10.1016/j.aca.2010.07.004
- Hatakka A (1994) Lignin-modifying enzymes from selected white-rot fungi: production and role from in lignin degradation. *FEMS Microbiol Rev* 13:125–135
- Hatakka A, Hammel KE (2010) Fungal biodegradation of lignocelluloses. In: Hofrichter M (ed) *The Mycota, a comprehensive treatise on fungi as experimental systems for basic and applied research, industrial applications*, vol 10. Springer, Berlin, pp 319–340. doi:10.1007/978-3-642-11458-8_15
- Hegde S, Muralikrishna G (2009) Isolation and partial characterization of alkaline feruloyl esterases from *Aspergillus niger* CFR 1105 grown on wheat bran. *World J Microbiol Biotechnol* 25:1963–1969. doi:10.1007/s11274-009-0095-2
- Henriksson G, Johansson G, Pettersson G (2000) A critical review of cellobiose dehydrogenases. *J Biotechnol* 78:93–113. doi:10.1016/s0168-1656(00)00206-6
- Heremans K (1982) High pressure effects on proteins and other biomolecules. *Annu Rev Biophys Bioeng* 11:1–21. doi:10.1146/annurev.bb.11.060182.000245
- Herrmann WA, Weskamp T, Zoller JP, Fischer RW (2000) Methyltrioxorhenium: oxidative cleavage of CC-double bonds and its application in a highly efficient synthesis of vanillin from biological waste. *J Mol Catal A: Chem* 153:49–52. doi:10.1016/s1381-1169(99)00370-2
- Hocking MB (1997) Vanillin: synthetic flavoring from spent sulfite liquor. *J Chem Educ* 74:1055. doi:10.1021/ed074p1055
- Hofrichter M, Lundell T, Hatakka A (2001) Conversion of milled pine wood by manganese peroxidase from *Phlebia radiata*. *Appl Environ Microbiol* 67:4588–4593. doi:10.1128/aem.67.10.4588-4593.2001
- Hofrichter M, Ullrich R, Pecyna M, Liers C, Lundell T (2010) New and classic families of secreted fungal heme peroxidases. *Appl Microbiol Biotechnol* 87:871–897. doi:10.1007/s00253-010-2633-0
- Holladay JE, White JF, Bozell JJ, Johnson D (2007) Top value-added chemicals from biomass, volume II—results of screening for potential candidates from biorefinery lignin. Pacific Northwest National Laboratory, DOE
- Holtman KM, Chang HM, Kadla JF (2007) An NMR comparison of the whole lignin from milled wood, MWL, and REL dissolved by the DMSO/NMI procedure. *J Wood Chem Technol* 27:179–200. doi:10.1080/02773810701700828
- Hou H, Zhou J, Wang J, Du C, Yan B (2004) Enhancement of laccase production by *Pleurotus ostreatus* and its use for the decolorization of anthraquinone dye. *Process Biochem* 39:1415–1419. doi:10.1016/s0032-9592(03)00267-x
- Hu TQ, Lee C-L, James BR, Rettig SJ (1997) Stereoselective hydrogenation of lignin degradation model compounds. *Can J Chem* 75:1234–1239. doi:10.1139/v97-149
- Isobe K, Kato A, Sasaki Y, Suzuki S, Kataoka M, Ogawa J, Iwasaki A, Hasegawa J, Shimizu S (2007) Purification and characterization of a novel alcohol oxidase from *Paenibacillus* sp. AIU 311. *J Biosci Bioeng* 104:124–128. doi:10.1263/jbb.104.124
- Isroi MR, Syamsiah S, Niklasson C, Cahyanto MN, Lundquist K, Tahezadeh MJ (2011) Biological pretreatment of lignocelluloses with white-rot fungi and its applications: a review. *BioResources* 6:5224–5259
- Jadhav U, Dawkar V, Tamboli D, Govindwar S (2009) Purification and characterization of veratryl alcohol oxidase from *Comamonas* sp. UVS and its role in decolorization of textile dyes. *Biotechnol Bioproc Eng* 14:369–376. doi:10.1007/s12257-008-0300-4
- Jeoung JH, Pippig DA, Martins BM, Wagener N, Dobbek H (2007) HTHP: a novel class of hexameric, tyrosine-coordinated heme proteins. *J Mol Biol* 368:1122–1131. doi:10.1016/j.jmb.2007.02.079
- Jin L, Schultz TP, Nicholas DD (1990) Structural characterization of brown-rotted lignin. *Holzforschung* 44:133–138. doi:10.1515/hfsg.1990.44.2.133
- Jochems P, Satyawali Y, Diels L, Dejonghe W (2011) Enzyme immobilization on/in polymeric membranes: status, challenges and perspectives in biocatalytic membrane reactors (BMRs). *Green Chem* 13:1609–1623. doi:10.1039/C1GC15178A
- Johannes C, Majcherczyk A (2000) Natural mediators in the oxidation of polycyclic aromatic hydrocarbons by laccase mediator systems.

- Appl Environ Microbiol 66:524–528. doi:10.1128/aem.66.2.524-528.2000
- Johansson T, Nyman PO (1993) Isozymes of lignin peroxidase and manganese(II) peroxidase from the white-rot basidiomycete *Trametes versicolor*: I. Isolation of enzyme forms and characterization of physical and catalytic properties. Arch Biochem Biophys 300:49–56. doi:10.1006/abbi.1993.1007
- Joosten V, van Berkel WJH (2007) Flavoenzymes. Curr Opin Chem Biol 11:195–202. doi:10.1016/j.cbpa.2007.01.010
- Joseleau J-P, Gharibian S, Comtat J, Lefebvre A, Ruel K (1994) Indirect involvement of ligninolytic enzyme systems in cell wall degradation. FEMS Microbiol Rev 13:255–263. doi:10.1111/j.1574-6976.1994.tb00046.x
- Kamm B, Gruber PR, Kamm M (2007) Biorefineries—industrial processes and products. In: Ullmann's encyclopedia of industrial chemistry. Wiley, Weinheim
- Kapich A, Hofrichter M, Vares T, Hatakka A (1999a) Coupling of manganese peroxidase-mediated lipid peroxidation with destruction of nonphenolic lignin model compounds and ¹⁴C-labeled lignins. Biochem Biophys Res Commun 259:212–219. doi:10.1006/bbrc.1999.0742
- Kapich AN, Jensen KA, Hammel KE (1999b) Peroxyl radicals are potential agents of lignin biodegradation. FEBS Lett 461:115–119. doi:10.1016/S0014-5793(99)01432-5
- Kashima K, Maeda Y, Oshima M (1964) Method for liquefying lignin. Canadian Patent 700210
- Kellner H, Luis P, Zimdars B, Kiesel B, Buscot F (2008) Diversity of bacterial laccase-like multicopper oxidase genes in forest and grassland Cambisol soil samples. Soil Biol Biochem 40:638–648. doi:10.1016/j.soilbio.2007.09.013
- Kersten P, Cullen D (2007) Extracellular oxidative systems of the lignin-degrading basidiomycete *Phanerochaete chrysosporium*. Fungal Genet Biol 44:77–87. doi:10.1016/j.fgb.2006.07.007
- Kim J, Clark DS, Dordick JS (2000) Intrinsic effects of solvent polarity on enzymic activation energies. Biotechnol Bioeng 67:112–116. doi:10.1002/(sici)1097-0290(2000105)67:1<112::aid-bit13>3.0.co;2-e
- Kim SG, Jung BW, Kim H (2011) Hemocyanin-derived phenoloxidase activity with broad temperature stability extending into the cold environment in hemocytes of the hair crab *Erimacrus isenbeckii*. Comp Biochem Physiol B 159:103–108. doi:10.1016/j.cbpb.2011.02.004
- Kinne M, Poraj-Kobielska M, Ullrich R, Nousiainen P, Sipilä J, Scheibner K, Hammel KE, Hofrichter M (2011) Oxidative cleavage of non-phenolic β-O-4 lignin model dimers by an extracellular aromatic peroxygenase. Holzforschung 65:673–679. doi:10.1515/hf.2011.057
- Koseki T, Fushinobu S, Ardiansyah A, Shirakawa H, Komai M (2009) Occurrence, properties, and applications of feruloyl esterases. Appl Microbiol Biotechnol 84:803–810. doi:10.1007/s00253-009-2148-8
- Kudanga T, Nyanhongo GS, Guebitz GM, Burton S (2011) Potential applications of laccase-mediated coupling and grafting reactions: a review. Enzyme Microb Technol 48:195–208. doi:10.1016/j.enzmictec.2010.11.007
- Kumar A, Goswami P (2006) Functional characterization of alcohol oxidases from *Aspergillus terreus*; MTCC 6324. Appl Microbiol Biotechnol 72:906–911. doi:10.1007/s00253-006-0381-y
- Lan J, Huang X, Hu M, Li Y, Qu Y, Gao P, Wu D (2006) High efficient degradation of dyes with lignin peroxidase coupled with glucose oxidase. J Biotechnol 123:483–490. doi:10.1016/j.jbiotec.2005.12.034
- Leatham GF (1986) The ligninolytic activities of *Lentinus edodes* and *Phanerochaete chrysosporium*. Appl Microbiol Biotechnol 24:51–58. doi:10.1007/bf00266285
- Lee K, Moon SH (2003) Electroenzymatic oxidation of veratryl alcohol by lignin peroxidase. J Biotechnol 102:261–268. doi:10.1016/S0168-1656(03)00027-0
- Lee SH, Doherty TV, Linhardt RJ, Dordick JS (2009) Ionic liquid-mediated selective extraction of lignin from wood leading to enhanced enzymatic cellulose hydrolysis. Biotechnol Bioeng 102:1368–1376. doi:10.1002/bit.22179
- Leitner C, Volc J, Haltrich D (2001) Purification and characterization of pyranose oxidase from the white rot fungus *Trametes multicolor*. Appl Environ Microbiol 67:3636–3644. doi:10.1128/aem.67.8.3636-3644.2001
- Levasseur A, Piumi F, Coutinho PM, Rancurel C, Asther M, Delattre M, Henrissat B, Pontarotti P, Asther M, Record E (2008) FOLy: an integrated database for the classification and functional annotation of fungal oxidoreductases potentially involved in the degradation of lignin and related aromatic compounds. Fungal Genet Biol 45:638–645. doi:10.1016/j.fgb.2008.01.004
- Liers C, Bobeth C, Pecyna M, Ullrich R, Hofrichter M (2010) DyP-like peroxidases of the jelly fungus *Auricularia auricula-judae* oxidize nonphenolic lignin model compounds and high-redox potential dyes. Appl Microbiol Biotechnol 85:1869–1879. doi:10.1007/s00253-009-2173-7
- Liu JZ, Wang TL, Huang MT, Song HY, Weng LP, Ji LN (2006) Increased thermal and organic solvent tolerance of modified horseradish peroxidase. Protein Eng Des Sel 19:169–173. doi:10.1093/protein/gzj016
- Lobos S, Larrain J, Salas L, Cullen D, Vicuña R (1994) Isoenzymes of manganese-dependent peroxidase and laccase produced by the lignin-degrading basidiomycete *Ceriporiopsis subvermispora*. Microbiology 140:2691–2698. doi:10.1099/00221287-140-10-2691
- Ludwig R, Harreither W, Tasca F, Gorton L (2010) Cellobiose dehydrogenase: a versatile catalyst for electrochemical applications. ChemPhysChem 11:2674–2697. doi:10.1002/cphc.201000216
- Lundell TK, Mäkelä MR, Hildén K (2010) Lignin-modifying enzymes in filamentous basidiomycetes—ecological, functional and phylogenetic review. J Basic Microbiol 50:5–20. doi:10.1002/jobm.200900338
- Ma YS, Chang CN, Chiang YP, Sung HF, Chao AC (2008) Photocatalytic degradation of lignin using Pt/TiO₂ as the catalyst. Chemosphere 71:998–1004. doi:10.1016/j.chemosphere.2007.10.061
- Mahdavi B, Lafrance A, Martel A, Lessard J, Méard H, Brossard L (1997) Electrocatalytic hydrogenolysis of lignin model dimers at Raney nickel electrodes. J Appl Electrochem 27:605–611. doi:10.1023/a:1018463131891
- Mansfield SD, Mooney C, Saddler JN (1999) Substrate and enzyme characteristics that limit cellulose hydrolysis. Biotechnol Prog 15:804–816. doi:10.1021/bp9900864
- Marquardt W, Harwardt A, Hechinger M, Kraemer K, Viell J, Voll A (2010) The biorenewables opportunity—toward next generation process and product systems. AIChE J 56:2228–2235. doi:10.1002/aic.12380
- Marr AC, Liu S (2011) Combining bio- and chemo-catalysis: from enzymes to cells, from petroleum to biomass. Trends Biotechnol 29:199–204. doi:10.1016/j.tibtech.2011.01.005
- Martínez D, Larrondo LF, Putnam N, Gelpke MDS, Huang K, Chapman J, Helfenbein KG, Ramaiya P, Detter JC, Larimer F, Coutinho PM, Henrissat B, Berka R, Cullen D, Rokhsar D (2004) Genome sequence of the lignocellulose degrading fungus *Phanerochaete chrysosporium* strain RP78. Nat Biotechnol 22:695–700. doi:10.1038/nbt967
- Martínez ÁT, Speranza M, Ruiz-Dueñas FJ, Ferreira P, Camarero S, Guillén F, Martínez MJ, Gutiérrez A, del Río JC (2005) Biodegradation of lignocelluloses: microbial, chemical, and enzymatic aspects of the fungal attack of lignin. Int Microbiol 8:195–204

- Marzullo L, Cannio R, Giardina P, Santini MT, Sannia G (1995) Veratryl alcohol oxidase from *Pleurotus ostreatus* participates in lignin biodegradation and prevents polymerization of laccase-oxidized substrates. *J Biol Chem* 270:3823–3827. doi:10.1074/jbc.270.8.3823
- Mateo C, Palomo JM, Fernandez-Lorente G, Guisan JM, Fernandez-Lafuente R (2007) Improvement of enzyme activity, stability and selectivity via immobilization techniques. *Enzyme Microb Technol* 40:1451–1463. doi:10.1016/j.enzmictec.2007.01.018
- Mayer AM (2006) Polyphenol oxidases in plants and fungi: going places? A review. *Phytochemistry* 67:2318–2331. doi:10.1016/j.phytochem.2006.08.006
- Meier D, Berns J, Faix O, Balfanz U, Baldauf W (1994) Hydrocracking of organocellulose lignin for phenol production. *Biomass Bioenerg* 7:99–105. doi:10.1016/j.phytochem.2006.08.006
- Mercer DK, Iqbal M, Miller P, McCarthy AJ (1996) Screening actinomycetes for extracellular peroxidase activity. *Appl Environ Microbiol* 62:2186–2190
- Mester T, Field JA (1998) Characterization of a novel manganese peroxidase-lignin peroxidase hybrid isozyme produced by *Bjerkandera* species strain BOS55 in the absence of manganese. *J Biol Chem* 273:15412–15417. doi:10.1074/jbc.273.25.15412
- Michels J, Wagemann K (2010) The German lignocellulose feedstock biorefinery project. *Biofuels, Bioprod Biorefin* 4:263–267. doi:10.1002/bbb.216
- Mielgo I, López C, Moreira MT, Feijoo G, Lema JM (2003) Oxidative degradation of azo dyes by manganese peroxidase under optimized conditions. *Biotechnol Prog* 19:325–331. doi:10.1021/bp020136w
- Miyazaki K (2005) A hyperthermophilic laccase from *Thermus thermophilus* HB27. *Extremophiles* 9:415–425. doi:10.1007/s00792-005-0458-z
- Miyazaki-Imamura C, Oohira K, Kitagawa R, Nakano H, Yamane T, Takahashi H (2003) Improvement of H₂O₂ stability of manganese peroxidase by combinatorial mutagenesis and high throughput screening using in vitro expression with protein disulfide isomerase. *Protein Eng* 16:423–428. doi:10.1093/protein/gz054
- Morawski B, Quan S, Arnold FH (2001) Functional expression and stabilization of horseradish peroxidase by directed evolution in *Saccharomyces cerevisiae*. *Biotechnol Bioeng* 76:99–107. doi:10.1002/bit.1149
- Morozova O, Shumakovich G, Shleev S, Yaropolov Y (2007) Laccase-mediator systems and their applications: a review. *Appl Biochem Microbiol* 43:523–535. doi:10.1134/s0003683807050055
- Moukoui M, Topakas E, Christakopoulos P (2008) Cloning, characterization and functional expression of an alkalitolerant type C feruloyl esterase from *Fusarium oxysporum*. *Appl Microbiol Biotechnol* 79:245–254. doi:10.1007/s00253-008-1432-3
- Muheim A, Waldner R, Sanglard D, Reiser J, Schoemaker HE, Leisola MSA (1991) Purification and properties of an aryl-alcohol dehydrogenase from the white-rot fungus *Phanerochaete chrysosporium*. *Eur J Biochem* 195:369–375. doi:10.1111/j.1432-1033.1991.tb15715.x
- Murzin DY, Leino R (2008) Sustainable chemical technology through catalytic multistep reactions. *Chem Eng Res Des* 86:1002–1010. doi:10.1016/j.cherd.2008.03.017
- Muurinen E (2000) Organosolv pulping—a review and distillation study related to peroxyacid pulping. Dissertation, University of Oulu, Oulu, Finland
- Niladevi KN, Jacob N, Prema P (2008) Evidence for a halotolerant-alkaline laccase in *Streptomyces psammoticus*: purification and characterization. *Process Biochem* 43:654–660. doi:10.1016/j.procbio.2008.02.002
- Odaci D, Telefoncu A, Timur S (2010) Maltose biosensing based on co-immobilization of α -glucosidase and pyranose oxidase. *Bioelectrochemistry* 79:108–113. doi:10.1016/j.bioelechem.2009.12.010
- Ogino H, Ishikawa H (2001) Enzymes which are stable in the presence of organic solvents. *J Biosci Bioeng* 91:109–116. doi:10.1016/s1389-1723(01)80051-7
- Okamoto K, Yanase H (2002) Aryl alcohol oxidases from the white-rot basidiomycete *Pleurotus ostreatus*. *Mycoscience* 43:391–395. doi:10.1007/s102670200057
- Ortiz-Bermúdez P, Srebotnik E, Hammel KE (2003) Chlorination and cleavage of lignin structures by fungal chloroperoxidases. *Appl Environ Microbiol* 69:5015–5018. doi:10.1128/aem.69.8.5015-5018.2003
- Ozawa S, Klibanov AM (2000) Myoglobin-catalyzed epoxidation of styrene in organic solvents accelerated by bioimprinting. *Biotechnol Lett* 22:1269–1272. doi:10.1023/a:1005640915361
- Ozimek P, Veenhuis M, van der Klei IJ (2005) Alcohol oxidase: a complex peroxisomal, oligomeric flavoprotein. *Fems Yeast Res* 5:975–983. doi:10.1016/j.femsyr.2005.06.005
- Pakhadnia Y, Malinouski N, Lapko A (2009) Purification and characteristics of an enzyme with both bilirubin oxidase and laccase activities from mycelium of the basidiomycete *Pleurotus ostreatus*. *Biochem Mosc* 74:1027–1034. doi:10.1134/s0006297909090119
- Pandey MP, Kim CS (2011) Lignin depolymerization and conversion: a review of thermochemical methods. *Chem Eng Technol* 34:29–41. doi:10.1002/ceat.201000270
- Pardini VL, Vargas RR, Viertler H, Utley JHP (1992) Anodic cleavage of lignin model dimers in methanol. *Tetrahedron* 48:7221–7228. doi:10.1016/s0040-4020(01)88262-4
- Parpot P, Bettencourt AP, Carvalho AM, Belgsir EM (2000) Biomass conversion: attempted electrooxidation of lignin for vanillin production. *J Appl Electrochem* 30:727–731. doi:10.1023/a:1004003613883
- Partenheimer W (2009) The aerobic oxidative cleavage of lignin to produce hydroxyaromatic benzaldehydes and carboxylic acids via metal/bromide catalysts in acetic acid/water mixtures. *Adv Synth Catal* 351:456–466. doi:10.1002/adsc.200800614
- Paszczyński A, Crawford RL, Huynh VB (1988) Manganese peroxidase of *Phanerochaete chrysosporium*: purification. *Methods Enzymol* 161:264–270. doi:10.1016/0076-6879(88)61028-7
- Patel RN, Hou CT, Laskin AI, Derelanko P (1981) Microbial oxidation of methanol: properties of crystallized alcohol oxidase from a yeast, *Pichia* sp. *Arch Biochem Biophys* 210:481–488. doi:10.1016/0003-9861(81)90212-5
- Périé FH, Sheng D, Gold MH (1996) Purification and characterization of two manganese peroxidase isozymes from the white-rot basidiomycete *Dichomitus squalens*. *BBA-Protein Struct Mol Enzymol* 1297:139–148. doi:10.1016/s0167-4838(96)00096-9
- Petri A, Gambicorti T, Salvadori P (2004) Covalent immobilization of chloroperoxidase on silica gel and properties of the immobilized biocatalyst. *J Mol Catal B-Enzym* 27:103–106. doi:10.1016/j.jmolcatb.2003.10.001
- Plasseraud L, Süß-Fink G (1997) Catalytic hydrogenation of benzene derivatives under biphasic conditions. *J Organomet Chem* 539:163–170. doi:10.1016/s0022-328x(97)00003-x
- Polizzi KM, Bommaris AS, Broering JM, Chaparro-Riggers JF (2007) Stability of biocatalysts. *Curr Opin Chem Biol* 11:220–225. doi:10.1016/j.cbpa.2007.01.685
- Portjanskaja E, Preis S (2007) Aqueous photocatalytic oxidation of lignin: the influence of mineral admixtures. *J Photoenergy*. doi:10.1155/2007/76730, Article ID 76730
- Portjanskaja E, Stepanova K, Klauson D, Preis S (2009) The influence of titanium dioxide modifications on photocatalytic oxidation of lignin and humic acids. *Catal Today* 144:26–30. doi:10.1016/j.cattod.2008.12.021
- Qiu H, Li Y, Ji G, Zhou G, Huang X, Qu Y, Gao P (2009) Immobilization of lignin peroxidase on nanoporous gold: enzymatic properties and in situ release of H₂O₂ by co-immobilized glucose

- oxidase. *Bioresour Technol* 100:3837–3842. doi:10.1016/j.biortech.2009.03.016
- Ramachandra Rao S, Ravishankar GA (2000) Vanilla flavour: production by conventional and biotechnological routes. *J Sci Food Agric* 80:289–304. doi:10.1002/1097-0010(200002)80:3<289::aid-jsfa543>3.0.co;2-2
- Ramachandra M, Crawford DL, Hertel G (1988) Characterization of an extracellular lignin peroxidase of the lignocellulolytic actinomycete *Streptomyces viridosporus*. *Appl Environ Microbiol* 54:3057–3063
- Reading NS, Aust SD (2000) Engineering a disulfide bond in recombinant manganese peroxidase results in increased thermostability. *Biotechnol Prog* 16:326–333. doi:10.1021/bp0000151
- Reetz MT, Carballeira JD, Vogel A (2006) Iterative saturation mutagenesis on the basis of B factors as a strategy for increasing protein thermostability. *Angew Chem Int Ed* 45:7745–7751. doi:10.1002/anie.200602795
- Rocheffort D, Leech D, Bourbonnais R (2004) Electron transfer mediator systems for bleaching of paper pulp. *Green Chem* 6:14–24. doi:10.1039/b311898n
- Ruiz-Dueñas FJ, Martínez ÁT (2009) Microbial degradation of lignin: how a bulky recalcitrant polymer is efficiently recycled in nature and how we can take advantage of this. *Microb Biotechnol* 2:164–177. doi:10.1111/j.1751-7915.2008.00078.x
- Ruiz-Dueñas FJ, Morales M, García E, Miki Y, Martínez MJ, Martínez ÁT (2009) Substrate oxidation sites in versatile peroxidase and other basidiomycete peroxidases. *J Exp Bot* 60:441–452. doi:10.1093/jxb/em261
- Rüttimann-Johnson C, Cullen D, Lamar RT (1994) Manganese peroxidases of the white rot fungus *Phanerochaete sordida*. *Appl Environ Microbiol* 60:599–605
- Ryan BJ, Ó'Fágáin C (2007) Effects of single mutations on the stability of horseradish peroxidase to hydrogen peroxide. *Biochimie* 89:1029–1032. doi:10.1016/j.biochi.2007.03.013
- Sánchez C (2009) Lignocellulosic residues: biodegradation and bio-conversion by fungi. *Biotechnol Adv* 27:185–194. doi:10.1016/j.biotechadv.2008.11.001
- Sanderson K (2011) Lignocellulose: a chewy problem. *Nature* 474:12–14. doi:10.1038/474S012a
- Santacoloma P, Sin G, Gernaey K, Woodley J (2011) Multienzyme-catalyzed processes: next-generation biocatalysis. *Org Process Res Dev* 15:203–212. doi:10.1021/op1002159
- Santhanam N, Badri DV, Decker SR, Manter DK, Reardon KF, Vivanco JM (2012) Lignocellulose decomposition by microbial secretions. In: Vivanco JM, Baluška F (eds) Secretions and exudates in biological systems. Springer, Berlin, pp 125–153. doi:10.1007/978-3-642-23047-9_7
- Sasaki Y, Kataoka M, Urano N, Ogawa J, Iwasaki A, Hasegawa J, Isobe K, Shimizu S (2010) Cloning, sequencing and expression analysis of a gene encoding alcohol oxidase in *Paenibacillus* sp. *AIU* 311. *J Biosci Bioeng* 110:147–151. doi:10.1016/j.jbiosc.2010.01.019
- Schäfer A, Bieg S, Huwig A, Kohring G, Giffhorn F (1996) Purification by immunoaffinity chromatography, characterization, and structural analysis of a thermostable pyranose oxidase from the white rot fungus *Phlebiopsis gigantea*. *Appl Environ Microbiol* 62:2586–2592
- Schlosser D, Höfer C (2002) Laccase-catalyzed oxidation of Mn²⁺ in the presence of natural Mn³⁺ chelators as a novel source of extracellular H₂O₂ production and its impact on manganese peroxidase. *Appl Environ Microbiol* 68:3514–3521. doi:10.1128/aem.68.7.3514-3521.2002
- Schou C, Christensen MH, Schulein M (1998) Characterization of a cellobiose dehydrogenase from *Humicola insolens*. *Biochem J* 330:565–571
- Schulz J, Roucoux A, Patin H (2000) Stabilized rhodium(0) nanoparticles: a reusable hydrogenation catalyst for arene derivatives in a biphasic water–liquid system. *Chem-Eur J* 6:618–624. doi:10.1002/(sici)1521-3765(20000218)6:4<618::aid-chem618>3.0.co;2-a
- Selinheimo E, Saloheimo M, Ahola E, Westerholm-Parvinen A, Kalkkinen N, Buchert J, Kruus K (2006) Production and characterization of a secreted, C-terminally processed tyrosinase from the filamentous fungus *Trichoderma reesei*. *FEBS J* 273:4322–4335. doi:10.1111/j.1742-4658.2006.05429.x
- Sellés-Marchart S, Casado-Vela J, Bru-Martínez R (2006) Isolation of a latent polyphenol oxidase from loquat fruit (*Eriobotrya japonica* Lindl.): kinetic characterization and comparison with the active form. *Arch Biochem Biophys* 446:175–185. doi:10.1016/j.abb.2005.12.004
- Senczuk AM, Machwe A, Kapoor M (2003) High constitutive peroxidase activity and constitutive thermotolerance in *Neurospora crassa*. *Mycoscience* 44:129–137. doi:10.1007/s10267-003-0095-2
- Serdakowski AL, Dordick JS (2008) Enzyme activation for organic solvents made easy. *Trends Biotechnol* 26:48–54. doi:10.1016/j.tibtech.2007.10.007
- Sergeev AG, Hartwig JF (2011) Selective, nickel-catalyzed hydrogenolysis of aryl ethers. *Science* 332:439–443. doi:10.1126/science.1200437
- Shah V, Nerud F (2002) Lignin degrading system of white-rot fungi and its exploitation for dye decolorization. *Can J Microbiol* 48:857–870. doi:10.1139/w02-090
- Shao X, Gao Y, Jiang M, Li L (2009) Deletion and site-directed mutagenesis of laccase from *Shigella dysenteriae* results in enhanced enzymatic activity and thermostability. *Enzyme Microb Technol* 44:274–280. doi:10.1016/j.enzmictec.2008.12.013
- Sheldon RA (2007) Enzyme immobilization: the quest for optimum performance. *Adv Synth Catal* 349:1289–1307. doi:10.1002/chin.200736266
- Sheldon RA (2008) E factors, green chemistry and catalysis: an odyssey. *Chem Commun* 3352–3365. doi:10.1039/b803584a
- Shimizu S, Hattori S, Hata H, Yamada H (1988) A novel fungal enzyme, NADPH-dependent carbonyl reductase, showing high specificity to conjugated polyketones. *Eur J Biochem* 174:37–44. doi:10.1111/j.1432-1033.1988.tb14059.x
- Shin K, Oh I, Kim C (1997) Production and purification of Remazol brilliant blue r decolorizing peroxidase from the culture filtrate of *Pleurotus ostreatus*. *Appl Environ Microbiol* 63:1744–1748
- Sigoillot C, Lomascolo A, Record E, Robert JL, Asther M, Sigoillot JC (2002) Lignocellulolytic and hemicellulolytic system of *Pycnoporus cinnabarinus*: isolation and characterization of a cellobiose dehydrogenase and a new xylanase. *Enzyme Microb Technol* 31:876–883. doi:10.1016/s0141-0229(02)00208-9
- Silva JL, Weber G (1993) Pressure stability of proteins. *Annu Rev Phys Chem* 44:89–113. doi:10.1146/annurev.physchem.44.1.89
- Simpson C, Jordaan J, Gardiner NS, Whiteley C (2007) Isolation, purification and characterization of a novel glucose oxidase from *Penicillium* sp. CBS 120262 optimally active at neutral pH. *Protein Expr Purif* 51:260–266. doi:10.1016/j.pep.2006.09.013
- Singer SJ (1963) The properties of proteins in nonaqueous solvents. *Adv Protein Chem* 17:1–68. doi:10.1016/S0065-3233(08)60051-0
- Singh Arora D, Kumar Sharma R (2010) Ligninolytic fungal laccases and their biotechnological applications. *Appl Biochem Biotechnol* 160:1760–1788. doi:10.1007/s12010-009-8676-y
- Singh D, Zeng J, Chen S (2011) Increasing manganese peroxidase productivity of *Phanerochaete chrysosporium* by optimizing carbon sources and supplementing small molecules. *Lett Appl Microbiol* 53:120–123. doi:10.1111/j.1472-765X.2011.03070.x
- Sixta H (2006) Handbook of pulp. Wiley, Weinheim

- Sun N, Rodriguez H, Rahman M, Rogers RD (2011) Where are ionic liquid strategies most suited in the pursuit of chemicals and energy from lignocellulosic biomass? *Chem Commun* 47:1405–1421. doi:10.1039/c0cc03990j
- Suzuki T, Honda Y, Mukasa Y, Kim SJ (2006) Characterization of peroxidase in buckwheat seed. *Phytochemistry* 67:219–224. doi:10.1016/j.phytochem.2005.11.014
- Taboada-Puig R, Junghanns C, Demarche P, Moreira MT, Feijoo G, Lema JM, Agathos SN (2011) Combined cross-linked enzyme aggregates from versatile peroxidase and glucose oxidase: production, partial characterization and application for the elimination of endocrine disruptors. *Bioresour Technol* 102:6593–6599. doi:10.1016/j.biortech.2011.03.018
- Takakura Y, Kuwata S (2003) Purification, characterization, and molecular cloning of a pyranose oxidase from the fruit body of the basidiomycete, *Tricholoma matsutake*. *Biosci Biotechnol Biochem* 67:2598–2607. doi:10.1271/bbb.67.2598
- Thring RW, Breau J (1996) Hydrocracking of solvolysis lignin in a batch reactor. *Fuel* 75:795–800. doi:10.1016/0016-2361(96)00036-1
- Tolba R, Tian M, Wen J, Jiang ZH, Chen A (2010) Electrochemical oxidation of lignin at IrO₂-based oxide electrodes. *J Electroanal Chem* 649:9–15. doi:10.1016/j.jelechem.2009.12.013
- Topakas E, Vafiadi C, Christakopoulos P (2007) Microbial production, characterization and applications of feruloyl esterases. *Process Biochem* 42:497–509. doi:10.1016/j.procbio.2007.01.007
- Turner NJ (2009) Directed evolution drives the next generation of biocatalysts. *Nat Chem Biol* 5:567–573. doi:10.1038/nchembio.203
- Uzan E, Nousiainen P, Balland V, Sipila J, Piumi F, Navarro D, Asther M, Record E, Lomascolo A (2010) High redox potential laccases from the ligninolytic fungi *Pycnoporus coccineus* and *Pycnoporus sanguineus* suitable for white biotechnology: from gene cloning to enzyme characterization and applications. *J Appl Microbiol* 108:2199–2213. doi:10.1111/j.1365-2672.2009.04623.x
- Valderrama B, Ayala M, Vazquez-Duhalt R (2002) Suicide inactivation of peroxidases and the challenge of engineering more robust enzymes. *Chem Biol* 9:555–565. doi:10.1016/s1074-5521(02)00149-7
- van de Velde F, Bakker M, van Rantwijk F, Rai GP, Hager LP, Sheldon RA (2001) Engineering chloroperoxidase for activity and stability. *J Mol Catal B: Enzym* 11:765–769. doi:10.1016/s1381-1177(00)00022-9
- van den Heuvel RHH, Fraaije MW, Laane C, van Berkel WJH (2001) Enzymatic synthesis of vanillin. *J Agric Food Chem* 49:2954–2958. doi:10.1021/jf010093j
- van Haveren J, Scott EL, Sanders J (2008) Bulk chemicals from biomass. *Biofuel Bioprod Biorefin* 2:41–57. doi:10.1002/bbb.43
- van Rantwijk F, Sheldon RA (2007) Biocatalysis in ionic liquids. *Chem Rev* 107:2757–2785. doi:10.1021/cr050946x
- Vares T, Kalsi M, Hatakka A (1995) Lignin peroxidases, manganese peroxidases, and other ligninolytic enzymes produced by *Phlebia radiata* during solid-state fermentation of wheat straw. *Appl Environ Microbiol* 61:3515–3520
- Vennestrøm PNR, Christensen CH, Pedersen S, Grunwaldt J-D, Woodley JM (2010a) Next-generation catalysis for renewables: combining enzymatic with inorganic heterogeneous catalysis for bulk chemical production. *ChemCatChem* 2:249–258. doi:10.1002/cctc.200900248
- Vennestrøm PNR, Taarning E, Christensen CH, Pedersen S, Grunwaldt J-D, Woodley JM (2010b) Chemoenzymatic combination of glucose oxidase with titanium silicalite-1. *ChemCatChem* 2:943–945. doi:10.1002/cctc.201000120
- Vernwal SK, Yadav RSS, Yadav KDS (2006) Purification of a peroxidase from *Solanum melongena* fruit juice. *Indian J Biochem Biophys* 43:239–243
- Voitl T, Rudolf von Rohr P (2010) Demonstration of a process for the conversion of kraft lignin into vanillin and methyl vanillate by acidic oxidation in aqueous methanol. *Ind Eng Chem Res* 49:520–525. doi:10.1021/ie901293p
- Voitl T, Nagel MV, Rudolf von Rohr P (2009) Analysis of products from the oxidation of technical lignins by oxygen and H₃PMo₁₂O₄₀ in water and aqueous methanol by size-exclusion chromatography. *Holzforchung* 64:13–19. doi:10.1515/hf.2010.006
- Wang Y, Vazquez-Duhalt R, Pickard MA (2002) Purification, characterization, and chemical modification of manganese peroxidase from *Bjerkandera adusta* UAMH 8258. *Curr Microbiol* 45:77–87. doi:10.1007/s00284-001-0081-x
- Wang Z, Cai Y, Liao X, Zhang F, Zhang D, Li Z (2010) Production and characterization of a novel laccase with cold adaptation and high thermal stability from an isolated fungus. *Appl Biochem Biotechnol* 162:280–294. doi:10.1007/s12010-009-8801-y
- Werhan H, Mir JM, Voitl T, Rudolf von Rohr P (2011) Acidic oxidation of kraft lignin into aromatic monomers catalyzed by transition metal salts. *Holzforchung* 65:703–709. doi:10.1515/hf.2011.071
- Whittaker JW (2005) The radical chemistry of galactose oxidase. *Arch Biochem Biophys* 433:227–239. doi:10.1016/j.abb.2004.08.034
- Wong D (2006) Feruloyl esterase. *Appl Biochem Biotechnol* 133:87–112. doi:10.1385/abab:133:2:87
- Wong D (2009) Structure and action mechanism of ligninolytic enzymes. *Appl Biochem Biotechnol* 157:174–209. doi:10.1007/s12010-008-8279-z
- Wu YR, Luo ZH, Kwok-Kei Chow R, Vrijmoed LLP (2010) Purification and characterization of an extracellular laccase from the anthracene-degrading fungus *Fusarium solani* MAS2. *Bioresour Technol* 101:9772–9777. doi:10.1016/j.biortech.2010.07.091
- Wyman C, Goodman B (1993) Biotechnology for production of fuels, chemicals, and materials from biomass. *Appl Biochem Biotechnol* 39–40:41–59. doi:10.1007/bf02918976
- Yadav P, Sharma JK, Singh VK, Yadav KDS (2010) N-oxidation of arylamines to nitrosobenzenes using chloroperoxidase purified from *Musa paradisiaca* stem juice. *Biocatal Biotransform* 28:222–226. doi:10.3109/10242422.2010.489943
- Yelle DJ, Ralph J, Lu F, Hammel KE (2008) Evidence for cleavage of lignin by a brown rot basidiomycete. *Environ Microbiol* 10:1844–1849. doi:10.1111/j.1462-2920.2008.01605.x
- Zakrzewska ME, Bogel-Lukasik E, Bogel-Lukasik R (2010) Solubility of carbohydrates in ionic liquids. *Energy Fuel* 24:737–745. doi:10.1021/ef901215m
- Zakzeski J, Bruijninx PCA, Jongerius AL, Weckhuysen BM (2010a) The catalytic valorization of lignin for the production of renewable chemicals. *Chem Rev* 110:3552–3599. doi:10.1021/cr900354u
- Zakzeski J, Jongerius AL, Weckhuysen BM (2010b) Transition metal catalyzed oxidation of Alcell lignin, soda lignin, and lignin model compounds in ionic liquids. *Green Chem* 12:1225–1236. doi:10.1039/c001389g
- Zakzeski J, Bruijninx PCA, Weckhuysen BM (2011) In situ spectroscopic investigation of the cobalt-catalyzed oxidation of lignin model compounds in ionic liquids. *Green Chem* 13:671–680. doi:10.1039/c0gc00437e
- Zamocky M, Ludwig R, Peterbauer C, Hallberg BM, Divne C, Nicholls P, Haltrich D (2006) Cellobiose dehydrogenase—a flavocytochrome from wood-degrading, phytopathogenic and

- saprotropic fungi. *Curr Protein Pept Sci* 7:255–280. doi:[10.2174/138920306777452367](https://doi.org/10.2174/138920306777452367)
- Zhang YH (2008) Reviving the carbohydrate economy via multi-product lignocellulose biorefineries. *J Ind Microbiol Biotechnol* 35:367–375. doi:[10.1007/s10295-007-0293-6](https://doi.org/10.1007/s10295-007-0293-6)
- Zhao H (2010) Methods for stabilizing and activating enzymes in ionic liquids—a review. *J Chem Technol Biotechnol* 85:891–907. doi:[10.1002/jctb.2375](https://doi.org/10.1002/jctb.2375)
- Zhao X, Cheng K, Liu D (2009) Organosolv pretreatment of lignocellulosic biomass for enzymatic hydrolysis. *Appl Microbiol Biotechnol* 82:815–827. doi:[10.1007/s00253-009-1883-1](https://doi.org/10.1007/s00253-009-1883-1)
- Zumárraga M, Bulter T, Shleev S, Polaina J, Martínez-Arias A, Plou FJ, Ballesteros A, Alcalde M (2007) In vitro evolution of a fungal laccase in high concentrations of organic cosolvents. *Chem Biol* 14:1052–1064. doi:[10.1016/j.chembiol.2007.08.010](https://doi.org/10.1016/j.chembiol.2007.08.010)