

Nano-Ceria (CeO₂): An Efficient Catalyst for the Multi-Component Synthesis of a Variety of Key Medicinal Heterocyclic Compounds

Ahmadi, Sheida; Hosseinian, Akram; Delir Kheirollahi Nezhad, Parvaneh; Monfared, Aazam; Vessally, Esmail***

Department of Chemistry, Payame Noor University, 19395-4697 Tehran, I.R. IRAN

ABSTRACT: *This review gives an overview of the applications of ceria nanoparticles as inexpensive, efficient, reusable, and environmentally sustainable heterogeneous catalyst for the synthesis of a variety of key medicinal heterocyclic compounds with the emphasis on the mechanistic aspects of the reactions. Literature has been surveyed from 2005 to 2018.*

KEYWORDS: *Ceria nanoparticles; Multicomponent reactions; Heterocycles; Catalyst; Synthesis.*

INTRODUCTION

Organic chemistry covers more than 12.5 million known carbon-containing compounds, about half of them contain heterocyclic systems [1]. In particular, heterocycles are common structural units of the vast majority of marketed drugs [2]. Of the top five small molecule drugs by US retail sales in 2014, four are contained at least one heterocyclic fragment in their structures (Fig. 1) [3]. Due to the diversity of this class of organic compounds in the therapeutic response profile, many researchers have been working to develop novel, practical and convenient protocols for their synthesis to improve energy consumption, atom economy and reaction yields [4].

Multi-Component Reactions (MCRs) represent one of the most efficient one-pot processes for the synthesis of heterocyclic compounds, in which more than three

reactants are combined sequentially to construct complex organic molecules that contains almost all of the atoms of the starting materials [5]. In addition to avoidance of intermediates separation and purification processes, these reactions are generally environment and user friendly, time and energy saving, cost-efficient, and selective [6].

In the recent past, nanoparticles have gained increasing attention in organic synthesis as reusable and environmentally sustainable catalysts [7]. The high surface to volume ratio and reactive morphology of nanoparticles made them very successful heterogeneous catalysts in multi-component reactions [8]. Among metal nanoparticles, ceria nanoparticles (CeO₂-NPs) have recently received much attention because of their excellent catalytic activities, reusability, cost efficiency, non-toxicity, and

* To whom correspondence should be addressed.

+ E-mail: vessally@yahoo.com

• Other Address: School of Engineering Science, College of Engineering, University of Tehran, P.O. Box 11365-4563 Tehran, I.R. IRAN

1021-9986/2019/6/1-19

19/\$/6.09

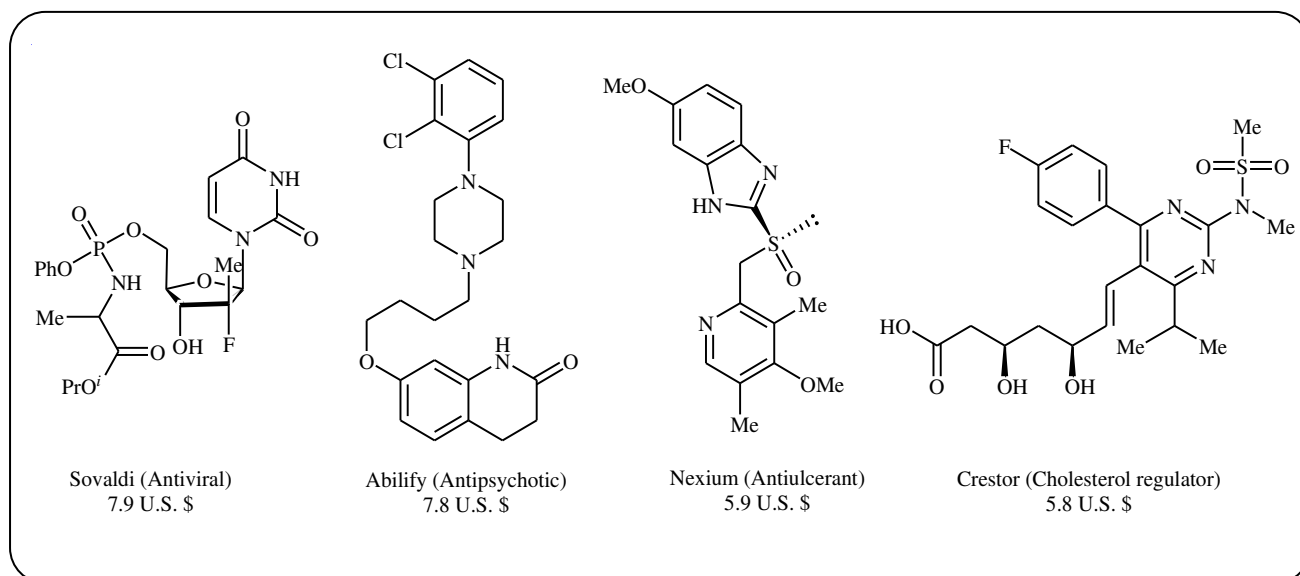


Fig. 1: Heterocycle molecule drugs present in the US top five prescription drugs and respective retail sales in 2014 (in billions of U.S. \$) [3].

versatility [9]. To the best of our knowledge, the significance and power of CeO_2 -NPs as heterogeneous catalyst in multi-component reactions has not been reviewed thus far. This review includes available information on using CeO_2 -NPs as catalyst for the synthesis of a board range of key medicinal heterocyclic compounds through multi-component reactions (Fig. 2). Herein, we have classified these reactions based on the desired products. Literature has been surveyed from 2005 to 2018 and mechanistic aspects of the reactions are considered and discussed in detail.

1,2,3-Triazoles

1,2,3-triazole is a five-membered aromatic heterocycle with molecular formula $\text{C}_2\text{H}_3\text{N}_3$, containing three nitrogen atoms in the 1,2,3-positions. This heterocycle is the base core for a number of drugs, such as voriconazole, fluconazole, isovuconazole, cefatrizine, and tazobactam [10] The synthesis of this framework strongly relies on click chemistry *via* reaction of aryl/alkyl halides, alkynes and NaN_3 [11].

In 2014, *Albadi, Shiran, and Mansournzhad* reported the preparation of CuO-CeO_2 nanocomposite through a co-precipitation of cerium and copper nitrates in water at room temperature [12]. The nanocomposite was used as an efficient heterogeneous catalyst for the click synthesis of biologically important 1,4-disubstituted-1,2,3-triazoles

3 from benzyl and phenacyl bromides **1**, phenyl acetylenes **2**, and amberlite-supported azide in refluxing ethanol (Scheme 1). This CuO-CeO_2 NPs-catalyzed azide-alkyne [3 + 2] cycloaddition reaction tolerated a wide range of substituents on the benzyl and phenacyl bromides and was efficient for the use of different phenyl acetylenes with diverse steric and electronic properties. Moreover, the catalyst was reusable and preserved its catalytic activity after recycling for five runs of reaction.

Inspired by this work, *Amini and Chae* along with their co-workers reported a CuNPs/CeO_2 catalyzed preparation of 1,2,3-triazoles **6** starting from different benzyl halides **4**, acetylenes **5**, and sodium azide in water at 70 °C (Scheme 2) [13]. Under optimized conditions, the reaction tolerated both aromatic and aliphatic alkynes and gave corresponding 1,2,3-triazole products in good to excellent yields.

PYRROLES

The pyrrole framework is a privileged structure in chemistry due to its presence in a large number of molecules that exhibit a broad range of biological and pharmaceutical properties, such as anticancer, anxiolytic, antipsychotic, antiprotozoal, antimalarial, antibacterial, antifungal, and many more [14]. Due to these benefits, a number of synthetic methods have been developed



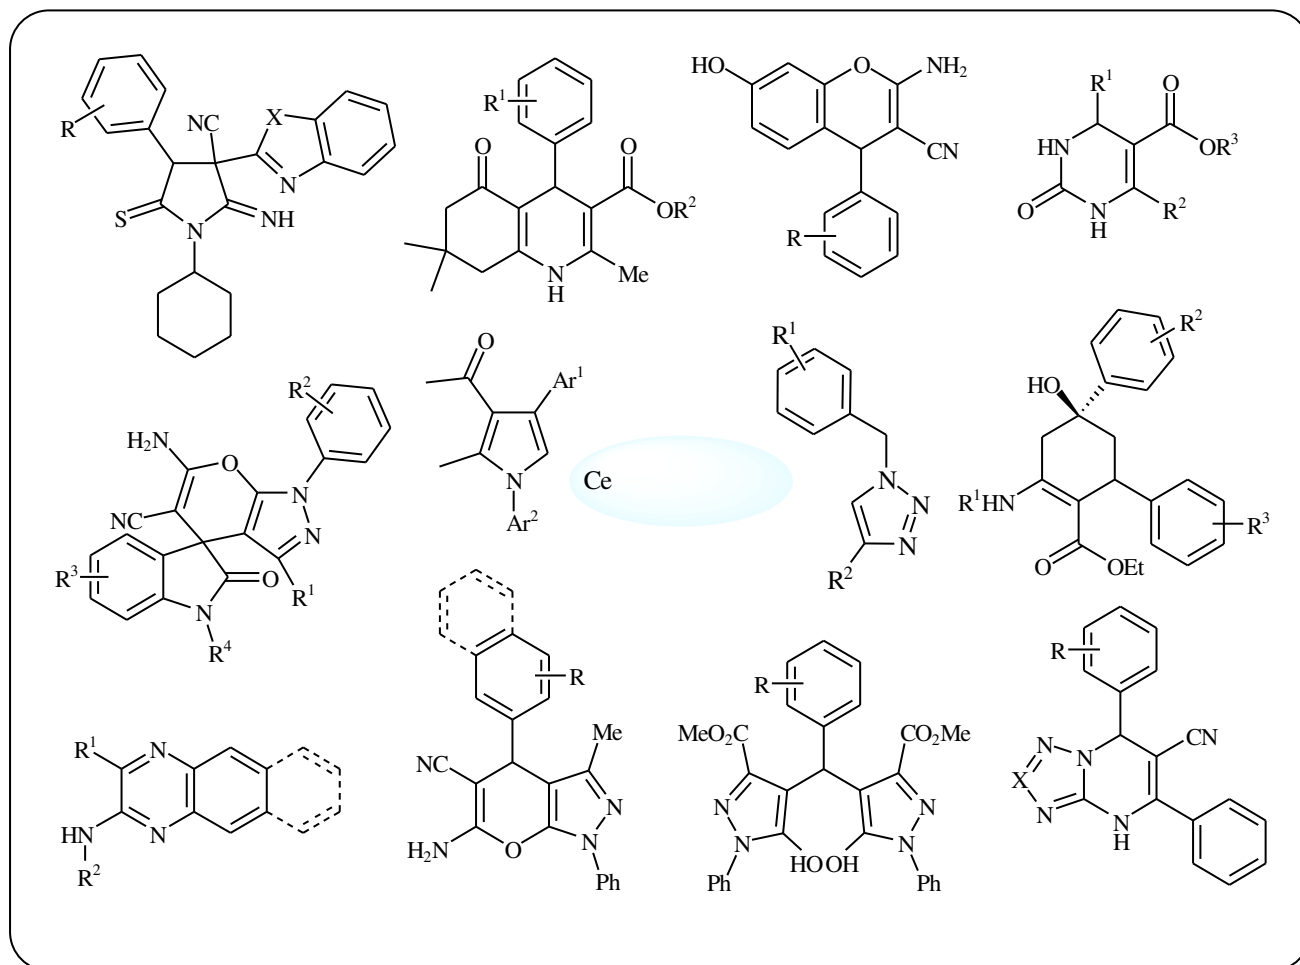


Fig. 2: Some important heterocyclic compounds synthesized by ceria nanoparticles catalyzed multi-component reactions.

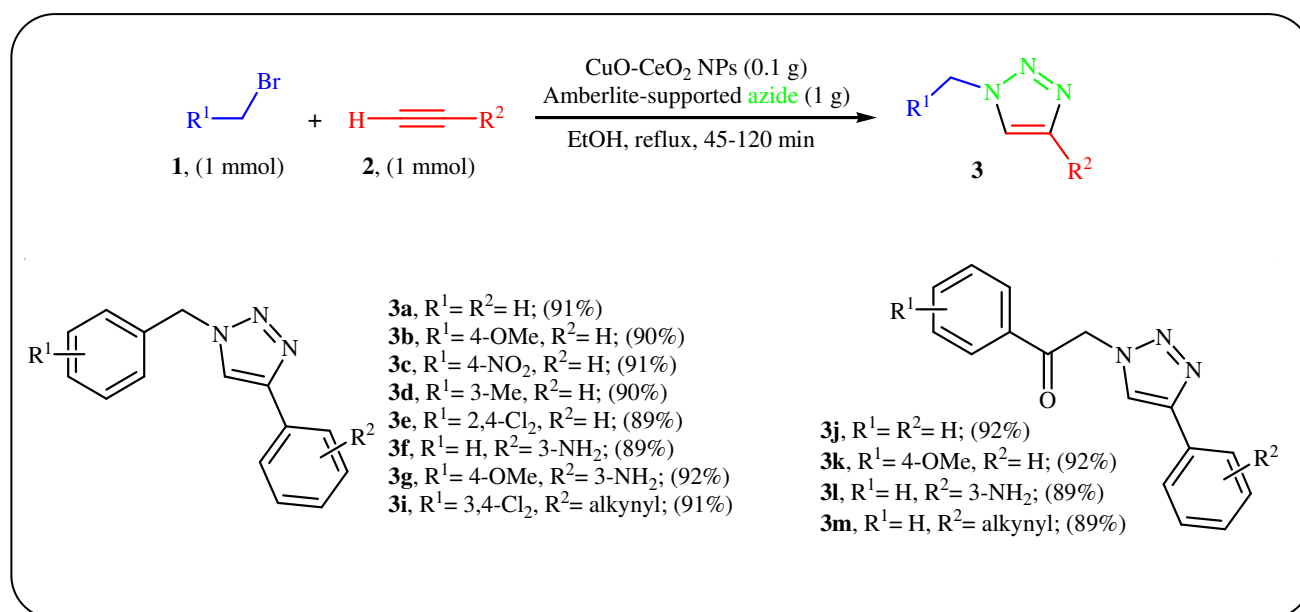

Scheme 1: CuO-CeO₂ NPs-catalyzed click synthesis of 1,4-disubstituted-1,2,3-triazoles 3 reported by Albadi.

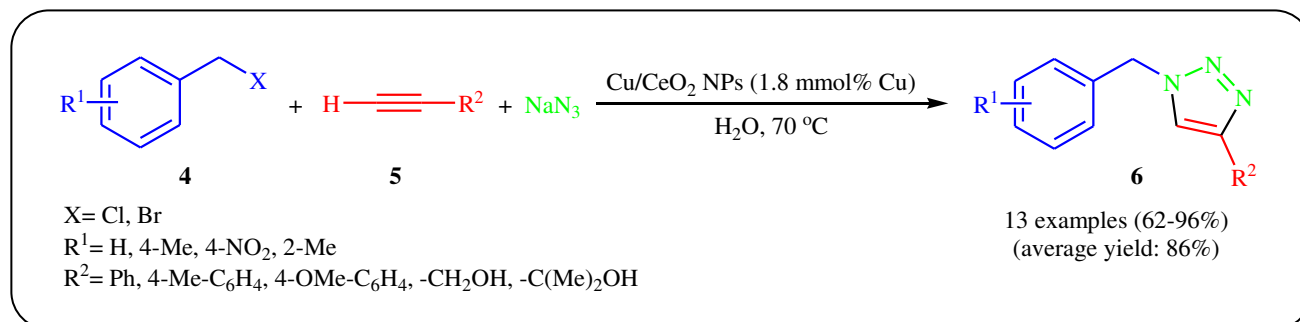

Scheme 2: Amini's synthesis of 1,4-disubstituted-1,2,3-triazoles 6.

to construct this biologically important heterocycle [15]. Synthesis of this key heterocycle by multi-component routes have attracted a large amount of attention due to their efficiency and intrinsic atom-economy [16].

In 2016, Samai and co-workers reported a three-component reaction from nitrostyrenes **7**, pentane-2,4-dione **8** and anilines **9**, catalyzed by nano-sized CeO₂-PVP (polyvinylpyrrolidone), for the synthesis of *N*-aryl pyrrole derivatives **10** [17]. The reactions were performed in the presence of 1.0 of ammonium acetate as an additive in refluxing toluene and generally provided highly substituted pyrroles **10** in good yields (Scheme 3). The catalyst could be efficiently reused for four catalytic cycles without significant loss of its activity. It is noteworthy that CeO₂-P123 (triblock copolymer PEO₂₀-PPO₇₀-PEO₂₀) and CeO₂-17R4 (reverse triblock copolymer PPO₁₄-PEO₂₄-PPO₁₄) were also found to promote the reaction but in slightly lower yields. The authors explained this fact by the smaller size and greater surface area of CeO₂-PVP compare to CeO₂-17R4 and CeO₂-P123.


Very recently, the group of Wu developed a one-pot, four-component reaction between aromatic aldehydes **11**, malononitrile **12**, isocyanide **13**, and 2-mercaptobenzazoles **14** catalyzed by porous CeO₂ nanorod, for the synthesis of highly functionalized iminopyrrolidine-thione derivatives **15** (Scheme 4) [18]. Among the various solvents like MeCN, MeOH, EtOH, H₂O, MeCN:H₂O (1:1), MeCN:H₂O (1:3), MeCN:H₂O (3:1); MeCN:H₂O (3:1) was the most efficient for this transformation. It should be mentioned that commercial CeO₂, granular CeO₂ NPs, fusiform CeO₂ NPs and linear CeO₂ NPs all could also be used to promote the reaction but afforded a lower yield of the final product. The results demonstrated that aromatic aldehydes bearing electron-

withdrawing groups gave higher yields than those bearing electron-donating groups and 2-mercaptobenzoxazole compare to 2-mercaptobenothiazole gave higher yield of desired product. The mechanism proposed for this transformation is summarized in Scheme 5 and starts with the Knoevenagel condensation between the aldehyde **11** and the malononitrile **12**, leading to the formation of a gem-dicyano olefin intermediate **A**, which reacts with isocyanide **13** to furnish intermediate **B**. Its reaction with thiol **14** yields intermediate **C** that undergoes Ugi-Smiles-type rearrangement through intermediate **D** to the intermediate **E**. Finally, nucleophilic addition of the amino group onto the cyano group affords the expected product **15**.


PYRIDINES

Pyridine is the most important six-membered heterocycles, present in more than one hundred currently marketed drugs [19]. Consequently, a number of methods have been reported for the synthesis of this biologically interesting *N*-heterocycle [20].


In 2013, Gawande and co-workers have synthesized a novel magnetite-based catalyst by coating Fe₃O₄ with CeO₂ nanoparticles [21]. The catalyst successfully applied in the synthesis of functionalized 1,4-dihydropyridines **19** by a one-pot four-component reaction of aromatic aldehydes **16**, β-ketoesters **17**, 5,5-dimethyl-1,3-cyclohexanedione **18**, and ammonium acetate in ethanol at room temperature (Scheme 6). The process showed very good functional group tolerance, including CN, OH, OMe, OPh, and Br functionalities that would allow further elaboration of the products. Importantly, the catalyst could be easily recycled from the reaction mixture by applying an external magnetic field without loss of catalytic activity within six cycles of reuse. Previously,

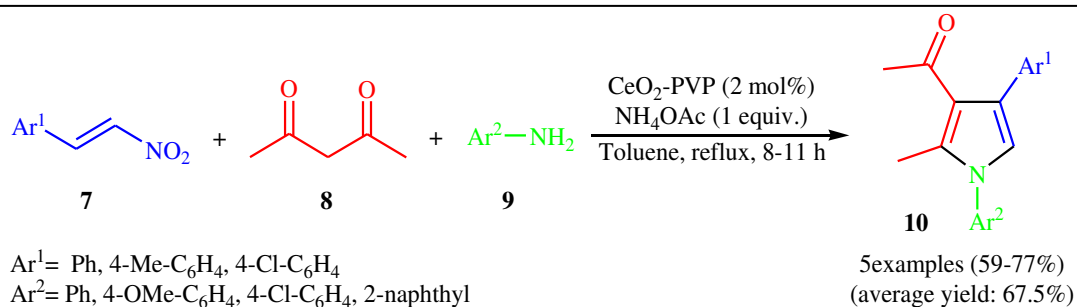

Scheme 3: Three-component pyrrole 10 synthesis from nitrostyrenes 7, pentane-2,4-dione 8 and anilines 9.

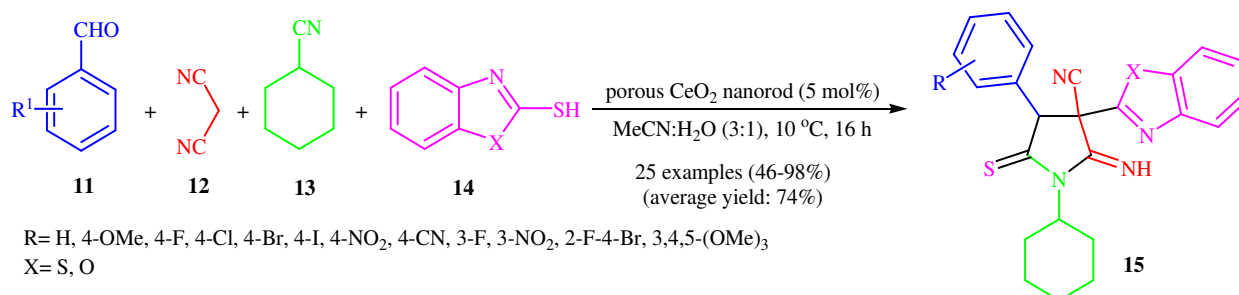

Scheme 4: Porous CeO₂ nanorod catalyzed four-component synthesis of imino-pyrrolidine-thione derivatives 15.

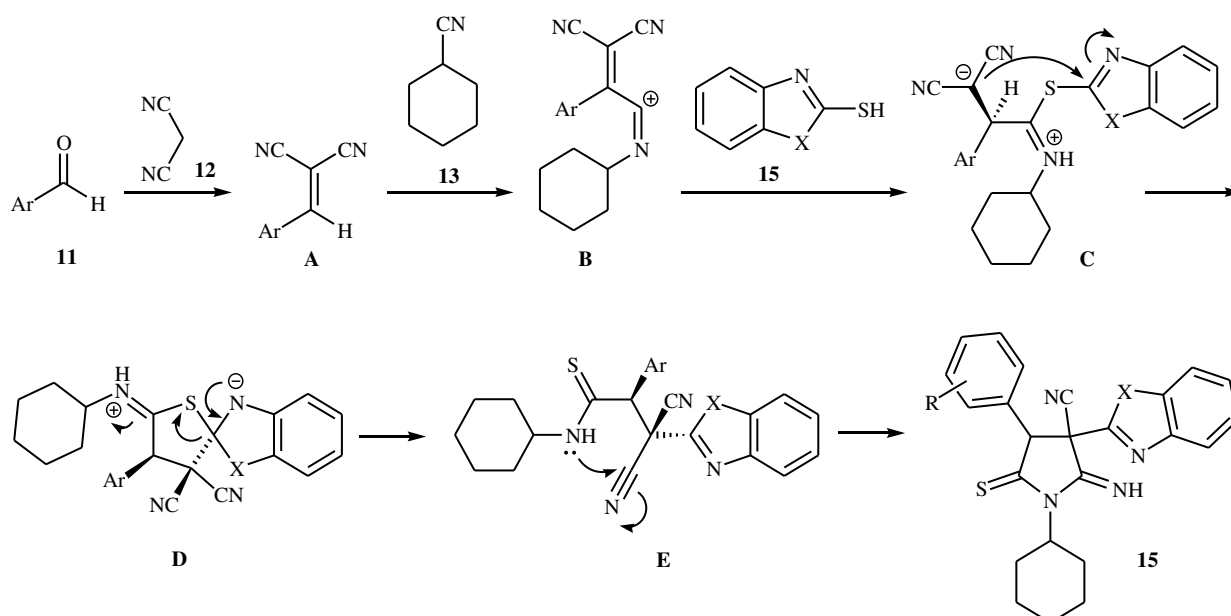

Scheme 5'': Mechanism proposed to explain the imino-pyrrolidine-thione 15 synthesis.

the group of Naik reported the usefulness of free-ceria nanoparticles for the same reaction under solvent-free conditions [22].

Another environmentally benign procedure has been developed for the preparation of highly substituted 1,4-dihydropyridine derivatives **23**, the condensation of 5,5-dimethyl-1,3-cyclohexanediones **20**, 4-hydroxy-3-methoxy-5-((4-substituted-phenyl)-diazanyl)-benzaldehydes **21** and glycine **22** in the presence of Eu₂O₃ modified CeO₂ nanoparticles (nano-CeO₂-Eu₂O₃) as heterogeneous catalyst in water [23]. A library of (4-hydroxy-3-methoxy-5-(substituted-phenyldiazanyl)-dihydropyridine)acetic acids **23** were prepared by performing all the reactions for 2-2.5 h at 80 °C to give a 69–91% yield (Scheme 7). The author proposed mechanism of the condensation is given in Scheme 8.

PYRIMIDINES

Pyrimidine is one of the most important classes of heterocyclic compounds exhibiting remarkable pharmacological activities such as antineoplastic, anthelmintic, antibacterial, antifungal, antiviral, and antiparkinson activities [24, 25]. Many commercially available drugs, including minoxidil, flucytosine, doxazosin, complera, etravirine, and rilpivirine are derived from pyrimidine core entities. The synthesis of functionalized pyrimidines through multi-component reactions has been the object of a number of studies [26], and a variety of MCR-based methods are now available. In 2005, Sabitha and co-workers used ceria nanoparticles supported on poly(4vp-co-dvb) as a heterogeneous catalyst (10 mol%) for the preparation of 3,4-dihydropyrimidin-2(1H)-ones **28** by a one-pot three-component condensation of aldehydes **25**, β-ketoesters **26** and urea **27** in moderate to excellent yields in the most environmentally benign solvent, water [27]. Various aromatic/heteroaromatic/aliphatic aldehydes, aminopyridines, and β-ketoesters were used to establish the general applicability of this synthetic process. Interestingly, the electronic character of the substituents in aromatic aldehydes had a remarkably little effect on the facility of the reaction. As shown in Scheme 9 both electron-rich and electron-poor aromatic aldehydes worked well under this reaction conditions. This methodology was also modified using β-diketone in place of the β-ketoester, providing corresponding


product in good yield. The synthesis of 3,4-dihydropyrimidin-2(1H)-ones using 22% Co/CeO₂-ZrO₂ nanoparticles as the heterogeneous catalyst has also been described [28]. In 2013, Albadi and Mansournezhad reinvestigated the same reaction by using CuO-CeO₂ nanocomposite as a green recyclable catalyst under aerobic condition. A series of 3,4-dihydropyrimidin-2(1H)-ones (10 examples) in excellent yields (up to 94%) with good functional group tolerance were obtained [29].

Recently, the group of Chandramouli used CeO₂ NPs (7-9 nm) for the synthesis of triazolo/tetrazolo[1,5-*a*]pyrimidine derivatives **32** via multi-component condensation reaction of aromatic aldehydes **29**, benzoylacetone nitrile **30**, and 5-aminotriazole/5-aminotetrazole **31** (Scheme 10) [30]. Water was found to be the best solvent for the reaction and, among several solvents tested, EtOH, MeCN, toluene, and dioxane were found to be less effective. The reaction *did not* give any *desired product* when neat condition was used. Apparently, the outcome of the condensation was also dependent on the reaction temperature, the best results were obtained by performing the process at 80 °C. The optimized conditions tolerated a variety of aromatic aldehydes containing both electron-donating and electron-withdrawing substituents at *ortho*-, *meta*- or *para*-positions and provided the expected fused pyrimidines in excellent yields. The mechanism suggested by the authors is depicted in Scheme 11, and involves an initial Knoevenagel condensation between aromatic aldehyde **29** and benzoylacetone nitrile **30** to give the intermediate **A**, followed by Michael addition with 5-aminotriazole/5-aminotetrazole **31** to form intermediate **B**, which then undergoes intermolecular cyclization to afford intermediate **C**. Intermolecular dehydrogenation of this intermediate affords the final product **32** with the liberation of catalyst.


CHROMENES

The synthesis of functionalized 2-chromenes has attracted significant attention in recent years [31] as these classes of heterocyclic compounds constitute structural frameworks of several commercially available drugs and naturally occurring compounds [32].

In 2012, the group of Mishra synthesized a series of CeO₂-CaO nanocomposite oxides containing 5, 10, 20, 50 and 80 mol% of CeO₂ by the amorphous citrate method [33].

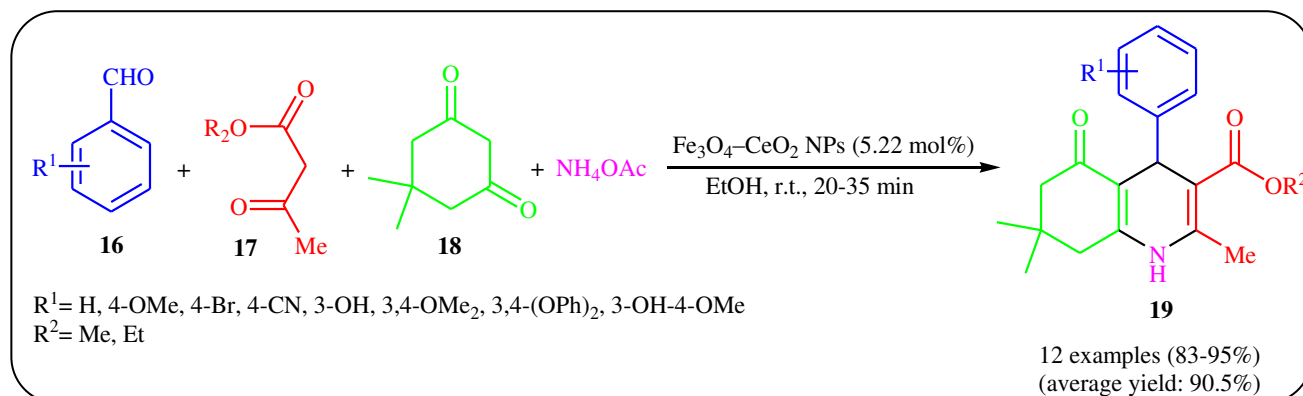


Scheme 6: Gawande's synthesis of 1,4-dihydropyridines 19.

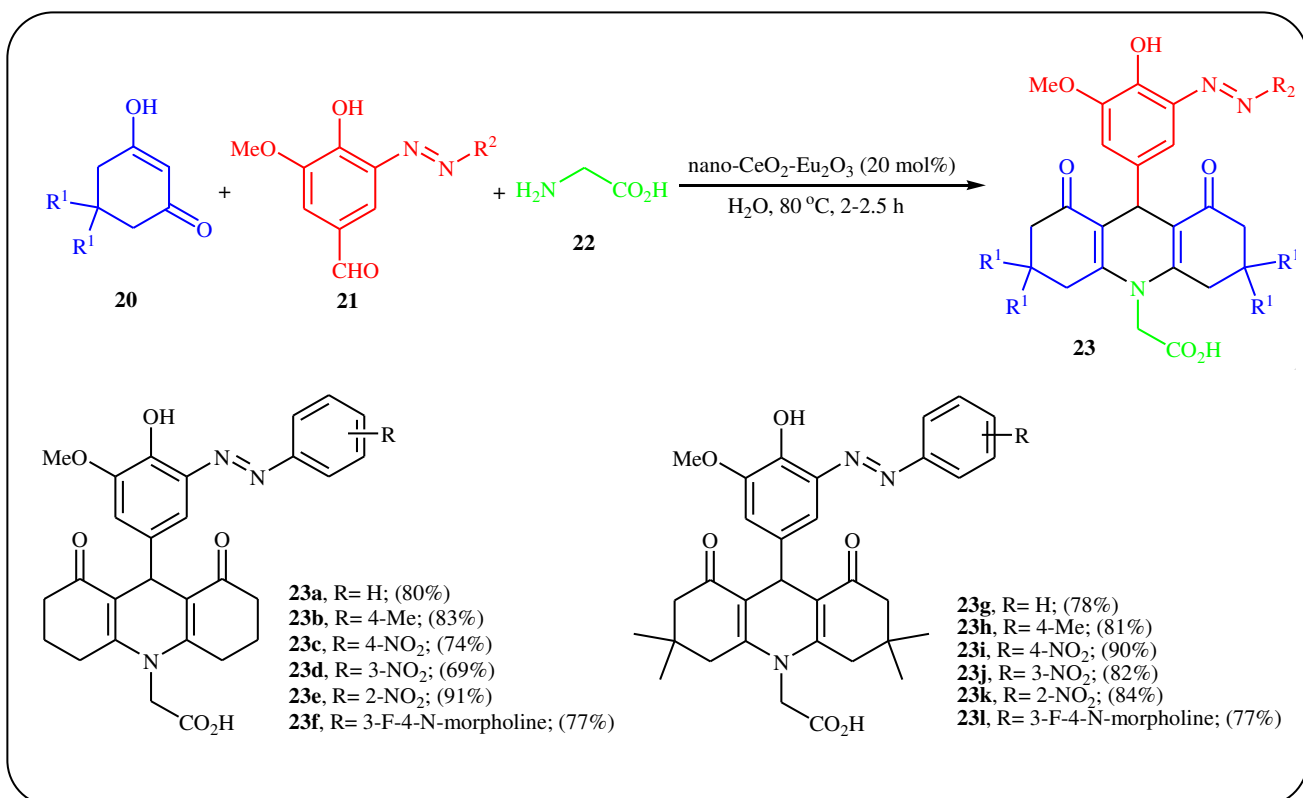Scheme 7: Nano-CeO₂-Eu₂O₃-catalyzed four-component synthesis of 1,4-dihydropyridine derivatives 23.


The catalytic activity of these nanocomposites were investigated for aqueous phase one-pot synthesis of 2-amino-2-chromenes **35** through three-component reaction between aromatic aldehydes **33**, α -naphthol **34**, and malononitrile **12**. The results proved that among all the catalysts, the 20CeO₂-CaO exhibited a higher catalytic activity in this reaction. Under the optimized conditions (20CeO₂-CaO, H₂O, 80 °C), various electron-neutral, electron-rich and electron-poor aromatic aldehydes afforded the corresponding 2-amino-2-chromenes in good


to high yields (Scheme 12). The catalyst was reusable and could be recovered and reused for three reaction runs with negligible loss of performance.

In a related investigation, Albadi and co-workers reported the use of CeO₂-CuO nanocomposite as an efficient and recyclable catalyst for the synthesis of chromene derivatives **38** via the one-pot three-component reaction of aromatic aldehydes **36**, resorcinol **37**, and malononitrile **12** under solvent-free conditions (Scheme 13) [34]. The reaction was performed at 80 °C,

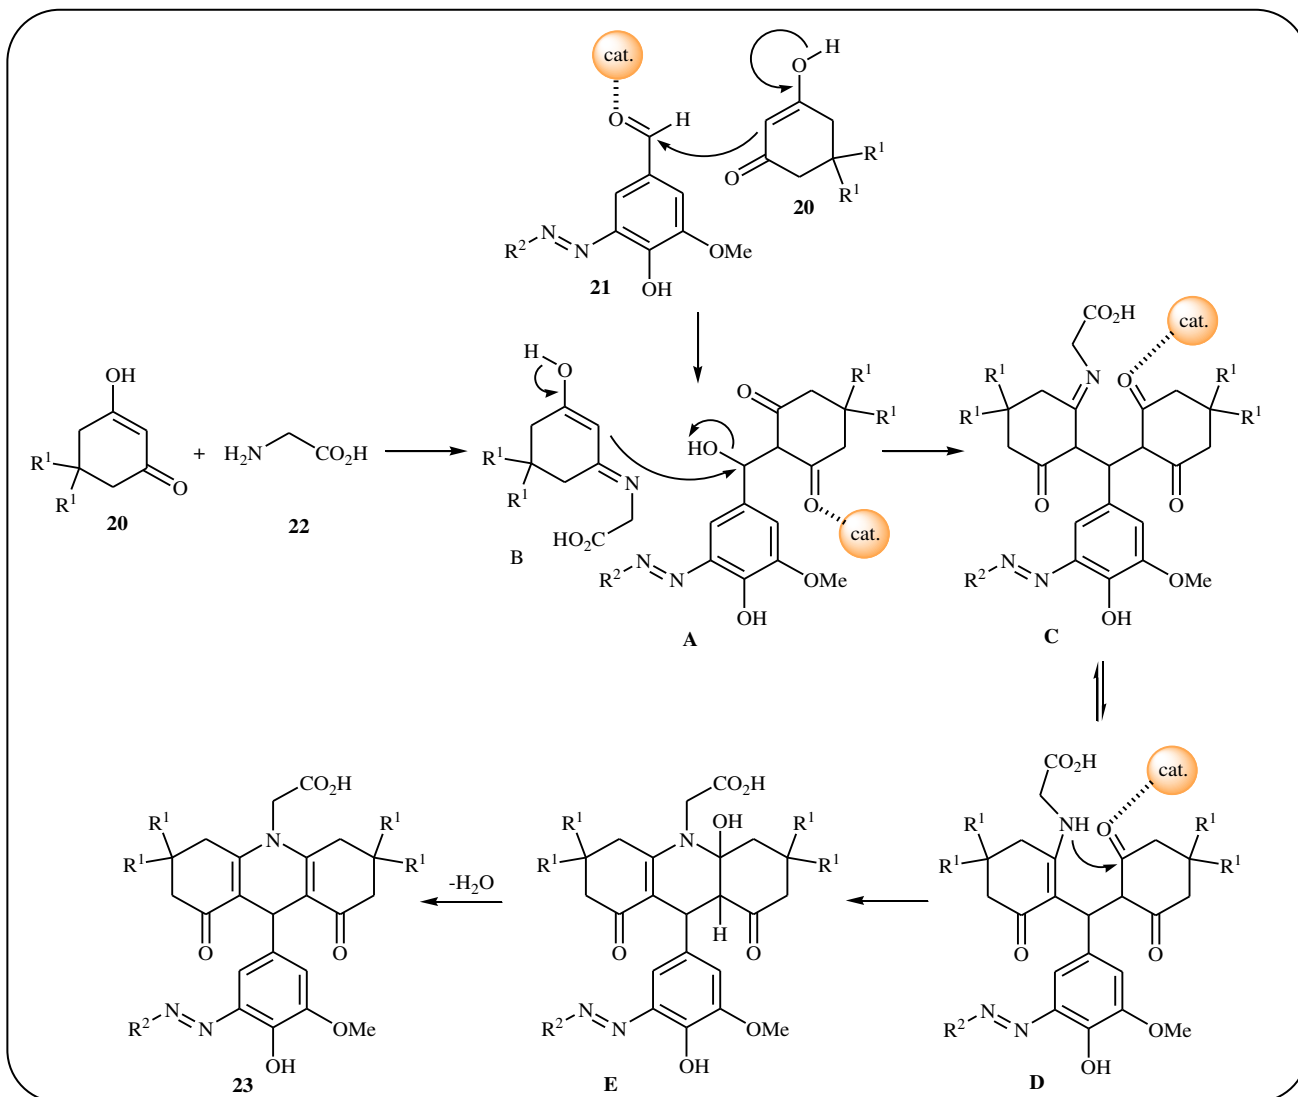


Scheme 8: Mechanism proposed for the reaction in Scheme 7.

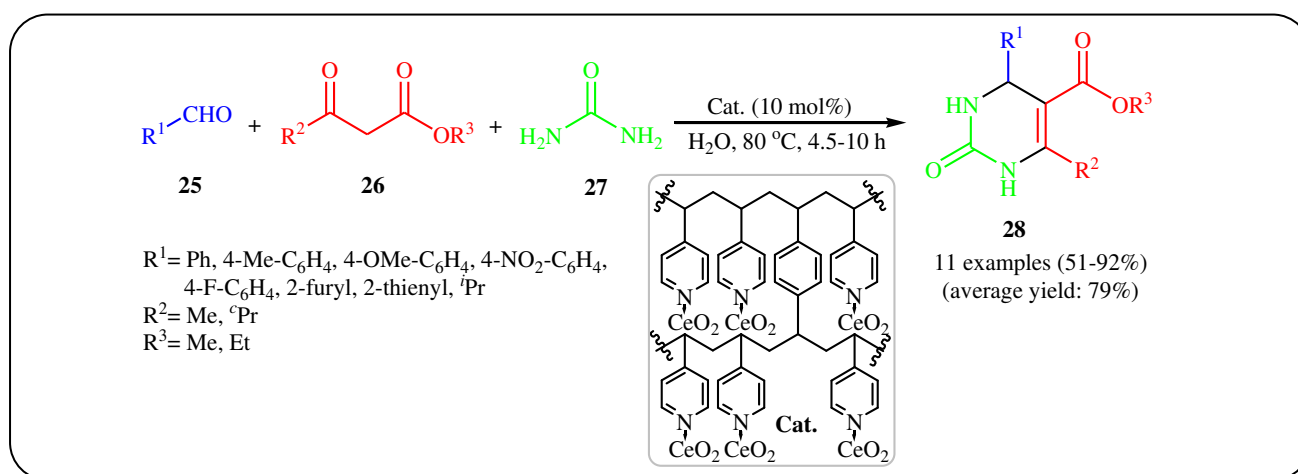Scheme 9: Ceria/vinylpyridine polymer nanocomposite-catalyzed synthesis of 3,4-dihydropyrimidin-2(1H)-ones **28** developed by Sabitha.

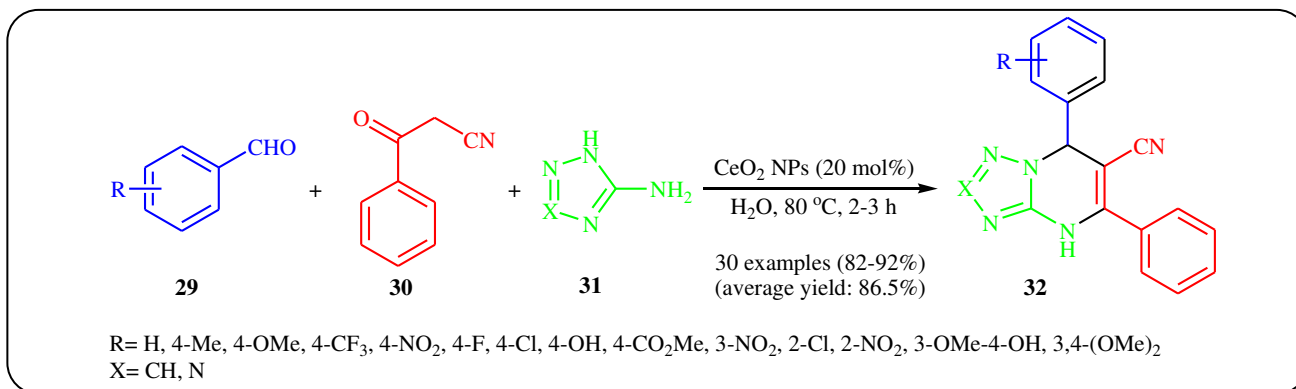

Scheme 10: CeO_2 -NPs-catalyzed synthesis of triazolo/tetrazolo[1,5-a]pyrimidines **32** from aldehydes **29**, benzoylacetonitrile **30**, and 5-amino-1,2,4-triazole/5-amino-1,2,3,4-tetrazole **31**.

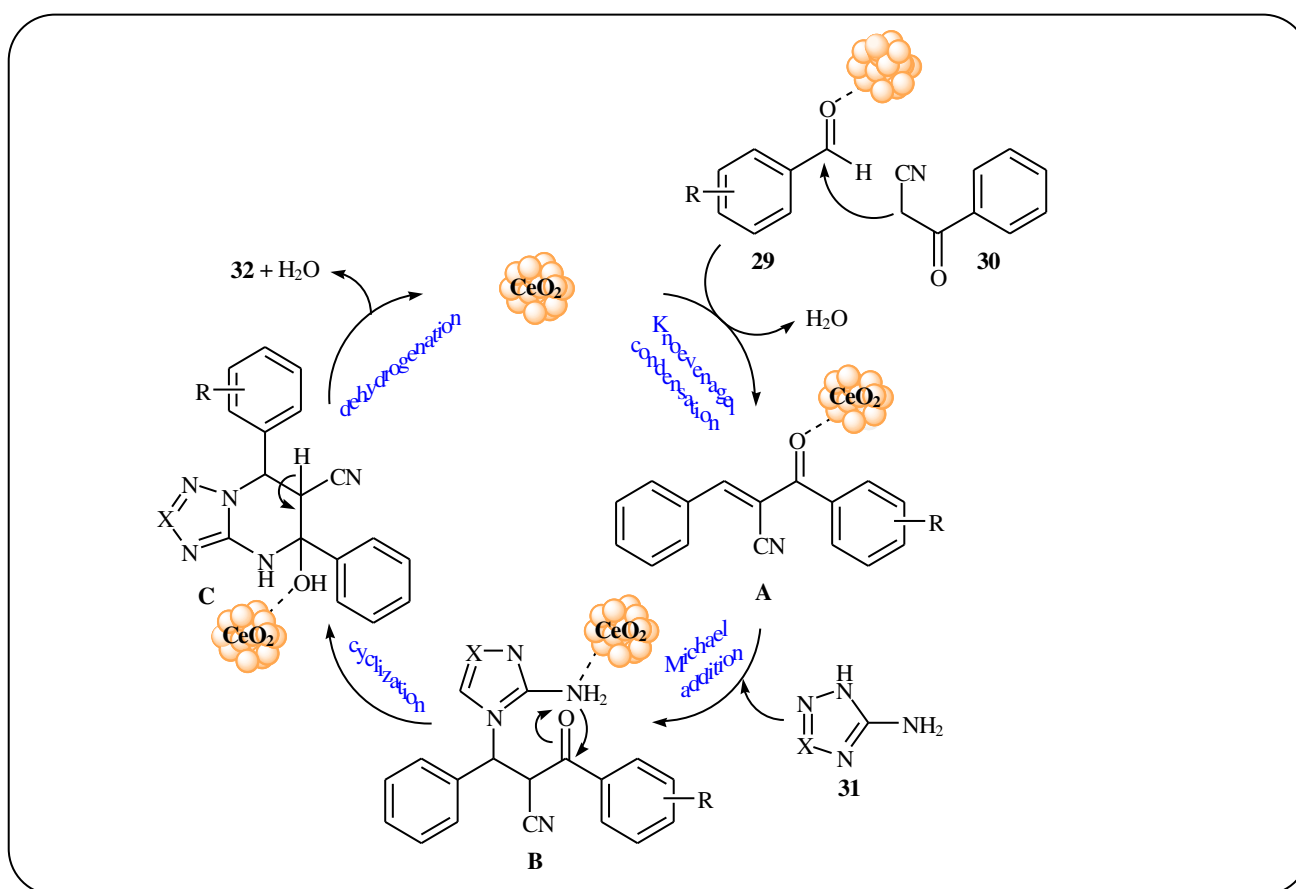


Scheme 11: Mechanistic explanation of the synthesis of triazolo/tetrazolo[1,5-a]pyrimidines **32**.


tolerated a variety of sensitive functional groups (e.g., nitro, cyano, amino, bromo, chloro, methoxy, and hydroxy), and generally provided the highly substituted chromenes **38** in high to excellent yields.

Recently, the group of Chandramouli reported an efficient synthesis of a number of 2-amino-4-(4-hydroxy-3-methoxy-5-(substituted-phenyl-diazenyl)-chromene-3-

carbonitrile derivatives **40** through nano-sized $\text{CeO}_2\text{-ZrO}_2$ catalyzed three-component reaction between 1,3-dicarbonyl compounds **39**, 4-hydroxy-3-methoxy-5-(substituted-phenyl-diazenyl) benzaldehydes **21**, and malononitrile **12** in water medium at room temperature (Scheme 14) [35]. Other metal oxide nanoparticles were also found to promote the reaction (e.g., Fe_3O_4 , ZnO ,

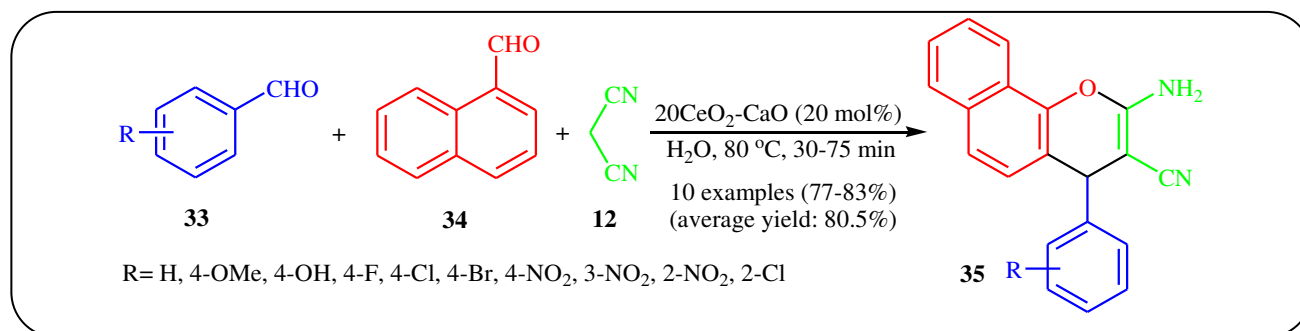

Scheme 12: Three-component synthesis of 2-amino-2-chromenes **35** catalyzed by 20CeO₂-CaO nanocomposite.

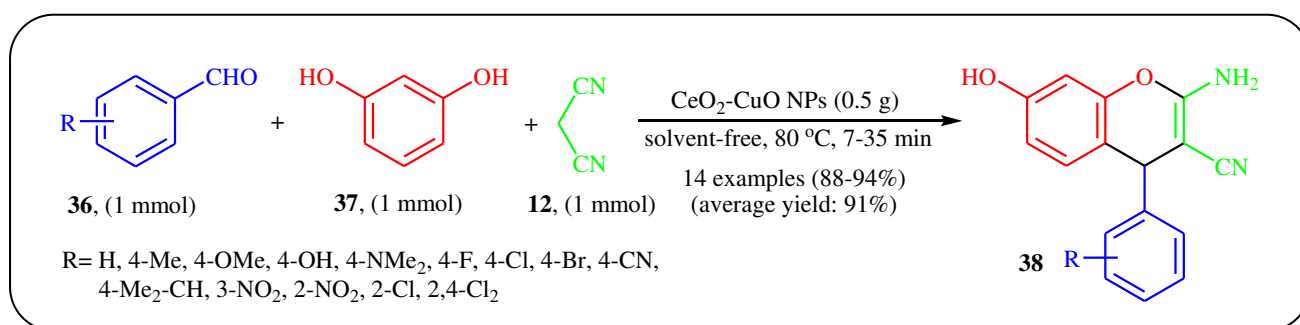

Scheme 13: Three-component syntheses of chromenes **38** reported by Albadi, catalysed by the CeO₂-CuO nanocomposite.

TiO₂, CeO₂); however, in lower yields. According to the author proposed mechanism, this reaction proceeded via a Knoevenagel condensation/Michael addition/tautomerization/intramolecular cyclization sequential process (Scheme 15).


QUINOZALINES

In 2014, Edayadulla and Lee explored the catalytic activity of CeO₂ nanoparticles for the synthesis of quinoxalin-2-amines **44** via a three-component reaction between aliphatic aldehydes **41**, 1,2-diamines **42**, and isocyanides **43**, in water at 80 °C (Scheme 16) [36]. Benzaldehyde did not take part in the reaction and therefore no other aromatic aldehydes were examined in the protocol. A variety of 3,4-dihydroquinoxalin-2-amine derivatives were also successfully synthesized under standard conditions by reactions between ketones, 1,2-diamines, and isocyanides. Good to high yields, short reaction times, relatively mild reaction conditions, and reusability of the catalyst were the advantages, mentioned for this green protocol. The mechanism for this quinoxaline synthesis was proposed to be initiated by the generation of the iminium ion **A** from CeO₂NPs-promoted condensation between aldehyde **41** and 1,2-diamine **42** followed by nucleophilic addition of

isocyanide **43** to this intermediate to give the intermediate **B**. Intramolecular cycloaddition of **B** affords intermediate **C**, which undergoes isomerization to intermediate **D**. Finally, the oxidation of intermediate **D** affords the observed product **44** (Scheme 17).

MISCELLANEOUS REACTIONS


In 2013, Albadi and *et al.* have reported the synthesis of biologically important 4*H*-benzo[*b*]pyran derivatives **47** under solvent-free conditions using CuO-CeO₂ nanocomposite as an efficient recyclable catalyst [37]. The mixture of aromatic aldehydes **45**, 3-methyl-1-phenyl-2-pyrazoline-5-one **46**, and malononitrile **12** in 1 : 1 : 1 molar ratios in the presence of catalytic amounts of CuO-CeO₂, were heated at 80 °C to give the desired products in excellent yields (Scheme 18a). The reaction is noteworthy in that both electron-rich and electron-poor aromatic aldehydes are well tolerated. It should be noted that the catalyst could be easily recovered from the reaction mixture by a simple filtration, followed by washing with acetone to remove traces of organic compounds and drying. The separated nanocatalyst could be reused for at least eight successive times without tangible loss of its catalytic activity. A subsequent study

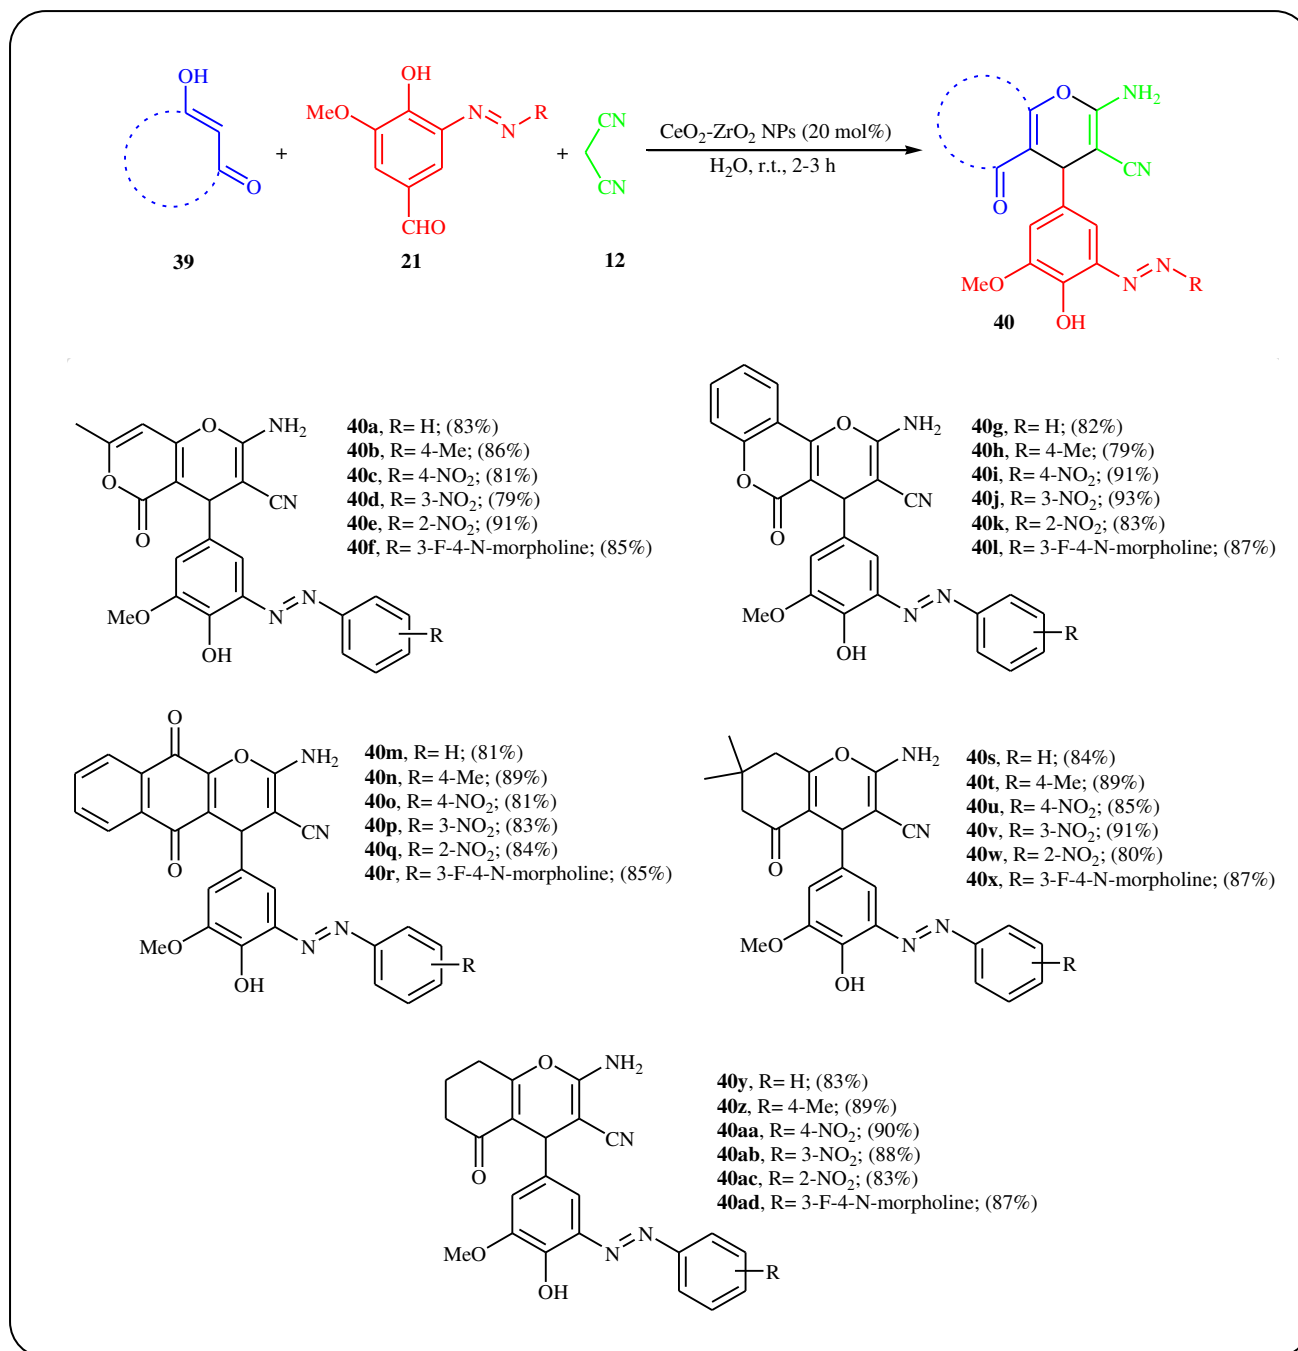


Scheme 14: Multicomponent synthesis of 2-amino-4-(4-hydroxy-3-methoxy-5-(substituted-phenyl-diazenyl)-chromene-3-carbonitrile derivatives **40** catalyzed by zirconium doped ceria nanoparticles.

by the same authors showed that 1,8-dioxooctahydroxanthenes **50** could be prepared by three-component reaction of one molecule of aromatic aldehydes **48** with two molecules of 1,3-dicarbonyl compounds **49** employing CuO-CeO_2 nanocomposite as the catalyst (Scheme 18b) [38]. This protocol afforded the optimum yield in refluxing water.

In 2015, *Safaei-Ghomi* and co-workers have described a synthesis of C-tethered bispyrazol-5-ols **54** by using a five-component reaction of one molecule of aromatic aldehydes **51**, two molecules of acetylenedicarboxylate **52**, and two molecules of phenylhydrazine **53** at 70 °C in water (Scheme 19) [39].


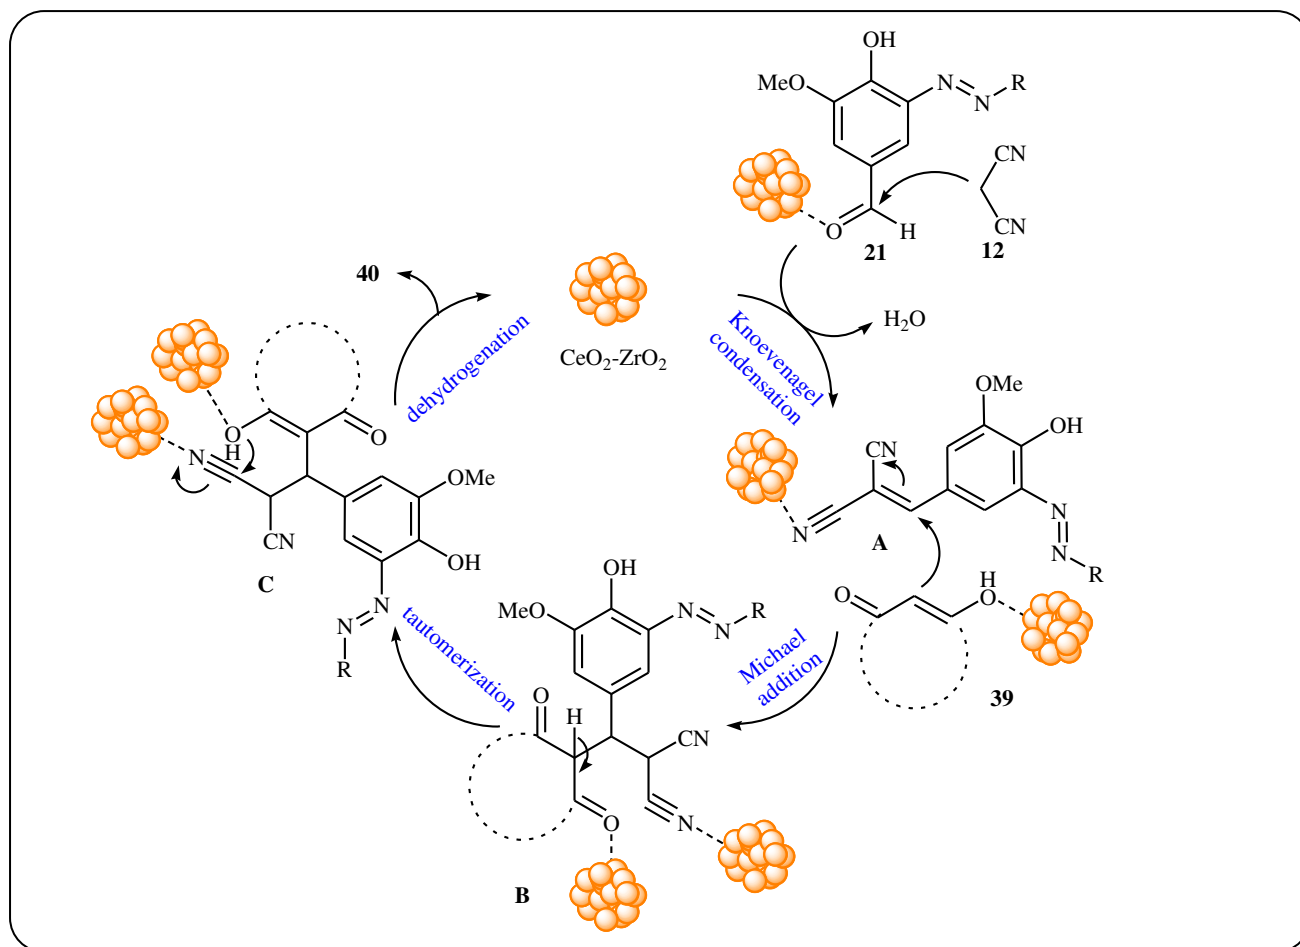


Scheme 15. Mechanistic proposal for the reaction in Scheme 14.

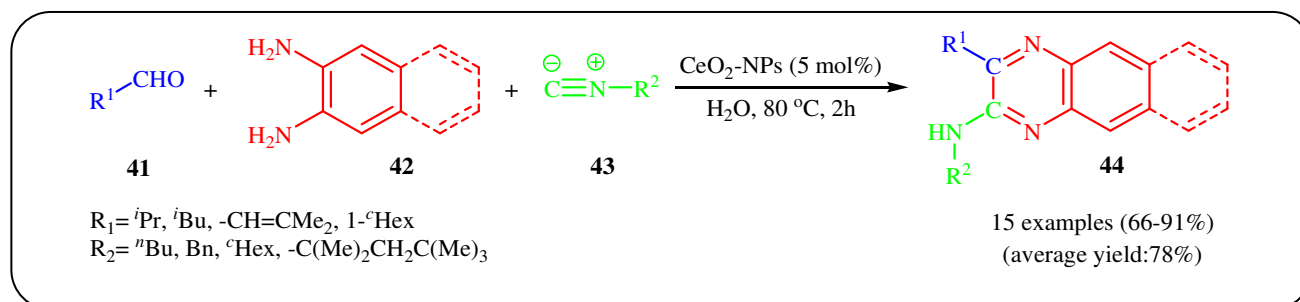
Scheme 16: CeO_2 nanoparticles-catalyzed three-component reaction between aldehydes **41**, 1,2-diamines **42**, and isocyanides **43**.

A variety of metal catalysts such as CuO , NiO , CaO , ZrO_2 , CeO_2 , Al_2O_3 , and Nd_2O_3 have been tested for this multicomponent reaction. Nanosized ceria has been shown as an effective catalyst for this reaction. Under optimized conditions, the corresponding C-tethered bispyrazol-5-ols **54** were obtained in high to excellent yields. The author proposed mechanism for this transformation is represented in Scheme 20.


The synthesis of a range of cyclic β -aminoesters **58** in good to high yields (up to 85 %) was also reported by the same research team through a simple and environmentally benign three-component reaction between primary amines **55**, ethyl acetoacetate **56**, and chalcones **57** using CeO_2 NPs as an efficient heterogeneous catalyst in ethanol at room temperature (Scheme 21) [40].

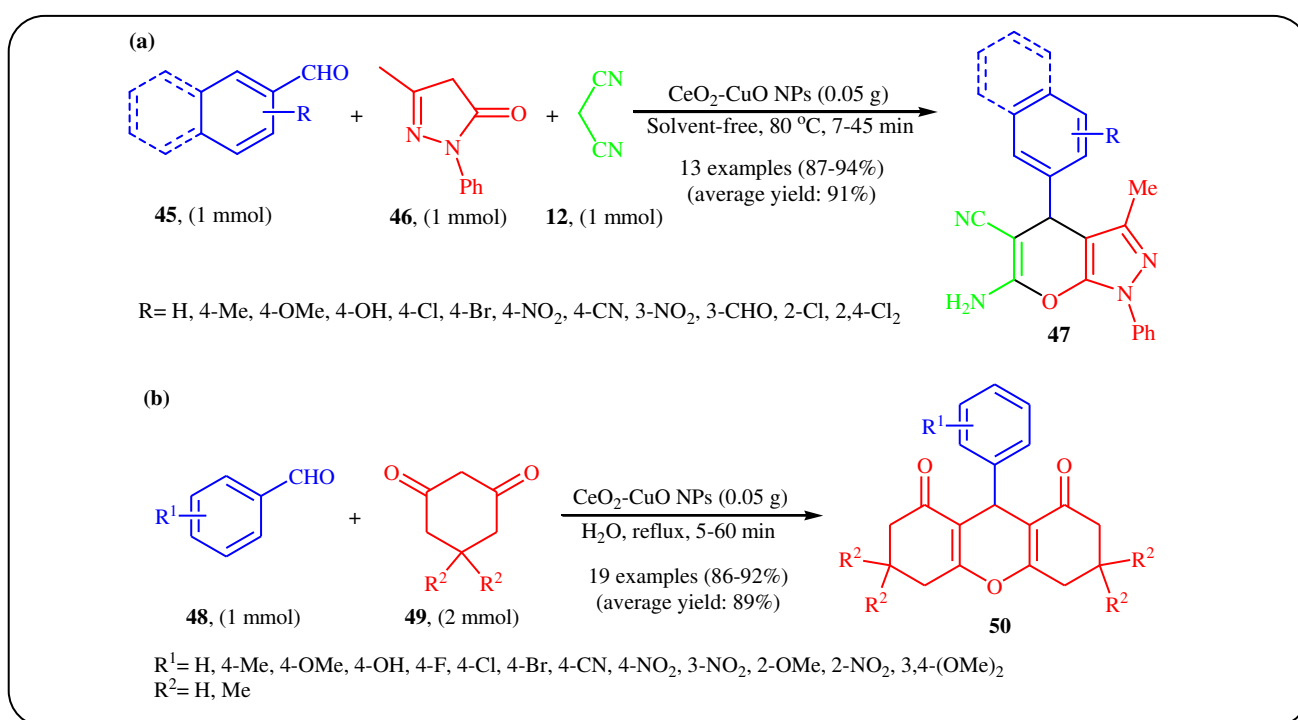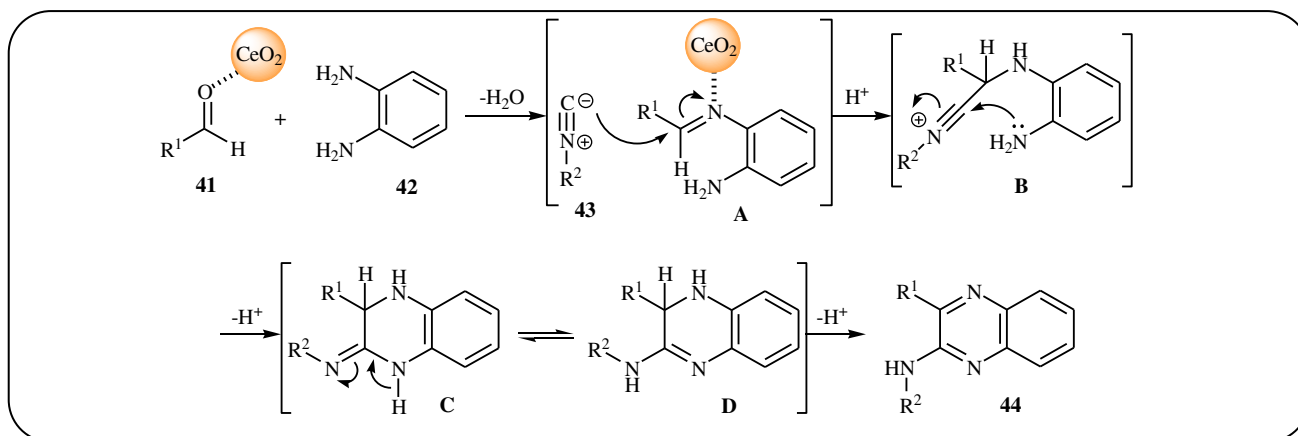


Scheme 18: Albadi's synthesis of (a) 4H-benzo[b]pyran derivatives 47; (b) 1,8-dioxooctahydroxanthenes 50.

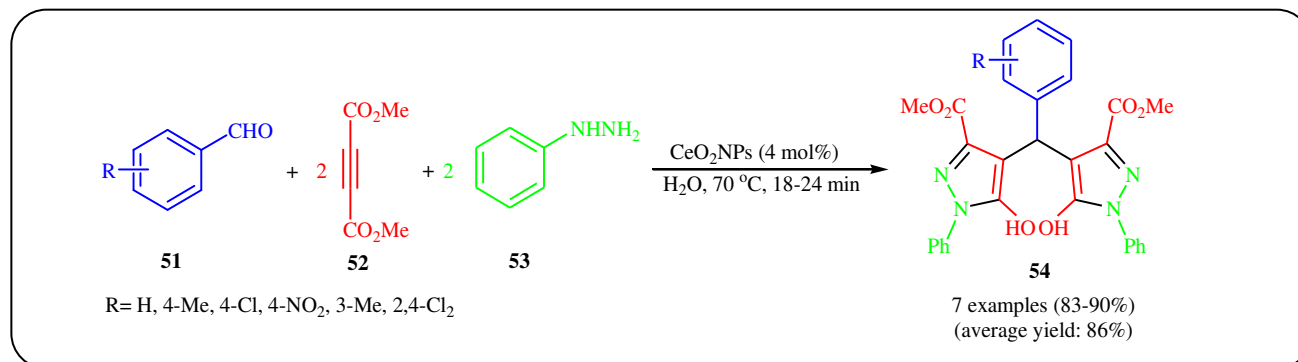


Scheme 19: Multicomponent synthesis of C-tethered bispyrazol-5-ols 54 using CeO₂ nanoparticles as catalyst.

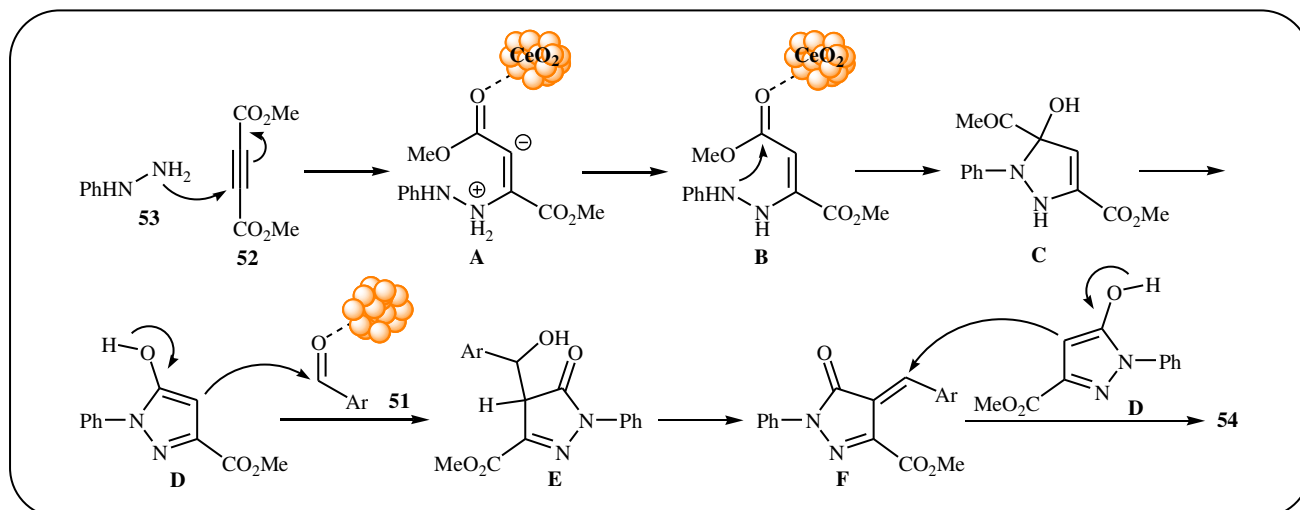

Scheme 20: Plausible mechanism for the synthesis of C-tethered bispyrazol-5-ols **54**.

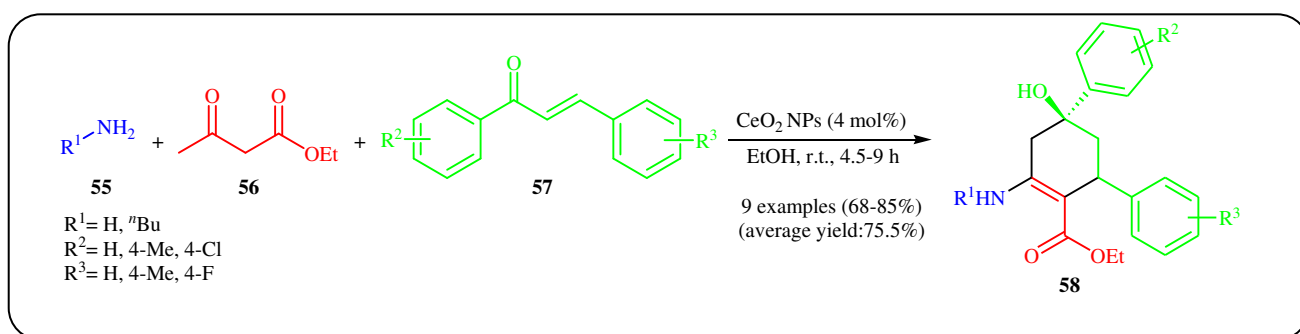


Scheme 21: CeO₂ NPs-catalyzed synthesis of cyclic β -aminoesters **58** by three-component reaction of primary amines **55**, ethyl acetoacetate **56**, and chalcones **57**.

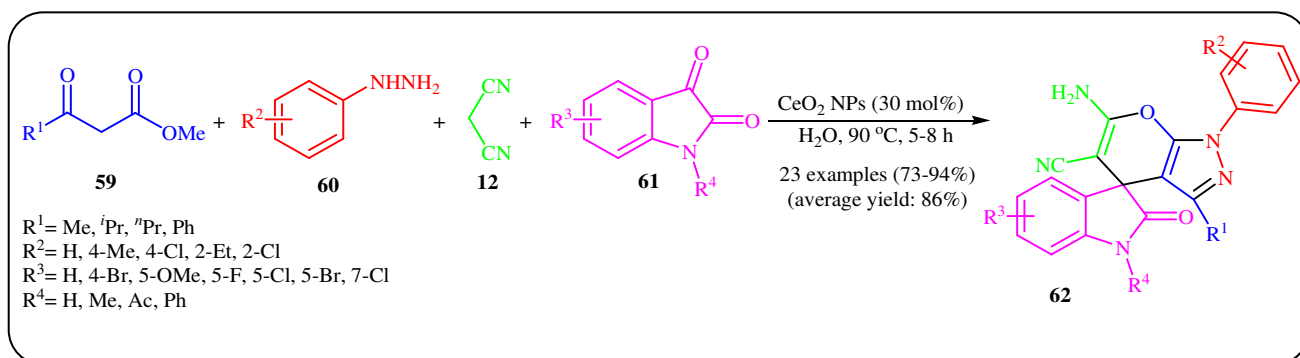

Scheme 22: Four-component synthesis of spiro[indoline-3,4'-pyrano[2,3-c]pyrazole] derivatives **62** catalyzed by ceria nanoparticles.

A four-component reaction of β -ketoesters **59**, phenylhydrazines **60**, malononitrile **12**, isatins **61** in the presence of 30 mol% of CeO₂-NPs as catalyst has been reported by Shrestha *et al.* in water at 90 °C [41]. The protocol furnished the formation of highly functionalized and biologically interesting spiro[indoline-3,4'-pyrano[2,3-

c]pyrazole] derivatives **62** in good to excellent yields (Scheme 22). The prepared spirooxindoles exhibit potent antioxidant and antibacterial activities. Mechanistically, this reaction proceeded *via* a condensation/ Knoevenagel reaction/ Michael reaction/ intramolecular cyclization/ isomerization sequential process (Scheme 23).

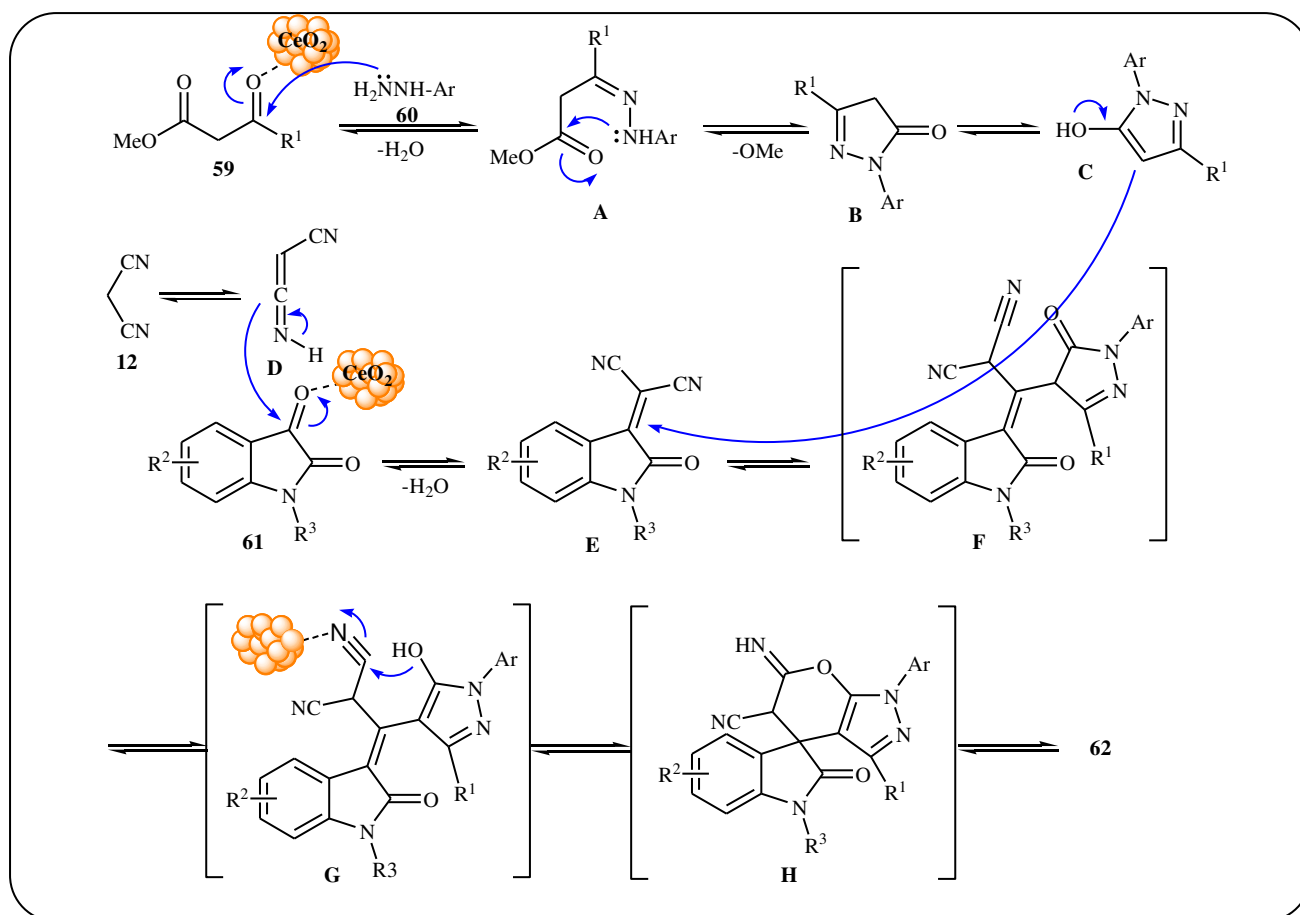

Scheme 23: Mechanism that accounts for the formation of spirooxindoles 62.

CONCLUSIONS

This Focus Review describes the recent advances on the synthesis of biologically interesting heterocyclic compounds using ceria nanoparticles as inexpensive, efficient, reusable, and environmentally sustainable heterogeneous catalyst. As illustrated, most of the reactions covered in this review have been performed in the most environmentally benign solvent, water, at room temperature. These results clearly show the potential application of CeO₂NPs-catalyzed multi-component reactions in industry. Hopefully, multi-component reactions catalyzed by CeO₂ NPs will be employed in the synthesis of complex natural and biologically important heterocyclic compounds in future studies.

Received : Apr. 20, 2019 ; Accepted : Sep. 10, 2018

REFERENCES

- [1] Eicher T., Hauptmann S., Speicher A., "The Chemistry of Heterocycles", Georg Thieme, Stuttgart (2003).
- [2] Gomtsyan A., [Heterocycles in Drugs and Drug Discovery](#), *Chem. Heterocycl. Compd.*, **48**: 7-10 (2012).
- [3] Martins P., Jesus J., Santos S., Raposo L.R., Roma-Rodrigues, C., Baptista P.V., Fernandes, A.R., [Heterocyclic Anticancer Compounds: Recent Advances and the Paradigm Shift Towards the Use of Nanomedicine's Tool Box](#), *Molecules*, **20**: 16852-16891 (2015).
- [4] (a) Vessally E., Abdoli M., [Oxime Ethers as Useful Synthons in the Synthesis of a Number of Key Medicinal Heteroaromatic Compounds](#), *J. Iran. Chem. Soc.*, **13**: 1235-1256 (2016);
(b) Babazadeh M., Soleimani-Amiri S., Vessally E., Hosseinian A., Edjlali L., [Transition Metal-Catalyzed \[2+ 2+ 2\] Cycloaddition of Nitrogen-Linked 1, 6-Diynes: A Straightforward Route to Fused Pyrrolidine Systems](#), *RSC Adv.*, **7**: 43716-43736 (2017);

- (c) Arshadi S., Vessally E., Edjlali L., Ghorbani-Kalhor E., Hosseinzadeh-Khanmiri, R., **N-Propargylic β -Enaminocarbonyls: Powerful and Versatile Building Blocks in Organic Synthesis**, *RSC Adv.*, **7**: 13198-13211 (2017);
- (d) Arshadi S., Vessally E., Sobati M., Hosseinian A., Bekhradnia A., **Chemical Fixation of CO₂ to N-Propargylamines: A Straightforward Route to 2-Oxazolidinones**, *J. CO₂ Util.*, **19**: 120-129 (2017);
- (e) Vessally E., Babazadeh M., Didehban K., Hosseinian A., Edjlali L., **Intramolecular Cyclization of N-Arylpropiolamides: A New Strategy for the Synthesis of Functionalized 2-Quinolones**, *Cur. Org. Chem.*, **21**: 2561-2572 (2017);
- (f) Vessally E., Hosseinian A., Edjlali L., Ghorbani-Kalhor E., Hosseinzadeh-Khanmiri R., **Intramolecular Cyclization of N-Propargyl Anilines: A New Synthetic Entry Into Highly Substituted Indoles**, *J. Iran. Chem. Soc.*, **14**: 2339-2353 (2017);
- (g) Vessally E., Hosseinian A., Edjlali L., Babazadeh M., Hosseinzadeh-Khanmiri R., **New Strategy for the Synthesis of Morpholine Cores: Synthesis from N-Propargylamines**, *Iran. J. Chem. Chem. Eng. (IJCCE)*, **36**: 1-13 (2017).
- [5] (a) D'Souza D.M., Mueller T.J., **Multi-Component Syntheses of Heterocycles by Transition-Metal Catalysis**, *Chem. Soc. Rev.*, **36**: 1095-1108 (2007);
- (b) Jiang B., Rajale T., Wever W., Tu S.J., Li G., **Multicomponent Reactions for the Synthesis of Heterocycles**, *Chem. Asian J.*, **5**: 2318-2335 (2010).
- (c) Banerjee B., **Recent Developments on Ultrasound-Assisted One-Pot Multicomponent Synthesis of Biologically Relevant Heterocycles**, *Ultrason Sonochem.*, **35**: 15-35 (2017);
- (d) Ibarra I.A., Islas-Jácome A., González-Zamora E., **Synthesis of Polyheterocycles via Multicomponent Reactions**, *Org. Biomol. Chem.*, **16**: 1402-1418 (2018);
- (e) Ramazani A., Reza Kazemizadeh A., **Preparation of Stabilized Phosphorus Ylides via Multicomponent Reactions and their Synthetic Applications**, *Cur. Org. Chem.*, **15**: 3986-4020 (2011);
- (f) Reza Kazemizadeh A., Ramazani A., **Synthetic Applications of Passerini Reaction**, *Cur. Org. Chem.*, **16**: 418-450 (2012);
- (g) Marjani A.P., Khalafy J., Chitan M., Mahmoodi S., **Microwave-Assisted Synthesis of Acridine-1,8(2H,5H)-Diones via a One-Pot, Three Component Reaction**, *Iran. J. Chem. Chem. Eng. (IJCCE)*, **36**: 1-6 (2017).
- [6] Bhaskaruni S.V., Maddila S., Gangu K.K., Jonnalagadda S.B., **A Review on Multi-Component Green Synthesis of N-Containing Heterocycles Using Mixed Oxides as Heterogeneous Catalysts**, *Arab. J. Chem.*, (2017).
DOI: 10.1016/j.arabjc.2017.09.016.
- [7] (a) Vessally E., Babazadeh M., Hosseinian A., Arshadi S., Edjlali L., **Nanocatalysts for Chemical Transformation of Carbon Dioxide**, *J. CO₂ Util.*, **21**: 491-502 (2017);
- (b) Didehban K., Vessally E., Hosseinian A., Edjlali L., Khosroshahi E.S., **Nanocatalysts for C–Se Cross-Coupling Reactions**, *RSC Adv.*, **8**: 291-301 (2018);
- (c) Vessally E., Didehban K., Mohammadi R., Hosseinian A., Babazadeh M., **Recent Advantages in the Metal (bulk and nano)-Catalyzed S-Arylation Reactions of Thiols with Aryl Halides in Water: A Perfect Synergy for Eco-Compatible Preparation of Aromatic Thioethers**, *J. Sulfur Chem.*, **39**: 332-349 (2018);
- (d) Ramazani A., Asiabi P.A., Aghahosseini H., Gouranlou F., **Review on the Synthesis and Functionalization of SiO₂ Nanoparticles as Solid Supported Catalysts**, *Cur. Org. Chem.*, **21**: 908-922 (2017);
- (e) Aghahosseini H., Ramazani A., Gouranlou F., Woo J.S., **Nanoreactors Technology in Green Organic Synthesis**, *Cur. Org. Synth.*, **14**: 810-864 (2017);
- (f) Nakhaei A., Davoodnia A., Yadegarian S., **An Efficient Green Approach for the Synthesis of Fluoroquinolones as Potential Antibacterial Using Nano Zirconia Sulfuric Acid as Highly Efficient Recyclable Catalyst**, *Iran. J. Chem. Chem. Eng. (IJCCE)*, **37**(3): 33-42 (2018).
- (g) Kalhor M., Seyedzade Z., **Ni@zeolite-Y Nano-Porous: Preparation and Application as a High Efficient Catalyst for Facile Synthesis of Quinoxaline, Pyridopyrazine and Indoloquinoxaline Derivatives**, *Iran. J. Chem. Chem. Eng. (IJCCE)*, **38**(1): 27-41 (2019)..

- [8] Shirini F., Abedini M., [Application of Nanocatalysts in Multi-Component Reactions](#), *J. Nanosci. Nanotechnol.*, **13**: 4838-4860 (2013).
- [9] (a) Juárez R., Concepción P., Corma A., García H., [Cerium Nanoparticles as Heterogeneous Catalyst for CO₂ Fixation by \$\omega\$ -Aminoalcohols](#), *ChemComm.*, **46**: 4181-4183 (2010);
(b) Leyva-Pérez A., Cómbita-Merchán D., Cabrero-Antonino J.R., Al-Resayes S.I., Corma A., [Oxyhalogenation of Activated Arenes with Nanocrystalline Ceria](#), *ACS Catal.*, **3**: 250-258 (2013);
(c) Shelkar R., Sarode S., Nagarkar J., [Nano Ceria Catalyzed Synthesis of Substituted Benzimidazole, Benzothiazole, and Benzoxazole in Aqueous Media](#), *Tetrahedron Lett.*, **54**: 6986-6990 (2013).
- [10] Dheer D., Singh V., Shankar R., [Medicinal Attributes of 1, 2, 3-Triazoles: Current Developments](#), *Bioorganic. Chem.*, **71**: 30-54 (2017).
- [11] (a) Agalave S.G., Maujan S.R., Pore V.S., [Click Chemistry: 1, 2, 3-Triazoles as Pharmacophores](#), *Chem. Asian J.*, **6**: 2696-2718 (2011);
(b) Jalani H.B., Karagöz A.Ç., Tsogoeva S.B., [Synthesis of Substituted 1, 2, 3-Triazoles Via Metal-Free Click Cycloaddition Reactions and Alternative Cyclization Methods](#), *Synthesis*, **49**: 29-41 (2017);
(c) Saeidian H., Sadighian H., Abdoli M., Sahandi M., [Versatile and Green Synthesis, Spectroscopic Characterizations, Crystal Structure and DFT Calculations of 1, 2, 3-Triazole-Based Sulfonamides](#), *J. Mol. Struct.*, **1131**: 73-78 (2017).
- [12] Albadi J., Shiran J.A., Mansourneshad A., [Click Synthesis of 1,4-Disubstituted-1,2,3-Triazoles Catalysed by CuO-CeO₂ Nanocomposite in the Presence of Amberlite-Supported Azide](#), *J. Chem. Sci.*, **126**: 147-150 (2014).
- [13] Amini M., Hassandoost R., Bagherzadeh M., Gautam S., Chae K.H. [Copper Nanoparticles Supported on CeO₂ as an Efficient Catalyst for Click Reactions of Azides with Alkynes](#), *Catal. Commun.*, **85**: 13-16 (2016).
- [14] Bhardwaj V., Gumber D., Abbot V., Dhiman S., Sharma P., [Pyrrole: A Resourceful Small Molecule in Key Medicinal Hetero-Aromatics](#), *RSC Adv.*, **5**: 15233-15266 (2015).
- [15] Vessally E., [A New Avenue to the Synthesis of Highly Substituted Pyrroles: Synthesis from N-Propargylamines](#), *RSC Adv.*, **6**: 18619-18631 (2016).
- [16] (a) Estevez V., Villacampa M., Menendez J.C., [Multicomponent Reactions for the Synthesis of Pyrroles](#), *Chem. Soc. Rev.*, **39**: 4402-4421 (2010);
(b) Estévez V., Villacampa M., Menéndez J.C., [Recent Advances in the Synthesis of Pyrroles by Multicomponent Reactions](#), *Chem. Soc. Rev.*, **43**: 4633-4657 (2014);
(c) Saeidian H., Abdoli M., Salimi R., [One-Pot Synthesis of Highly Substituted Pyrroles Using Nano Copper Oxide as an Effective Heterogeneous Nanocatalyst](#), *C. R. Chim.*, **16**: 1063-1070 (2013).
- [17] Samai B., Sarkar S., Chall S., Rakshit S., Bhattacharya S.C., [Polymer-Fabricated Synthesis of Cerium Oxide Nanoparticles and Applications as a Green Catalyst Towards Multicomponent Transformation with Size-Dependent Activity Studies](#), *Cryst. Eng. Comm.*, **18**: 7873-7882 (2016).
- [18] Wang Y., Ge W., Fang Y., Ren X., Cao S., Liu G., Li M., Xu J., Wan Y., Han X., [Porous CeO₂ Nanorod-Catalyzed Synthesis of Poly-Substituted Imino-Pyrrolidine-Thiones](#), *Res. Chem. Intermed.*, **43**: 631-640 (2017).
- [19] (a) Goetz A.E., Garg N.K., [Regioselective Reactions of 3, 4-Pyridynes Enabled by the Aryne Distortion Model](#), *Nature Chem.*, **5**: 54-60 (2013);
(b) Baumann M., Baxendale I.R., [An Overview of the Synthetic Routes to the Best Selling Drugs Containing 6-Membered Heterocycles](#), *Beilstein J. Org. Chem.*, **9**: 2265-2319 (2013).
- [20] (a) Hill M.D., [Recent Strategies for the Synthesis of Pyridine Derivatives](#), *Chem. Eur. J.*, **16**: 12052-12062 (2010);
(b) Vessally E., Hosseinian A., Edjlali L., Bekhradnia A., Esrafil M.D., [New Page to Access Pyridine Derivatives: Synthesis from N-Propargylamines](#), *RSC Adv.*, **6**: 71662-71675 (2016).
- [21] Gawande M.B., Bonifácio V.D., Varma R.S., Nogueira I.D., Bundaleski N., Ghumman C.A.A., Teodoro O.M., Branco P.S., [Magnetically Recyclable Magnetite-Ceria \(Nanocat-Fe-Ce\) Nanocatalyst-Applications in Multicomponent Reactions under Benign Conditions](#), *Green Chem.*, **15**: 1226-1231 (2013).

- [22] Girija D., Naik H.S.B., Sudhamani C., Kumar B.V., Cerium Oxide Nanoparticles - A Green, Reusable, and Highly Efficient Heterogeneous Catalyst for the Synthesis of Polyhydroquinolines under Solvent-Free Conditions, *Arch. Appl. Sci. Res.*, **3**: 373-382 (2011).
- [23] Kumar P.S.V., Suresh L., Vinodkumar T., Chandramouli G., Eu_2O_3 Modified CeO_2 Nanoparticles as a Heterogeneous Catalyst for an Efficient Green Multicomponent Synthesis of Novel Phenylidiazanyl-acridinedione-Carboxylic acid derivatives in Aqueous Medium, *RSC Adv.*, **6**: 91133-91140 (2016).
- [24] Sharma V., Chitranshi N., Agarwal A.K., Significance and Biological Importance of Pyrimidine in the Microbial World, *Int. J. Med. Chem.*, (2014) DOI: 10.1155/2014/202784.
- [25] Selvam T.P., James C.R., Dniandev P.V., Valzita S.K., A Mini Review of Pyrimidine and Fused Pyrimidine Marketed Drugs, *Res. Pharm.*, **2**: 1-9 (2015).
- [26] Gore R.P., Rajput A.P., A review on recent Progress in Multicomponent Reactions of Pyrimidine Synthesis, *Drug Inv. Today*, **5**: 148-152 (2013).
- [27] Sabitha G., Reddy K.B., Yadav J., Shailaja D., Sivudu K.S., Ceria/vinylpyridine Polymer Nanocomposite: an Ecofriendly Catalyst for the Synthesis of 3, 4-dihydropyrimidin-2 (1H)-ones, *Tetrahedron Lett.*, **46**: 8221-8224 (2005).
- [28] Biklarian H., Behbahani F.K., Fakhroueian Z., 22% Co/ CeO_2 - ZrO_2 -catalyzed Synthesis of 1, 2, 3, 4-tetrahydro-2-pyrimidinones and-thiones, *Lett. Org. Chem.*, **9**:580-584 (2012).
- [29] Albadi J., Mansournezhad A., CuO- CeO_2 Nanocomposite: A Green Recyclable Catalyst for the Synthesis of 3, 4-dihydropyrimidin-2 (1H)-Ones/Thiones, *Iran. J. Catal.*, **3**, 73-77 (2013).
- [30] Suresh L., Kumar P.S.V., Vinodkumar T., Chandramouli G., Heterogeneous Recyclable Nano- CeO_2 Catalyst: Efficient and Eco-Friendly Synthesis of Novel Fused Triazolo and Tetrazolo Pyrimidine Derivatives in Aqueous Medium, *RSC Adv.*, **6**: 68788-68797 (2016).
- [31] (a) Ballini R., Bosica G., Conforti M.L., Maggi R., Mazzacani A., Righi P., Sartori G., Three-Component Process for the Synthesis of 2-amino-2-Chromenes in Aqueous Media, *Tetrahedron*, **57**, 1395-1398 (2001);
- (b) Maggi R., Ballini R., Sartori G., Sartorio R., Basic Alumina Catalyzed Synthesis of Substituted 2-amino-2-chromenes via Three-Component reaction, *Tetrahedron Lett.*, **45**: 2297-2299 (2004);
- (c) Sabitha G., Bhikshapathi M., Nayak S., Srinivas R., Yadav J., Triton B Catalyzed Three-Component, One-Pot Synthesis of 2-amino-2-chromenes at Ambient Temperature, *J. Heterocycl. Chem.*, **48**: 267-271 (2011).
- [32] Pratap R., Ram V.J., Natural and Synthetic Chromenes, Fused Chromenes, and Versatility of Dihydrobenzo[h]chromenes in Organic Synthesis, *Chem. Rev.*, **114**: 10476-10526 (2014).
- [33] Samantaray S., Pradhan D., Hota G., Mishra B., Catalytic Application of CeO_2 - CaO Nanocomposite Oxide Synthesized Using Amorphous Citrate Process Toward the Aqueous Phase One Pot Synthesis of 2-amino-2-chromenes, *Chem. Eng. J.*, **193**: 1-9 (2012).
- [34] Albadi J., Razeghi A., Mansournezhad A., Azarian Z., CuO- CeO_2 Nanocomposite Catalyzed Efficient Synthesis of Aminochromenes, *JNSC*, **3**: 85- (2013).
- [35] Sagar Vijay Kumar P., Suresh L., Vinodkumar T., Reddy B.M., Chandramouli G., Zirconium Doped Ceria Nanoparticles: An Efficient and Reusable Catalyst for a Green Multicomponent Synthesis of Novel Phenylidiazanyl-chromene Derivatives Using Aqueous Medium, *ACS Sustain. Chem. Eng.*, **4**: 2376-2386 (2016).
- [36] Edayadulla N., Lee Y.R., Cerium oxide Nanoparticle-catalyzed Three-Component Protocol for the Synthesis of Highly Substituted Novel Quinoxalin-2-Amine Derivatives and 3,4-Dihydroquinoxalin-2-Amines in Water, *RSC Adv.*, **4**: 11459-11468 (2014).
- [37] Albadi J., Mansournezhad A., Derakhshandeh Z., CuO- CeO_2 Nanocomposite: a Highly Efficient Recyclable Catalyst for the Multicomponent Synthesis of 4H-benzo [b] pyran Derivatives, *Chin. Chem. Lett.*, **24**: 821-824 (2013).
- [38] Albadi J., Mansournezhad A., Abbaszadeh H., CuO- CeO_2 Nanocomposite: A Highly Efficient Recyclable Catalyst for the Green Synthesis of 1,8-dioxooctahydroxanthenes in Water, *J. Chin. Chem. Soc.*, **60**: 1193-1196 (2013).

- [39] Safaei-Ghomi J., Asgari-Keirabadi M., Khojastehbakhht-Koopaei B., Shahbazi-Alavi H., [Multicomponent Synthesis of C-Tethered Bispyrazol-5-ols Using CeO₂ Nanoparticles as an Efficient and Green Catalyst](#), *Res. Chem. Intermed.*, **42**, 827-837 (2016).
- [40] Saraei-Ghomi J., Kalhor S., Shahbazi-Alavi H., Asgari-Kheirabadi M., [Three-Component Synthesis of Cyclic β-aminoesters Using CeO₂ Nanoparticles as an Efficient and Reusable Catalyst](#), *Turk. J. Chem.*, **39**, 843-849 (2015).
- [41] Shrestha R., Sharma K., Lee Y.R., Wee Y.J., [Cerium Oxide-catalyzed Multicomponent Condensation Approach to Spirooxindoles in Water](#), *Mol. Divers.*, **20**, 847-858 (2016).