

## $\text{ND}_4$ Deuteron NMR and the Smearing of the Glass Transition in $\text{Rb}_{1-x}(\text{ND}_4)_x\text{D}_2\text{PO}_4$

This content has been downloaded from IOPscience. Please scroll down to see the full text.

1988 Europhys. Lett. 6 55

(<http://iopscience.iop.org/0295-5075/6/1/010>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 153.90.170.56

This content was downloaded on 09/07/2015 at 17:07

Please note that [terms and conditions apply](#).

## ND<sub>4</sub> Deuteron NMR and the Smearing of the Glass Transition in Rb<sub>1-x</sub>(ND<sub>4</sub>)<sub>x</sub>D<sub>2</sub>PO<sub>4</sub>.

R. BLINC(\*), J. DOLINŠEK(\*), V. H. SCHMIDT(\*\*) and D. C. AILION(\*\*\*)

(\*) *J. Stefan Institute, E. Kardelj University of Ljubljana, Ljubljana, Yugoslavia*

(\*\*) *Montana State University, Physics Department, Bozeman, MT, U.S.A.*

(\*\*\*) *University of Utah, Physics Department, Salt Lake City, UT, U.S.A.*

(received 2 December 1987; accepted in final form 25 February 1988)

PACS. 64.70P – Glass transitions.

PACS. 76.60 – Nuclear magnetic resonance and relaxation.

**Abstract.** – The broadening of the rotationally averaged ND<sub>4</sub><sup>+</sup> deuteron lines in Rb<sub>0.56</sub>(ND<sub>4</sub>)<sub>0.44</sub>D<sub>2</sub>PO<sub>4</sub> due to the gradual «acid» deuteron freeze-out allows for a direct determination of the Edwards-Anderson pseudospin glass order parameter  $q$  far above the nominal glass transition temperature  $T_G$ . The data provide strong evidence for a model where the basic difference between magnetic spin glasses and proton or deuteron pseudospin glasses is the presence of an inherent random field resulting from the substitutional disorder. This field acts as an ordering field conjugate to the pseudospin glass order parameter  $q$  and is responsible for the smearing of the deuteron glass transition.

A frozen proton pseudospin glass phase has been recently observed at low temperatures in mixed solid solutions Rb<sub>1-x</sub>(NH<sub>4</sub>)<sub>x</sub>H<sub>2</sub>PO<sub>4</sub> of ferroelectric RbH<sub>2</sub>PO<sub>4</sub> (RbDP) and antiferroelectric NH<sub>4</sub>H<sub>2</sub>PO<sub>4</sub> (ADP) for  $0.22 \leq x \leq 0.74$  [1, 2]. In contrast to magnetic spin glasses the cusp in the dielectric susceptibility is rounded [1, 2] and the freezing takes place over an unusually large-temperature interval [1-4] far above the glass transition temperature  $T_G$  [5, 6]. The microscopic origin of this behaviour—which points towards a basic difference between spin glasses and proton glasses—is still a subject of intensive research.

The ferroelectric (FE) transition in RbDP is connected with the ordering of the «acid» O-H...O protons into the two polar H<sub>2</sub>PO<sub>4</sub> Slater configurations, whereas the antiferroelectric (AFE) transition in ADP involves a different type of «acid» O-H...O ordering. Here the O-H...O protons order into the four «lateral» H<sub>2</sub>PO<sub>4</sub> Slater configurations [7]. X-ray diffraction results [8, 9] have shown that in ADP each NH<sub>4</sub> ion is shifted below  $T_c$  to an off-centre position by forming two shorter and two longer N-H...O hydrogen bonds with the four surrounding PO<sub>4</sub> tetrahedra.

The microscopic origin of the difference in the O-H...O proton ordering [10] in FE RbDP and AFE ADP is an NH<sub>4</sub>-mediated indirect pseudospin-type interaction between «acid» O-H...O protons belonging to different PO<sub>4</sub> groups [11-13]. When a PO<sub>4</sub> oxygen is connected to an NH<sub>4</sub> group by a «short» N-H...O bond, it tends to keep the «acid» proton in the O-H...O bond in the «far» position, whereas it tends to keep the «acid» proton in the «close»

position nearby if the N-H...O bond is «long». The requirement that two adjacent N-H...O bonds be short is incompatible with the FE ordering of protons around the PO<sub>4</sub> groups, but is compatible with AFE ordering. This indirect proton-proton coupling is random in Rb<sub>1-x</sub>(NH<sub>4</sub>)<sub>x</sub>H<sub>2</sub>PO<sub>4</sub>. There, the NH<sub>4</sub> ions also induce a tilt in the double-well potentials of those O-H...O bonds, where one oxygen is N-H...O bonded, while the other neighbours on a Rb ion. This tilt can be simulated by a random field acting on the O-H...O pseudospins [14].

In the paraelectric phase of deuterated ADP all ND<sub>4</sub> groups in the unit cell are equivalent<sup>(1)</sup>. The environment of each ND<sub>4</sub><sup>+</sup> ion is identical and axially symmetric along the crystal *c*-axis on the time scale of the NMR experiment. This is so because of the fast intrabond motion of the «acid» deuterons between the two possible equilibrium sites in the O-D...O bonds. In view of the fast hindered rotation [14] of the ND<sub>4</sub><sup>+</sup> groups—which is, however, much slower than the O-D...O intrabond motion—each D site in a given ammonium ion experiences the same time-averaged electric-field gradient (EFG) tensor which is axially symmetric. Such a behaviour has been indeed observed in paraelectric DADP (see<sup>(1)</sup>) and DADA [10], where the ND<sub>4</sub> deuteron quadrupole coupling constant  $e^2qQ/h$  has been found to be 3.6 kHz and the asymmetry parameter is zero  $\eta = (V_{XX} - V_{YY})/V_{ZZ} = 0$ .

In the AFE phase the situation is radically different. The freeze-out of the «acid» O-D...O deuteron intrabond motion at  $T_c$  results in a nonaxially symmetric environment and the «static» formation of two «short» and two «long» N-H...O bonds for a given ND<sub>4</sub><sup>+</sup> off-center site. This results in a nonzero value of the asymmetry parameter  $\eta$ . Above 110 K the hindered rotation of the ND<sub>4</sub><sup>+</sup> ion is still fast enough so that all four deuterons in a given ND<sub>4</sub> group experience the same rotationally averaged EFG tensor. Any one of the four AFE domains has an ND<sub>4</sub><sup>+</sup> deuteron EFG tensor, whose direction cosines have the same *c* component, but whose projections on the (*a*, *b*)-plane differ in view of the asymmetric positions that the ND<sub>4</sub> ions occupy relative to the four oxygens to which they are hydrogen bonded. This is indeed what has been found below  $T_c$  in DADP (see<sup>(1)</sup>) and DADA [10]. Here all ND<sub>4</sub><sup>+</sup> EFG tensors [10] are characterized by the quadrupole coupling constant  $e^2qQ/h = 8.1$  kHz and the asymmetry parameter  $\eta = 0.87$ .

The observation of the rotationally averaged ND<sub>4</sub><sup>+</sup> deuteron EFG tensor in Rb<sub>1-x</sub>(ND<sub>4</sub>)<sub>x</sub>D<sub>2</sub>PO<sub>4</sub> should thus allow for a high-resolution study of the gradual O-D...O «acid» deuteron freeze-out and the role of the ND<sub>4</sub><sup>+</sup> ions in this pseudospin glass transition.

The temperature and angular dependences of the ND<sub>4</sub><sup>+</sup> deuteron Fourier transform NMR spectra have been measured for a series of mixed Rb<sub>1-x</sub>(ND<sub>4</sub>)<sub>x</sub>D<sub>2</sub>PO<sub>4</sub> single crystals at  $\nu_L(^2\text{H}) = 41.462$  MHz using a 90°(*x*) – 90°(*y*) spin echo sequence. The width of the 90° pulse was 4  $\mu$ s. Quadrature detection was used. The homogeneous linewidth  $T_2^{-1}$  was measured by the Hahn echo and the spin-lattice relaxation time  $T_1$  by the (180 ÷ 90)° pulse sequence.

The temperature dependence of the ND<sub>4</sub><sup>+</sup> deuteron lineshapes for  $\vec{a} \perp \vec{H}_0$ ,  $\vec{c} \parallel \vec{H}_0 = 150^\circ$  and  $x = 0.44$  are shown in fig. 1. Between room temperature ( $T = 17^\circ\text{C}$ ) and  $T = -115^\circ\text{C}$  the spectrum is a doublet which can be described as a superposition of two Gaussians displaced by 3.9 kHz. The width of the two Gaussians slowly increases with decreasing temperature, whereas their separation and position are practically temperature independent. Due to the increase in the linewidth of the two Gaussians, the doublet splitting disappears below  $-120^\circ\text{C}$  and only a single «broad» line remains. At still lower temperatures the ND<sub>4</sub> rotation slows down so much that the ND<sub>4</sub><sup>+</sup> spectrum is not anymore rotationally averaged and additional fine structure due to the «rigid» lattice spectra of the ND<sub>4</sub><sup>+</sup> deuterons appears.

(<sup>1</sup>) Unpublished work from this laboratory.

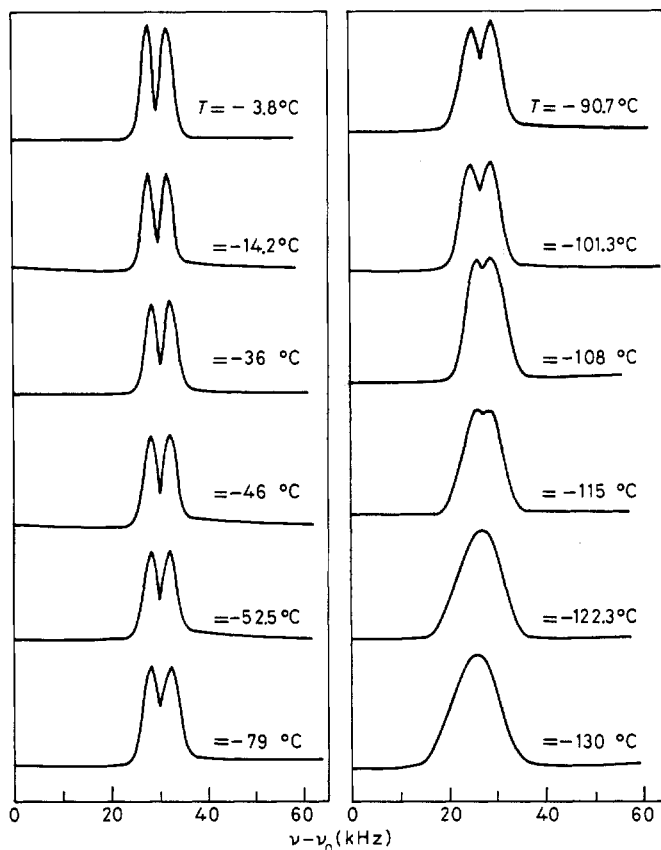


Fig. 1. - Temperature dependence of the ND<sub>4</sub><sup>+</sup> deuteron NMR lineshapes in Rb<sub>0.56</sub>(ND<sub>4</sub>)<sub>0.44</sub>D<sub>2</sub>PO<sub>4</sub> for  $\vec{a} \perp \vec{H}_0$ ,  $\angle \vec{c}, \vec{H}_0 = 150^\circ$ .  $\nu_0(^2\text{H}) = 41.46$  MHz.

The ND<sub>4</sub><sup>+</sup> doublet splitting observed at room temperature in Rb<sub>0.56</sub>(ND<sub>4</sub>)<sub>0.44</sub>D<sub>2</sub>PO<sub>4</sub> is analogous to the one found in pure deuterated ADP. It is compatible with the axially symmetric ND<sub>4</sub><sup>+</sup> EFG tensor expected to be found in the paraelectric phase at the ammonium site if all «acid» deuterons move fast between the two equilibrium sites in the O-D...O bonds. What is highly unusual—and very different from the situation in deuterated ADA—is the temperature-dependent broadening of the doublet components between +17°C and -115°C. The broadening is inhomogeneous—as shown by Hahn echo measurements—and anisotropic as expected if it is due to the gradual «freeze-out» of the «acid»-deuteron intrabond motion. At room temperature the homogeneous linewidth is ~700 Hz and the inhomogeneous 2.6 kHz, whereas at ~130°C these two values are 900 Hz and 9.6 kHz, respectively. This cannot be due to the onset of the rotational freeze-out of the ND<sub>4</sub> groups as we are in the interval from +17°C to -117°C on the high-temperature side of the  $T_1$  minimum (fig. 2) and thus in the fast-motion regime, where  $\omega_L \tau_{\text{rot}} \ll 1$ . An additional argument in favour of this statement is provided by the fact that the activation energy for ND<sub>4</sub> rotation is about 160 meV, whereas the activation energy for the observed ND<sub>4</sub> line broadening—if one tries to describe this as a thermally activated process—would amount to only 25 meV. It is thus safe to conclude that the observed ND<sub>4</sub><sup>+</sup> broadening is due to a gradual «freeze-out» of the «acid»-deuteron intrabond motion far above the glass

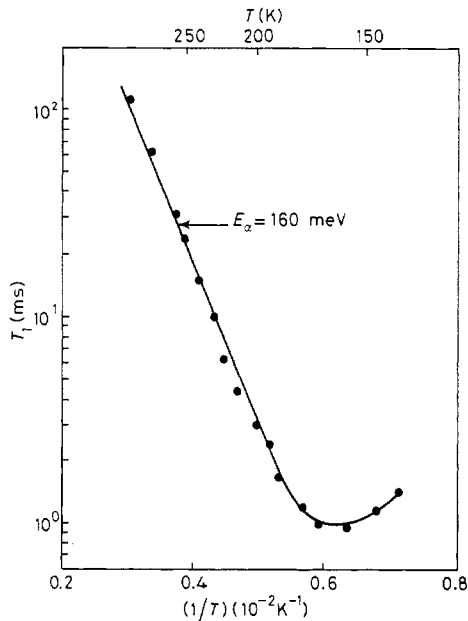


Fig. 2. - Temperature dependence of the  $\text{ND}_4^+$  deuteron spin-lattice relaxation time  $T_1$  in  $\text{Rb}_{0.56}(\text{ND}_4)_{0.44}\text{D}_2\text{PO}_4$  for  $\bar{a} \perp \bar{H}_0$ ,  $\angle \bar{c}, \bar{H}_0 = 150^\circ$ .

transition  $T_G \approx 90$  K. It should be noted that above  $T_G$  in pure  $\text{KD}_2\text{PO}_4$ -type crystals the «acid» deuterons move between the two equilibrium sites in the O-D...O bonds with a rate ( $10^{10} \div 10^{11}$ ) Hz and this motion «freezes-out» only below  $T_G$ .

The observed «acid» deuteron «freeze-out» far above  $T_G$  in  $\text{Rb}_{1-x}(\text{ND}_4)_x\text{D}_2\text{PO}_4$  for  $x = 0.44$  can be understood as a result of a random field smearing of the deuteron glass transition [14, 15]. The variance of the random field induced by the substitutional disorder acts as an ordering field conjugate to the Edwards-Anderson spin glass order parameter [15] and induces a finite value of this order parameter far above the nominal transition temperature  $T_G$ . This results in a random gradual O D...O deuteron freeze-out which in turn produces a broadening of the NMR line.

The effect on the  $\text{ND}_4^+$  NMR lineshape far above  $T_G$  can be described by a temperature-dependent inhomogeneous broadening ( $\sigma_1^2 q$ ) which is proportional to the Edwards-Anderson order parameter and thus reflects the biasing of the O-D...O deuteron intrabond motion

$$I = I_0 \exp [ - (\nu - \nu_0)^2 / 2 (\sigma_0^2 + \sigma_1^2 q) ]. \quad (1)$$

The lineshape is Gaussian far above  $T_G$ . The temperature-independent broadening  $\sigma_0^2$  reflects the inherent width of the  $\text{ND}_4$  line in the paraelectric phase.

The biasing effect can be derived as follows. The EFG tensor at the  $\text{ND}_4^+$  site is influenced by the four N-D...O bonds to the four phosphate oxygens hydrogen bonded to the given ammonium ion. This contribution depends on the state of order of the deuterons in all four O-D...O bonds which take part in the N-H—O bonding scheme. The frequency shift induced by the acid deuteron «freeze-out» is thus given by

$$\nu - \nu_0 = \sum_{i=1}^4 C_i p_i + \dots, \quad (2)$$

where the local bond order parameter  $p_i = \langle S_i^z \rangle$  measures the amount of deuteron ordering between the two equilibrium sites  $S^z = \pm 1$  in the  $i$ -th O-D...O bond. NMR measures the random average of eq. (2)

$$\overline{\nu - \nu_0} = \sum_{i=1}^4 C_i p_i = 0, \tag{3a}$$

which is zero in a pseudospin glass where

$$\overline{p_i} = \frac{1}{N} \sum_{i=1}^N \langle S_i^z \rangle = 0, \tag{3b}$$

in view of the absence of long-range ordering. The deuteron «freeze-out»  $\langle S_i^z \rangle \neq 0$  results, however, in a line broadening

$$\sigma^2 = \overline{(\nu - \nu_0)^2} = \left( \sum_{i=1}^4 C_i p_i \right)^2 = \sigma_1^2 q, \tag{4}$$

which is directly proportional to the Edwards-Anderson order parameter  $q$ . It should be noted that the four  $C_i p_i$  values in the sum (3a) are essentially uncorrelated. This is so as any path joining two acid deuterons in the sum crosses at least two phosphate groups, so that there is at least one intervening acid H-bond.

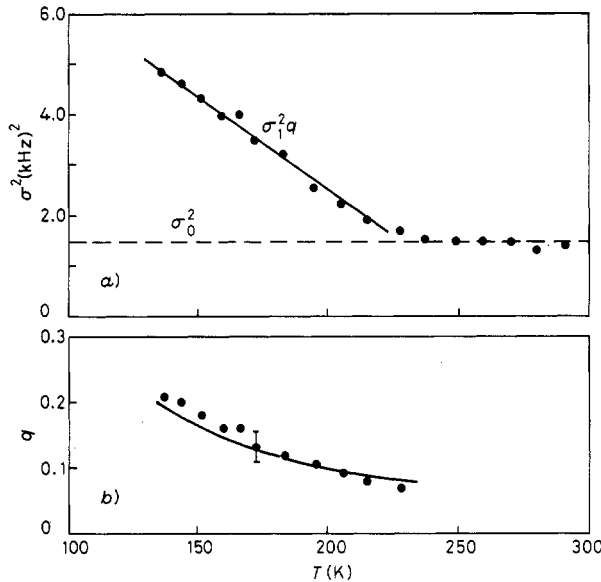


Fig. 3. - a) Temperature dependence of the ND<sub>4</sub><sup>+</sup> line broadening  $\sigma_1^2 q$  in the interval from room  $T$  to  $-117^\circ\text{C}$  for  $\text{Rb}_{0.56}(\text{ND}_4)_{0.44}\text{D}_2\text{PO}_4$ . b) Temperature dependence of the Edwards-Anderson order parameter  $q$  for  $\text{Rb}_{0.56}(\text{ND}_4)_{0.44}\text{D}_2\text{PO}_4$  as determined from the linewidth data. The experimental points can be fitted to the theoretical curve (eq. (5)) for  $\Delta/\bar{J}^2 = 1.3$  and  $\bar{J}/k_B = 60$  K. ● experiment; — theory.

According to eqs. (1) and (4) we can separate (fig. 3a)) the total width of the ND<sub>4</sub><sup>+</sup> line into a temperature-independent ( $\sigma_0^2$ ) and a temperature-dependent part ( $\sigma_1^2 q$ ). Using the data of pure DADP (see (1)) we can estimate  $\sigma_1^2$  at  $\bar{\epsilon}, \bar{H} = 150^\circ$  from the difference between

the maximum  $\text{ND}_4^+$  splitting below  $T_c$ —where all the acid protons are ordered—and the width at room temperature as  $\sigma_1 \approx 4$  kHz. The resulting  $T$ -dependence of  $q$  is shown in fig. 3b).

The theoretical temperature dependence of  $q$  can be derived from the random bond-random field Sherrington-Kirkpatrick-type Ising model of spin glasses [15] as

$$q = \frac{1}{\sqrt{2\pi}} \int_{-\infty}^{+\infty} \exp[-x^2/2] \operatorname{tgh}^2 \left( \frac{\bar{J}}{kT} \sqrt{q + \Delta/\bar{J}^2} x \right) dx, \quad (5)$$

where  $\bar{J} = J\sqrt{N}$ ,  $J^2$  is the variance of the random bond and  $\Delta$  the variance of the random field distributions [15, 16]. For  $\Delta \neq 0$ ,  $q$  is  $\neq 0$  even for  $T > T_G$ , whereas  $q = 0$  for  $T > T_G$  if  $\Delta = 0$ . The least-square fit of eq. (5) to the experimental data allows for an independent determination of  $\bar{J}$  and  $\Delta$ . We have measured a whole series of mixed deuterated solid solutions  $\text{Rb}_{1-x}(\text{ND}_4)_x\text{D}_2\text{PO}_4$  with different ammonium concentrations (see (1)) and found that  $0.4 \leq \Delta/\bar{J}^2 \leq 1.3$  and  $90 \text{ K} \geq \bar{J}/k_B \geq 60 \text{ K}$ . For  $x = 0.44$  the theoretical  $T$ -dependence of  $q$  for  $\Delta/\bar{J}^2 = 1.3$  and  $\bar{J}/k_B = 60 \text{ K}$  agrees (fig. 3b)) rather well with the one obtained from the  $T$ -dependence of the line-broadening thus yielding strong support for the random field smearing [15] of the glass transition in  $\text{Rb}_{1-x}(\text{ND}_4)_x\text{D}_2\text{PO}_4$  systems. The  $q$ -values vary from  $q = 0.08$  at 227 K to  $q = 0.21$  at 143 K, whereas the Almeida-Thouless replica symmetry breaking transition [15]  $T_G$  occurs in these systems below 90 K.

It should be noted that the above results obtained for deuteron glasses agree with previous observations in proton glasses [5, 6] that a nonzero Edwards-Anderson order parameter develops far above  $T_G$ . We believe that a random field smearing of the glass transition occurs in proton glasses as well.

## REFERENCES

- [1] COURTENS E., *Ferroelectrics*, **72** (1987) 229 and references therein.
- [2] HAYASE S., SAKASHITA H. and TERAUCHI H., *Ferroelectrics*, **72** (1987) 245 and references therein.
- [3] SCHMIDT V. H. and WANG J. T. and SCHNACKENBERG P., *Jpn. J. Appl. Phys.*, **24** (1985) 944, Suppl. 24-2.
- [4] BLINC R., AILION D. C., GÜNTHER B. and ŽUMER S., *Phys. Rev. Lett.*, **57** (1986) 2826.
- [5] COURTENS E., *J. Phys. (Paris) Lett.*, **43** (1982) L-199.
- [6] COURTENS E., HUARD F. and VACHER R., *Phys. Rev. Lett.*, **55** (1985) 722.
- [7] SILSBEE H. B., UEHLING E. A. and SCHMIDT V. H., *Phys. Rev. A*, **133** (1964) 165.
- [8] HEWAT A. W., *Nature (London)*, **246** (1973) 90.
- [9] KEELING R. O. jr. and PEPINSKY R., *Z. Kristallogr.*, **106** (1955) 236.
- [10] BLINC R., SLAK J. and LUZAR M., *Phys. Status Solidi A*, **40** (1977) K-121.
- [11] SCHMIDT V. H., *Ferroelectrics*, **72** (1987) 157 and references therein.
- [12] SELKE W. and COURTENS E., *Ferroelectr. Lett.*, **5** (1986) 173.
- [13] MATSUSHITA E. and MATSUBARA T., *J. Phys. Soc. Jpn.*, **56** (1987) 200.
- [14] BLINC R., GÜNTHER B. and AILION D. C., *Phys. Scr.*, **13** (1986) 205.
- [15] PIRC R., TADIĆ B. and BLINC R., *Phys. Rev. B*, **36**, 11 (1987).
- [16] PIRC R., TADIĆ B. and BLINC R., *Z. Phys. B*, **61** (1985) 69.