

AD-A253 658



2

OFFICE OF NAVAL RESEARCH

Contract N00014-82K-0612

R&T CODE: 4133032

TECHNICAL REPORT NO. 75

Near-IR Absorption Spectra for the C₇₀ Fullerene Anions

by

D. R. Lawson, D. L. Feldheim, C. A. Foss, P. K. Dorhout, C. M. Elliott, C. R. Martin and B. A. Parkinson

Prepared for publication

in

Journal of Physical Chemistry

Department of Chemistry
Colorado State University
Ft. Collins, CO 80523

DTIC
ELECTE
JUL 31 1992
S B D

July 20, 1992

Reproduction in whole or part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

Near-IR Absorption Spectra for the C₇₀ Fullerene Anions

Del R. Lawson, Daniel L. Feldheim, Colby A. Foss, Peter K. Dorhout,*
C. Michael Elliott,* Charles R. Martin,* Bruce Parkinson*

*Department of Chemistry
Colorado State University
Fort Collins, CO 80523*

* To whom correspondence should be addressed.

92 7 28 061



Abstract

C_{70} , like C_{60} , can exist in a number of oxidation states including C_{70}^{1-} , C_{70}^{2-} , C_{70}^{3-} and C_{70}^{4-} . We have discovered unique visible and near-IR absorption transitions which appear upon reduction of C_{70} . These transitions are observed upon one, two, three and four-electron electrochemical reductions of C_{70} . In contrast to C_{60} , however, the electronic properties of C_{70} are less well understood. In particular, previous theoretical studies of C_{70}^{1-} failed to predict the existence of the near-IR transition we observe in the spectrum of C_{70}^{1-} . In this paper, in addition to presenting the, heretofore unreported, spectra of the various C_{70} anions, we attempt a first-order explanation of the energies and intensities of the various spectral absorptions; this explanation is based on the published molecular orbital diagram for neutral C_{70} and a structural distortion that we suggest occurs upon reduction of C_{70} .

MISSING PAGES WILL BE INSERTED AT AN LATER DATE
AS ERRATA(S)

REPORT DOCUMENTATION PAGE

OMB No 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE 7-20 -- 1992	3. REPORT TYPE AND DATES COVERED Interim	
4. TITLE AND SUBTITLE Near-IR Absorption Spectra for the C ₇₀ Fullerene Anions		5. FUNDING NUMBERS Contract # N00014-82K-0612	
6. AUTHOR(S) D. R. Lawson, D. L. Feldheim, C. A. Foss, P. K. Dorhout, C. M. Elliott, C. R. Martin and B. Parkinson		8. PERFORMING ORGANIZATION REPORT NUMBER ONR TECHNICAL REPORT #75	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Dr. Charles R. Martin Department of Chemistry Colorado State University Fort Collins, CO 80523		10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22217		11. SUPPLEMENTARY NOTES	
12a. DISTRIBUTION AVAILABILITY STATEMENT Reproduction in whole or part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) See attached.			
14. SUBJECT TERMS C ₇₀ , Fullerenes, spectroscopy			15. NUMBER OF PAGES
17. SECURITY CLASSIFICATION OF REPORT			16. PRICE CODE
18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT	

Abstract

C_{70} , like C_{60} , can exist in a number of oxidation states including C_{70}^{1-} , C_{70}^{2-} , C_{70}^{3-} and C_{70}^{4-} . We have discovered unique visible and near-IR absorption transitions which appear upon reduction of C_{70} . These transitions are observed upon one, two, three and four-electron electrochemical reductions of C_{70} . In contrast to C_{60} , however, the electronic properties of C_{70} are less well understood. In particular, previous theoretical studies of C_{70}^{1-} failed to predict the existence of the near-IR transition we observe in the spectrum of C_{70}^{1-} . In this paper, in addition to presenting the, heretofore unreported, spectra of the various C_{70} anions, we attempt a first-order explanation of the energies and intensities of the various spectral absorptions; this explanation is based on the published molecular orbital diagram for neutral C_{70} and a structural distortion that we suggest occurs upon reduction of C_{70} .

DTIC QUALITY INSPECTED 3

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

We have recently reported that the anionic forms of C_{60} (i.e. C_{60}^{n-} where $n = 1-4$) show near-IR absorption bands that are characteristic for each oxidation state.¹ We have since carried out analogous spectroelectrochemical investigations on the C_{70} anions. C_{70} , like C_{60} , can undergo electrochemical reduction to C_{70}^{1-} , C_{70}^{2-} , C_{70}^{3-} and C_{70}^{4-} .² Previous investigations of C_{70}^{1-} (the only C_{70} anion to be studied spectroscopically, to date), failed to detect any unique electronic transitions related to this species within the spectral ranges studied.³⁻⁵ We present in this paper the first observations of unique visible and near-IR transitions for the C_{70} anions, including a previously-undetected near-IR transition for C_{70}^{1-} . In addition to presenting the spectra of the various C_{70} anions, we attempt a first-order rationalization of the energies and intensities of the spectral absorptions; this explanation is based on modifications of the calculated molecular orbital (MO) diagram for neutral C_{70} .⁶

C_{70} (99.9%) was obtained from Texas Fullerenes. C_{70} solutions (ca. 0.15 mM) were prepared in benzonitrile that was 0.1M in Bu_4NPF_6 supporting electrolyte. Spectra of the various C_{70} species were obtained at room temperature using the method described previously.¹ Briefly, an optically-transparent thin-layer electrochemical cell⁷ was mounted within the sample chamber of a Hitachi 3501 UV-visible-near-IR spectrometer. A spectrum of C_{70} was first obtained with the cell at open circuit. Cyclic voltammetric experiments were then run to determine the electrode potentials necessary to quantitatively reduce C_{70} to the mono, di, tri and tetravalent anion. These voltammograms were essentially identical to those presented in the literature for C_{70} .² Potentials of -1.0, -1.6, -2.2 and -2.9 V (vs. Ag/Ag^+)¹ were used to generate the C_{70}^{1-} , C_{70}^{2-} , C_{70}^{3-} and C_{70}^{4-} species, respectively. Each of the C_{70} anions, generated in this manner, was stable during the lifetime of the

spectroelectrochemical experiment in rigorously-deoxygenated solutions, and could be subsequently reoxidized and re-reduced through appropriate potential control.

As previously reported,⁸ the UV-visible spectrum of C₇₀ shows strong absorptions at 330, 358, 378 and 468 nm (Figure 1, curve A). The near-IR region for C₇₀ is featureless. In contrast, all of the C₇₀ anions show absorption bands in the near-IR and/or visible regions (Figures 1 and 2). This is, apparently, the first time these bands have been described in the literature. Indeed, the only spectral data for the C₇₀ⁿ⁻ species currently in the literature is for C₇₀¹⁻.³⁻⁵ These prior reports do not, however, describe the strong absorption we observe at 1368 nm (Figure 1, curve B), because data were obtained at wavelengths below 1300 nm. The wavelengths and extinction coefficients of the absorptions of the C₇₀ anions are presented in Table I. The magnitude of these extinction coefficients (>2,000 M⁻¹cm⁻¹) indicate that the electronic transitions leading to these absorptions are symmetry allowed.

A portion of the Hückel calculated MO diagram of the D_{5h} C₇₀ molecule is shown in Figure 3A.⁶ The HOMO is the completely-filled a₂^{''} orbital and the LUMO is the a₁^{''} orbital. The HOMO → LUMO transition is forbidden and the first allowed transition, a₂^{''} → e₁^{''}, must be of sufficiently weak oscillator strength that it is not readily observed. Transitions from high-lying occupied orbitals to higher unoccupied orbitals account for the UV-visible absorptions in the spectrum of C₇₀ (Figure 1, curve A). These transitions have not been assigned previously and are not the subject of this report.

A number of theoretical methods have been used to predict the absorption spectrum of C₇₀¹⁻.³⁻⁵ Unfortunately, these theoretical analyses failed to predict the experimentally-observed spectrum. For example, Greaney and Gorun⁴ used Self Consistent Field-Hartree-Fock (SCF-HF)

calculations⁹ on neutral C₇₀ to predict the spectrum of the monoanion; this analysis suggests that there should be no near-IR transitions for C₇₀¹⁻.^{4,5} Furthermore, this analysis predicts a HOMO → LUMO transition at 2200 cm⁻¹. Both of these predictions are not consistent with the observed spectral data, as we have observed an allowed transition in the near-IR spectrum of C₇₀¹⁻ (Figure 1, curve B) and the 2200 cm⁻¹ IR transition was not detected^{4,5} for C₇₀¹⁻. Kato, et al.,³ used CNDO/S calculations on neutral C₇₀ to predict a single HOMO → LUMO transition at 2840 nm for C₇₀¹⁻. However, we have collected spectral data out to 3200 nm and do not observe any spectral absorptions beyond 1500 nm for C₇₀¹⁻.

The failure of these prior theoretical analyses to accurately predict the absorption spectrum of C₇₀¹⁻, leads us to conclude that the MO diagram of C₇₀, obtained from SCF-HF⁹ and CNDO/S³ calculations, is not directly applicable to the monoanion. Furthermore, the MO diagram for C₇₀ obtained from Hückel calculations⁶ is also not directly applicable to C₇₀¹⁻ (Figure 3A). Addition of one electron to the Hückel MO diagram for C₇₀ should populate the a₁" orbital. From a₁", however, there are no allowed transitions in the near-IR (a₁" → e₁', a₁' are forbidden). Thus, it is impossible to rationalize the experimentally-observed near-IR absorption spectrum of C₇₀¹⁻ by simply adding an electron to any of the existing MO diagrams of C₇₀.^{3-6,9} Because of the inadequacies of these previous theoretical analyses in treating C₇₀¹⁻, we have taken an approach that is analogous to that used in our successful interpretation of the spectra of the C₆₀ⁿ⁻ anions.¹ In this approach, it is assumed that addition of an electron to C₇₀ causes a geometrical distortion of the molecule that reduces symmetry.

The experimental absorption spectrum for C₇₀¹⁻ can be rationalized if it is assumed that addition of an electron to C₇₀ causes a lowering of the

symmetry from D_{5h} to C_{5v} .^{10,11} Distortion from D_{5h} to C_{5v} symmetry occurs through the loss of the mirror plane perpendicular to the principal five-fold axis. With this type of distortion, the C_{70}^{1-} molecule can exist as a dipolar anion (not supported in D_{5h}). It is conceivable that the driving force for this distortion arises from ion pairing between C_{70}^{1-} and its associated countercation or interactions with solvent dipoles. That is, the electrostatic interaction with the countercation may polarize the C_{70}^{1-} anion, creating the dipolar anion described by C_{5v} symmetry. If this is true, we would expect that the solvent and electrolyte would play a major role in the appearance of the various spectral transitions for the C_{70} anions.

We are currently examining solvent and supporting electrolyte effects on the near-IR transitions of both C_{60} and C_{70} . At this time, however, we note that the near-IR transition observed for C_{70}^{1-} appears at the same wavelength in benzonitrile and dichloromethane solutions. Furthermore, the transition energy remains constant in the presence of tetrabutyl ammonium, tetraethyl ammonium, and lithium cationic supporting electrolytes. While these studies are not exhaustive, they suggest that the distortion that occurs upon reduction of C_{70} may be an inherent feature of the fullerene anions.

In the C_{5v} configuration, the electron added to C_{70} , to make C_{70}^{1-} , occupies an a_2 orbital (Figure 3B). The electron in the a_2 orbital is allowed a single transition that should appear in the near-IR region.⁶ We have assigned the experimentally-observed near-IR absorption at 1368 nm to this C_{5v} -allowed $a_2 \rightarrow e_1$ electronic transition (Figure 1, curve B). Further support for the C_{5v} configuration of C_{70}^{1-} arises from the fact that we do not observe any absorptions in the far-visible region of the C_{70}^{1-} spectrum; transitions from $a_2 \rightarrow a_1, e_2$ (predicted to occur at ca. 700 nm)⁶ are forbidden in C_{5v} . Distortion from D_{5h} symmetry is also supported by the red-shift

and broadening of the UV-visible transitions in the spectrum of C_{70}^{1-} (Fig. 1). A similar red-shift and broadening was observed in the 330 nm transition of C_{60} upon reduction and was attributed to reduced symmetry in C_{60}^{1-} .¹

The C_{5v} MO diagram can also be used to rationalize the spectra of the other C_{70} anions.^{11, 12} The spectrum of C_{70}^{2-} is shown in Figure 2, curve A. The peak at 1368 nm, observed for C_{70}^{1-} , quantitatively disappears, and new peaks appear in the visible at 670 nm^{13,14} and the near-IR at 1170 nm. Based upon ESR measurements, C_{70}^{2-} is $S=1$.¹⁵ Consequently, the electrons must be unpaired and two configurations can be postulated. In one scenario, the two unpaired electrons are found in an asymmetric ground state configuration, $a_2^1 e_1^1$. However, the predicted near-IR transitions for this configuration are not consistent with the observed C_{70}^{2-} spectrum. The second scenario assumes a symmetric ground state¹ in which the electrons are found in the e_1 orbital as shown in Figure 3C. In this e_1^2 arrangement, the allowed near-IR and visible transitions, $e_1 \rightarrow e_1, a_1$ and $e_1 \rightarrow a_1, e_2$, should be observed. The energy of the e_1 orbital must be lowered enough, relative to the a_2 orbital, to overcome electron pairing energy. Therefore, the near-IR transitions of the divalent species ($e_1 \rightarrow e_1, a_1$) should be found at higher energy than in C_{70}^{1-} . This accounts for the shift in the near-IR transition from 1368 nm for C_{70}^{1-} to 1170 nm for C_{70}^{2-} . The energies of the LUMO+1 (e_1) and LUMO+2 (a_1) orbitals, as shown in Figure 3C, are predicted to lie very close in energy.⁶ Therefore, although two allowed near-IR transitions are expected, they appear as a single unresolved peak (Figure 3C). Similarly, the visible transitions, assigned as $e_1 \rightarrow a_1, e_2$, appear as a broad, ill-defined absorption centered at 670 nm.

The spectra of the electrochemically generated C_{70}^{3-} and C_{70}^{4-} species are shown in Figure 2, curves B and C, respectively. The peak positions of

the visible and near-IR absorptions remain at the same energy as in the spectrum of C_{70}^{2-} (a shoulder does appear at 760 nm in the spectrum of C_{70}^{3-} that quantitatively disappears upon reduction to C_{70}^{4-}). This suggests that the added electrons occupy the half-filled e_1 orbital. From this model, we would predict that C_{70}^{3-} would be $S=1/2 (e_1)^3$ and C_{70}^{4-} would be $S=0 (e_1)^4$. ESR measurements of these anions could be used to test these configurations. The visible transitions at 670 nm increase in intensity as C_{70}^{2-} is reduced to the trivalent and tetravalent forms. In contrast, the near-IR transitions at 1170 nm decrease in intensity and broaden as electrons are added to the e_1 orbital. These changes in absorption intensity may be caused by changes in oscillator strength resulting from population of π^* orbitals.

It is particularly difficult to rationalize the remarkable similarity between the spectra of the di, tri and tetravalent anions. In our first-order approximation presented above, we have attributed this similarity to a progressive filling of the $C_{5v} e_1$ orbital. Intuitively, however, we would expect the addition of the third and fourth electrons to shift the energies of the various electronic transitions with respect to the spectrum of C_{70}^{2-} .¹⁶ Nevertheless, the electronic transitions appear at the same energy in the spectra of the C_{70}^{2-} , C_{70}^{3-} and C_{70}^{4-} species. We do note a change in the visible absorption of C_{70}^{3-} (a reproducible shoulder appears at 760 nm that is not apparent in the C_{70}^{2-} and C_{70}^{4-} spectra; Figure 2B). If this feature resulted from further reduction in the symmetry of C_{70}^{3-} , shifts in the 670 and 1370 nm absorptions should be seen;¹¹ these shifts were not observed. At this time, we are unable to explain the feature at 760 nm in the spectrum of C_{70}^{3-} .

In conclusion, it is important to note that the Hückel calculations, upon which the first-order analysis presented here are based, are imperfect

with regard to predicting exact orbital energies. Therefore, although our analysis, using a modified Hückel MO diagram, qualitatively explains the experimentally-observed spectra, other more rigorous methods may lead to a better quantitative description of the electronic transitions of the C₇₀ anions. Obviously, the best theoretical treatment of the MO diagram of the C₇₀ anions would be obtained from calculations on the anions themselves. These calculations, however, are complicated by the number of atoms (seventy), and the somewhat ambiguous role of solvent and ion-pairing.

Acknowledgments

This work was supported by the Office of Naval Research and the National Science Foundation (CHE-8516904).

References

1. Lawson, D.R.; Feldheim, D.L.; Foss, C.A.; Dorhout, P.; Elliott, C.M.; Martin, C.R.; Parkinson, B. *J. Electrochemical Soc.*, **1992**, *139*, L68.
2. (a) Allemand, P.-M.; Koch, A.; Wudl, F.; Rubin, Y.; Diederich, F.; Alvarez, M.; Anz, S.; Whetten, R. *J. Am. Chem. Soc.* **1991**, *113*, 1050. (b) Dubois, D.; Kadish, K.; Flanagan, S.; Haufler, R.; Chibante, L.; Wilson, L. *J. Am. Chem. Soc.* **1991**, *113*, 4364. (c) Cox, D.; Behal, S.; Disko, M.; Gorun, S.; Greaney, M.; Hsu, C.; Kollin, E.; Miller, J.; Robbins, J.; Robbins, W.; Sherwood, R.; Tindall, P. *J. Am. Chem. Soc.* **1991**, *113*, 2940.
3. Kato, T.; Kodama, T.; Oyama, M.; Shida, T.; Nakagawa, T.; Matsui, Y.; Suzuki, S.; Shiromaru, H.; Yamauchi, K.; Achiba, Y. *Chem. Phys. Letters*, **1991**, *180*, 446.
4. Greaney, M.; Gorun, S. *J. Phys. Chem.*, **1991**, *95*, 7142.
5. Gorun, S.; Greaney, M.; Day, V.; Day, C.; Upton R.; Briant, C. In *Fullerenes*, ACS Symposium Series, Vol. 481; Hammond, G., Kuck, V., Eds.; American Chemical Society: Washington, DC, 1992; pp 41-53.
6. Fowler, P.; Woolrich, J. *Chem. Phys. Letters*, **1986**, *127*, 78.
7. Bard, A.J.; Faulkner, L. *Electrochemical Methods*; Wiley: New York, 1980; p 578.
8. (a) Ajie, H.; Alvarez, M.; Anz, S.; Beck, R.; Diederich, F.; Fostiropoulos, K.; Huffman, D.; Krätschmer, W.; Rubin, Y.; Schriver, K.; Sensharma, D.; Whetten, R. *J. Phys. Chem.* **1990**, *94*, 8630. (b) Hare, J.; Kroto, H.; Taylor, R. *Chem. Phys. Letters*. **1991**, *177*, 394. (c) Hebard, A.; Haddon, R.; Fleming, R.; Kortan, A. *Appl. Phys. Lett.*, **1991**, *59*, 2109. (d) Kroto, H.; Allaf, A.; Balm, S. *Chem. Rev.*, **1991**, *91*, 1913.
9. Scuseria, G. *Chem. Phys. Letters*. **1991**, *180*, 451.

10. Wilson, E.B.; Decius, J.; Cross, P. *Molecular Vibrations*, Dover Press: New York, 1955; p 337.
11. Other subgroups of D_{5h} , including D_5 ($D_{5h} \supset D_5$) and C_{2v} ($D_{5h} \supset C_{2v}$), were considered, but these were not consistent with the observed spectra.
12. We note that the transitions observed for the di, tri and tetravalent anions are also consistent with the ground state D_{5h} C_{70} MO diagram. In this configuration, the unpaired electrons would occupy the e_1'' orbital, lowered in energy below the a_1'' orbital. Allowed transitions to the a_2'' (visible) and e_1' (near-IR) orbitals can also explain the observed spectra of the multivalent anions. We have not ruled out this configuration, but for the sake of consistency, we show the proposed MO diagram of C_{70}^{2-} (Fig. 3C) as C_{5v} .
13. Tanigaki, K.; Ebbesen, T.; Kuroshima, S. *Chem. Phys. Letters*. **1991**, *185*, 189.
14. It is interesting to note the similarity between the visible absorption we observe at 670 nm for the multivalent C_{70} anions and the visible absorption seen at ca. 700 nm for photoexcited C_{70} in reference 13. Although the authors did not assign this absorption as other than an $S_1 \rightarrow S_n$ transition, the similarity between the photoexcited C_{70} spectrum and the spectra of the multivalent C_{70} anions suggests that the $S_1 \rightarrow S_n$ transition may result from a transition from an electron excited into an e-type orbital.
15. Dubois, D.; Kadish, K.; Flanagan, S.; Wilson, L. *J. Am. Chem. Soc.* **1991**, *113*, 7773.
16. These energy shifts would be expected from (a) electron pairing stabilization, (b) populating a π^* orbital which lowers bond order (c) the degeneracy of the C_{70}^{3-} species which should Jahn-Teller distort¹ and (d) increasing solvent and ion-pairing effects on the multivalent anions. Any or all of these effects should lead to variations in the observed absorption energy.

Table I. Spectral data for the various C₇₀ species in Benzonitrile.^a

Species	λ max (nm)	Extinction Coefficient (M ⁻¹ cm ⁻¹)
C ₇₀	330	31,000
	358	23,000
	378	31,000
	468	17,000
C ₇₀ ¹⁻	1368	4,000
C ₇₀ ²⁻	1170	7,200
	670	2,600
C ₇₀ ³⁻	1170	5,800
	670	4,600
C ₇₀ ⁴⁻	1170	3,000
	670	6,000

^a The average uncertainty in ϵ measurements is ca. 20%.

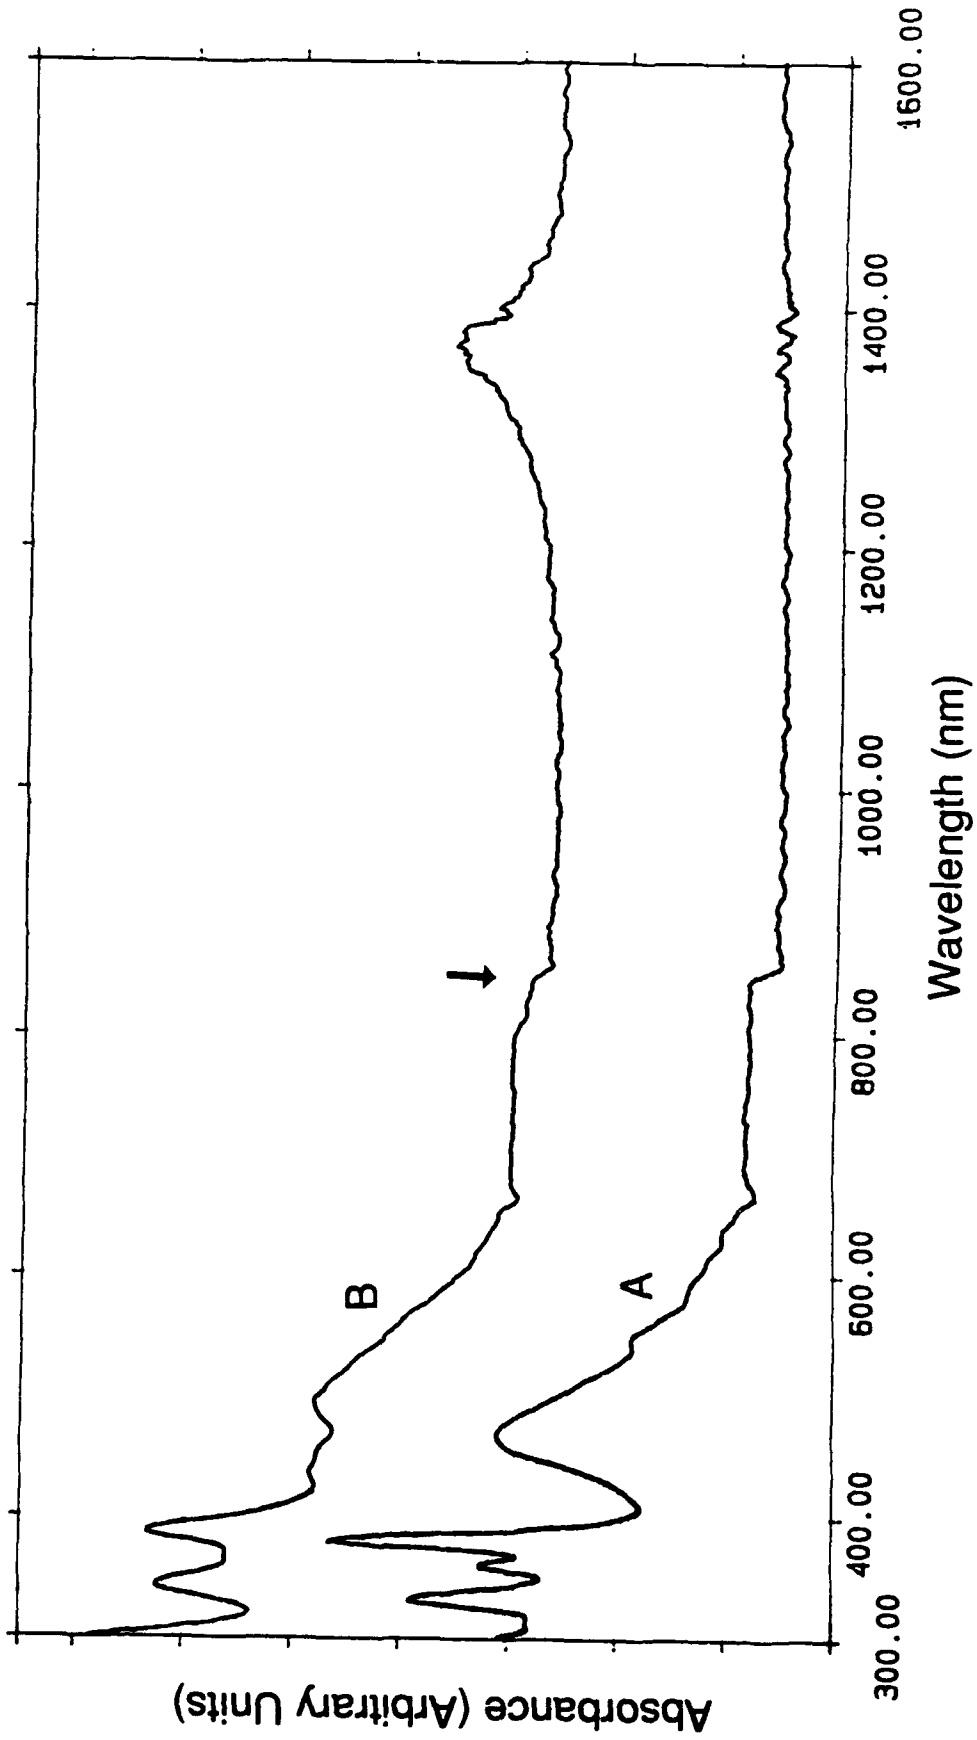


Figure Captions

- Figure 1.** UV-visible-near-IR absorption spectra for (A) C_{70} and (B) C_{70}^{1-} obtained in benzonitrile/0.1M Bu_4NPF_6 . A blank sample of the supporting electrolyte solution was used for background subtraction. The feature at 840 nm, indicated by the arrow, corresponds to an instrument detector change.
- Figure 2.** Visible-near-IR absorption spectra for (A) C_{70}^{2-} , (B) C_{70}^{3-} and (C) C_{70}^{4-} obtained in benzonitrile/0.1M Bu_4NPF_6 . A solution of the supporting electrolyte containing neutral C_{70} was used for background subtraction. The feature at 840 nm, indicated by the arrow, corresponds to an instrument detector change. Note absorbance scale is 0.7 relative to Figure 1.
- Figure 3.** (A) Relevant portion of the molecular orbital diagram of C_{70} .⁶ Proposed molecular orbital diagram for (B) C_{70}^{1-} and (C) C_{70}^{2-} . The transitions in B and C are labeled and assigned to the simulated visible-near-IR spectrum placed above each diagram.