



Cite as  
Nano-Micro Lett.  
(2019) 11:49

Received: 15 April 2019  
Accepted: 14 May 2019  
Published online: 6 June 2019  
© The Author(s) 2019

## Novel Insights into Energy Storage Mechanism of Aqueous Rechargeable Zn/MnO<sub>2</sub> Batteries with Participation of Mn<sup>2+</sup>

Yongfeng Huang<sup>1,2</sup>, Jian Mou<sup>1</sup>, Wenbao Liu<sup>1,2</sup>, Xianli Wang<sup>1</sup>, Liubing Dong<sup>1</sup> ✉, Feiyu Kang<sup>1,2</sup> ✉, Chengjun Xu<sup>1</sup> ✉

Yongfeng Huang and Jian Mou have contributed equally to this work.

✉ Liubing Dong, dong1060@126.com; Feiyu Kang, fykang@mail.tsinghua.edu.cn; Chengjun Xu, vivaxuchengjun@163.com


<sup>1</sup> Shenzhen Geim Graphene Center, Graduate School at Shenzhen, Tsinghua University, Shenzhen 518055, People's Republic of China

<sup>2</sup> State Key Laboratory of New Ceramics and Fine Processing, School of Materials Science and Engineering, Tsinghua University, Beijing 100084, People's Republic of China

### HIGHLIGHTS

- Pourbaix diagram of Mn–Zn–H<sub>2</sub>O system was used to analyze the charge–discharge processes of Zn/MnO<sub>2</sub> batteries.
- Electrochemical reactions with the participation of various ions inside Zn/MnO<sub>2</sub> batteries were revealed.
- A detailed explanation of phase evolution inside Zn/MnO<sub>2</sub> batteries was provided.

**ABSTRACT** Aqueous rechargeable Zn/MnO<sub>2</sub> zinc-ion batteries (ZIBs) are reviving recently due to their low cost, non-toxicity, and natural abundance. However, their energy storage mechanism remains controversial due to their complicated electrochemical reactions. Meanwhile, to achieve satisfactory cyclic stability and rate performance of the Zn/MnO<sub>2</sub> ZIBs, Mn<sup>2+</sup> is introduced in the electrolyte (e.g., ZnSO<sub>4</sub> solution), which leads to more complicated reactions inside the ZIBs systems. Herein, based on comprehensive analysis methods including electrochemical analysis and Pourbaix diagram, we provide novel insights into the energy storage mechanism of Zn/MnO<sub>2</sub> batteries in the presence of Mn<sup>2+</sup>. A complex series of electrochemical reactions with the co-participation of Zn<sup>2+</sup>, H<sup>+</sup>, Mn<sup>2+</sup>, SO<sub>4</sub><sup>2-</sup>, and OH<sup>-</sup> were revealed. During the first discharge process, co-insertion of Zn<sup>2+</sup> and H<sup>+</sup> promotes the transformation of MnO<sub>2</sub> into Zn<sub>x</sub>MnO<sub>4</sub>, MnOOH, and Mn<sub>2</sub>O<sub>3</sub>, accompanying with increased electrolyte pH and the formation of ZnSO<sub>4</sub>·3Zn(OH)<sub>2</sub>·5H<sub>2</sub>O. During the subsequent charge process, Zn<sub>x</sub>MnO<sub>4</sub>, MnOOH, and Mn<sub>2</sub>O<sub>3</sub> revert to α-MnO<sub>2</sub> with the extraction of Zn<sup>2+</sup> and H<sup>+</sup>, while ZnSO<sub>4</sub>·3Zn(OH)<sub>2</sub>·5H<sub>2</sub>O reacts with Mn<sup>2+</sup> to form ZnMn<sub>3</sub>O<sub>7</sub>·3H<sub>2</sub>O. In the following charge/discharge processes, besides aforementioned electrochemical reactions, Zn<sup>2+</sup> reversibly insert into/extract from α-MnO<sub>2</sub>, Zn<sub>x</sub>MnO<sub>4</sub>, and ZnMn<sub>3</sub>O<sub>7</sub>·3H<sub>2</sub>O hosts; ZnSO<sub>4</sub>·3Zn(OH)<sub>2</sub>·5H<sub>2</sub>O, Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>, and ZnMn<sub>2</sub>O<sub>4</sub> convert mutually with the participation of Mn<sup>2+</sup>. This work is believed to provide theoretical guidance for further research on high-performance ZIBs.

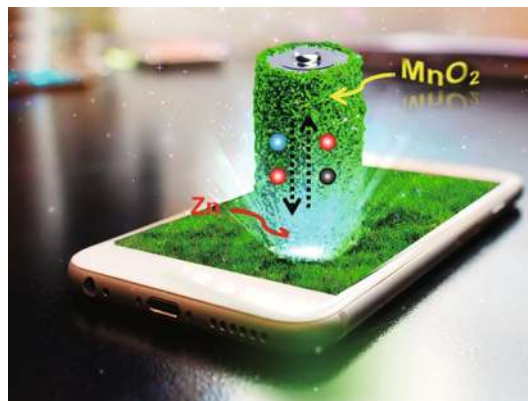

**KEYWORDS** Zinc-ion battery; MnO<sub>2</sub> cathode; Energy storage mechanism; Phase evolution



## 1 Introduction

Lithium-ion batteries (LIBs) have been widely used in consumer electronics due to high energy density, portability, and some other merits [1–4], whereas their security concerns and high cost restrict their large-scale applications in stationary grid storage and electric vehicles [5, 6]. Therefore, much attention has been paid to seek safe, eco-friendly, low-cost, and high-performance battery systems [6, 7]. Aqueous rechargeable zinc-ion batteries (ZIBs) are developed as a battery system, in which low-cost, non-toxic, and naturally abundant zinc metal is used as an anode and environment-friendly neutral aqueous  $\text{Zn}^{2+}$ -containing solution serves as electrolyte [8]. In recent years, a series of high-performance cathode materials for ZIBs have also been studied such as Prussian blue analog [9–11], vanadium oxides [12–19], manganese oxides [20–28], and some metal sulfides [29–31]. Among these materials,  $\text{MnO}_2$  is particularly concerned for its high theoretical specific capacity, low cost, eco-friendliness, and diverse crystallographic polymorphs (e.g.,  $\alpha$ - $\text{MnO}_2$ ,  $\delta$ - $\text{MnO}_2$ , and  $\gamma$ - $\text{MnO}_2$ ) [27, 28, 32].

Many efforts have been made to reveal the energy storage mechanisms of  $\text{Zn}/\text{MnO}_2$  ZIBs. Up to now, three types of energy storage mechanisms were proposed, including (i)  $\text{Zn}^{2+}$  insertion/extraction into/from  $\text{MnO}_2$  [8, 33–36], (ii) conversion between  $\text{MnO}_2$  and  $\text{MnOOH}$  with the participation of  $\text{H}^+$  [37], and (iii) co-insertion of  $\text{H}^+$  and  $\text{Zn}^{2+}$  [38]. Mechanisms (i) and (ii) explain the formation of  $\text{ZnMn}_2\text{O}_4$  and  $\text{MnOOH}$  as discharging products on  $\text{MnO}_2$  cathode in ZIBs, respectively, while cannot explain that there are two redox processes during one charge/discharge cycle of ZIBs. Mechanism (iii) seems to be capable of explaining the coexistence of  $\text{ZnMn}_2\text{O}_4$  and  $\text{MnOOH}$  as discharging products on  $\text{MnO}_2$  cathode, but deeper analysis will find that it is not accurate: The mechanism deems that potential of  $\text{Zn}^{2+}$  insertion is lower than that of  $\text{H}^+$  insertion (this means that  $\text{MnOOH}$  forms before  $\text{ZnMn}_2\text{O}_4$  once the battery discharge process begins), being conflicted to the experimental result that  $\text{MnOOH}$  appears latter than  $\text{ZnMn}_2\text{O}_4$ . In short, the current mechanisms are unsatisfactory to explain genuine charge/discharge process in ZIBs, mainly because they were proposed based on a simplistic view that the insertion of  $\text{Zn}^{2+}$  and  $\text{H}^+$  and the phase change from  $\text{MnO}_2$  to  $\text{ZnMn}_2\text{O}_4$  or  $\text{MnOOH}$  are highly reversible. Furthermore, to achieve

satisfactory cyclic stability and rate performance of the  $\text{Zn}/\text{MnO}_2$  ZIBs,  $\text{Mn}^{2+}$  ions are always introduced in the electrolyte [37]. However, electrochemical reactions inside the ZIBs become more complicated in such cases, thus corresponding energy storage mechanism has not been clearly revealed. Therefore, it is necessary to re-examine the thermodynamic and kinetic characteristics of  $\text{Zn}/\text{MnO}_2$  ZIBs to propose a reasonable  $\text{Zn}^{2+}$  storage mechanism.

In fact, for the active materials in aqueous ZIBs and some other rechargeable aqueous batteries, their structure and phase generally undergo complex changes during charge/discharge processes (e.g., the active materials can interact with not only metal ions, but also  $\text{H}^+$ ,  $\text{OH}^-$ , and water molecules) [39]. This is an important reason why the energy storage mechanism of  $\text{MnO}_2$  cathode in ZIBs is still inconclusive [40–43]. Besides general experimental techniques such as cyclic voltammetry (CV) and galvanostatic charge–discharge (GCD) tests, Pourbaix diagram (E–pH diagram) has been widely used to study electrochemical reactions in aqueous solution [44–47]. The electrochemical reductive products of active materials can be predicted according to the thermodynamics, which is beneficial for us to understand the charge/discharge process. Therefore, we combined experimental methods with the E–pH diagram of the  $\text{Mn}$ – $\text{Zn}$ – $\text{H}_2\text{O}$  system together to comprehensively analyze the charge/discharge processes of  $\text{MnO}_2$  cathode in ZIBs and tried to reveal the authentic energy storage mechanism.

Herein, based on comprehensive analysis methods including electrochemical analysis and E–pH diagram, etc., we provide novel insights into the energy storage mechanism of  $\text{Zn}/\text{MnO}_2$  batteries with the co-participation of  $\text{Zn}^{2+}$ ,  $\text{H}^+$ ,  $\text{Mn}^{2+}$ ,  $\text{SO}_4^{2-}$ , and  $\text{OH}^-$ . During the first discharge process, co-insertion of  $\text{Zn}^{2+}$  and  $\text{H}^+$  promotes the transformation of  $\text{MnO}_2$  into  $\text{Zn}_x\text{MnO}_4$ ,  $\text{MnOOH}$ , and  $\text{Mn}_2\text{O}_3$ , accompanying with increased electrolyte pH and the formation of  $\text{ZnSO}_4 \cdot 3\text{Zn}(\text{OH})_2 \cdot 5\text{H}_2\text{O}$  (noted as “BZSP”). During the subsequent charge process,  $\text{Zn}_x\text{MnO}_4$ ,  $\text{MnOOH}$ , and  $\text{Mn}_2\text{O}_3$  revert to  $\alpha$ - $\text{MnO}_2$  with the extraction of  $\text{Zn}^{2+}$  and  $\text{H}^+$ , while BZSP reacts with  $\text{Mn}^{2+}$  to form  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$ . In the following charge/discharge processes, besides aforementioned electrochemical reactions,  $\text{Zn}^{2+}$  reversibly inserts into/extract from  $\alpha$ - $\text{MnO}_2$ ,  $\text{Zn}_x\text{MnO}_4$ , and  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  hosts, and BZSP,  $\text{Zn}_2\text{Mn}_3\text{O}_8$ , and  $\text{ZnMn}_2\text{O}_4$  convert mutually with the participation of  $\text{Mn}^{2+}$ . This work is believed to provide theoretical guidance for further research on high-performance ZIBs.

## 2 Experimental

### 2.1 Material Synthesis

MnO<sub>2</sub> cathode material was synthesized through a chemical co-precipitation method. One hundred and fifty milliliters of 0.1 M MnSO<sub>4</sub> aqueous solution was dropped into 100 mL of KMnO<sub>4</sub> (0.1 M) solution under magnetic stirring, followed by continuous stirring for 6 h at room temperature. The resulting precipitate was filtered, washed repeatedly with deionized water, and dried at 80 °C for 12 h. The obtained sample was thoroughly ground in an agate mortar and then annealed at 400 °C for 5 h in air atmosphere. Note that we applied the heat treatment to improve the crystalline of MnO<sub>2</sub> because this makes it easier for us to use X-ray diffraction (XRD) and transmission electron microscopy (TEM) to detect the phase evolution of MnO<sub>2</sub> cathode during charge/discharge processes.

### 2.2 Electrochemical Characterizations

The cathode was prepared by coating a mixture paste of 70 wt% of MnO<sub>2</sub> powder, 20 wt% of acetylene black, and 10 wt% of LA133 binder on a stainless steel foil and dried overnight under vacuum conditions at 80 °C. In the prepared cathode, the mass loading of MnO<sub>2</sub> is around 1 mg cm<sup>-2</sup>. Zn/MnO<sub>2</sub> ZIBs were assembled based on MnO<sub>2</sub> cathode, metallic Zn foil anode, air-laid paper separator, and zinc salt solution electrolyte (2 M ZnSO<sub>4</sub> or 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> solution).

The assembled ZIBs were kept more than 4 h before electrochemical measurements. The CV and GCD tests were performed on a Bio-logic VMP3 multichannel electrochemical station and a Land CT2001 battery tester, respectively. CV tests of the prepared MnO<sub>2</sub> cathode were also carried out in a three-electrode system, in which a platinum plate as the counter electrode, a saturated calomel electrode (SCE) as the reference electrode, and 50 mL electrolyte was applied.

### 2.3 Material Characterizations

Microstructure and composition were characterized by XRD (Rigaku 2500) with Cu-K $\alpha$  radiation operating

at 40 kV and 100 mA within an angle range of 10° to 70° at a scan speed of 5° min<sup>-1</sup>. Micro-morphology was observed by field emission scanning electron microscopy (SEM, Zeiss Supra 55) and TEM (Tecnai G2 F30). Element content in electrodes and electrolytes was analyzed by inductively coupled plasma atomic emission spectrometry (ICP-AES).

## 3 Results and Discussion


### 3.1 Characterization of MnO<sub>2</sub>

The MnO<sub>2</sub> material used in this work was synthesized through a chemical co-precipitation method. XRD pattern and micro-morphology observations in Fig. 1a–c show that the synthesized MnO<sub>2</sub> powder is crystalline  $\alpha$ -MnO<sub>2</sub> nanorod with a diameter of 10–60 nm and length of several hundred nanometers. From the XRD pattern in Fig. 1a, it seems that the strongest peak is the one at ~12.8°, but if the background is taken into account, the strongest peak is still the one at ~37.5°, which matches well with the  $\alpha$ -MnO<sub>2</sub> (PDF# 44-0141). In addition, since the as-prepared sample is nanobelts, (110) plane (corresponding to the diffraction peak at ~12.8°) is considered as preferred orientation, thus leading to high diffraction intensity. A similar phenomenon was also observed for some other MnO<sub>2</sub> nanomaterials [38]. From the high-resolution TEM (HRTEM) image in Fig. 1d, the crystal planes (121) and (330) of the  $\alpha$ -MnO<sub>2</sub> with a corresponding interplanar spacing of 0.238 nm and 0.233 nm respectively are observed, and high crystallinity of the as-synthesized  $\alpha$ -MnO<sub>2</sub> sample is also confirmed.

### 3.2 Electrochemical Analysis

We first studied the electrochemical behaviors of MnO<sub>2</sub> cathode in two different electrolytes, including 50 mL 2 M ZnSO<sub>4</sub> (Fig. 2a) and 50 mL 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> mixture solution (Fig. 2b–d). The capacity and rate performance of the MnO<sub>2</sub> cathode in ZnSO<sub>4</sub> + MnSO<sub>4</sub> electrolyte are exhibited in Fig. S1. Note that MnO<sub>2</sub> cathode would dissolve in ZnSO<sub>4</sub> electrolyte during charge/discharge processes, as detected by ICP-AES tests in Table S1. (This has also been pointed out in previous researches.) [37] With the addition of Mn<sup>2+</sup> in the electrolyte, the redox peaks in CV curves (except for the 1st CV cycle) in Fig. 2a, b become



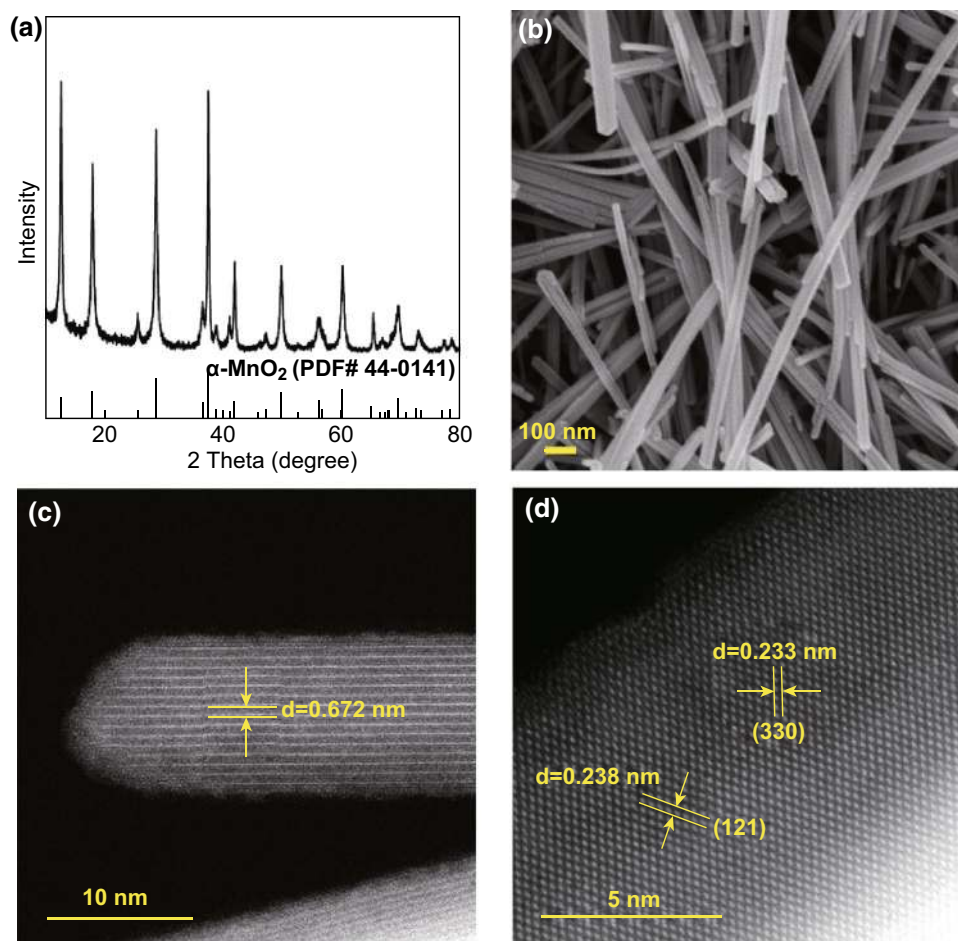


**Fig. 1** **a** XRD pattern, **b** SEM image, **c** STEM, and **d** HRSTEM images of the synthesized MnO<sub>2</sub> nanorods

more obvious, and meanwhile, the gap between oxidation peak and reduction peak becomes smaller, which indicates that the reversibility of electrochemical process gets better. In Fig. 2a, the reduction peak is much stronger than the oxidation peak in the first cycle, which means that discharge products cannot be electrochemically oxidized completely. By contrast, the intensity of the reduction peak is close to that of the oxidation peak in Fig. 2b. Above phenomenon suggests that Mn<sup>2+</sup> concentration in electrolyte plays a crucial role in the first discharge/charge process [48]. There are two pairs of redox peaks when the electrode discharges/charges in the 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte (Fig. 2b). The reduction peaks at low and high potentials are denoted as R<sub>1</sub> and R<sub>2</sub>, respectively, and the oxidation peaks at low and high potentials are denoted as O<sub>1</sub> and O<sub>2</sub>, respectively. Considering that electro-deposition of Mn<sup>2+</sup> will occur only when the cathode potential reaches about

0.8 V versus SCE at the constant current of 0.1 A cm<sup>-2</sup> (Fig. S2), the oxidation reactions of O<sub>1</sub> and O<sub>2</sub> ranging from 0.5 to 0.65 V versus SCE (Fig. 2b) are not caused by the electro-deposition of Mn<sup>2+</sup>. This confirms that the preclusion of MnO<sub>2</sub> dissolution by Mn<sup>2+</sup> in the electrolyte should be the dominant reason for good reversibility of discharge/charge processes in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte.

There is a dip and a platform in the initial GCD curve (Fig. 2c) and the reaction type of R<sub>1</sub> (at about 1.2 V) and R<sub>2</sub> (at about 1.4 V) are further studied by the constant voltage discharge test (Fig. 2d). The current changes greatly when the battery is discharged at 1.2 V at which R<sub>1</sub> will happen, and it keeps almost flat when discharged at 1.4 V at which R<sub>2</sub> will occur. This indicates that a heterogeneous reaction occurs during R<sub>1</sub> and a homogeneous reaction occurs during R<sub>2</sub>. Such a heterogeneous reaction between solid phases accompanying with nucleation process and

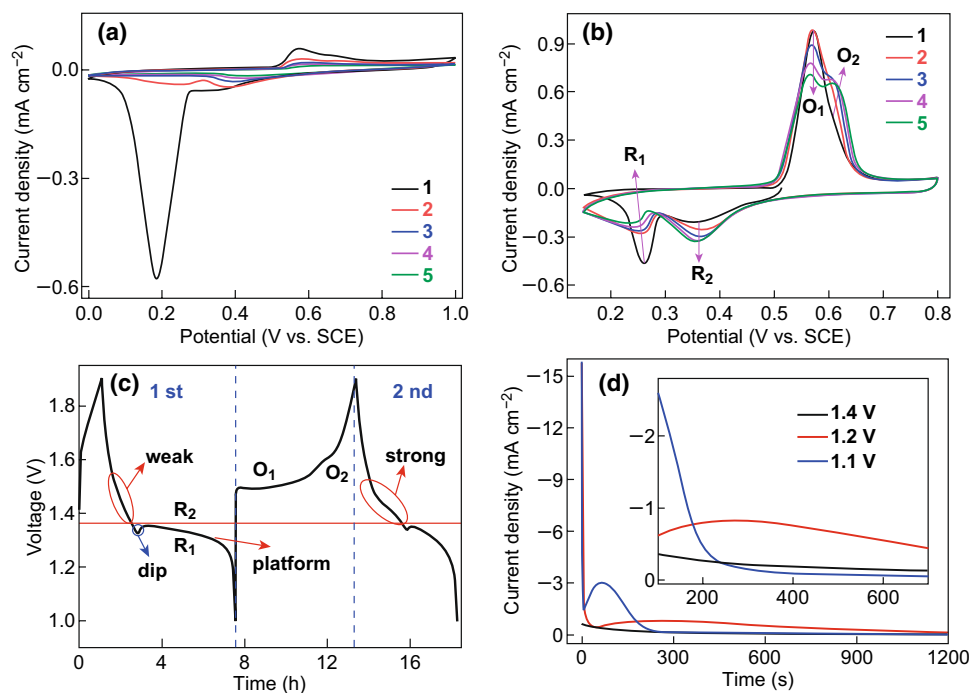

**Fig. 2** Electrochemical behaviors of the prepared cathodes: **a** CV curves in 50 mL 2 M ZnSO<sub>4</sub> solution (first to fifth cycles); **b** CV (first to fifth cycles) and **c** GCD curves in 50 mL 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> solution; **d** constant voltage discharge at various voltages (1.4, 1.2, and 1.1 V) and local magnification diagram (the inset)


electro-crystallization process will cause the formation of the dip and steep curve in the discharge curve in Fig. 2c [49]. With the increasing CV cycles (Fig. 2b), the peak current intensity of R<sub>1</sub> and O<sub>1</sub> is getting weaker, while the peak current intensity of R<sub>2</sub> and O<sub>2</sub> becomes stronger. Therefore, the redox reactions R<sub>1</sub>/O<sub>1</sub> and R<sub>2</sub>/O<sub>2</sub> are more likely to be independent of each other. That the initial process differs from the subsequent one can also be seen from Fig. 2c (the red circle). R<sub>2</sub> is weaker in the initial discharge process than that in the second one, which indicates that a new phase may generate as active materials.

### 3.3 Phase Evolution of Cathode in the Initial Discharge Process

ex situ XRD tests of the cathodes at different charge/discharge states support were performed. As shown in Fig. S3, when the cathode is initially discharged from 1.9 to 1.4 V, no new phase produces, while the cathode is further discharged to 1.0 V, several new diffraction peaks occur, indicating the appearance of new phases. In the charging process, some diffraction peaks cannot be detected,


which means the disappearance of some phases. After 100 charges/discharge cycles, the XRD pattern is not in conformity with the XRD patterns of the cathode at the original state and fully charged state in the 1st charge process. These demonstrate that the cathode undergoes a complicated phase evolution. In the following, phase evolution of MnO<sub>2</sub> cathodes during the 1st discharge process, the 1st charge process and subsequent discharge/charge processes were investigated in detail.

To investigate phases evolution of cathode in the initial discharge process in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte, R<sub>1</sub> and R<sub>2</sub> reactions (as defined in Fig. 2, the same hereinafter) are separately studied. Only R<sub>2</sub> occurs when the voltage of the battery is above 1.4 V. No new phase produces are seen from the XRD pattern (Fig. 3a). Nevertheless, characteristic peaks of the MnO<sub>2</sub> active material such as the peaks at 28° and 38° shift (inset of Fig. 3a), which is attributed to the change of the layer spacing of MnO<sub>2</sub>. This means that the active material undergoes structure change. The nanorods become shorter (Fig. 3b) which is greatly different from that of the as-prepared material (Fig. 1b). Energy dispersive spectrometer (EDS)

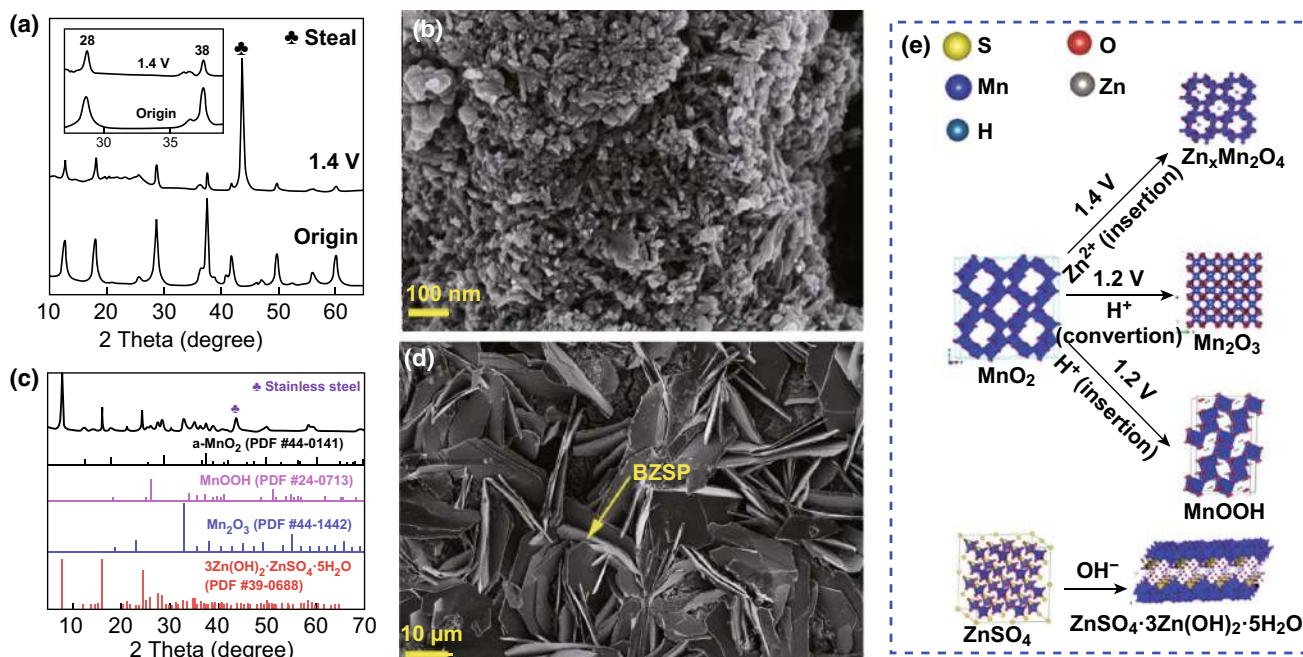



**Fig. 3** The results of the cathode which is constant current discharged to 1.4 V and then constant voltage discharged at 1.4 V in 2 M  $\text{ZnSO}_4 + 0.5 \text{ M MnSO}_4$  electrolyte for 2 h: **a** XRD pattern and locally enlarged image (the inset); **b** SEM image of the surface of the cathode. Another cathode which is constant current discharged to 1.0 V: **c** XRD pattern; **d** SEM image of the surface of the cathode; **e** phase evolution of cathode during the first discharge process

analysis in Fig. S4 suggests that the molar ratio of Zn, Mn, and S is approximately 1:16:0. To exclude the influence of electrolyte's absorption, we immersed the electrodes in 2 M  $\text{ZnSO}_4$  for 48 h and washed several times with deionized water. Neither Zn nor S element is found in the SEM-EDS result (Fig. S5). Thus, the existence of Zn in the cathode when discharging to 1.4 V is caused by the insertion of zinc ions in  $\text{MnO}_2$ , instead of zinc ion adsorption on the cathode surface. In other words, zinc ion insertion happens when the voltage of the Zn/ $\text{MnO}_2$  battery is above 1.4 V. The process of zinc-ion insertion in  $\text{MnO}_2$  can be written as:




$R_1$  reaction is then studied. When the battery is discharged to 1.2 V and then to the 1 V at constant current several new phases (XRD patterns in Fig. 3c) appear, which are confirmed as BZSP (PDF#39-0688),  $\alpha\text{-MnOOH}$  (PDF#24-0713), and  $\alpha\text{-Mn}_2\text{O}_3$  (PDF#44-1442). There are many large hexagonal nanosheets in the SEM image (Fig. 3d). The Zn, O, and S element distribute evenly over the whole hexagonal nanosheets (Fig. S6b, c, e, f). And the atomic proportion of Zn to S is about 4:1 from the SEM-EDS results (Fig. S6d). Combined with the XRD result, we conclude that the

hexagonal nanosheets are BZSP. The structure evolution of cathode in the first discharge is shown in Fig. 3e. The existence of  $\alpha\text{-MnOOH}$  and  $\alpha\text{-Mn}_2\text{O}_3$  is further demonstrated by HRTEM (Fig. 4). The  $\alpha\text{-Mn}_2\text{O}_3$  is semi-coherent with the  $\alpha\text{-MnOOH}$  phase (Fig. 4c). These substances and their reactions can be written as [21, 28, 37]:



Phases in regions e, f, g, and h in Fig. 4c, d marked by yellow dash can be identified as  $\alpha\text{-MnOOH}$ ,  $\alpha\text{-Mn}_2\text{O}_3$ ,  $\alpha\text{-Mn}_2\text{O}_3$ , and  $\alpha\text{-Zn}_x\text{MnO}_2$ , respectively, through fast Fourier transform (FFT) in Fig. 4e–h (detailed calculation procedures are given in Table S2–S4). From the TEM-EDS result, the Zn element can be found in both regions A and B and there is no S element in these regions (Fig. 4b), further confirming that zinc-ion inserts into the nanorods. Besides, the generation of BZSP and  $\alpha\text{-MnOOH}$  indicates that  $\text{H}^+$  and  $\text{Zn}^{2+}$  participate in the reaction. From the above discussions, zinc ion insertion in  $\alpha\text{-MnO}_2$  occurs around 1.4 V versus  $\text{Zn}^{2+}/\text{Zn}$  to generate  $\alpha\text{-Zn}_x\text{MnO}_2$ , and proton conversion reaction

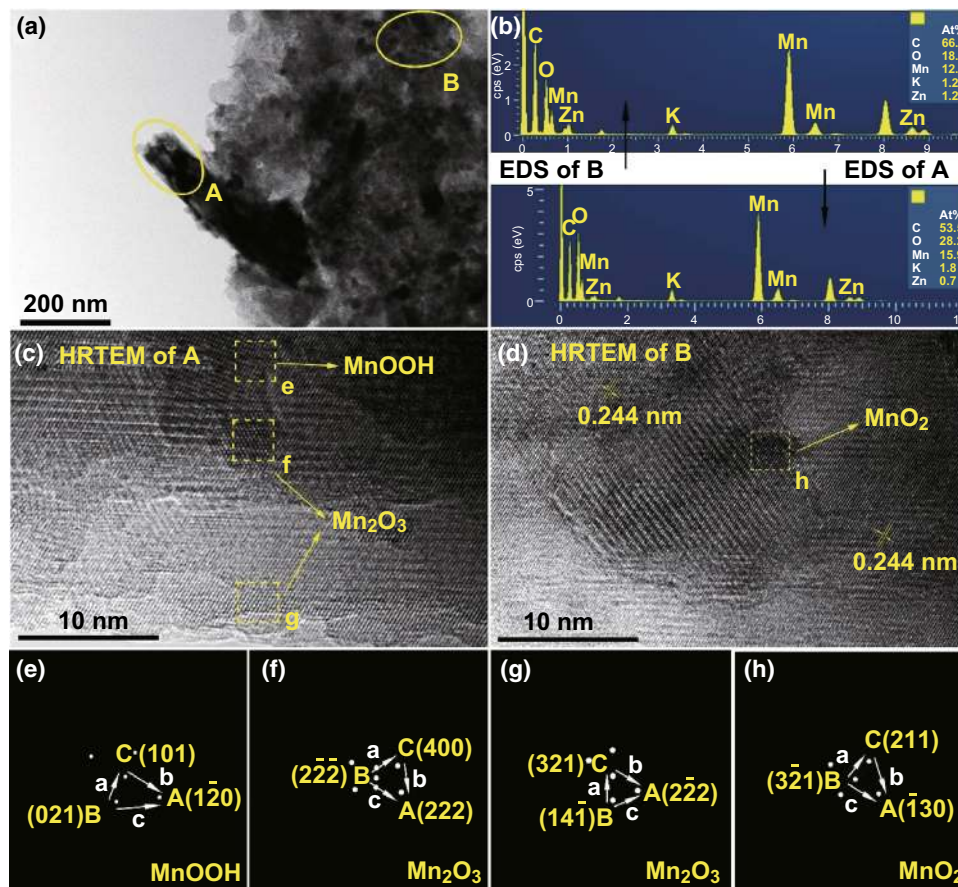


**Fig. 4** TEM, HRTEM image, and TEM-EDS spectrum of the sample constant current discharge to 1.0 V: **a** TEM image **b** TEM-EDS spectrum result of region A and B marked in **a**. **c**, **d** HRTEM image of region A and B marked in Fig. 4a, respectively. **e**, **f** FFT of the region marked by a yellow dash in **c** and **d**, respectively

happens between 1.0 and 1.3 V in the cathode and leads to the generation of MnOOH, Mn<sub>2</sub>O<sub>3</sub>, and BZSP.

### 3.4 Phase Evolution of Cathode in the First Charge Process


To detect the phase evolution of MnO<sub>2</sub> cathode during the charge process, the battery is discharged to 1.0 V and then charged to 1.9 V in 2 M ZnSO<sub>4</sub> and 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte, respectively. The discharging products of Mn<sub>2</sub>O<sub>3</sub>, BZSP, and MnO<sub>2</sub> still exist on the charged cathode, and besides, new phase ZnMn<sub>3</sub>O<sub>7</sub>·3H<sub>2</sub>O generates (Fig. 5a). It is worth noting that when adding Mn<sup>2+</sup> in the electrolyte, the diffraction peaks of ZnMn<sub>3</sub>O<sub>7</sub>·3H<sub>2</sub>O become strong while the diffraction peaks of BZSP become weak (Fig. 5a). The morphology of cathode changes greatly (from hexagonal nanosheets to ball-like nanoflowers) during the

initial charging process as shown in Figs. S7a–f and S8a–d. Figure S7a–f shows that BZSP exists in the 2 M ZnSO<sub>4</sub> solution while almost disappears in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> solution during the charging process. It means that added Mn<sup>2+</sup> in the electrolyte can promote the dissolution of BZSP. To confirm this, the fresh cathode was discharged to 1.0 V in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> solution and then soaked in potassium hydrogen phthalate solution (pH = 4.0) for 72 h to completely dissolve BZSP. The electrode without BZSP was then charged in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte. Meanwhile, the discharged electrode with BZSP was separately charged in the electrolytes of 2 M ZnSO<sub>4</sub> and 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub>. The charge processes of the three conditions are shown in Fig. 5b. It can be seen that the platform, which means heterogeneous reaction happens, occurs at 1.5 V only when BZSP and Mn<sup>2+</sup> both exist. To further confirm this, a discharged electrode with

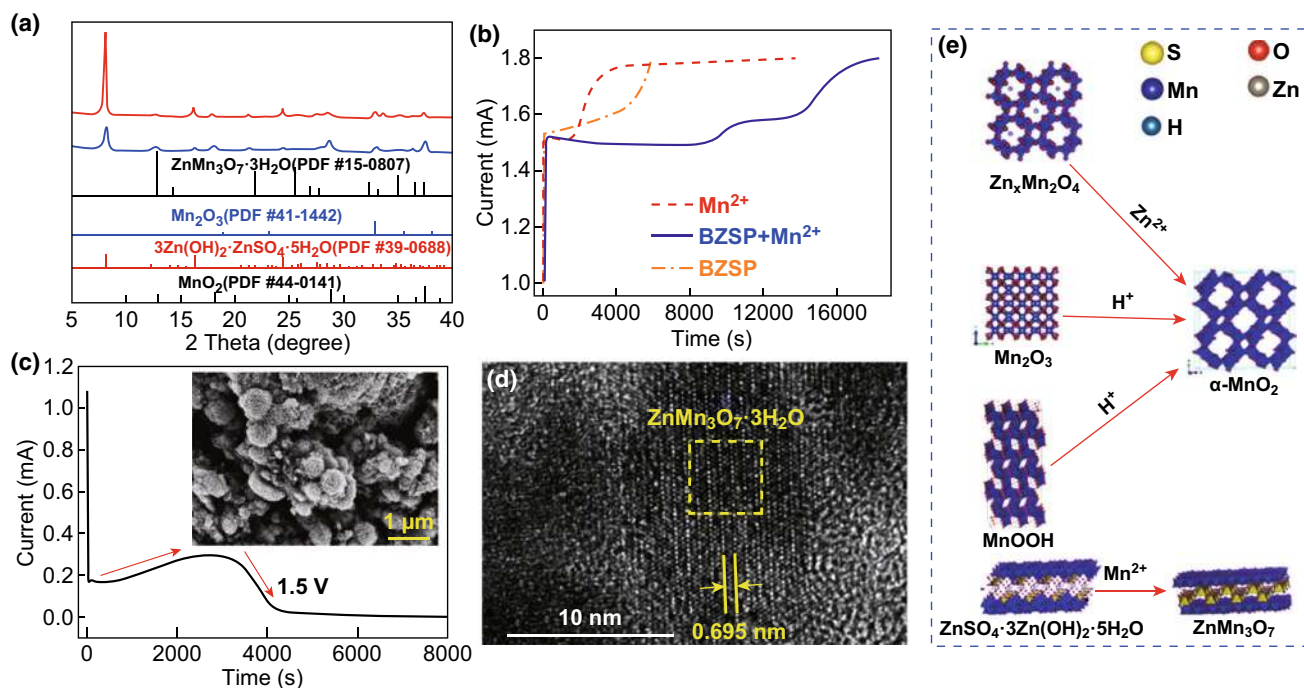

**Fig. 5** The first charge process: **a** XRD pattern of the fully charged cathode in the first charge process; **b** charging curves of  $\alpha$ - $\text{MnO}_2$  electrodes after discharge to 1 V in different cases; **c** constant voltage test; **d** HRTEM image and analysis result. **e** Phase evolution of cathode during the first charge process

BZSP charge at 1.5 V in the 2 M  $\text{ZnSO}_4$  + 0.5 M  $\text{MnSO}_4$  solution. The nanoflower-like product generates (inset in Fig. 5c) as expected.  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  is also found in HRTEM in Fig. 5d. Combining with the result of XRD, the nanoflower is  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$ . The dissolution of BZSP (nanosheets in Fig. S8a–d) and the occurrence of the new phase (nanoflowers in Fig. S8a–b)  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  indicate that  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  generate from the conversion reaction between BZSP and  $\text{Mn}^{2+}$ . The nanoflower is  $\text{Zn}(\text{OH})_2$  and  $\text{MnO}_2$  alternately layered structure as seen from Fig. S9. The conversion reactions are as follows:  $\text{Zn}^{2+}$  in the interlayer of  $\text{Zn}(\text{OH})_2$  (Fig. S10) exchanges with  $\text{Mn}^{2+}$  and then the  $\text{Mn}^{2+}$  is chemically oxidized during the charging process. With continuous oxidation of  $\text{Mn}^{2+}$ , the  $\text{Mn}^{2+}$  reacts with  $\text{H}_2\text{O}$  to generate  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  (Fig. S10). The structure evolution of cathode in the first charge is shown in Fig. 5e. In other words, besides  $\text{H}^+$  and  $\text{Zn}^{2+}$ ,  $\text{Mn}^{2+}$  also participates in the reactions that occur during the discharge/charge process as the conversion reactions are supposed as follows:

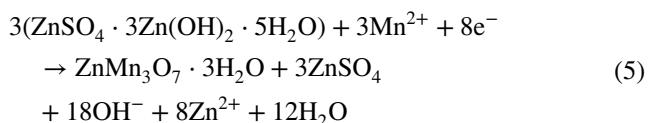


The generation of  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  during the first charge process can explain the phenomenon that the second discharge curve of the battery is different from the first discharge curve. In a word, during the first charging process,  $\text{Zn}_x\text{Mn}_2\text{O}_4$  and  $\text{MnOOH}$  reversibly become  $\alpha$ - $\text{MnO}_2$  with the extraction of  $\text{Zn}^{2+}$  and  $\text{H}^+$ , while  $\text{ZnMn}_3\text{O}_7 \cdot 3\text{H}_2\text{O}$  acts as the host for the insertion of  $\text{Zn}^{2+}$  forms through the reaction between  $\text{Mn}^{2+}$  and BZSP.

### 3.5 Phase Evolution of Cathode in Subsequent Discharge/Charge Processes



The phases of the battery system after 100 charges/discharge cycles are also studied. XRD patterns of the discharged cathode after 100 cycles in 2 M  $\text{ZnSO}_4$  + 0.5 M  $\text{MnSO}_4$  solution in Fig. 6a imply that the main phases of the system are  $\text{ZnMn}_2\text{O}_4$  (PDF#24-1133),  $\text{Zn}_2\text{Mn}_3\text{O}_8$  (PDF#32-1472),  $\text{Mn}_2\text{O}_3$ , BZSP, and  $\alpha$ - $\text{MnO}_2$ . These components are confirmed in HRTEM images in Fig. 6b–d. As a contrast, the battery in the 2 M  $\text{ZnSO}_4$  solution, the main phases of the system are  $\text{ZnMn}_2\text{O}_4$ ,  $\text{ZnMn}_3\text{O}_7$ ,  $\text{Mn}_2\text{O}_3$ , and BZSP (Fig. S11a, b).  $\text{ZnMn}_2\text{O}_4$  is on the surface of the  $\alpha$ - $\text{MnO}_2$  in HRTEM (Fig. 6b), so it may be



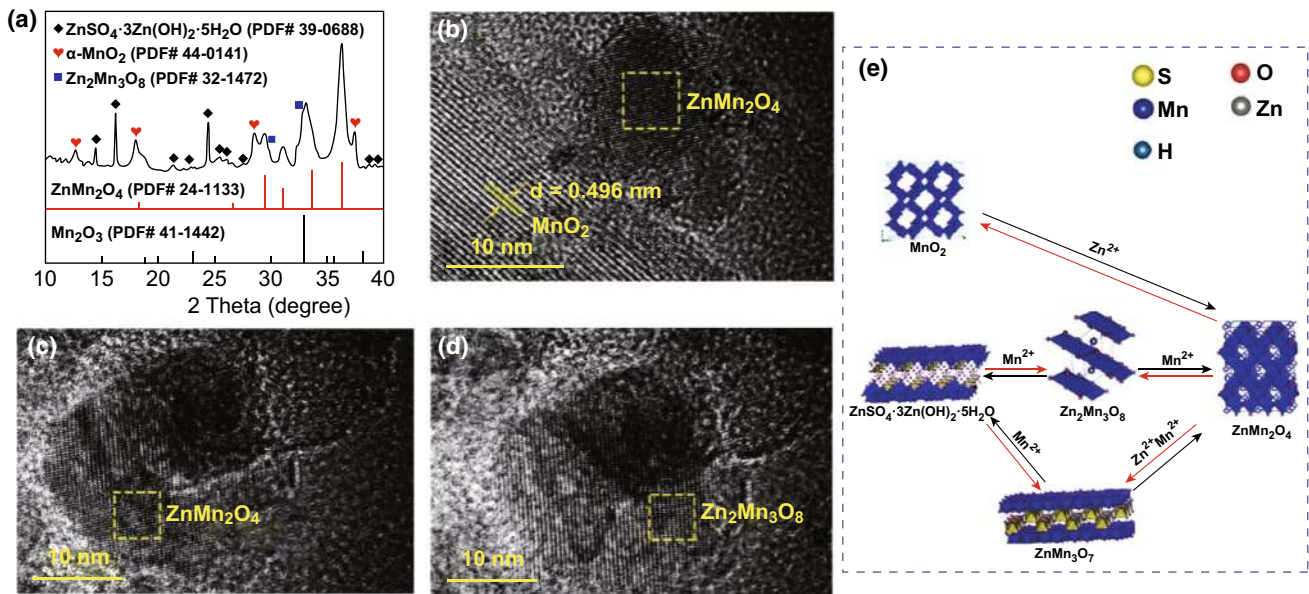

**Fig. 6** The MnO<sub>2</sub> cathode after 100 charge/discharge cycles in 2 M ZnSO<sub>4</sub> + 0.5 M MnSO<sub>4</sub> electrolyte: **a** XRD patterns; **b–d** HRTEM images; **e** phase evolution of cathode during the repeated charge/discharge processes after the first charge/discharge cycle

converted from  $\alpha$ -MnO<sub>2</sub>. Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> and ZnMn<sub>2</sub>O<sub>4</sub> are coherent in the HRTEM (Fig. 6c, d). Thus, Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> reacts with Mn<sup>2+</sup> to form ZnMn<sub>2</sub>O<sub>4</sub>. (This will be further analyzed in the Mn–Zn–O diagram in the following part.) There are two kinds of nanoparticles after 100 cycles (Fig. S12), which may be converted from BZSP and Mn<sup>2+</sup> as nanosheets and nanoparticles surround each other. Combining the XRD result (Fig. 6a), the phase is Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>. Thus, Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> is generated from the reactions between BZSP and Mn<sup>2+</sup>. The structure evolution of cathode after 100 cycles is shown in Fig. 6e. Reactions between them are as follows:




To sum up, within the continuous charge/discharge process, ZnMn<sub>2</sub>O<sub>4</sub> and Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> as host for insertion of Zn<sup>2+</sup> further generate on the surface of MnO<sub>2</sub>, which implies that the phase change of MnO<sub>2</sub> cathode is irreversible.

### 3.6 Thermodynamic Analysis

When dynamic conditions are met, the phases can be predicted from Zn–Mn–O diagram since the system of the Zn/ZnSO<sub>4</sub> + MnSO<sub>4</sub>/MnO<sub>2</sub> battery reaches an equilibrium state

after a certain cycle. The isothermal cross section of the phase diagram (25 °C) is shown in Fig. 7a. Since MnO<sub>2</sub> is used as an active material and ZnSO<sub>4</sub> + MnSO<sub>4</sub> as the electrolyte for the beginning, the phase of the reaction is bound to three elements (Mn, O, and Zn). When the thermodynamic stability of the system reaches, the definite phases include manganese oxide (MnO<sub>2</sub>, Mn<sub>2</sub>O<sub>3</sub>, Mn<sub>3</sub>O<sub>4</sub>, and MnO) and zinc manganese oxide (ZnMn<sub>2</sub>O<sub>4</sub> and Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>) (Fig. 7a). Detailed density functional theory calculation and theoretical analysis of MnO<sub>2</sub> as a cathode of ZIBs are given in Discussion S1 and S2 in Supporting Information). There are two paths to the reduction of MnO<sub>2</sub>: (i) MnO<sub>2</sub> → Mn<sub>2</sub>O<sub>3</sub> → Mn<sub>3</sub>O<sub>4</sub> → MnO, in which path there is no Zn involvement; (ii) MnO<sub>2</sub> → ZnMn<sub>2</sub>O<sub>4</sub> with Zn involvement. For Mn<sub>2</sub>O<sub>3</sub> oxidation, it is directly oxidized to MnO<sub>2</sub>: Mn<sub>2</sub>O<sub>3</sub> → MnO<sub>2</sub>. The oxidation of ZnMn<sub>2</sub>O<sub>4</sub> has two paths: Zn extracts out completely from ZnMn<sub>2</sub>O<sub>4</sub> to generate MnO<sub>2</sub> or Mn partially removes from ZnMn<sub>2</sub>O<sub>4</sub> to generate Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>. They can express as: (1) ZnMn<sub>2</sub>O<sub>4</sub> → MnO<sub>2</sub>; (2) ZnMn<sub>2</sub>O<sub>4</sub> → Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>. And there's only one way for the Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> reduction: Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> → ZnMn<sub>2</sub>O<sub>4</sub>. In the Zn/ZnSO<sub>4</sub> + MnSO<sub>4</sub>/α-MnO<sub>2</sub> system studied in this paper, MnO dissolves in the electrolyte or can be inhibited when there is a certain concentration of Mn<sup>2+</sup>. Thus, there are five kinds of phases that may exist, such as MnO<sub>2</sub>, Mn<sub>2</sub>O<sub>3</sub>, Mn<sub>3</sub>O<sub>4</sub>, ZnMn<sub>2</sub>O<sub>4</sub>, and Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub>. When taking PH and potentials into consideration, MnO<sub>2</sub>, Mn<sub>2</sub>O<sub>3</sub>, ZnMn<sub>2</sub>O<sub>4</sub>, MnOOH,

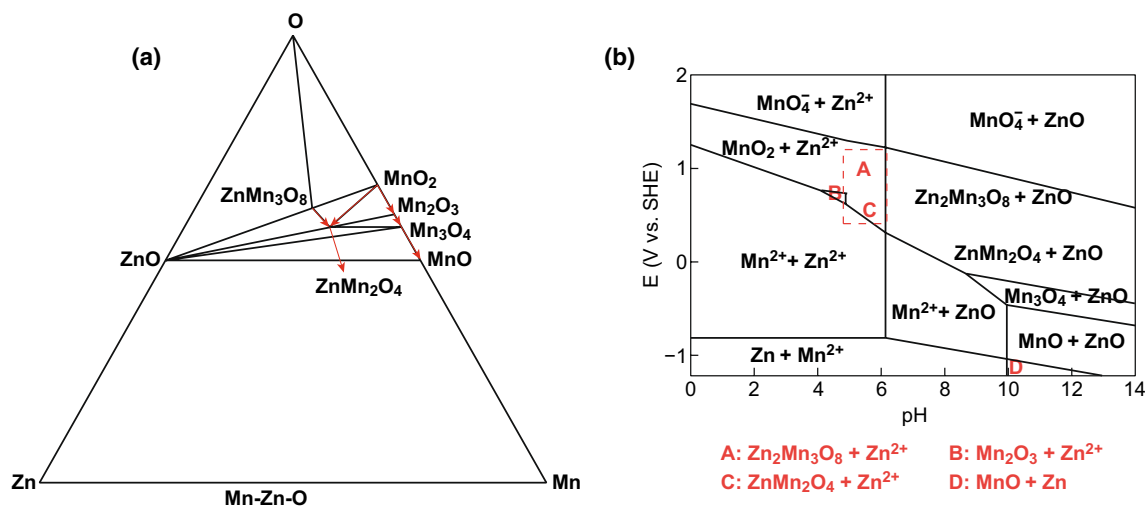

**Fig. 7** a Zn–Mn–O diagram and b E–pH diagram of Zn–Mn–H<sub>2</sub>O system

and Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> can form in our system but MnOOH is not stable, which matches well with our work (the red region in Fig. 7b). The reaction route is concluded to be as follows: (1) MnO<sub>2</sub> → Mn<sub>2</sub>O<sub>3</sub>, (2) MnO<sub>2</sub> → ZnMn<sub>2</sub>O<sub>4</sub> and (3) Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> → ZnMn<sub>2</sub>O<sub>4</sub> (Fig. 7a). MnO<sub>2</sub>, Mn<sub>2</sub>O<sub>3</sub>, ZnMn<sub>2</sub>O<sub>4</sub>, and Zn<sub>2</sub>Mn<sub>3</sub>O<sub>8</sub> are stable phases and all can store Zn<sup>2+</sup> (Fig. 7b).

Overall, we combined electrochemical analysis, phase identification with E–pH diagram of the Mn–Zn–H<sub>2</sub>O system together to analyze charge/discharge processes of aqueous rechargeable Zn//MnO<sub>2</sub> batteries and revealed complicated phase evolution of the cathode (i.e., what new phases will form and how can they form in different charge/discharge stages). We obtained some different conclusions from previous literature. For example, Sun et al. thought that the conversion of H<sup>+</sup> occurs before Zn<sup>2+</sup> insertion [38]. But we find that Zn<sup>2+</sup> insertion occurs before the conversion of H<sup>+</sup> in the first discharge process, and this is confirmed by thermodynamic analysis. Besides, previous literature deemed that the disappearance of BZSP is always caused by the change in electrolyte pH [34], but we find that BZSP can react with Mn<sup>2+</sup> in the electrolyte to form a new phase of ZnMn<sub>3</sub>O<sub>7</sub>.

## 4 Conclusions

Based on experimental results and theoretical analysis of Zn//MnO<sub>2</sub> ZIBs with the mixture electrolyte of ZnSO<sub>4</sub> + MnSO<sub>4</sub> aqueous solution, we found that the mechanism in ZIBs is

dynamic and the phase transformation at MnO<sub>2</sub> cathode is irreversible during charge/discharge processes. Not only H<sup>+</sup> and Zn<sup>2+</sup> but also Mn<sup>2+</sup> in the electrolyte take part in the reactions. In the first discharge process, Zn<sub>x</sub>MnO<sub>2</sub>, MnOOH, Mn<sub>2</sub>O<sub>3</sub>, and by-product BZSP generate, and then in the first charge process, α-MnO<sub>2</sub> and ZnMn<sub>3</sub>O<sub>7</sub>·3H<sub>2</sub>O appear. In the following charge/discharge processes, ZnMn<sub>2</sub>O<sub>4</sub> and ZnMn<sub>3</sub>O<sub>8</sub> are further generated on the surface of MnO<sub>2</sub> and serve as the hosts for Zn<sup>2+</sup> insertion. The mechanism becomes dynamic and complex because of the co-participation of the insertion process, conversion reaction, and oxidation reactions. The aforementioned phase changes inside ZIBs are well explained by the Mn–Zn–O phase diagram and the E–pH diagram. This work can provide guidance for continual research from the following aspects. (i) The research method combining electrochemical analysis and phase identification with E–pH diagram together can be used to analyze charge/discharge processes of other electrochemical energy storage systems, such as aqueous rechargeable Zn//V<sub>2</sub>O<sub>5</sub> batteries. (ii) According to the proposed energy storage systems in this work, at least two approaches can be applied to enhance cycling performance of ZIBs: One is adding Mn<sup>2+</sup> to promote the disappearance of BZSP, and the other one is adding pH buffer into the electrolytes or preparing solid electrolytes to prohibit the generation of OH<sup>-</sup> and BZSP.

**Acknowledgements** The authors appreciate the financial support from the International Science & Technology Cooperation Program of China (No. 2016YFE0102200), Shenzhen Technical Plan Project (No. JCYJ20160301154114273), National Key Basic Research

(973) Program of China (No. 2014CB932400), and Local Innovative and Research Teams Project of Guangdong Pearl River Talents Program (2017BT01N111).

**Open Access** This article is distributed under the terms of the Creative Commons Attribution 4.0 International License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made.

**Electronic supplementary material** The online version of this article (<https://doi.org/10.1007/s40820-019-0278-9>) contains supplementary material, which is available to authorized users.

## References

1. T.-H. Kim, J.-S. Park, S.K. Chang, S. Choi, J.H. Ryu, H.-K. Song, The current move of lithium-ion batteries towards the next phase. *Adv. Energy Mater.* **2**, 860–872 (2012). <https://doi.org/10.1002/aenm.201200028>
2. B. Dunn, H. Kamath, J.M. Tarascon, Electrical energy storage for the grid: a battery of choices. *Science* **334**, 928–935 (2011). <https://doi.org/10.1126/science.1212741>
3. H. Sun, J.-G. Wang, Y. Zhang, W. Hua, Y. Li, H. Liu, Ultrafast lithium energy storage enabled by interfacial construction of interlayer-expanded MoS<sub>2</sub>/N-doped carbon nanowires. *J. Mater. Chem. A* **6**, 13419–13427 (2018). <https://doi.org/10.1039/C8TA04852E>
4. J.-G. Wang, H. Liu, R. Zhou, X. Liu, B. Wei, Onion-like nanospheres organized by carbon encapsulated few-layer MoS<sub>2</sub> nanosheets with enhanced lithium storage performance. *J. Power Sources* **413**, 327–333 (2019). <https://doi.org/10.1016/j.jpowsour.2018.12.055>
5. C. Delmas, M. Maccario, L. Croguennec, F. Le Cras, F. Weill, Lithium deintercalation in LiFePO<sub>4</sub> nanoparticles via a domino-cascade model. *Nat. Mater.* **7**, 665–671 (2008). <https://doi.org/10.1038/nmat2230>
6. N. Alias, A.A. Mohamad, Advances of aqueous rechargeable lithium-ion battery: a review. *J. Power Sources* **274**, 237–251 (2015). <https://doi.org/10.1016/j.jpowsour.2014.10.009>
7. J.O.G. Posada, A.J.R. Rennie, S.P. Villar, V.L. Martins, J. Marinaccio et al., Aqueous batteries as grid-scale energy storage solutions. *Renew. Sustain. Energy Rev.* **68**, 1174–1182 (2017). <https://doi.org/10.1016/j.rser.2016.02.024>
8. C. Xu, B. Li, H. Du, F. Kang, Energetic zinc ion chemistry: the rechargeable zinc ion battery. *Angew. Chem. Int. Ed.* **51**, 933–935 (2012). <https://doi.org/10.1002/anie.201106307>
9. L. Zhang, L. Chen, X. Zhou, Z. Liu, Towards high-voltage aqueous metal-ion batteries beyond 1.5 V: the zinc/zinc hexacyanoferrate system. *Adv. Energy Mater.* **5**, 1400930 (2015). <https://doi.org/10.1002/aenm.201400930>
10. R. Trocoli, F. La Mantia, An aqueous zinc-ion battery based on copper hexacyanoferrate. *Chemsuschem* **8**, 481–485 (2015). <https://doi.org/10.1002/cssc.201403143>
11. Z. Liu, G. Pulletikurthi, F. Endres, A prussian blue/zinc secondary battery with a bio-ionic liquid-water mixture as electrolyte. *ACS Appl. Mater. Interfaces* **8**, 12158–12164 (2016). <https://doi.org/10.1021/acsami.6b01592>
12. Y. Wu, Y. Yang, X. Zhao, Y. Tan, Y. Liu, Z. Wang, F. Ran, A novel hierarchical porous 3D structured vanadium nitride/carbon membranes for high-performance supercapacitor negative electrodes. *Nano-Micro Lett.* **10**, 63 (2018). <https://doi.org/10.1007/s40820-018-0217-1>
13. Y. Yang, Y. Tang, G. Fang, L. Shan, J. Guo et al., Li<sup>+</sup> intercalated V<sub>2</sub>O<sub>5</sub>·nH<sub>2</sub>O with enlarged layer spacing and fast ion diffusion as an aqueous zinc-ion battery cathode. *Energy Environ. Sci.* **11**, 3157–3162 (2018). <https://doi.org/10.1039/C8EE01651H>
14. J.H. Jo, Y.-K. Sun, S.-T. Myung, Hollandite-type al-doped VO<sub>1.52</sub>(OH)<sub>0.77</sub> as a zinc ion insertion host material. *J. Mater. Chem. A* **5**, 8367–8375 (2017). <https://doi.org/10.1039/C7TA01765K>
15. X. Guo, G. Fang, W. Zhang, J. Zhou, L. Shan et al., Mechanistic insights of Zn<sup>2+</sup> storage in sodium vanadates. *Adv. Energy Mater.* **18**, 1801819 (2018). <https://doi.org/10.1002/aenm.201801819>
16. D. Kundu, B.D. Adams, V. Duffort, S.H. Vajargah, L.F. Nazar, A high-capacity and long-life aqueous rechargeable zinc battery using a metal oxide intercalation cathode. *Nat. Energy* **1**, 16119 (2016). <https://doi.org/10.1038/nenergy.2016.119>
17. C.W. Mason, F. Lange, Aqueous ion battery systems using sodium vanadium phosphate stabilized by titanium substitution. *ECS Electrochem. Lett.* **4**, A79–A82 (2015). <https://doi.org/10.1149/2.0011508eel>
18. H.B. Zhao, C.J. Hu, H.W. Cheng, J.H. Fang, Y.P. Xie et al., Novel rechargeable M<sub>3</sub>V<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub>//zinc (M = Li, Na) hybrid aqueous batteries with excellent cycling performance. *Sci. Rep.* **6**, 25809 (2016). <https://doi.org/10.1038/srep25809>
19. B. Tang, G. Fang, J. Zhou, L. Wang, Y. Lei, C. Wang, T. Lin, Y. Tang, S. Liang, Potassium vanadates with stable structure and fast ion diffusion channel as cathode for rechargeable aqueous zinc-ion batteries. *Nano Energy* **51**, 579–587 (2018). <https://doi.org/10.1016/j.nanoen.2018.07.014>
20. B. Zhang, Y. Liu, X. Wu, Y. Yang, Z. Chang, Z. Wen, Y. Wu, An aqueous rechargeable battery based on zinc anode and Na<sub>0.95</sub>MnO<sub>2</sub>. *Chem. Commun.* **50**, 1209–1211 (2014). <https://doi.org/10.1039/C3CC48382G>
21. N. Zhang, F. Cheng, Y. Liu, Q. Zhao, K. Lei, C. Chen, X. Liu, J. Chen, Cation-deficient spinel ZnMn<sub>2</sub>O<sub>4</sub> cathode in Zn(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub> electrolyte for rechargeable aqueous Zn-ion battery. *J. Am. Chem. Soc.* **138**, 12894–12901 (2016). <https://doi.org/10.1021/jacs.6b05958>
22. G. Yuan, J. Bai, T.N.L. Doan, P. Chen, Synthesis and electrochemical investigation of nanosized LiMn<sub>2</sub>O<sub>4</sub> as cathode material for rechargeable hybrid aqueous batteries. *Mater.*



- Lett. **137**, 311–314 (2014). <https://doi.org/10.1016/j.matlet.2014.09.019>
23. J. Zhao, Y. Li, X. Peng, S. Dong, J. Ma, G. Cui, L. Chen, High-voltage Zn/LiMn<sub>0.8</sub>Fe<sub>0.2</sub>PO<sub>4</sub> aqueous rechargeable battery by virtue of “water-in-salt” electrolyte. *Electrochem. Commun.* **69**, 6–10 (2016). <https://doi.org/10.1016/j.elecom.2016.05.014>
  24. G. Fang, C. Zhu, M. Chen, J. Zhou, B. Tang, X. Cao, X. Zheng, A. Pan, S. Liang, Suppressing manganese dissolution in potassium manganate with rich oxygen defects engaged high-energy-density and durable aqueous zinc-ion battery. *Adv. Funct. Mater.* **29**, 1808375 (2019). <https://doi.org/10.1002/adfm.201808375>
  25. J. Lee, J.B. Ju, W.I. Cho, B.W. Cho, S.H. Oh, Todorokite-type MnO<sub>2</sub> as a Zinc-ion intercalating material. *Electrochim. Acta* **112**, 138–143 (2013). <https://doi.org/10.1016/j.electacta.2013.08.136>
  26. T. Yamamoto, T. Shoji, Rechargeable Zn–ZnSO<sub>4</sub>–MnO<sub>2</sub>-type cells. *Inorg. Chim. Acta* **117**, L27–L28 (1986). [https://doi.org/10.1016/S0020-1693\(00\)82175-1](https://doi.org/10.1016/S0020-1693(00)82175-1)
  27. M.H. Alfaruqi, S. Islam, J. Gim, J. Song, S. Kim et al., A high surface area tunnel-type  $\alpha$ -MnO<sub>2</sub> nanorod cathode by a simple solvent-free synthesis for rechargeable aqueous zinc-ion batteries. *Chem. Phys. Lett.* **650**, 64–68 (2016). <https://doi.org/10.1016/j.cplett.2016.02.067>
  28. M.H. Alfaruqi, J. Gim, S. Kim, J. Song, D.T. Pham, J. Jo, Z. Xiu, V. Mathew, J. Kim, A layered  $\delta$ -MnO<sub>2</sub> nanoflake cathode with high zinc-storage capacities for eco-friendly battery applications. *Electrochem. Commun.* **60**, 121–125 (2015). <https://doi.org/10.1016/j.elecom.2015.08.019>
  29. G. Fang, J. Zhou, A. Pan, S. Liang, Recent advances in aqueous zinc-ion batteries. *ACS Energy Lett.* **3**, 2480–2501 (2018). <https://doi.org/10.1021/acseenergylett.8b01426>
  30. P. He, M. Yan, G. Zhang, R. Sun, L. Chen, Q. An, L. Mai, Layered VS<sub>2</sub> nanosheet-based aqueous Zn ion battery cathode. *Adv. Energy Mater.* **7**, 601920 (2017). <https://doi.org/10.1002/aenm.201601920>
  31. Y. Cheng, L. Luo, L. Zhong, J. Chen, B. Li et al., Highly reversible zinc-ion intercalation into chevrel phase Mo<sub>6</sub>S<sub>8</sub> nanocubes and applications for advanced zinc-ion batteries. *ACS Appl. Mater. Interfaces* **8**, 13673–13677 (2016). <https://doi.org/10.1021/acsaami.6b03197>
  32. M.H. Alfaruqi, V. Mathew, J. Gim, S. Kim, J. Song, J.P. Baboo, S.H. Choi, J. Kim, Electrochemically induced structural transformation in a  $\gamma$ -MnO<sub>2</sub> cathode of a high capacity zinc-ion battery system. *Chem. Mater.* **26**, 3609–3620 (2015). <https://doi.org/10.1021/cm504717p>
  33. B. Lee, H.R. Lee, H. Kim, K.Y. Chung, B.W. Cho, S.H. Oh, Elucidating the intercalation mechanism of zinc ions into  $\alpha$ -MnO<sub>2</sub> for rechargeable zinc batteries. *Chem. Commun.* **51**, 9265–9268 (2015). <https://doi.org/10.1039/C5CC02585K>
  34. B. Lee, H.R. Seo, H.R. Lee, C.S. Yoon, J.H. Kim, K.Y. Chung, B.W. Cho, S.H. Oh, Critical role of pH evolution of electrolyte in the reaction mechanism for rechargeable zinc batteries. *Chemosuschem* **9**, 2948–2956 (2016). <https://doi.org/10.1002/cssc.201600702>
  35. B. Lee, C.S. Yoon, H.R. Lee, K.Y. Chung, B.W. Cho, S.H. Oh, Electrochemically-induced reversible transition from the tunneled to layered polymorphs of manganese dioxide. *Sci. Rep.* **4**, 6066 (2014). <https://doi.org/10.1038/srep06066>
  36. M.H. Alfaruqi, J. Gim, S. Kim, J. Song, J. Jo, S. Kim, V. Mathew, J. Kim, Enhanced reversible divalent zinc storage in a structurally stable  $\alpha$ -MnO<sub>2</sub> nanorod electrode. *J. Power Sources* **288**, 320–327 (2015). <https://doi.org/10.1016/j.jpowsour.2015.04.140>
  37. H. Pan, Y. Shao, P. Yan, Y. Cheng, K.S. Han et al., Reversible aqueous zinc/manganese oxide energy storage from conversion reactions. *Nat. Energy* **1**, 16039 (2016). <https://doi.org/10.1038/nenergy.2016.39>
  38. W. Sun, F. Wang, S. Hou, C. Yang, X. Fan et al., Zn/MnO<sub>2</sub> battery chemistry with H<sup>+</sup> and Zn<sup>2+</sup> coinserion. *J. Am. Chem. Soc.* **139**, 9775–9778 (2017). <https://doi.org/10.1021/jacs.7b04471>
  39. G.G. Yadav, J.W. Gallaway, D.E. Turney, M. Nyce, J. Huang, X. Wei, S. Banerjee, Regenerable Cu-intercalated MnO<sub>2</sub> layered cathode for highly cyclable energy dense batteries. *Nat. Commun.* **8**, 14424 (2017). <https://doi.org/10.1038/ncomms14424>
  40. N. Jabeen, A. Hussain, Q. Xia, S. Sun, J. Zhu, H. Xia, High-performance 2.6 V aqueous asymmetric supercapacitors based on in situ formed Na<sub>0.5</sub>MnO<sub>2</sub> nanosheet assembled nanowall arrays. *Adv. Mater.* **29**, 1700804 (2017). <https://doi.org/10.1002/adma.201700804>
  41. A. Konarov, N. Voronina, J.H. Jo, Z. Bakenov, Y.-K. Sun, S.-T. Myung, Present and future perspective on electrode materials for rechargeable zinc-ion batteries. *ACS Energy Lett.* **3**, 2620–2640 (2018). <https://doi.org/10.1021/acseenergylett.8b01552>
  42. M. Song, H. Tan, D. Chao, H.J. Fan, Recent advances in Zn-ion batteries. *Adv. Funct. Mater.* **28**, 1802564 (2018). <https://doi.org/10.1002/adfm.201802564>
  43. J. Hao, J. Mou, J. Zhang, L. Dong, W. Liu, C. Xu, F. Kang, Electrochemically induced spinel-layered phase transition of Mn<sub>3</sub>O<sub>4</sub> in high performance neutral aqueous rechargeable zinc battery. *Electrochim. Acta* **259**, 170–178 (2018). <https://doi.org/10.1016/j.electacta.2017.10.166>
  44. D. Grujicic, B. Pesic, Reaction and nucleation mechanisms of copper electrodeposition from ammoniacal solutions on vitreous carbon. *Electrochim. Acta* **50**, 4426–4443 (2005). <https://doi.org/10.1016/j.electacta.2005.02.012>
  45. A. Anderko, S.J. Sanders, R.D. Young, Real-solution stability diagrams: a thermodynamic tool for modeling corrosion in wide temperature and concentration ranges. *Corrosion* **53**, 43–53 (1997). <https://doi.org/10.5006/1.3280432>
  46. A.G. Tyurin, A role of manganese in the corrosion and electrochemical behavior of stainless steels. *Prot. Met.* **41**, 68–75 (2005). <https://doi.org/10.1007/s11124-005-0010-7>
  47. X. Zhou, C. Wei, M. Li, S. Qiu, X. Li, Thermodynamics of vanadium–sulfur–water systems at 298 K. *Hydrometallurgy* **106**, 104–112 (2011). <https://doi.org/10.1016/j.hydromet.2010.12.003>

48. M. Chamoun, W.R. Brant, C.-W. Tai, G. Karlsson, D. Noréus, Rechargeability of aqueous sulfate Zn/MnO<sub>2</sub> batteries enhanced by accessible Mn<sup>2+</sup> ions. *Energy Storage Mater.* **15**, 351–360 (2018). <https://doi.org/10.1016/j.ensm.2018.06.019>
49. K.J. Vetter, A general thermodynamic theory of the potential of passive electrodes and its influence on passive corrosion. *J. Electrochem. Soc.* **110**, 597–605 (1963). <https://doi.org/10.1149/1.2425837>

