

This is a repository copy of *Observation of Small Polaron and Acoustic Phonon Coupling in Ultrathin La_{0.7}Sr_{0.3}MnO₃/SrTiO₃ Structures*.

White Rose Research Online URL for this paper:
<https://eprints.whiterose.ac.uk/143474/>

Version: Accepted Version

Article:

Liu, Bo, Niu, Wei, Ruan, Xuezhong et al. (8 more authors) (2019) Observation of Small Polaron and Acoustic Phonon Coupling in Ultrathin La_{0.7}Sr_{0.3}MnO₃/SrTiO₃ Structures. *Physica Status Solidi - Rapid Research Letters*. 1800657. ISSN 1862-6254

<https://doi.org/10.1002/pssr.201800657>

Reuse

Items deposited in White Rose Research Online are protected by copyright, with all rights reserved unless indicated otherwise. They may be downloaded and/or printed for private study, or other acts as permitted by national copyright laws. The publisher or other rights holders may allow further reproduction and re-use of the full text version. This is indicated by the licence information on the White Rose Research Online record for the item.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.

Advanced Materials

Ultrafast orbital-oriented control of magnetization in half-metallic La_{0.7}Sr_{0.3}MnO₃ films --Manuscript Draft--

Manuscript Number:	adma.201806443R2
Full Title:	Ultrafast orbital-oriented control of magnetization in half-metallic La _{0.7} Sr _{0.3} MnO ₃ films
Article Type:	Communication
Section/Category:	
Keywords:	spintronics; ultrafast magnetization; perovskite; spin-orbit coupling; Ultrafast spectroscopy
Corresponding Author:	Bo Liu Nanjing University Nanjing, Jiangsu CHINA
Additional Information:	
Question	Response
Please submit a plain text version of your cover letter here.	<p>Dear Editor:</p> <p>Please find our enclosed manuscript titled "Ultrafast orbital-oriented control of magnetization in half-metallic La_{0.7}Sr_{0.3}MnO₃ ultrathin films" for submission as a Communication Article of the Advanced Materials.</p> <p>Manipulating spin in ultrafast timescale is of great interest to condensed matter physics and also important to spintronics applications. While it is well known that the spin-orbit coupling plays a key role in the spin dynamics relaxation, the possible effect of the anisotropic spin-orbit coupling on the transient magnetization is still not answered experimentally. At the same time, the colossal magnetoresistance manganite (CMR) materials provide perfect platforms to exploit this general and fundamental issue as they have the anisotropic spin-orbit coupling due to the strong coupling between spin, charge, orbital and lattice degrees of freedom.</p> <p>In our work, we demonstrate for the first time the effect of the anisotropic spin-orbit coupling on the temporal magnetization with a prototype CMR material, namely, La_{0.7}Sr_{0.3}MnO₃ ultrathin film. The results have provided new perspectives for ultrafast control of magnetic order. We believe the following specific aspects of our findings will be of interests to the general readers of Advanced Materials:</p> <ol style="list-style-type: none">1. The transient magnetic order within sub-picosecond can be enhanced or attenuated by tuning the probe light polarizations. This observation is explained by a model based on the Elliott-Yafet spin-flip scattering arising from the anisotropic spin-orbit coupling.2. The subsequent slow demagnetization component (lasting for hundreds of picoseconds) follows the four-fold symmetry of the dx²-y² orbitals, which is also attributed to the effect of the anisotropic spin-orbit coupling. <p>A list of potential reviewers is also attached. Thank you for your time and consideration. We are looking forward to hearing from you.</p> <p>Sincerely, Professor Yongbing Xu Director, York-Nanjing International Center of Spintronics (YNICS) The University of York, UK Nanjing University, Nanjing 210093, China Email : ybxu@nju.edu.cn</p>
Do you or any of your co-authors have a conflict of interest to declare?	No. The authors declare no conflict of interest.

Corresponding Author Secondary Information:	
Corresponding Author's Institution:	Nanjing University
Corresponding Author's Secondary Institution:	
First Author:	Bo Liu
First Author Secondary Information:	
Order of Authors:	Bo Liu
	Wei Niu
	Yongda Chen
	Xuezhong Ruan
	Zhixiong Tang
	Xuefeng Wang
	Wenqing Liu
	Liang He
	Yao Li
	Jing Wu
	Shaolong Tang
	Jun Du
	Rong Zhang
	Yongbing Xu
Order of Authors Secondary Information:	
Abstract:	<p>Manipulating spins by ultrafast pulse laser provides a new avenue to switch the magnetization for spintronic applications. While the spin-orbit coupling is known to play a pivotal role in the ultrafast laser-induced demagnetization, the effect of the anisotropic spin-orbit coupling on the transient magnetization remains an open issue. Here, we uncover the role of anisotropic spin-orbit coupling in the spin dynamics in a half-metallic La_{0.7}Sr_{0.3}MnO₃ film by ultrafast pump-probe technique. The magnetic order is found to be transiently enhanced or attenuated within the initial sub-picosecond when the probe light is tuned to be s- or p-polarized, respectively. The subsequent slow demagnetization amplitude follows the four-fold symmetry of the dx²-y² orbitals as a function of the polarization angles of the probe light. A model based on the Elliott-Yafet spin-flip scatterings is proposed to reveal that the transient magnetization enhancement is related to the spin-mixed states arising from the anisotropic spin-orbit coupling. Our findings provide new insights into the spin dynamics in magnetic systems with anisotropic spin-orbit coupling as well as perspectives for the ultrafast control of information process in spintronic devices.</p>

Ultrafast orbital-oriented control of magnetization in half-metallic $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ films

Bo Liu,¹ Wei Niu,¹ Yongda Chen,¹ Xuezhong Ruan,^{1,*} Zhixiong Tang², Xuefeng Wang,^{1,*}
Wenqing Liu³, Liang He,¹ Yao Li¹, Jing Wu⁴, Shaolong Tang², Jun Du², Rong Zhang¹, and
Yongbing Xu^{1,4*}

¹Jiangsu Provincial Key Laboratory of Advanced Photonic and Electronic Materials,
Collaborative Innovation Center of Advanced Microstructures, School of Electronic Science
and Engineering, Nanjing University, Nanjing 210093, P. R. China

²Department of Physics, Nanjing University, Nanjing 210093, P. R. China

³Department of Electronic Engineering, Royal Holloway, University of London, Egham,
Surrey TW20 0EX, UK

⁴York-Nanjing Joint Center in Spintronics, Department of Electronic Engineering and
Department of Physics, The University of York, York YO10 5DD, UK

*Correspondence Emails: xzruan@nju.edu.cn; xfwang@nju.edu.cn; ybxu@nju.edu.cn

1 Manipulating spins by ultrafast pulse laser provides a new avenue to switch the magnetization
2
3 for spintronic applications. While the spin-orbit coupling is known to play a pivotal role in the
4
5 ultrafast laser-induced demagnetization, the effect of the anisotropic spin-orbit coupling on the
6
7 transient magnetization remains an open issue. Here, we uncover the role of anisotropic spin-
8
9 orbit coupling in the spin dynamics in a half-metallic $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ film by ultrafast pump-
10
11 probe technique. The magnetic order is found to be transiently enhanced or attenuated within
12
13 the initial sub-picosecond when the probe light is tuned to be s- or p-polarized, respectively.
14
15 The subsequent slow demagnetization amplitude follows the four-fold symmetry of the $d_{x^2-y^2}$
16
17 orbitals as a function of the polarization angles of the probe light. A model based on the Elliott-
18
19 Yafet spin-flip scatterings is proposed to reveal that the transient magnetization enhancement
20
21 is related to the spin-mixed states arising from the anisotropic spin-orbit coupling. Our findings
22
23 provide new insights into the spin dynamics in magnetic systems with anisotropic spin-orbit
24
25 coupling as well as perspectives for the ultrafast control of information process in spintronic
26
27 devices.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 Since the observation that a femtosecond laser pulse can quench the magnetization in the
2 ferromagnetic Ni film,^[1] the field of femtosecond magnetism has attracted great attentions due
3 to the potential advantages of ultra-fast spin manipulation for the advanced data storage.^[2-4]
4 One of the key issues related to the ultrafast spin dynamics of magnetic materials is the
5 demagnetization process. In the transition 3d ferromagnetic metals,^[5-8] the magnetic order was
6 found to be quenched in a sub-picosecond timescale and then re-magnetized in a longer
7 timescale of several picoseconds (ps). In half metals,^[9-11] such as Sr₂FeMoO₆, CrO₂ and
8 La_{0.6}Sr_{0.4}MnO₃, experimental observations have shown that the ultrafast demagnetization
9 involves two steps: an initial instantaneous decrease within a ps and a subsequent slow
10 decreasing response lasting for several hundreds of ps. The second step of the slow
11 demagnetization in the half metals is attributed to the spin-lattice relaxation.^[9-12] However, in
12 both the 3d transition and half-metallic metals, the microscope origin of the first step of sub-ps
13 demagnetization is still in debate. One of the most prominent mechanisms is the scatterings of
14 various quasiparticles, such as electron-electron, electron-phonon and electron-magnon
15 scatterings.^[7,10,13,14] Another completely different explanation for ultrafast demagnetization is
16 the superdiffusive transport of the majority and minority spin polarized electrons.^[5,15]
17 Alternatively, Illg *et al.*^[16] claimed that the combination of electron-phonon and electron-
18 magnon scatterings was a possible explanation for ultrafast demagnetization. The above-
19 mentioned momentum-related scattering events involve both the spin and orbit degrees of
20 freedom. For electrons, the spin-orbit interactions (SOI) connect the spin degree of freedom to
21 their orbital motion. Therefore, it is widely believed that spin-orbit interactions (SOI) play an
22 important role in ultrafast demagnetization process as also confirmed by previous X-ray
23 Magnetic Circular Dichroism (XMCD) measurements.^[17,18] Hence, utilizing the SOI are
24 expected to allow the control of magnetism in the ultrafast regime.

1 The colossal magneto-resistive (CMR) materials with half-metallic properties are potential
2 candidates for high efficient spintronic devices and their strong SOI offer the tunability of the
3
4 couplings between spin, charge, lattice, and orbital degrees of freedom.^[19,20] The effect of the
5
6 anisotropic SOI on the electron transport properties in the CMR manganites is evidenced by
7
8 the anisotropic magnetoresistance (AMR).^[21-23] Recently, the emergence of anisotropic Gilbert
9
10 damping has been demonstrated in ultrathin Fe layers on GaAs (001) substrate, which is
11
12 attributed to the anisotropic interfacial SOI.^[24] Taking into account the correlation between the
13
14 damping and relaxation rate of the demagnetization,^[13] the anisotropic SOI which determine
15
16 the Gilbert damping are expected to play a vital role on the ultrafast demagnetization process
17
18 in the CMR materials. As discussed above, the SOI have been demonstrated to play an
19
20 important role in the demagnetization process. However, the general issue of the effect of the
21
22 anisotropic SOI on the temporal magnetization has not been addressed so far. This issue is
23
24 fundamental to both the understanding of ultrafast demagnetization mechanisms and the optical
25
26 manipulation of spins in fs/ps time scale.
27
28
29
30
31
32
33

34 In this letter, we demonstrate the ultrafast manipulation of the magnetization through the orbital
35
36 orientation in ferromagnetic $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ (LSMO) thin films by using the time-resolved
37
38 magneto-optical Kerr effect (TR-MOKE) technique. The ultrafast enhancement or decrease of
39
40 magnetization within one ps is achieved under s- or p-polarized probe light, respectively. This
41
42 fast magnetization process correlated with the polarization orientation of the probe light within
43
44 a ps is explained by a model based on the Elliott-Yafet spin-flip scattering. After this initial
45
46 fast stage, a slow demagnetization process is then followed, lasting for hundreds of ps. The
47
48 demagnetization amplitudes under different directions of probe light polarization are found to
49
50 follow the four-fold symmetry of the orbital order.
51
52
53
54
55
56

57 The sample studied here with a thickness of 16 nm (40 unit cells) was grown on (001) oriented
58
59 single crystalline SrTiO_3 (STO) terraced substrate. The crystallographic c-axis [001] is normal
60
61
62
63
64
65

1 to the sample plane. The in-plane crystallographic directions of [100] and [010] are shown in
2 Figure 1 (a). More details of the growth information are given in the Supplemental Materials
3 (SM) and other refs.^[25,26] The Curie temperature T_C of the film is ~ 334 K (See Figure.S1(a) of
4 SM). This well resembles the previous results for bulk LSMO,^[10,27] indicating the high quality
5 of the film. In bulk LSMO, the $d_{x^2-y^2}/d_{z^2-y^2}$ orbitals that partially filled by electrons are
6 responsible for the metallic character and the double-exchange interaction between Mn^{3+} and
7 Mn^{4+} is responsible for the ferromagnetic order. As the sample exceeds the critical thickness
8 of 2.5 nm, ferromagnetism is well reserved.^[28] The LSMO thin film used in our measurements
9 exhibits in-plane magnetic anisotropy, which originates from the in-plane tensile strain caused
10 by the STO substrate. In the epitaxial film, the strain that originated from the substrate may
11 modify the orbital occupancy.^[29] As demonstrated by recent X-ray linear dichroism (XLD)
12 measurements,^[29,30] the tensile strain in LSMO thin film induced by STO substrate implies a
13 preferential occupancy of the $d_{x^2-y^2}$ orbital. The static Kerr rotation at room temperature is
14 shown in Figure.S1 (b), showing relatively strong magneto-optical response at high photon
15 energy. In our pump-probe measurements, 3.1 eV photons were used to probe the sample's
16 magnetism as indicated by the blue arrow in Figure.S1(b). All the measurements were
17 performed at room temperature.

18 The measurement geometry is schematically shown in Figure 1 (a). We used 1.55 eV photons
19 to excite the sample and the s-polarized 3.1 eV photons to measure the resulting changes of
20 magnetization. Figure 1 (c) shows the photoinduced change of Kerr rotation $\Delta\theta$ normalized by
21 the static value θ_0 before optical excitation. After the photoexcitation at $\Delta t = 0$ ps, an
22 instantaneous increase of $\Delta\theta/\theta_0$ up to 0.15 is observed within 1 ps. Following this
23 instantaneous increase, the amplitude of $\Delta\theta/\theta_0$ continuously decreases, passes zero at 40 ps,
24 and finally reaches a minimum of -0.6 at 1.36 ns. Note that the positive sign here represents
25 the increase of magnetization. Upon the observation of the transient increase of magnetization

1 with the s-polarized probe beam, the hysteresis loops at different delay-times were measured
2 as shown in Figure 1(d). It clearly shows two reversed types of the transient hysteresis loops at
3
4 0.67 ps and 1.36 ns, respectively. These results confirm that, as probed with s-polarized light,
5
6 an ultrafast increase in magnetization occurs after photoexcitation.
7

8
9 The ultrafast increase in magnetization of perovskite manganites has been reported in several
10
11 refs.^[31-35] The underlying physical mechanisms are fundamentally linked to the density of
12
13 photogenerated carriers. For example, Yada *et al.*^[31] found that the magnetization in
14
15 $\text{La}_{0.9}\text{Sr}_{0.1}\text{MnO}_3/\text{SrTiO}_3$ heterostructures increased within 0.2 ps due to the rapid hole injection
16
17 from STO into the manganite. Li *et al.*^[34] showed a femtosecond generation of ferromagnetic
18
19 order in $\text{Pr}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$ with photoexcitation threshold behaviour. If the photogenerated
20
21 carriers dominate the ultrafast increase of magnetism in our sample, then tuning the carrier
22
23 density will lead to the variation of the ultrafast enhancement. We have conducted one
24
25 experiment to test this prediction. As shown in Figure2, we extract respectively the amplitudes
26
27 of the transient hysteresis loops at $\Delta t = 0.67$ ps and 1.36 ns under different pump excitation
28
29 intensity. The raw data of the transient hysteresis loops under different pump fluence is shown
30
31 in Figure S2. Clearly, the values at $\Delta t = 0.67$ ps exhibit independence on the pump fluence,
32
33 demonstrating that the photo-carrier generation does not contribute to this fast magnetization
34
35 increase.
36
37
38
39
40
41
42
43

44 We notice that the ensuing slow decreasing component in Figure1 (c) is in the ns timescale.
45
46 This slow magnetization relaxation is associated with the demagnetization due to the increase
47
48 of the spin temperature by optically heating the spin system through the transferred energy
49
50 from the equilibrium electron-lattice system. Such spin-lattice relaxation is consistent with
51
52 previous empirical demagnetization process observed in materials with half-metallic
53
54 property.^[9,10,36,37] In Figure 2, the amplitude of the slow demagnetization component (1.36 ns)
55
56 increases with increasing pump excitation intensity, which also supports the expectation of the
57
58
59
60
61
62
63
64
65

1 thermal demagnetization. However, the transient enhancement of the magnetization observed
2 with s-polarized probe light cannot be expected from the thermal process, which should lead
3 to an instantaneous drop rather than increase in magnetization as previously reported.^[8]
4

5
6
7 Considering the strongly coupled degrees of freedom between the spin and orbital in the LSMO
8 film, we expect that the orbital orientation plays a role in the magnetization enhancement. To
9 verify this assumption, we have investigated the effect of the probe light polarization
10 orientation on the pump-induced spin dynamics. In Figure 3(a), the recorded temporal trace
11 was measured by the p-polarized probe beam. The polarization orientation and the excitation
12 intensity of the pump beam remain the same as those in Figure 1(c). Under this experimental
13 configuration, the instantaneous change of $\Delta\theta/\theta_0$ within the initial 1 ps points to the negative
14 direction, representing the ultrafast demagnetization. With p-polarized probe beam, the $\Delta\theta/\theta_0$
15 trace shows a typical two-step demagnetization characteristics, consisting of a step-like
16 decrease and a subsequent slow demagnetization process of hundreds of ps or ns timescale.
17 This observation is consistent with the previous results mentioned above. The transient
18 hysteresis loops at $\Delta t = 30$ ps and 1.36 ns shown in Figure 3(b) confirm the in-phase decrease
19 of magnetization. To further study the demagnetization behaviors under different polarization
20 orientations of the probe beam, we have carried out systematic measurements to address this
21 issue. In Figure 3(c), the values of $\Delta\theta/\theta_0$ at time delay of 0.67 ps and 1.36 ns are plotted as a
22 function of the polarization angles of the probe beam. Here, $\varphi = 0^\circ$ and 90° represent the p-
23 and s-polarization of the probe beam, respectively. The orientation of the s-polarized probe
24 beam aligns with the [010] crystallographic axis of the LSMO thin film. The values of $\Delta\theta/\theta_0$
25 at 0.67 ps crosses zero at 130° . The sign of the values at 1.36 ns remains the same but their
26 amplitudes change periodically. In Figure 3(d), the demagnetization amplitudes under different
27 probe polarization angles at $\Delta t = 1.36$ ns show a four-fold symmetry, which is similar to the
28 occupied $d_{x^2-y^2}$ orbitals as included in Figure 1(b). As experimentally demonstrated by
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 Buchner *et al.*,^[38] the MOKE method is a powerful tool of probing the interfacial SO coupling
2 by tuning the polarization angle of the probing laser beam. The polarization orientation of the
3 pump beam is found to have no impact on the demagnetization in our measurements (see in
4 Figure S3). This suggests that the pump laser disturbs the sample mainly by the heating effect
5 rather than the electron transition.
6

7
8
9
10
11 The initial quenching of magnetization in half metals has been explained by several models
12 based on the Elliott-Yafet(EY) type spin dependent scattering, such as the electron-electron,
13 electron-phonon or electron-impurity interactions.^[14,37,39,40] These microscopic mechanisms
14 are all momentum-dependent scattering events due to the spin-orbit coupling, which would
15 lead to a mixture of the two spin states near the Fermi level. The four-fold symmetry of the
16 demagnetization amplitude at $\Delta t = 1.36$ ns in Figure 3(d) reveals different spin scattering rates
17 along different spatial directions, as expected from the anisotropic spin-orbital coupling in the
18 CMR materials. We have also obtained similar results on two other samples with different
19 thicknesses of 30 and 35 uc, respectively (as shown in Figure S4). The consistent results on
20 different samples support our findings very well. We notice that the anisotropic Gilbert
21 damping in $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ thin film is recently reported,^[41] which is ascribed to the anisotropic
22 SO coupling. Similar spin relaxation rates were also reported in other materials arising from
23 the anisotropic spin-orbit coupling.^[24,42,43] The fast change of magnetism (~ 0.67 ps) in Figure
24 3(c) also has a dependence on probe light polarization orientation, showing different spin
25 scattering rates along various orbital orientations. Note that the polarization of the light can
26 access to different spatial directions of the orbitals.^[44,45]
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50

51 Considering the significant effect of the anisotropic spin-orbit coupling on spin relaxation, we
52 propose a model to explain the observed ultrafast orbital-orientation demagnetization, as shown
53 by the schematic diagram in Figure 4. In the presence of the spin-orbital coupling, an electron
54 state near the Fermi level (straight dash line) is a mixture of the spin-up and spin-down states.^[46]
55
56
57
58
59
60
61
62
63
64
65

1 Therefore, a number of spin-down electrons exist in the minority-spin band gap (dash curves
2 in Figure 4). As shown in Figure 4, after photoexcitation by the pump light, non-equilibrium
3 electrons (solid cyan circles) and holes (open circles) with up-spins are generated above and
4 below the E_F , respectively. Since there exist a few spin-down states near the Fermi level, only
5 a small part of the non-equilibrium carriers can be relaxed into the minority empty states via
6 the spin-flip scattering. The p and s polarized probe light correspond to the x and y directions,
7 respectively, as shown in Figure 1(a). Based on the above-mentioned consideration of
8 anisotropic spin-orbit coupling, the photoexcited spin-up electrons prefer the scattering
9 channels along x or y directions, as probed with p- or s-polarized light, respectively. In the case
10 of p-polarized probe light (P process in Figure 4(a)), the spin-up electrons are relaxed into the
11 empty spin-down states via the EY-based spin flip mechanism, leading to an instantaneous
12 decrease of magnetization. For the s-polarized probe light (S process in Figure 4(b)), the
13 electron spin-flip scattering along x direction is prohibited. However, the minority spin-down
14 electrons can recombine with the majority spin-up holes below the Fermi level via the spin-flip
15 scattering along the y direction, leading to an instantaneous increase of the magnetization. In
16 the two processes of S and P, different spin-flip behaviour are necessary to account for the
17 ultrafast demagnetization and remagnetization, respectively. Previous theoretical and
18 experimental studies have suggested specific scattering ways to achieve spin flipping, e.g.,
19 electron-phonon, electron-defect and electron-electron scatterings.^[14,47-49] As a consequence,
20 the spin angular momentum can be transferred quickly to other degrees of freedom or vice
21 versa. We notice that Wüstenberg et al. have previously revealed the possibility of ultrafast
22 remagnetization via recombination of majority holes and minority electrons in half-metallic
23 Heusler alloy $\text{Co}_2\text{Cr}_{0.6}\text{Fe}_{0.4}\text{Al}$ thin films.^[50] Their results support ours well. After the initial
24 EY-based instantaneous increase or decrease in magnetization, the spin order of the remaining
25 excited electrons (labeled as slow in Figure 4) is disturbed further via the slow spin-lattice
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 relaxation channel due to the increasing of the spin temperature. To further demonstrate the
2 effect of orbital-oriented transient magnetization, we have also measured the pump-induced
3 Kerr rotations at time-delays of 0.67 ps and 1.36 ns respectively by rotating the sample
4 orientation angle ϕ with fixed p-polarization of the probe beam. The results obtained by
5 rotating the sample were identical to those obtained by varying the polarization angles of the
6 probe light. The corresponding results are shown in Figure S5 in SM. In the above discussion
7 on the EY-based spin-flip mechanisms, we did not address the specific scattering events
8 (electron-electron, electron-phonon, electron-magnon, or electron-impurity scattering).
9 However, the distinct dependence of the spin order on the orbital orientation suggests that the
10 phonon-mediated scattering events play dominant roles in the sub-ps time scale, which have
11 been reported in previous studies.^[37,39,47] We believe that the phenomena of the ultrafast orbital-
12 orientation demagnetization should exist in other ferromagnetic perovskite manganites, where
13 the anisotropic spin-orbital coupling is a general characteristic of this material system.
14
15 In summary, the ultrafast orbital-oriented demagnetization process in the thin LSMO film has
16 been studied by the TR-MOKE measurements, which reveals the novel effect of the anisotropic
17 spin-orbit coupling on the temporal magnetization evolution. The transient magnetization
18 enhancement as well as the decrease within the initial 1 ps after photoexcitation has been
19 observed via tuning the polarization orientation of the probe light. A model based on the
20 anisotropic spin-orbit coupling has been proposed to illustrate the spin-flip scattering
21 happening within sub-ps regime. The anisotropic spin-orbit coupling has also been found to
22 induce a four-fold symmetry in the subsequent slowly-relaxed demagnetization process
23 measured by tuning the direction of the probe light polarization. This work has provided new
24 insights into the underlying physics of ultrafast magnetism in the magnetic material systems
25 with anisotropic spin-orbit coupling and new parameters for the ultrafast optical control of the
26 magnetic order.
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Experimental Section

The experimental geometry of our TR-MOKE measurement is shown in Figure 1a. The incident pump beam is along the sample normal and the incident angle of the probe beam is around 45° away from the sample normal direction. The femtosecond pulse laser is generated by an amplified Ti: sapphire laser system with a 1 KHz repetition rate, a ~ 50 fs duration time, and a central wavelength of 800 nm (1.55 eV). The majority of the output laser intensity is used to excite the sample as a pump beam. The remainder passing through a BBO crystal is employed to measure the pump induced magnetic variation. The time delay between the two beams is achieved by a mechanical delay stage. The polarization angle of the probe light is tuned by a half-wave plate, as shown in Figure 1a. To obtain the genuine magnetic information, we define $\Delta\theta/\theta_0 = (\Delta\theta_+/\theta_0 - \Delta\theta_-/\theta_0)/2$. Here, $\Delta\theta_+$ and $\Delta\theta_-$ represent the pump-induced Kerr rotations under positive and negative magnetic fields, respectively. θ_0 represents the static Kerr rotation without pump excitation. In the measurements, the sample temperature rise induced by laser illumination was ignored as the time interval between two laser pulses (a millisecond) is long enough for the heat diffusion. One thing that needs to be addressed here is that the raw data in FIG. 3(d) was measured only from 90 – 270°. The data of 270 – 90° was obtained by the four-fold symmetry.

Supporting Information

Supporting Information is available.

Acknowledgements

This work was supported in part by National Basic Research Program of China (2014CB921101, 2017YFA0206304, 2013CB932900); National Natural Science Foundation of China (11774160, 61427812, 61378025, 61274102, 61322407, 11304148, U1732159); National Young 1000 Talent Plan; A 'Jiangsu Shuangchuang Team' Program; Program for

1 New Century Excellent Talents in University of Ministry of Education of China (NCET-13-
2 0094); Jiangsu NSF (BK20140054).
3

4
5 **Conflict of Interest**
6

7 The authors declare no conflict of interest.
8
9

10
11 **Keywords**
12

13 Spintronics, ultrafast magnetization, perovskite, spin-orbit coupling, ultrafast spectroscopy
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

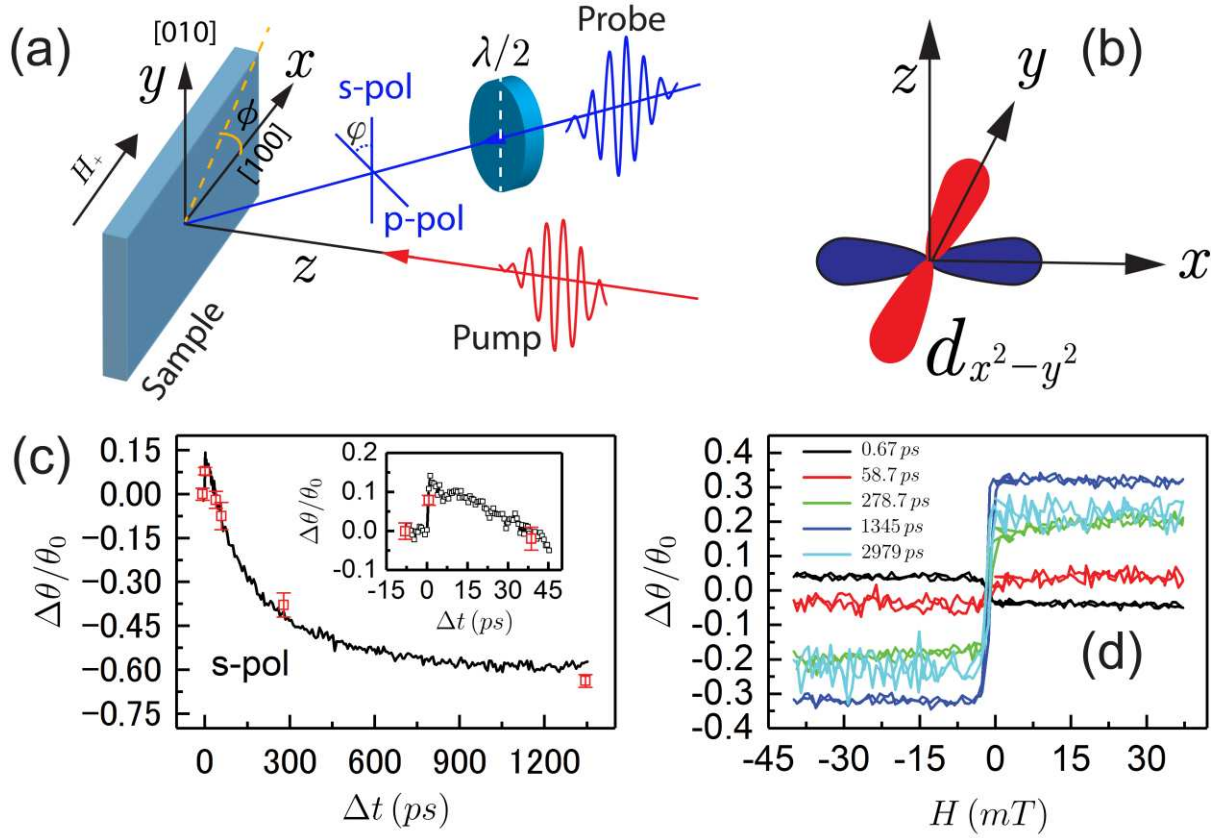


Figure 1. (a) The geometry diagram of the time-resolved magneto-optical Kerr effect. The pump beam is incident perpendicularly on the sample surface. The incident angle of the probe light is 45° with respect to the sample normal direction. A half-wave plate ($\lambda/2$) is used to rotate the polarization plane of the probe light. φ here represents the rotation angle with respect to the incident plane of probe light. In the case of $\varphi = 0^\circ$, the electric field of light lies in the plane of the incident probe beam. ϕ is defined as the angle between the spatial x-axis and the crystallographic axis [100] of the LSMO thin film. (b) Diagram of the $d_{x^2-y^2}$ orbitals occupied by the e_g electrons. (c) Temporal characteristics of the pump-induced Kerr rotation with the s-polarized probe beam. The inset shows a magnified view of the ultrafast increase of $\Delta\theta/\theta_0$. (d) The transient hysteresis loops of LSMO film measured at different delay-times. The hysteresis loop probed at 0.67 ps is obviously opposite to those measured at other delay-times. The red squares in (c) represent the amplitude of the transient hysteresis loops at different time delays as shown in (d).

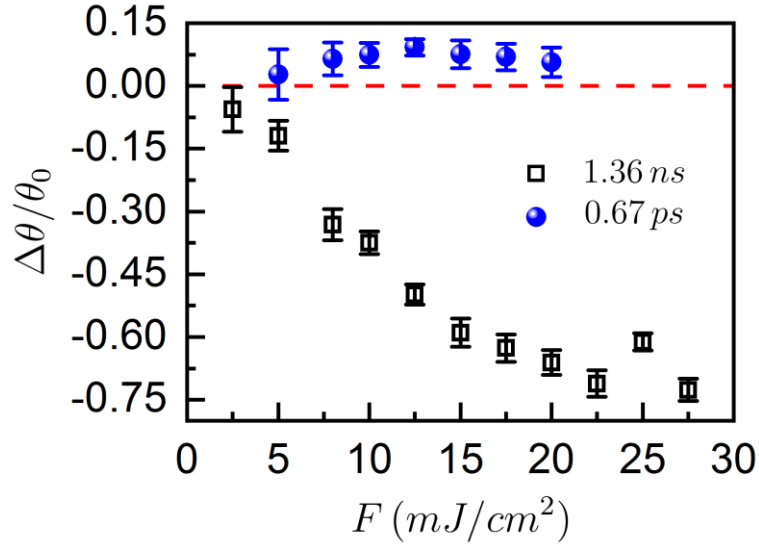


Figure 2. Fluence dependence of the normalized Kerr rotations at different time-delays. The blue and black squares represent the values of $\Delta\theta/\theta_0$ at $\Delta t = 0.67$ ps and 1.36 ns, respectively. The positive sign means the increase of magnetization, while the negative shows the demagnetization. The transient enhancement in magnetization is nearly independent of the pump fluence, while the slow demagnetization component is affected by laser heating.

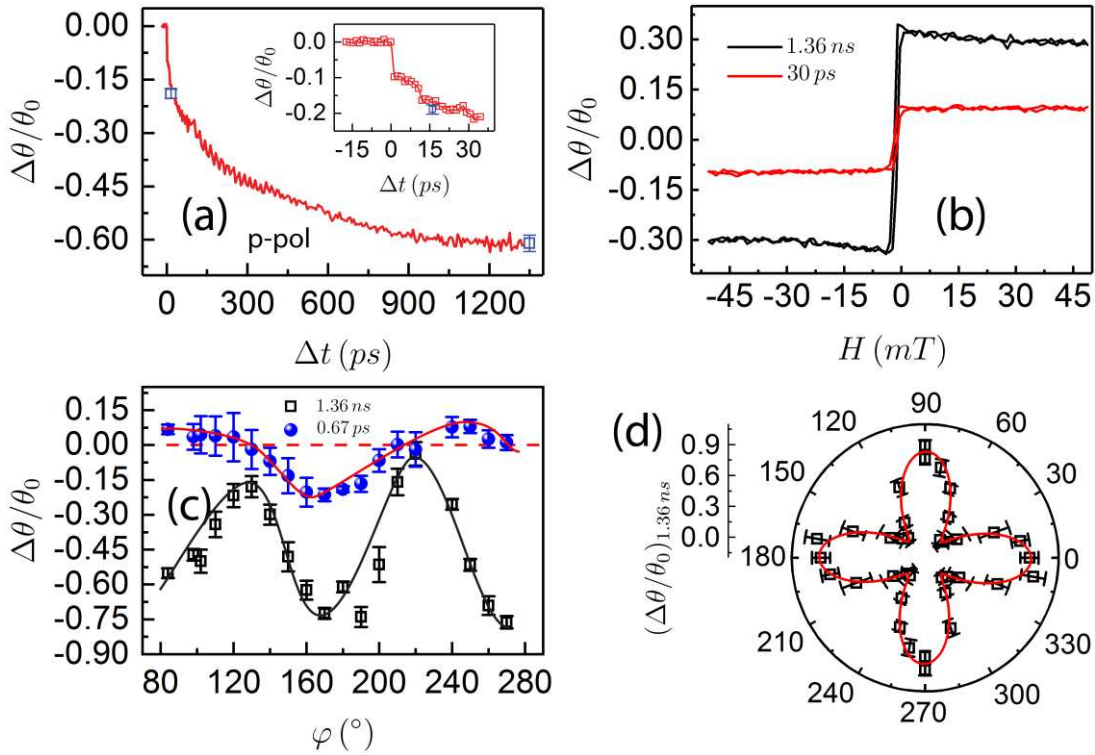


Figure 3. (a) The time evolution of the pump induced change of Kerr rotation probed with s-polarized probe. Inset: The enlargement of the pump induced Kerr signal at short time window of ~ 30 ps. (b) Transient hysteresis loops measured at $\Delta t = 30$ ps and 1.36 ns. Their amplitude with error bars are shown in (a) at the corresponding time delays. (c) The probe beam polarization orientation dependence of $\Delta\theta/\theta_0$ values at time delays of 0.67 ps and 1.36 ns. The polarization angle of probe beam φ varies from 87° to 180° , corresponding to s and p polarization, respectively. (d) The probe beam polarization orientation dependence of the demagnetization amplitudes at 1.36 ns. The φ is ranged from 0° to 360° . The black and red solid lines in (c) and (d) are guides to the eyes.

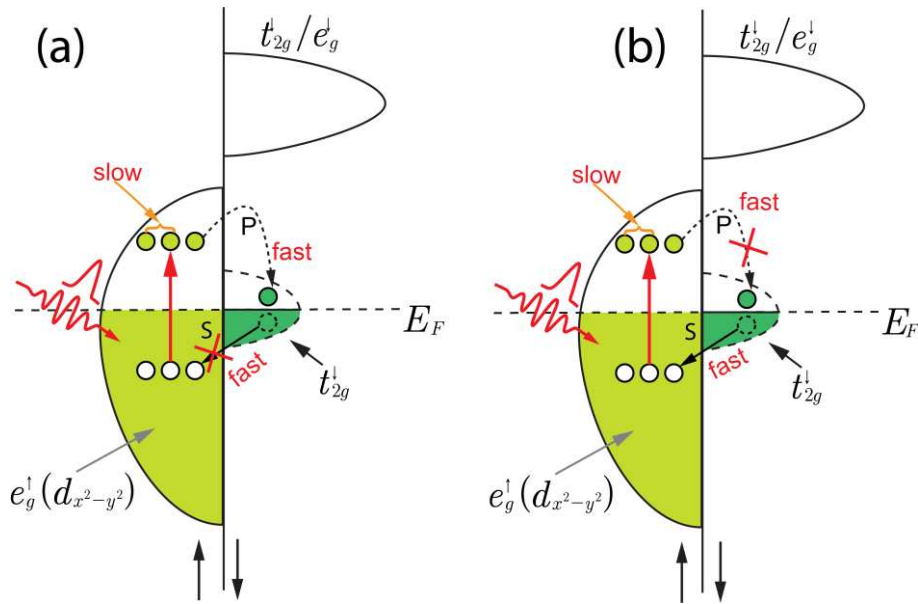


Figure 4. (a) The ultrafast magnetization decrease under p-polarized probe. The occupied and unoccupied minority spin density states (green and blank areas) are shown near the Fermi level E_F , which originates from the spin-orbit coupling. The cyan part below the Fermi level is e_g orbitals occupied by the majority spins. The red arrows mean the photoexcitation by 1.55 eV pump beam, generating non-equilibrium electrons and holes (cyan and blank circles respectively). The black dash arrow P represents that a part of the excited spin-up electrons is

1 scattered into the empty spin-down states. Note that the process S is switched off. (b) The
2 schematic process for magnetization increase. Under s-polarized probe, the process P is
3 blocked, while S (solid straight arrow) is switched on. The spin-down electrons in minority
4 electron bands recombine with the excited majority spin-up holes, leading to a transient
5 increase of the magnetism. In both (a) and (b), only a small amount of the excited carriers take
6 part in the fast spin-flip process while the remaining part is relaxed through the slow spin-
7 lattice channel.
8
9
10
11
12
13
14
15
16

17 Reference

- 18
19
20
21 [1] E. Beaurepaire, J. C. Merle, A. Daunois, J. Y. Bigot, *Phys. Rev. Lett.*
22 **1996**, *76*, 4250.
23
24 [2] J. Walowski, M. Münzenberg, *Journal of Applied Physics* **2016**, *120*,
25 140901.
26
27 [3] A. Stupakiewicz, K. Szerenos, D. Afanasiev, A. Kirilyuk, A. V. Kimel,
28 *Nature* **2017**, *542*, 71.
29
30 [4] Y. Xu, M. Deb, G. Malinowski, M. Hehn, W. Zhao, S. Mangin,
31 *Advanced Materials* **2017**, *29*, 1703474.
32
33 [5] N. Bergeard, M. Hehn, S. Mangin, G. Lengaigne, F. Montaigne, M. L.
34 M. Lalieu, B. Koopmans, G. Malinowski, *Phys. Rev. Lett.* **2016**, *117*,
35 147203.
36
37 [6] B. Koopmans, van Kampen M, J. T. Kohlhepp, W. J. M. de Jonge,
38 *Journal of Applied Physics* **2000**, *87*, 5070.
39
40 [7] E. Carpene, E. Mancini, C. Dallera, M. Brenna, E. Puppini, S. De
41 Silvestri, *Phys Rev B* **2008**, *78*, 174422.
42
43 [8] J.-H. Shim, A. Ali Syed, C.-H. Kim, K. M. Lee, S.-Y. Park, J.-R. Jeong,
44 D.-H. Kim, D. Eon Kim, *Nature Communications* **2017**, *8*, 796.
45
46 [9] T. Kise, T. Ogasawara, M. Ashida, Y. Tomioka, Y. Tokura, M. Kuwata-
47 Gonokami, *Phys. Rev. Lett.* **2000**, *85*, 1986.
48
49 [10] T. Ogasawara, K. Ohgushi, Y. Tomioka, K. S. Takahashi, H. Okamoto,
50 M. Kawasaki, Y. Tokura, *Phys. Rev. Lett.* **2005**, *94*, 087202.
51
52 [11] Q. Zhang, A. V. Nurmikko, G.-X. Miao, G. Xiao, A. Gupta, *Phys Rev B*
53 **2006**, *74*, 064414.
54
55 [12] G. M. Müller, J. Walowski, M. Djordjevic, G.-X. Miao, A. Gupta, A. V.
56 Ramos, K. Gehrke, V. Moshnyaga, K. Samwer, J. Schmalhorst, A.
57 Thomas, A. Hütten, G. Reiss, J. S. Moodera, M. Münzenberg, *Nat Mater*
58 **2009**, *8*, 56.
59
60 [13] B. Koopmans, J. J. M. Ruigrok, F. D. Longa, W. J. M. de Jonge, *Phys.*
61
62
63
64
65

- Rev. Lett.* **2005**, *95*, 267207.
- [14] M. Krauß, T. Roth, S. Alebrand, D. Steil, M. Cinchetti, M. Aeschlimann, H. C. Schneider, *Phys Rev B* **2009**, *80*, 180407.
- [15] A. J. Schellekens, W. Verhoeven, T. N. Vader, B. Koopmans, *Appl. Phys. Lett.* **2013**, *102*, 252408.
- [16] C. Illg, M. Haag, M. Fähnle, *Phys Rev B* **2013**, *88*, 152.
- [17] C. Boeglin, E. Beaupaire, V. Halté, V. López-Flores, C. Stamm, N. Pontius, H. A. Dürr, J. Y. Bigot, *Nature* **2010**, *465*, 458.
- [18] C. Stamm, T. Kachel, N. Pontius, R. Mitzner, T. Quast, K. Holldack, S. Khan, C. Lupulescu, E. F. Aziz, M. Wietstruk, H. A. Dürr, W. Eberhardt, *Nat Mater* **2007**, *6*, 740.
- [19] F. Li, C. Song, Y. D. Gu, M. S. Saleem, F. Pan, *Phys Rev B* **2017**, *96*, 245108.
- [20] F. Li, C. Song, B. Cui, J. Peng, Y. Gu, G. Wang, F. Pan, *Advanced Materials* **2017**, *29*, 1604052.
- [21] R.-W. Li, H. Wang, X. Wang, X. Z. Yu, Y. Matsui, Z.-H. Cheng, B.-G. Shen, E. W. Plummer, J. Zhang, *Proc Natl Acad Sci USA* **2009**, *106*, 14224.
- [22] P. Perna, D. Maccariello, F. Ajejas, R. Guerrero, L. Méchin, S. Flament, J. Santamaria, R. Miranda, J. Camarero, *Advanced Functional Materials* **2017**, *27*, 1700664.
- [23] J.-B. Yau, X. Hong, A. Posadas, C. H. Ahn, W. Gao, E. Altman, Y. Bason, L. Klein, M. Sidorov, Z. Krivokapic, *Journal of Applied Physics* **2007**, *102*, 103901.
- [24] L. Chen, S. Mankovsky, S. Wimmer, M. A. W. Schoen, H. S. Körner, M. Kronseder, D. Schuh, D. Bougeard, H. Ebert, D. Weiss, C. H. Back, *Nature Physics* **2018**, *26*, 1366.
- [25] W. Niu, M. Gao, X. Wang, F. Song, J. Du, X. Wang, Y. Xu, R. Zhang, *Scientific reports* **2016**, *6*, 26081.
- [26] W. Niu, X. Wang, M. Gao, Z. Xia, J. Du, Y. Nie, F. Song, Y. Xu, R. Zhang, *AIP Advances* **2016**, *7*, 056404.
- [27] A. M. Haghiri-Gosnet, J. P. Renard, *J Phys D Appl Phys* **2003**, *36*, R127.
- [28] M. Huijben, L. W. Martin, Y. H. Chu, M. B. Holcomb, P. Yu, G. Rijnders, D. H. A. Blank, R. Ramesh, *Phys Rev B* **2008**, *78*, 094413.
- [29] D. Pesquera, G. Herranz, A. Barla, E. Pellegrin, F. Bondino, E. Magnano, F. Sánchez, J. Fontcuberta, *Nature Communications* **2012**, *3*, 1189.
- [30] B. Wang, L. You, P. Ren, X. Yin, Y. Peng, Bin Xia, L. Wang, X. Yu, S. M. Poh, P. Yang, G. Yuan, L. Chen, A. Rusydi, J. Wang, *Nature Communications* **2013**, *4*, 2778.
- [31] H. Yada, M. Matsubara, H. Yamada, A. Sawa, H. Matsuzaki, H. Okamoto, *Phys Rev B* **2011**, *83*, 165408.
- [32] H. Yada, M. Matsubara, H. Matsuzaki, H. Yamada, A. Sawa, H.



- Okamoto, *Phys Rev B* **2011**, *84*, 045114.
- [33] M. Matsubara, A. Schroer, A. Schmehl, A. Melville, C. Becher, M. Trujillo-Martinez, D. G. Schlom, J. Mannhart, J. Kroha, M. Fiebig, *Nature Communications* **2015**, *6*, 6724.
- [34] T. Li, A. Patz, L. Mouchliadis, J. Yan, T. A. Lograsso, I. E. Perakis, J. Wang, *Nature* **2013**, *496*, 69.
- [35] S. Koshihara, A. Oiwa, M. Hirasawa, S. Katsumoto, Y. Iye, C. Urano, H. Takagi, H. Munekata, *Phys. Rev. Lett.* **1997**, *78*, 4617.
- [36] A. I. Lobad, R. D. Averitt, C. Kwon, A. J. Taylor, *Appl. Phys. Lett.* **2000**, *77*, 4025.
- [37] B. Koopmans, G. Malinowski, F. D. Longa, D. Steiauf, M. Fähnle, T. Roth, M. Cinchetti, M. Aeschlimann, *Nat Mater* **2009**, *9*, 259.
- [38] M. Buchner, P. Högl, S. Putz, M. Gmitra, S. Günther, M. A. W. Schoen, M. Kronseder, D. Schuh, D. Bougeard, J. Fabian, C. H. Back, *Phys. Rev. Lett.* **2016**, *117*, 565.
- [39] K. Carva, M. Battiato, P. M. Oppeneer, *Phys. Rev. Lett.* **2011**, *107*, 207201.
- [40] K. Leckron, S. Vollmar, H. C. Schneider, *Phys Rev B* **2017**, *96*, 140408.
- [41] Q. Qin, S. He, H. Wu, P. Yang, L. Liu, W. Song, S. J. Pennycook, J. Chen, *arXiv* **2018**, *cond-mat.mtrl-sci*.
- [42] T. Wakamura, F. Reale, P. Palczynski, S. Guéron, C. Mattevi, H. Bouchiat, *Phys. Rev. Lett.* **2018**, *120*, 106802.
- [43] L. A. Benítez, J. F. Sierra, W. Savero Torres, A. Arrighi, F. Bonell, M. V. Costache, S. O. Valenzuela, *Nature Physics* **2017**, *14*, 303.
- [44] C. Jozwiak, C.-H. Park, K. Gotlieb, C. Hwang, D.-H. Lee, S. G. Louie, J. D. Denlinger, C. R. Rotundu, R. J. Birgeneau, Z. Hussain, A. Lanzara, *Nature Physics* **2013**, *9*, 293.
- [45] C. Jozwiak, J. A. Sobota, K. Gotlieb, A. F. Kemper, C. R. Rotundu, R. J. Birgeneau, Z. Hussain, D.-H. Lee, Z.-X. Shen, A. Lanzara, *Nature Communications* **2016**, *7*, 13143.
- [46] B. Casals, R. Cichelero, P. García Fernández, J. Junquera, D. Pesquera, M. Campoy-Quiles, I. C. Infante, F. Sánchez, J. Fontcuberta, G. Herranz, *Phys. Rev. Lett.* **2016**, *117*, 026401.
- [47] S. Essert, H. C. Schneider, *Phys Rev B* **2011**, *84*, 224405.
- [48] B. Koopmans, H. H. J. E. Kicken, van Kampen M, W. J. M. de Jonge, *Journal of Magnetism and Magnetic Materials* **2005**, *286*, 271.
- [49] D. Steil, S. Alebrand, T. Roth, M. Krauß, T. Kubota, M. Oogane, Y. Ando, H. C. Schneider, M. Aeschlimann, M. Cinchetti, *Phys. Rev. Lett.* **2010**, *105*, 217202.
- [50] J.-P. Wüstenberg, D. Steil, S. Alebrand, T. Roth, M. Aeschlimann, M. Cinchetti, *physica status solidi (b)* **2011**, *248*, 2330.



[Click here to access/download](#)

Supporting Information



R2 Revised Supporting Information.docx






Click here to access/download



Production Data
Figure 1.tif





Click here to access/download



Production Data
Figure 2.tif





Click here to access/download

Production Data
Figure 3.tif





Click here to access/download

Production Data
Figure 4.tif

