

# Overview of porous media/metal foam application in fuel cells and solar power systems

Weng Cheong Tan<sup>a</sup>, Lip Huat Saw<sup>a\*</sup>, Hui San Thiam<sup>a</sup>, Jin Xuan<sup>b</sup>, Zuansi Cai<sup>c</sup>, Ming Chian Yew<sup>a</sup>

<sup>a</sup> Lee Kong Chian Faculty of Engineering and Science, UTAR, Kajang, Malaysia – 43000.

<sup>b</sup> Department of Chemical Engineering, Loughborough University, Loughborough, UK.

<sup>c</sup> School of Engineering and The Built Environment, Edinburgh Napier University, Edinburgh EH10 5DT, UK.

Phone: +603-90860288

Fax: +603-90197062

\*E-mail address: [sawlh@utar.edu.my](mailto:sawlh@utar.edu.my), [bernardsaw81@yahoo.com](mailto:bernardsaw81@yahoo.com)

## Abstract

Fuel cells and solar energy are promising candidates for electricity generation. It is forecast that fuel cells and solar power systems will play an important role in reducing the greenhouse gas footprint and replacing fossil fuels. Therefore, the limitations of fuel cells and solar power systems, such as low efficiency, high cost, and low reliability, must be addressed appropriately to enable their full potentials. Metal foam is a new class of material that has gained immense attention due to its excellent properties suitable for a wide range of applications. Its unique characteristics distinguish it from typical solid metals. The properties of metal foam can be modified during the fabrication stage by manipulating its physical structure. The goal of this paper is to review the application of metal foam in fuel cells and solar power systems. Besides, the performance of metal foam in fuel cells and solar systems is also discussed. Metal foam has been applied to the electrodes, gas diffusion layer and flow field of fuel cells to enhance performance, especially in regard to current density and flow distribution. Furthermore, metal foam is a heat exchanger for the solar energy harvesting system to improve its efficiency. Superior performances in experimental testing allows the possibility of commercialization of metal foam products in the renewable energy field.

Keywords: renewable energy; solar energy; clean energy; porous electrode; thermal  
management

**Word count: 14000**

## 1. Introduction

Renewable energy, such as solar, waves, geothermal and wind energy, is an energy source that will not be depleted. Using renewable energy can reduce the greenhouse gas footprint by minimizing the consumption of fossil fuels used for electricity generation. This is important to ensure a cleaner and greener environment. In addition, the European Union aims to cover full energy demands, using the renewable and sustainable energy system. This has motivated researchers to explore the application of the renewable energy field to help the European Union achieve the 100% renewable energy target [1]. However, renewable energy also faces challenges due to its low efficiency and high production cost with a low return on investment. Therefore, it is essential to reduce production costs and improve efficiency to promote renewable energy globally [2, 3].

Fuel cell is an electrochemical device to convert chemical energy into electrical energy. Unlike a battery, which stores the chemical energy within it, the fuel cell generates electrical energy from the chemical energy supplied at the anode and cathode. Depending on the types of fuel cells, the power density may vary with different types of reactants. Various types of fuel cells are available in the laboratory and market, such as Proton Exchange Membrane Fuel Cell (PEMFC), Microbial Fuel Cell (MFC), Phosphoric Acid Fuel Cell (PAFC), Solid Acid Fuel Cell (SAFC), Solid Oxide Fuel Cell (SOFC), Alkaline Fuel Cell (AFC), Direct Methanol Fuel Cell (DMFC), etc. The by-product of a fuel cell is environmentally friendly, which makes the fuel cell a preferable choice for the renewable energy system. The fuel cell market is growing worldwide, and by 2020, the stationary fuel cell market is expected to reach 50 GW [4]. To advance the commercialization of the fuel cell, different approaches have been taken to improve the existing fuel cell with the aim to reduce the cost and to improve performance through modification of the fuel cell components [5-7].

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
Solar energy is a permanent heat and light source that is emitted from the sun to the Earth. The Earth receives ~170 trillion kW of incoming solar radiation (insolation) at the upper atmosphere. Approximately, 47% of the energy reaches the Earth's surface. The rest is reflected back into space by clouds (~17%), absorbed by ozone, water vapor and dust (~19%), scattered by air molecules (~8%), absorbed by clouds (~4%), and reflected into space by the surface (~6%) [8, 9]. Solar energy is important because it is renewable energy that exists abundantly, is non-polluting and is free. The solar energy received by the Earth in one and a half hours (480 EJ) is more than the energy consumption in the year 2011 retrieved from all sources (430 EJ) [10]. Therefore, development of a solar energy harvesting system is an essential approach to promote globally renewable energy production and use to solve the issues of depletion of fossil fuels for electricity generation. Besides, solar energy can help combat global warming by reducing the dependency on fossil fuels, which emit harmful gases into the atmosphere.

31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
There are numerous solar energy harvesting systems available in the market, such as solar chimney, solar thermal energy storage, solar heater, concentrate photovoltaic, solar receiver/collector, solar pond, photovoltaic panel, etc. Low efficiency and high cost are key factors preventing the usage of solar energy harvesting systems abundantly in generating electricity. Hence, improvement of solar energy harvesting systems, such as improving the heat transfer or cooling performance, is crucial in promoting the application of solar energy harvesting systems in the worldwide market.

48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65  
Metal foam is a new class of material with excellent properties that can be applied in various applications [11]. Metal foam provides excellent mechanical properties and is lightweight, while maintaining high strength and rigidity. It also has excellent acoustic properties for sound absorption application. The complex geometry within the metal foam increases the surface area per unit volume. This is an ideal characteristic for heat transfer

1 application or thermal management applications, such as heat exchangers. By varying the  
2 characteristics of metal foam, such as permeability, pore size, pores per inch (PPI), etc., the  
3 metal foam can provide a unique interaction with the fluid that flows through it and results in  
4 different observations.  
5  
6  
7

8  
9 There are two classes of metal foam. The first type is open cell, while the second type is  
10 a closed cell. Open cell metal foam allows the fluid to flow freely through one cell to another,  
11 and the cells are not closed. The typical open cell metal foam structure is shown in Fig. 1.  
12 The closed-cell metal foam consists of continuous cell walls, which separate one cell from  
13 another with the formation of a discrete section. The geometry of the cell is usually spherical  
14 in shape [13]. Depending on the application, different characteristics of metal foam should be  
15 chosen to meet the design requirements.  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

26 In view of the above, metal foam can bring a new dimension in renewable energy  
27 application. For example, it has been used as a gas diffusion layer, electrode or flow field in  
28 fuel cells as well as heat transfer media in solar energy harvesting systems to improve  
29 efficiency and electrical performance. Metal foam, with its excellent thermal conductivity  
30 and high solid to fluid interfacial area that enhances fluid mixing, is an ideal heat transfer  
31 candidate for solar energy harvesting systems.  
32  
33  
34  
35  
36  
37  
38  
39  
40

41 Although there are many solar energy harvesting systems, not every system is suitable  
42 for metal foam. Solar chimneys, solar collectors/receivers, solar heat exchangers/heaters and  
43 thermal energy storage are solar energy harvesting systems that are appropriate for metal  
44 foam [14]. In addition, the cost of metal foam has been significantly reduced due to the  
45 advancement of manufacturing methods. For example, Alcoa (USA) introduced a new  
46 process to manufacture metal foam which could lead to the price of aluminum foam being as  
47 low as USD 5 per kg [11]. This new manufacturing process can greatly help to reduce the  
48 production cost, so the metal foam can be commercialized. Selection of metal foam for a  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 certain application is further simplified by standardization by the agency. This will further  
2 promote the application of metal foam in the renewable energy field.  
3

4 In this study, a critical review of applications of metal foam in fuel cells and solar energy  
5 harvesting systems is conducted, encompassing various types of metal foam application in  
6 fuel cells. This includes proton exchange membrane fuel cells, microbial fuel cells, direct  
7 methanol fuel cells, alkaline fuel cells and solid oxide fuel cells. Applications of metal foam  
8 in solar collectors and thermal energy storage systems are also discussed. This review not  
9 only aims to provide an overview of the performance of the metal foam in fuel cells and solar  
10 power systems, but also to provide useful insight into the future development of fuel cells and  
11 solar power systems using metal foam. In addition, the challenges associated with metal foam  
12 use in fuel cells and solar power systems are also covered in the discussion.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

## 26 **2. Methodology**

27 Despite metal foam having been used in fuel cells and solar power systems for a number  
28 of years, the understanding of the flow field and electrical and heat transfer characteristics in  
29 such systems is very limited. This is partly due to the complicated internal geometrical  
30 structure of (the strut) metal foam. As metal foam generally exhibits a random structure, it is  
31 very difficult to obtain a general correlation to describe the characteristics of this material.  
32 Numerous studies have suggested that metal foam is suitable for various applications in  
33 automotive, aerospace and electronics industries [11]. However, there are few comprehensive  
34 reviews of the application of metal foam in the renewable energy field, especially in fuel cells  
35 and solar cells.  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49

50 Hence, a review of the applications of metal foam in different components of the fuel cell  
51 system such as anode, cathode and gas diffusion layer is presented. This review not only  
52 explores the technological advantages and challenges of these applications, but also proposes  
53 approaches to overcome the limitations of these applications. In addition, key factors  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 affecting the performance of these applications are identified with critical discussions of  
2 future perspectives of metal foam in the individual components of fuel cells. In addition to  
3 the fuel cell system, the applications of metal foam as a heat sink in solar power systems are  
4 also reviewed. The performance of the metal foam in solar collectors and thermal energy  
5 storage systems is examined.  
6  
7  
8  
9  
10

### 11 **3. Fuel cell**

#### 12 **3.1 Proton Exchange Membrane Fuel Cell**

13  
14  
15  
16  
17 The Proton Exchange Membrane Fuel Cell (PEMFC) is one of the most famous types of  
18 fuel cell available in the market, also known as Polymer Electrolyte Membrane Fuel Cell.  
19 Compared to other types of fuel cells, the PEMFC offers several advantages, such as cost-  
20 effectiveness, high durability and high efficiency. The United States Department of Energy  
21 (DOE) recognized it as a potential candidate to replace the internal combustion engine in the  
22 transportation sector [14]. A PEMFC consists of bipolar plates (flow field), electrodes,  
23 catalyst, membrane and current collector as shown in Fig. 2.  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33

34 The PEMFC uses hydrogen as a reactant at the anode and consumes oxygen at the  
35 cathode to generate electricity. Both reactants are harmless and abundant in quantity and can  
36 be obtained through water electrolysis. The by-product of the PEMFC is water, which is  
37 clean and harmless. As illustrated in Fig. 2, an electron travels outside the circuit and  
38 generates electricity. The cation,  $H^+$ , travels through the membrane electrode assembly (MEA)  
39 and combines with the anion,  $O^{2-}$ , to produce water. The electrochemical equations at the  
40 anode and cathode are shown below:  
41  
42  
43  
44  
45  
46  
47  
48  
49



1 The bipolar plate is an important component of the fuel cell and contributes more than 70%  
2 of the fuel cell weight [16, 17], and more than 40% of the fuel cell's cost is attributed to it.  
3 Hence, research has been conducted on the bipolar plate to reduce its weight and improve its  
4 performance. The bipolar plate acts as the backbone of the PEMFC, current collectors and  
5 flow field for reactants. A graphite bipolar plate is commonly used in the PEMFC. Graphite  
6 is a material with good surface contact resistance and superior corrosion resistance. On the  
7 downside, the graphite bipolar plate demonstrates lower performance when compared to the  
8 metal foam bipolar plate [16-28]. It is also expensive and difficult to fabricate. The key  
9 characteristics of the bipolar plate were provided by Tawfik et al. [18]. An effective bipolar  
10 plate should have high corrosion resistance, low ohmic resistance, high surface tension of  
11 water, be lightweight, have high mechanical strength, be cost-effective, and not produce  
12 metal ions. Reddy and Kumar studied the application of metal foam as the flow field and  
13 compared it with conventionally used rectangular channels through numerical analysis [19].  
14 In the simulation, MEA, anode, and cathode were classified as flow domain with roughly 0.4  
15 million mesh sizes. Thermodynamics equations for the electrochemical reactions and  
16 equations for membrane properties were all defined with some assumptions made in the  
17 simulation. The SIMPLE algorithm was used to solve the momentum equations, continuity  
18 equations, species flux equations and transport equations. The study concluded that  
19 decreasing the permeability of metal foam resulted in an improvement in the fuel cell's  
20 electrical performance. The average current density is about 5943 A.m<sup>-2</sup> when the  
21 permeability is about 10<sup>-6</sup> m and increases to 8325 A.m<sup>-2</sup> when the permeability is reduced to  
22 10<sup>-11</sup> m. The simulation results agreed with experimental data from Kumar and Reddy in  
23 which the relationship between permeability and performance of fuel cells agreed  
24 qualitatively [20]. The experimental results showed that the improvement of the fuel cell was  
25 due to pressure drop increases across the flow field. Although lower permeability produced



1 better fuel performance, it is impossible to manufacture metal foam with a permeability lower  
2 than  $10^{-8}$  m because of the difficulty in machining such thin cross-sectional channels. The  
3  
4 improvement of permeability will remain limited until a new manufacturing process is  
5  
6 introduced.  
7

8  
9 To improve the role of metal foam on bipolar plates, other parameters are considered.  
10  
11 Afshari et al. studied the effects of channel depth and effect of metal foam porosity  
12  
13 numerically [21]. The current density increased with increasing metal foam porosity which,  
14  
15 however, induced a higher pressure drop. It was observed that the porosity of metal foam in  
16  
17 the range of 0.85 to 0.7 does not affect the temperature variation along the flow channel. This  
18  
19 phenomenon was corroborated by Hossain and Shabani's investigation [22].  
20  
21

22  
23 The design of the flow field of the bipolar plate is critical in determining the performance  
24  
25 of the fuel cell. Tsai et al. studied the effects of the design of the flow field by applying metal  
26  
27 foam as the flow distributor [23]. Five types of flow fields based on metal foam were  
28  
29 proposed and compared with the graphite bipolar plate. A metal foam flow distributor  
30  
31 performed better than a graphite bipolar plate. Performance can also be improved by using  
32  
33 multiple inlets and dividing metal foam into multiple regions. This can ensure better gas  
34  
35 distribution, which will enhance the performance further. In addition, different designs of  
36  
37 anode housing (flow field) using aluminum foam was proposed by Wilberforce et al. [24].  
38  
39 Flow plate designs were investigated numerically and they concluded that open pore cellular  
40  
41 foam performs better when compared to traditional fuel cell flow plate designs. The new  
42  
43 design reduces dead zones, which can lead to accumulation of water that affects fuel cell  
44  
45 performance.  
46  
47  
48  
49  
50  
51

52  
53 Carton and Olabi conducted a numerical simulation to study the flow distribution [25]. A  
54  
55 double channel flow plate was compared with a flow plate made from pore cellular foam  
56  
57 material. The results showed that the distribution of oxygen and hydrogen from the inlet to  
58  
59  
60  
61

1 outlet were more even when open pore cellular foam was used as flow plates. On the other  
2 side, the double channel fuel cell exhibited a poor distribution of reactants. Under the same  
3  
4 operating conditions, the current density of the foam flow plate surged by more than 55% at  
5  
6  
7 0.7 V compared to the double channel.  
8

9  
10 Tseng et al. investigated the effect of porosity, hydrophobic treatment and operating  
11 conditions of the metal foam flow field experimentally [26]. Metal foam performed better  
12 than the conventional graphite plate flow channel with a negligible corrosion problem.  
13  
14 Hossain and Shabani summarized the challenges of using metal foam in the PEMFC [22].  
15  
16 The challenges included corrosion of the metal body, which will lead to decreasing  
17 conductivity. It is believed that metal foam is a good candidate for the PEMFC, but more  
18 experimental data are needed to validate it. Besides, existing numerical models are not yet  
19 mature. Hence, an in-depth investigation of metal foam should be conducted to make use of  
20 its unique properties for fuel cell applications. Besides this, the corrosion issues of metal  
21 foam can be balanced by applying a layer of coating. Some common coatings used are noble  
22 metals, metal oxides, metal carbides and graphite [29-31].  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35

36 Temperature can affect the performance of a fuel cell. An optimum operating  
37 temperature is desirable to achieve a high-performance fuel cell. At low temperature, the rate  
38 of reactions of the fuel cell will be reduced and lead to performance losses, especially in  
39 current density. At high temperature, it will dry the membrane and reduce the ionic  
40 conductivity and the maximum theoretical voltage of a fuel cell will be affected.  
41  
42  
43  
44  
45  
46  
47

48 In winter, it is hard to start a fuel cell, especially when the ambient temperature is below  
49 0 °C at which temperature water freezes and causes a blockage on the cathode. It is vital to  
50 make sure the fuel cell maintains its function in winter, especially in automotive applications.  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 performance of metal foam for cathode flow distribution is better than that of the  
2 conventional parallel flow channel. Applying metal foam results in better gas flow and  
3 improved ice storage.  
4  
5

6  
7 The effect of high temperature on the PEMFC was investigated by Tseng et al. [28]. At  
8 high temperature, the water is not in a liquid state but in its steam phase. A fuel cell installed  
9 with metal foam performed 20% better than a graphite serpentine flow field plate at high  
10 temperature. A high temperature PEMFC (HT-PEMFC) offers benefits of higher  
11 electrochemical kinetics on the catalyst, faster rate of reaction, improved external thermal  
12 management, simplified internal water-management, and no water flooding.  
13  
14  
15  
16  
17  
18  
19  
20

21 A study of the PEMFC thermal management system was conducted by Odabae et al.  
22 experimentally [32] and Afshari et al. numerically [33]. Odabae et al. used a metal foam  
23 heat exchanger as the thermal management system for the PEMFC [32]. The water cooling  
24 system of the fuel cell was replaced with an air cooling system using aluminum metal foam.  
25 Compared to a water-cooled fuel cell system, only half of the pumping power was required  
26 for the aluminum foam to remove the same heat under the same operating conditions. Besides,  
27 the air-cooled metal foam generated more uniform temperature distribution within the  
28 graphite plate. Afshari et al. inserted cooling plates (bipolar plates) within the PEMFC stack  
29 and concluded that metal foam is able to maintain temperature uniformity with a low pressure  
30 drop [33]. This is mainly contributed by the high permeability coefficient of metal foam.  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45

46 Water management is essential to ensure smooth operation of the PEMFC. Too little  
47 water will reduce the membrane's durability and lead to poor electrode adhesion on the  
48 membrane, while too much water will cause flooding at the cathode gas diffusion layer  
49 (GDL). Balancing the water content in the PEMFC is important for its operation [34]. Three  
50 main problems yet to be resolved in a conventional PEMFC membrane humidifier are the  
51 cost of machining, disturbance of water diffusion under the ribs of the channel plates, and  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 additional weight and volume imposed on the channel. The above-mentioned problems can  
2 be solved by applying metal foam [35]. Using metal foam on both sides (wet and dry) can  
3 enhance performance. However, there is no improvement when using metal foam on the dry  
4 side. Besides this, lightweight metal foams can reduce the mass and provide a high surface to  
5 volume ratio that can enhance the reaction sites, which further improves the flow distribution.  
6  
7




8  
9  
10  
11 An Air-breathing PEM fuel cell (ABPEM) is a new type of PEMFC, with the cathode  
12 side open to the atmosphere. The absorption of oxygen by the cathode is mainly based on the  
13 convection from its surroundings. Since it does not require an extra component to supply  
14 oxygen to the cathode, it is simpler compared to a pressurized air PEM (PAPEM). Its  
15 lightness and simple design are ideal for portability. However, it performed poorly with only  
16 350 mW.cm<sup>-2</sup> of power density produced compared to PAPEM with 566 mW.cm<sup>-2</sup> [36]. To  
17 improve its efficiency, the idea to apply open pore cellular foam on the anode and cathode  
18 sides was proposed by Baroutaji et al. [37]. The findings concluded that the ABPEM has a  
19 weakness in the form of a water management problem, which can be solved by coating the  
20 PTFE on the metal foam. Compared to the work done by Jeong et al. [38], application of  
21 metal foam on the ABPEM exhibited a 77% increment of performance as compared to the  
22 conventional flow distributor ABPEM using a graphite flow field.  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40

41 In summary, metal foam is widely used in the PEMFC. It can be used on various  
42 components of a fuel cell to optimize the fuel cell performance, such as GDL, thermal  
43 management system, bipolar plate, flow distributor, etc. Although metal foam brings  
44 tremendous advantages to the fuel cell, it is also associated with disadvantages, such as  
45 corrosion, hydrophobicity, and pressure drop. Future studies to address these problems are  
46 needed.  
47  
48  
49  
50  
51  
52  
53  
54  
55

### 56 **3.2 Direct Methanol Fuel Cell**

57  
58  
59  
60  
61  
62  
63  
64  
65

1 The Direct Methanol Fuel Cell (DMFC) uses methanol as a reagent on the anode. It is  
2 well-known for its portability because methanol is in its liquid state at room temperature and  
3 its structure is simpler compared to other types of fuel cells. Although the DMFC offers  
4 higher power and energy density, the efficiency is low compared to the PEMFC. Since the  
5 DMFC is made for portability, it is lightweight. Various methods have been proposed for the  
6 DMFC, such as air-breathing and passive methanol solution supply. These designs can  
7 eliminate the parasitic power losses, as it does not require the powering of ancillary devices  
8 [39]. The operating process and structure of the DMFC are shown in Fig. 3. Electrochemical  
9 equations for the DMFC are shown in Eqs. (4) to (6).  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20



30 One drawback of the DMFC is that the methanol used in the anode contains water and  
31 methanol, which will reduce the power density of the fuel cell. Using a high concentration of  
32 methanol at the anode will cause fuel cross-over. Cross-over occurs when highly  
33 concentrated methanol diffuses through the membrane to the cathode and rapidly consumes  
34 the oxygen. Less than 30% of chemical energy in methanol can be converted to electrical  
35 energy, while the rest of the energy is converted to heat due to this phenomenon [41]. As a  
36 consequence, it is impossible to use pure methanol at the anode using current technology.  
37 Low concentration helps to hinder the diffusion rate (reduce methanol crossover) but also  
38 reduces the power density. Therefore, there should be a balance between concentrations of  
39 methanol to optimize the performance of the DMFC.  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53

54 The flow field is important in the DMFC, because it helps in methanol distribution at the  
55 anode, and oxygen distribution at the cathode. As discussed, metal foam is a suitable  
56 candidate to replace graphite bipolar plates in the PEMFC. This is also applied to the DMFC  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 [42-44]. Arisetty et al. examined the performance of the DMFC using metal foam as the flow  
2 field [42]. The factors to be considered are pore size and density of the metal foam. To  
3  
4 maintain the accuracy and consistency of the experiment, the operating condition was strictly  
5 controlled. The operating temperature was maintained at 50 °C with a constant airflow rate of  
6  
7 400 cm<sup>3</sup>.min<sup>-1</sup>. The back pressure was kept at 1 bar. A methanol solution of 2M was used and  
8  
9 heated to 50 °C before injection into the fuel cell. Deionized water was used to flush the fuel  
10  
11 cell after every experiment testing to remove any residue left in the fuel cell for 15 minutes.  
12  
13 Increasing the pore per inch (PPI) and the density of metal foam resulted in better  
14  
15 performance, especially in current density and electrical conductivity. There will always be  
16  
17 an obvious increase in performance when compared to a serpentine flow field. Similar to the  
18  
19 PEMFC, the effect of corrosion is unavoidable. After 40 hours of operation, there was  
20  
21 significant metal corrosion present in the fuel cell. A nickel coating was suggested for the  
22  
23 metal foam to resist corrosion.  
24  
25  
26  
27  
28  
29  
30

31 The GDL is important to ensure the fuel cell's performance by preventing flooding,  
32 maintaining humidity and ensuring an even distribution of reactants over the electrode  
33  
34 surface. The feasibility of using metal foam as the GDL was also explored and the results  
35  
36 showed an improvement compared to cloth and metal mesh [42]. The idea to eliminate the  
37  
38 GDL was proposed by Chen and Zhao to reduce the weight of the DMFC [45]. New MEA  
39  
40 was suggested by eliminating the cathode GDL and replacing it with Ni-Cr alloy metal foam  
41  
42 for transporting oxygen, thereby acting as a current collector. When compared to  
43  
44 conventional MEA, this new MEA exhibited better performance and proved that application  
45  
46 of metal foam in fuel cells is worth investing in.  
47  
48  
49  
50  
51  
52

53 Chen and Zhao also studied the possibility of using porous current collectors in passive  
54  
55 DMFCs experimentally [39]. Ni-Cr alloy metal foam current collectors used in the passive  
56  
57 DMFC performed better than the perforate-plate current collector. Besides this, it was more  
58  
59  
60  
61  
62  
63  
64  
65

1 stable and more lightweight. Yan et al. replaced the conventional anode collector with a  
2 micro-porous anode current collector and experimented with it to investigate its performance  
3 [46]. This method can greatly reduce the effect of methanol crossover and allows more  
4 concentrated methanol to be fed to the anode. The experimental results showed that 22M  
5 methanol can generate a power capacity of  $41.4 \text{ mW cm}^{-2}$ , which is 35% higher than that of  
6 the conventional DMFC.  
7

8  
9  
10  
11  
12  
13  
14 Huang et al. studied the effect of using an anode porous catalyst layer (CL) and anode  
15 porous micro-porous layer (MPL) [47]. The porous CL and porous MPL were prepared using  
16 magnesium oxide as a sacrificial pore-former and varied with the percentage of magnesium  
17 oxide to produce a CL and MPL with different porosities. The findings concluded that the  
18 highest performance was achieved by the DMFC with a porous CL and MPL followed by the  
19 DMFC with a porous CL and the conventional DMFC. The results of the fuel cell impedance  
20 were in the opposite sequence. This proved that porous material in a CL and MPL can greatly  
21 enhance the performance of the DMFC, by increasing the catalyst utilization with a larger  
22 electrochemical surface area and reduce the charge-transfer resistance. Besides this, fuel cell  
23 performance was affected by the percentage of magnesium oxide as a pore-forming agent.  
24 When the percentage of MgO was increased from 0% to 20%, the peak power density  
25 improved from  $30 \text{ mW cm}^{-2}$  to  $36 \text{ mW cm}^{-2}$ . In addition to the anode CL, the cathode CL also  
26 plays a role in fuel cell performance. The effect of the porosity of the cathode CL was  
27 investigated by Lee et al. [48]. The porosity effect in the cathode CL contributed to the  
28 increment of fuel cell performance by 55.5%, which is 11% greater than the effect of using a  
29 porous anode CL. This showed that the porosity effect is greater at the cathode and weaker at  
30 the anode. This is due to the pores in the cathode CL being more capable of removing water  
31 from the electrode and preventing flooding.  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 Similar to the PEMFC, metal foam showed a positive impact when applied on the DMFC.  
2 It can be used in the CL, MPL, current collector, MEA and GDL of a DMFC. The  
3 development of metal foam on the DMFC should be continued, so the technology becomes  
4 more mature and can be commercialized, especially for portable application. It may replace  
5 the rechargeable battery due to a 5- to 10-fold improvement in energy density and having a  
6 longer cycle life [41]. The issues of methanol crossover and corrosion have yet to be resolved.  
7 Furthermore, using metal foam in MEA shows larger impedance, which is also an issue to be  
8 tackled so that cell performance can be enhanced [45].

### 19 **3.3 Microbial Fuel Cell**

21 The Microbial Fuel Cell (MFC) generate electricity by the aid of exoelectrogenic  
22 bacteria found in various ecological niches. Bacteria can remove organic matter from  
23 wastewater through anaerobic respiration and release electrons for electricity generation. The  
24 efficiency of the power generation depends on the type of MFC. For example, using oxidative  
25 phosphorylation can yield about 65% energy efficiency [49], while the potential efficiency is  
26 about 59% with a high current for acetate [50]. Many advantages are associated with the  
27 MFC, such as high conversion efficiency by direct conversion of substrate energy to  
28 electricity, does not require further gas treatment of by-products, and does not require energy  
29 input for aeration given that the cathode is passively aerated and the MFC can operate at  
30 ambient or low temperatures efficiently [51]. The energy recovery rate from municipal liquid  
31 waste fraction can be improved through three stages of treatment but still requires further  
32 studies for better performance [52]. However, the MFC is limited by cost, high activation loss  
33 [53] and limited power density [54]. Factors that affect the performance of the MFC are the  
34 oxidation of substrates in an anode, permeability of PEM, and supply and consumption of  
35 oxygen in the cathode chamber. Besides, transfer of electrons from the anode compartment to  
36 anode surface is also another factor that affects the performance of the MFC [55]. To date,  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1 the main application of the MFC is still limited to laboratory-scale devices. It is proposed that  
2 the MFC can be used in applications, such as biosensors, biohydrogen production [56],  
3 bioelectricity generation and wastewater treatment [57].  
4

5  
6  
7 Construction of the MFC is illustrated in Fig. 4, and it shows that bacteria tend to stick to  
8 the anode electrode and oxidation takes place to release electrons and hydrogen ion. The  
9 electrochemical equations of the MFC are rather complicated because of different  
10 microorganisms at the anode and electron acceptors at the cathode. The byproducts of the  
11 MFC reactions are water and carbon dioxide.  
12  
13  
14  
15  
16  
17  
18

19 Some common bacteria and corresponding substrate used in the MFC are shown in Table  
20  
21  
22 1. Types of substrates used with the corresponding power density are shown in Table 2. By  
23 varying the type of substrate and microbes, different power densities can be achieved.  
24  
25  
26

27 MFC-derived bioelectrochemical cells, in particular MECs (Microbial Electrolysis Cells)  
28 were reviewed by Kumar et al. [61]. A guideline was provided to develop a microbial  
29 electrochemical cell. The startup time should be kept as low as possible. The performance of  
30 the MFC can be affected by anode potential, concentration of substrate, operating  
31 temperature and material of electrodes. Besides, Kook et al. studied the feasibility of  
32 replacing commonly used Nafion membrane with supported ionic liquid membrane (SILM)  
33 [62, 63]. The findings concluded that the energy yield can be improved in a MFC because  
34 SILM has low electrical resistivity. This suggests that metal foam with low electrical  
35 resistivity is an ideal candidate to apply on the MFC.  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

48 Although many studies have been conducted to modify the anode to improve  
49 performance such as carbon nanotube, stainless steel, nanocomposite metal oxide, conducting  
50 polymer and graphite-based material used for anode modification, there is a lack of studies  
51 using metal foam at an anode. Using metal foam at an anode aims to provide a higher specific  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 surface area and increase the coverage for attachment of bacteria, which can aid to increase  
2 performance.  
3

4 Yang et al. investigated the effect of different types of metallic anode on performance  
5 [64]. The results showed that the conductivity of the anode is closely related to MFC  
6 performance. Increasing the porosity will reduce the conductivity and cause lower power  
7 performance. Hence, high porosity metal foam is not desired for the MFC. However, the  
8 limitation of using metal foam can be curbed by modifying it, as shown in the work done by  
9 Karthikeyan et al. [65]. Different types of anodes were used and compared with unmodified  
10 nickel foam. The observation proved that modified nickel foam has lower ohmic resistance  
11 than unmodified one. It was suggested that the electrode used in the MFC should have  
12 characteristics such as good electrical conductivity, low resistance, anti-corrosion, chemical  
13 stability, large surface area, high biocompatibility, and good mechanical strength and  
14 toughness for better performance [66]. From the suggested characteristics, metal foam  
15 possesses a high surface area to volume ratio, good mechanical properties, high current  
16 conductivity and low resistance, which make it suitable for the electrodes.  
17  
18

19 Jiang et al. used macroporous graphite carbon foam (MGCF) as an anode to increase the  
20 surface area and polydopamine (PDA) was coated on the MGCF to improve the  
21 biocompatibility [67]. The MFC then underwent the test to determine its performance. The  
22 findings showed that the MFC with the MGCF-PDA showed the highest performance, which  
23 yielded a power density of  $1735 \text{ mW.cm}^{-2}$  compared to the MGCF with the power density of  
24  $784 \text{ mW.cm}^{-2}$  and conventional carbon foam with the power density of  $258 \text{ mW.cm}^{-2}$ . The  
25 improvement was about 220% and 672% for the MFC with the MGCF-PDA and the MFC  
26 with the MGCF, respectively. This is because the MGCF provides a higher surface area for  
27 bacteria attachment, while the PDA is a coating that enhances the hydrophilicity which can  
28 further promote bacteria attachment. These two factors greatly improved the performance of  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 the MFC. The feasibility of using graphene foam as an anode was also investigated. It was  
2 found that a graphene foam anode has increased electrochemical interactions and results in  
3 reducing bio-convertible substrate consumption, while maintaining a short response time [68].  
4 This is in agreement with the work by Kwok et al. who made the observation that the flow-  
5 through design is better than the flow-over design for a MFC with graphene aerogel as a  
6 porous electrode [69].  
7  
8  
9  
10  
11  
12  
13


14 Cheng and Wu investigated the performance of an air cathode MFC when using nickel  
15 foam as the current collector, PTFE as the binder and carbon as the catalyst [70]. Linear  
16 sweep voltammetry (LSV) was used to evaluate the performance of the fuel cell. From the  
17 result, a nickel foam cathode can produce current and power density about 11% and 22%  
18 higher than that of a carbon cloth cathode. This is attributed to the fact that nickel foam has  
19 lower ohmic resistance due to its highly porous structure. The internal resistance of nickel  
20 foam is 85  $\Omega$  while that of carbon cloth is 109  $\Omega$ . However, a platinum cathode still  
21 outperformed nickel foam when it was used as a current collector with the power density of  
22 1320  $\text{mW}\cdot\text{cm}^{-2}$  versus  $1190 \pm 50 \text{ mW}\cdot\text{cm}^{-2}$ . On the bright side, nickel foam is only 1/30 of the  
23 cost of the platinum cathode, which is very attractive for mass production.  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38

39 The investigation of metal foam application on the MFC is still in its premature stage  
40 with limited experimental results [71]. Hence, it required a long time to commercialize the  
41 MFC. Although attempts have been made to achieve large application of the MFC, the results  
42 are not promising [72]. The start-up time is too long and the electrodes are prone to  
43 degradation and corrosion. Therefore, this provides a useful insight to promote the research in  
44 this area. The enhancement of the conductivity of the porous electrode is needed to improve  
45 the performance of the MFC. Replacing carbon cloth as the current collector with nickel  
46 mesh or stainless-steel mesh achieved a cost reduction, yet was able to produce a high power  
47 density [73, 74].  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

### 3.4 Solid Oxide Fuel Cell

The Solid Oxide Fuel Cell (SOFC) is an attractive fuel cell that yields energy with high efficiency using hydrogen, hydrocarbon, syngas and biofuel without producing harmful by-products. It can reach an efficiency as high as 60% [75] and over 80% [76] if cogeneration of waste heat is carried out. Due to its flexibility of fuel feed, it can be used in various stationary or mobile applications, such as auxiliary power units, combined heat and power units and portable power sources [77]. The structure of the SOFC consists of anode, solid electrolyte and cathode as shown in Fig. 5. The structure of the SOFC may look simple, but it is very complicated to ensure the high efficiency of a SOFC. Various components, such as current collector, bi-layer electrode and interface layer, are crucial to ensure its efficiency. The materials used and manufacturing methods of the components are keys factor in determining the efficiency of the fuel cell. Similar to other types of fuel cell, the SOFC can be stacked together to increase the electricity output. However, based on the study by Hiraiwa et al. [79], the power output of a single cell in a stack cell will reduce to 70% when compared to a single cell's performance with the variation of  $\pm 3\%$ . A stack fuel cell will suffer losses but prefers to be stacked together to produce a higher power output. Fig. 6 illustrates the construction of a SOFC stack. The electrochemical equations for the SOFC are listed below [78]:

Anode reaction :



Cathode reaction:



Although the SOFC offers a promising prospect for replacing fossil fuels for electricity generation, it remains limited due to some drawbacks. The main disadvantages are its high

1 operating temperature and cost. It usually needs to be operated within the temperature range  
2 between 800 °C and 1000 °C, which can greatly affect the reliability and durability of the fuel  
3 cell due to the failure of materials. Hence, material selection is vital to ensure fuel cell  
4 performance and lifetime. The cost of the SOFC is attributed to the material, manufacturing  
5 process and operating condition. The SOFC also suffers from sulfur poisoning [81], corrosion  
6 issues [82], and coking [81, 83], which further hinders its applications. The recent trend is to  
7 focus on developing a SOFC that can operate at low temperature and the introduction of new  
8 materials to improve performance, durability, reliability and cost.  
9

10 The feasibility study of using nickel foam as anode material was conducted by Arshad et  
11 al. [84]. The experiment was performed using three types of electrolytes with and without the  
12 presence of nickel foam as an anode. All three cases tested showed nickel foam as an anode  
13 produced higher power density than fuel cells without nickel foam as an anode. The peak  
14 power density was recorded at 411 mW.cm<sup>-2</sup> using samarium doped ceria (SDC) as  
15 electrolyte and nickel foam as an anode. This proved that nickel support is a good approach  
16 to enhance fuel cell performance. Zeng et al. investigated the effects of anode porosity for the  
17 SOFC [85]. The CFD approach based on FEM is used to study the effects of porosity on  
18 thermal stress, temperature, and polarization. The investigation results suggested that it is  
19 important to control the porosity as it can cause an improvement by eliminating stress in the  
20 electrodes. Increasing porosity will reduce the von Mises stress along the main flow direction,  
21 increase the polarization of the anode and improve the diffusion coefficient.  
22

23 The latest generation of the SOFC is called the metal supported cell (MSC) and the metal  
24 foam is important in determining performance. The MSC can provide excellent mechanical  
25 support to the fuel cell with a fast startup at a lower cost. However, it performs poorer than an  
26 anode supported cell (ASC) in regard to power density. The EVOLVE fuel cell is a project  
27 aimed to develop a new structure for the SOFC with a high power density. In 2013, a SOFC  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 with NiCrAl metal foam as metal support impregnated with La-doped strontium titanate (LST)  
2 with yttria-stabilized-zirconia (YSZ) as the electrolyte was developed [76]. In 2014, an anode  
3 functional layer made of gadolinium-doped ceria LST-GDC was laminated on NiCrAl metal  
4 foam and tested as a fuel cell [75]. The power density reached  $20 \text{ mW.cm}^{-2}$  [86]. The  
5 improvement was followed by optimization of the microstructure. In 2015, the fuel cell was  
6 tested with open circuit voltage measured at 0.97 V at the temperature of 750 °C, which was  
7 lower than the theoretical Nernst Potential [87]. The power density produced at 750 °C and  
8 0.7 V using lanthanum strontium cobalt ferrite (LSCF)-CGO as a composite cathode with the  
9 mixture of H<sub>2</sub> and N<sub>2</sub> as fuel was  $80 \text{ mW.cm}^{-2}$ . The result was not promising and further  
10 enhancement was conducted. It was predicted that pore size and thickness of NiCrAl-LST  
11 affected the performance, and further tuning of the microstructure was carried out. The latest  
12 update from the project was Jan 31<sup>st</sup>, 2017; the power density generated by the single fuel cell  
13 was  $170 \text{ mW.cm}^{-2}$  at 0.7 V and 750 °C [88]. This marked the end of the project. Gondolini et  
14 al. studied the feasibility of using NiCrAl metal foam as metal support for the SOFC but  
15 integrated it with nickel-gadolinium-doped-ceria (Ni-GDC) [89]. The porosity of the NiCrAl  
16 metal foam was about 80% to ensure high permeability for the gas diffusion while  
17 maintaining adequate mechanical stability of the system. Besides this, the presence of  
18 aluminum in the foam can increase the oxidation resistance by forming aluminum oxide,  
19 which improves the durability of the fuel cell.  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45

46 Understanding the microstructure of porous metal is important to determine its  
47 characteristics before applying it to the fuel cell. Masson studied the morphological modeling  
48 of the metal foam supported the SOFC configuration [90]. A 3D model was developed to  
49 estimate the transport properties, such as volume fraction of the phases, gas permeation, ionic  
50 conductivity and 3D tortuosity. The model developed was based on Pluri-Gaussian and SEM  
51 imaging. This work provided a useful insight into the effect of microstructure on the transport  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 properties. Maznoy et al. synthesized porous nickel-aluminum (Ni-Al) for the MSC  
2 application through a combustion synthesis route [91]. It was suggested that the size of  
3 powdered reagent was an important factor to determine the porosity and pore size of the final  
4 product. Combustion synthesis produced a porous Ni-Al plate, which was suitable to be used  
5 as a support substrate of the SOFC. The absence of chromium in the metal foam composition  
6 was to eliminate chromium poisoning, which may eventually cause degradation to the fuel  
7 cell [92]. Maznoy et al. concluded that porous Ni-Al can be a good support in the MSC after  
8 examining the effect of porosity parameters, mechanical properties and gas permeability of  
9 the synthesized material [91]. The usage of the porous Ni-Al alloy as metal support was also  
10 supported by other studies [93-95]. At 700 °C with humid hydrogen as fuel fed to the anode,  
11 a SOFC with deformation strengthened Ni-Al alloy foam as metal support could achieve a  
12 power density of 500 mW.cm<sup>-2</sup> [93]. In addition, the power density yielded by a SOFC with  
13 compressed Ni-Al alloy foam as metal support was 550 mW.cm<sup>-2</sup> under the same operating  
14 conditions [94]. Meanwhile, the power density could reach 400 mW.cm<sup>-2</sup> at 800 °C when the  
15 porous Ni-Al metal support was fabricated using self-propagating high-temperature synthesis  
16 [95]. The differences in power density obtained were explained by the different porous metal  
17 structure and different types of anode material, electrolyte and cathode.

18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41 Even though the MSC has significant advantages, it also creates a new problem for fuel  
42 cell design. The high-temperature corrosion rate of porous metal is strongly affected by the  
43 porosity level. Besides, high temperature will lead to the formation of oxide scale and  
44 increase specific area resistance. It was also found that electrical resistance is influenced by  
45 the porosity of the porous metal [96]. Hence, it is important to solve the corrosion issues in  
46 porous metal. Stange et al. studied the corrosion properties of porous alloy support for the  
47 SOFC and proposed a new method to overcome the corrosion [82]. Chromium poisoning  
48 happens when the chromium in the alloy diffuses and reacts with oxygen to form chromium  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

oxide. This will reduce the electrical conductivity and cause degradation of the fuel cell. Pre-coating and post-coating have been proposed to enhance the resistance of metal support to oxidation and chromium poisoning. Coating of La (Mn<sub>0.5</sub>Co<sub>0.5</sub>)<sub>0.8</sub> on the porous metal will increase conductivity, improve oxidation resistance and reduce chromium poisoning to enhance performance. Introducing manganese in the coating enhances corrosive resistance [97]. Creep of the porous metal support is another issue associated with the fuel cell that needs to be solved. Good creep resistance is needed to avoid electrolyte bending and thermal stress in the fuel cell [98]. Creep will gradually generate cracks in the electrolytes and finally cause degradation of stack integrity and result in fuel cell failure. Esposito et al. proposed an understanding of the secondary creep in the porous metal supports by developing a model using the continuum damage mechanics approach [99]. The oxide layer will significantly affect the creep behavior of the porous metal, and oxidation resistance is important. The model developed was able to estimate the time to rupture in a diffusional creep regime at low stress.

Metal foam is also used in the current collector of a SOFC. Nickel metal foam is commonly used as a current collector in the SOFC [79, 83, 100-102]. The applicability of nickel-based porous metal as the current collector was studied by Hiraiwa et al. [79, 100]. It was found that Ni-10Sn porous metal exhibits a lower area-specific resistance of 0.017 Ω.cm<sup>-2</sup> than pure nickel porous metal after 1,000 hours of heat treatment. Nickel-tin (Ni-Sn) porous metal produces the power density of 107 mW.cm<sup>-2</sup>, comparable to platinum mesh. This is an attractive result, as it can replace platinum mesh in the SOFC, which is otherwise costly. The cost can be further reduced without compromising performance. Using Ni-Sn porous material can reduce the operating temperature to below 600 °C, which is very promising for mobile application. The performance remains stable after 1,000 hours due to its excellent gas diffusion and current collecting ability. 10 wt% of Sn within the nickel porous metal is the



1 ideal composition that gives the best performance. Pure nickel metal foam is not attractive  
2 due to its high area-specific resistance and is prone to oxidation, which causes degradation of  
3 the fuel cell.  
4  
5

6  
7 However, applying nickel metal foam is still feasible if the appropriate coating is used on  
8 the nickel foam. For example, nickel-phosphorus coated nickel foam on the current collector  
9 is coke resistant [83]. Nickel-phosphorus was coated onto nickel foam through electroless  
10 plating. This process involved submerging the nickel foam samples into the plating solution.  
11 Next, the bubbles that formed in the foam were removed by evacuating the sample for 5  
12 minutes. The process was continued by heating the solution to 85 °C in a water bath and it  
13 was held for 10 to 30 minutes during the plating process. Last, deionized water was used to  
14 rinse the plated samples and left to dry in a stream of air. When testing under a syngas  
15 environment, it was found that plated nickel foam exhibited high carbon deposition resistance  
16 and remained stable when the coating contained more than 6.5 wt% of phosphorus. However,  
17 there was about a 247% weight gain in pure nickel foam, indicating the formation of carbon  
18 on its surface. This is because hydrogen sulfide (H<sub>2</sub>S) in syngas can poison nickel by forming  
19 nickel sulfide [103]. This greatly reduces fuel cell performance in the long term. When  
20 comparing plated nickel foam with uncoated nickel foam, both cells generate power densities  
21 of more than 900 mW.cm<sup>-2</sup>, indicating that both nickel foams can perform well. Plated nickel  
22 foam has an advantage, which is coke resistance.  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45

46 The performance of plated nickel foam is comparable to gold mesh as a current collector.  
47 It is suggested that nickel-phosphorus-coated nickel foam is an ideal candidate for the current  
48 collector. Copper is also an attractive coating solution for nickel foam [101]. Copper surface-  
49 modified nickel foam was prepared in such way that copper-coated nickel foam was heated  
50 while maintaining the weight ratio of copper and nickel in a reducing atmosphere [97]. The  
51 copper and nickel ratio was 1:2. The surface-modified nickel possessed higher coking  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 resistance and mechanical stability when compared to unmodified nickel foam. The power  
2 density was 10% higher than that of the gold mesh current collector in a syngas-fed SOFC.  
3  
4 The work was continued by Low et al. in which the composition of copper/nickel was  
5 changed to 2.5 using electrochemical plating [81]. Observations of carbon deposition were  
6 the same as in the work discussed previously, but the effect of the composition of copper and  
7 nickel on the resistance was not discussed in both papers. However, it is believed that a high  
8 copper/nickel ratio is necessary to improve the resistance to carbon deposition.  
9  
10  
11  
12  
13  
14  
15

16 Although copper offers more advantages as a current collector, it cannot be used in a  
17 high-temperature SOFC because copper has a low melting point, is structurally unstable at  
18 high temperature and ductile [104]. Copper will lose its electrode conductivity at a  
19 temperature higher than 1073 K. This explains why nickel will always remain the preferred  
20 choice. It is also difficult to ensure a uniform thickness of copper deposited in highly porous  
21 nickel foam.  
22  
23  
24  
25  
26  
27  
28  
29  
30

31 Electrodes are important components of the SOFC. They are used for electrochemical  
32 reaction sites and facilitate gas diffusion. The most commonly used materials for anode  
33 electrodes include Ni-YSZ cement anode, fluorite anode, perovskite anode, tungsten bronze  
34 anode and pyrochlore anode materials [78, 105]. Some of the commonly used materials for  
35 cathode electrodes include perovskite, lanthanum cobaltite and ferrite, ferro-cobaltite,  
36 lanthanum manganite, nickelate and  $K_2NiF_4$  [106]. A porous electrode can increase reaction  
37 sites due to high porosity with a large surface area. The porous structure also enables faster  
38 and even gas diffusion, which improves the performance of a SOFC.  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51 The application of metal foam on the electrode is still not popular nowadays. Williford  
52 and Chick studied the diffusion limitation in a porous anode [107]. It was suggested that  
53 optimization of the surface diffusion, reactive area and adsorption at the electrolyte/anode is  
54 important in determining the maximum power density of a SOFC. This can greatly enhance  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 the concentration polarization and promote a triple phase boundary. Evaluation of various  
2 electrode materials for low-temperature SOFCs was conducted by Jung et al. [102]. The  
3 performance of lanthanum strontium cobaltite (LCS), porous platinum and porous nickel  
4 were compared. Among three electrodes tested, porous nickel anodes always had the lowest  
5 peak power density, independent of the temperature. On the other hand, platinum electrodes  
6 performed well when applied as cathode and anode under 400 °C but performed poorer than  
7 LSC at a temperature above 450 °C as the cathode. The operating temperature is important in  
8 affecting the performance. This shows that metal foam is not suitable to be used as electrodes  
9 for the SOFC. Nickel foam performs poorly while platinum foam is too costly to be  
10 commercialized and can provide good efficiency only under low temperatures.

11 In a polymer fuel cell of a fuel cell stack, platinum contributes roughly 30% of the cost  
12 [108]. LSC has the advantage of producing high performance with reduced cost. Although  
13 metal foam performs poorly as the electrode in the SOFC, it can be used in other parts of a  
14 SOFC. The feasibility of using porous nickel foam as an anode conductive layer was studied  
15 by Corbin et al. [109]. As an anode conductive layer, the coefficient of thermal expansion  
16 (CTE) matching is important, while maintaining high electrical conduction and high porosity  
17 is needed to facilitate gas transport. Nickel foam possesses all the stated characteristics for  
18 CTE matching to be improved. When Ni/YSZ is used as an anode, pressing the nickel foam  
19 before sintering can reduce the CTE of the composite to match YSZ. High-pressed nickel  
20 foam will further enhance the electrical conductivity, which is ideal for the conductive layer.  
21 The study provides guidelines on creating a wide range of porous Ni/YSZ composites by  
22 controlling the microstructure of the nickel foam to maximize its potential as anode  
23 conductive layers.

24 Based on the characteristics of the metal foam, it has high electrical conductivity,  
25 porosity, high strength and is structurally stable, which meets the material requirements of a  
26

1 SOFC. However, metal foam is susceptible to corrosion, which is unavoidable in the fuel cell  
2 environment. To counter this issue, several coatings are introduced as discussed. Using metal  
3  
4 foam alone in a fuel cell is impossible, but using metal foam as a backbone and modifying it  
5  
6 by various means will make it possible to be used in the SOFC.  
7  
8




### 9 **3.5 Alkaline Fuel Cell**

10  
11 An alkaline fuel cell (AFC) is a fuel cell where the operating condition is in an alkaline  
12 medium. It is one of the oldest practical fuel cells, and was used in the U.S. Apollo space  
13 program in the mid-1960s [110]. Nowadays, the development of the AFC has drawn attention  
14 from researchers due to its high efficiency, low temperature and cheapness compared to the  
15 PEMFC. Conventional AFCs use hydrogen as fuel at the anode while consuming oxygen at  
16 the cathode to produce electricity through the redox reactions at the anode and cathode with  
17 potassium hydroxide (KOH) as the electrolyte.  
18  
19

20  
21 Due to the rapid development of the AFC, hydrogen is no longer the only fuel that is  
22 applicable. Fuel such as ethanol [111], glucose [112] and borohydride [113] can be fed into  
23 the anode while the electrolyte can be liquid or solid, such as an anion exchange membrane  
24 (AEM) providing the electrolyte that is maintained in an alkaline medium [114]. From the  
25 study, it was found that oxidation and reduction reactions are faster in alkaline medium than  
26 acidic medium, which contributes to the higher performance of the AFC, as it can enhance  
27 the conductivity of the AEM as well [115]. In addition, the application of cheaper metal  
28 catalysts and non-noble metals is made possible by eliminating platinum, which is expensive.  
29  
30 The study suggested that AEM (alkaline) is more suitable than PEM (acidic) for application  
31 in a fuel cell [116]. By replacing PEM with AEM, the peak power density rose from 1.5  
32 mW.cm<sup>-2</sup> to 20 mW.cm<sup>-2</sup> with glucose used as the fuel fed at the anode.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55

56 The state of the art in AFC structure is almost similar to the other type of fuel cell, which  
57 comprises an anode, GDL, CL, electrolyte and current collector as shown in Fig. 7. The AFC  
58  
59  
60  
61  
62  
63  
64  
65

1 can be stacked to increase the output power density. The electrochemical equations of the  
2 AFC are described in Eqs. (11) to (13). Hydrogen is fed to the anode, while oxygen is  
3 supplied at the cathode:  
4  
5



15 The electrochemical equations may differ from each other and are dependent on the type  
16 of fuel. For example, supplying glucose into the anode of the AFC may generate an  
17 intermediate product such as gluconic acid [109] and enediols [117]. The intermediate  
18 products may affect the performance of the AFC. Intermediate products reduce the electrons  
19 generated in the reaction process. One mole of glucose is able to release 24 electrons [118].  
20 This will reduce the performance and cause wastage of the chemical energy contained in the  
21 glucose.  
22  
23  
24  
25  
26  
27  
28  
29  
30

31 In the AFC, the properties of the cathode are important, and will affect the performance  
32 and durability of the AFC as reviewed by Bidault et al. [119]. It was shown that the material  
33 and manufacturing method of the cathode can affect the performance of the fuel cell.  
34 Furthermore, other issues of the AFC were also addressed. Some common problems that need  
35 to be solved are carbon dioxide effect, corrosion effect, weeping and flooding, fuel crossover,  
36 and production of carbonate, as they can all lead to the deterioration of the AFC's  
37 performance.  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

48 Since the cathode is important, development of the cathode is more aggressive than the  
49 anode. Bidault et al. presented a sizeable number of studies on the cathode of the AFC [120-  
50 123]. The feasibility of using nickel foam as the cathode (and its performance) was compared  
51 to silver-coated nickel foam and nickel mesh [120]. The performances were discussed in  
52 terms of resistance, impedance, cyclic voltammogram analysis and polarization curve. From  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 the result, nickel foam offers various advantages compared to nickel mesh. It is cheap, has  
2 enhanced electrochemical performance, has lower ohmic resistance, has low oxygen  
3 reduction, and has reaction charge transfer resistance. The silver coating on nickel foam is  
4 important in affecting the performance. Ohmic resistance and charge transfer resistance can  
5 be reduced when a coating of silver is applied to the nickel foam. However, there was an  
6 optimum silver coating loading which was about 11 mg.cm<sup>-2</sup>. High coating loading will not  
7 improve the fuel cell performance, but induce extra cost to the fabrication of the electrode.  
8 Besides this, no experimental work on power density was carried out in this study. The work  
9 was continued by incorporating the electrode with GDL [121]. An extra active layer  
10 consisting of manganese (IV) oxide deposited on the carbon black was added on the top of  
11 the GDL. The newly-integrated cathode electrode design is shown in Fig. 8.

12 The study suggested that MnO<sub>2</sub> is a suitable catalyst that can improve cathode  
13 performance with high potential. The polarization curve from experiments showed that the  
14 addition of manganese dioxide on the silver-plated nickel foam can produce 132 mA.cm<sup>-2</sup>  
15 compared to silver-plated nickel foam without manganese dioxide which showed only 40  
16 mA.cm<sup>-2</sup> at 0.8 V. In other words, the improvement was nearly threefold. The percentage of  
17 PTFE used was important to ensure that no flooding occurred on the electrode. The ratio of  
18 PTFE to carbon black of 3:1 showed superior improvement to the performance by increasing  
19 the hydrophobicity of the electrode. The GDL also played an important role in affecting cell  
20 performance and the optimum thickness was about 0.5 mm. Reducing the thickness can  
21 improve the oxygen permeability without causing electrolyte weeping. The performance of  
22 the fuel cell is not only limited by the type of material used for the electrode, thickness of  
23 GDL and the percentage of loading; the type of catalyst is a factor that needs to be considered.  
24 Using metal foam alone as the electrode is not enough to guarantee superior performance.

1 The performance of an integrated anode electrode was also investigated by Le and Zhao  
2 using ethanol as fuel [124]. The anode electrode was combined with a catalyst and diffusion  
3 layer as a whole, with nickel foam used as a skeleton substrate coated with palladium and  
4 PTFE as a binder. An AEM was used as an electrolyte. Fig. 9 shows the comparison between  
5 conventional and integrated anode electrodes. The result showed that the performance of the  
6 newly-integrated anode can produce a peak power density of  $74 \text{ mW.cm}^{-2}$  while conventional  
7 anodes can only generate  $54 \text{ mW.cm}^{-2}$ . This is due to the increment in mass transport of fuel,  
8 reduction in cell resistance and increment in surface area for the electrochemical sites. The  
9 amount of palladium loading was also important to the study, and it was suggested that  $2.0$   
10  $\text{mg.cm}^{-2}$  was the optimum loading condition for the best performance. This study also  
11 showed that the cathode is dominant in affecting the fuel cell performance. However, the  
12 development of the anode is also important, as it can contribute to the improvement of the  
13 performance. The effectiveness of manganese dioxide and palladium as the catalyst in  
14 integrated electrodes is not known and further experimental work can be conducted to  
15 compare them.

16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Chen et al. studied glucose fuel cells and measured their performance with silver/nickel  
foam as the electrode and AEM as the electrolyte [117]. Nickel foam was the base material of  
the electrode and was coated with silver through a simple spontaneous deposition method. At  
 $80 \text{ }^\circ\text{C}$ , the power density of  $2.03 \text{ mW.cm}^{-2}$  was reached when using silver/nickel foam. The  
power density was higher than the pure nickel foam electrodes [125]. During the  
electrochemical reaction, it was observed that the color of the glucose in KOH tended to  
change from transparent to claret red, indicating the formation of enediols. The presence of  
enediols can further boost the performance of the fuel cell.

The feasibility of using gold/nickel foam as both anode and cathode of a glucose fuel cell  
with AEM as the electrolyte was studied by Chen et al. [126]. Gold is a noble metal, and it

1 should be able to produce a high power density based on assumption. The simple  
2 spontaneous deposition method was used on deposit gold particles on the surface of the  
3 nickel foam. Factors such as glucose concentration, KOH concentration, and temperature  
4 were tested against peak power density. By maintaining the concentration of KOH and  
5 glucose at 6M and 0.5M respectively, the power density of  $26.6 \text{ mW.cm}^{-2}$  was yielded at  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Comparing both works done by Chen et al. [117, 126], it was found that gold/nickel foam can perform far superiorly to silver/nickel foam, and this indicates that gold is a better catalyst than silver. The performance of gold/nickel foam as anode and cathode electrodes was also studied by Cao et al. [113]. In this study, glucose was replaced with alkaline  $\text{NaBH}_4$  at the anode, while pure oxygen was replaced with hydrogen peroxide and a Nafion-115 membrane was used. From the SEM images, gold/nickel foam had a larger surface area than that of the nickel foam, and thus the current density obtained by gold/nickel foam was also higher. It yielded a maximum of  $100 \text{ mW.cm}^{-2}$  in power density. These results further prove that gold is a good catalyst in improving catalytic activity, and that using metal foam alone is not enough to yield good power density. High power density generated also indicates that borohydride is a suitable fuel candidate for the AFC.

Other than nickel foam, silver is also a popular selection for electrode material. Bidault and Kucernak investigated the application of porous silver membranes as the AFC cathode electrode [122]. Impedance measurement and a polarization curve were used to examine the fuel cell's performance. The anode was fed with pure hydrogen with a KOH solution and the cathode remained in open air. This air-breathing AFC fuel cell was measured against power density, and it showed the value of  $50 \text{ mW.cm}^{-2}$  at  $25 \text{ }^\circ\text{C}$ . The operation conditions allowed it to be applied for a mobile application. The power density was further improved from 15



1 mW.cm<sup>-2</sup> to 65 mW.cm<sup>-2</sup> [123]. This improvement was due to the replacement of PTFE with  
2 Teflon AF and adding the catalyst manganese dioxide or platinum. The Teflon AF coating  
3 was more uniform than the PTFE and this resulted in the excellent hydrophobicity of the  
4 structure, while manganese dioxide and platinum can increase the catalytic activity of the  
5 oxygen reduction reaction. Similar to nickel foam, using a silver membrane alone is not  
6 sufficient to guarantee a high power density. The addition of a catalyst on the surface is  
7 essential for improving the output. The performances of the nickel foam versus silver  
8 membrane as the cathode electrode were not compared, and this can serve as the new  
9 direction for future study.

10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22 It was believed that manufacturing methods of the electrode can affect the fuel cell's  
23 performance. Ma and Sahai investigated the impact of the AFC electrode fabrication method  
24 [127]. Two types of fabrication methods, namely the electron beam physical vapor deposition  
25 (PVD) and the ink paste methods were used to produce palladium-coated nickel foam and  
26 palladium-coated carbon paper, giving four sets of experiment subjects. The fabricated  
27 product was used as the anode of the AFC, with Nafion 212 membrane and platinum as the  
28 cathode. Borohydride, NaBH<sub>4</sub> in NaOH, was used as the fuel fed at the anode. In summary,  
29 nickel foam performed better than the carbon paper. The ink paste method exhibited better  
30 performance than electron beam physical vapor deposition due to greater palladium loading.  
31 The electrode prepared using PVD had lower metal loading, and yet was able to produce high  
32 power density close to the electrode prepared using ink paste.

33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65  
Li and He conducted an experiment to study the layer reduction method to fabricate  
palladium-coated nickel foam [128]. This method was able to avoid catalyst aggregation and  
also ensured a thin porous catalyst film was uniformly coated on the skeleton. Additionally, it  
caused improvement in the electrochemical kinetics and promoted the transportation of the  
reactant and electrons. Experimental results demonstrated that by using this method to

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
prepare palladium/nickel foam, an increment of 1.16 times of the current density can be achieved while an enhancement of power density of about 1.03 times can be achieved when compared to the conventional design. This improvement may be attributed to growth in the electrochemical surface area and mass transport due to high permeability.

34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65  
An innovative design was developed to break through the bottleneck faced by current AFCs. For instance, An et al. proposed a combination via an acid-alkaline fuel cell [129, 130]. This new design used an alkaline medium at the anode and acidic medium at the cathode. The anode electrode was made with nickel foam coated with palladium-nickel/carbon (PdNi/C), while the cathode was carbon black coated with platinum/carbon (Pt/C). The anode and cathode were separated by a Nafion 117 membrane. NaOH and ethanol were used as a fuel fed to the anode while hydrogen peroxide and sulfuric acid were supplied to the cathode. The output power density reached  $240 \text{ mW.cm}^{-2}$  at  $60 \text{ }^\circ\text{C}$  for this innovative fuel cell, which was considered the highest power density achieved in the year 2011. However, hydrogen decomposition was a problem that caused a dramatic drop in the cathode potential.

Fuel cell performance was further improved by replacing the cathode electrode with a bi-functional electrode composed of nickel-chromium foam as backbones, and deposited with gold particles [130]. The peak power density produced was  $200 \text{ mW.cm}^{-2}$ . Although the power density was  $40 \text{ mWcm}^{-2}$  lower than the previous study, it was still higher than the conventional electrode which produced only  $135 \text{ mW.cm}^{-2}$ . The benefits of using nickel-chromium metal foam coated with gold were its ability to reduce the hydrogen peroxide decomposition which can lead to severe degradation. Gold was chosen as a catalyst because gold is effective in preventing the gas evolution of hydrogen peroxide [131]. From this study, it was proven that metal foam is more suitable to be applied to the electrode than carbon black, as the porosity properties of the metal foam can enhance catalytic activity and thereby reduce transport resistance.

1 Nickel foam is widely used because of its excellent properties like its lightweight quality  
2 and high porosity in 3D structures, and it is able to provide sufficient mechanical strength.  
3  
4 Popular coatings such as palladium, gold and platinum were used as a catalyst to promote the  
5 catalytic activity. The drawback of AFCs, such as degradation, is seldom discussed. It is  
6 important to understand the degradation behavior so that improvements can be made in the  
7 future. The study of degradation was carried out by Li and Zhao [132]. Anode degradation  
8 happened after 520 hours of discharge, which caused voltage loss while AEM showed a  
9 reduction in its inherent conductivity. Thus, the factors that cause degradation and solutions  
10 to compensate for it should be proposed to improve the reliability of the fuel cell. Further  
11 work is still required to improve the performance of the Anion Exchange Membrane Fuel  
12 Cell (AEMFC) as suggested by Kucernak et al. [133]. This is because its performance is still  
13 below par as compared to the PEMFC. With similar platinum loadings, the AEMFC can only  
14 produce  $0.06 \text{ W.cm}^{-2}$  as compared to  $0.544 \text{ W.cm}^{-2}$  [134] and  $0.41 \text{ W.cm}^{-2}$  [135] of the  
15 PEMFC. The weak performance may be due to the poor hydroxide conduction at the catalyst  
16 layer. The performance can be enhanced by increasing the permeability, surface area, electric  
17 conductivity of the electrode, and the catalyst layer. Undoubtedly metal foam is the most  
18 suitable candidate due to its porosity characteristics.

19 Understanding transport phenomena is essential in the development of the AFC. It will  
20 help researchers to understand the effects of various parameters, such as anode/cathode  
21 material, concentration or type of fuel used and design structure of components that will  
22 affect the fuel cell performance without investing heavily in the experimental setup.

### 23 **3.6 Direct Ethanol Fuel Cell**

24 Wang et al. experimented on the Direct Ethanol Fuel Cell (DEFC) to identify the effect  
25 of metal foam on performance [136]. Two electrodes, palladium/nickel foam and  
26 palladium/palladium film foam were used. The loading of palladium on nickel foam and  
27

1 palladium film were kept constant at  $0.11 \text{ mg.cm}^{-2}$  and the results showed that  
2 palladium/nickel foam can produce an oxidation peak current density of  $107.7 \text{ mA.cm}^{-2}$ . The  
3 increment was eight times greater than that of the palladium film. Besides, palladium/nickel  
4 foam exhibited stability after 500 cycles. The performance of palladium film dropped after  
5 500 cycles. Nickel foam is a promising electrode for the DEFC.  
6  
7  
8  
9  
10

11 An and Zhao studied the transport phenomenon in the DEFC [137]. Transport  
12 phenomena in the anode, membrane, and cathode were discussed in detail. It was found that  
13 the anode diffusion layer should be kept as thin as possible for better delivery of reactants.  
14 Therefore, nickel foam was suitable to be used as a diffusion layer as it has high porosity  
15 (~95%). Application of nickel foam as a diffusion layer was also supported by Kamarudin et  
16 al. [111]. Nickel foam can enhance the ion conductivity and reduce diffusion resistance due  
17 to its high porosity and eventually leads to high performance of the fuel cell.  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28

29 An et al. developed a one-dimensional model to study the DEFC [138]. The model was  
30 used to explain the phenomenon of the fuel cell. Porosity of the diffusion layer was an  
31 important factor in affecting performance. High porosity and a thin diffusion layer will offer  
32 better performance. However, this may lead to poor mechanical properties. Yang et al.  
33 proposed two-dimensional transport models to investigate the DEFC [139]. A numerical  
34 study was conducted to validate the model. The model showed good agreement with  
35 experimental data. The model accounted for the structural design of the electrodes in  
36 affecting performance. Porosity and pore size of the metal foam can affect the performance of  
37 the fuel cell. However, there is a lack of numerical studies to understand the transport  
38 phenomenon in the DEFC.  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52

#### 53 **4. Solar power system**

##### 54 **4.1 Solar Collectors/Receivers**

1 The solar collector is a heat exchanger in which solar energy is absorbed and converted  
2 into heat. The heat is then carried away by the fluid flow within the solar collector and heat is  
3  
4 conducted to the user. It is used for low temperature application, such as providing heat for  
5  
6 building, hot water and solar cooling in air conditioning processes. Various parameters, such  
7  
8 as geometry, design, working fluid and operating conditions will affect the efficiency of a  
9  
10 solar collector. Flat plate solar collectors are popular for low and medium heating application.  
11  
12 The performance of a solar collector depends on how much solar energy is absorbed and how  
13  
14 well the heat is transferred to the working fluid. Low mean temperature between the collector  
15  
16 surface and the fluid will give better performance. The heat transfer rate should be increased  
17  
18 to produce higher efficiency.  
19  
20  
21  
22  
23

24 Sopian et al. experimented on the double-pass solar collector to evaluate the thermal  
25  
26 performance with and without porous material [8, 140]. Porous media were inserted into the  
27  
28 bottom channel and the experiment was carried out using halogen lamps to mimic solar  
29  
30 radiation. The study suggested that the thermal efficiency increased when porous media were  
31  
32 present and was attributed to the increase of heat transfer area. Naphon conducted a  
33  
34 numerical study of the double-pass flat plate solar air heater [141]. Porous media were  
35  
36 inserted into the bottom channel as illustrated in Fig. 10. The numerical result was compared  
37  
38 with the experimental work done by Sopian [8]. The result obtained for the solar air heater  
39  
40 gave an average difference of 18.4% in the presence of porous media and 4.3% in the absence  
41  
42 of porous media, respectively. In terms of thermal efficiency, there was an improvement of  
43  
44 25.9% due to the existence of porous media in the bottom channel of the solar air heater.  
45  
46  
47  
48  
49  
50

51 Heat transfer enhancement of a flat-plate solar water collector was studied with the  
52  
53 consideration of metal foam blocks in the flow channel [142]. Streamlines, pressure drops,  
54  
55 Nusselt numbers and temperature gradients were parameters considered in this study. A  
56  
57 correlation of Nusselt number in terms of Reynolds number, Prandtl number and porosity of  
58  
59  
60  
61  
62  
63  
64  
65

1 the metal foam was developed with  $\pm 15\%$  relative deviation. Thermal performance could be  
2 improved when the inner wall of the solar absorber was replaced with metal foam. The study  
3 was continued by performing a numerical simulation on a solar flat plate collector [143]. In  
4 this study, aluminum foam filled with paraffin was used. A finite volume approach was used  
5 to discretize the governing equation with a SIMPLEC algorithm used to solve momentum  
6 and continuity equations. Two temperature models were used for the simulation. The  
7 numerical study suggested that embedding of paraffin in the aluminum foam can affect the  
8 heat transfer and melting rate of paraffin. This will result in more uniform temperature  
9 distribution. The results were accurately predicted when using local non-thermal equilibrium  
10 assumptions. This showed that metal foam is able to enhance the performance of a solar  
11 collector and the performance can be further increased by embedding paraffin in it. The effect  
12 of the Nusselt number on metal foam in a flat plate solar collector was studied by Jouybari et  
13 al. [144]. It was shown that metal foam can increase the Nusselt number of the system.

14 The improvement of the solar collector's efficiency can be enhanced by using nanofluid.  
15 It was suggested that types of nanofluids, mass flow rate of nanofluids, concentration and size  
16 of nanofluids affect the efficiency of the solar collector. Using Cu-H<sub>2</sub>O as nanofluid exhibited  
17 an improvement of 23.83% in terms of solar collector efficiency [145]. Furthermore, solar  
18 collector efficiency underwent improvements of 15.7% and 16.7% when TiO<sub>2</sub>-H<sub>2</sub>O and CuO-  
19 H<sub>2</sub>O were used as nanofluid, respectively [146, 147].

20 The application of metal foam is not only limited to the flat-plate solar collector, but  
21 extends to other types of solar collector, such as the tubular solar receiver and volumetric  
22 solar receiver. Optimized design of the tubular solar receiver using porous medium was  
23 studied numerically by Lim et al. [148]. The design point was identified to provide guidelines  
24 for manufacturing processes. Porosity, thermal conductivity and the length of the porous  
25 medium were found to be factors producing a highly efficient tubular solar receiver. Thermal

1 conductivity and the porosity of porous materials were factors determining the maximum  
2 temperature of the solar collector. By combining all the design points, the outlet temperature  
3 of the tubular solar receiver was about 13 °C higher than the previous unmodified system.  
4 The performance of the porous disc enhanced receiver outweighed the performance of the  
5 tubular solar receiver in the study conducted by Reddy et al. [149]. The thermal gradient  
6 between the receiver surface and the fluid was less than the conventional tubular receiver in  
7 the case of the porous disc enhanced receiver. The efficiency of the tubular receiver was  
8 improved by Baskar et al. [150]. At a Reynolds number of 31,845, the Nusselt number for the  
9 porous disc receiver was about 70% higher than that for the tubular solar receiver.  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21

22       Regarding the volumetric solar receiver, a study was conducted by Becker et al., which  
23 concluded that a proper selection of porous material properties is able to reduce or avoid the  
24 flow instability [151]. The relationship between pressure drop and ceramic foam was  
25 investigated experimentally and numerically by Wu et al. [152]. The results showed that the  
26 pressure drop reduced with the increase of porosity and cell size of the ceramic foam in  
27 numerical and experimental works. Ergun's equation was the most successful model for  
28 predicting the pressure drop in the porous media. However, there should be an optimum  
29 porosity when applying ceramic foam to compromise the pressure drop and strength of the  
30 material. Nickel foam was used in the volumetric solar receiver and the thermal performance  
31 and flow effects were studied by Michailidis et al. [153]. From the study, the efficiency was  
32 affected by material parameters and flow conditions. The main drawback of using nickel  
33 foam is that nickel exhibits poor resistance to hot corrosion, which is the operating condition  
34 for the volumetric solar receiver. Hence, a simple treatment method using slurry  
35 aluminization of nickel foam was proposed to create a protective oxidation resistant coating  
36 on the porous material.  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 The discussion above was based on the use of the steady flow rate for the working fluid.  
2 The idea of using pulsation flow for thermal enhancement was numerically examined by  
3 Huang et al. [154]. Metal foam was attached to the absorbing plate as shown in Fig. 11. It  
4 was found that the average heat transfer enhancement factor was positively correlated with  
5 the pulsating amplitude, Reynolds number, effective conductivity ratio and reduction of  
6 porosity. The Nusselt number is dependent on the Reynolds number, porosity, pulsating  
7 frequency and oscillation amplitude of the axial inlet velocity in the pulsating flow. Pulsating  
8 flow can improve heat transfer but also introduce an additional pressure drop, which requires  
9 extra pumping power to circulate the fluid. Hence, heat transfer enhancement should be  
10 correlated with the induced pressure drop for economic consideration.  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23

24 Although most of the results discussed above prove that porous metal is an ideal  
25 candidate to promote heat transfer and enhance the thermal efficiency of the solar collector,  
26 this is not true for all cases. In the case of using curved flow technology, it behaves in the  
27 opposite way [155]. The duct of curved flow technology was filled with coarse aluminum  
28 chips with the porosity of 0.1453 and the fluid produced a low exit temperature compared to  
29 the clean duct. The pressure loss caused by porous media hinders the possibility of natural  
30 circulation. Hence, an extra pump power is needed to overcome the pressure loss and overall  
31 efficiency is reduced. This experiment gave an insight into the feasibility of using porous  
32 media in the solar collector which depends on the type of solar collector, as metal foam is not  
33 suitable for all types of solar collector. Investigation and experiments should be continued to  
34 identify the feasibility of metal foam for various applications.  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51 Xu et al. used different models to analyze the performance of the metal foam solar  
52 collector [156]. A modified fin analysis method was proposed for better estimation of the  
53 thermal performance. The application of different model assumptions, such as local thermal  
54 non-equilibrium (LTNE) and local thermal equilibrium (LTE) was adopted for different  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1 situations. For example, LTNE effect in the porous media is weakened with increasing  
2 porosity while LTE is valid for a low Darcy number. Significant differences were found  
3 when the Darcy model and Brinkman model were used for small duct scale. The differences  
4 were reduced when a large duct scale was applied. Hence, the modified fin analysis  
5 (combined fin-LTE model) helps to improve the accuracy.  
6  
7  
8  
9  
10

11 In conclusion, the thermal efficiency for various solar collectors can be increased to  
12 about 60 to 70% using porous material [14]. However, studies have also shown a decrement  
13 in curve flow technology efficiency. Metal foam provides an insight into the future  
14 development of the solar collector due to its excellent thermal properties. More research shall  
15 be conducted in this field for a better understanding of its impact.  
16  
17  
18  
19  
20  
21  
22  
23

#### 24 **4.2 Thermal energy storage systems**

25 Thermal energy storage (TES) is part of a component in the solar energy harvesting  
26 system. It is used to store solar energy captured by the solar collector for later use. The  
27 availability of sunlight depends on many factors. Solar radiation changes over time and  
28 weather. On a cloudy, hazy or rainy day, solar radiation decreases and eventually becomes  
29 zero at night. Hence, thermal energy storage is used to store the solar energy, so the energy is  
30 readily available when there is no solar radiation. To ensure the availability of energy at all  
31 times, thermal energy storage should have high thermal storage capacity with a good heat  
32 transfer rate and low response time [157]. To increase efficiency, the material used for TES  
33 should have the characteristics of high operating temperature, high thermal conductivity, high  
34 thermal absorption and high specific heat capacity [158].  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51 Metal foam possesses characteristics suitable for TES application. Metal foam cannot be  
52 used alone in TES application and usually is used with PCM to improve the performance of  
53 TES. PCM is a type of material that stores thermal energy in terms of chemical energy  
54 through melting to maintain a constant temperature in the TES. The amount of energy that  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 can be absorbed depends on the latent heat of fusion. PCM has a large space capacity and  
2 isothermal behavior during melting and is mainly used in latent thermal heat storage [159].  
3  
4 However, its main disadvantage is low thermal conductivity, which can be compensated for  
5  
6  
7 by applying embedded PCM in the metal foam.  
8

9  
10 Mesalhy et al. numerically investigated the effect of thermal conductivity of PCM  
11 embedded in the high thermal conductivity porous matrix [160]. From the study, it was  
12 shown that porosity has a positive effect on melting rate and heat transfer characteristics.  
13  
14 Low porosity can increase the melting rate, with the drawback of slowed convection motion.  
15  
16 Besides this, the melting rate is proportional to the thermal conductivity of the porous matrix.  
17  
18 By combining these two effects, it was suggested to use the porous matrix with high thermal  
19  
20 conductivity and high porosity to increase the response of PCM storage.  
21  
22  
23  
24  
25

26  
27 Xiao et al. measured the thermal conductivity of paraffin/metal foam [161]. Two types of  
28 PCM, paraffin/copper foam and paraffin/nickel foam, were used. The measurement showed  
29 that the composite paraffin PCM had higher conductivity. Paraffin/nickel foam has a thermal  
30 conductivity 3 times higher than that of pure paraffin, while paraffin/copper foam has a  
31 thermal conductivity 15 times higher than that of pure paraffin. The effect of conductivity is  
32 important as shown numerically and experimentally in the work done by Chen et al. [162].  
33  
34 During the melting of PCM, the structure of the metal can cause a significant impact on the  
35 heat transfer rate because the metal foam will improve the heat transfer in the solid-liquid  
36 phase, attributed to the excellent thermal conductivity of metal foam. Wu and Zhao used  
37 copper and steel alloy embedded with  $\text{NaNO}_3$  [163]. The findings suggested that the heat  
38 transfer rate was improved 2.5 times as compared to the case in which the metal foam was  
39 absent. From the study carried out by Zhao et al., the heat transfer rate was increased by 3 to  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 the structure and material of the metal foam. The time taken for solidification of PCM was  
2 reduced by more than half when metal foam was integrated into the PCM.  
3

4 The effect of melting rate in the presence of metal foam was investigated numerically by  
5 Yang et al. [165]. A tetrakaidecahedron unit cell was used to mimic real foam application in  
6 the study. It was found that metal foam can accelerate the melting rate of PCM. The melting  
7 time was 37.5% lower compared to the case without metal foam. This showed that the  
8 response time had been reduced and the efficiency of the TES had been increased. The  
9 numerical result agreed with the experimental result from Badenhorst et al. [166]. In this  
10 study, graphite foam was used for storage of concentrated solar energy and solar energy  
11 capture. The prototype of the solar concentrator was designed with a simple two-axis tracking  
12 method as shown in Fig. 12. The prototype was cheap and simple, yet able to reach  
13 concentration ratios in excess of 1,000 suns. Graphite foam reduced the melting time of PCM  
14 by 46% when compared to pure PCM. By manipulating the foam geometry and concentration  
15 ratio, the size of the receiver can be reduced by 75% and still provide the same efficiency.  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33

34 By using different types of PCM with different types of metal foam, it greatly enhances  
35 the TES efficiency in terms of response time and the heat transfer rate. The degree of  
36 improvement depends on the types of metal foam and its properties. Proper study of PCM  
37 and metal foam characteristics can help identify the combination of PCM and metal foam that  
38 should be used for a given application. The selection of suitable PCM for a certain  
39 application is a complicated process, and a study was carried out by Xu et al. to help in the  
40 selection of PCM for solar absorption cooling application [167]. The method helped to  
41 identify the most suitable PCM material for a specific application. As suggested by Rashidi et  
42 al., future study is needed, especially research on the high temperature thermal energy storage  
43 system as it is limited [9].  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57

## 58 **5. Current perspective**

59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Fuel cells and solar power systems are promising renewable sources that can replace fossil fuels in the future. The research in these two fields is ongoing and it can be foreseen that the performance of the fuel cell and solar power system will be increased in the near future. Metal foam with its excellent properties can improve the performance of fuel cells and solar energy power systems. Applying metal foam in both systems will improve the energy output, increase the waste heat rejection and stimulate a uniform flow field. The common issue faced by both applications is temperature control. Metal foam with its good thermal properties can enhance the heat rejection rate of the system to prolong the cycle life.

Most of the literature review is based on the performance of a single component but not a whole system and the experimental results are based on the laboratory environment. Hence, the main focus of the upcoming research should be on evaluating the performance of the fuel cell system and solar power system as a whole with metal foam components. The characteristics of metal foam are affected by pore density, porosity, permeability and interfacial area. The understanding of how these parameters affect the performance of the systems is necessary and not yet available in the literature.

Although the power density of the fuel cell can be improved by using metal foam electrodes, it also introduces serious corrosion issues. This will cause damage to the system in long-term operation. Hence, an anti-corrosion coating is needed for the metal foam. Coating methods required are far more complicated due to the presence of porosity in the metal foam. Besides, it is also necessary to ensure that the internal surface of the pores receives sufficient coating as compared to the outer metal foam surface. Other issues such as fuel crossover, high impedance of the fuel cell, hydrophobicity and pressure drop are interesting topics of concern as well.

There are many types of porous media available in the market with different pore density, porosity and material. Most of the studies are focused on a single characteristic of the metal

1 foam. For example, the application of metal foam in the fuel cell is focused on nickel foam  
2 only but other types of porous media are rarely investigated. Besides, study of the effect of  
3 using different combinations of porosity and pore density in a system is also very rare. On the  
4 other hand, the application of porous media in the solar energy harvesting system is relatively  
5 new and has not been applied in commercial products. This could provide a future direction  
6 of metal foam research in the renewable energy field especially in the fuel cell and solar  
7 power system.  
8  
9

## 10 **6. Conclusions**

11 Numerous experiments and numerical simulations have been conducted to study the  
12 application of metal foam on the fuel cell and solar energy harvesting system. It is concluded  
13 that metal foam is a promising material to be implemented in a fuel cell and solar energy  
14 harvesting system. It can boost performance and provide additional benefits, such as reduced  
15 cost and overall weight. In a fuel cell system, using metal foam alone as a component is not  
16 satisfactory. Metal foam is not corrosion resistant, is subject to carbon deposition at high  
17 temperature and is not hydrophobic. Hence, a coating is necessary to minimize the corrosion  
18 issue of metal foam. Besides, the coating also helps to prevent carbon deposition and repel  
19 water. The electrical characteristics can be further improved with a coating of metal foam. In  
20 the solar energy harvesting system, metal foam can be modified to enhance thermal  
21 performance, such as embedding paraffin into the metal foam. Most literature suggests nickel  
22 foam to be well-suited for fuel cell application, while there is no consensus on the types of  
23 metal foam to be used in the solar energy harvesting system. This can provide a new direction  
24 for future study. In addition, there are limited numerical studies that identify the relationship  
25 between the characteristics of metal foam and performance. Forthcoming studies can focus  
26 on developing porous media models to form a set of correlation equations. The equations can  
27 help predict the performance by manipulating the characteristics of the metal foam. This is  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 important, as it can greatly reduce the experimental time and cost of producing a prototype  
2 for experimental study.  
3

#### 4 **Acknowledgements**

5 This work is supported by UTARRF Grant No. IPSR/RMC/UTARRF/2016-C1/T8 and  
6  
7 Science fund Grant No. 03-02-11-SF0216 from the Ministry of Science, Technology and  
8  
9 Innovation, Malaysia.  
10

11 The authors would like to thank Elsevier for the permission of using Fig. 1 as in ref [12], Fig.  
12 5 as in ref [78], Fig. 8 as in ref [121], Fig. 9 as in ref [124], Fig 10, as in ref [8], Fig. 11 as in  
13 ref [142], Fig. 12 as in ref [166], Table 1 as in ref [59] and Table 2 as in ref [60].  
14

15 The authors would like to thank the fuel economy as in ref [15] for the permission of using  
16 Fig. 2.  
17

18 The authors would like to thank the Earth Science Australia as in ref [40] for the permission  
19 of using Fig. 3 and Fig. 7.  
20

21 The authors would like to thank the author as in ref [58] for the permission of using Fig. 4.  
22

23 The authors would like to thank Springer-Verlag for the permission of using Fig. 6 as in ref  
24 [80].  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## References:

- [1] Olabi AG. Energy quadrilemma and the future of renewable energy. *Appl Energy* 2016;108:1–6.
- [2] Saw LH, Ye Y, Tay AAO. Integration issues of Lithium-ion battery into battery pack for electric vehicles. *J Clean Prod* 2016;113:1032-1045.
- [3] Saw LH, Ye Y, Tay AAO. Electro-thermal analysis and integration issues of Lithium-ion battery for electric vehicles. *Appl Energ* 2014;131:97-107.
- [4] Prabhu RR. Stationary Fuel Cells Market size to reach 350,000 Shipments by 2022. *Renew India Campaign*, <http://www.renewindians.com/2013/01/stationary-fuel-cells-market-size-to-reach-350000-shipments-by-2022.html>; 2013 [accessed 15 August 2017].
- [5] Thiam HS, Daud WRW, Kamarudin SK, Mohamad AB, Kadhum AAH, Loh KS, Majlan EH. Overview on nanostructured membrane in fuel cell applications. *Int J Hydrog Energ* 2011;36:3187–3205.
- [6] Thiam HS, Daud WRW, Kamarudin SK, Mohamad AB, Kadhum AAH, Loh KS, Majlan EH. Nafion/Pd-SiO<sub>2</sub> nanofiber composite membranes for direct methanol fuel cell applications. *Int J Hydrog Energ* 2011;38:9474-9483.
- [7] Thiam HS, Daud WRW, Kamarudin SK, Mohamad AB, Kadhum AAH, Loh KS, Majlan EH. Performance of direct methanol fuel cell with a palladium-silica nanofibre/Nafion composite membrane. *Energy Convers Manag* 2013;75:718-726.
- [8] Sopian K, Supranto, Daud WRW, Othman MY, Yatim B. Thermal performance of the double-pass solar collector with and without porous media. *Renew Energy* 1999;18:557–64.
- [9] Basic of Solar energy. The electronic universe, <http://zebu.uoregon.edu/disted/ph162/14.html>; 2011 [accessed 20 Sept 2017].
- [10] Jeff T, Nate L, George C. Solar FAQs. Sandia National Laboratory, [http://www.sandia.gov/~jytsao/Solar FAQs.pdf](http://www.sandia.gov/~jytsao/Solar%20FAQs.pdf); 2006 [accessed 20 Sept 2017].
- [11] Lefebvre L-P, Banhart J, Dunand DC. Porous Metals and Metallic Foams: Current Status and Recent Developments. *Adv Eng Mater* 2008;10:775–87.
- [12] Saw LH, Ye Y, Yew MC, Chong WT, Yew MK, Ng TC. Computational fluid dynamics simulation on open cell aluminium foams for Li-ion battery cooling system. *Appl Energy* 2017;204:1489–1499.
- [13] Ashby MF, Evans A, Fleck NA, Gibson LJ, Hutchinson JW, Wadley HNG. *Metal Foams: A Design Guide*. *Met. Foam. A Des. Guid.* 1st ed., Butterworth-Heinemann; 2000, p. 181–8.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [14] Rashidi S, Esfahani JA, Rashidi A. A review on the applications of porous materials in solar energy systems. *Renew Sustain Energy Rev* 2017;73:1198–210.
  - [15] Fuel economy. How Fuel Cells Work, [https://www.fueleconomy.gov/feg/fcv\\_PEM.shtml](https://www.fueleconomy.gov/feg/fcv_PEM.shtml) [accessed August 20, 2017].
  - [16] Chang HP, Chou CL, Chen YS, Hou TI, Weng BJ. The design and cost analysis of a portable PEMFC UPS system. *Int J Hydrogen Energy* 2007;32:316–22.
  - [17] Afshari E, Jazayeri SA. Effects of the cell thermal behavior and water phase change on a proton exchange membrane fuel cell performance. *Energy Convers Manag* 2010;51:655–62.
  - [18] Tawfik H, Hung Y, Mahajan D. Metal bipolar plates for PEM fuel cell-A review. *J Power Sources* 2007;163:755–67.
  - [19] Kumar A, Reddy RG. Modeling of polymer electrolyte membrane fuel cell with metal foam in the flow-field of the bipolar/end plates. *J Power Sources* 2003;114:54–62.
  - [20] Kumar A, Reddy RG. Materials and design development for bipolar/end plates in fuel cells. *J. Power Sources* 2004;129:62–7.
  - [21] Afshari E, Mosharaf-Dehkordi M, Rajabian H. An investigation of the PEM fuel cells performance with partially restricted cathode flow channels and metal foam as a flow distributor. *Energy* 2017;118:705–15.
  - [22] Hossain MS, Shabani B. Metal foams application to enhance cooling of open cathode polymer electrolyte membrane fuel cells. *J Power Sources* 2015;295:275–91
  - [23] Tsai BT, Tseng CJ, Liu ZS, Wang CH, Lee CI, Yang CC, Lo SL. Effects of flow field design on the performance of a PEM fuel cell with metal foam as the flow distributor. *Int J Hydrogen Energy* 2012;37:13060–6.
  - [24] Wilberforce T, Makky AA, Baroutaji A, Sambhi R, Olabi AG. Computational Fluid Dynamic simulation and modelling (CFX) of flow plate in PEM fuel cell using aluminum open cellular foam material. *2017 IEEE Texas Power Energy Conf* 2017:1–6.
  - [25] Carton JG, Olabi AG. Three-dimensional proton exchange membrane fuel cell model: Comparison of double channel and open pore cellular foam flow plates. *Energy* 2017;136:185–95.
  - [26] Tseng CJ, Tsai BT, Liu ZS, Cheng TC, Chang WC, Lo SK. A PEM fuel cell with metal foam as flow distributor. *Energy Convers Manag* 2012;62:14–21.
  - [27] Huo S, Cooper NJ, Smith TL, Park JW, Jiao K. Experimental investigation on PEM fuel cell cold start behavior containing porous metal foam as cathode flow distributor. *Appl Energy* 2017;203:101–14.



- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [28] Tseng CJ, Heush YJ, Chiang CJ, Lee YH, Lee KR. Application of metal foams to high temperature PEM fuel cells. *Int J Hydrogen Energy* 2016;41:16196–204.
  - [29] Hung Y, El-Khatib KM, Tawfik H. Testing and evaluation of aluminum coated bipolar plates of pem fuel cells operating at 70 °C. *J Power Sources* 2006;163:509–13.
  - [30] Wang WL, He SM, Lan CH. Protective graphite coating on metallic bipolar plates for PEMFC applications. *Electrochim Acta* 2012;62:30–5.
  - [31] Wang Y, Northwood DO. An investigation into TiN-coated 316L stainless steel as a bipolar plate material for PEM fuel cells. *J Power Sources* 2007;165:293–8.
  - [32] Odabae M, Mancin S, Hooman K. Metal foam heat exchangers for thermal management of fuel cell systems - An experimental study. *Exp Therm Fluid Sci* 2013;51:214–9.
  - [33] Afshari E, Ziaei-Rad M, Shariati Z. A study on using metal foam as coolant fluid distributor in the polymer electrolyte membrane fuel cell. *Int J Hydrogen Energy* 2016;41:1902–12.
  - [34] Ji M, Wei Z. A review of water management in polymer electrolyte membrane fuel cells. *Energies* 2009;2:1057–106.
  - [35] Afshari E, Baharlou Houreh N. Performance analysis of a membrane humidifier containing porous metal foam as flow distributor in a PEM fuel cell system. *Energy Convers Manag* 2014;88:612–21.
  - [36] Ous T, Arcoumanis C. The formation of water droplets in an air-breathing PEMFC. *Int J Hydrogen Energy* 2009;34:3476–87.
  - [37] Baroutaji A, Carton JG, Stokes J, Olabi AG. Application of Open Pore Cellular Foam for air breathing PEM fuel cell. *Int J Hydrogen Energy* 2017;42:25630–8.
  - [38] Jeong SU, Cho EA, Kim HJ, Lim TH, Oh IH, Kim SH. Effects of cathode open area and relative humidity on the performance of air-breathing polymer electrolyte membrane fuel cells. *J Power Sources* 2006;158:348–53.
  - [39] Chen R, Zhao TS. Porous current collectors for passive direct methanol fuel cells. *Electrochim Acta* 2007;52:4317–24.
  - [40] Earth Science Australia. Fuel Cells, <http://earthsci.org/mineral/energy/fuelcell/fuelcell.html#TOP> [accessed August 20, 2017].
  - [41] Kamarudin SK, Achmad F, Daud WRW. Overview on the application of direct methanol fuel cell (DMFC) for portable electronic devices. *Int J Hydrogen Energy* 2009;34:6902–16.
  - [42] Arisetty S, Prasad AK, Advani SG. Metal foams as flow field and gas diffusion layer in direct methanol fuel cells. *J Power Sources* 2007;165:49–57.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [43] Jiang R, Rong C, Chu D. Determination of energy efficiency for a direct methanol fuel cell stack by a fuel circulation method. *J Power Sources* 2004;126:119–24.
- [44] Arisetty S, Advani SG, Prasad AK. Methanol diffusion rates through the anode diffusion layer in direct methanol fuel cells from limiting current measurements. *Heat Mass Transf* 2008;44:1199–206.
- [45] Chen R, Zhao TS. A novel electrode architecture for passive direct methanol fuel cells. *Electrochem Commun* 2007;9:718–24.
- [46] Yan XH, Zhao TS, An L, Zhao G, Zeng L. A micro-porous current collector enabling passive direct methanol fuel cells to operate with highly concentrated fuel. *Electrochim Acta* 2014;139:7–12.
- [47] Huang Q, Jiang J, Chai J, Yuan T, Zhang H, Zou Z, Zhang X, Yang H. Construction of porous anode by sacrificial template for a passive direct methanol fuel cell. *J Power Sources* 2014;262:213–8.
- [48] Lee Y, Kim TK, Choi YS. Effect of porosity in catalyst layers on direct methanol fuel cell performances. *Fuel Cells* 2013;13:173–80.
- [49] Rabaey K, Lissens G, Siciliano SD, Verstraete W. A microbial fuel cell capable of converting glucose to electricity at high rate and efficiency. *Biotechnol Lett* 2003;25:1531–5.
- [50] Lee HS, Parameswaran P, Kato-Marcus A, Torres CI, Rittmann BE. Evaluation of energy-conversion efficiencies in microbial fuel cells (MFCs) utilizing fermentable and non-fermentable substrates. *Water Res* 2008;42:1501–10.
- [51] Rabaey K, Verstraete W. Microbial fuel cells: Novel biotechnology for energy generation. *Trends Biotechnol* 2005;23:291–8.
- [52] Rozsenberszki T, Kook L, Bakonyi P, Nemestothy N, Logrono W, Perez M, Urquizo G, Recalde C, Kurdi R, Sarkady A. Municipal waste liquor treatment via bioelectrochemical and fermentation ( $H_2 + CH_4$ ) processes: Assessment of various technological sequences. *Chemosphere* 2017;171:692-701.
- [53] Pham TH, Rabaey K, Aelterman P, Clauwaert P, De Schamphelaire L, Boon N, Verstraete W. Microbial fuel cells in relation to conventional anaerobic digestion technology. *Eng Life Sci* 2006;6:285–92.
- [54] Hindatu Y, Annuar MSM, Gumel AM. Mini-review: Anode modification for improved performance of microbial fuel cell. *Renew Sustain Energy Rev* 2017;73:236–48.
- [55] Rahimnejad M, Ghoreyshi AA, Najafpour G, Jafary T. Power generation from organic substrate in batch and continuous flow microbial fuel cell operations. *Appl Energy* 2011;88:3999–4004.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [56] Bakonyi P, Kumar G, Kook L, Toth G, Rozsenberszki T, Belafi-Bako K, Nemestothy N. Microbial electrohydrogenesis linked to dark fermentation as integrated application for enhanced biohydrogen production: A review on process characteristics, experiences and lessons. *Bioresource Technology* 2018;251:381-389.
- [57] Rahimnejad M, Adhami A, Darvari S, Zirepour A, Oh SE. Microbial fuel cell as new technology for bioelectricity generation: A review. *Alexandria Eng J* 2015;54:745–56.
- [58] Parkash A. Microbial Fuel Cells: A Source of Bioenergy. *J Microb Biochem Technol* 2016;8:247–255.
- [59] Du Z, Li H, Gu T. A state of the art review on microbial fuel cells: A promising technology for wastewater treatment and bioenergy. *Biotechnology Advances* 2007;25:464-482.
- [60] Pant D, Bogaert GV, Diels L, Vanbroekhoven K. A review of the substrates used in microbial fuel cells (MFCs) for sustainable energy production. *Bioresource Technology* 2010;101:1533-1543.
- [61] Kumar G, Bakonyi P, Zhen G, Sivagurunathan P, Kook L, Kim SH, Toth G, Nemestothy N, Belafi-Bako K. Microbial electrochemical systems for sustainable biohydrogen production: Surveying the experiences from a start-up viewpoint. *Renew Sustain Energy Rev* 2017;70:589-597.
- [62] Kook L, Nemestothy N, Bakonyi P, zhen G, Kumar G, Lu X, Su L, Saratale GD, Kim SH, Gubicza L. Performance evaluation of microbial electrochemical systems operated with Nafion and supported ionic liquid membranes. *Chemosphere* 2017;175:350-355.
- [63] Kook L, Nemestothy N, Bakonyi P, Gollei A, Rozsenberszki T, Takacs P, Salekovics A, Kumar G, Belafi-Bako K. On the efficiency of dual chamber biocatalytic electrochemical cells applying membrane separators prepared with imidazolium-type ionic liquids containing  $[NTf_2]^-$  and  $[PF_6]^-$  anions. *Chem Eng J* 2017;324:296-302.
- [64] Yang YC, Chen CC, Huang CS, Wang CT, Ong HC. Developments of metallic anodes with various compositions and surfaces for the microbial fuel cells. *Int J Hydrogen Energy* 2017;42:22235–42.
- [65] Karthikeyan R, Krishnaraj N, Selvam A, Wong JWC, Lee PKH, Leung MKH, Berchmans S. Effect of composites based nickel foam anode in microbial fuel cell using *Acetobacter acetii* and *Gluconobacter roseus* as a biocatalysts. *Bioresour Technol* 2016;217:113–20.
- [66] Uzoma AH, Ekwutosi OT, Onyeka AC. Comparative Study of Effects of Electrode Materials and Catholyte on Simultaneous Generation of Bioelectricity and Waste water Treatment. *Int J of Bioorganic Chemistry* 2016;1:8-20.
- [67] Jiang H, Yang L, Deng W, Tan Y, Xie Q. Macroporous graphitic carbon foam decorated with polydopamine as a high-performance anode for microbial fuel cell. *J Power Sources* 2017;363:27–33.

- 1 [68] Jiang H, Ali MA, Xu Z, Halverson LJ, Dong L. Integrated Microfluidic Flow-  
2 Through Microbial Fuel Cells. *Sci Rep* 2017;7:41208.  
3
- 4 [69] Kwok YH, Tsang ACH, Wang Y, Leung DYC. Ultra-fine Pt nanoparticles on  
5 graphene aerogel as a porous electrode with high stability for microfluidic methanol  
6 fuel cell. *J Power Sources* 2017;349:75–83.  
7  
8
- 9 [70] Cheng S, Wu J. Air-cathode preparation with activated carbon as catalyst, PTFE as  
10 binder and nickel foam as current collector for microbial fuel cells.  
11 *Bioelectrochemistry* 2013;92:22–6.  
12  
13
- 14 [71] Zhen G, Lu X, Kumar G, Bakonyi P, Xu K, Zhao Y. Microbial electrolysis cell  
15 platform for simulations waste biorefinery and clean electrofuels generation: Current  
16 situation, challenges and future perspectives. *Prog Energy Combust Sci* 2017;63:119-  
17 145.  
18  
19
- 20 [72] Wang Q, Dong H, Yu H, Yu H, Liu M. Enhanced electrochemical reduction of carbon  
21 dioxide to formic acid using a two-layer gas diffusion electrode in a microbial  
22 electrolysis cell. *RSC Adv* 2015;5:10346-10351.  
23  
24
- 25 [73] Zhang F, Cheng S, Pant D, Bogaert G Van, Logan BE. Power generation using an  
26 activated carbon and metal mesh cathode in a microbial fuel cell. *Electrochem*  
27 *Commun* 2009;11:2177–9.  
28  
29
- 30 [74] Zhang F, Saito T, Cheng S, Hickner MA, Logan BE. Microbial fuel cell cathodes with  
31 poly(dimethylsiloxane) diffusion layers constructed around stainless steel mesh  
32 current collectors. *Environ Sci Technol* 2010;44:1490–5.  
33  
34
- 35 [75] Taroco HA, Santos JAF, Domingues RZ, Matencio T. Ceramic Materials for Solid  
36 Oxide Fuel Cells. In: Sikalidis C, editor. *Adv. Ceram. - Synth. Charact. Process.*  
37 *Specif. Appl., Rijeka: InTech; 2011.*  
38  
39
- 40 [76] Costa R, Ansar A. Evolved Materials and Innovative Design for High Performance,  
41 Durable and Reliable SOFC Cell and Stack Presentation and Status of the European  
42 Project EVOLVE. *ECS Trans* 2013;57:533–41.  
43  
44
- 45 [77] Shao Z, Tadé MO. *Application of SOFC Technology. Intermed. Solid Oxide Fuel*  
46 *Cells, Springer, Berlin, Heidelberg; 2016, p. 247–66.*  
47  
48
- 49 [78] Sun C, Stimming U. Recent anode advances in solid oxide fuel cells. *J Power Sources*  
50 2007;171:247–60.  
51
- 52 [79] Hiraiwa C, Okuno K, Tawarayama H, Majima M, Nishimura J, Tsuchida H.  
53 *Application of Ni porous metal to solid oxide fuel cells. SEI Tech Rev* 2016.  
54  
55
- 56 [80] Zuo C, Liu M, Liu M. Solid oxide fuel cells. In: Aparicio M, Jitianu A, Klein, LC,  
57 editors. *Sol-gel processing for conventional and alternative energy, New York:*  
58 *Springer-Verlag; 2012, p. 7-36.*  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [81] Low QX, Huang W, Fu XZ, Melnik J, Luo JL, Chuang KT, Sanger AR. Copper coated nickel foam as current collector for H<sub>2</sub>S-containing syngas solid oxide fuel cells. *Appl Surf Sci* 2011;258:1014–20.
- [82] Stange M, Denonville C, Larring Y, Brevet A, Montani A, Sicardy O, Mouglin J, Larsson PO. Improvement of corrosion properties of porous alloy supports for solid oxide fuel cells. *Int J Hydrogen Energy* 2017;42:12485–95.
- [83] Yan N, Fu XZ, Luo JL, Chuang KT, Sanger AR. Ni-P coated Ni foam as coking resistant current collector for solid oxide fuel cells fed by syngas. *J Power Sources* 2012;198:164–9.
- [84] Arshad MS, Mushtaq N, Ahmad MA, Naseem S, Atiq S, Ahmed Z, Ali R, Abbas G, Raza R. Nickel foam anode-supported solid oxide fuel cells with composite electrolytes. *Int J Hydrogen Energy* 2017;42:22288–93.
- [85] Zeng S, Xu M, Parbey J, Yu G, Andersson M, Li Q, Li B, Li T. Thermal stress analysis of a planar anode-supported solid oxide fuel cell: Effects of anode porosity. *Int J Hydrogen Energy* 2017;42:20239-48
- [86] Costa R, Ansar A. Progress in the development of Nickel-less SOFCs : status of the EU project EVOLVE. 11th Eur SOFC SOE Forum 2014:B0150.
- [87] Han F, Semerad R, Constantin G, Dessemond L, Costa R. Beyond the 3rd Generation of Planar SOFC: Development of Metal Foam Supported Cells with Thin Film Electrolyte. *ECS Trans Electrochem Soc* 2015;68:1889–96.
- [88] Project finalize!. Evolve fuel cell, <http://www.evolve-fcell.eu/index.php/newsreader/items/project-completion-by-the-31st-of-january-2017.html>; 2017 [accessed 1 Oct 2017].
- [89] Gondolini A, Mercadelli E, Sangiorgi A, Sanson A. Integration of Ni-GDC layer on a NiCrAl metal foam for SOFC application. *J Eur Ceram Soc* 2017;37:1023–30.
- [90] Masson D, Abdallah B, Willot F, Jeulin D, Mercadelli E, Sanson A, Chesnaud A, Thorel A. Morphological Modelling of a Metal Foam Supported SOFC Configuration. *ECS Trans* 2015;68:2951–60.
- [91] Maznoy A, Kirdyashkin A, Kitler V, Solovyev A. Combustion synthesis and characterization of porous Ni-Al materials for metal-supported solid oxide fuel cells application. *J Alloys Compd* 2017;697:114–23
- [92] Matsuzaki Y, Yasuda I. Dependence of SOFC Cathode Degradation by Chromium-Containing Alloy on Compositions of Electrodes and Electrolytes. *J Electrochem Soc* 2001;148:A126.
- [93] Sadykov VA, Usoltsev V V, Fedorova YE, Sobyenin VA, Kalinin P V, Arzhannikov A V, Vlasov AY, Korobeinikov MV, Bryazgin AA, Salanov AN, Predtechenskii MR, Bobrenok OF, Ulikhin AS, Uvarov NF, Smorygo OL, Il'yushchenko AF, Ul'yanitskii VY, Zlobin SB. Design of Medium-Temperature Solid Oxide Fuel Cells on Porous

Supports of Deformation Strengthened Ni-Al Alloy. Russ J Electrochem 2011;47:488–93.

- [94] Sadykov V, Mezentseva N, Usoltsev V, Smorygo O, Mikutski V, Marukovich A, Bobrenok O, Uvarov N. Metal Supported SOFC on the Gradient Permeable Metal Foam Substrate. *Adv Mater Res* 2010;123–125:1083–6.
- [95] Solov'ev AA, Sochugov NS, Ionov IV, Kirdyashkin AI, Kitler VD, Maznoi AS, Maksimov YM, Sigfusson TI. Synthesis and investigation of porous Ni-Al substrates for solid-oxide fuel cells. *Inorg Mater Appl Res* 2013;4:431–7.
- [96] Molin S, Gazda M, Jasinski P. High temperature oxidation of porous alloys for solid oxide fuel cell applications. *Solid State Ionics* 2010;181:1214–20.
- [97] Venkatachalam V, Molin S, Chen M, Smirnov I, Larsson PO, Hendriksen PV, Bonanos N. Optimization of ferritic steel porous supports for protonic fuel cells working at 600 ° C. *Mater Sci Technol* 2014:1231–40.
- [98] Boccaccini D, Frandsen H, Sudireddy BR, Blennow P, Persson ÅH, Kwok K, Vang Hendriksen P. Creep behaviour of porous metal supports for solid oxide fuel cells. *Int J Hydrogen Energy* 2014;39:21569–21580.
- [99] Esposito L, Boccaccini DN, Pucillo GP, Frandsen HL. Secondary creep of porous metal supports for solid oxide fuel cells by a CDM approach. *Mater Sci Eng A* 2017;691:155–61.
- [100] Hiraiwa C, Tawarayama H, Ota H, Higashino T, Okuno K, Majima M. Long-term stability of Ni–Sn porous metals for cathode current collector in solid oxide fuel cells. *Int J Hydrogen Energy* 2017;42:12567–73.
- [101] Fu XZ, Melnik J, Low QX, Luo JL, Chuang KT, Sanger AR, Yang QM. Surface modified Ni foam as current collector for syngas solid oxide fuel cells with perovskite anode catalyst. *Int J Hydrogen Energy* 2010;35:11180–7.
- [102] Jung H, Bae K, Jang DY, Lee YH, Cha SW, Shim JH. Evaluation of porous platinum, nickel, and lanthanum strontium cobaltite as electrode materials for low-temperature solid oxide fuel cells. *Int. J. Hydrogen Energy* 2014;39:17828–35.
- [103] Dong J, Cheng Z, Zha S, Liu M. Identification of nickel sulfides on Ni-YSZ cermet exposed to H<sub>2</sub> fuel containing H<sub>2</sub>S using Raman spectroscopy. *J Power Sources* 2006;156:461–5.
- [104] Gross MD, Vohs JM, Gorte RJ. Recent progress in SOFC anodes for direct utilization of hydrocarbons. *J Mater Chem* 2007;17:3071.
- [105] Shaikh SPS, Muchtar A, Somalu MR. A review on the selection of anode materials for solid-oxide fuel cells. *Renew Sustain Energy Rev* 2015;51:1–8.
- [106] Sun C, Hui R, Roller J. Cathode materials for solid oxide fuel cells: A review. *J Solid State Electrochem* 2010;14:1125–44.

- 1 [107] Williford RE, Chick LA, Maupin GD, Simner SP, Stevenson JW. Diffusion  
2 Limitations in the Porous Anodes of SOFCs. *J Electrochem Soc* 2003;150:A1067.  
3  
4 [108] An J, Kim Y-B, Prinz FB. Ultra-thin platinum catalytic electrodes fabricated by  
5 atomic layer deposition. *Phys Chem Chem Phys* 2013;15:7520.  
6  
7 [109] Corbin SF, Clemmer RMC, Yang Q. Development and characterization of porous  
8 composites for solid oxide fuel cell anode conduction layers using ceramic-filled  
9 highly porous ni foam. *J Am Ceram Soc* 2009;92:331–7.  
10  
11 [110] Perry ML, Fuller TF. A Historical Perspective of Fuel Cell Technology in the 20th  
12 Century. *J Electrochem Soc* 2002;149:S59.  
13  
14 [111] Kamarudin MZF, Kamarudin SK, Masdar MS, Daud WRW. Review: Direct ethanol  
15 fuel cells. *Int J Hydrogen Energy* 2013;38:9438–53.  
16  
17 [112] Yang Y Lou, Liu XH, Hao MQ, Zhang PP. Performance of a low-cost direct glucose  
18 fuel cell with an anion-exchange membrane. *Int J Hydrogen Energy* 2015;40:10979–  
19 84.  
20  
21 [113] Cao D, Gao Y, Wang G, Miao R, Liu Y. A direct NaBH<sub>4</sub>-H<sub>2</sub>O<sub>2</sub> fuel cell using Ni  
22 foam supported Au nanoparticles as electrodes. *Int J Hydrogen Energy* 2010;35:807–  
23 13.  
24  
25 [114] Merle G, Wessling M, Nijmeijer K. Anion exchange membranes for alkaline fuel  
26 cells: A review. *J Memb Sci* 2011;377:1–35.  
27  
28 [115] Blizanac BB, Ross PN, Markovic NM. Oxygen electroreduction on Ag(111): The pH  
29 effect. *Electrochim Acta* 2007;52:2264–71.  
30  
31 [116] Fujiwara N, Yamazaki S ichi, Siroma Z, Ioroi T, Senoh H, Yasuda K. Nonenzymatic  
32 glucose fuel cells with an anion exchange membrane as an electrolyte. *Electrochem*  
33 *Commun* 2009;11:390–2.  
34  
35 [117] Chen J, Zhao CX, Zhi MM, Wang K, Deng L, Xu G. Alkaline direct oxidation  
36 glucose fuel cell system using silver/nickel foams as electrodes. *Electrochim Acta*  
37 2012;66:133–8.  
38  
39 [118] Spets JP, Kuosa MA, Kiros Y, Anttila T, Rantanen J, Lampinen MJ, Saari K.  
40 Enhancement of glucose electro-oxidation by an external electromagnetic field in  
41 direct-mode fuel cells. *J Power Sources* 2010;195:475–9.  
42  
43 [119] Bidault F, Brett DJL, Middleton PH, Brandon NP. Review of gas diffusion cathodes  
44 for alkaline fuel cells. *J Power Sources* 2009;187:39–48.  
45  
46 [120] Bidault F, Brett DJL, Middleton PH, Abson N, Brandon NP. A new application for  
47 nickel foam in alkaline fuel cells. *Int J Hydrogen Energy* 2009;34:6799–808.  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [121] Bidault F, Brett DJL, Middleton PH, Abson N, Brandon NP. An improved cathode for alkaline fuel cells. *Int J Hydrogen Energy* 2010;35:1783–8.
  - [122] Bidault F, Kucernak A. A novel cathode for alkaline fuel cells based on a porous silver membrane. *J Power Sources* 2010;195:2549–56.
  - [123] Bidault F, Kucernak A. Cathode development for alkaline fuel cells based on a porous silver membrane. *J Power Sources* 2011;196:4950–6.
  - [124] Li YS, Zhao TS. A high-performance integrated electrode for anion-exchange membrane direct ethanol fuel cells. *Int J Hydrogen Energy* 2011;36:7707–13.
  - [125] Zhao CX, Wang K, Yan H, Xu Gu. Output current increase in alkaline glucose fuel cells. *J. of the Electrochemical Society* 2011;158:B1055-B1059
  - [126] Chen J, Zheng H, Kang J, Yang F, Cao Y, Xiang M. An alkaline direct oxidation glucose fuel cell using three-dimensional structural Au/Ni-foam as catalytic electrodes. *RSC Adv* 2017;7:3035–42.
  - [127] Ma J, Sahai Y. Effect of electrode fabrication method and substrate material on performance of alkaline fuel cells. *Electrochem Commun* 2013;30:63–6.
  - [128] Li Y, He Y. Layer reduction method for fabricating Pd-coated Ni foams as high-performance ethanol electrode for anion-exchange membrane fuel cells. *RSC Adv* 2014;4:16879.
  - [129] An L, Zhao TS, Chen R, Wu QX. A novel direct ethanol fuel cell with high power density. *J Power Sources* 2011;196:6219–22.
  - [130] An L, Zhao TS, Xu JB. A bi-functional cathode structure for alkaline-acid direct ethanol fuel cells. *Int J Hydrogen Energy* 2011;36:13089–95.
  - [131] Gu L, Luo N, Miley GH. Cathode electrocatalyst selection and deposition for a direct borohydride/hydrogen peroxide fuel cell. *J Power Sources* 2007;173:77–85.
  - [132] Li YS, Zhao TS. Understanding the performance degradation of anion-exchange membrane direct ethanol fuel cells. *Int J Hydrogen Energy* 2012;37:4413–21.
  - [133] Kucernak A, Bidault F, Smith G. Membrane electrode assemblies based on porous silver electrodes for alkaline anion exchange membrane fuel cells. *Electrochim. Acta* 2014;82:284–90.
  - [134] Millington B, Whipple V, Pollet BG. A novel method for preparing proton exchange membrane fuel cell electrodes by the ultrasonic-spray technique. *J Power Sources* 2011;196:8500–8.
  - [135] Tian ZQ, Lim SH, Poh CK, Tang Z, Xia Z, Luo Z, Shen PK, Chua D, Feng YP, Shen Z, Lin J. A highly order-structured membrane electrode assembly with vertically aligned carbon nanotubes for ultra-low Pt loading PEM fuel cells. *Adv Energy Mater* 2011;1:1205–14.



- 1 [136] Wang YL, Zhao YQ, Xu CL, Zhao DD, Xu MW, Su ZX, Li HL. Improved  
2 performance of Pd electrocatalyst supported on three-dimensional nickel foam for  
3 direct ethanol fuel cells. *J Power Sources* 2010;195:6496–9.  
4  
5 [137] An L, Zhao TS. Transport phenomena in alkaline direct ethanol fuel cells for  
6 sustainable energy production. *J Power Sources* 2017;341:199–211.  
7  
8 [138] An L, Chai ZH, Zeng L, Tan P, Zhao TS. Mathematical modeling of alkaline direct  
9 ethanol fuel cells. *Int J Hydrogen Energy* 2013;38:14067–75.  
10  
11 [139] Yang WW, Lu MY, He YL. Performance study of an alkaline direct ethanol fuel cell  
12 with a reduced two-dimensional mass transport model. *Int J Hydrogen Energy*  
13 2016;41:20693–708.  
14  
15 [140] Sopian K, Alghoul MA, Alfegi EM, Sulaiman MY, Musa EA. Evaluation of thermal  
16 efficiency of double-pass solar collector with porous-nonporous media. *Renew*  
17 *Energy* 2009;34:640–5.  
18  
19 [141] Naphon P. Effect of porous media on the performance of the double-pass flat plate  
20 solar air heater. *Int Commun Heat Mass Transf* 2005;32:140–50.  
21  
22 [142] Chen CC, Huang PC. Numerical study of heat transfer enhancement for a novel flat-  
23 plate solar water collector using metal-foam blocks. *Int J Heat Mass Transf*  
24 2012;55:6734–56.  
25  
26 [143] Chen Z, Gu M, Peng D. Heat transfer performance analysis of a solar flat-plate  
27 collector with an integrated metal foam porous structure filled with paraffin. *Appl*  
28 *Therm Eng* 2010;30:1967–73.  
29  
30 [144] Jouybari HJ, Saedodin S, Zamzamian A, Nimvari ME, Wongwises S. Effects of  
31 porous material and nanoparticles on the thermal performance of a flat plate solar  
32 collector: An experimental study. *Renew Energy* 2017;114:1407–18.  
33  
34 [145] He Q, Zeng S, Wang S. Experimental investigation on the efficiency of flat-plate solar  
35 collectors with nanofluids. *Appl Therm Eng* 2014;88:165–71.  
36  
37 [146] Chaji H, Ajabshirchi Y, Esmaeilzadeh E, Heris SZ, Hedayatizadeh M, Kahani M.  
38 Experimental study on thermal efficiency of flat plate solar collector using tio<sub>2</sub>/water  
39 nanofluid. *Mod Appl Sci* 2013;7:60–9.  
40  
41 [147] Moghadam AJ, Farzane-Gord M, Sajadi M, Hoseyn-Zadeh M. Effects of CuO/water  
42 nanofluid on the efficiency of a flat-plate solar collector. *Exp Therm Fluid Sci*  
43 2014;58:9–14.  
44  
45 [148] Lim S, Kang Y, Lee H, Shin S. Design optimization of a tubular solar receiver with a  
46 porous medium. *Appl Therm Eng* 2014;62:566–72.  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [149] Reddy KS, Ravi Kumar K, Ajay CS. Experimental investigation of porous disc enhanced receiver for solar parabolic trough collector. *Renew Energy* 2015;77:308–19.
  - [150] Baskar.P, Edison G, Ravikumar.T.S, Sathyamurthy R. Modeling, simulation and performance analysis of porous disc receiver for solar parabolic trough collector. *Int J Sci Eng Res* 2013;4:108–11.
  - [151] Becker M, Fend T, Hoffschmidt B, Pitz-Paal R, Reutter O, Stamatov V, Steven M, Trimis D. Theoretical and numerical investigation of flow stability in porous materials applied as volumetric solar receivers. *Sol Energy* 2006;80:1241–8.
  - [152] Wu Z, Caliot C, Bai F, Flamant G, Wang Z, Zhang J, Tian C. Experimental and numerical studies of the pressure drop in ceramic foams for volumetric solar receiver applications. *Appl Energy* 2010;87:504–13.
  - [153] Michailidis N, Stergioudi F, Omar H, Missirlis D, Vlahostergios Z, Tsipas S, Albanakis C, Granier B. Flow, thermal and structural application of Ni-foam as volumetric solar receiver. *Sol Energy Mater Sol Cells* 2013;109:185–91.
  - [154] Huang PC, Chen CC, Hwang HY. Thermal enhancement in a flat-plate solar water collector by flow pulsation and metal-foam blocks. *Int J Heat Mass Transf* 2013;61:696–720.
  - [155] Rabadi NJ, Mismar SA. Enhancing solar energy collection by using curved flow technology coupled with flow in porous media: An experimental study. *Sol Energy* 2003;75:261–8.
  - [156] Xu H, Gong L, Huang S, Xu M. Non-equilibrium heat transfer in metal-foam solar collector with no-slip boundary condition. *Int J Heat Mass Transf* 2014;76:357–65.
  - [157] Tian Y, Zhao CY. A review of solar collectors and thermal energy storage in solar thermal applications. *Appl Energy* 2013;104:538–53.
  - [158] Kasaeian A, Eshghi AT, Sameti M. A review on the applications of nanofluids in solar energy systems. *Renew Sustain Energy Rev* 2015;43:584–98.
  - [159] Pandey KM, Chaurasiya R. A review on analysis and development of solar flat plate collector. *Renew Sustain Energy Rev* 2017;67:641–50.
  - [160] Mesalhy O, Lafdi K, Elgafy A, Bowman K. Numerical study for enhancing the thermal conductivity of phase change material (PCM) storage using high thermal conductivity porous matrix. *Energy Convers Manag* 2005;46:847–67.
  - [161] Xiao X, Zhang P, Li M. Preparation and thermal characterization of paraffin/metal foam composite phase change material. *Appl Energy* 2013;112:1357–66.
  - [162] Chen Z, Gao D, Shi J. Experimental and numerical study on melting of phase change materials in metal foams at pore scale. *Int J Heat Mass Transf* 2014;72:646–55.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [163] Wu ZG, Zhao CY. Experimental investigations of porous materials in high temperature thermal energy storage systems. *Sol Energy* 2011;85:1371–80.
  - [164] Zhao CY, Lu W, Tian Y. Heat transfer enhancement for thermal energy storage using metal foams embedded within phase change materials (PCMs). *Sol Energy* 2010;84:1402–12.
  - [165] Yang X, Meng X, Wang Z, Jin L, Zhang Q, Zhang Q, Lu T. Direct Numerical Simulation on Melting Phase Change Behavior in Open-cell Metal Foam. *Energy Procedia* 2017; 105:4254–9.
  - [166] Badenhorst H, Fox N, Mutalib A. The use of graphite foams for simultaneous collection and storage of concentrated solar energy. *Carbon N Y* 2016;99:17–25.
  - [167] Xu H, Sze JY, Romagnoli A, Py X. Selection of Phase Change Material for Thermal Energy Storage in Solar Air Conditioning Systems. *Energy Procedia* 2017;105:4281–8.

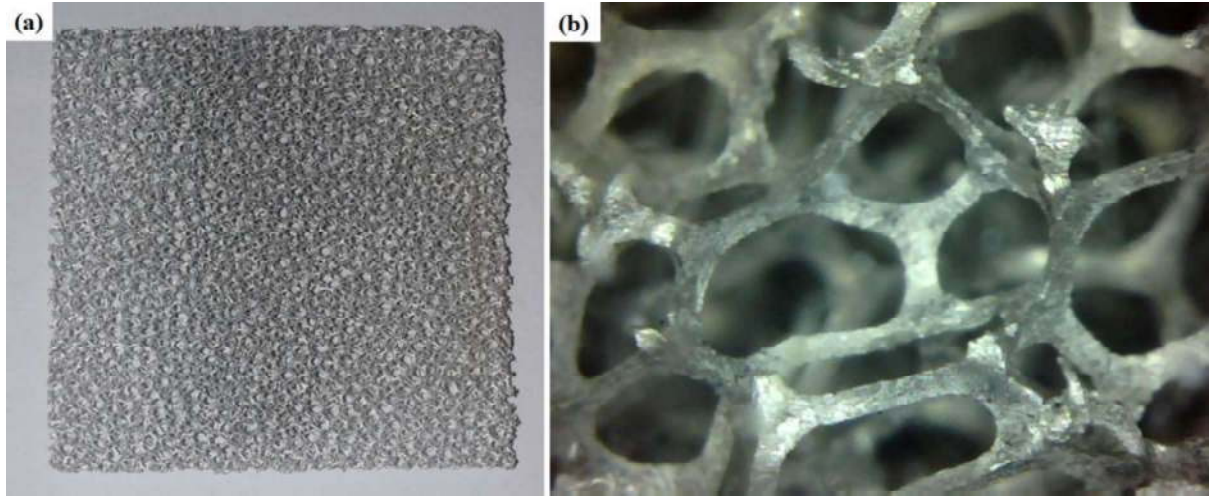


Fig. 1. a) Aluminium foam sample and b) close view of the aluminium foam structure [12].

Figure 2

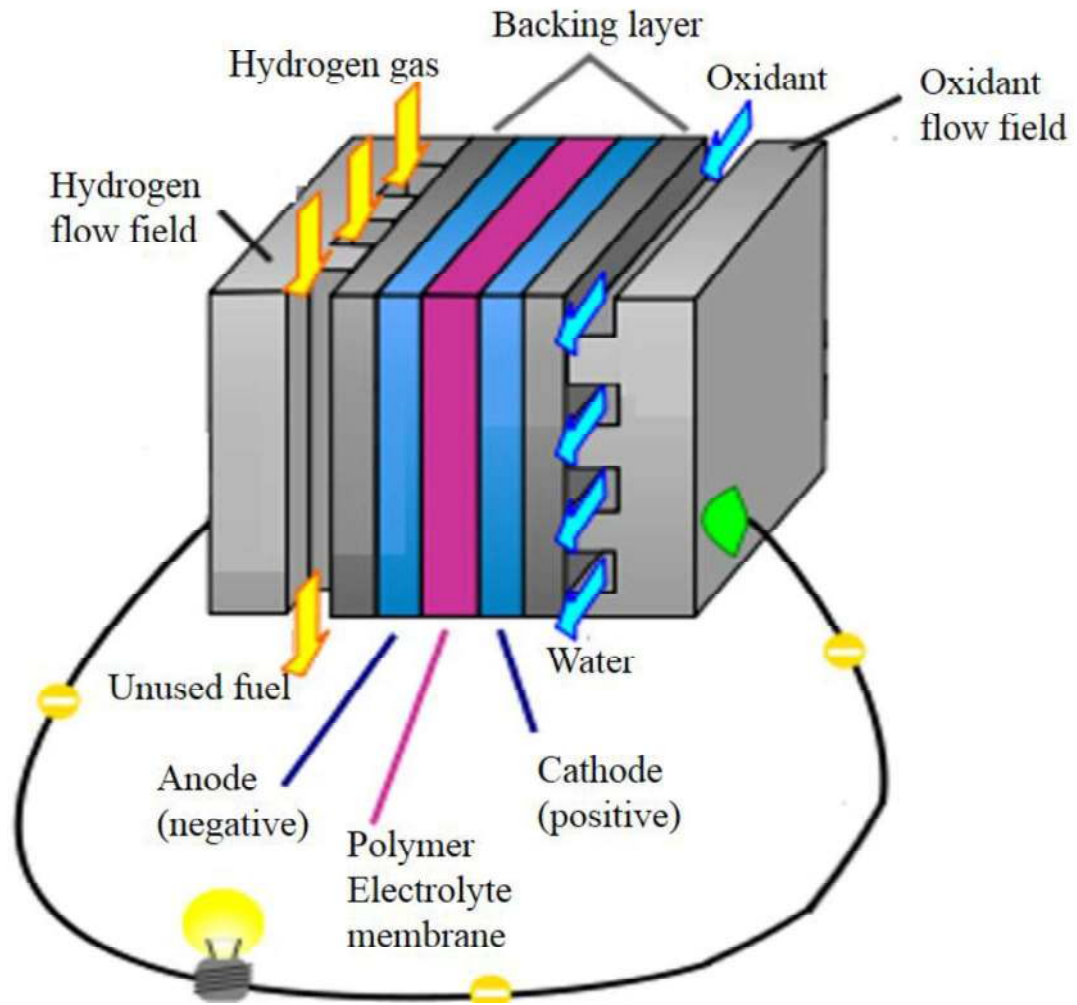


Fig. 2. Proton Exchange Membrane Fuel Cell design [15].

Figure 3

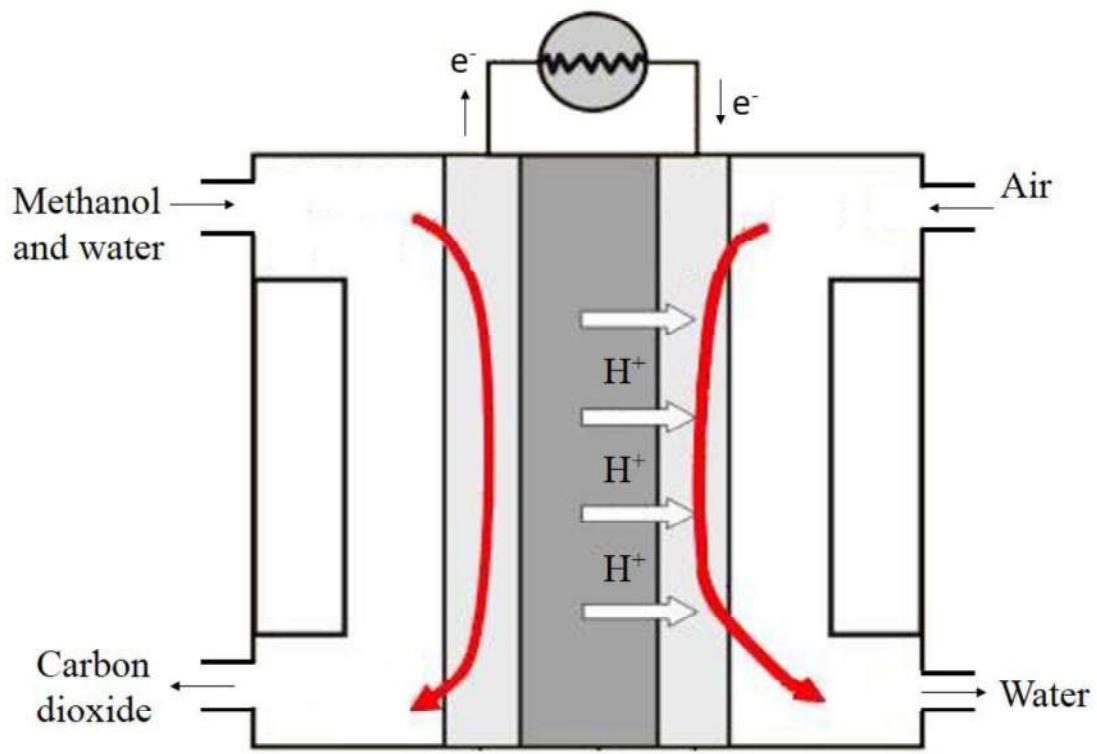


Fig. 3. Schematic diagram of a Direct Methanol Fuel Cell [40].

Figure 4

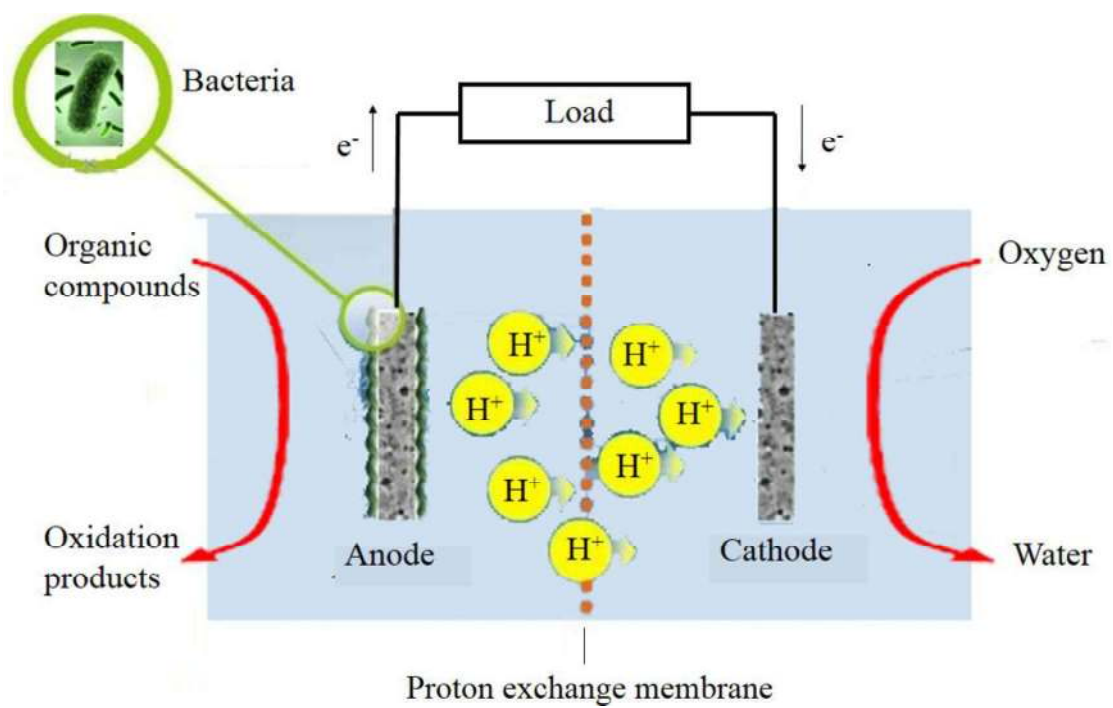


Fig. 4. Schematic diagram of a Microbial Fuel Cell [58].

Figure 5

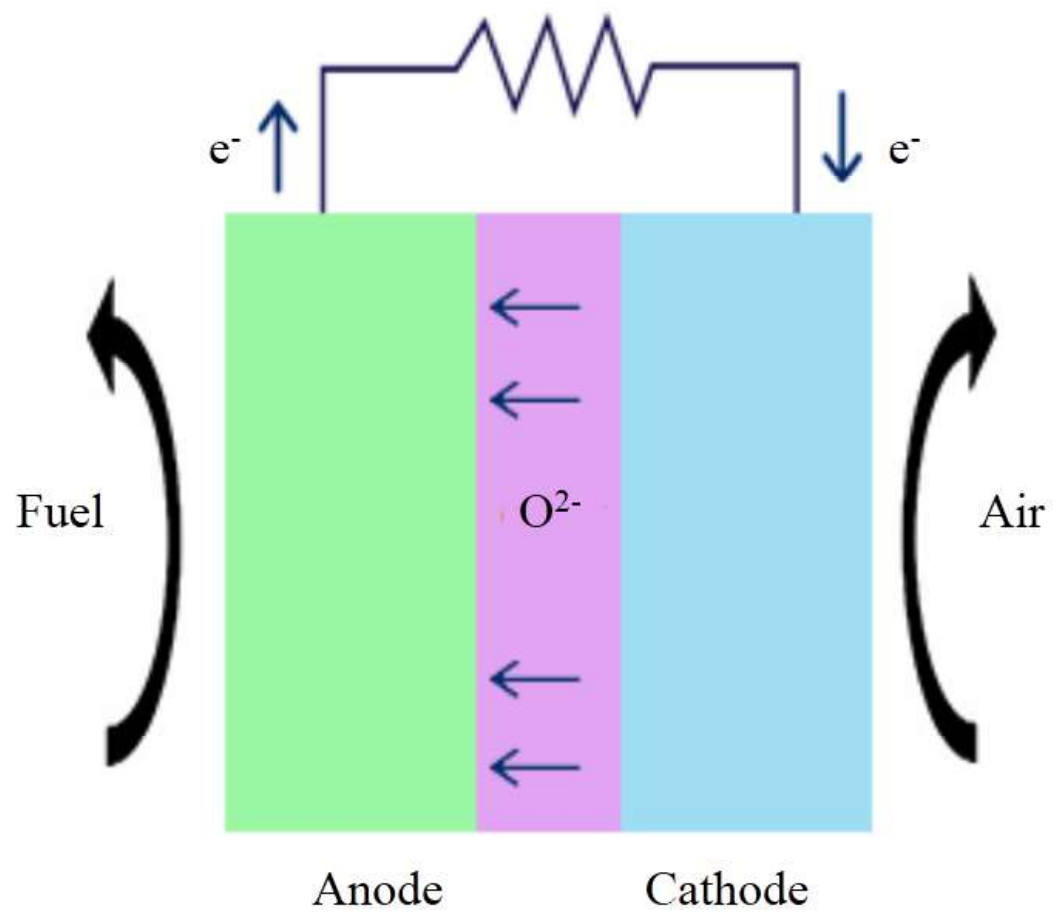


Fig. 5. Structure of a Solid Oxide Fuel Cell [78].



Figure 6

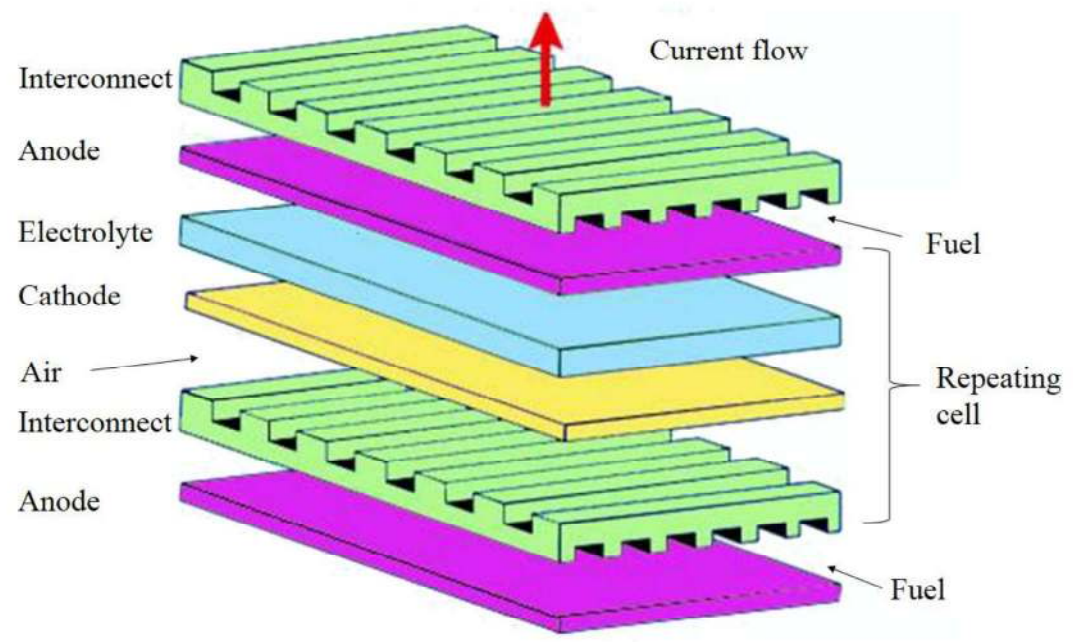


Fig. 6. Construction layout of the Solid Oxide Fuel Cell stack [80].

Figure 7

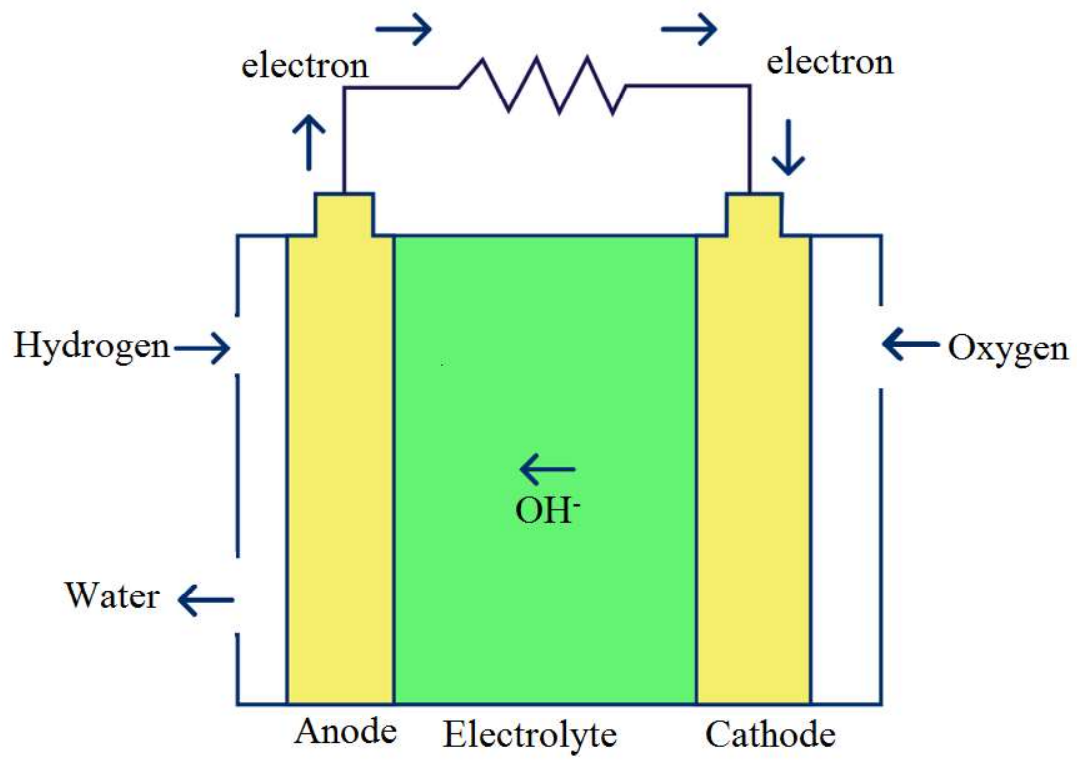


Fig. 7. Schematic diagram of an Alkaline Fuel Cell [40].

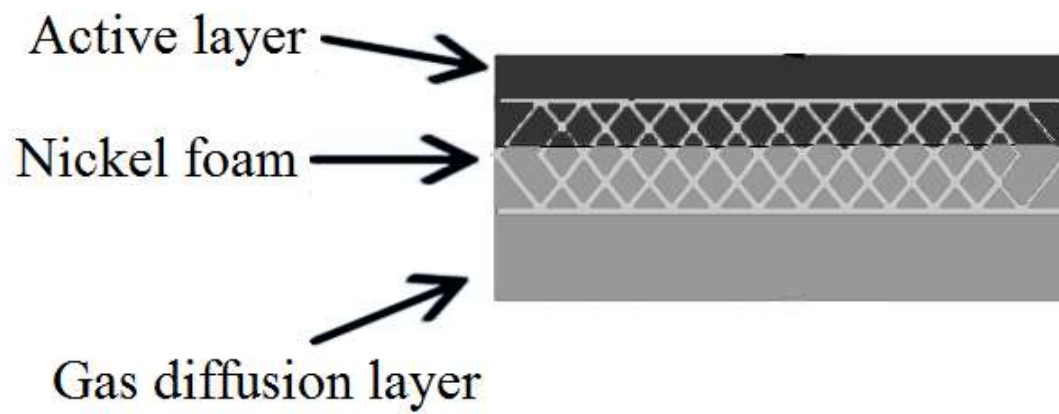


Fig. 8. Schematic diagram of an integrated cathode electrode [121].

Figure 9

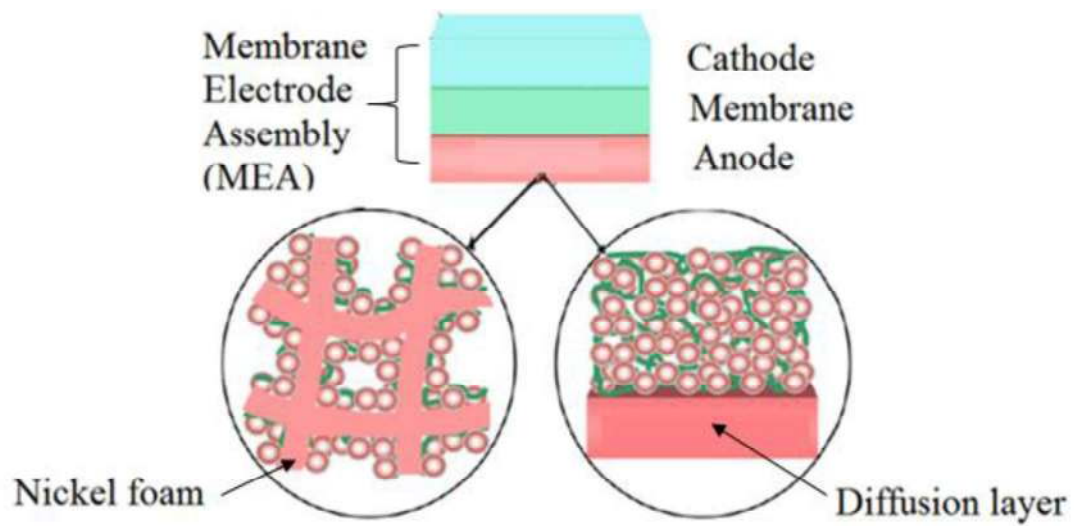


Fig. 9. Diagram of an anode structure: newly developed integrated anode electrode (left), conventional anode electrode (right) [124].

Figure 10

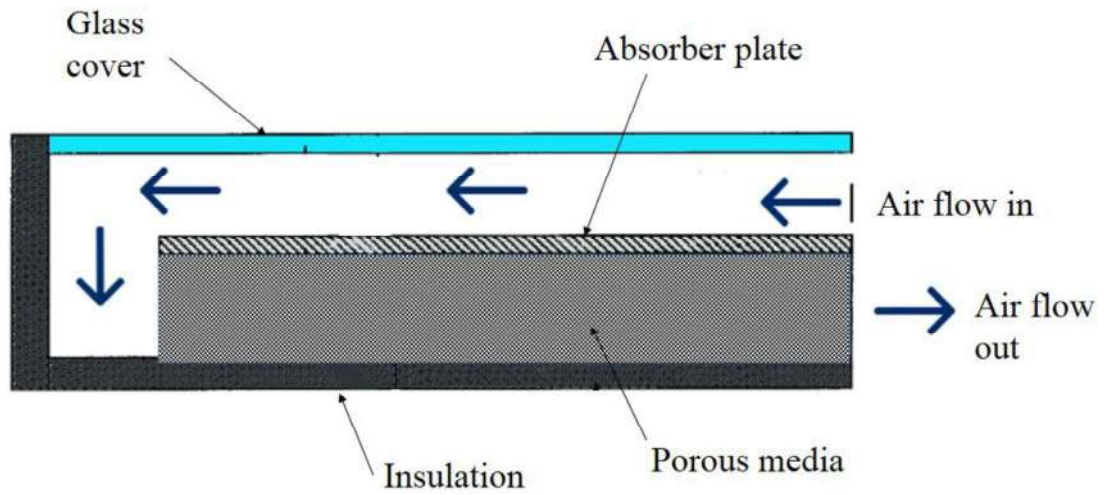


Fig. 10. Schematic diagram of a double-pass thermal solar collector with porous media in the second channel [8].

Figure 11

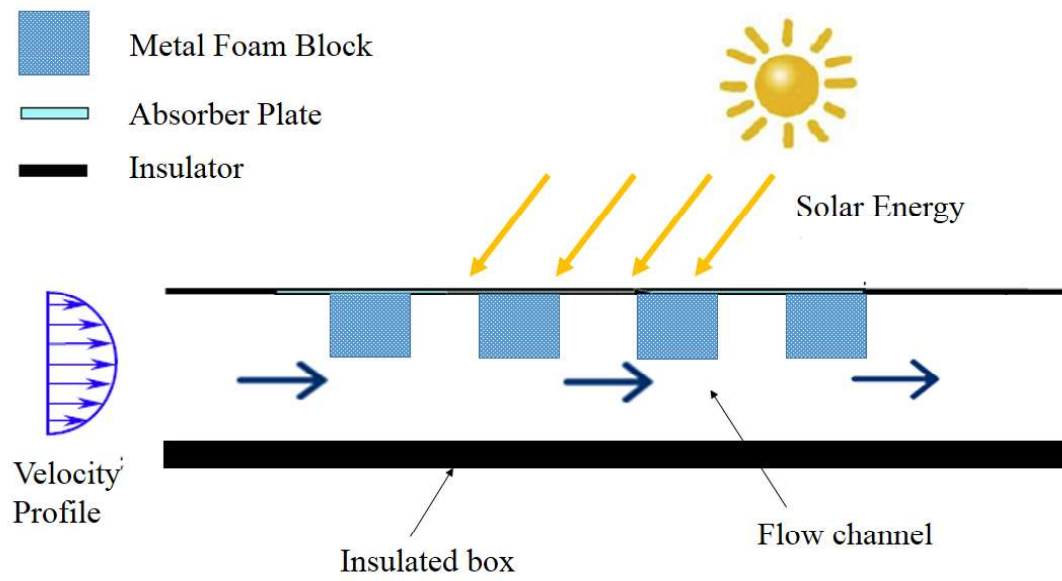


Fig. 11. Schematic diagram of a flat-plate solar collector [142].

Figure 12

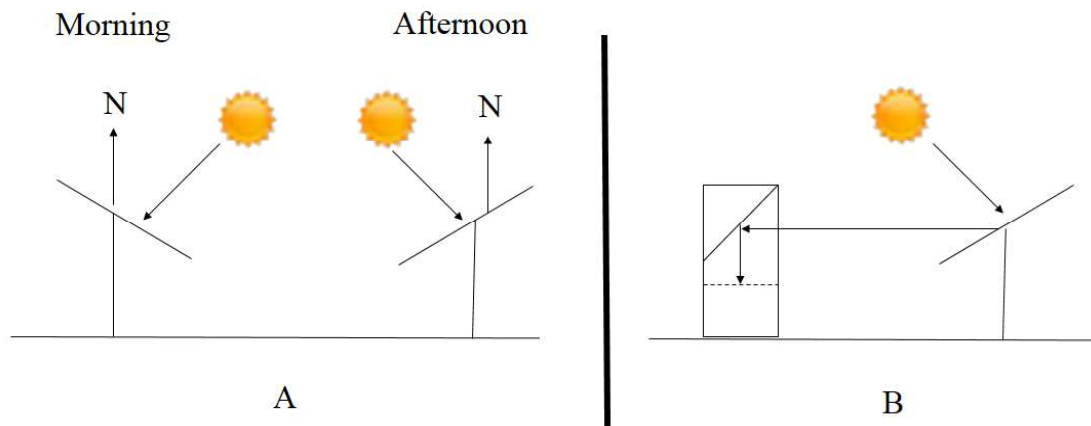


Fig. 12. Illustration of tracking system from morning to afternoon [166].

Table 1. Example of Microbes and its corresponding substrate [59].

Microbes	Substrate
Actinobacillus Succinogenes	Glucose
Escherichia Coli	Glucose, Sucrose
Clostridium Butyricum	Starch, Glucose, Lactate, Molasses
Aeromonas Hydrophilia	Acetate
Desulfovibrio Desulfuricans	Sucrose



Table 2. Example of substrate with its corresponding the power density [60].

Substrates	Power produced in mA.cm <sup>-2</sup>
Lactate	0.005
1,2-Dichloroethane	0.008
Cysteine	0.0186
Ethanol	0.025
Propionate	0.035
Carboxymethyl cellulose	0.05
Azo dye with glucose	0.09
Phenol	0.1
Furfural	0.17
Sucrose	0.19
Sodium formate	0.22
Mannitol	0.58
Starch	0.62
Sorbitol	0.62
Arabitol	0.68
Glucose	0.70
Xylitol	0.71
Ribitol	0.73
Xylose	0.74
Galactitol	0.78
Acetate	0.8
Glucuronic acid	1.18

## Highlights

- This article reviews the past research on metal foam in fuel cell and solar power systems.
- Metal foam applications on bipolar plates, electrodes and the gas diffusion layer in a fuel cell.
- Metal foam as a thermal management system in solar power systems.
- Barriers and future perspectives of metal foam applications in fuel cells and solar power systems.