

Photocatalytic degradation of azo dye Orange II in aqueous solutions using copper-impregnated titania

N. Divya · A. Bansal · A. K. Jana

Received: 13 October 2011 / Revised: 30 January 2012 / Accepted: 27 July 2012 / Published online: 17 April 2013
© Islamic Azad University (IAU) 2013

Abstract During dyeing process, industries consume large quantity of water and subsequently produce large volume of wastewater. This wastewater is rich in color and contains different dyes. Orange II is one of them. In this article, metal-impregnated TiO₂ P-25 catalyst was used to enhance the photocatalytic degradation of Orange II dye. Photodegradation percentage was followed spectrophotometrically by the measurements of absorbance at $\lambda_{\text{max}} = 483$ nm. The effect of copper-impregnated TiO₂ P-25 photocatalyst for the degradation of Orange II has been investigated in terms of percentage removal of color, chemical oxygen demand (COD) and total organic carbon (TOC). As such 98 % color removal efficiency, 97 % percentage removal of COD and 89 % percentage removal of TOC was achieved with TiO₂ P-25/Cu catalysts under typical conditions. Copper-impregnated TiO₂ P-25 photocatalyst showed comparatively higher activity than UV/H₂O₂ homogeneous photodegradation. The relative electrical energy consumption for photocatalytic degradation was considerably lower with TiO₂ P-25/Cu photocatalyst

than that with homogeneous photodegradation. Transmission electron microscopic analysis was used for catalyst characterization.

Keywords Degradation · Electrical energy requirement per order · Mineralization · Orange II · Photocatalyst · Transmission electron microscopic analysis

Introduction

An effective treatment is necessary for the degradation of harmful dye, which is discharged into the surface waters. In many industries (textile, leather, plastics, paper, food and cosmetics) dyes are used as a coloring agent. More than one million tons of dyes annually produced in the world are azo dyes (Cho and Zoh 2007; Somasiri et al. 2006). 10–15 % of the total used colorants are discharged into effluent during their synthesis and dyeing processes (Dave and Dave 2009; Divya et al. 2009). The resulting effluent may contain some components or moieties that could be toxic, carcinogenic or mutagenic to aquatic life. Photocatalysis has emerged as an effective and promising technique among advanced oxidation processes (AOPs) for the degradation of these organic pollutants in wastewater (Behnajady et al. 2008). During photocatalysis very powerful oxidizing agent hydroxyl radical (OH[·]) and/or superoxide radical (O₂^{·-}) are generated. The oxidizing agent is responsible to destroys hazardous pollutants.

Complex organic pollutants such as dyes can completely be mineralized using suitable photocatalyst. The organic pollutants react with the oxidizers to form CO₂, water and dilute concentration of simple mineral acids. The semiconductor may be in the form of a powder suspended in the





N. Divya
Department of Chemical Engineering, National Institute of Technology, Bhopal 462051, Madhya Pradesh, India

A. Bansal (✉)
Department of Chemical Engineering, National Institute of Technology, Jalandhar 144011, Punjab, India
e-mail: drajaybansal@gmail.com

A. K. Jana
Department of Biotechnology, National Institute of Technology, Jalandhar 144011, Punjab, India

water or coated on a support. Heterogeneous photodegradation has proved to be an effective and promising method among AOPs for the degradation of various organic pollutants including dyes in wastewater (Daneshvar et al. 2004).

The combination of different semiconductors (such as TiO₂, ZnO, Fe₂O₃, CdS and ZnS) with UV/solar lights are used in photocatalysis. But titanium dioxide is the most widely studied catalyst using its physical and chemical stability, low cost, ease of availability, non-toxicity and electronic and optical property (Goncalves et al. 2005). The mechanism of photodegradation of organic compounds by UV/TiO₂ as described by (Wu 2008) as follows:



The OH[·] radicals are principally responsible for the degradation of organic compounds. Oxygen serves as an efficient electron trap (Eq. 4), which prevents the recombination of electrons and photogenerated holes. If oxygen is limited, rapid recombination of photo produced electrons and holes in TiO₂ lowers the efficiency of the photocatalytic reactions; consequently the usefulness of such a system has limited practical application (Wu 2008). The addition of oxidants eliminates the recombination process as the added oxidants rapidly react with conduction band electrons, generating extremely reactive oxidizing radicals, which increases the efficiency of TiO₂. Some times TiO₂ catalysts have been used with supported adsorbent (Bhattacharyya et al. 2004).

The photoactivity of TiO₂ is altered by doping with transition metals like Pt, Pd, Au, Ag, Mn, Fe and Cu or oxides such as WO₃, which act as charge separators of the photo-induced electron/hole pair (Arabatzis et al. 2003; Arana et al. 2005; Galindo et al. 2000; Gracien et al. 2007; Gupta et al. 2006; Tokumura et al. 2006; Zhao et al. 2007). The combination of semiconductor substrate and metal cluster gives improved photocatalytic activity by trapping the photo-induced charge carriers, thereby improving the charge transfer processes (Nasr-Esfahani and Habibi 2008). They may enhance the electron–hole separation by acting as electron traps, extend the light absorption into the visible range, enhance surface electron excitation and modify the surface properties of photocatalysts.

In the recent years, copper ions are used for metal doping/deposition, because of their novel effects on the improvement of photoactivity of semiconductor photocatalysis nanocrystallites (Sahoo et al. 2005). It effectively retards the recombination of photogenerated electrons and holes. This process has shown to improve the overall efficiency for a number of photocatalytic reactions (Behnajady et al. 2008; Sahoo et al. 2005; Menendez-Flores et al. 2008).

Orange II azo dye is one of the organic compounds found in the textile wastewaters. It has a high photo and thermal stability. It is carcinogenic and mutagenic and affects the aquatic life seriously. In the present study the degradation of Orange II has been investigated for homogeneous and heterogeneous conditions involving UV/H₂O₂ and TiO₂ P-25. TiO₂ P-25 catalyst has been impregnated with copper metal ions to study the degradation of Orange II dye in aqueous solution. H₂O₂ has been used to inhibit the recombination of electron/hole pairs and improve the photodegradation efficiency (Luo et al., 2002).

The effect of impregnated TiO₂ on dye degradation has been discussed in terms of color removal, percentage removal of COD and TOC. The degradation kinetics was also studied. This research has been carried out in the Chemical Engineering Department, National Institute of Technology, Jalandhar (Punjab, India), from February to April 2009.

Materials and methods

Reagents

Degussa TiO₂ P-25, procured from Evonic (Degussa), Germany, was used as a photocatalyst. It is 80 % anatase and 20 % rutile and has a BET surface area of 50 m²/g. The Orange II (85 % dye content), H₂O₂ (30 % w/v), HCl (34 %), sodium hydroxide pellets purified (NaOH), ferrous ammonium sulphate (NH₃(FeSO₄)₂·6H₂O), potassium dichromate (K₂Cr₂O₇), silver sulphate (AgSO₄), mercury sulphate (HgSO₄), sulphuric acid (H₂SO₄) were procured from S.D. Fine Chemicals Limited, Mumbai, India. Ferroin indicator, copper nitrate [Cu(NO₃)₂] were procured from Qualigens Fine Chemicals Limited, Mumbai, India. They were used without any further treatment or purification.

Preparation of TiO₂ P-25/Cu-modified nano-size titania-based catalyst

Modification of catalyst was done using impregnation method. Metal ion doped TiO₂ (Degussa P-25) was prepared using the following procedure. The titania-based photocatalyst employed was commercial titanium dioxide

powder (Degussa P-25). The doping was done using transition metal salt $\text{Cu}(\text{NO}_3)_2$. 0.0018 mol of $\text{Cu}(\text{NO}_3)_2$ was dissolved in 30 ml of distilled water in a porcelain bowl. 0.99 mol of TiO_2 was then added to the solution. The solution was stirred well and was allowed to stand for 24 h. The contents were heated at $100 \pm 5^\circ\text{C}$ to evaporate all the water. The dried solids were first ground and then calcined at 400°C for 6 h in a muffle furnace.

Irradiation experiments

All experiments were carried out in a batch photoreactor. The radiation source consisted of two 15 W UV tubes (F15T8/GL), positioned on opposite sides of the cabinet interior nearer to top. The details of photochemical reactor are available elsewhere (Divya et al. 2009; Liu and Chiou 2005).

Stock solution of the dye (1,000 ppm) was prepared with double distilled water from which working solution (50, 100 ppm, etc.) was prepared. Then solution pH value was adjusted to 3.0 using 0.1 N NaOH and 0.1 N HCl. For homogeneous photodegradation, 20 ml of the working solution of the dye (50 ppm) was taken in a beaker then H_2O_2 was added. The zero time reading was taken and the solution was then subjected to irradiation. Aliquots were taken at regular intervals to analyze the percent degradation of the dye. In case of heterogeneous photocatalysts, titania-based catalyst was added along with H_2O_2 . The solution was then subjected to continuous stirring for 60 min in dark and the rest of the procedure was same as that for homogeneous photodegradation.

Analysis

The degradation of Orange II was measured with UV–vis spectrophotometer (LaMotte, USA). A calibration plot based on Beer–Lambert’s law was established by relating the absorbance to the concentration. The measurement of maximum absorbance was taken for Orange II was 483 nm. The decolorization has been reported and discussed in terms of, η , photodegradation efficiency (Divya et al. 2009). The total mineralization of Orange II has been measured by using the disappearance of the total organic carbon (TOC) and chemical oxygen demand (COD). Estimation of TOC and COD had been done by standard methods. The efficiency of dye mineralization was estimated using the following expressions (Aleboyeh et al. 2008):

$$\text{Mineralization \%} = \left[1 - \frac{\text{COD (or TOC)}}{\text{COD}_0 \text{ (or TOC}_0)} \right] \times 100 \quad (8)$$

where COD, TOC correspond to time t and COD_0 , TOC_0 correspond to initial conditions.

To check the reproducibility of the experimental system some sets of experiments were repeated under similar conditions. The uncertainty in experimental system was calculated in term of square root mean error (SRME), given as follows:

$$\text{Square root mean error} = \sqrt{\left\{ \sum \frac{(\eta_1 - \eta_2)^2}{N} \right\}}$$

where, η_1 = degradation efficiency during first run, η_2 = degradation efficiency during second run and N = no. of turn efficiency observed.

The SRME observed for the experimental system was found to be less than or equal to $\pm 2\%$.

Characterization of catalysts using transmission electron microscopy

Transmission electron microscopy (TEM) can give a real space image on the distribution of particles, their surface and shape. With a finely focused electron probe, not only imaging of materials is possible, but also a single particle can be identified. Besides, electron microscopy shows the shape and state of particles. Samples were placed onto a carbon-coated copper grid (400 holes) by physically interacting the grid and powders, and analyzed to see the particles that remained adhered to the grids. Detailed surface images of photocatalyst were obtained by transmission electron microscope (TEM). The TEM studies were performed using a Hitachi 7500 (SAIF, Panjab University, Chandigarh).

The crystallite morphology of the P-25 TiO_2 in solid-state and transition metal modified P-25 TiO_2 based catalysts were observed by transmission electron microscopy (TEM) (Fig. 1). TEM of powder catalyst was performed at 100 kV. It was observed that the mean particle size of P-25 TiO_2 was 10 ± 2 nm (Fig. 1a) observed at $300,000\times$ direct magnification. Deposited Cu particle (Fig. 1b) size was in the range of 3–4 nm at $500,000\times$ direct magnification (Fig. 1b). The nano-sized modified photocatalyst was subjected to the removal of color, COD and TOC of Orange II in aqueous solution. The results obtained are discussed as follows.

Results and discussion

Series of experiments were conducted for the photocatalytic degradation of Orange II azo dye. The physical and

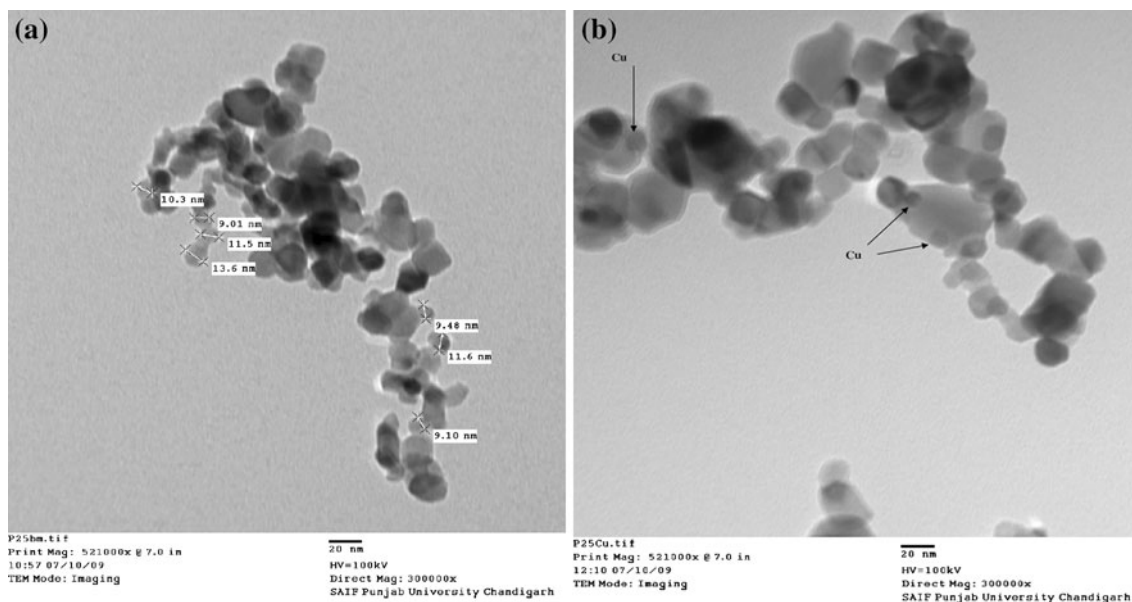


Fig. 1 Transmission electron microscopy (TEM) of **a** TiO₂ P-25 and **b** copper modified TiO₂ P-25/Cu and modified catalysts

Table 1 Physical and chemical characteristics of dye

Title	Properties
Dye name	Orange II
Abbreviation	AO7, OII
Generic name	Acid Orange 7
Color index (CI)	15,510
Appearance	Orange powder
Chemical formula	C ₁₆ H ₁₁ N ₂ NaO ₄ S
Molecular weight	350.33
λ_{max} , nm	483
Toxic fumes	Carbon monoxide, carbon dioxide, nitrogen oxides, sulphur oxides
Chemical structure	

chemical characteristics of Orange II azo dye are reported in Table 1. Experiments were conducted to find out the effect of homogeneous and heterogeneous photodegradation in the removal of color, COD and TOC due to Orange II azo dye in aqueous solutions. All parameters were kept identical under pre-optimized operational conditions (pH 3, Concentration = 50 ppm, H₂O₂ = 0.5 % of total used sample,

volume of sample used = 20 ml) in different sets of experiments for all the studies (Divya et al. 2009). 10 mg/L catalyst dose was used for the studies (Bansal et al. 2010). The degradation studied has been discussed as under.

Color removal efficiency

Homogeneous photodegradation

A series of experiments were conducted for different concentrations of Orange II in the range of 50–400 ppm (Fig. 2). The decolorization of dye was found to depend on the concentration of the dye. As the initial concentration of dye increases the color removal efficiency decreases. The results indicated that the low concentration solution degraded fast. The time needed for color removal depended on the initial dye concentration. For higher concentration of Orange II (400 ppm), it took rather long time of more than 450 min for near total degradation in comparison to 90 min for 50 ppm solution. Probably it happened because at the high initial concentration of dye, the color might have hindered the penetration of light into the bulk of the reaction sample (Divya et al. 2009). Consequently, the degradation of the dye decreased as the initial dye concentration increased. The present result agreed with various previous studies (Lachheb et al. 2002; Kiriakidou et al. 1999; Mahmoodi et al. 2005; Muruganandham and Swaminathan 2004; Tokumura et al. 2006).



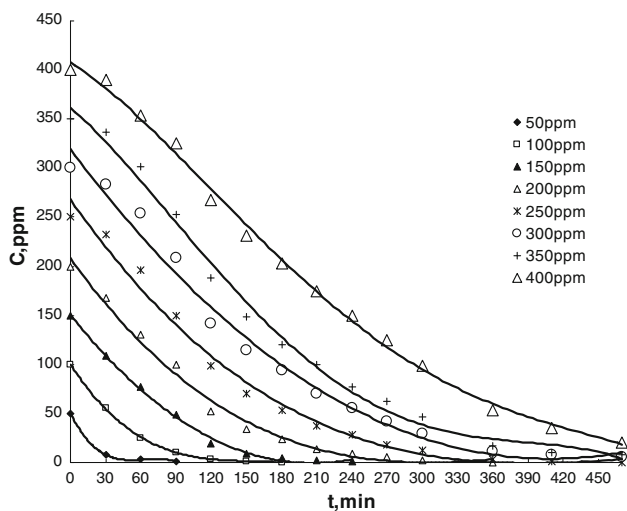


Fig. 2 Effect of different initial concentrations of Orange II (pH = 3, H₂O₂ = 0.5 % of total sample)

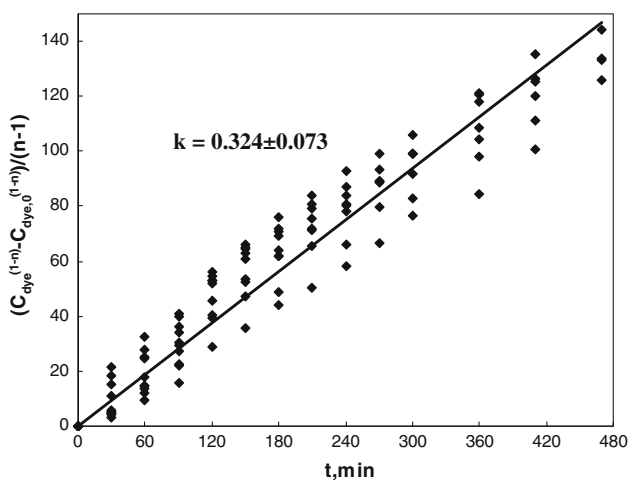


Fig. 3 *n*th order kinetics model of decolorization for Orange II (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample)

The experimental data were well fitted to an *n*th order rate equation (Levenspiel 1995). The rate of reaction was calculated using the expressions given below.

$$-r_{\text{dye}} = -\frac{dC_{\text{dye}}}{dt} = kC_{\text{dye}}^n \tag{9}$$

$$-r_{\text{dye}} = -\frac{dC_{\text{dye}}}{C_{\text{dye}}^n} = kdt \tag{10}$$

$$-\int_{C_{\text{dye},0}}^{C_{\text{dye}}} \frac{dC_{\text{dye}}}{C_{\text{dye}}^n} = k \int_0^t dt \tag{11}$$

$$C_{\text{dye}}^{(1-n)} - C_{\text{dye},0}^{(1-n)} = (n-1)kt \quad n \neq 1 \tag{12}$$

$$\frac{[C_{\text{dye}}^{(1-n)} - C_{\text{dye},0}^{(1-n)}]}{(1-n)} = kt \tag{13}$$


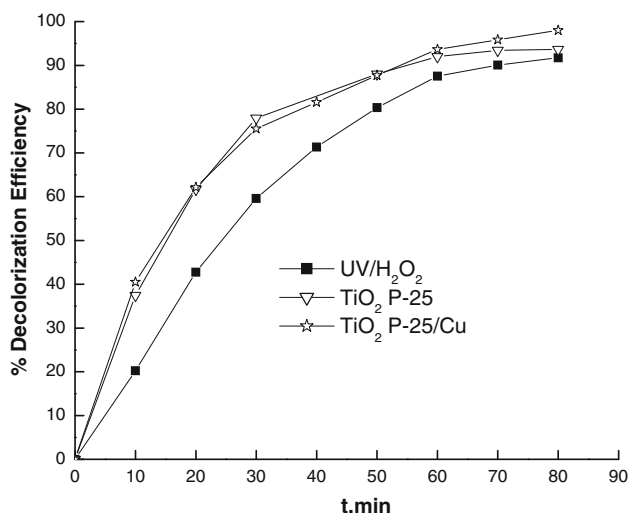


Fig. 4 Percent degradation efficiency for orange II with UV- H₂O₂ and different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample, amount of catalyst = 10 mg L⁻¹)

The linear fit of *n*th order reaction rate was plotted $\frac{[C_{\text{dye},0}^{(1-n)} - C_{\text{dye}}^{(1-n)}]}{(1-n)} - Vs - t$. The decolorization rate of Orange II follows the *n*th order kinetics (Fig. 3). The values of $k = 0.324 \pm 0.073$ and $R^2 = 0.97$ for $n = 0.204 \pm 0.042$.

Heterogeneous photocatalysis

The catalysts used for Orange II degradation are P-25 TiO₂ and P-25 TiO₂/Cu (10 mg/L). The copper-impregnated nano-size catalyst enhanced the color removal efficiency of Orange II (Fig. 4). The color removal efficiency of Orange II azo dye was higher, i.e., 98 % with P-25 TiO₂/Cu catalysts. As discussed, the presence of Cu²⁺-ions can help to efficiently separate the electron/hole pairs by attracting the conduction band photoelectrons, thus avoiding the recombination. The valence band photogenerated holes are free to react with OH⁻ adsorbed onto the TiO₂ to create hydroxyl radicals (OH⁻) and the conduction band electrons (at least a number of them) react with electron acceptors such as oxygen creating oxygen radicals (O₂⁻). These radicals (OH, O₂⁻) present extremely strong oxidizing properties and probably lead to degradation of Orange II dye. Simultaneously, H₂O₂-trapped photogenerated electrons and inhibited the recombination of photogenerated electron/hole pairs.



The results indicate that the color removal efficiency was higher with heterogeneous photocatalysis in comparison to

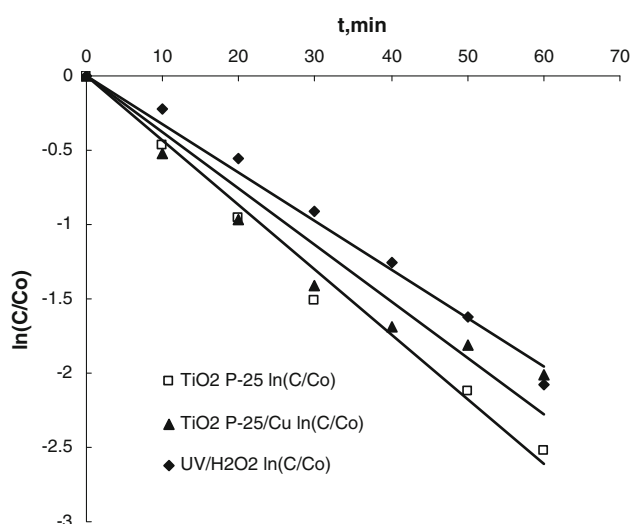


Fig. 5 Pseudo first order kinetics model of degradation for Orange II with different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample)

Table 2 Correlation coefficient R^2 and ' k ' value for Orange II dye for different catalysts


Photocatalyst	Decolorization		COD removal		TOC removal	
	R^2	k /min	R^2	k /min	R^2	k /min
TiO ₂ P-25/Cu	0.95	0.041	0.85	0.0032	0.97	0.0044
TiO ₂ P-25	0.98	0.045	0.93	0.0007	0.97	0.0025

homogeneous photodegradation (Fig. 4). Further an efficiency of 98 % (with TiO₂ P-25/Cu as a catalyst in 80 min), is significantly much higher for similar studies on biodegradation of Orange II by Sharma et al. (2009) (85 % dye removal in 5 days for 100 ppm Concentration, using *Phanerochaete chrysosporium*) and Oranusi and Ougubue (2005) (79.29 % decolorization efficiency using *Pseudomonas* sp.).

Heterogeneous photocatalysis followed the pseudo-first-order kinetics for OII degradation (Fig. 5). The correlation coefficients and reaction rate constants are tabulated in Table 2.

Percentages removal of chemical oxygen demand

The COD varies during the photocatalytic degradation of Orange II (50 ppm, 20 mL) (Table 3; Fig. 6). Within 9 h of irradiation, the percentage removal of COD with UV/H₂O₂, TiO₂ P-25 and TiO₂ P-25/Cu was 26, 42 and 97 %, respectively, indicating that the degradation of the Orange II with TiO₂ P-25/Cu was the highest. Although the catalytic activity of TiO₂ P-25 catalyst was slightly higher than that of UV/H₂O₂, it was noted that the very small amount of TiO₂ P-25-based heterogeneous photocatalytic degradation of the Orange II shows efficient changes in degradation efficiency, indicating that the titania-based transition metal modified catalysts particles in this process exhibit very good photocatalytic activity. Finally, it was found that the COD disappearance efficiency was better with heterogeneous photocatalysis against homogeneous photodegradation. The stoichiometry for the mineralization of Orange II could be suggested as:



The percentage removal of COD was much lower than that of decolorization under continuous UV radiation; it did not increase when complete decolorization of the solution was achieved. This is expected since the photosensitization mechanism is operable only when dye molecules are present on the photocatalyst surface. When this is the case, electron injection from the excited molecule into the conduction band of the semiconductor takes place, and the dye molecule converts into its cationic radical. The injected electron may then reduce surface chemisorbed oxidants, usually oxygen, to yield oxidizing species (O₂⁻, HOO[·] and OH radicals) which can cause photodegradation (Stylidi et al. 2003). It was observed that there was small decrease in COD during the first few hours under irradiation. This indicates that decolorization is due to decomposition of Orange II molecules to lower molecular weight compounds, such as formic acid, which eventually decompose to yield CO₂. Formation of CO₂ probably takes

Table 3 Percent COD and TOC removal, color removal, relative EE/O for color and COD removal with different photocatalysts after UV irradiation

Photocatalyst/process	% COD removal (9 h)	% TOC removal (9 h)	% color removal (80 min)	Relative EE/O value for color removal (80 min)	Relative EE/O value for COD removal (9 h)
TiO ₂ P-25/Cu	97	89	98	0.640	0.082
TiO ₂ P-25	42	72	94	0.905	0.551
UV/H ₂ O ₂	26	55	92	1	1




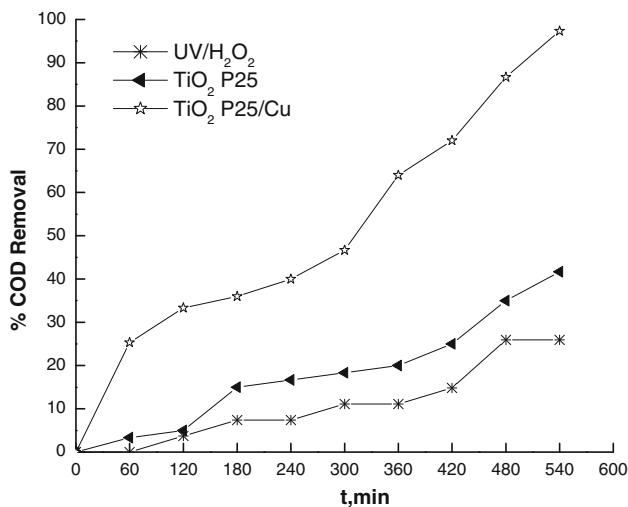


Fig. 6 Percent mineralization efficiency (% COD removal) for Orange II with UV-H₂O₂ and different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample, amount of catalyst = 10 mg L⁻¹)

place by decarbonylation of carboxylic acids via the “photo-Kolbe” reaction (Stylidi et al. 2003):



This may still be contributing to the COD of the solution. Complete decolorization was achieved at 90 min, and for nearly complete removal of COD it took rather long time. Prolonged irradiation of the suspension results in elimination of the COD of the solution, indicating that complete mineralization occurs after 9 h. Homogeneous and heterogeneous photodegradation (P-25 TiO₂) followed the pseudo-first-order kinetics for Orange II degradation (Fig. 7). But TiO₂ P-25/Cu photocatalysts do not follow the pseudo-first-order kinetics. The correlation coefficients (*R*²) and reaction rate constants (*k*) are tabulated in Table 2.

Percentage removal of total organic carbon

Mineralization of Orange II was studied in terms of percentage removal of TOC with transition metal modified nano-size catalysts such as TiO₂ P-25 and TiO₂ P-25/Cu. TOC removal was also measured for the homogeneous photodegradation (Fig. 8). Within 9 h of UV irradiation, the TOC removal of the Orange II by UV/H₂O₂, TiO₂ P-25 and TiO₂ P-25/Cu is 55, 72 and 89 %, respectively (Table 3; Fig. 8). Results indicated that the TOC removal of the Orange II using TiO₂ P-25/Cu is the fastest, than that of UV/H₂O₂ for the degradation. TiO₂ P-25 catalysts show

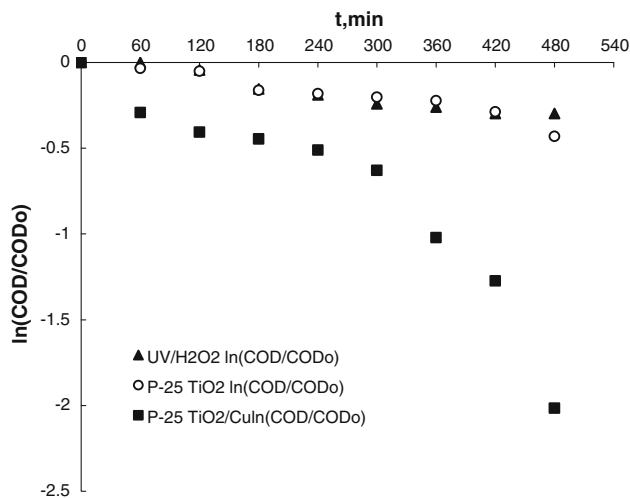


Fig. 7 Pseudo first order kinetics model of COD removal for Orange II with different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample)

slightly higher catalytic activity than that of UV/H₂O₂. It indicated that the TOC removal was comparatively slow than decolorization of Orange II. TOC removal of Orange II under homogeneous and heterogeneous photodegradation followed the pseudo-first-order kinetics (Fig. 9). The correlation coefficients (*R*²) and reaction rate constants (*k*) are tabulated in Table 2.

Electrical energy consumption

Photodegradation of aqueous organic pollutant is an electric energy-intensive process. A major fraction of the operating costs is represented by electrical energy. The values of electrical energy requirement per order (EE/O) for photocatalytic decolorization and mineralization of Orange II was calculated for a batch type photoreactor as (Daneshvar et al. 2007).

$$EE/O = \frac{P \times t \times 1,000}{V \times 60 \times \log \frac{C_i}{C_f}} \quad (18)$$

where *P* is the input power (kW) to the AOP system, *t* is the irradiation time (min), *V* is the volume of water (liter) in the reactor, *C_i* and *C_f* is the initial and final concentration of organic pollutants, respectively. The relative electrical energy requirement was calculated for the low concentration (50 ppm) of Orange II solution. The relative EE/O value can be calculated through below give equation.

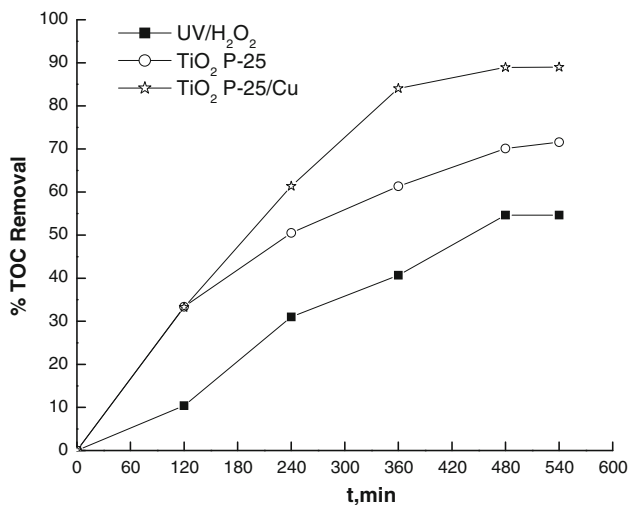


Fig. 8 Percent mineralization efficiency (% TOC removal) for Orange II with UV- H₂O₂ and different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample, amount of catalyst = 10 mg L⁻¹)

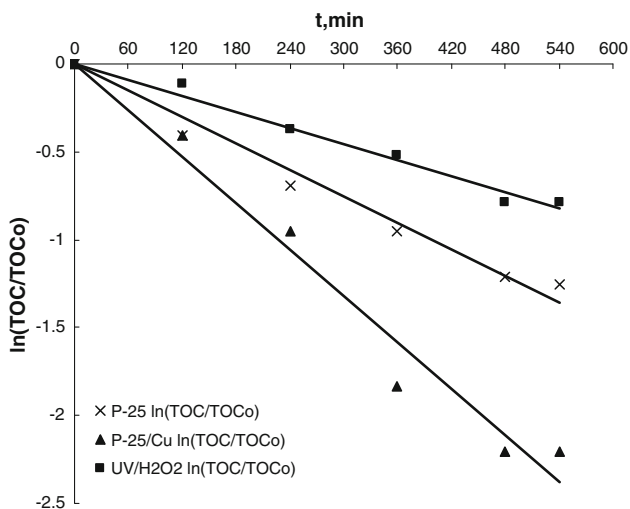


Fig. 9 Pseudo first order kinetics model of TOC removal for Orange II with different catalysts (pH = 3, concentration = 50 ppm, H₂O₂ = 0.5 % of total sample)

$$\text{Relative EE/O} = \frac{\text{EE/O}(\text{withcatalysts})}{\text{EE/O}(\text{homogeneous photodegradation})} \quad (19)$$

The relative EE/O values for photocatalytic decolorization and mineralization of Orange II with TiO₂ P-25/Cu process were 0.64 and 0.082 and for other combinations values are tabulated in Table 3. The

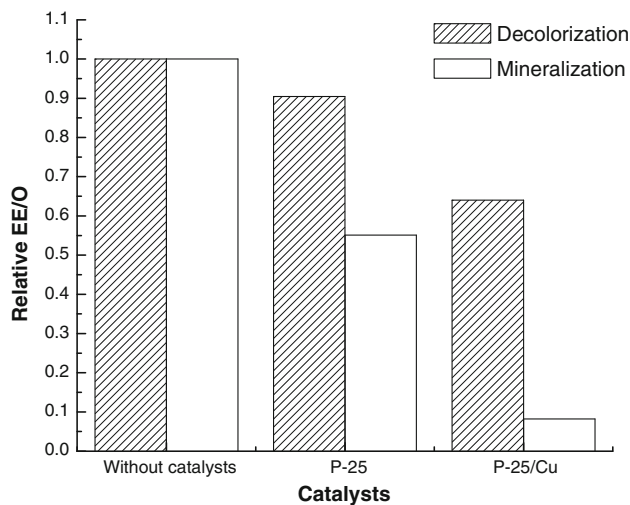


Fig. 10 Relative electrical energy requirements for the decolorization and mineralization of Orange II azo dye

relative EE/O value for Orange II decolorization was very high with homogeneous photodegradation, but it decreased with modification of nano-sized titania-based catalyst (such as TiO₂ P-25 > TiO₂ P-25/Cu). It is also clear that TiO₂ P-25/Cu catalysts offered the best energy efficiency (Fig. 10). In case of removal of COD relative EE/O values was high with UV/H₂O₂ and gradually decreased with TiO₂ P-25, TiO₂ P-25/Cu, photocatalysts similar to decolorization (Fig. 10).

It is clear from the calculation of relative EE/O value that the modified TiO₂ P-25/Cu-based catalyst offered best energy efficiency for both decolorization and mineralization (Fig. 10).

Conclusion

TEM analysis performed on copper-impregnated TiO₂ P-25 photocatalysts indicated that particles were nano-sized. The sizes of the particles are in the range of 10 ± 2 nm TiO₂ P-25, and 3–4 nm Cu. Kinetic studies of homogeneous photodegradation revealed that the degradation of Orange II follows *n*th order kinetics with *n* close to 0.204 ± 0.042. The concentration of dye had the effect on its degradation. The removal efficiency was higher for low concentration dye solutions. In case of heterogeneous photocatalysis TiO₂ P-25/Cu-modified catalyst showed better photocatalytic degradation activity as compared with TiO₂ P-25 catalyst. Pseudo-first-order reaction kinetics followed the heterogeneous photocatalysis reasonably well.

The results show that the COD, TOC and color removal efficiency was faster with heterogeneous photocatalysis (transition metal modified nano-sized catalysts) than that for homogeneous photodegradation. The best results, however, were obtained corresponding to TiO₂ P-25/Cu.

The relative electrical energy consumption for photocatalytic degradation of Orange II with TiO₂ P-25/Cu catalyst was lesser than that of other combinations of catalysts and homogeneous photodegradation.

Acknowledgments The authors thank Evonic (Degussa) Company, Germany, for kindly providing TiO₂ P-25 for the present research work.

References

- Aleboeyeh A, Olya ME, Aleboeyeh H (2008) Electrical energy determination for an azo dye decolorization and mineralization by UV/H₂O₂ advanced oxidation process. *Chem Engg J* 137: 518–524
- Arabatzi IM, Stergiopoulos T, Bernard MC, Labou D, Neophytides SG, Falaras P (2003) Silver-modified titanium dioxide thin films for efficient photodegradation of methyl orange. *Appl Catal B Environ* 42:187–201
- Arana J, Fernandez Rodriguez C, Gonzalez Diaz O, Herrera Melian JA, Perez Pena J (2005) Role of Cu in the Cu-TiO₂ photocatalytic degradation of dihydroxybenzenes. *Catal Today* 101:261–266
- Bansal A, Divya N, Jana AK (2010) Performance of titania based Nano-Photocatalysts on the degradation of Orange G azo dye. The 5th IASME/WSEAS international conference on energy and environment. 23–25 February, Cambridge University, UK, 140–146
- Behnajady MA, Modirshala N, Shokri M, Rad B (2008) Enhancement of photocatalytic activity of TiO₂ nanoparticles by silver doping: photodeposition versus liquid impregnation methods. *Glob Nest J* 10:1–7
- Bhattacharyya A, Kawi S, Ray MB (2004) Photocatalytic degradation of Orange II by TiO₂ catalysts supported on adsorbents. *Catal Today* 98:431–439
- Cho I-H, Zoh K-D (2007) Photocatalytic degradation of azo dye (Reactive Red 120) in TiO₂/UV system: optimization and modeling using a response surface methodology (RSM) based on the central composite design. *Dyes Pigments* 75:533–543
- Daneshvar N, Salari D, Khataee AR (2004) Photocatalytic degradation of azo dye acid red 14 in water on ZnO as an alternative catalyst to TiO₂. *J Photochem Photobiol A Chem* 162:317–322
- Daneshvar N, Aber S, Dorraji MSS, Khataee AR, Rasoulifard MH (2007) Preparation and investigation of photocatalytic properties of ZnO nanocrystals: effect of operational parameters and kinetic study. *Int J Chem Bio Engg* 1:24–29
- Dave SR, Dave RH (2009) Isolation and characterization of *Bacillus thuringiensis* for Acid red 119 dye decolorisation. *Bioresour Technol* 100:249–253
- Divya N, Bansal A, Jana AK (2009) Degradation of acidic Orange G dye using UV-H₂O₂ in batch photoreactor. *Int J Bio Chem Sci* 3(1):54–62
- Galindo C, Jacques P, Kalt A (2000) Photodegradation of the aminoazobenzene acid Orange 52 by three advanced oxidation processes: UV/H₂O₂, UV/TiO₂ and VIS/TiO₂ Comparative mechanistic and kinetic investigations. *J Photochem Photobiol A Chem* 130:35–47
- Goncalves MST, Pinto EMS, Nkeonye P, Oliveira-Campos AMF (2005) Degradation of C.I. reactive Orange 4 and its simulated dyebath wastewater by heterogeneous photocatalysis. *Dyes Pigment* 64:135–139
- Gracien EB, Shen J, Sun X, Liu D, Li M (2007) Effect of additive oxidant agent on the discoloration and mineralization of acid Orange 7 by using iron-doped titanium dioxide produced by re-anodization method. *Chem Engg J*. doi:10.1016/j.cej.2007.05.050
- Gupta AK, Pal A, Sahoo C (2006) Photocatalytic degradation of a mixture of Crystal Violet (Basic Violet 3) and Methyl Red dye in aqueous suspensions using Ag⁺ doped TiO₂. *Dyes Pigment* 69:224–232
- Kiriakidou F, Kondarides DI, Verykios XE (1999) The effect of operational parameters and TiO₂-doping on the photocatalytic degradation of azo-dyes. *Catal Today* 54:119–130
- Lachheb H, Puzenat E, Houas A, Ksibi M, Elaloui E, Guillard C, Herrmann JM (2002) Photocatalytic degradation of various types of dyes (Alizarin S, Crocein Orange G, Methyl Red, Congo Red, Methylene Blue) in water by UV-irradiated titania. *Appl Catal B Environ* 39:75–90
- Levenspiel O (1995) *Chemical reaction engineering*, 2nd edn. Wiley, Singapore
- Liu H-L, Chiou Y-R (2005) Optimal decolorization efficiency of Reactive Red 239 by UV/TiO₂ photocatalytic process coupled with response surface methodology. *Chem Engg J* 112:173–179
- Luo J, Yartym J, Hepel M (2002) Photoelectrochemical degradation of Orange II textile dye on nanostructured WO₃ film electrodes. *J New Mat Elect Syst* 5:315–321
- Mahmoodi NM, Arami M, Nargess YL, Nooshin ST (2005) Decolourisation and aromatic ring degradation kinetics of Direct Red 80 by UV oxidation in the presence of hydrogen peroxide utilizing TiO₂ as a photocatalyst. *Chem Eng J* 112:191–196
- Menendez-Flores VM, Friedmann D, Detlef WB (2008) Durability of Ag-TiO₂ photocatalysts assessed for the degradation of dichloroacetic acid. *Int J Photoenergy* 1–11. doi:10.1155/2008/280513
- Muruganandham M, Swaminathan M (2004) Photochemical oxidation of reactive azo dye with UV-H₂O₂ process. *Dyes Pigment* 62:269–275
- Nasr-Esfahani M, Habibi MH (2008) Silver doped TiO₂ nanostructure composite photocatalyst film synthesized by Sol-Gel Spin and Dip Coating Technique on Glass. *Int J Photoenergy* 1–11. doi:10.1155/2008/628713
- Oranus NA, Ogugbue CJ (2005) Effect of pH and nutrient starvation on biodegradation of azo dyes by *Pseudomonas* sp. *J Appl Sci Environ* 91:39–43
- Sahoo C, Gupta AK, Pal A (2005) Photocatalytic degradation of Crystal Violet (C.I. Basic Violet 3) on silver ion doped TiO₂. *Dyes Pigment* 66:189–196
- Sharma P, Singh L, Dilbaghi N (2009) Biodegradation of Orange II dye by *Phanerochaete Chrysosporium* in simulated wastewater. *J Sci Ind Res* 68:157–161
- Somasiri W, Ruan W, Xiufen L, Jian C (2006) Decolorization of textile wastewater containing acid dyes in UASB reactor system under mixed anaerobic granular sludge. *Electron J Environ Agric Food Chem* 5:1224–1234
- Stylidi M, Kondarides DI, Verykios XE (2003) Mechanistic and kinetic study of solar-light induced photocatalytic degradation of acid Orange 7 in aqueous TiO₂ suspensions. *Int J Photoenergy* 5:59–67
- Tokumura M, Znad HT, Kawase Y (2006) Modeling of an external light irradiation slurry photoreactor: UV light or sunlight-photoassisted



- Fenton discoloration of azo-dye Orange II with natural mineral tourmaline powder. *Chem Engg Sci* 61:6361–6371
- Wu C-H (2008) Effects of operational parameters on the decolorization of C.I. Reactive Red 198 in UV/TiO₂-based systems. *Dyes Pigment* 77:31–38
- Zhao D, Zhou J, Liu N (2007) Surface characteristics and photoactivity of silver-modified palygorskite clays coated with nanosized titanium dioxide particles. *Mater Charact* 58:249–255

