

Photoelectrocatalytic Oxidation of Ethinylestradiol on a Ti/TiO₂ Electrode: Degradation Efficiency and Search for By-Products

Karla Moreira Vieira¹, Fabiana Maria Monteiro Paschoal², Maria Valnice Boldrin Zanoni², Clésia Cristina Nascentes³, Rodinei Augusti^{3*}

¹Departamento de Ciências Exatas e Aplicadas, Universidade Federal de Ouro Preto, Loanda, Brazil

²Instituto de Química, Universidade Estadual Paulista, Araraquara, Brazil

³Departamento de Química, Universidade Federal de Minas Gerais, Belo Horizonte, Brazil

Email: augusti.rodinei@gmail.com

Received 11 June 2014; revised 8 July 2014; accepted 6 August 2014

Copyright © 2014 by authors and Scientific Research Publishing Inc.

This work is licensed under the Creative Commons Attribution International License (CC BY).

<http://creativecommons.org/licenses/by/4.0/>



Open Access

Abstract

The degradation of ethinylestradiol (EE, an orally bio-active estrogen) in an aqueous-methanolic solution using a Ti/TiO₂ thin-film electrode and UV radiation (a photoelectrocatalytic system) was evaluated. Hence, HPLC/UV analysis shows that EE (at 0.34 mmol) is totally consumed after 30 minutes of exposure to the photoelectrocatalytic system in the presence of Na₂SO₄ (0.1 mol·L⁻¹) and with an applied bias potential of +1.0 V versus the Ag/AgCl reference electrode. Moreover, monitoring by direct infusion electrospray ionization mass spectrometry (ESI-MS) and SPME-GC/MS (solid phase microextraction coupled with gas chromatography-mass spectrometry) reveals that apparently no degradation products are formed under these conditions. Hence, this study demonstrates that the photoelectrocatalytic system can be efficiently used to promote the complete degradation (and likely mineralization) of this hormone under these conditions.

Keywords

Photoelectrocatalytic Oxidation, Ethinylestradiol, Ti/TiO₂ Thin-Film Electrode, Degradation Efficiency, Search for By-Products

*Corresponding author.

1. Introduction

Pharmaceuticals are predominantly synthetic chemicals, designed to produce a pharmacological response at specific sites of action within the target organism, and require a certain chemical stability in order to reach these sites on an unaltered form. The adverse consequence of the relatively high stability of these compounds is that they are not completely removed during wastewater treatment [1]. Whereas the presence of pharmaceuticals in the natural environment has been fairly reported [2], recent studies have shown that these compounds cause severe and uncontrollable outcomes on numerous aquatic ecosystems as well as serious and irreversible effects on the health of humans and other animal species [3]-[8].

Ethinylestradiol (EE), one of the most commonly used pharmaceuticals, constitutes the active principle of many contraceptive agents and therapy drugs [9] [10]. The occurrence of EE, and other synthetic estrogen hormones, in natural systems, such as surface waters, soils, and sediments, has become a subject of major concern [11]. For instance, their occurrence in natural waters has been associated with critical problems such as the feminization of male fishes [12]-[15]. Effects on human health, which include a range of reproductive tract abnormalities (reduced fertility, skewed male/female sex ratios, loss of fetus, menstrual disorders), early puberty, mental and emotional illnesses, impaired immune functions, and various types of cancer, have also been directly ascribed to these compounds [16]-[19].

Conventional water treatment processes are usually ineffective in promoting the complete depletion of recalcitrant pharmaceutical compounds. For instance, oxidation processes, which usually include the use of ozone, chlorine, and chlorine dioxide as effective oxidants, have been widely applied in treatment facilities not only for disinfection of wastewaters but also for elimination of undesired micro-pollutants from drinking water [11] [17] [20]. To surpass these drawbacks, alternative methodologies that make use of oxidative processes have been proposed [21]-[29]. Among them, heterogeneous photo-catalysis has attracted the foremost attention due to its lower cost and superior efficiency. In this process, target organic compounds are oxidized by hydroxyl radicals ($\cdot\text{OH}$), a powerful oxidizing agent generated by the decomposition of water molecules adsorbed at the catalyst surface. Moreover, several studies [30]-[32] have persistently corroborated that the application of an external electric field greatly enhances degradation rates since the high degree of charges recombination at the heterogeneous catalyst surface can be successfully solved by applying an anodic bias [31] [33]-[37]. As a consequence, photoelectrocatalysis has been effectively employed for the degradation of a number of organic pollutants, including dyes, anionic surfactants, pesticides, and microcystin toxins [38]-[44].

At the time when sustainable development has progressively become an important issue, queries regarding environmental protection have been inserted in all human activities. In consonance with this essential matter, herein we report on the photoelectrocatalytic degradation of EE in aqueous solution on nanoporous Ti/TiO₂ thin-film electrode exposed to UV irradiation and applied potential. To assess the effectiveness of this method and to verify whether residual organic compounds could be formed under these conditions, a number of techniques were employed: HPLC, direct infusion electrospray ionization mass spectrometry (ESI-MS) and GC-MS. Aiming at detecting the residual hormone and the degradation products at quite low levels, two extraction/preconcentration procedures that precede the GC-MS analysis are evaluated: solid phase micro-extraction (SPME) and liquid-liquid extraction (LLE).

2. Experimental Section

2.1. Reagents

All the reagents used herein, EE (Organon, São Paulo, Brazil), Na₂SO₄ (Merck, Darmstadt, Germany), H₂SO₄ (Merck, Darmstadt, Germany), dichloromethane (Tedia, Fairfield, USA), acetonitrile (Tedia, Fairfield, USA), methanol (Merck, Darmstadt, Germany), were employed as received. The solutions and HPLC mobile phase were prepared using ultrapure water, which was generated via a Millipore Milli-Q system (Milford, MA, USA).

2.2. Preparation of the Ti/TiO₂ Thin-Film Electrodes

Titanium (IV) isopropoxide (Aldrich) was used as a precursor for preparing TiO₂ colloidal suspensions. Typically, 20 mL of titanium isopropoxide was added to a nitric acid solution keeping the ratio Ti/HNO₃/H₂O at 1/1.5/200. The resulting precipitate was continuously stirred until completely peptized to a stable colloidal suspension. This suspension was dialyzed against ultrapure water (Milli-Q Millipore) to a pH of 3.5 by using a Mi-

cropore 3500 MW cut off membrane. Thin-film photo-electrodes were dip-coated onto a titanium foil back contact (0.05 or 0.5 mm thick, Goodfellow Cambridge Ltd.), after heating the Ti foils at 350°C. A sequence of dipping, drying and firing at 450°C for 30 min were used after each coating (five repetitions), according to a procedure previously described [45].

2.3. Techniques Employed to Characterize the Electrodes

The morphological analysis of the Ti/TiO₂ surface was performed by Field Emission Gun-Scanning Electron Microscopy (FEG-SEM) with field emission source of electrons (instrument: JEOL; model: JSM-7500-F). The surface was also characterized by X-ray powder diffraction (XRD) with a Siemens D5000 diffractometer (CuK α radiation, $\lambda = 1.541 \text{ \AA}$), using a curved graphite monochromator, and a fix divergence slit of $1/8^\circ$ in a Bragg-Brentano configuration. The electrode was electrochemically characterized by linear scan voltammetry using a reactor and Na₂SO₄ at $0.10 \text{ mol}\cdot\text{L}^{-1}$ as supporting electrolyte. The reactor was submitted to irradiation of 150 W by Xe lamps (Oriol), corresponding to the ultraviolet region. The electrochemical reactor is composed of a counter-electrode (Pt gauze), a reference electrode (Ag/AgCl plus saturated KCl) and a working electrode (Ti/TiO₂).

2.4. Photoelectrocatalytic System and Degradation Procedure

The photoelectrocatalytic oxidation experiments were performed in a 250 mL reactor equipped with water refrigeration using an ultra-thermostatic bath (Nova Técnica, Brazil). In the cell, the reference electrode was connected to the working electrode using a bridge tube containing a Vycor frit tip. The photoactive area of the anode (TiO₂) was 12 cm^2 and it was illuminated with the UV light source. This lamp was placed in the center of the quartz sleeve (2.5 cm away from the anode). The anode was tested during 6 months of application on the photoelectrocatalytic oxidation with loss of 5% of activity. A potentiostat/galvanostat (EG & G PARC, model 283) controlled by the electrochemical 270 software was used to bias the anode in the photoelectrocatalytic oxidation experiments.

Samples of EE solution (200 mL) at 0.34 mmol in water-methanol 10:1 v/v containing Na₂SO₄ ($0.1 \text{ mol}\cdot\text{L}^{-1}$) at pH 2 (achieved by adding small quantities of H₂SO₄ $0.1 \text{ mol}\cdot\text{L}^{-1}$) was put into the photoelectrocatalytic reactor of one compartment. Aliquots were taken at assorted intervals (from 5 to 150 minutes) and stored in a refrigerator (at -10°C) for posterior analysis using HPLC and GC-MS. A mixture of methanol and water was used as solvent to improve the solubility of EE.

2.5. Extraction Procedures

For the GC-MS analyses, two extraction procedures were evaluated: liquid-liquid extraction (LLE) and solid-phase microextraction (SPME). The LLE was performed by mixing 0.5 mL of a reaction aliquot and 0.5 mL of dichloromethane followed by vortex (Phoenix, Araraquara, Brazil) stirring for 30 seconds. The organic phase was isolated and the aqueous layer submitted to two extra extraction cycles. The organic extracts were combined and the solvent evaporated. Then, 1 mL of dichloromethane was added to the raw extract.

The manual SPME holder with the CAR/PDMS (carboxen/polydimethylsiloxane) or DVB/CAR/PDMS (divinylbenzene/carboxen/polydimethylsiloxane) fibers were purchased from Supelco (Bellefonte, PA, USA). Prior to use, the fibers were conditioned following the manufacturer's instructions. The fibers were immersed into the solutions (prepared by diluting the aliquots 100 times with MilliQ water) for 10 min at ambient temperature (25°C) and then introduced into the GC inlet to allow thermal desorption of the analytes.

2.6. Instruments

HPLC analysis were performed on an SPD-M10A VP instrument (Shimadzu, Kyoto, Japan) using a Hypersil C18 column (250 mm long, 4.6 mm i.d., $5 \mu\text{m}$ particle size) and acetonitrile/H₂O (1:1) as mobile phase. The isocratic elution was maintained at a flow rate of $1 \text{ mL}\cdot\text{min}^{-1}$ for the 10 min chromatographic runs. The injection volume was $20 \mu\text{L}$ and the UV detector was set at 210 and 280 nm wavelengths.

ESI-MS analysis were conducted on a LCQFleet (ThermoScientific, San Jose, CA) mass spectrometer bearing an electrospray ionization (ESI) source and operating in the negative ion mode. Mass spectra were obtained as an average of 50 scans, each one requiring 0.02 s. The samples (aliquots withdrawn from the reactor) were di-

rectly infused into the ESI source at a flow rate of $25 \mu\text{L}\cdot\text{min}^{-1}$ by means of a 500- μL microsyringe (Hamilton, Reno, NV). The ESI source conditions were as follows: heated capillary temperature of 285°C , sheath gas (N_2) flow rate at 20 (arbitrary units), spray voltage of 5.0 kV, capillary voltage of -38 V , tube lens offset voltage of -110 V .

GC-MS analysis were conducted on a gas chromatograph (Trace GC Ultra) coupled to an ion trap mass spectrometer (POLARIS Q) from ThermoElectron Corporation (San Jose, CA, USA). A HP-5MS (Agilent, Santa Clara, CA) capillary column ($30 \text{ m} \times 0.25 \text{ mm i.d.} \times 0.25 \mu\text{m}$ film) containing 5% diphenyl and 95% dimethylpolysiloxane was used. The injector was operated in the splitless mode (for 2 min) under a temperature of 250°C . The oven temperature program was as follows: 120°C (holding time 2 min) with an increment of $10^\circ\text{C}\cdot\text{min}^{-1}$ up to 290°C (holding time 10 min) and finishing with an increase of $10^\circ\text{C}\cdot\text{min}^{-1}$ up to 300°C for 2 minutes. The total run time was 27 minutes and helium was used as carrier gas at a constant flow of $1.5 \text{ mL}\cdot\text{min}^{-1}$. Other typical mass spectrometer parameters were as follows: electron ionization at 70 eV, full scan mode with a mass range of 50 - 200, and a source temperature of 200°C .

3. Results and Discussion

3.1. Electrode Characteristics

FEG-SEM images obtained for the Ti/TiO₂ material are illustrated in **Figure 1**. The top view FEG-SEM micrographs clearly show that the morphology of the surface material is characterized by the presence of roughness due to a nanoporous formation consisting of particles with sizes close to 100 nm. These are better visualized in the image captured using increased resolution. The XRD pattern obtained for the electrode annealed at 450°C (not shown) revealed the presence of a mixture of the two forms of TiO₂ (anatase and rutile) in its composition. The peaks at 25.4° and 48.2° are identified as (101) and (200) of the anatase form and the peaks at 17.5° , 36.2° and 54.4° are due to the rutile phase (110, 101 and 211 of the crystallites). The other peaks at 35° , 38° , 40° , 52° , 63° , 70° , 76° and 77° are due to the metal Ti.

Figure 2 illustrates the photoactivity of the Ti/TiO₂ electrode verified by recording linear voltammetric curves ($0.001 \text{ V}\cdot\text{s}^{-1}$) in Na_2SO_4 $0.1 \text{ mol}\cdot\text{L}^{-1}$ under two different conditions: in the absence (a) and presence (b) of UV irradiation. The current intensity was negligible in dark conditions (curve a) but underwent a remarkable increase under irradiation at a potential higher than -0.2 V , with maximum values of current ($200 \mu\text{A}\cdot\text{cm}^{-2}$) at potentials higher than 1 V vs Ag/AgCl (curve b). As calculated from onset potential measurements, the flat-band

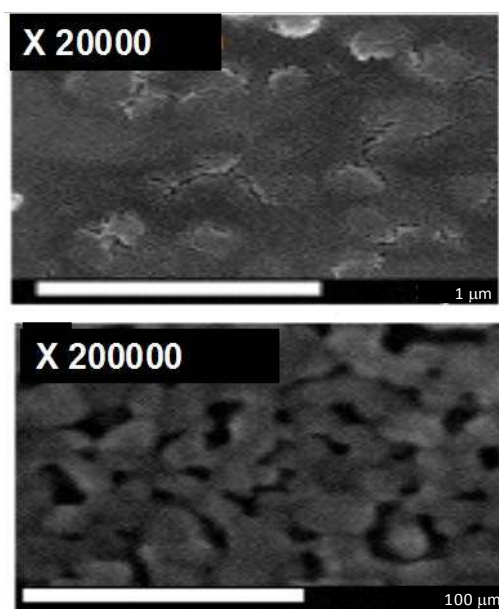


Figure 1. FE-SEM images of nanoporous Ti/TiO₂ thin-film electrode annealed at 450°C (30 min) (up) and magnified image (bottom).

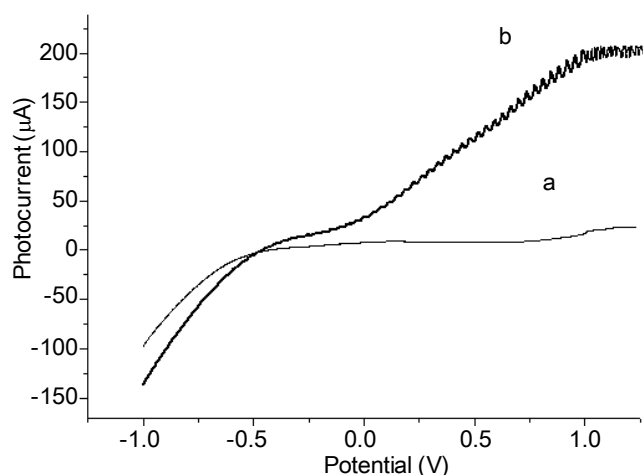


Figure 2. Current/potential curves (scan rate = $0.001 \text{ V}\cdot\text{s}^{-1}$) obtained for the Ti/TiO₂ thin-film electrode in Na₂SO₄ $0.1 \text{ mol}\cdot\text{L}^{-1}$ and pH 2, without (a) and under UV irradiation (b).

potential obtained for the TiO₂ in $0.1 \text{ mol}\cdot\text{L}^{-1}$ Na₂SO₄ media was about -0.24 V . A bias potential positive to the flat-band potential produces a bending of the conduction band causing a more effective charge separation and increases the current (lph) that begins to flow and likely promotes a better oxidative degradation process. Thus, this behavior indicates that photo-generated electrons (e^-) and holes (h^+) are formed by irradiation and separated by a positive bias potential on the photo-anode, which drives the lacunas towards the surface of photo-anode and the electrons to the counter-electrode (gauze Pt). This process reduces the recombination electron/hole, increases the lifetime of $\cdot\text{OH}$ radicals generated on the surface of the photo-anode due to water oxidation and produces high current. The bias potential of 1 V was therefore chosen in the further studies.

3.2. Degradation of EE: HPLC Monitoring

To verify the efficiency of the photoelectrocatalytic system in promoting the depletion of EE and to check the formation of possible oxidation products, the reaction was firstly monitored by HPLC. Moreover, control experiments revealed that photocatalysis (conducted with no applied potential), electrochemical oxidation (with no use of UV radiation), and photolysis (with utilization of UV radiation solely) displayed negligible performance in depleting EE. Hence, a solution of EE at 0.34 mmol was submitted to the photoelectrocatalytic system for 150 min. The Na₂SO₄ concentration and the pH of the reaction medium were adjusted to furnish a maximum degradation rate for EE. The optimized values were $0.1 \text{ mol}\cdot\text{L}^{-1}$ and 2, respectively. **Figure 3** shows the normalized concentration of EE for several aliquots collected after successive exposure times to the optimal photoelectrocatalytic system. These data clearly demonstrated an outstanding performance of this degradation system as EE (a molecule that possess high stability and is usually unaffected by other oxidative processes [18]) was almost completely depleted (degradation rate of 98%) after a reaction time as short as 30 min. The utilization of a supporting electrolyte (Na₂SO₄ at $0.1 \text{ mol}\cdot\text{L}^{-1}$) showed to be critical since its absence caused the attainment of much inferior degradation rates (as similarly reported in reference [46]). Although total organic carbon (TOC) data could not be obtained (due to the use of a mixture of water/methanol to assure the complete solubility of the hormone), the results from the HPLC analysis, *i.e.* the complete consumption of the substrate and the absence of degradation products, strongly support the assumption that EE is completely mineralized under these conditions.

3.3. Degradation of EE: ESI-MS Monitoring

Direct infusion electrospray ionization mass spectrometry in the negative ion mode, ESI(-)-MS, was also applied to monitor not only the substrate consumption but also a possible formation of polar intermediates and by-products. In fact, direct infusion ESI-MS, because of its appealing and unique attributes, has been routinely applied to monitor an increasing number of relevant environmental processes [47]-[56]. **Figure 4** displays the ESI(-)-MS of the original EE solution as well as the aliquots collected after successive times (from 0 to 150 min)

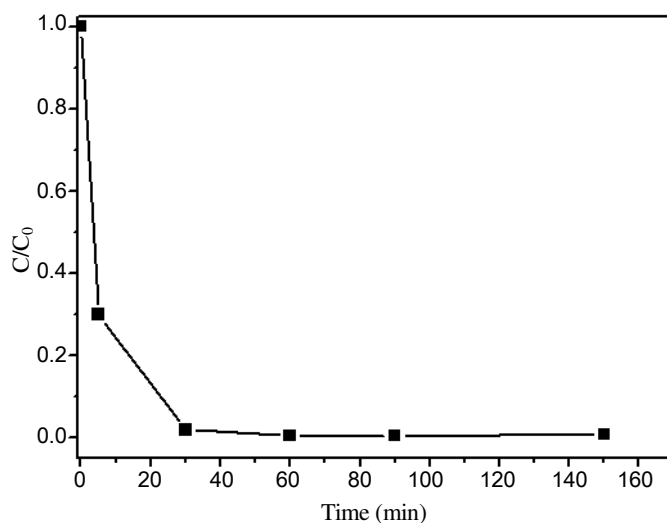


Figure 3. Normalized concentration (C/C_0) of EE (initial concentration at 0.34 mmol) in water-methanol 10:1 v/v (in the presence of Na_2SO_4 at $0.1 \text{ mol}\cdot\text{L}^{-1}$ and pH 2) and of the aliquots collected after assorted times (up to 150 minutes) of exposure to the photoelectrocatalytic system.

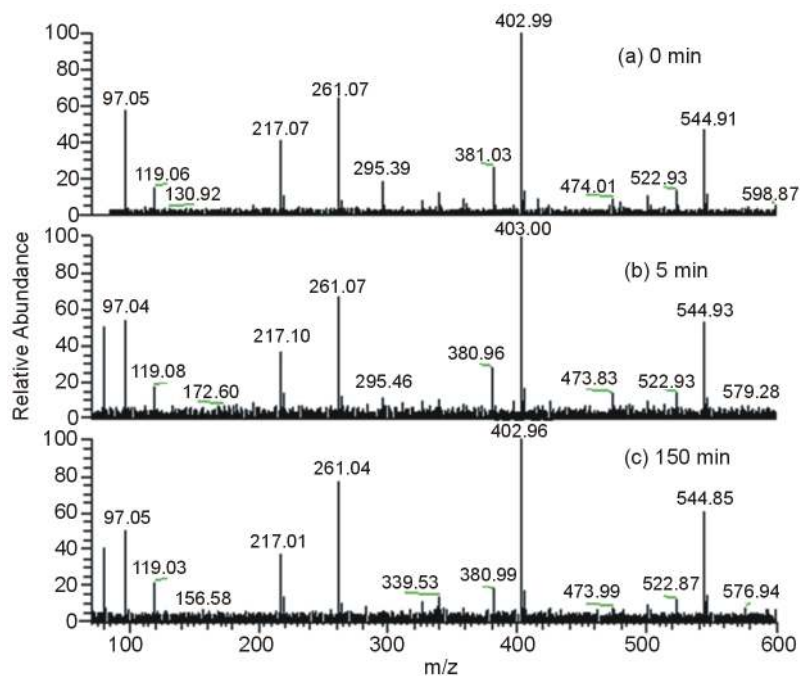


Figure 4. ESI(-)-MS of: (a) EE solution (at 0.34 mmol) in water-methanol 10:1 v/v (in the presence of Na_2SO_4 at $0.1 \text{ mol}\cdot\text{L}^{-1}$ and pH 2); (b) (c) the aliquots collected after assorted times (up to 150 minutes) of exposure to the photoelectrocatalytic system.

of exposure to the photoelectrocatalytic system. Hence, the ESI(-)-MS of the initial solution (**Figure 4(a)**) revealed the presence of an anion of m/z 295, ascribed to be the deprotonated form of EE, *i.e.* $[\text{EE}-\text{H}]^-$. After 5 minutes, however, this anion was barely detectable thus revealing the prompt depletion of the hormone. Note the presence of spurious anions of m/z 217, 261, 403 and 545 in all the ESI(-)-MS, including the mass spectrum of the initial solution (**Figure 4**). Hence, rather than indicating the possible formation of degradation products, the

occurrence of these anions is probably related to trace amounts of impurities in the reagents or in the instrumental apparatus.

3.4. Degradation of EE: GC-MS Monitoring

To verify whether non-polar or volatile degradation products could be formed under these conditions, GC-MS analyses were performed using two different extraction procedures: solid phase microextraction (SPME) and liquid-liquid extraction (LLE) with dichloromethane. Furthermore, the ability of GC-MS (in conjunction with SPME and LLE extraction and pre-concentration procedures) in attaining quite low detection limits for a number of analytes (including EE) was used to estimate the residual EE that remain in solution after the photoelectrocatalytic treatment. In the SPME procedure, two fibers with distinct polarities were evaluated: divinylbenzene/carboxen (DVB/CAR) and divinylbenzene/carboxen/polydimethylsiloxane (DVB/CAR/PDMS). In spite of these distinct characteristics, the extraction with both fibers led to the attainment of quite similar chromatograms. **Figure 5(a)** and **Figure 5(b)** show, respectively, the chromatograms, obtained with the DVB/CAR/PDMS fiber, of the initial solution and of the aliquot withdrawn after 30 minutes of exposure to the photoelectrocatalytic system. Note that the chromatographic peak related to EE (at a retention time of ca. 19.65 minutes) was completely vanished after treatment. Similar chromatographic profiles (not shown) were also achieved when the LLE procedure was employed. As previously verified by the HPLC and ESI-MS analysis, no degradation products could be detected as indicated by the lack of unambiguous chromatographic peaks in the chromatograms (not shown) of the aliquots collected at intermediate times (10 and 20 min). These results once more confirm the great efficiency of photoelectrocatalytic oxidation in causing the degradation and possibly mineralization of the hormone EE.

4. Conclusion

As demonstrated by the data from HPLC and ESI(-)-MS the photoelectrocatalysis approach represents an alternative method potentially applied to the degradation (and likely mineralization) of the hormone EE. This methodology displayed excellent results with degradation rates reaching 98% after a treatment time of 30 min. As revealed by GC-MS, the level of residual EE that remains in solution after the photoelectrocatalytic treatment is quite low (below its detection limit). Finally, studies are underway to verify the effectiveness of such methodology to promote the depletion of other persistent pollutants, such as some pesticides and other pharmaceuticals.

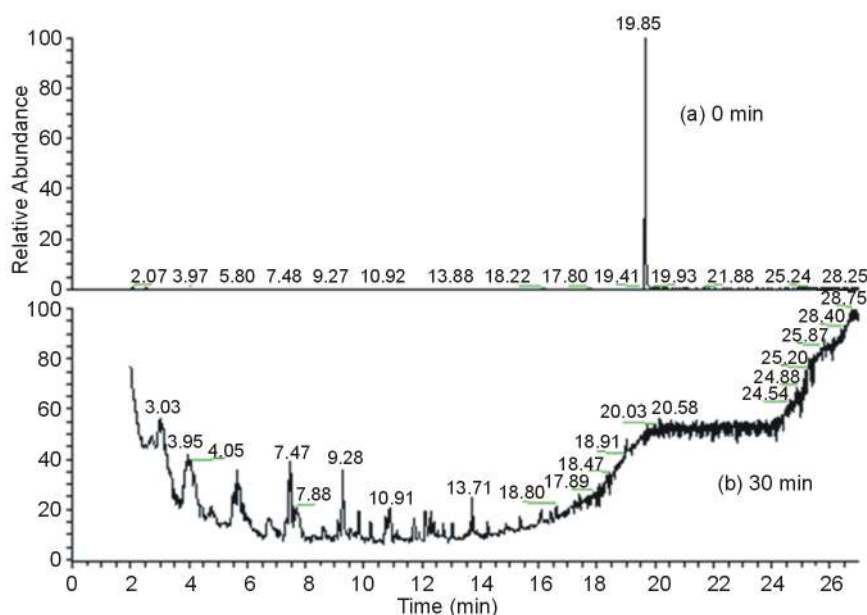


Figure 5. SPME-GC-MS (DVB/CAR/PDMS fiber) of: (a) EE solution (at 0.34 mmol) in water-methanol 10:1 v/v (in the presence of Na_2SO_4 at $0.1 \text{ mol}\cdot\text{L}^{-1}$ and pH 2); (b) the aliquot collected after 30 minutes of exposure to the photoelectrocatalytic system.

Acknowledgements

The authors are grateful to the Brazilian sponsor agencies, CNPq and FAPEMIG (EDT PRONEX 479/07), for the financial support.

References

- [1] Zhang, Y.P. and Zhou, J.L. (2008) Occurrence and Removal of Endocrine Disrupting Chemicals in Wastewater. *Chemosphere*, **73**, 848-853. <http://dx.doi.org/10.1016/j.chemosphere.2008.06.001>
- [2] Roig, B., Greenwood, R. and Barcelo, D. (2009) An International Conference on "Pharmaceuticals in the Environment" in a Frame of EU Knappe Project. *Environment International*, **35**, 763-765. <http://dx.doi.org/10.1016/j.envint.2009.01.012>
- [3] Kummerer, K. (2009) The Presence of Pharmaceuticals in the Environment Due to Human Use—Present Knowledge and Future Challenges. *Journal of Environmental Management*, **90**, 2354-2366. <http://dx.doi.org/10.1016/j.jenvman.2009.01.023>
- [4] Cooper, E.R., Siewicki, T.C. and Phillips, K. (2008) Preliminary Risk Assessment Database and Risk Ranking of Pharmaceuticals in the Environment. *Science of the Total Environment*, **398**, 26-33. <http://dx.doi.org/10.1016/j.scitotenv.2008.02.061>
- [5] Daughton, C.G. and Ruhoy, I.S. (2009) Environmental Footprint of Pharmaceuticals: The Significance of Factors beyond Direct Excretion to Sewers. *Environmental Toxicology and Chemistry*, **28**, 2495-2521. <http://dx.doi.org/10.1897/08-382.1>
- [6] Rahman, M.F., Yanful, E.K. and Jasim, S.Y. (2009) Occurrences of Endocrine Disrupting Compounds and Pharmaceuticals in the Aquatic Environment and Their Removal from Drinking Water: Challenges in the Context of the Developing World. *Desalination*, **248**, 578-585. <http://dx.doi.org/10.1016/j.desal.2008.05.105>
- [7] Rahman, M.F., Yanful, E.K. and Jasim, S.Y. (2009) Endocrine Disrupting Compounds (EDCs) and Pharmaceuticals and Personal Care Products (PPCPs) in the Aquatic Environment: Implications for the Drinking Water Industry and Global Environmental Health. *Journal of Water and Health*, **7**, 224-243. <http://dx.doi.org/10.2166/wh.2009.021>
- [8] Khetan, S.K. and Collins, T.J. (2007) Human Pharmaceuticals in the Aquatic Environment: A Challenge to Green Chemistry. *Chemical Reviews*, **107**, 2319-2364. <http://dx.doi.org/10.1021/cr020441w>
- [9] Li, H.Q., Song, Y.X. and Peng, X.F. (2008) Improved Synthesis of Mestranol and Ethinyl Estradiol (Ee) Related Degradation Products as Authentic References. *Steroids*, **73**, 488-494. <http://dx.doi.org/10.1016/j.steroids.2007.12.024>
- [10] Zhao, Y.P., Hu, J.Y. and Jin, W. (2008) Transformation of Oxidation Products and Reduction of Estrogenic Activity of 17 Beta-Estradiol by a Heterogeneous Photo-Fenton Reaction. *Environmental Science & Technology*, **42**, 5277-5284. <http://dx.doi.org/10.1021/es703253q>
- [11] Huber, M.M., Canonica, S., Park, G.Y. and Von Gunten, U. (2003) Oxidation of Pharmaceuticals During Ozonation and Advanced Oxidation Processes. *Environmental Science & Technology*, **37**, 1016-1024. <http://dx.doi.org/10.1021/es025896h>
- [12] Hansen, P.D., Dizer, H., Hock, B., Marx, A., Sherry, J., McMaster, M. and Blaise, C. (1998) Vitellogenin—A Biomarker for Endocrine Disruptors. *Trac-Trends in Analytical Chemistry*, **17**, 448-451. [http://dx.doi.org/10.1016/S0165-9936\(98\)00020-X](http://dx.doi.org/10.1016/S0165-9936(98)00020-X)
- [13] Hiramatsu, N., Matsubara, T., Fujita, T., Sullivan, C.V. and Hara, A. (2006) Multiple Piscine Vitellogenins: Biomarkers of Fish Exposure to Estrogenic Endocrine Disruptors in Aquatic Environments. *Marine Biology*, **149**, 35-47. <http://dx.doi.org/10.1007/s00227-005-0214-z>
- [14] Sole, M., Porte, C. and Barcelo, D. (2001) Analysis of the Estrogenic Activity of Sewage Treatment Works and Receiving Waters Using Vitellogenin Induction in Fish as a Biomarker. *Trac-Trends in Analytical Chemistry*, **20**, 518-525. [http://dx.doi.org/10.1016/S0165-9936\(01\)00055-3](http://dx.doi.org/10.1016/S0165-9936(01)00055-3)
- [15] Sumpter, J.P. and Jobling, S. (1995) Vitellogenesis as a Biomarker for Estrogenic Contamination of the Aquatic Environment. *Environmental Health Perspectives*, **103**, 173-178. <http://dx.doi.org/10.1289/ehp.95103s7173>
- [16] Deborde, M., Rabouan, S., Duguet, J.P. and Legube, B. (2005) Kinetics of Aqueous Ozone-Induced Oxidation of Some Endocrine Disruptors. *Environmental Science & Technology*, **39**, 6086-6092. <http://dx.doi.org/10.1021/es0501619>
- [17] Lee, Y., Escher, B.I. and Von Gunten, U. (2008) Efficient Removal of Estrogenic Activity during Oxidative Treatment of Waters Containing Steroid Estrogens. *Environmental Science & Technology*, **42**, 6333-6339. <http://dx.doi.org/10.1021/es7023302>

- [18] Rosenfeldt, E.J. and Linden, K.G. (2004) Degradation of Endocrine Disrupting Chemicals Bisphenol A, Ethinyl Estradiol, and Estradiol During UV Photolysis and Advanced Oxidation Processes. *Environmental Science & Technology*, **38**, 5476-5483. <http://dx.doi.org/10.1021/es035413p>
- [19] Rosu, F., De Pauw, E. and Gabelica, V. (2008) Electrospray Mass Spectrometry to Study Drug-Nucleic Acids Interactions. *Biochimie*, **90**, 1074-1087. <http://dx.doi.org/10.1016/j.biochi.2008.01.005>
- [20] Huber, M.M., Gobel, A., Joss, A., Hermann, N., Löffler, D., Mcardell, C.S., Ried, A., Siegrist, H., Ternes, T.A. and von Gunten, U. (2005) Oxidation of Pharmaceuticals during Ozonation of Municipal Wastewater Effluents: A Pilot Study. *Environmental Science & Technology*, **39**, 4290-4299. <http://dx.doi.org/10.1021/es048396s>
- [21] Pignatello, J.J., Oliveros, E. and MacKay, A. (2006) Advanced Oxidation Processes for Organic Contaminant Destruction Based on the Fenton Reaction and Related Chemistry. *Critical Reviews in Environmental Science and Technology*, **36**, 1-84. <http://dx.doi.org/10.1080/10643380500326564>
- [22] Adewuyi, Y.G. (2005) Sonochemistry in Environmental Remediation. 1. Combinative and Hybrid Sonophotocatalytic Oxidation Processes for the Treatment of Pollutants in Water. *Environmental Science & Technology*, **39**, 3409-3420. <http://dx.doi.org/10.1021/es049138y>
- [23] Adewuyi, Y.G. (2005) Sonochemistry in Environmental Remediation. 2. Heterogeneous Sonophotocatalytic Oxidation Processes for the Treatment of Pollutants in Water. *Environmental Science & Technology*, **39**, 8557-8570. <http://dx.doi.org/10.1021/es0509127>
- [24] Buzzini, A.P., Miwa, D.W., Motheo, A.J. and Pires, E.C. (2006) Use of Electrochemical Oxidation Process as Post-Treatment for the Effluents of a UASB Reactor Treating Cellulose Pulp Mill Wastewater. *Water Science and Technology*, **54**, 207-213. <http://dx.doi.org/10.2166/wst.2006.507>
- [25] Gomes, L., Freitas, R.G., Malpass, G.R.P., Pereira, E.C. and Motheo, A.J. (2009) Pt Film Electrodes Prepared by the Pechini Method for Electrochemical Decolourisation of Reactive Orange 16. *Journal of Applied Electrochemistry*, **39**, 117-121. <http://dx.doi.org/10.1007/s10800-008-9649-5>
- [26] Malpass, G.R.P., Miwa, D.W., Machado, S.A.S. and Motheo, A.J. (2008) Decolourisation of Real Textile Waste Using Electrochemical Techniques: Effect of Electrode Composition. *Journal of Hazardous Materials*, **156**, 170-177. <http://dx.doi.org/10.1016/j.jhazmat.2007.12.017>
- [27] Malpass, G.R.P., Miwa, D.W., Machado, S.A.S., Olivi, P. and Motheo, A.J. (2006) Oxidation of the Pesticide Atrazine at DSA (R) Electrodes. *Journal of Hazardous Materials*, **137**, 565-572. <http://dx.doi.org/10.1016/j.jhazmat.2006.02.045>
- [28] Malpass, G.R.P., Neves, R.S. and Motheo, A.J. (2006) A Comparative Study of Commercial and Laboratory-Made Ti/Ru_{0.3}Ti_{0.7}O₂ DSA (R) Electrodes: "In Situ" and "Ex Situ" Surface Characterisation and Organic Oxidation Activity. *Electrochimica Acta*, **52**, 936-944. <http://dx.doi.org/10.1016/j.electacta.2006.06.032>
- [29] Malpass, G.R.P., Miwa, D.W., Mortari, D.A., Machado, S.A.S. and Motheo, A.J. (2007) Decolorisation of Real Textile Waste Using Electrochemical Techniques: Effect of the Chloride Concentration. *Water Research*, **41**, 2969-2977. <http://dx.doi.org/10.1016/j.watres.2007.02.054>
- [30] Butterfield, I.M., Christensen, P.A., Hamnett, A., Shaw, K.E., Walker, G.M., Walker, S.A. and Howarth, C.R. (1997) Applied Studies on Immobilized Titanium Dioxide Films as Catalysts for the Photoelectrochemical Detoxification of Water. *Journal of Applied Electrochemistry*, **27**, 385-395. <http://dx.doi.org/10.1023/A:1018453402332>
- [31] Kesselman, J.M., Lewis, N.S. and Hoffmann, M.R. (1997) Photoelectrochemical Degradation of 4-Chlorocatechol at TiO₂ Electrodes: Comparison between Sorption and Photoreactivity. *Environmental Science & Technology*, **31**, 2298-2302. <http://dx.doi.org/10.1021/es960888k>
- [32] Vinodgopal, K., Hotchandani, S. and Kamat, P.V. (1993) Electrochemically Assisted Photocatalysis: TiO₂ Particulate Film Electrodes for Photocatalytic Degradation of 4-Chlorophenol. *Journal of Physical Chemistry*, **97**, 9040-9044. <http://dx.doi.org/10.1021/j100137a033>
- [33] Pelegrini, R., Peralta-Zamora, P., de Andrade, A.R., Reyes, J. and Duran, N. (1999) Electrochemically Assisted Photocatalytic Degradation of Reactive Dyes. *Applied Catalysis B: Environmental*, **22**, 83-90. [http://dx.doi.org/10.1016/S0926-3373\(99\)00037-5](http://dx.doi.org/10.1016/S0926-3373(99)00037-5)
- [34] Rodriguez, J., Gomez, M., Lindquist, S.E. and Granqvist, C.G. (2000) Photo-Electrocatalytic Degradation of 4-Chlorophenol over Sputter Deposited Ti Oxide Films. *Thin Solid Films*, **360**, 250-255. [http://dx.doi.org/10.1016/S0040-6090\(99\)01080-9](http://dx.doi.org/10.1016/S0040-6090(99)01080-9)
- [35] Vinodgopal, K., Stafford, U., Gray, K.A. and Kamat, P.V. (1994) Electrochemically Assisted Photocatalysis. 2. The Role of Oxygen and Reaction Intermediates in the Degradation of 4-Chlorophenol on Immobilized TiO₂ Particulate Films. *Journal of Physical Chemistry*, **98**, 6797-6803. <http://dx.doi.org/10.1021/j100078a023>
- [36] Vinodgopal, K., Wynkoop, D.E. and Kamat, P.V. (1996) Environmental Photochemistry on Semiconductor Surfaces:

- Photosensitized Degradation of a Textile Azo Dye, Acid Orange 7, on TiO₂ Particles Using Visible Light. *Environmental Science & Technology*, **30**, 1660-1666. <http://dx.doi.org/10.1021/es950655d>
- [37] Walker, S.A., Christensen, P.A., Shaw, K.E. and Walker, G.M. (1995) Photoelectrochemical Oxidation of Aqueous Phenol Using Titanium-Dioxide Aerogel. *Journal of Electroanalytical Chemistry*, **393**, 137-140. [http://dx.doi.org/10.1016/0022-0728\(95\)04186-R](http://dx.doi.org/10.1016/0022-0728(95)04186-R)
- [38] Brunelli, T.F.T., Guaraldo, T.T., Paschoal, F.M.M. and Zanoni, M.V.B. (2009) Photoelectrochemical Degradation of Disperse Dyes in Textile Effluent on Photoanodes of Ti/TiO₂. *Quimica Nova*, **32**, 67-71. <http://dx.doi.org/10.1590/S0100-40422009000100013>
- [39] Catanho, M., Malpass, G.R.P. and Motheo, A.D. (2006) Evaluation of Electrochemical and Photoelectrochemical Methods for the Degradation of Three Textile Dyes. *Quimica Nova*, **29**, 983-989. <http://dx.doi.org/10.1590/S0100-40422006000500018>
- [40] Catanho, M., Malpass, G.R.P. and Motheo, A.J. (2006) Photoelectrochemical Treatment of the Dye Reactive Red 198 Using DSA (R) Electrodes. *Applied Catalysis B: Environmental*, **62**, 193-200. <http://dx.doi.org/10.1016/j.apcatb.2005.07.011>
- [41] Fraga, L.E., Anderson, M.A., Beatriz, M.L.P.M.A., Paschoal, F.M.M., Romao, L.P. and Zanoni, M.V.B. (2009) Evaluation of the Photoelectrocatalytic Method for Oxidizing Chloride and Simultaneous Removal of Microcystin Toxins in Surface Waters. *Electrochimica Acta*, **54**, 2069-2076. <http://dx.doi.org/10.1016/j.electacta.2008.08.060>
- [42] Malpass, G.R.P., Miwa, D.W., Miwa, A.C.P., Machado, S.A.S. and Motheo, A.J. (2007) Photo-Assisted Electrochemical Oxidation of Atrazine on a Commercial Ti/Ru_{0.3}Ti_{0.7}O₂ DSA Electrode. *Environmental Science & Technology*, **41**, 7120-7125. <http://dx.doi.org/10.1021/es070798n>
- [43] Paschoal, F.M.M., Anderson, M.A. and Zanoni, M.V.B. (2008) Photoelectrocatalytic Oxidation of Anionic Surfactant Used in Leather Industry on Nanoporous Ti/TiO₂ Electrodes. *Journal of the Brazilian Chemical Society*, **19**, 803-810. <http://dx.doi.org/10.1590/S0103-50532008000400027>
- [44] Paschoal, F.M.M., Anderson, M.A. and Zanoni, M.V.B. (2009) Simultaneous Removal of Chromium and Leather Dye from Simulated Tannery Effluent by Photoelectrochemistry. *Journal of Hazardous Materials*, **166**, 531-537. <http://dx.doi.org/10.1016/j.jhazmat.2008.11.058>
- [45] Zanoni, M.V.B., Sene, J.J. and Anderson, M.A. (2003) Photoelectrocatalytic Degradation of Remazol Brilliant Orange 3r on Titanium Dioxide Thin-Film Electrodes. *Journal of Photochemistry and Photobiology A: Chemistry*, **157**, 55-63. [http://dx.doi.org/10.1016/S1010-6030\(02\)00320-9](http://dx.doi.org/10.1016/S1010-6030(02)00320-9)
- [46] Osugi, M.E., Umbuzeiro, G.A., De Castro, F.J.V. and Zanoni, M.V.B. (2006) Photoelectrocatalytic Oxidation of Remazol Turquoise Blue and Toxicological Assessment of Its Oxidation Products. *Journal of Hazardous Materials*, **137**, 871-877. <http://dx.doi.org/10.1016/j.jhazmat.2006.03.036>
- [47] Dalmazio, I., de Urzedo, A.P.F.M., Alves, T.M.A., Catharino, R.R., Eberlin, M.N., Nascentes, C.C. and Augusti, R. (2007) Electrospray Ionization Mass Spectrometry Monitoring of Indigo Carmine Degradation by Advanced Oxidative Processes. *Journal of Mass Spectrometry*, **42**, 1273-1278. <http://dx.doi.org/10.1002/jms.1159>
- [48] Dalmazio, I., Santos, L.S., Lopes, R.P., Eberlin, M.N. and Augusti, R. (2005) Advanced Oxidation of Caffeine in Water: On-Line and Real-Time Monitoring by Electrospray Ionization Mass Spectrometry. *Environmental Science & Technology*, **39**, 5982-5988. <http://dx.doi.org/10.1021/es047985v>
- [49] de Urzedo, A.P.F.M., Diniz, M.E.R., Nascentes, C.C., Catharino, R.R., Eberlin, M.N. and Augusti, R. (2007) Photolytic Degradation of the Insecticide Thiamethoxam in Aqueous Medium Monitored by Direct Infusion Electrospray Ionization Mass Spectrometry. *Journal of Mass Spectrometry*, **42**, 1319-1325. <http://dx.doi.org/10.1002/jms.1204>
- [50] de Urzedo, A.P.F.M., Nascentes, C.C., Diniz, M.E.R., Catharino, R.R., Eberlin, M.N. and Augusti, R. (2007) Indigo Carmine Degradation by Hypochlorite in Aqueous Medium Monitored by Electrospray Ionization Mass Spectrometry. *Rapid Communications in Mass Spectrometry*, **21**, 1893-1899. <http://dx.doi.org/10.1002/rcm.3037>
- [51] Florencio, M.H., Pires, E., Castro, A.L., Nunes, M.R., Borges, C. and Costa, F.M. (2004) Photodegradation of Diquat and Paraquat in Aqueous Solutions by Titanium Dioxide: Evolution of Degradation Reactions and Characterization of Intermediates. *Chemosphere*, **55**, 345-355. <http://dx.doi.org/10.1016/j.chemosphere.2003.11.013>
- [52] Hess, T.F., Renn, T.S., Watts, R.J. and Paszczynski, A.J. (2003) Studies on Nitroaromatic Compound Degradation in Modified Fenton Reactions by Electrospray Ionization Tandem Mass Spectrometry (ESI-MS-MS). *Analyst*, **128**, 156-160. <http://dx.doi.org/10.1039/b209776c>
- [53] Lopes, R.P., de Urzedo, A.P.F.M., Nascentes, C.C. and Augusti, R. (2008) Degradation of the Insecticides Thiamethoxam and Imidacloprid by Zero-Valent Metals Exposed to Ultrasonic Irradiation in Water Medium: Electrospray Ionization Mass Spectrometry Monitoring. *Rapid Communications in Mass Spectrometry*, **22**, 3472-3480.

- <http://dx.doi.org/10.1002/rcm.3749>
- [54] Madeira, P., Nunes, M.R., Borges, C., Costa, F.M.A. and Florencio, M.H. (2005) Benzidine Photodegradation: A Mass Spectrometry and UV Spectroscopy Combined Study. *Rapid Communications in Mass Spectrometry*, **19**, 2015-2020. <http://dx.doi.org/10.1002/rcm.2019>
- [55] Moura, F.C.C., Araujo, M.H., Dalmazio, I., Alves, T.M.A., Santos, L.S., Eberlin, M.N., Augusti, R. and Lago, R.M. (2006) Investigation of Reaction Mechanisms by Electrospray Ionization Mass Spectrometry: Characterization of Intermediates in the Degradation of Phenol by a Novel Iron/Magnetite/Hydrogen Peroxide Heterogeneous Oxidation System. *Rapid Communications in Mass Spectrometry*, **20**, 1859-1863. <http://dx.doi.org/10.1002/rcm.2523>
- [56] Santos, L.S., Dalmazio, I., Eberlin, M.N., Claeys, M. and Augusti, R. (2006) Mimicking the Atmospheric OH-Radical-Mediated Photooxidation of Isoprene: Formation of Cloud-Condensation Nuclei Polyols Monitored by Electrospray Ionization Mass Spectrometry. *Rapid Communications in Mass Spectrometry*, **20**, 2104-2108. <http://dx.doi.org/10.1002/rcm.2574>

Scientific Research Publishing (SCIRP) is one of the largest Open Access journal publishers. It is currently publishing more than 200 open access, online, peer-reviewed journals covering a wide range of academic disciplines. SCIRP serves the worldwide academic communities and contributes to the progress and application of science with its publication.

Other selected journals from SCIRP are listed as below. Submit your manuscript to us via either submit@scirp.org or [Online Submission Portal](#).

