

REVIEW ARTICLE

Potential applications of natural origin polymer-based systems in soft tissue regeneration

Simone S. Silva^{1,2}, João F. Mano^{1,2}, and Rui L. Reis^{1,2}

¹3B's Research Group- Biomaterials, Biodegradables and Biomimetics, Dept. of Polymer Engineering, University of Minho, Headquarters of the European Institute of Excellence on Tissue Engineering and Regenerative Medicine - AvePark, Zona Industrial da Gandra - Caldas das Taipas - 4806-909 Guimarães- Portugal, ²IBB - Institute for Biotechnology and Bioengineering, PT Associated Laboratory, Guimarães, Portugal

Abstract

Despite the many advances in tissue engineering approaches, scientists still face significant challenges in trying to repair and replace soft tissues. Nature-inspired routes involving the creation of polymer-based systems of natural origins constitute an interesting alternative route to produce novel materials. The interest in these materials comes from the possibility of constructing multi-component systems that can be manipulated by composition allowing one to mimic the tissue environment required for the cellular regeneration of soft tissues. For this purpose, factors such as the design, choice, and compatibility of the polymers are considered to be key factors for successful strategies in soft tissue regeneration. More recently, polysaccharide-protein based systems have been increasingly studied and proposed for the treatment of soft tissues. The characteristics, properties, and compatibility of the resulting materials investigated in the last 10 years, as well as commercially available matrices or those currently under investigation are the subject matter of this review.

Keywords: *Natural polymers, multicomponent systems, biotechnology, soft tissue, tissue engineering, polysaccharide-protein interactions*

Introduction

Despite the many advances in tissue engineering (TE) approaches, scientists still face significant challenges in repairing or replacing soft tissues such as tendons, ligaments, skin, liver, nerve, and cartilage to improve the quality of life for people. The conventional therapeutic treatments targeted to reconstruct injured tissues or organs have some limitations such as donor limitations and graft rejections. Based on the principles of TE (Langer and Vacanti, 1993; Lanza et al., 2000), alternative therapeutic strategies have been developed as current treatments involving biodegradable constructs containing specific populations of living cells and growth factors. For example, skin can be regenerated using epidermal sheets, dermal replacements, and complex skin substitutes (Metcalf and Ferguson, 2007; MacNeil, 2007; Barbul, 2001), while cartilage defects can be treated

with cells seeded on three-dimensional (3D) matrices (Chung and Burdick, 2008; Temenoff and Mikos, 2000; Hutmacher, 2000). Nature-inspired routes involving the creation of polymer-based systems of natural origin (e.g. polysaccharide-protein) constitute an interesting alternative to produce novel materials that can fulfil all the necessary requirements for the success of these approaches. However, the properties of these systems will depend on the choice of the composition of the system, the intrinsic characteristics (e.g. molecular weight, charge) of each component, their degree of interaction, and their miscibility (McClements, 2006; Turgeon et al., 2003). Both polysaccharides and proteins exhibit the relevant characteristics such as their availability in nature, chemical diversity, biodegradability, and may be modified relatively easily (Damodaran, 1997; Lloyd et al., 1998; Gomes et al., 2008; Mano et al., 2007). These features

Address for Correspondence: Simone S. Silva, 3B's Research Group - Biomaterials, Biodegradables and Biomimetics, University of Minho, Headquarters of the European Institute of Excellence on Tissue Engineering and Regenerative Medicine, Avepark, 4806-909 Taipas, Guimarães, Portugal. Tel.: +351 253510900; Fax: +351 253510909; E-mail: simonesilva@dep.uminho.pt

(Accepted 02 June 2010)

when combined have proven to be a useful route to obtain bioengineered biomatrices with better mechanical and biological properties compared to their individual components. In this review, attention has been focused on polymer-based systems of natural origins composed mainly of chitin/chitosan, glycosaminoglycans, alginate, and cellulose combined with different proteins, which have been recently proposed for applications for soft tissue repair and regeneration.

Natural origin polymers and their combinations

Most of the current researchers have headed towards studying the use of natural biodegradable polymers such as collagen (Gomes et al., 2008; Stark et al., 2006; Pieper et al., 2002), chitosan (Gomes et al., 2008; Kumar, 2000; Kim et al., 2008; Madhally and Matthew, 1999; Suh and Matthew, 2000), hyaluronic acid (Gomes et al., 2008; Yoo et al., 2005; Aigner et al., 1998; Kogan et al., 2007), cellulose (Gomes et al., 2008; Pulkkinen et al., 2006), starch (Malafaya et al., 2006; Gomes et al., 2008; Gomes et al., 2006; Oliveira et al., 2007; Santos et al., 2007; Silva et al., 2007a), soy protein (Gomes et al., 2008; Vaz et al., 2002; Vaz et al., 2003), gelatin (Gomes et al., 2008; Kang et al., 1999), silk fibroin (Gomes et al., 2008; Vepari and Kaplan, 2007; Altman et al., 2003; MacIntosh et al., 2008; Unger et al., 2004), and alginate (Gomes et al., 2008; Eiselt et al., 2000) separately, or combined them for TE applications (Gomes et al., 2008; Malafaya et al., 2007; Mano et al., 2007; Seal et al., 2001; Chang et al., 2003a; Funakoshi et al., 2005; Lee et al., 2005; Liao et al., 2007; Ma et al., 2003). The material choice for a particular application depends upon the type of material required, the nature of the tissues to be regenerated, and their regeneration time. Besides that, the wide variety of structures and the unique biological, chemical or physical functionalities of these polymers can be associated, allowing one to create interesting materials such as membranes, hydrogels, scaffolds, and micro/nanospheres. These natural origin polymer-based materials offer advantages such as the creation of new opportunities for mimicking the tissue microenvironment and can stimulate the appropriate physiological responses required for cellular regeneration. It seems that all these features associated with a controlled biodegradation rate and the biocompatibility of these naturally based-systems can be advantageous when compared to synthetic polymers. Figure 1 shows some devices organized according to their geometrical dimensions. The polymeric matrices can be produced using several techniques. For example, membranes can be obtained by solvent casting of polymeric solutions, while hydrogels can be processed by traditional synthesis, including cross-linking reactions and copolymerization reactions (Kopecek and Yang, 2007; Hennink and van Nostrum, 2002). However, some methods are limited with respect to the control of their resulting structures

due to side reactions, unreacted pendant groups, and entanglements. Scaffolds are usually prepared by freeze-drying techniques, emulsion freeze-drying methods, salt leaching methods, rapid prototyping, fiber bonding, melt based methodologies, among many others (Gomes and Reis, 2004; Mano et al., 2007; Mikos and Temenoff, 2000; Correlo et al., 2007a; Chen et al., 2002; Lee et al., 2009). Among these, the freeze-drying technique is the most widely used method (Correlo et al., 2007a; Suh and Matthew, 2000) to produce scaffolds with different shapes, porosities, and pore size distributions by varying the parameters such as the polymer concentration, type of solvent, freezing temperature, and type of molds. Also, the electrospinning process has become a promising method for the preparation of 3D porous mats with large surface areas, and high porosity, which can mimic the extracellular matrix (ECM). Other advantages of this method are the possibility of large-scale production, easy processing, easy functionalization, and the availability of advanced modes of electrospinning (Agarwal et al., 2009; Lee et al., 2009). Recently, electrospun polyblend nanofibers have been prepared from a combination of polymers, which take advantage of the varying strengths, bioactivities, and degradation rates of all the components involved (Gunn and Zhang, 2010). Using this approach, the solubilization and electrospinning issues of some natural polymers have been overcome, allowing their production in nanofiber technology.

The selection of the design and processing techniques to create adequate scaffold architectures allows the preparation of porous structures with controlled porosity, pore size, and interconnectivity, as well as tissue matching mechanical properties (Gomes and Reis, 2004). However, these requirements will depend on the tissue to be regenerated (Lanza et al., 2000). For example, successful nerve regeneration requires tissue-engineered scaffolds that provide not only mechanical support for the growing neuritis, but also the biological signals to direct the axonal growth cone to the distal stump (Schmidt and Leach, 2003; Huang and Huang, 2006). This is particularly true for osteochondral defects, where the use of single scaffolds to regenerate cartilage may not be effective, and the employment of bilayered constructs has been proposed as an alternative solution (Mano and Reis, 2007; Malafaya et al., 2005; Oliveira et al., 2006; Gao et al., 2002). This approach consists of developing a 3D porous structure that combines a mechanical support resembling the subchondral bone, while also providing a chondrogenic support for cartilage repair.

In this review, the characteristics of the main biopolymers and their combinations are described in the following sections, and the tables (Tables 1 to 4) summarize the most frequently proposed blend systems (e.g. polysaccharide-protein) as applications for soft tissue repair. These tables also include the methods for production for blend systems, the matrix shape, the aimed TE application, the biologically

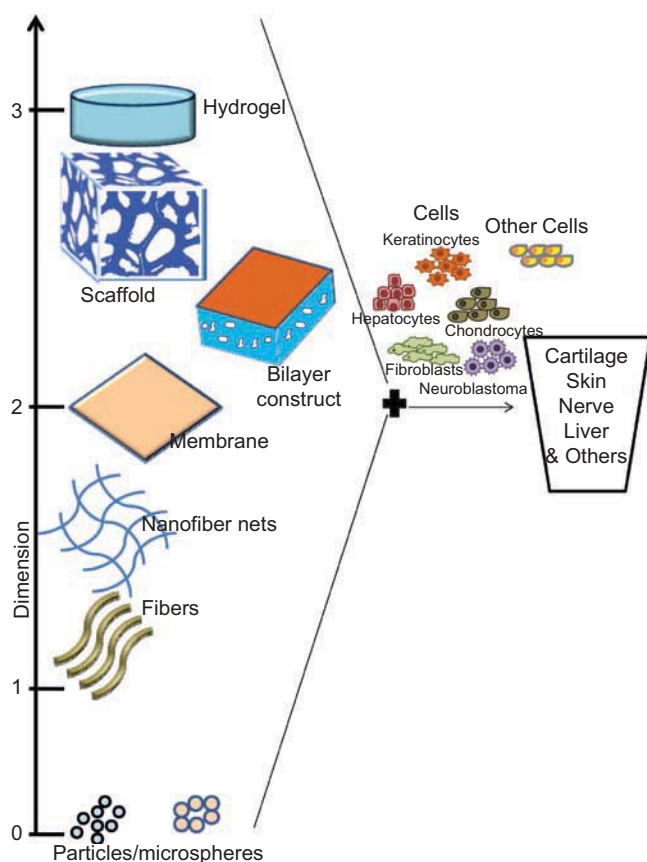


Figure 1. Scheme of different polymeric architectures proposed for soft tissue repair.

active biomolecule to be delivered, and the source of the cell used for the *in vitro* tests. When applicable the animal model used is also indicated.

Chitin/chitosan

Chitin is the second most abundant natural polymer in nature, it is found in the shell of crustaceans, the cuticles of insects, and the cell walls of fungi (Kumar et al., 2004; Kurita, 2001; Kumar, 2000). Structurally, chitin is composed of $\beta(1-4)$ -linked N-acetyl-D-glucosamine (Kumar, 2000). This polymer has bacteriostatic and fungistatic activities, which are favorable for promoting rapid dermal regeneration and for accelerating wound healing (Kumar, 2000; Peniche et al., 2008). However, the applications of chitin have been limited due to its insolubility in water and also in most of the common organic solvents (Kumar, 2000). Nevertheless, chitin is soluble in hexafluoroisopropanol, hexafluoroacetone and dimethylacetamide containing 5% lithium chloride (Kumar, 2000). Therefore, some researchers have investigated the use of some types of chitin-based materials (filaments, granules, sponges, and films) as components for wound management products (Koji et al., 1987; Fox and Allen, 1996). Despite the intrinsic properties of chitin, some studies have suggested that an improvement

in the biocompatibility of chitin for use in appropriate dressings can be achieved by associating the chitin with other polysaccharides or proteins (Lee et al., 2004; Hirano et al., 2001), or by creating chitin derivatives (e.g. carboxymethyl chitin, water-soluble chitin, dibutyl chitin) (Pielka et al., 2003; Muzzarelli et al., 2005; Cho et al., 1999) using chemical modification.

Chitosan is a polysaccharide obtained by the alkaline deacetylation of chitin (Kumar, 2000; Kumar et al., 2004). This polymer has many properties such as its polyelectrolyte and cationic nature, mucoadhesion, hemostatic action, film-forming ability, biodegradability, bacteriostatic, and fungistatic activity (Kumar, 2000; Peniche et al., 2008). Besides, the presence of functional groups (hydroxyl, amine) it has been beneficial for chemical modification to introduce the desired properties into chitosan, which can be useful for specific uses in diversified fields (Kumar et al., 2004; Kim et al., 2008; Jayakumar et al., 2005; Mourya and Inamdhar, 2008). Because of the stable crystalline structure, chitosan is normally insoluble in water, but soluble in dilute aqueous acidic solutions. These solutions have been used in the production of gels, membranes, microparticles, nanofibers, porous structures, and tubes, which combined with its pH sensitivity and high charge density (positive electrical charge) has allowed the development of drug delivery devices, composites, polyelectrolyte complexes, and implants for tissue engineering applications. Several chitosan-based matrices have been developed to be used as dermal substitutes, wound dressings, porous structures for cartilage repair, and other TE applications (see Table 1). Considering that chitosan promotes good protection of the wound, accelerated wound healing, and an antibacterial action (Khor and Lim, 2003; Kim et al., 2008), chitosan membranes have been proposed as simple wound coverings or as sophisticated artificial skin matrices, and hydrogels. Although the preparation, properties, and characterization of both chitosan films and bilayer membranes for use as wound dressings have been extensively investigated, (Aoyagi et al., 2007; Khan et al., 2000; Khan and Peh, 2003; Azad et al., 2004; Marreco et al., 2004; Azevedo et al., 2006; Mizuno et al., 2003; Queiroz et al., 2003; Mi et al., 2002b; Ma et al., 2001), a few reports concerned with clinical trials have been described in the literature (Azad et al., 2004).

With the rise of nanotechnology, chitosan together with other macromolecules has been fabricated into various bionanocomposites, providing alternative applications in regenerative medicine and drug delivery vesicles (Chen et al., 2008; Zhou et al., 2008; Lee et al., 2009). For example, composite nanofibrous membranes of collagen/chitosan/polyethylene oxide blends have demonstrated unique combinations of mechanical, biological, and structural properties suitable as wound dressings for skin regeneration (Chen et al., 2008). On the other hand, some studies have described the complexation of chitosan with

Table 1. Chitosan-based matrices proposed for applications in soft tissue repair. Targeted tissues and organs include cartilage, skin, liver, nerve, tendon, and ligaments.

Composition	Processing Methodology	Matrix type	Active substance	Potential TE application	Cell type (source/line)	Animal model	Reference
Chitosan-alginate	Solvent casting	Membranes	-	Wound dressing	Fibroblast like cells	Sprague Dawley rats	(Wang et al., 2002)
	Interpolyelectrolyte complex method	Macroporous membranes	AgSD	Wound dressing	-	-	(Yu et al., 2005a)
	Freeze-drying	Scaffolds	-	Cartilage	Chondrocyte like cells	-	(Li and Zhang, 2005)
	Coagulation bathspinning	Fibers	-	Cartilage	Chondrocytes (rabbit)	-	(Iwasaki et al., 2004)
	Freeze-drying	Scaffolds	-	Cartilage	ATDC5 cell line	-	(Tigli and Gumusderelioglu, 2009)
	Wet spinning	Fibers	-	Tendons and ligaments	Fibroblast(rabbit)	-	(Majima et al., 2005)
	Spinning mandrel technology	Hydrogels	NGF	Nerve conduit	-	-	(Pfister et al., 2008)
Chitosan-alginate-fucoidan	-	Hydrogels	Mitomycin C	Wound dressing	Human dermal fibroblast/dermal micro-vascular endothelial	Sprague Dawley rats	(Murakami et al., 2010)
Galactosylated chitosan-alginate	Freeze-drying	Sponges	-	Liver	Hepatocytes(mouse)	-	(Yang et al., 2001;
	Cross-linking (CaCl ₂)	-	-	-	-	-	Chung et al., 2002)
Galactosylated chitosan-alginate	Freeze-drying	Scaffolds	-	Bioartificial liver	Co-culture of hepatocytes (mice)	-	(Seo et al., 2006c)
	Cross-linking(CaCl ₂)	-	-	-	NIH 3T3 Fibroblasts	-	
Galactosylated chitosan-alginate-heparin	Freeze-drying	Scaffolds	-	Bioartificial liver	Hepatocytes(mice)	-	(Seo et al., 2006a)
	Cross-linking (CaCl ₂)	-	-	-	NIH 3T3 Fibroblasts	-	
Chitosan-alginate-hyaluronan	Solvent casting	Membranes and scaffolds	-	Cartilage	Chondrocytes	-	(Hsu et al., 2004)
	Freeze-drying	-	-	-	-	-	
Chitosan-bacterial cellulose	Biosynthesis	Hydrogels	-	Wound dressing	-	-	(Ciechanska, 2004a)
Chitosan-chondroitin-6-sulfate-dermatan	Freeze-drying	Scaffolds	-	Cartilage	Chondrocytes (Wistar rats)	-	(Chen et al., 2007b)
	Cross-linking	-	-	-	-	-	
Chitosan-collagen	Freeze-gelation	Scaffolds	-	Skin	Embryonic Fibroblasts (human)	-	(Tsai et al., 2007)
	Cross-linking (EDC)	-	-	-	-	-	
	Quenching ethanol extraction	Porous membranes	-	Dermal regeneration template	-	-	Gao et al., 2003b)
	Freeze-drying DHT	Scaffolds	-	Dermal equivalent	Human fibroblast	Rabbit ear	(Ma et al., 2003a)
	Cross-linking (GA)	-	-	-	-	-	
	Solvent casting	Films	HN-300	Antimicrobial wound dressing	Fibroblast-like cells (mouse)	-	(Guan et al., 2007a)
	Solvent casting	Films	-	Artificial livers	Hepatocytes (rats)	-	(Wang et al., 2003)
	Cross-linking (EDC)	-	-	-	-	-	

Table 1. continued on next page

Table 1. Continued.

Composition	Processing Methodology	Matrix type	Active substance	Potential TE application	Cell type (source/line)	Animal model	Reference
	Freeze-drying Ammonia treatment	Scaffolds	-	Liver	Hepatocytes (rats)	-	(Wang et al., 2005)
	Freeze-drying Steam-extrusion Cross-linking (GA)	Scaffolds	-	Nerve regeneration	Retina cells	-	(Wang et al., 2009b)
Carboxymethyl chitosan-collagen	Freeze-drying Cross-linking (EDC)	Porous matrices	-	Wound dressing	Fibroblasts (human)	Wistar rats	(Chen et al., 2006b)
Chitosan-collagen-chondroitin sulfate	Emulsion Freeze-drying Cross-linking (EDC)	Microspheres encapsulated in scaffolds	TGF- β 1	Cartilage	Chondrocytes (rabbits)	-	(Lee et al., 2004a)
	Freeze-drying Cross linking (EDC)	Scaffolds	-	Cartilage	Chondrocytes (rabbits)	-	(Lee et al., 2005)
	Freeze-drying Cross-linking (EDC)	Scaffolds	-	Cartilage	Chondrocytes (rabbits)	Athymic male mice	(Yan et al., 2007a)
	Freeze-drying	Scaffolds	-	Dermal substitute	foreskin and adult dermal fibroblast	Rats	(Kellouche et al., 2007)
Chitosan-collagen-chondroitin sulfate	Freeze-drying	Sponges	-	Skin equivalent	Co-cultures of keratinocytes, fibroblasts, and HUVEC (human)	-	(Black et al., 1998)
	Freeze-drying Solvent casting Ammonia treatment	Scaffolds Membranes	-	Liver	Hepatocytes (rats)	-	(Wang et al., 2005)
	Freeze-drying Cross-linking (EDC)	Scaffolds	-	Liver	Hepatocytes (rats)	-	(Yu et al., 2005b)
Chitosan-collagen-hyaluronan	Freeze-drying Cross-linking (EDC)	Scaffolds	-	Cartilage	Chondrocytes (rabbits)	-	(Yan et al., 2006)
Chitosan-collagen-PEO	Electro spinning Cross-linking (GA vapour)	Nanofibres membranes	-	Wound dressing	Fibroblasts-like cells	SD rats	(Chen et al., 2007a)
Chitosan-collagen-silicone	Freeze-drying Cross-linking (GA)	Bilayers (scaffold/membrane)	-	Dermal equivalent	Fibroblasts (human)	-	(Shi et al., 2005)
	Freeze-drying Cross-linking (GA)	Bilayers (scaffold/membrane)	-	Dermal equivalent	Fibroblasts (human)	Pigs	(Ma et al., 2007a)
Chitosan-gelatin	Freeze-drying Cross-linking (GA) Freeze-drying	Scaffolds	-	Artificial bilayer skin <i>in vitro</i>	Co-cultures of keratinocytes and fibroblasts	-	(Mao et al., 2003)
	Freeze-drying	Scaffolds	Plasmid DNA	Cartilage	Chondrocytes (rabbit)	-	(Guo et al., 2006)
Chitosan-gelatin	Solvent casting Cross-linking (EDC) Freeze-drying	Films	Dexamethasone	Cartilage	Cartilage	-	(Medrado et al., 2006b)
	Freeze-drying	Scaffolds	-	Cartilage	Autologous chondrocytes (pigs)	Pigs	(Xia et al., 2004)
	Freeze-gelation Solvent casting	Scaffolds Films	-	Cartilage Nerve regeneration	Chondrocytes (rabbit) Rat PC12 cells	-	(Wang et al., 2009a) (Cheng et al., 2003b)

Table 1. continued on next page

Table 1. Continued.

Composition	Processing Methodology	Matrix type	Active substance	Potential TE application	Cell type (source/line)	Animal model	Reference
	-	Gels	-	Liver	-	Rats	(Wang et al., 2007b)
	Freeze-drying, SFF Microreplication	Scaffolds	-	Liver	Hepatocytes (rats)	-	(Jiankang et al., 2007)
	Cross-linking (GA)						
	3D cell assembly technique	3D structures	-	Bioartificial liver	Hepatocytes (rats)	-	(Chen et al., 2005)
	Cross-linking (TPP and GA)						
hitosan-gelatin	Solvent casting	Membranes	-	Nerve repair	Fibroblast-like cells	-	(Chiono et al., 2008b)
	Cross-linking (G)				Neuroblastoma-like cells		
Chitosan-gelatin-hyaluronan	Freeze-drying	Scaffolds	-	Artificial skin	Co-cultures of keratinocytes and fibroblasts	-	(Liu et al., 2007b, Liu et al., 2004b)
	Cross-linking (EDC)						
Chitosan-heparin	Freeze-drying	Scaffolds	bFGF	Cartilage	Chondrocytes (rabbits)	-	(Tan et al., 2007)
	Cross-linking (EDC)						
	Solvent casting	Membranes	-	Wound healing	<i>In vitro</i> model	-	(Kratz et al., 1997a)
	-	Powder	-	Wound healing	-	Wistar rats	(Jin et al., 2007b)
	-	Powder ointment	-	Wound healing	-	Rats	(Kweon et al., 2003)
Chitosan-Hyaluronan	Solvent casting	Films	-	Wound dressing	Fibroblasts (human)	SD mice	(Xu et al., 2007)
	Wet spinning	Fibres	-	Cartilage	Chondrocytes (rabbits)	-	(Yamane et al., 2005)
	Wet spinning	Fiber scaffolds	-	Ligament	Fibroblasts (rabbits)	-	(Funakoshi et al., 2005a)
	Wet spinning	Fiber scaffolds	-	Ligament and tendons	Fibroblasts (rabbits)	Wistar-King rats	(Majima et al., 2007a)
Chitosan-galatosylated hyaluronan	Freeze-drying	Sponges	AgSD	Wound dressing	-	Wistar rats	(Lee et al., 2003b)
	Freeze-drying	Sponges	-	Bioartificial liver	Hepatocytes (wistar rats)	-	(Fan et al., 2010)
Chitosan-keratin	Solvent casting	Films	-	Wound dressing	Fibroblasts-like cells	-	(Tanabe et al., 2002a)
Chitosan-silkfibroin	Solvent casting	Membranes	-	Wound dressing	-	-	(Kweon et al., 2001a)
	Cross-linking (G)	Sponges	-	Cartilage	Chondrocytes-like cells	-	(Silva et al., 2008)
	Freeze-drying	Scaffolds	-	Liver	Hepatocytes	-	(She et al., 2009)
	Freeze-drying	Scaffolds	-	Liver	Hepatocytes (mice)	-	(She et al., 2010)
Chitosan-silk fibroin-heparin	Solvent casting	Membranes	-	Wound dressing	Fibroblasts-like cells	-	(Silva et al., 2005)
	Cross-linking (GA)						
Chitosan-soyprotein	Solvent casting	Membranes	-	Wound dressing	-	Sprague Dawley rats	(Santos et al., 2010b)
	Freeze-drying	Scaffolds	-	Cartilage	-	-	(Silva et al., 2006b)

AgSD: silver sulfadiazine; NGF: nerve growth factor; bFGF: basic fibroblast growth factor; CaCl₂: calcium chloride; EDC: (N-(3-dimethylaminopropyl)-N-ethylcarbodiimide; DHT: dehydrothermal treatment; GA: glutaraldehyde; PEO: polyethylene oxide; TPP: triethylphosphate; 3D structures: three dimensional structures; TE: Tissue Engineering; SFF: solid free form; W/O: Water-in-oil emulsion; O/W emulsion: Oil/water emulsion; G- genipin.

Table 2. Glycosaminoglycans-based matrices proposed for applications in soft tissue repair. Targeted tissues and organs include cartilage, skin, liver, nerve, and ligaments.

Composition	Processing methodology	Matrixtype	Activesubstance	Potential TE application	Cell type (source/line)	Animal model	Reference
Chondroitin- sulfate- collagen	Freeze-drying Cross-linking (EDC)	Scaffolds	-	Skin substitute	Co-cultures of keratinocytes and fibroblasts (human)	-	(Powell and Boyce, 2006)
	Freeze-drying Cross-linking (HT)	Scaffolds	TGF-01, PDGF-AB, EGF, or FGF-2*	Ligaments	Explants (human ACL)	-	(Murray et al., 2003)
	Freeze-drying Cross-linking (UV)	Scaffolds	-	Cartilage	Chondrocytes (dogs)	-	(Nehrer et al., 1997)
	Freeze-drying Cross-linking (HT)	Scaffolds	-	Cartilage	-	Dogs	(Nehrer et al., 1998)
	Freeze-drying Cross-linking (EDC, NHS)	Scaffolds	FGF-2, IGF-1	Cartilage	Chondrocytes (dogs)	-	(Veilleux and M. Spector, 2005)
Chondroitin- sulfate- collagen	Freeze-drying Cross-linking (EDC, HT, GA, UV)	Scaffolds	-	Cartilage	Chondrocytes (dogs)	-	(Lee et al., 2001)
	Freeze-drying Freeze-drying	Scaffolds Porous matrices	- -	Cartilage/ bone Nerve regeneration	MSCs -	- Rats	(Farrell et al., 2006) (Chamberlain et al., 1998) (Chamberlain et al., 2000)
Chondroitin- sulfate- collagen- chitosan	Freeze-drying	Scaffolds	-	Skin equivalent model	Keratinocytes Fibroblasts HUVEC	-	(Dambuyant et al., 2006)
Chondroitin- sulfate- collagen- heparin	Solvent casting Cross-linking (DAH)	Films	-	Liver	Hepatocytes (rats)	-	(Kataropoulou et al., 2005)
Chondroitin sulfate- gelatin- hyaluronan	Emulsion Freeze-drying Cross-linking (EDC)	Scaffolds containing microspheres	TGF-β1	Cartilage	Mesenchymal stem cells (rabbits)	Rabbits	(Fan et al., 2006a)
	Freeze-drying Cross-linking (EDC)	Scaffolds	-	Cartilage	Chondrocytes (porcine knee joints)	Pigs	(Chang et al., 2003a, Chang et al., 2006)
Chondroitin sulfate- gelatin- hyaluronan	Solvent casting Freeze drying cross-linking (EDC)	Porous- bilayered_ membrane	-	Skin	Keratinocytes Fibroblasts (human)	-	(Wang et al., 2006a, Wang et al., 2007a)
	Freeze drying cross-linking (EDC)	Bilayer scaffolds	-	Skin	Keratinocytes Fibroblasts (human)	Rats	(Wang et al., 2006b)
Chondroitin- hyaluronan- gelatin- PLGA	Low temperature- deposition Cross-linking (EDC)	Scaffolds	-	Cartilage	Mesenchymal stem cells	Rabbits	(Fan et al., 2006b)
Hyaluronan- chitosan	Freeze-drying	Sponges	AgSD	Wound dressing	-	Wistar rats	(Lee et al., 2003b)

Table 2. continued on next page

Table 2. Continued.

Composition	Processing methodology	Matrixtype	Activesubstance	Potential TE application	Cell type (source/line)	Animal model	Reference
Hyaluronan-chondroitin sulfate	Solvent casting Cross-linking (PEG, propiondi-aldehyde)	Films	-	Bio-interactive dressing	-	Mouse	(Kirker et al., 2002a)
	Freeze-drying cross-linking (EDC)	Porous matrices	-	Dermal tissue regeneration	Fibroblasts (human)	Guinea pig	(Park et al., 2003b)
	Freeze drying cross-linking (EDC)	Porous matrices	bFGF, PDGF-BB, tobramycin, ciprofloxacin	Skin substitute	Fibroblasts (human)	Male Dunking-Hartley guinea pigs	(Park et al., 2004b)
	Freeze-drying	Scaffolds	-	Cartilage	Chondrocytes(dogs)	-	(Tang et al., 2007a)
	Cross-linking (EDC)	Composite matrices	-	Cartilage	-	-	(Taguchi et al., 2002b)
	Cross-linking (EDC)	Membranes	-	Dermal substitutes	-	Wistar rats and IPR mice	(Koller et al., 2000b; Koller et al., 2001b)
	Solvent casting	Sponges	VEGF Fibronectin	Dermal substitutes	Fibroblasts	Sprague-Dawley rats	(Kubo and Kuroyanagi, 2003a; Kubo and Kuroyanagi, 2003b; Kubo and Kuroyanagi, 2004)
	Cross-linking (Ethylene glycol ^{10*})						(Harvanova et al., 2009)
	Freeze-drying	Sponge/membrane	-	Cartilage	-	Chondrocytes (rabbit)	(Choi et al., 1999a)
	Freeze-drying	Sponges	AgSD	Wound dressing	-	Wistar rats	(Choi et al., 1999a)
	Cross-linking (EDC)	Sponges	EGF/AgSD	Wound dressing	-	Wistar rats	Hong et al., 2001)
	Freeze drying	Sponges	-	Cartilage/bone	-	-	(Angele et al., 1999)
	Cross-linking (EDC)	Scaffolds	TGF- β 1	Artificial dermis	-	-	(Lee et al., 2003a)
	Salt leaching	Scaffolds	-	Cartilage	Bone marrow (rabbit)	-	
	Freeze-drying	Scaffolds	-	Artificial dermis	-	-	
	Cross-linking (EDC)	Scaffolds	TGF- β 1	Cartilage	Chondrocytes (porcine knee joints)	-	(Chou et al., 2006)
	Freeze-drying cross-linking (EDC)	Scaffolds	-	Wound dressings	Fibroblast-like cells	-	(Dawlee et al., 2005)
	Periodate oxidation	Hydrogels	-	Wound dressings	-	-	

AgSD: silver sulfadiazine; HUVEC: human umbilical vein endothelial cells; Hep-2: human larynx carcinoma cells; PLGA: poly-(lactic-co-glycolic acid); TGF- β 1: transforming growth factor- β 1; VEGF: vascular endothelial growth factor; HMDIC: hexamethylenediisocyanate; EDC: 1-Ethyl-3-[3-dimethylaminopropyl]carbodiimide; SF6: solid free-form fabrication method; HT: hydrothermal treatment. TGF- β 1, PDGF-AB, EGF, or FGF-2*: The culture medium was supplemented with these growth factors; human ACL- human anterior cruciate ligament; MSCs: mesenchymal stem cells; DAH: 1,6-diaminohexane; Ethylene glycol*: Ethylene glycol diglycidylether; NHS: N-hydroxysuccinimide.; UV - ultraviolet.; FGF-2: fibroblast growth factor; IGF-1: insulin-like growth factor; PEG: poly(ethylene glycol).

Table 4. Cellulose-based matrices proposed for application in soft tissue repair.

Composition	Processing methodology	Matrixtype	Active substance	Potential TE application	Cell type (source/line)	Animal model	Reference
Cellulose-silk fibroin	Wet spinning	Fibers	–	Wound dressing	–	–	(Strobin et al., 2006)
ORC-collagen	Freeze-drying	Scaffolds	–	Clinical settings in wound repair	Fibroblasts (human)	Diabetic mouse	(Hart et al., 2002)
	Cross-linking (dehydrothermal)		–	Clinical setting in acute wounds			
	Freeze-drying	Scaffolds	PDGF	Chronic wounds	–	–	(Cullen et al., 2002b)

ORC: oxidised regenerated cellulose; GA: glutaraldehyde; PDGF: platelet-derived growth factor.

selected negatively charged molecules (e.g. proteins, anionic polysaccharides, and nucleic acids) in the design of different polymeric matrices for tissue engineering applications (Liu et al., 2007b; Hamman, 2010; Yu et al., 2005). The chitosan-based complexes have an excellent ability to be processed into sponges and bilayer scaffolds for use as dermal equivalents, especially with collagen or alginate, (Ma et al., 2003; Ma et al., 2007) and also for skin regeneration. With regard to collagen/chitosan complexes, the presence of collagen resulted in the improvement of the cell compatibility of these matrices, where the additional use of cross-linking agents increased the biostability of the chitosan/collagen (CC) composite scaffolds (Ma et al., 2003). Interestingly studies have suggested that the polyelectrolyte complex (PEC) between alginate and chitosan should be mechanically stronger at a lower pH where chitosan dissolves (Hamman, 2010). Chitosan also interacts with gelatin to provide thermosensitive hydrogels for the controlled release of proteins (Chang et al., 2009) or in microspheres loaded with basic fibroblast growth factor (bFGF) to increase the production of laminin by human fibroblasts, which may be helpful for angiogenesis in skin regeneration (Liu et al., 2007a). Some examples of PEC systems formed by chitosan-alginate or chitosan-heparin, and others are shown in Table 1. Many papers have been concerned with chitosan/heparin complexes as nanoparticles (Liu et al., 2007b), and multilayer thin films (Lundin et al., 2010). Considering that heparin is well-known for its anti-coagulant activity and for having a high negative charge density due to its carboxyl and sulfonate groups (Salmivirta et al., 1996), the resulting matrices may have potential therapeutic uses for enhanced tissue regeneration. Some researchers (Kratz et al., 1997; Kweon et al., 2003; Jin et al., 2007) have suggested that the heparin-chitosan complex stimulates re-epithelialization of a full-thickness wound in human skin, in a heparin dose dependent effect (Kratz et al., 1997). Recent investigations have focused on the interactions between chitosan and other proteins, besides gelatin, as pathways to investigate matrices with suitable mechanical properties, biodegradability, and good biocompatibility for skin applications (Kweon et al., 2001;

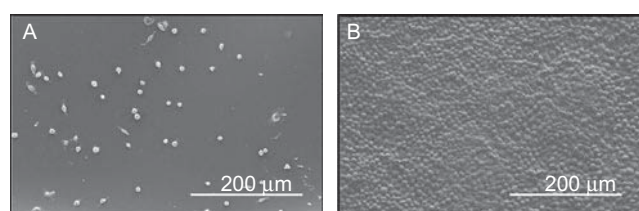


Figure 2. SEM micrographs of L929 cells cultured on chitosan membrane (a) and chitosan/soy protein blended membrane cross-linked with 0.1 M Ga (b). Culture time: 3 days. (Unpublished results).

Silva et al., 2005; Tanabe et al., 2002). In our group, Silva and co-workers (Silva et al., 2005; Silva et al., 2007b) have explored the blending of chitosan with soy protein isolate, the major component of the soybean (Vaz et al., 2002), in the development of a series of blended membranes. The chitosan/soy protein (CSS) blended systems are not completely miscible and *in situ* chemical cross-linking with glutaraldehyde solutions has been used to enhance the degree of interaction between chitosan and the soy protein, and thus overcome the drawback of its immiscibility. As a consequence, the fibroblast-like cell attachment on cross-linked CSS membranes was found to be enhanced in comparison with chitosan membranes (Figure 2). Subsequent *in vivo* studies (Santos et al., 2010) demonstrated that the CSS membranes accelerated skin wound healing in rats after two weeks of dressing. All these findings support the suitability of CSS membranes as wound dressing materials.

Chitosan seems to be a good candidate particularly for cartilage tissue engineering applications, in that its structure and characteristics resemble those of glycosaminoglycans (GAGs), which are well known constituents of the cartilage extracellular matrix, and it also has a critical role in supporting chondrogenesis both *in vitro* and *in vivo* (Suh and Matthew, 2000). Even considering these characteristics, the development of an ideal chitosan scaffold for cartilage TE remains a challenging task. The most well known method to prepare chitosan scaffolds is freezing and then lyophilizing chitosan solutions in appropriate molds (Suh and Matthew, 2000; Oliveira et al., 2006; Silva et al., 2006; Madhally and Matthew,

1999) and several other methods such as melt processing (Correlo et al., 2007b; Correlo et al., 2009), sol-gel technique (Silva et al., 2006), and electrospinning (Lee et al., 2009) have all been used to produce chitosan scaffolds with different geometries and porosities, interconnectivity and so on. Promising results have also been obtained by associating chitosan with other biomacromolecules or bioactive agents in order to promote cartilage regeneration (Silva et al., 2008; Medrado et al., 2006; Lee et al., 2004). In addition, multi-component chitosan scaffolds, whose composition mimics the natural cartilage matrix, have been proposed to facilitate the formation of articular cartilaginous both *in vitro* and *in vivo* (Yan et al., 2007). It has also been reported that porous collagen/chitosan/GAG loaded with transforming growth factor- β 1 (TGF- β 1) provided the controlled release of TGF- β 1 and promoted cartilage regeneration (Lee et al., 2004). Although the combination of chitosan with biomacromolecules, as well as technologies used in the creation of chitosan scaffolds have demonstrated some successful findings, other approaches using chitosan hydrogels/gels as injectable scaffolds for cartilage repair have also been widely studied (Hao et al., 2010; Nettles et al., 2002; Tan et al., 2009). For instance, some strategies involved the reconstruction of the tissue-engineered cartilage *in vitro* using injectable temperature-responsive hydrogel chitosan (Hao et al., 2010), while others have demonstrated that chitosan composite hydrogel matrices supported cell survival retaining the chondrocytic morphology (Tan et al., 2009).

Apart from the promising findings of chitosan-based matrices for skin and cartilage regeneration, their applications and benefits have also been expanded to liver regeneration. The role of a hepatocyte-specific 3D scaffold involved the creation of a microenvironment that mimicked the organized architecture of the native liver. Bearing this in mind, researchers suggested that collagen/chitosan (CC) matrices (Wang et al., 2003) can create an appropriate environment for the regeneration of liver cells. Nevertheless, the low mechanical strength and poor blood compatibility of these natural polymers have limited their further use in liver TE. Other researchers (Tai et al., 2010) have proposed the delivery of liver-differentiated human mesenchymal stem cells (hMSCs) from RGD-modified chitosan-alginate fibrous scaffolds as a potential therapy to aid in liver regeneration. In view of the complexity of the liver, some approaches have focused on the design of complex 3D architectures with predefined internal vascular channels to favor angiogenesis (Jiankang et al., 2007; Yan et al., 2005; He et al., 2009). Following these strategies, chitosan/gelatin scaffolds with well organized architectures and highly porous structures have been fabricated and combining rapid prototyping, microreplication, and freeze drying techniques. With respect to nerve regeneration, various studies have focused on nerve guidance conduits made

from polyelectrolyte complexes between chitosan and alginate (Pfister et al., 2008) as well as the associations of chitosan with proteins (collagen, albumin, and gelatine) or poly-L-lysine (Cheng et al., 2003a; Cheng et al., 2003b) as promising alternatives to the conventional treatments. More details about these systems are shown in Table 1. Furthermore, applications of chitosan-based blended systems to tendon and ligament TE have been recently reported (Majima et al., 2007; Funakoshi et al., 2005).

Glycosaminoglycans (hyaluronic acid and chondroitin-sulfate)

Glycosaminoglycans (GAGs), including hyaluronan (HA) and chondroitin sulfate (CS), are amino sugar containing polysaccharides that are present in the extracellular matrix (ECM) of all vertebrates (Kirker et al., 2002). Hyaluronic acid or hyaluronan (HA) is a linear polysaccharide with a repeating disaccharide structure composed of glucuronic acid and N-acetyl glucosamine residues (Kogan et al., 2007). This water soluble polysaccharide is widely distributed throughout the ECM of all connective tissues in humans and other animals (Kogan et al., 2007) and has various important biological functions. Based on its positive biological effects on cell behavior *in vitro*, HA have participated in many polymeric systems for different TE applications, as listed in Table 2. There have been several studies involving HA alone or mixed with collagen and gelatin for skin applications (see Table 2). In some cases, the collagen/HA mixture was cross-linked to stabilize the materials, and then their performance was improved (Tang et al., 2007; Taguchi et al., 2002; Koller et al., 2000; Koller et al., 2001; Bakos and Koniarova, 1999; Kubo and Kuroyanagi, 2003; Park et al., 2003). Park et al. (2003) showed that dermis treated with EDC-cross linked-collagen-HA matrix was thicker than the control (porous polyurethane matrix), and that epithelial regeneration was accelerated *in vivo*. The presence of growth factors into collagen-hyaluronan matrices significantly enhanced wound healing (Park et al., 2004). As commented previously, the matrices from combinations of HA and collagen have been actively developed for wound repair. However, these and other HA-based combinations have been suggested for both cartilage and neural repair (see examples in Table 2).

Chondroitin sulfate is quite water soluble, and for this reason it has been frequently combined with other polymers (see examples listed in Table 2). In fact, its anionic nature enables efficient interaction with cationic molecules to form interesting structures for soft tissue repair. For skin regeneration, Yannas and Burke (Yannas and Burke, 1980; Burke et al., 1981) developed a bilayer artificial skin from the association of chondroitin sulfate with collagen, which is known as Integra[®] (Integra Life Sciences Holding, New Jersey). Similarly, bi-layered gelatin-chondroitin sulfate-HA constructs with different pore

sizes on either side were prepared to mimic the composition of skin and to create an appropriate microenvironment for cell growth, differentiation, and migration (Wang et al., 2006). As a component of cartilage ECM, chondroitin sulfate has a stimulatory potential on both cell-proliferation and matrix retention, in turn this polymer has been used as an interesting component in the production of multi-component scaffolds for use in cartilage TE. For instance, chondrocytes seeded on gelatin/chondroitin sulfate/hyaluronan scaffolds were evenly distributed in matrices, secreted new ECM, retained their phenotype, and secreted type II collagen (Chang et al., 2003a). Moreover, TGF- β 1 was immobilized onto the surface of gelatin/hyaluronic acid/chondroitin-6-sulfate (GHCS) to suppress any undesired differentiation during cartilage growth *in vitro* (Chou et al., 2006). As proposed by Murray et al. (Murray et al., 2003), the addition of selected growth factors to medium for an implantable collagen-glycosaminoglycan (CGG) scaffold may enhance ligament cell behavior within the CG scaffold.

Alginate

Alginate is a polymer derived from sea algae, formed by linear block copolymers of 1-4 linked β -D-mannuronic acid and L-guluronic acid. It is water soluble at room temperature and in the presence of certain divalent cations, such as calcium, barium, and strontium; it forms stable hydrogels that have been explored for a broad range of biomedical applications (Gomes et al., 2008; Eiselt et al., 2000; Hunt and Grover, 2010). One of the drawbacks of alginate hydrogels can be that degradation occurs via a slow and unpredictable dissolution process *in vivo* (Boontheekul et al., 2005; Bouhadir et al., 2001). Alginate has been used as a wound dressing (Qin, 2008; Suzuki et al., 1998; Chiu et al., 2008), delivery vehicles for drugs (Hunt et al., 2009), and cell encapsulation (Hunt and Grover, 2010). Furthermore, combinations of alginate with another polysaccharide have led to the formation of biopolymeric matrices for soft tissue repair (see Table 3). Most of these have been based on the addition of one or two components of ECM to alginate in order to create composites that mimic the properties of natural tissues and then to enhance the functionality of the engineered materials. For instance, a commercial collagen-alginate topical wound dressing (FIBRACOL PLUS Dressing, Johnson & Johnson Gateway[®]) has demonstrated its efficacy and safety in the treatment of diabetic foot ulcers (Donaghue et al., 1998). Although these strategies are of interest for TE, the inclusion of other biomacromolecules such as silk fibroin to alginate could also contribute useful properties for wound treatment (Roh et al., 2006). In cartilage studies (Gerard et al., 2005), beads composed of alginate-hyaluronan that combine the gel forming ability of alginate with the healing properties of hyaluronan have been proposed. However, studies involving alginate-based

systems have also been expanded towards liver regeneration, where conjugations of alginate with galactosylated chitosan (Seo et al., 2006b), and also with heparin (Seo et al., 2006a) have been suggested to enhance their liver specific function for the design of bioartificial liver devices.

Cellulose

Cellulose is the most abundant organic polymer in the world. It is insoluble in most solvents due to its strong intra or intermolecular hydrogen bonding (Klemm et al., 2005). Despite this, it is still used in the mass production of conventional dressing materials (Boateng et al., 2008). Cellulose derivatives can be associated with proteins (e.g. silk fibroin, collagen) with the formation of sponges for cartilage tissue engineering (Pulkkinen et al., 2006), and as scaffolds in clinical settings for wound repair (Hart et al., 2002; Jeschke et al., 2005; Cullen et al., 2002) (see Table 4). Oxidized regenerated cellulose and its blends have been applied as a wound dressing, this is because oxidized cellulose has proved to be an effective hemostat and also has antibacterial activity (Martina et al., 2009). For instance, in the presence of chronic wound exudates, ORC/collagen forms a soft, conformable, and biodegradable gel that physically binds and inactivates the matrix metalloproteases (MMPs), stabilizing their levels and contributing to a positive effect on the wound healing process, since a high level of MMPs in chronic wounds may lead to the degradation of important proteins and inactivate growth factors (Hart et al., 2002; Cullen et al., 2002). Promogran[®] is an example of a spongy matrix containing oxidized regenerated cellulose (45% ORC) and collagen (55%), which has been introduced to both the USA and EU markets. Recently, room temperature ionic liquids have been proposed as possible new solvents for the derivatization of cellulose, opening new paths for the shaping of cellulose through its precipitation with an excess of polar solvents like water, acetone or a combination of these (Pinkert et al., 2009). Also, cellulose composites in different shapes (films, beads, scaffolds) can be obtained by changing the composition, the precipitation method and conditions, which have a potential use in tissue engineering. Cellulose can also be produced by *Gluconacetobacter xylinus* (*Acetobacter xylinum*) (Klemm et al., 2005; Svensson et al., 2005; Czaja et al., 2007). Although identical to the cellulose of plant origin in terms of molecular formula, bacterial cellulose is characterized by a crystalline nano and microfibril structure that determines its extraordinary physical and mechanical properties (Czaja et al., 2007; Klemm et al., 2005). Bacterial cellulose or microbial cellulose has unique properties, including high purity, high crystallinity, moldability *in situ*, biocompatibility, and high water holding ability. In addition to its cost efficient production, it has high mechanical strength in the wet state (Czaja et al., 2007; Svensson et al., 2005).

Due to its versatility, bacterial cellulose has been studied as a wound dressing, for tubular implants, and as scaffolds for cartilage repair, among other applications (Czaja et al., 2007; Svensson et al., 2005; Klemm et al., 2005). Bacterial cellulose/chitosan wound dressings have good antibacterial and barrier properties; they also have mechanical properties in the wet state and optimal moisture conditions for rapid wound healing without irritation (Ciechanska, 2004). In cartilage studies (Svensson et al., 2005), bacterial cellulose has been shown to be a potential scaffold for cartilage TE since the chondrocytes maintained their differentiated form and the scaffold supported cell ingrowth.

Consideration of polysaccharide and protein interactions

In biological systems, proteins and polysaccharides have an important role in the organization of living cells, and the interactions between these polymers of natural origin leads to the formation of macromolecular structures through association. Basic information related to the phase behavior and the interactions between polysaccharides and proteins have been obtained during the last three decades, mainly in the field of food science (McClements, 2006; Turgeon et al., 2003; Ya and Tolstoguzov, 1997; Tolstoguzov, 2000; Doublier et al., 2000; Kruif and Tuinier, 2001). Mixed systems of globular proteins and polysaccharides have been widely used to control the structure, texture, and stability of food products (Musampa et al., 2007; Berthand and Turgeon, 2007), whereas polymer based systems of natural origin can also be used for biomedical applications. Different examples of the biomedical applications of these systems are shown in Tables 1 to 4. Besides the low cost and versatility of this strategy, the introduction of proteins into matrix materials may improve its cell behavior because they are able to interact favorably with cells through specific recognition domains present in their structure. Also, the interaction between natural polymers with different chemical structures through hydrogen bonding or electrostatic interactions in nature may reinforce the mechanical properties of the materials obtained from such mixtures. Nevertheless, most polymer blends are immiscible or only partially miscible. Depending on the polymer characteristics (molecular weight, polysaccharide/protein ratio, conformation, and charge density), and on the solution conditions (pH, ionic strength, total concentration, solvent quality, etc.), the association of biomacromolecules may result in the formation of a complex or a phase separation (Turgeon et al., 2003). When polysaccharides and proteins attract each other through electrostatic interactions, the polymers associate excluding the solvent from their vicinity (complex coacervation), thus allowing the formation of soluble complexes or an aggregative phase separation (precipitate) (Doublier

et al., 2000; de Kruif et al., 2004). Sometimes the complex coacervates are highly unstable and a structural stabilization by chemical agents can become necessary (Sanchez and Renard, 2002). The formation of complexes and coacervates induced by electrostatic interactions is a fundamental physico-chemical phenomenon, which is relevant to a number of known biological processes such as protein transcription and antigen-antibody reactions (Turgeon et al., 2003). Additionally, protein-polysaccharide complexes are important in the design of multi-layered structures (Noel et al., 2007), encapsulation processes (Xing et al., 2005), and the formation and stabilization of food emulsions (Dickinson, 2006). On the other hand, the phase separation can occur due to a strong repulsion between the polymers caused by similar electrical charges or because one or both polymers are uncharged (McClements, 2006; Doublier et al., 2000). At low concentrations, the polymers can be intimately mixed and form a one phase solution. However, when the total concentration of the system increases, exceeding a certain critical value of about 4% for globular proteins and polysaccharide mixtures (Musampa et al., 2007), a phase separation occurs. As a result, the system exhibits one phase that is rich in protein and the other is rich in polysaccharide (Doublier et al., 2000; McClements, 2006). Miscibility in a polymer blend is associated with specific interactions between the polymeric components. The major forces responsible for the polymer interactions are electrostatic in nature but other common interactions such as hydrogen bonding or hydrophobic interactions may be significant in the stabilization of the interactions (McClements, 2006; Feldman, 2005). Several authors (Taravel and Domard, 1995; Yin et al., 2005; Yin et al., 1999; Silva et al., 2007b; Berthand and Turgeon, 2007; Malay et al., 2007; Palmiere et al., 1999; Naidu et al., 2005; Sionkowska et al., 2004) have studied the interactions between polymers of natural origin regarding their promising applications in food formulation, biotechnological, and biomedical areas. For example, studies performed by Taravel and Domard (Taravel and Domard, 1993; Taravel and Domard, 1995) and Sionskowska et al. (2004) suggested that chitosan/collagen blends are miscible and that the interactions between them are electrostatic in nature with the formation of low complexes. These matrices have been proposed as films for dermal regeneration templates (Gao et al., 2003), as wound dressings (Guan et al., 2007), and as scaffolds for liver TE (Wang et al., 2003). Malay et al. (Malay et al., 2007) investigated the formation of pH-induced complexation of silk fibroin and hyaluronic acid, while Naidu et al. (Naidu et al., 2005) evaluated the compatibility of sodium alginate/hydroxyethylcellulose blends both in solution and as solid films. One study (Christopoulou et al., 2000) indicated that the compatibility between the polymers in solution would remain, even when the solvent is absent ("memory effect"). Besides the miscibility, the nature and strength

of interactions involved between polymer based systems of natural origin can be studied using a wide variety of analytical techniques. For example, in polymer blend solutions, the existence of the thermodynamic interaction (attraction or repulsion) between polymers induces a non-ideal mixing, resulting in changes of viscosity. Therefore, viscosimetry is an effective, quick, and inexpensive method to determine the miscibility of polymers (Naidu et al., 2005). Also, the compatibility of a blend system can be studied by its glass transition temperature (T_g), which is usually determined by differential scanning calorimetry (DSC). An immiscible blend usually exhibits the T_g s of the components, while miscible polymers involve thermodynamic solubility and should have one phase and only a single T_g . On the other hand, the type of morphology in a blend system is dependent on the nature and amount of the polymers in the mixture, viscosity, and also on their miscibility (Malay et al., 2007; Koning et al., 1998). Heterogeneous blends can appear as a dispersion of one polymer in the matrix of the other polymer, with the formation of co-continuous morphology.

Strategies for compatibilization and surface modification on polymeric blends

Compatibilizers and chemical cross-linking treatments

As most polymeric blends are immiscible, compatibilization could be required. The compatibilization of polymer blends is possible by adding to the system non reactive or reactive compatibilizers (Feldman, 2005; Koning et al., 1998). Reactive compatibilizers chemically react with the blend components, while non-reactive compatibilizers are block and graft copolymers, having chain segments that are identical or similar to the components to be mixed (Feldman, 2005; Koning et al., 1998). Graft copolymers work as emulsifiers reducing the interfacial tension of blends. This leads to a phase size small enough for the material to be considered as macroscopically homogeneous and consequently improving the mechanical properties of the system (Feldman, 2005). Besides the usual compatibilizers, cross-linking methods have been used to improve the structural stability and mechanical properties of binary systems. A particular cross-linker should be chosen based on its chemical reactivity, solubility, spacer length, and compatibility of the reaction with the application. Glutaraldehyde (GA), formaldehyde, 1-ethyl-3-(3-dimethylaminopropyl)-carbodiimide (EDC), polyepoxide, and polyglycidyl ether are commonly used as cross-linking agents (Hennink and van Nostrum, 2002; Silva et al., 2005; Park et al., 2003; Park et al., 2002; Harriger et al., 1997; Silva et al., 2004; Sung et al., 1996). Of these, glutaraldehyde and EDC are the most widely used for polymeric systems due to their high cross-linking efficiency. However, depending on the concentration used, extracts from the cross-linked materials can be released into the tissue, resulting in cytotoxicity

and inflammation. In contrast to glutaraldehyde, water-soluble carbodiimide (EDC) does not remain as a part of the linkage but simply changes into water-soluble urea derivatives with low cytotoxicity. Park et al. (Park et al., 2002) reported that a collagen/HA matrix cross-linked with EDC had good resistance to enzymatic degradation with acceptable toxicity. Genipin has been considered as a natural cross-linking agent with a lower cytotoxicity when compared to the alternative cross-linkers like glutaraldehyde (Sung et al., 1998). Genipin is obtained from its parent compound geniposide, which is extracted from the fruits of *Gardenia jasminoides Ellis* (Koo et al., 2004). Genipin has been used to cross-link gelatin (Chang et al., 2003b; Liu et al., 2004), collagen (Sundararaghavan et al., 2008), kappa-carrageenan (Meena et al., 2007), chitosan (Mi et al., 2002a; Kuo and Lin, 2006; Chen et al., 2005; Muzzarelli, 2009), alginate/chitosan (Chen et al., 2006), chitosan/gelatin blends (Chiono et al., 2008), and the chitosan/silk fibroin system (Silva et al., 2008). One interesting characteristic of the reaction of genipin with amino acids lies in the formation of dark blue pigments, which are the result of oxygen radical induced polymerization of genipin (Sung et al., 1998). These blue pigments are used as a natural colorant in foods (Park, 2002), and can also aid in following the evolution of genipin cross-linking reactions (Chen et al., 2005). Typically, matrices cross-linked with genipin present good mechanical properties, reduced swelling, a slower degradation rate, and good biocompatibility (Chang et al., 2003b; Mi et al., 2002a). Proanthocyanidins (PAs) have also been indicated as non-toxic cross-linkers (Han et al., 2003). PAs are widespread in fruits and vegetables, and belong to the category known as condensed tannins, which consist of highly hydroxylated structures capable of forming insoluble complexes with carbohydrates and proteins (Han et al., 2003). Studies have indicated that PAs are less cytotoxic than glutaraldehyde, could efficiently cross-link collagen matrices (Han et al., 2003), and chitosan/gelatin membranes (Kim et al., 2005). Kim et al. (Kim et al., 2005) reported that proanthocyanidin cross-linked chitosan/gelatin membranes have good mechanical properties, thermal properties, and a slower degradation rate *in vivo* with no inflammatory reaction found in all the implants that were tested when compared to uncross-linked gelatin films and chitosan/gelatin membranes.

Surface modification

A biomaterial with good bulk properties does not necessarily possess the surface characteristics suitable for a given biomedical application. Therefore, modification of the biomaterial surface is often needed (Oehr, 2003; Chu et al., 2002). Various methods have been employed for modifying polymer surfaces including chemical modification (Pashkuleva et al., 2005; Tangpasuthadol et al., 2003), ultra-violet (UV) (Olbrich et al., 2007; Welle et al., 2005; Gumpenberger et al., 2003), gamma irradiation (Yang

et al., 2002; Mao et al., 2004), and plasma surface modification (Oehr, 2003; Pashkuleva et al., 2005; Silva et al., 2007c; Zhu et al., 2005; Pashkuleva and Reis, 2005; Huang et al., 2007; Lopez-Perez et al., 2007; Ratner, 1995). For instance, these modifications will determine the possible interactions of polymers with bioactive agents, namely drugs, growth factors as well as the possibility of allowing for their clinical use in the regeneration of hard/soft tissues (Pashkuleva and Reis, 2005; Goddard and Hotchkiss, 2007; Ratner, 1995). Depending of the chosen method and conditions, a surface can be modified to become hydrophilic or hydrophobic, be functionalized or only be activated for further reactions (Pashkuleva and Reis, 2005; Goddard and Hotchkiss, 2007). Chemical etching with a potassium permanganate-nitric acid system has been shown to enhance the surface energy and wettability of starch based blends (Pashkuleva et al., 2005). UV irradiation has been used to create patterned polystyrene substrates for tissue engineering applications, especially in neuroscience (Welle et al., 2005). Plasma surface modification is a method widely used to tailor surface functionality using different atmospheres (Chu et al., 2002; Pashkuleva and Reis, 2005). Usually, plasma treatment only affects the outermost layers (2.5–10 nm) of the material's surface, while the bulk properties of the polymer remain intact (Oehr, 2003). When a material is exposed to a partially ionized gas, its surface is bombarded with ions, electrons, and radicals from the plasma. This process results in the formation of radicals on the polymer surface. The highly reactive species so formed combine with the radicals from the working gas to modify the surface (Chu et al., 2002). Depending on the interaction between the plasma and the polymer, and on the operating conditions (gas, power, and exposure time), the reactions of modification and degradation can occur (Chu et al., 2002; Oehr, 2003; Khonsari et al., 2003). When degradation is prominent, etching will take place on the polymer surface. An etching reaction occurs when the polymers are exposed to plasma for a long period, and the exposed layers of the polymers are etched off (Chu et al., 2002). As a result, etching produces nano-roughness on the polymer surface, which can create the desirable features on biomaterials to meet the requirements of biocompatibility *in vivo* (Chu et al., 2002). Figure 3 shows that the prolonged exposure time on chitosan/soy protein membranes to argon plasma (Figure 3B and 3C) promoted an increase of the surface roughness when compared to the initial surface membrane (Figure 3A). On the other hand, plasma can also be used to create functionalized surfaces with direct binding of new chemical groups or their inclusion after surface activation by plasma treatment (Chu et al., 2002; Lopez-Perez et al., 2007). For example, oxygen (-OH, -C=O, -COOH groups) or nitrogen (-NO₂, -NH₂, -CONH₂ groups) plasma have been used to increase the material hydrophilicity (Inagaki, 1996). As a result,

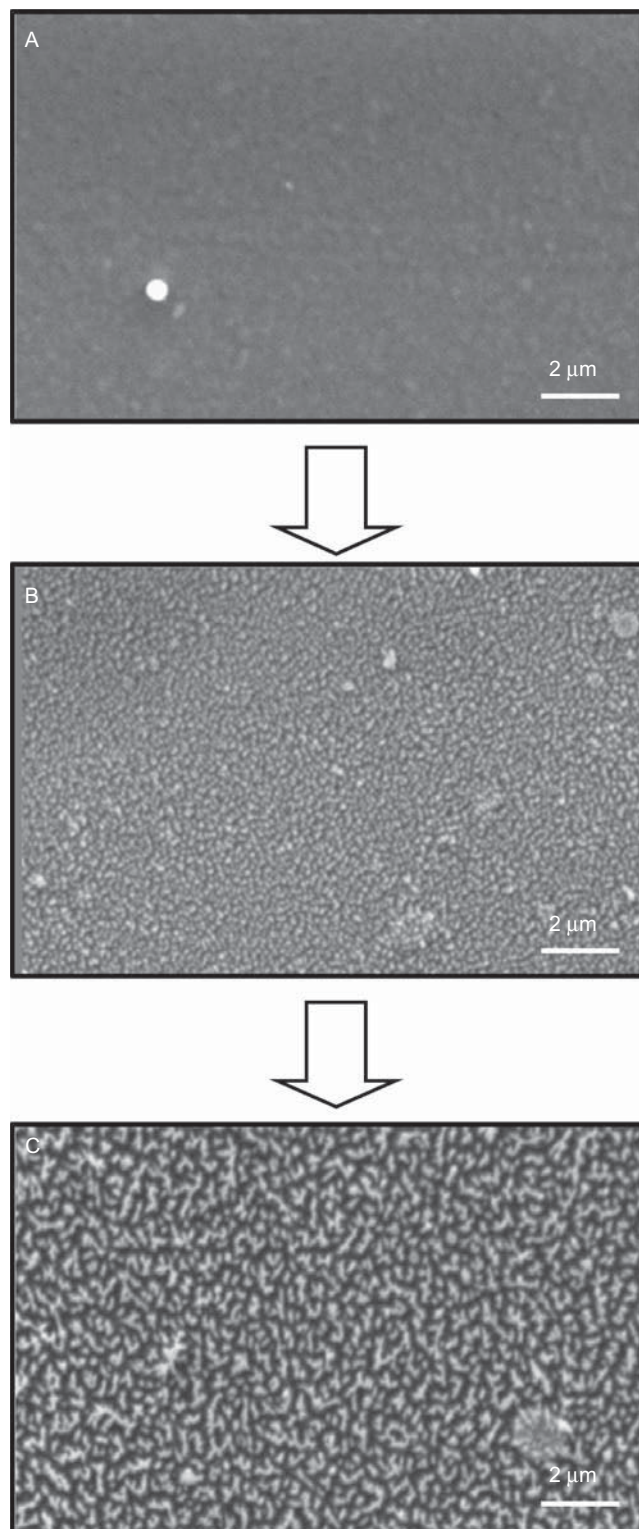


Figure 3. SEM micrographs showing the effect of the prolonged time exposure to argon plasma on surface of chitosan-soy protein (CSS) based membranes; (a) CSS membrane without treatment, (b) CSS after argon plasma (40 watts, 5 minutes) and (c) CSS after argon plasma (40 watts, 20 minutes). (Unpublished results)

improved adhesion strength, biocompatibility, and other relevant properties were observed (Inagaki, 1996; Chu et al., 2002). Similar results were obtained in our group by Silva et al. (Silva et al., 2007c) who investigated the surface modification of chitosan membranes using nitrogen and argon plasma to improve its fibroblast cell adhesion *in vitro*. The proposed modifications would facilitate the use of chitosan-based materials as wound dressings. In addition, plasma grafting polymerization can be used to modify inert surfaces. This includes activation of the surface by plasma followed by polymerization reactions, resulting from the contact between the activated surface with monomers in the liquid or gas phase (Chu et al., 2002; Pashkuleva and Reis, 2005; Lopez-Perez et al., 2007; Forch et al., 2005). Therefore, grafted copolymers are formed onto the surface. Using such procedures, smart surfaces may be produced, where the wettability can be responsive to the change of external variables, being useful for some biomedical applications (Ando et al., 2007; da Silva et al., 2007). Recently, Huang et al. (Huang et al., 2007) suggested that oxygen plasma is a better method to incorporate laminin onto the surface of chitosan membrane, resulting in a significant increase of the attachment of Schwann cells and to help the affinity for directing peripheral nerve regeneration.

Final remarks

Several polymers based on natural origins, either alone or in binary or ternary blend systems, are proposed for use in soft tissue repair. Among the various tissues that these systems can target, skin, and cartilage are probably the most prominent. The features of a particular blended system, in general, must be modulated and designed in an appropriate shape for a determined biomedical application. Most of the polymer combinations have been used as a means to overcome problems observed in simple systems with regard to the mechanical strength of the scaffolds, proliferation ability, and implantation difficulties. Although some successful findings have been reported, these systems still need some improvement in terms of structural stability due to water-solubility for some polysaccharides, which have been solved through their complexation or cross-linking reactions. In addition, the construction of adequate surface properties is also important for the tissue/cell interface, making it necessary to apply surface modification on the polymer matrix. With regard to tissue targets, interesting strategies have been proposed such as co-cultures of keratinocytes and fibroblasts on bilayer constructs (scaffold/membrane) as dermal equivalents, as well as the development of multi-component scaffolds with living cells for cartilage repair have shown promise. In some cases, a sustained release of a bioactive substance (drugs or growth factors) incorporated into these biomatrices enhanced the cell response, and thus tissue

regeneration. Moreover, advanced processing techniques such as a solid-free form have been proposed to produce porous matrices with complex geometric shapes and suitable porosities tailored to the tissue target, for example in the design of bioartificial livers. Although the approaches described have demonstrated promising results both *in vitro* and *in vivo*, there are still many challenging issues to be addressed in order to obtain clinically successful materials as well as to create novel therapeutic approaches. Bearing this in mind, extensive research must be done to develop materials interacting with cells on healing tissue and other host processes. Also, further study is needed to understand the *in vivo* interactions among biomaterials, cells and growth factors at the molecular level. Current trends also suggest that the intensification of the development of hydrogel materials from blended systems with thermosensitive materials can be a powerful tool for the production of multifunctional materials that can provide complex biological signals and respond to environmental stimuli. For all these purposes, it is essential to have collaborative research between material researchers, biologists, and clinicians which could lead to advanced materials that fulfill all the needs of polymer combinations for soft tissue regeneration.

Acknowledgements

The authors wish to thank J. Benesch, I. Paskuleva, J. Grech, and J.M. Oliveira for their useful discussions.

Declaration of interest

S.S. Silva would like to acknowledge the Portuguese Foundation for Science and Technology (FCT) for a post doctoral fellowship (SFRH/BD/45307/2008). This work was partially supported by the European-Union-funded FP7 Project: Find and Bind (NMP4-SL-2009-229292) and STREP project HIPPOCRATES (NMP3-CT-2003-505758) and was carried out under the scope of the European NoE EXPERTISSUES (NMP3-CT-2004-500283).

References

- Agarwal S, Wendorff JH, Greiner A. (2009). Progress in the field of electrospinning for tissue engineering applications. *Adv Mater*, 21, 3343-3351.
- Aigner J, Tegeler J, Hutzler P, Campoccia D, Paveio A, Hammer C, Kastenbauer E, Naumann A. (1998). Cartilage tissue engineering with novel nonwoven structured biomaterial based on hyaluronic acid benzyl ester. *J Biomed Mater Res*, 42, 172-181.
- Altman GH, Diaz F, Jakuba C, Calabro T, Horan RL, Chen JS, Lu H, Richmond J, Kaplan DL. (2003). Silk-based biomaterials. *Biomaterials*, 24, 401-416.
- Ando W, Tateishi K, Hart DA, Katakai D, Tanaka Y, Nakata K, Hashimoto J, Fujie H, Shino, K, Yoshikawa H, Nakamura N. (2007). Cartilage repair using an *in vitro* generated scaffold-free tissue-engineered construct derived from porcine synovial mesenchymal stem cells. *Biomaterials*, 28, 5462-5470.

- Angele P, Kujat R, Nerlich M, Yoo J, Golberg V, Johnstone B. (1999). Engineering of osteochondral tissue with bone marrow mesenchymal progenitor cells in a derivatized hyaluronan-gelatin composite sponge. *Tissue Eng* 5,545-553.
- Aoyagi S, Onishi H, Machida Y. (2007). Novel chitosan wound dressing loaded with minocycline for the treatment of severe burn wounds. *Int J Pharm* 330, 138-145.
- Azad AK, Sermsintham N, Chandkrachang S, Stevens WF. (2004). Chitosan membrane as a wound-healing dressing: Characterization and clinical application. *J Biomed Mater Res B*, 69B, 216-222.
- Azevedo EP, Saldanha TDP, Navarro MVM, Medeiros AC, Ginani MF, Raffin FN. (2006). Mechanical properties and release studies of chitosan films impregnated with silver sulfadiazine. *J Appl Polym Sci*, 102, 3462-3470.
- Bakos D, Koniarova D. (1999). Collagen and collagen/hyaluronan complex modifications. *Chem Papers*, 53, 431-435.
- Balakrishnan B, Mohanty M, Umashankar PR, Jayakrishnan A. (2005). Evaluation of an in situ forming hydrogel wound dressing based on oxidized alginate and gelatin. *Biomaterials* 26,6335-6342.
- Balakrishnan B, Mohanty M, Fernandez AC, Parayanthara VM, Jayakrishnan A. (2006). Evaluation of the effect of incorporation of dibutyl cyclic adenosine monophosphate in an in situ forming hydrogel wound dressing based on oxidized alginate and gelatin. *Biomaterials* 27,1355-1361.
- Barbul A. (2001). Wound Healing: Physiology And Possible Role Of Skin Substitutes. In: Horch RE, Munster AM, Achauer BM, eds. *Cultured Human Keratinocytes And Tissue Engineered Skin Substitutes*. New York: Georg Thieme Verlag, p. 23-36.
- Berthand ME, Turgeon SL. (2007). Improved gelling properties of whey protein isolate by addition of xanthan gum. *Food Hydrocolloid*, 21, 159-166.
- Black AF, Berthod F, L'Heureux N, Germain L, Auger FA. (1998). In vitro reconstruction of a human capillary-like network in a tissue-engineered skin equivalent. *FASEB J* 12, 1331-1340.
- Boateng JS, Matthews KH, Stevens HNE, Eccleston GM. (2008). Wound healing dressings and drug delivery systems: A review. *J Pharm Sci*, 97, 2892-2923.
- Boonthekul T, Kong HJ, Mooney DJ. (2005). Controlling alginate gel degradation utilizing partial oxidation and bimodal molecular weight distribution. *Biomaterials*, 26, 2455-2465.
- Bouhadir KH, Lee KY, Alsberg E, Damm KL, Anderson KW, Mooney DJ. (2001). Degradation of partially oxidized alginate and its potential application for tissue engineering. *Biotechnol Progr*, 17, 945-950.
- Burke JF, Yannas IV, Quinby WC, Bondoc CC, Jung WK. (1981). Successful use of a physiologically acceptable artificial skin in the treatment of extensive burn injury. *Ann Surg* 194, 413-428.
- Chamberlain LJ, Yannas IV, Hsu, H.-P., Strichartz G, Spector M. (1998). Collagen-GAG substrate enhances the quality of nerve regeneration through collagen tubes up to level of autograft. *Exp Neurol* 154,315-329.
- Chang CH, Liu HC, Lin CC, Chou CH, Lin FH. (2003a). Gelatin-chondroitin-hyaluronan tri-copolymer scaffold for cartilage tissue engineering. *Biomaterials*, 24, 4853-4858.
- Chang WH, Chang Y, Lai PH, Sug HW. (2003b). A genipin-crosslinked gelatin membrane as wound-dressing material: in vitro and in vivo studies. *J Biomater Sci Polym Ed*, 14, 481-495.
- Chang YH, Xiao L, Tang Q. (2009). Preparation and Characterization of a Novel Thermosensitive Hydrogel Based on Chitosan and Gelatin Blends. *J Appl Polym Sci*, 113, 400-407.
- Chen G, Ushida T, Tateishi T. (2002). Scaffold design for tissue engineering. *Macromol Biosci*, 2, 67-77.
- Chen H, Ouyang W, Lawuyi B, Martoni C, Prakash S. (2005). Reaction of chitosan with genipin and its fluorogenic attributes for potential microcapsule membrane characterization. *J Biomed Mater Res A* 75, 917-927.
- Chen H, Ouyang W, Lawuyi B, Prakash S. (2006). Genipin cross-linked alginate-chitosan microcapsules: membrane characterization and optimization of cross-linking reaction. *Biomacromolecules*, 7, 2091-2098.
- Chen JP, Chang GY, Chen JK. (2008). Electrospun collagen/chitosan nanofibrous membrane as wound dressing. *Colloid Surface A*, 313, 183-188.
- Chen YL, Lee HP, Chan HY, Sung LY, Chen HC, Hu YC. (2007). Composite chondroitin-6-sulfate/dermatan sulfate/chitosan scaffolds for cartilage tissue engineering. *Biomaterials* 28, 2294-2305.
- Cheng M, Cao W, Gao Y, Gong Y, Zhao N, Zhang X. (2003a). Studies on nerve cell affinity of biodegradable modified chitosan films. *J Biomater Sci Polym Ed*, 14, 1155-1167.
- Cheng M, Deng J, Yang F, Gong Y, Zhao N, Zhang X. (2003b). Study on physical properties and nerve cell affinity of composite films from chitosan and gelatin solutions. *Biomaterials*, 24, 2871-2880.
- Chiono V, Pulieri E, Vozzi G, Ciardelli G, Ahluwalia A, Giusti P. (2008). Genipin-crosslinked chitosan/gelatin blends for biomedical applications. *J Mater Sci-Mater M*, 19, 889-898.
- Chiu C-T, Lee J-S, Chu C-S, Chang Y-P, Wang Y-J. (2008). Development of two alginate-based wound dressings. *J Mater Sci-Mater M*, 19, 2503-2513.
- Cho YW, Cho YN, Chung SH, Yoo G, Ko SW. (1999). Water-soluble chitin as a wound healing accelerator. *Biomaterials*, 20, 2139-2145.
- Choi YS, Hong SR, Lee YM, Song KW, Park MH, Nam YS. (1999). Studies on gelatin-containing artificial skin: II. Preparation and characterization of cross-linked gelatin-hyaluronate sponge. *J Biomed Mater Res* 48,631-639.
- Choi YS, Lee SB, Hong SR, Lee YM, Song KW, Park MH. (2001). Studies on gelatin-based sponges. Part III: A comparative study of cross-linked gelatin/alginate, gelatin/hyaluronate and chitosan/hyaluronate sponges and their application as a wound dressing in full-thickness skin defect of rat. *J Mater Sci-Mater M* 12,67-73.
- Chou CH, Cheng WT, Lin CC, Chang CH, Tsai CC, Lin FH. (2006). TGF-beta1 immobilized tri-co-polymer for articular cartilage tissue engineering. *J Biomed Mater Res B*, 77, 338-348.
- Christopoulou V, Papanagopoulos D, Dondos A. (2000). Relation between the repulsion of incompatible and compatible polymers in solution and their degree of mixing in the solid state: the memory effect. *Polym Int*, 49, 1365-1370.
- Chu PK, Chen JY, Wang LP, Huang N. (2002). Plasma surface modification of biomaterials. *Mater Sci Eng R*, 36, 143-206.
- Chung C, Burdick JA. (2008). Engineering cartilage tissue. *Adv Drug Deliver Rev* 60, 243-262.
- Ciechanska D. (2004). Multifunctional bacterial cellulose/chitosan composite materials for medical applications. *Fibres Text East Eur*, 12, 69-72.
- Correlo VM, Boesel LF, Pinho E, Costa-Pinto AR, Da Silva MLA, Bhattacharya M, Mano JF, Neves NM, Reis RL. (2009). Melt-based compression-molded scaffolds from chitosan-polyester blends and composites: Morphology and mechanical properties. *J Biomed Mater Res A*, 91A, 489-504.
- Correlo VM, Gomes ME, Tuzlakoglu K, Oliveira JM, Malafaya PB, Mano JF, Neves N M, Reis RL. (2007a). Tissue Engineering Using Natural Polymers In: Jenkins M, ed. *Biomedical Polymers*. Woodhead Publishing and Maney Publishing, Cambridge, p. 197-217.
- Correlo VM, Pinho ED, Pashkuleva I, Bhattacharya M, Neves NM, Reis RL. (2007b). Water absorption and degradation characteristics of chitosan-based polyesters and hydroxyapatite composites. *Macromol Biosci*, 7, 354-363.
- Cullen B, Watt PW, Lundqvist C, Silcock D, Schmidt RJ, Bogan D, Light ND. (2002). The role of oxidised regenerated cellulose/collagen in chronic wound repair and its potential mechanism of action. *Int J Biochem Cell Biol*, 34, 1544-1556.
- Czaja WK, Young DJ, Kaweck M, Brown RM. (2007). The future prospects of microbial cellulose in biomedical applications. *Biomacromolecules*, 8, 1-12.
- Dambuyant CD, Black A, Bechetoille N, Bouez C, Maréchal S, Auxenfans C, Cenizo V, Pascal P, Perrier E, Damour O. (2006). Evolutionary skin reconstructions: From the dermal collagen-glycosaminoglycan-chitosane substrate to an immunocompetent reconstructed skin. *Biomed Mater Eng* 16,S85-S94.
- Damodaran S. (1997). *Food Proteins and Their Applications*. New York, Marcel Dekker.
- da Silva RMP, Mano JF, Reis RL. (2007). Smart thermo-responsive coatings and surfaces for tissue engineering: switching cell-material boundaries. *Trends Biotechnol* 25, 577-583.
- Dawlee S, Sugandhi A, Balakrishnan B, Labarre D, Jayakrishnan A. (2005). Oxidized chondroitin sulfate-cross-linked gelatin matrixes: A new class of hydrogels. *Biomacromolecules* 6,2040-2048.
- De Kruijff CG, Weinbreck F, De Vries R. (2004). Complex coacervation of proteins and anionic polysaccharides. *Curr Opin Colloid In*, 9, 340-349.
- Dickinson E. (2006). Colloid science of mixed ingredients *Soft Matter*, 2, 642-652.
- Donaghue VM, Chrzan JS, Rosenblum BI, Giurini JM, Habershaw GM, Veves A. (1998). Evaluation of a collagen-alginate wound dressing in the management of diabetic foot ulcers. *Adv Wound Care*, 11, 114-119.
- Doublier JL, Garnier C, Renard D, Sanchez C. (2000). Protein-polysaccharide interactions. *Curr Opin Colloid In*, 5, 202-214.
- Eiselt P, Yeh, J, Latvala RK, Shea LD, Mooney DJ. (2000). Porous carriers for biomedical applications based on alginate hydrogels. *Biomaterials* 21, 1921-1927.
- Fan H, Hu Y, Qin L, Li X, Wu H, Lv R. (2006). Porous gelatin-chondroitin-hyaluronate tri-copolymer scaffold containing microspheres loaded with TGF-beta1 induces differentiation of mesenchymal stem cells in vivo for enhancing cartilage repair. *J Biomed Mater Res A* 77,785-794.

- Fan JY, Shang Y, Yuan YJ, Yang J. (2010). Preparation and characterization of chitosan/galactosylated hyaluronic acid scaffolds for primary hepatocytes culture. *J Mater Sci-Mater M* 21,319-327.
- Fan LH, Du YM, Huang RH, Wang Q, Wang XH, Zhang LN. (2005). Preparation and characterization of alginate/gelatin blend fibers. *J Appl Polym Sci* 96,1625-1629.
- Farrell E, O'Brien FJ, Doyle P, Fischer J, Yannas I, Harley BA, O'Connell B, Prendergast PJ, Campbell VA. (2006). A collagen-glycosaminoglycan scaffold supports adult rat mesenchymal stem cell differentiation along osteogenic and chondrogenic Routes. *Tissue Eng* 12,459-469.
- Feldman D. (2005). Polyblend compatibilization. *J Macromol Sci Pure*, 42, 587-605.
- Forch R, Zhang Z, Knoll W. (2005). Soft plasma treated surfaces: tailoring of structure and properties for biomaterial applications. *Plasma Process Polym*, 2, 351-372.
- Fox AS, Allen AE, inventors; Gel forming system for use as wound dressing patent US Patent No. 5578661. 1996.
- Funakoshi T, Majima T, Iwasaki N, Yamane S, Masuko T, Minami A, Harada K, Tamura H, Tokura S, Nishimura SI. (2005). Novel chitosan-based hyaluronan hybrid polymer fibers as a scaffold in ligament tissue engineering. *J Biomed Mater Res A*, 74A, 338-346.
- Gao CY, Wang DY, Shen JC. (2003). Fabrication of porous collagen/chitosan scaffolds with controlling microstructure for dermal equivalent. *Polym Adv Technol*, 14, 373-379.
- Gao J, Dennis JE, Solchage LA, Golberg VM, Caplan AL. (2002). Repair of osteochondral defect with tissue-engineered two-phase composite material of injectable calcium phosphate and hyaluronan sponge. *Tissue Eng*, 8, 827-837.
- Gerard C, Catuogno C, Amargier-Huin C, Grossin L, Hubert P, Gillet P, Netter P, Dellacherie E, Payan E. (2005). The effect of alginate, hyaluronate and hyaluronate derivatives biomaterials on synthesis of non-articular chondrocyte extracellular matrix. *J Mater Sci-Mater M*, 16, 541-551.
- Goddard JM, Hotchkiss JH. (2007). Polymer surface modification for the attachment of bioactive compounds. *Prog Polym Sci*, 32, 698-725.
- Gomes ME, Azevedo HS, Malafaya PB, Silva SS, Oliveira JM, Sousa RA, Mano JE, Reis RL. (2008). Natural polymers in tissue engineering applications. In Blitterswijk C, Lindahl A, Thomsen P, Williams D, Hubbell J, Cancedda R. Eds. *Tissue Eng*. Amsterdam: Elsevier p. 145-192.
- Gomes ME, Holtorf HL, Reis RL, Mikos AG. (2006). Influence of the porosity of starch-based fiber mesh scaffolds on the proliferation and osteogenic differentiation of bone marrow stromal cells cultured in a flow perfusion bioreactor. *Tissue Eng*, 12, 801-809.
- Gomes ME, Reis RL. (2004). Biodegradable polymers and composites in biomedical applications: from catgut to tissue engineering. Part 2 Systems for temporary replacement and advanced tissue regeneration. *Int Mater Rev*, 49, 274-285.
- Guan M, Ren L, Wu T, Sun LP, Li LR, Zhang QQ. (2007). Potential wound dressing with improved antimicrobial property. *J Appl Polym Sci*, 105, 1679-1686.
- Gumpenberger T, Heitz J, Bäuerle D, Kahr H, Graz I, Romanin C, Svorcik V, Leisch F. (2003). Adhesion and proliferation of human endothelial cells on photochemically modified polytetrafluoroethylene. *Biomaterials*, 24, 5139-5144.
- Gunn J, Zhang M. (2010). Polyblend nanofibers for biomedical applications: perspectives and challenges. *Trends Biotechnol*, 28, 189-197.
- Guo T, Zhao JN, Chang JB, Ding Z, Hong H, Chen JN, Zhang JF. (2006). Porous chitosan-gelatin scaffold containing plasmid DNA encoding transforming growth factor-beta 1 for chondrocytes proliferation. *Biomaterials* 27, 1095-1103.
- Hamman JH. (2010). Chitosan Based Polyelectrolyte Complexes as Potential Carrier Materials in Drug Delivery Systems. *Mar Drugs*, 8, 1305-1322.
- Han B, Jauregui J, Tang BW, Nimni ME. (2003). Proanthocyanidin: A natural crosslinking reagent for stabilizing collagen matrices. *J Biomed Mater Res A*, 65, 118-124.
- Hao T, Wen N, Cao JK, Wang HB, Lu SH, Liu T, Lin QX, Duan CM, Wang CY. (2010). The support of matrix accumulation and the promotion of sheep articular cartilage defects repair *in vivo* by chitosan hydrogels. *Osteoarthr Cartilage*, 18, 257-265.
- Harriger MD, Supp AP, Warden GD, Boyce ST. (1997). Glutaraldehyde crosslinking of collagen substrates inhibits degradation in skin substitutes grafted to athymic mice. *J Biomed Mater Res*, 35, 137-145.
- Hart J, Silcock D, Gunnigle S, Cullen BD, Light ND, Watt PW. (2002). The role of oxidised regenerated cellulose/collagen in wound repair: effect in vitro on fibroblast biology and in vivo in a model of compromised healing. *Int J Biochem Cell Biol* 34, 1557-1570.
- Harvanova D, Rosocha J, Bakos D, Svihla R, Vasko G, Hornak S, Ledecy V, Gromosova S, Cibur P, Rasi R. (2009). Collagen/hyaluronan membrane as a scaffold for chondrocytes cultivation. *Biologia* 64,1032-1038.
- Hashimoto T, Suzuki Y, Tanihara M, Kakimaru Y, Suzuki K. (2004). Development of alginate wound dressings linked with hybrid peptides derived from laminin and elastin. *Biomaterials* 25,1407-1414.
- He JK, Li DC, Liu YX, Yao B, Zhan HX, Lian Q, Lu BH, Lv Y. (2009). Preparation of chitosan-gelatin hybrid scaffolds with well-organized microstructures for hepatic tissue engineering. *Acta Biomaterialia*, 5, 453-461.
- Hennink WE, Van Nostrum CF. (2002). Novel crosslinking methods to design hydrogels. *Advanced Drug Reviews*, 54, 13-36.
- Hirano S, Zhang M, Nakagawa M. (2001). Release of glycosaminoglycans in physiological saline and water by wet-spun chitin-acid glycosaminoglycan fibers. *J Biomed Mater Res*, 56, 556-561.
- Hong SR, Lee SJ, Shim JW, Choi YS, Lee YM, Song KW, Park MH, Nam YS, Lee SI. (2001). Study on gelatin-containing artificial skin IV: a comparative study on the effect of antibiotic and EGF on cell proliferation during epidermal healing. *Biomaterials* 22,2777-2783.
- Huang Y-C, Huang C-C, Huang Y-Y, Chen K-S. (2007). Surface modification and characterization of chitosan or PLGA membrane with laminin by chemical and oxygen plasma treatment for neural regeneration. *Journal of Biomedical Materials Research - Part A*, 82A, 842-851.
- Huang YC, Huang YY. (2006). Biomaterials and strategies for nerve regeneration. *Artif Organs*, 30, 514-522.
- Hunt NC, Grover LM. (2010). Cell encapsulation using biopolymer gels for regenerative medicine. *Biotechnol Lett*, 32, 733-742.
- Hunt NC, Shelton RM, Grover L. (2009). An alginate hydrogel matrix for the localised delivery of a fibroblast/keratinocyte co-culture. *Biotechnol J*, 4, 730-7.
- Hutmacher DW. (2000). Scaffolds in tissue engineering bone and cartilage. *Biomaterials*, 21, 2529-2543.
- Inagaki N. (1996). Plasma modification by implantation. *Plasma Surface Modification and Plasma Treatment*. Basel: Technomic Publishing Company.
- Iwasaki N, Yamane ST, Majima T, Kasahara Y, Minami A, Harada K, Nonaka S, Maekawa N, Tamura H, Tokura S, Shiono M, Monde K, Nishimura SI. (2004). Feasibility of polysaccharide hybrid materials for scaffolds in cartilage tissue engineering: Evaluation of chondrocyte adhesion to polyion complex fibers prepared from alginate and chitosan. *Biomacromolecules* 5, 828-833.
- Jayakumar R, Prabakaran M, Reis RL, Mano JE. (2005). Graft copolymerized chitosan- present status and applications. *Carbohydr Polym*, 62, 142-158.
- Jeschke MG, Sandmann G, Schubert T, Klein D. (2005). Effect of oxidized regenerated cellulose/collagen matrix on dermal and epidermal healing and growth factors in an acute wound. *Wound Repair Regen*, 13, 324-331.
- Jiankang H, Dichen L, Yaxiong L, Bo Y, Bingheng L, Qin L. (2007). Fabrication and characterization of chitosan/gelatin porous scaffolds with predefined internal microstructures. *Polymer* 48, 4578-4588.
- Jin Y, Ling PX, He YL, Zhang TM. (2007). Effects of chitosan and heparin on early extension of burns. *Burns*, 33, 1027-1031.
- Kang H-W, Tabata Y, Ikada Y. (1999). Fabrication of porous gelatin scaffolds for tissue engineering. *Biomaterials*, 20, 1339-1344.
- Kataropoulou M, Henderson C, Grant H. (2005). Metabolic studies of hepatocytes cultured on collagen substrata modified to contain glycosaminoglycans. *Tissue Eng* 11,1263-1273.
- Kellouche S, Martin C, Korb G, Rezzonico R, Bouard D, Benbunan M, Dubertret L, Soler C, Legrand C, Dosquet C. (2007). Tissue engineering for full-thickness burns: A dermal substitute from bench to bedside. *Biochem Bioph Res Co* 363, 472-478.
- Khan TA, Peh KK. (2003). A preliminary investigation of chitosan film as dressing for punch biopsy wounds in rats. *J Pharm Pharmaceut Sci*, 6, 20-26.
- Khan TA, Peh KK, Ch'ng HS. (2000). Mechanical, bioadhesive strength and biological evaluations of chitosan films for wound dressing. *J Pharm Pharm Sci*, 3, 303-311.
- Khonsari FA, Tatoulian M, Shahidzadeh N, Amouroux J. (1997). Study of the plasma treated polymers and the stability of the surface properties. In Agostino R, Favia P, Fracassi F, eds. *Plasma Processing Of Polymers*. The Netherlands: Kluwer Academic Publishers; 1997. p. 165-207. Please correct the year of the reference for 1997 instead 2003.
- Khor E, Lim LY. (2003). Implantable applications of chitin and chitosan. *Biomaterials*, 24, 2339-2349.
- Kim I-Y, Seo S-J, Moon H-S, Yoo M-K, Park I-Y, Kim B-C, Cho C-S. (2008). Chitosan and its derivatives for tissue engineering applications. *Biotechnol Adv*, 26, 1-21.

- Kim S, Nimni ME, Yang Z, Han B. (2005). Chitosan/gelatin-based films crosslinked by proanthocyanidin. *J Biomed Mater Res B*, 75B, 442-450.
- Kirker KR, Luo Y, Nielson JH, Shelby J, Prestwich GD. (2002). Glycosaminoglycan hydrogel films as bio-interactive dressings for wound healing. *Biomaterials*, 23, 3661-3671.
- Klemm D, Heublein B, Fink HP, Bohn A. (2005). Cellulose: fascinating biopolymer and sustainable raw material. *Angew Chem Int Ed Engl* 44, 3358-3393.
- Kogan G, Soltes L, Stern R, Gemeiner P. (2007). Hyaluronic acid: a natural biopolymer with a broad range of biomedical and industrial applications. *Biotechnol Lett*, 29, 17-25.
- Koji K, Yasuhiko Y, Hiroyuki T, inventors; Wound dressing patent US Patent No. 4651725. 1987.
- Koller J, Bakos D, Sadlonova I. (2000). Biocompatibility studies of a new biosynthetic dermal substitute based on collagen/hyaluronan conjugate. *Cell Tissue Bank* 1, 75-80.
- Koller J, Bakos D, Sadlonova I. (2001). Biocompatibility studies of modified collagen /hyaluronan membranes after implantation. *Cell Tissue Bank* 2, 135-142.
- Koning C, Van Duin M, Pagnouille C, Jerome R. (1998). Strategies for compatibilization of polymer blends. *Prog Polym Sci*, 23, 707-757.
- Koo HJ, Song YS, Kim HJ, Lee YH, Hong SM, Kim SJ, Kim BC, Jin C, Lim CJ, Park, EH. (2004). Antiinflammatory effects of genipin, an active principle of gardenia. *European J Pharmacol* 495, 201-208.
- Kopecek J, Yang J. (2007). Review - Hydrogels as smart biomaterials. *Polym Int*, 56, 1078-1098.
- Kratz G, Arnander C, Swedenborg J, Back M, Falk C, Gouda I, Larm O. (1997). Heparin-chitosan complexes stimulate wound healing in human skin. *Scand J Plast Reconstr*, 31, 119-123.
- Kruif CG, Tuinier R. (2001). Polysaccharide protein interactions. *Food Hydrocolloid*, 15, 555-563.
- Kubo K, Kuroyanagi Y. (2003). Development of a cultured dermal substitute composed of a spongy matrix of hyaluronic acid and atelo-collagen combined with fibroblasts: fundamental evaluation. *J Biomat Sci-Polym E* 14,625-641.
- Kubo K, Kuroyanagi Y. (2004). Development of a cultured dermal substitute composed of a spongy matrix of hyaluronic acid and atelo-collagen combined with fibroblasts: cryopreservation. *Artif Organs* 28,182-188.
- Kubo K, Kuroyanagi Y. (2003). Spongy matrix of hyaluronic acid and collagen as a cultured dermal substitute: evaluation in an animal test. *J Artif Organs*, 6, 64-70.
- Kumar MNVR. (2000). A review of chitin and chitosan applications. *React Funct Polym*, 46, 1-27.
- Kumar MNVR, Muzzarelli RAA, Muzzarelli C, Sashiwa H, Domb AJ. (2004). Chitosan chemistry and pharmaceutical perspectives. *Chem Rev* 104, 6017-6084.
- Kuo YC, Lin CY. (2006). Effect of genipin-crosslinked chitin-chitosan scaffolds with hydroxyapatite modifications on the cultivation of bovine knee chondrocytes. *Biotechnol Bioeng*, 95, 132-144.
- Kurita K. (2001). Controlled functionalization of the polysaccharide chitin. *Prog Polym Sci*, 26, 1921-1971.
- Kweon D-K, Song S-B, Park Y-Y. (2003). Preparation of water-soluble chitosan/heparin complex and its application as wound healing accelerator. *Biomaterials*, 24, 1595-1601.
- Kweon H, Ha HC, Um IC, Park YH. (2001). Physical properties of silk fibroin/chitosan blend films. *J Appl Polym Sci*, 80, 928-934.
- Langer R, Vacanti J. (1993). *Tissue engineering*. Science, 260, 920-926.
- Lanza R, Langer R, Vacanti JP. (2000). *Principles of Tissue Engineering*. New York: Academic Press.
- Lee CR, Grodzinsky AJ, Spector M. (2001). The effects of cross-linking of collagen-glycosaminoglycan scaffolds on compressive stiffness, chondrocyte-mediated contraction, proliferation and biosynthesis. *Biomaterials* 22,3145-3154.
- Lee JE, Jeong MH, Ahn HJ, Kim JK, Choi K, Chang CB, Kim HJ, Seong SC, Lee MC. (2005). Evaluation of chondrogenesis in collagen/chitosan/glycosaminoglycan scaffolds for cartilage tissue engineering. *Tissue Eng Regen Med*, 2, 41-49.
- Lee JE, Kim KE, Kwon IC, Ahn HJ, Lee S-H, Cho H, Kim HJ, Seong SC, Lee MC. (2004). Effects of the controlled-released TGF- β 1 from chitosan microspheres on chondrocytes cultured in a collagen/chitosan/glycosaminoglycan scaffold. *Biomaterials*, 25, 4163-4173.
- Lee KY, Jeong L, Kang YO, Lee SJ, Park WH. (2009). Electrospinning of polysaccharides for regenerative medicine. *Adv Drug Deliver Rev*, 61, 1020-1032.
- Lee SB, Lee YM, Song KW, Park MH. (2003). Preparation and properties of polyelectrolyte complex sponges composed of hyaluronic acid and chitosan and their biological behaviors. *J Appl Polym Sci* 90,925-932.
- Li ZS, Zhang MQ. (2005). Chitosan-alginate as scaffolding material for cartilage tissue engineering. *J Biomed Mater Res A* 75A,485-493.
- Liao E, Yaszemski M, Krebsbach P, Hollister S. (2007). Tissue-engineered cartilage constructs using composite hyaluronic acid/collagen I hydrogels and designed poly(propylene fumarate) scaffolds. *Tissue Eng*, 13, 537-550.
- Lindenhayn K, Perka C, Spitzer RS, Heilmann HH, Pommerening K, Mennicke J, Sittinger M. (1999). Retention of hyaluronic acid in alginate beads: aspects for in vitro cartilage engineering. *J Biomed Mater Res* 44,149-155.
- Liu BS, Yao CH, Hsu SH, Yeh TS, Chen YS, Kao ST. (2004). A novel use of genipin-crosslinked gelatin as extracellular matrix for peripheral nerve regeneration. *J Biomater Appl*, 19, 21-34.
- Liu HF, Fan HB, Cui YL, Chen YP, Yao KD, Goh JCH. (2007a). Effects of the controlled-released basic fibroblast growth factor from chitosan-gelatin microspheres on human fibroblasts cultured on a chitosan-gelatin scaffold. *Biomacromolecules*, 8, 1446-1455.
- Liu ZG, Jiao YP, Liu F, Zhang ZY. (2007b). Heparin/chitosan nanoparticle carriers prepared by polyelectrolyte complexation. *J Biomed Mater Res A*, 83A, 806-812.
- Lloyd LL, Kennedy JF, Methacanon P, Paterson M, Knill CJ. (1998). Carbohydr Polym as wound management aids. *Carbohydr Polym* 37, 315-322.
- Lopez-Perez PM, Marques AP, Da Silva RMP, Pashkuleva I, Reis RL. (2007). Effect of chitosan membrane surface modification via plasma induced polymerization on the adhesion of osteoblast-like cells. *J Mater Chem*, 17, 4064-4071.
- Lundin M, Blomberg E, Tilton RD. (2010). Polymer dynamics in layer-by-layer assemblies of chitosan and heparin. *Langmuir*, 26, 3242-3251.
- Ma JB, Wang HJ, He BL, Chen JT. (2001). A preliminary *in vitro* study on the fabrication and tissue engineering applications of a novel chitosan bilayer material as a scaffold of human neonatal dermal fibroblasts. *Biomaterials*, 22, 331-336.
- Ma L, Gao C, Mao Z, Zhou J, Shen J, Hu X, Han C. (2003). Collagen/chitosan porous scaffolds with improved biostability for skin tissue engineering. *Biomaterials*, 24, 4833-41.
- Ma L, Shi YC, Chen YX, Zhao HH, Gao CY, Han CM. (2007). *In vitro* and *in vivo* biological performance of collagen-chitosan/silicone membrane bilayer dermal equivalent. *J Mater Sci-Mater M*, 18, 2185-2191.
- MacIntosh AC, Kearns VR, Crawford A, Hattton PV. (2008). Skeletal tissue engineering using silk biomaterials. *J Tissue Eng Regen Med*, 2, 71-80.
- MacNeil S. (2007). Progress and opportunities for tissue-engineered skin. *Nature*, 445, 874-880.
- Madhally SV, Matthew HWT. (1999). Porous chitosan scaffolds for tissue engineering. *Biomaterials*, 20, 1133-1142.
- Majima T, Irie T, Sawaguchi N, Funakoshi T, Iwasaki N, Harada K, Minami A, Nishimura SI. (2007). Chitosan-based hyaluronan hybrid polymer fibre scaffold for ligament and tendon tissue engineering. *P I Mech Eng H*, 221, 537-546.
- Majima T, Funakoshi T, Iwasaki N, Yamane S-T, Harada K, Nonaka S, Minami A, Nishimura S-H. (2005). Alginate and chitosan polyion complex hybrid fibers for scaffolds in ligament and tendon tissue engineering. *J Orthop Res* 10, 302-307.
- Malafaya PB, Pedro AJ, Peterbauer A, Gabriel C, Redl H, Reis, RL. (2005). Chitosan particles agglomerated scaffolds for cartilage and osteochondral tissue engineering approaches with adipose tissue derived stem cells. *J Mater Sci-Mater M*, 16, 1077-1085.
- Malafaya PB, Silva GA, Reis RL. (2007). Natural-origin polymers as carriers and scaffolds for biomolecules and cell delivery in tissue engineering applications. *Advanced Drug Reviews*, 59, 207-233.
- Malafaya PB, Stappers F, Reis RL. (2006). Starch-based microspheres produced by emulsion crosslinking with a potential media dependent responsive behavior to be used as drug delivery carriers. *J Mater Sci-Mater M*, 17, 371-377.
- Malay O, Bayraktar O, Batigun A. (2007). Complex coacervation of silk fibroin and hyaluronic acid. *Int J Biol Macromol*, 40, 387-393.
- Mano JF, Reis RL. (2007). Osteochondral defects: present situation and tissue engineering approaches. *J Tissue Eng Regen Med*, 1, 261-273.
- Mano JF, Silva GA, Azevedo HS, Malafaya PB, Sousa RA, Silva SS, Boesel LF, Oliveira JM, Santos TC, Marques AP, Neves NM, Reis RL. (2007). Natural origin biodegradable systems in *Tissue Eng Regen Med*: present status and some moving trends. *J R Soc Interface*, 4, 999-1030.
- Mao C, Qiu YZ, Sang HB, Mei H, Zhu AP, Shen J, Lin SC. (2004). Various approaches to modify biomaterial surfaces for improving hemocompatibility. *Adv Colloid Interfac*, 110, 5-17.

- Marreco PR, Da Luz Moreira P, Genari SC, Moraes AM. (2004). Effects of different sterilization methods on the morphology, mechanical properties, and cytotoxicity of chitosan membranes used as wound dressings. *J Biomed Mater Res B*, 71B, 268-277.
- Martina B, Krej C, Kate O, Rcaron I, Miloslava R, Jan G, Ruta, M. (2009). Oxycellulose: Significant characteristics in relation to its pharmaceutical and medical applications. *Adv Polym Tech*, 28, 199-208.
- McClements DJ. (2006). Non-covalent interactions between proteins and polysaccharides. *Biotechnol Adv*, 24, 621-625.
- Medrado GCB, Machado CB, Valerio P, Sanches MD, Goes AM. (2006). The effect of a chitosan-gelatin matrix and dexamethasone on the behavior of rabbit mesenchymal stem cells. *Biomed Mater*, 1, 155-161.
- Meena R, Prasad K, Siddhanta AK. (2007). Effect of genipin, a naturally occurring crosslinker on the properties of kappa-carrageenan. *Int J Biol Macromol*, 41, 94-101.
- Metcalfe, AD, Ferguson MW. (2007). Tissue engineering of replacement skin: the crossroads of biomaterials, wound healing, embryonic development, stem cells and regeneration. *J R Soc Interface*, 4, 413-437.
- Mi FL, Tan YC, Liang HF, Sung HW. (2002a). *In vivo* biocompatibility and degradability of a novel injectable-chitosan-based implant. *Biomaterials*, 23, 181-191.
- Mi FL, Wu YB, Shyu SS, Schoung JY, Huang YB, Tsai YH, Hao, JY. (2002b). Control of wound infections using a bilayer chitosan wound dressing with sustainable antibiotic delivery. *J Biomed Mater Res*, 59, 438-449.
- Mikos AG, Temenoff JS. (2000). Formation of highly porous biodegradable scaffolds for tissue engineering. *EJB*, 3, 1-6.
- Miralles G, Baudoin R, Dumas D, Baptiste D, Hubert P, Stoltz JF, Dellacherie E, Mainard D, Netter P, Payan E. (2001). Sodium alginate sponges with or without sodium hyaluronate: In vitro engineering of cartilage. *J Biomed Mater Res* 57,268-278.
- Mizuno K, Yamamura K, Yano K, Osada T, Saeki S, Takimoto N, Sakurai T, Nimura Y. (2003). Effect of chitosan film containing basic fibroblast growth factor on wound healing in genetically diabetic mice. *J Biomed Mater Res A*, 64A, 177-181.
- Mourya VK, Inamdar NN. (2008). Chitosan-modifications and applications: Opportunities galore. *Reactive Functional Polymers*, 68, 1013-1051.
- Murakami K, Aoki H, Nakamura S, Nakamura S, Takikawa M, Hanzawa M, Kishimoto S, Hattori H, Tanaka Y, Kiyosawa T, Sato Y, Ishihara M. (2010). Hydrogel blends of chitin/chitosan, fucoidan and alginate as healing-impaired wound dressings. *Biomaterials* 31, 83-90.
- Murray MM, Rice K, Wright RJ, Spector M. (2003). The effect of selected growth factors on human anterior cruciate ligament cell interactions with a three-dimensional collagen-GAG scaffold. *J Orthop Res* 21, 238-244.
- Musampa RM, Alves MM, Maia JM. (2007). Phase separation, rheology and microstructure of pea protein-kappa-carrageenan mixtures. *Food Hydrocolloid*, 21, 92-99.
- Muzzarelli RAA. (2009). Genipin-crosslinked chitosan hydrogels as biomedical and pharmaceutical aids. *Carbohydr Polym*, 77, 1-9.
- Muzzarelli RAA, Guerrieri M, Goteri G, Muzzarelli C, Armeni T, Ghiselli R, Cornelissen M. (2005). The biocompatibility of dibutyl chitin in the context of wound dressings. *Biomaterials*, 26, 5844-5854.
- Naidu BVK, Sairam M, Raju KVS, Aminabhavi TM. (2005). Thermal, viscoelastic, solution and membrane properties of sodium alginate/hydroxyethylcellulose blends. *Carbohydr Polym*, 61, 52-60.
- Nehrer S, Breinan HA, Ramappa A, Young G, Louie LK, Sledge CB, Yannas IV, Spector M. (1997). Matrix collagen type and pore size influence behaviour of seeded canine chondrocytes *Biomaterials* 16,769-776.
- Nehrer S, Breinan HA, Ramappa A, Hsu HP, Minas T, Shortkro S, Sledge CB, Yannas IV, Spector M. (1998). Chondrocyte seeded collagen matrices implanted in a chondral defect in a canine model *Biomaterials* 19,2313-2328.
- Nettles DL, Elder SH, Gilbert JA. (2002). Potential use of chitosan as a cell scaffold material for cartilage tissue engineering. *Tissue Eng*, 8, 1009-1016.
- Noel TR, Krzeminski A, Moffat J, Parker R, Wellner N, Ring SG. (2007). The deposition and stability of pectin/protein and pectin/poly-L-lysine/protein multilayers. *Carbohydr Polym*, 70, 393-405.
- Oehr C. (2003). Plasma surface modification of polymers for biomedical use. *Nucl Instrum Meth B Research B* 208, 40-47.
- Olbrich M, Punshon G, Frischauf I, Salacinski H, Rebollar E, Romanin C, Seifalian AM, Heitz J. (2007). UV surface modification of a new nanocomposite polymer to improve cytocompatibility. *J Biomater Sci Polym Ed*, 18, 453-468.
- Oliveira JM, Rodrigues MT, Silva SS, Malafaya PB, Gomes ME, Viegas CA, Dias IR, Azevedo JT, Mano JF, Reis RL. (2006). Novel hydroxyapatite/chitosan bilayered scaffold for osteochondral tissue-engineering applications: Scaffold design and its performance when seeded with goat bone marrow stromal cells. *Biomaterials*, 27, 6123-6137.
- Oliveira JT, Crawford A, Mundy JM, Moreira AR, Gomes ME, Hattin PV, Reis RL. (2007). A cartilage tissue engineering approach combining starch-polycaprolactone fibre mesh scaffolds with bovine articular chondrocytes. *J Mater Sci-Mater M*, 18, 295-302.
- Palmiere GP, Lauri D, Martelli S, Wehrle P. (1999). Methoxybutyrate micro-encapsulation by gelatin-acacia complex coacervation. *Drug Dev Ind Pharm*, 25, 399-407.
- Park JE. (2002). Isolation and characterization of water-soluble intermediates of blue pigments transformed from geniposide of gardenia jasminoides. *J Agric Food Chem*, 50, 6511-6514.
- Park SN, Kim JK, Suh H. (2004). Evaluation of antibiotic-loaded collagen-hyaluronic acid matrix as a skin substitute. *Biomaterials*, 25, 3689-3698.
- Park SN, Lee HJ, Lee KH, Suh H. (2003). Biological characterization of EDC-crosslinked collagen-hyaluronic acid matrix in dermal tissue restoration. *Biomaterials*, 24, 1631-1641.
- Park SN, Park JC, Kim HO, Song MJ, Suh H. (2002). Characterization of porous collagen/hyaluronic acid scaffold modified by 1-ethyl-3-(3-dimethylaminopropyl)carbodiimide cross-linking. *Biomaterials*, 23, 1205-1212.
- Pashkuleva I, Marques AP, Vaz F, Reis RL. (2005). Surface modification of starch based blends using potassium permanganate-nitric acid system and its effect on the adhesion and proliferation of osteoblast-like cells. *J Mater Sci-Mater M*, 16, 81-92.
- Pashkuleva I, Reis RL. (2005). Surface Activation And Modification - A Way For Improving The Biocompatibility Of Degradable Biomaterials. In: Reis RL, Román JS, eds. *Biodegradable Systems in Tissue Eng Regen Med*. CRC Press. Boca Raton, p. 429-454.
- Peniche C, Argüelles-Monol W, Goycoolea F. (2008). Chitin and Chitosan: Major Sources, Properties and Applications. In: Belgacem M, Gandini A, eds. *Monomers, Polymers and Composites from Renewable Resources*. Elsevier, Oxford: Elsevier 2008. p. 517-542.
- Pfister LA, Alther E, Papaloizos ML, Merkle HP, Gander B. (2008). Controlled nerve growth factor release from multi-ply alginate/chitosan-based nerve conduits. *Eur J Pharm Biopharm*, 69, 563-572.
- Pielka S, Paluch D, Staniszevska-Kus J, Zywicka B, Solski L, Szosland L, Czarny A, Zaczynska E. (2003). Wound healing acceleration by a textile dressing containing dibutylchitin and chitin. *Fibres Text East Eur*, 11, 79-84.
- Pieper JS, Van Der Kraan PM, Hafmans T, Kamp J, Buma P, Van Susante JLC, Van Den Berg WB, Veerkamp JH, Van Kuppevelt TH. (2002). Crosslinked type II collagen matrices: preparation, characterization, and potential for cartilage engineering. *Biomaterials* 23, 3183-3192.
- Pinkert A, Marsh KN, Pang SS, Staiger MP. (2009). Ionic Liquids And Their Interaction With Cellulose. *Chem Rev*, 109, 6712-6728.
- Powell HM, Boyce ST. (2006). EDC cross-linking improves skin substitute strength and stability. *Biomaterials* 27,5821-5827.
- Pulkkinen H, Virpi Tiitu V, Lammentausta E, Hämäläinen ER, Kiviranta J, Lammi MJ. (2006). Cellulose sponge as a scaffold for cartilage tissue engineering. *Biomed Mater Eng* 16, S29-S35.
- Qin Y. (2008). Alginate fibres: an overview of the production processes and applications in wound management. *Polym Int*, 57, 171-180.
- Queiroz AAA, Ferraz HG, Abraham GA, Fernandez M, Bravo AL, Roman JS. (2003). Development of new hydroactive dressings based on chitosan membranes: characterization and in vivo behavior. *Journal of Biomedical Materials Research - Part A*, 64A, 147-154.
- Ratner BD. (1995). Surface modification of polymers: chemical, biological and surface analytical challenges. *Biosens Bioelectron* 10, 797-804.
- Roh DH, Kang SY, Kim JY, Kwon YB, Kweon HY, Lee KG, Park YH, Baek RM, Heo CY, Choe J, Lee JH. (2006). Wound healing effect of silk fibroin/alginate-blended sponge in full thickness skin defect of rat. *J Mater Sci-Mater M*, 17, 547-552.
- Salmivirta M, Lidholt K, Lindahl U. (1996). Heparan sulfate: a piece of information. *FASEB J*, 10, 1270-1279.
- Sanchez C, Renard D. (2002). Stability and structure of protein-polysaccharide coacervates in the presence of protein aggregates. *Int J Pharm*, 242, 319-324.
- Santos MI, Fuchs S, Gomes ME, Unger RE, Reis RL, Kirkpatrick J. (2007). Response of micro- and macrovascular endothelial cells to starch-based fiber meshes for bone tissue engineering. *Biomaterials* 28,240-248.
- Santos TC, Marques AP, Silva SS, Oliveira JM, Mano JF, Reis RL. (2010). *In vivo* performance of chitosan/soy-based membranes as wound dressing devices for acute skin wounds. *Tissue Eng*. In press
- Schmidt C, Leach JB. (2003). Neural tissue engineering: strategies for repair and regeneration. *Ann Rev Biomed Eng* 5, 293-347.

- Seal BL, Otero TC, Panitch A. (2001). Polymeric biomaterials for tissue and organ regeneration *Mater Sci Eng R*, 34, 147-230.
- Seo SJ, Choi YJ, Akaike T, Higuchi A, Cho CS. (2006a). Alginate/galactosylated chitosan/heparin scaffold as a new synthetic extracellular matrix for hepatocytes. *Tissue Eng*, 12, 33-44.
- Seo SJ, Kim IY, Choi YJ, Akaike T, Cho CS. (2006b). Enhanced liver functions of hepatocytes cocultured with NIH 3T3 in the alginate/galactosylated chitosan scaffold. *Biomaterials*, 27, 1487-1495.
- She ZD, Liu WQ, Feng QL. (2009). Self-assembly model, hepatocytes attachment and inflammatory response for silk fibroin/chitosan scaffolds. *Biomed Mater* 4,045014
- She ZD, Liu WQ, Feng QL. (2010). Silk fibroin/chitosan/heparin scaffold: preparation, antithrombogenicity and culture with hepatocytes. *Polym Int* 59,55-61.
- Shi H, Ma L, Zhou J, Mao Z, Gao C. (2005). Collagen/chitosan-silicone membrane bilayer scaffold as a dermal equivalent *Polym Adv Technol* 16, 789-794.
- Silva GA, Coutinho OP, Ducheyne P, Shapiro IM, Reis RL. (2007a). Starch-based microparticles as vehicles for the delivery of active platelet-derived growth factor. *Tissue Eng*, 13, 1259-1268.
- Silva RM, Silva GA, Coutinho OP, Mano JF, Reis RL. (2004). Preparation and characterisation in simulated body conditions of glutaraldehyde crosslinked chitosan membranes. *J Mater Sci-Mater M*, 15, 1105-1112.
- Silva SS, Goodfellow BJ, Benesch J, Rocha J, Mano JF, Reis RL. (2007b). Morphology and miscibility of chitosan/soy protein blended membranes. *Carbohydr Polym*, 70, 25-31.
- Silva SS, Luna SM, Gomes ME, Benesch J, Paskuleva I, Mano JF, Reis RL. (2007c). Plasma surface modification of chitosan membranes: characterization and preliminary cell response studies. *Macromol Biosci. Macromol Biosci*, 8, 568-576.
- Silva SS, Motta A, Rodrigues MT, Pinheiro AFM, Gomes ME, Mano JF, Reis RL, Migliaresi C. (2008). Novel genipin-cross-linked chitosan/silk fibroin sponges for cartilage engineering strategies. *Biomacromolecules*, 9, 2764-2774.
- Silva SS, Oliveira JM, Mano JF, Reis RL. (2006). Physicochemical characterization of novel chitosan-soy protein/TEOS porous hybrids for tissue engineering applications. *Mater Sci Forum* 111, Pts 1 and 2, 514-516, 1000-1004.
- Silva SS, Santos MI, Coutinho OP, Mano JF, Reis RL. (2005). Physical properties and biocompatibility of chitosan/soy blended membranes. *J Mater Sci-Mater M*, 16, 575-579.
- Sionkowska A, Wisniewski M, Skopinska J, Kennedy CJ, Wess TJ. (2004). Molecular interactions in collagen and chitosan blends. *Biomaterials*, 25, 795-801.
- Stark Y, Suck K, Kasper C, Wieland M, Van Griensven M, Schepel T. (2006). Application of collagen matrices for cartilage tissue engineering. *Exp Toxicol Pathol*, 57, 305-311.
- Strobin G, Wawro D, Stepleski W, Ciechanska D, Józwicka J, Sobczak S, Haga A. (2006). Formation of cellulose/silk fibroin blended fibres. *Fibres Text* 14,32-35.
- Suh JKF, Matthew HWT. (2000). Application of chitosan-based polysaccharide biomaterials in cartilage tissue engineering: a review. *Biomaterials*, 21, 2589-2598.
- Sundararaghavan HG, Monteiro GA, Lapin NA, Chabal YJ, Miksan JR, Shreiber DI. (2008). Genipin-induced changes in collagen gels: Correlation of mechanical properties to fluorescence. *J Biomed Mater Res A*, 87A, 308-320.
- Sung H-W, Huang R-N, Huang LLH, Tsai C-C, Chiu C-T. (1998). Feasibility study of a natural crosslinking reagent for biological tissue fixation. *J Biomed Mater Res*, 42, 560-567.
- Sung HW, Hsu CS, Lee YS, Lin DS. (1996). Crosslinking characteristics of an epoxy-fixed porcine tendon: effects of pH, temperature and fixative concentration. *J Biomed Mater Res*, 31, 511-518.
- Suzuki Y, Yoshihiko N, Tanihara M, Suzuki K, Kitahara AK, Yamawaki Y, Nakamura T, S. himizu Y, Kakimaru Y. (1998). Development of alginate gel dressing. *J Artif Organs*, 1, 28-32.
- Svensson A, Nicklasson E, Harrah T, Panlaitis B, Kaplan DL, Brittberg M, Gatenholm P. (2005). Bacterial cellulose as a potential scaffold for tissue engineering of cartilage. *Biomaterials*, 26, 419-431.
- Taguchi T, Ikoma T, Tanaka J. (2002). An improved method to prepare hyaluronic acid and type II collagen composite matrices. *J Biomed Mater Res*, 61, 330-336.
- Tai BCU, Du C, Gao SJ, Wan ACA, Ying JY. (2010). The use of a polyelectrolyte fibrous scaffold to deliver differentiated hMSCs to the liver. *Biomaterials*, 31, 48-57.
- Tan HP, Chu CR, Payne KA, Marra KG. (2009). Injectable *in situ* forming biodegradable chitosan-hyaluronic acid based hydrogels for cartilage tissue engineering. *Biomaterials*, 30, 2499-2506.
- Tan HP, Gong YH, Lao LH, Mao ZW, Gao CY. (2007). Gelatin/chitosan/hyaluronan ternary complex scaffold containing basic fibroblast growth factor for cartilage tissue engineering. *J Mater Sci-Mater Med* 18, 1961-1968.
- Tanabe T, Okitsu N, Tachibana A, Yamauchi K. (2002). Preparation and characterization of keratin-chitosan composite film. *Biomaterials*, 23, 817-825.
- Tang SQ, Vickers SM, Hsu HP, Spector M. (2007). Fabrication and characterization of porous hyaluronic acid-collagen composite scaffolds. *J Biomed Mater Res A*, 82A, 323-335.
- Tangpasuthadol V, Pongchaisirikul N, Hoven VP. (2003). Surface modification of chitosan films. Effects of hydrophobicity on protein adsorption. *Carbohydr Res*, 338, 937-942.
- Taravel MN, Domard A. (1993). Relation between the physicochemical characteristics of collagen and its interactions with chitosan. *Biomaterials* 14, 930-938.
- Taravel MN, Domard A. (1995). Collagen and its interaction with chitosan II. Influence of the physicochemical characteristics of collagen. *Biomaterials*, 16, 665-671.
- Temenoff JS, Mikos AG. (2000). Review: tissue engineering for regeneration of articular cartilage. *Biomaterials*, 21, 431-440.
- Tigli RS, Gumusderelioglu M. (2009). Evaluation of alginate-chitosan semi IPNs as cartilage scaffolds. *J Mater Sci-Mater M* 20, 699-709.
- Tolstoguzov VB. (2000). Phase behaviour of macromolecular components in biological and food systems. *Nahrung*, 44, 299-308.
- Tsai SP, Hsieh CY, Hsieh CY, Wang DM, Huang LLH, Lai JY, Hsieh HJ. (2007). Preparation and cell compatibility evaluation of chitosan/collagen composite scaffolds using amino acids as crosslinking bridges. *J Appl Polym Sci* 105, 1774-1785.
- Turgeon SL, Beaulieu M, Schmitt C, Sanchez C. (2003). Protein-polysaccharide interactions: phase-ordering kinetics, thermodynamic and structural aspects. *Curr Opin Colloid In*, 8, 401-414.
- Unger RE, Peters K, Wolf M, Motta A, Migliaresi C, Kirkpatrick CJ. (2004). Endothelialization of a non-woven silk fibroin net for use in tissue engineering: growth and gene regulation of human endothelial cells. *Biomaterials*, 25, 5137-5146.
- Vaz CM, De Graaf LA, Reis RL, Cunha AM. (2003). *In vitro* degradation behaviour of biodegradable soy plastics: effects of crosslinking with glyoxal and thermal treatment. *Polym Degrad Stab* 81, 65-74.
- Vaz CM, Graaf LA, Reis RL, Cunha AM. (2002). Soy protein-based systems for different tissue regeneration applications. In Reis RL, Cohn D, eds. *Polymer Based Systems on Tissue Engineering, Replacement and Regeneration*. Kluwer Academic Publishers. Dordrecht
- Veilleux MS, Spector M. (2005). Effects of FGF-2 and IGF-1 on adult canine articular chondrocytes in type II collagen-glycosaminoglycan scaffolds *in vitro* *Osteoarth Cartilage* 13,278-286.
- Vepari C, Kaplan DL. (2007). Silk as a biomaterial. *Prog Polym Sci*, 32, 991-1007.
- Wang TW, Sun JS, Wu H-C, Huang Y-C, Lin F-H. (2007). Evaluation and biological characterization of biolayer gelatin/chondroitin-6-sulphate/hyaluronic acid membrane *J Biomed Mater Res B* 82B,390-399.
- Wang TW, Wu HC, Huang YC, Sun JS, Lin FH. (2006). Biomimetic bilayered gelatin-chondroitin-6-sulfate-hyaluronic acid biopolymer as a scaffold for skin equivalent tissue engineering. *Artif Organs*, 30, 141-149.
- Wang XH, Li DP, Wang WJ, Feng QL, Cui FZ, Xu YX, Song XH, Werf M. (2003). Crosslinked collagen/chitosan matrix for artificial livers. *Biomaterials*, 24, 3213-3220.
- Wang XM, Zhang J, Chen H, Wang QR. (2009). Preparation and Characterization of Collagen-Based Composite Conduit for Peripheral Nerve Regeneration. *J Appl Polym Sci* 112, 3652-3662.
- Wang LH, Khor E, Wee A, Lim LY. (2002). Chitosan-alginate PEC membrane as a wound dressing: Assessment of incisional wound healing. *J Biomed Mater Res*, 63, 610-618.
- Welle A, Horn S, Schimmelpfeng J, Kalka D. (2005). Photo-chemically patterned polymer surfaces for controlled PC-12 adhesion and neurite guidance. *J Neurosci Methods*, 142, 243-250.
- Xia WY, Liu W, Cui L, Liu YC, Zhong W, Liu DL, Wu JJ, Chua KH, Cao YL. (2004). Tissue engineering of cartilage with the use of chitosan-gelatin complex scaffolds. *J Biomed Mater Res B* 71B, 373-380.
- Xing F, Cheng GX, Yang B, Ma L. (2005). Nanoencapsulation of capsaicin by complex coacervation of gelatine, Acacia, and tannins. *J Appl Polym Sci*, 96, 2225-2229.

- Xu HT, Ma L, Shi HF, Gao CY, Han CM. (2007). Chitosan-hyaluronic acid hybrid film as a novel wound dressing: *in vitro* and *in vivo* studies. *Polym Advan Technol* 18, 869-875.
- Ya GV, Tolstoguzov VB. (1997). Thermodynamic incompatibility of proteins and polysaccharides in solutions. *Food Hydrocolloid* 11, 145-158.
- Yamane S, Iwasaki N, Majima T, Funakoshi T, Masuko T, Harada K, Minami A, Monde K, Nishimura S. (2005). Feasibility of chitosan-based hyaluronic acid hybrid
- Yan JH, Qi NM, Zhang QQ. (2007). Rabbit articular chondrocytes seeded on collagen-chitosan-GAG scaffold for cartilage tissue engineering *in vivo*. *Artif Cell Blood Sub*, 35, 333-344.
- Yan J. H., Li XM, Liu LR, Wang FJ, Zhu TW, Zhang QQ. (2006). Potential use of collagen-chitosan-hyaluronan tri copolymer scaffold for cartilage tissue engineering *Artif Cells Blood Sub* 34, 27-39.
- Yan Y, Wang X, Pan Y, Liu H, Cheng J, Xiong Z, Lin F, Wu R, Zhang R, Lu Q. (2005). Fabrication of viable tissue-engineered constructs with 3D cell-assembly technique. *Biomaterials*, 26, 5864-5871.
- Yan Y, Wang X, Pan Y, Liu H, Cheng J, Xiong Z, Lin F, Wu R, Zhang R, Lu Q. (2005b). Fabrication of viable tissue-engineered constructs with 3D cell-assembly technique. *Biomaterials* 26,5864-5871.
- Yang F, Li X, Cheng M, Gong Y, Zhao N, Zhang X. (2002). Performance modification of chitosan membranes induced by gamma irradiation. *J Biomater Appl*, 16, 215-226.
- Yang J, Chung TW, Nagaoka M, Goto M, Cho CS, Akaike T. (2001). Hepatocyte-specific porous polymer-scaffolds of alginate/galactosylated chitosan sponge for liver-Tissue Eng. *Biotechnol Lett* 23, 1385-1389.
- Yannas IV, Burke JF. (1980). Design of an artificial skin. I. Basic design principles. *J Biomed Mater Res*, 14, 65-81.
- Yin YJ, Li ZY, Sun YB, Yao KD. (2005). A preliminary study on chitosan/gelatin polyelectrolyte complex formation. *J Mater Sci*, 40, 4649-4652.
- Yin YJ, Yao KD, Cheng GX, Ma JB. (1999). Properties of polyelectrolyte complex films of chitosan and gelatin. *Polym Int*, 48, 429-432.
- Yoo HS, Lee EA, Yoon JJ, Park TG. (2005). Hyaluronic acid modified biodegradable scaffolds for cartilage Tissue Eng. *Biomaterials*, 26, 1925-1933.
- Yu X, Bichtelen A, Wang XH, Yan YN, Lin F, Xiong Z, Wu RD, Zhang RJ, Lu QP. (2005). Collagen/chitosan/heparin complex with improved biocompatibility for hepatic Tissue Eng. *J Bioact Compat Pol*, 20, 15-28.
- Zhou YS, Yang DZ, Chen XM, Xu Q, Lu FM, Nie J. (2008). Electrospun water-soluble carboxyethyl chitosan/poly(vinyl alcohol) nanofibrous membrane as potential wound dressing for skin regeneration. *Biomacromolecules*, 9, 349-354.
- Zhu X, Chian KS, Chan-Park MBE, Lee ST. (2005). Effect of argon-plasma treatment on proliferation of human-skin-derived fibroblast on chitosan membrane *in vitro*. *J Biomed Mater Res A*, 73A, 264-274.