



Predicting the compressive and tensile strength of rocks from indentation hardness index

by S. Kahraman*, M. Fener†, and E. Kozman‡

Synopsis

The prediction of rock properties from indirect testing methods is important, particularly for preliminary investigations since indirect tests are easier and cheaper than the direct tests. In this study, we investigate the predictability of the uniaxial compressive strength (*UCS*) and Brazilian tensile strength (*BTS*) of rocks from the indentation hardness index (*IHI*) obtained using point load apparatus. Forty-six different rock types, 14 of which were igneous, 15 were metamorphic, and 17 were sedimentary were tested in the laboratory. The *UCS* and *BTS* values were correlated with the corresponding *IHI* values and the results were statistically analysed. The influence of rock classes on the relationships was also investigated. A strong correlation between *UCS* and *IHI* was found for all data. The correlation between *BTS* and *IHI* is not as strong as the correlation between *UCS* and *IHI*. However, it is in the acceptable limits. When the regression analyses were repeated for igneous, metamorphic, and sedimentary rocks, the correlation coefficients were generally increased.

The results show the *UCS* and *BTS* can be estimated from *IHI*. In addition, the effect of rock classes on the relationships between *IHI* and both *UCS* and *BTS* is important.

Keywords

uniaxial compressive strength, Brazilian tensile strength, indentation hardness index

Introduction

Rock engineers have commonly used the uniaxial compressive strength (*UCS*) and Brazilian tensile strength (*BTS*) of rock for designing surface and underground structures. Determining these rock strengths is time-consuming and expensive, particularly for the preliminary studies of projects. For this reason, indirect tests such as Schmidt rebound number and, ultrasonic test are often used for predicting rock strength. Since indirect tests require less or no sample preparation and the testing equipment is less sophisticated, these tests are very easy to carry out. In addition, these tests can usually be performed in the field. The indentation hardness test is a simple and easy test and can be conducted using a point load test apparatus. The test is of particular value when only a limited amount of

rock material, e.g. a thin disc of core or a small lump sample, is available¹. The *UCS* and *BTS* can easily be predicted from the indentation hardness index (*IHI*) for the preliminary investigations, if strong predictive correlations are established.

Since rock indentation is the basic process in drilling and boring, numerous researchers²⁻¹⁶ have carried out indentation tests to understand the indentation phenomena or to develop prediction models for drilling or boring. Kahraman *et al.*¹⁵ also investigated the relationships between the slope of load-indentation curves and the rock properties. They found good correlations between the slope of load-indentation curves and the rock properties. Kahraman and Gunaydin¹⁷ investigated the sawability prediction of carbonate rocks from indentation hardness tests carried out by attaching a dial gauge to the point load apparatus for measuring penetration. They concluded that the indentation hardness test can be used for predicting the sawability of carbonate rocks. Recently, Yagiz¹⁸ suggested a new brittleness index and rock brittleness classification based on type, strength, and density of rock together with the results of punch penetration tests.

A standard indentation test was recommended by ISRM¹ and Equation [1] was suggested for the prediction of *UCS* from *IHI*

$$UCS = 3.1IHI^{1.09} \quad [1]$$

where *UCS* is the uniaxial compressive strength (MPa) and *IHI* is the indentation hardness index (kN/mm).

* Mining Engineering Department, Nigde University, Turkey.

† Geological Engineering Department, Nigde University, Turkey.

‡ Graduate School of Natural and Applied Sciences, Nigde University, Turkey.

© The Southern African Institute of Mining and Metallurgy, 2012. SA ISSN 0038-223X/3.00 + 0.00. Paper received Jan. 2012; revised paper received Jan. 2012.

Predicting the compressive and tensile strength of rocks from indentation hardness index

Equation [1] was obtained from the *IHI* testing performed on ultramafic and basaltic rocks. In this study, the relation between *IHI* and both *UCS* and *BTS* was investigated for igneous, metamorphic, and sedimentary rocks.

The main objective of this study is to investigate the predictability of the *UCS* and *BTS* of rocks from the *IHI* obtained using a point load apparatus. For this reason, 46 different rock types, including igneous, metamorphic, and sedimentary rocks were tested in the laboratory. The test results were statistically analysed and the *UCS* and *BTS* values were correlated with the corresponding *IHI* values. In addition, the influence of rock classes on the relationships was investigated.

Sampling

Rock blocks were collected from natural outcrops, stone and marble quarries, and stone processing plants in the Nigde, Kayseri, Konya, Antalya, and Afyon areas of Turkey for laboratory testing. Block samples were inspected for

macroscopic defects to provide test specimens free from fractures, partings, or alteration zones. A total of 46 different rock types were sampled, 14 of which were igneous, 15 were metamorphic, and 17 were sedimentary. Table I shows the locations and names of the rocks sampled.

Experimental studies

Indentation hardness test

The indentation hardness test suggested by ISRM¹ requires a loading system having a capacity of 30 kN and a conical platen having a 60° cone and 5 mm radius spherical tip. A point load apparatus is suitable for this purpose. After attaching a dial gauge to the point load apparatus for measuring penetration, indentation hardness tests can be carried out.

NX core samples having a height-to-diameter ratio of at least 0.75 were used in the tests. The surfaces of the samples were diamond-sawed. The samples were cemented into a steel frame using a high-grade plaster having a compressive

Table I

The location and name of the rocks sampled

Rock code	Location	Rock type	Rock class
1	Altinhisar/Nigde	Basalt	Igneous
2	Yesilburc/Nigde	Andesite	Igneous
3	Ulukisla/Nigde	Tracheandesite	Igneous
4	Meke/Konya	Volcanic bomb	Igneous
5	Uckapili/Nigde	Granodiorite	Igneous
6	Uckapili/Nigde	Metagabbro	Igneous
7	Uckapili/Nigde	Granite	Igneous
8	Ortakoy/Aksaray	Granite (Anadolu grey)	Igneous
9	Kaman/Kirsehir	Granite(Kaman rosa)	Igneous
10	Kaman/Kirsehir	Granite (Kircicegi)	Igneous
11	Unknown	Granite (King rosa)	Igneous
12	Porrino/Spain	Granite (Rosa Porrino)	Igneous
13	Porrino/Spain	Granite (Pink Porrino)	Igneous
14	Kozak/Balikesir	Granite	Igneous
15	Gumusler/Nigde	Quartzite	Metamorphic
16	Gumusler/Nigde	Marble	Metamorphic
17	Uckapili/Nigde	Marble	Metamorphic
18	Altindag/Kütahya	Marble	Metamorphic
19	Iscehisar/Afyon	Marble (Afyon sekeri)	Metamorphic
20	Yatagan/Mugla	Marble (Mugla beyazi)	Metamorphic
21	Marmara Island/ Istanbul	Marble	Metamorphic
22	Iscehisar/Afyon	Marble (Kaplan postu)	Metamorphic
23	Milas/Mugla	Marble	Metamorphic
24	Kemalpasas/Bursa	Marble	Metamorphic
25	Gumusler/Nigde	Amphibole schist	Metamorphic
26	Gumusler/Nigde	Gneiss	Metamorphic
27	Gumusler/Nigde	Mica schist	Metamorphic
28	Gumusler/Nigde	Migmatite	Metamorphic
29	Kilavuzkoy/Nigde	Serpentinite	Metamorphic
30	Kolsuz/Nigde	Sandstone	Sedimentary
31	Kavlaktepe/Nigde	Sandstone	Sedimentary
32	Ulukisla/Nigde	Anhydrite	Sedimentary
33	Sogutalan/Bursa	Limestone	Sedimentary
34	Korkuteli/Antalya	Limestone	Sedimentary
35	Yahyali/Kayseri	Dolomitic limestone	Sedimentary
36	Fethiye/Mugla	Limestone	Sedimentary
37	Bunyan/Kayseri	Limestone (Rosa)	Sedimentary
38	Gokbez/Nigde	Travertine	Sedimentary
39	Yildizeli/Sivas	Travertine	Sedimentary
40	Finike/Antalya	Travertine (Limra)	Sedimentary
41	Bucak/Burdur	Travertine (Limra)	Sedimentary
42	Demre/Antalya	Travertine (Demre stone)	Sedimentary
43	Demre/Antalya	Travertine (Limra)	Sedimentary
44	Godene/Konya	Travertine	Sedimentary
45	Mut/Icel	Travertine	Sedimentary
46	Karaman	Travertine	Sedimentary

Predicting the compressive and tensile strength of rocks from indentation hardness index



Figure 1—Cemented samples in the circular steel frames



Figure 2—Indentation testing using point load apparatus

strength of 60.6 MPa (Figure 1). After placing the sample into the centre of the steel frame, viscous plaster was filled into the gap between the steel frame and the sample. The samples were placed on the lower platen of the point load apparatus and loaded up to 20 kN as suggested by ISRM¹. The corresponding penetration was read from the dial gauge (Figure 2). At least three tests were conducted on intact and fine grained samples. On the coarse-grained samples, more than three tests were carried out. *IHI* values were calculated by dividing the maximum load (20 kN in all tests) by the maximum penetration (mm). Figure 3 shows some samples after the *IHI* test.

Uniaxial compressive strength test

Uniaxial compressive strength tests were conducted on prepared core samples, which had a diameter of 38 mm and a length-to-diameter ratio of 2–2.5. The stress rate was applied within the limits of 0.5–1.0 MPa/s. At least five tests were done for each rock type and the average value was recorded as the *UCS*. Figure 4 shows some samples that failed in uniaxial compression tests.

Brazilian tensile strength test

Brazilian tensile strength tests were conducted on core

samples having a diameter of 38 mm and a height-to-diameter ratio of 0.5–1.0. The tensile load on the specimen was applied continuously at a constant stress rate such that failure took place within 5 minutes of loading. At least five samples were tested for each rock type and the results were averaged. Figure 5 shows some samples that failed in Brazilian tensile tests.

Results

The average values of the *IHI*, *UCS*, and *BTS* are listed in Table II. It can be seen that *IHI*, *UCS*, and *BTS* values have wide ranges. Figures 6, 7, and 8 show the histograms of *IHI*, *UCS*, and *BTS* values. The *IHI* values range from 3.7 kN/mm for the Mut/Icel travertine to 186.5 kN/mm for the Altinhisar/Nigde basalt. The *UCS* values range from 24.1 MPa for the Kemalpasa/Bursa marble to 210.6 MPa for the Kilavuzkoy/Nigde serpentinite. The *BTS* values range from 2.2 MPa for the Mut/Icel travertine to 18.1 MPa for the Kilavuzkoy/Nigde serpentinite.



Figure 3—Some samples after IHI test

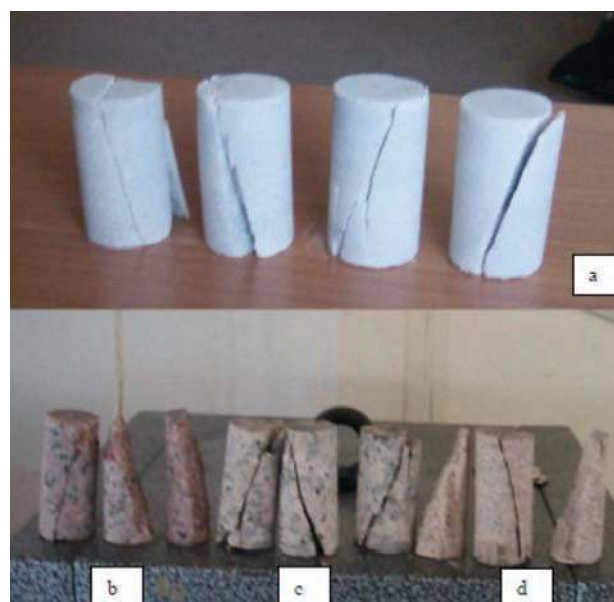


Figure 4—Some samples failed in the uniaxial compression test: a) Milas/Mugla marble, b) unknown granite (King Rosa), c) Kaman/Kirsehir granite (Kaman Rosa), d) Porrino/Spain (Pink Porrino)

Predicting the compressive and tensile strength of rocks from indentation hardness index



Figure 5—Some samples that failed in the Brazilian tensile test: a) Kozak/Balikesir granite b) unknown granite (King Rosa), c) Kaman/Kirsehir granite (Kaman Rosa), e) Marmara Island/ Istanbul marble, f) Iscehisar/Afyon marble (Kaplan postu), g) Uckapili/Nigde marble, h) Milas/Mugla marble

Table II
Indentation hardness index (IHI), uniaxial compressive strength (UCS), Brazilian tensile strength values (BTS), and some statistical parameters

Rock code	Indentation hardness index			Uniaxial compressive strength			Brazilian tensile strength		
	IHI (kN/mm)	Standard deviation	Coeff. of var. (%)	UCS (MPa)	Standard deviation	Coeff. of var. (%)	BTS (MPa)	Standard deviation	Coeff. of var. (%)
1	186.5 (3)*	8.6	4.6	202.9 (6)	10.1	5.0	17.0 (5)	2.30	13.5
2	42.6 (4)	1.7	4.0	77.5 (7)	6.7	8.6	9.0 (6)	0.43	4.8
3	49.2 (5)	7.4	15.1	78.2 (8)	9.3	11.9	8.5 (7)	0.49	5.8
4	27.2 (3)	0.2	0.7	50.2 (5)	5.4	10.8	6.9 (5)	1.06	15.4
5	85.0 (3)	1.8	2.1	109.2 (6)	4.5	4.1	12.1 (7)	1.60	13.2
6	144.8 (3)	5.2	3.6	115.4 (5)	8.2	7.1	10.6 (5)	1.99	18.8
7	119.4 (4)	2.5	2.1	133.2 (8)	5.2	3.9	11.4 (7)	1.75	15.4
8	123.1 (5)	7.4	6.0	114.5 (6)	3.6	3.1	9.0 (5)	0.62	6.9
9	99.1 (5)	1.5	1.5	84.9 (7)	4.7	5.5	8.0 (6)	0.45	5.6
10	51.8 (6)	2.2	4.2	89.6 (6)	5.7	6.4	6.6 (8)	0.76	11.5
11	142.9 (5)	16.3	11.4	120.3 (6)	6.3	5.2	14.8 (5)	1.10	7.4
12	94.8 (4)	15.9	16.8	90.0 (4)	7.2	8.0	7.6 (6)	1.02	13.4
13	98.3 (3)	12.3	12.5	120.0 (5)	7.7	6.4	12.6 (5)	1.31	10.4
14	108.5 (4)	5.7	5.3	121.8 (6)	3.9	3.2	11.6 (7)	0.76	6.6
15	97.6 (3)	3.7	3.8	111.5 (7)	9.5	8.5	13.9 (6)	1.38	9.9
16	45.5 (3)	1.9	4.2	69.8 (8)	8.0	11.5	9.9 (7)	0.70	7.1
17	56.3 (3)	2.1	3.7	90.5 (8)	4.3	4.8	5.7 (7)	0.52	9.1
18	41.7 (3)	2.1	5.0	73.4 (6)	5.6	7.6	10.2 (5)	0.60	5.9
19	36.7 (3)	2.6	7.1	68.5 (7)	0.8	1.2	8.4 (6)	0.37	4.4
20	22.5 (3)	3.6	16.0	35.2 (6)	3.6	10.2	5.7 (5)	0.31	5.4
21	25.0 (3)	2.1	8.4	55.3 (5)	5.9	10.7	6.1 (6)	0.94	15.4
22	16.7 (4)	1.8	10.8	28.9 (7)	3.6	12.5	5.8 (6)	0.90	15.5
23	20.0 (3)	0.5	2.5	31.9 (6)	0.7	2.2	4.9 (5)	0.61	12.4
24	20.4 (3)	1.0	4.9	24.1 (5)	2.8	11.6	6.7 (5)	0.60	9.0
25	112.9 (3)	6.6	5.8	186.5 (7)	13.4	7.2	16.6 (8)	1.60	9.6
26	55.3 (4)	4.3	7.8	85.9 (8)	9.9	11.5	14.3 (8)	1.00	7.0
27	45.5 (3)	2.9	6.4	70.9 (6)	6.6	9.3	9.4 (5)	0.65	6.9
28	133.3 (3)	4.9	3.7	203.6 (5)	15.1	7.4	17.2 (7)	0.60	3.5
29	116.0 (3)	4.4	3.8	210.6 (6)	9.2	4.4	18.1 (5)	1.00	5.5
30	97.4 (4)	12.2	12.5	120.3 (7)	5.8	4.8	10.6 (5)	0.74	7.0
31	107.3 (3)	6.7	6.2	168.6 (5)	6.7	4.0	15.7 (5)	0.31	2.0
32	29.1 (3)	0.3	1.0	48.8 (6)	3.9	8.0	5.2 (8)	0.68	13.1
33	100.0 (3)	12.7	12.7	128.8 (8)	16.3	12.7	6.2 (7)	0.51	8.2
34	94.0 (3)	8.5	6.7	134.2 (6)	8.9	6.6	6.0 (8)	0.54	9.0
35	104.3 (4)	5.1	4.9	136.7 (8)	4.8	3.5	10.2 (8)	1.21	11.9
36	74.2 (5)	6.3	8.5	79.5 (7)	4.2	5.3	5.5 (7)	0.50	9.1
37	118.6 (4)	3.5	3.0	175.0 (6)	13.5	7.7	7.4 (7)	0.63	8.5
38	54.6 (4)	3.2	5.9	87.8 (8)	9.6	10.9	5.5 (6)	0.85	15.5
39	65.5 (4)	2.3	3.5	83.3 (7)	6.0	7.2	5.8 (8)	0.55	9.5
40	24.9 (3)	2.0	8.0	80.0 (5)	3.9	4.9	4.3 (6)	0.32	7.4
41	21.5 (3)	2.4	11.2	50.3 (6)	5.2	10.3	2.8 (6)	0.23	8.2
42	37.8 (3)	3.2	8.5	57.6 (5)	5.7	9.9	4.8 (7)	0.53	11.0
43	52.4 (4)	1.6	3.1	112.3 (7)	3.6	3.2	4.0 (5)	0.34	8.5
44	25.3 (4)	0.6	2.5	45.4 (8)	6.3	13.9	4.6 (8)	0.41	8.9
45	3.7 (5)	0.2	4.6	30.4 (8)	3.1	10.2	2.2 (7)	0.20	9.1
46	15.4 (4)	1.3	8.4	50.3 (7)	6.1	12.1	4.1 (7)	0.44	10.7
Overall average			6.4			7.5			9.4

*The values in the parenthesis show the number of tested samples

Predicting the compressive and tensile strength of rocks from indentation hardness index

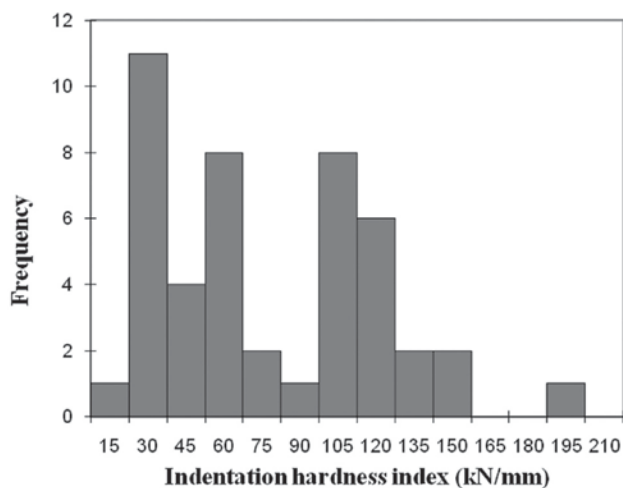


Figure 6—Histogram of IHI values

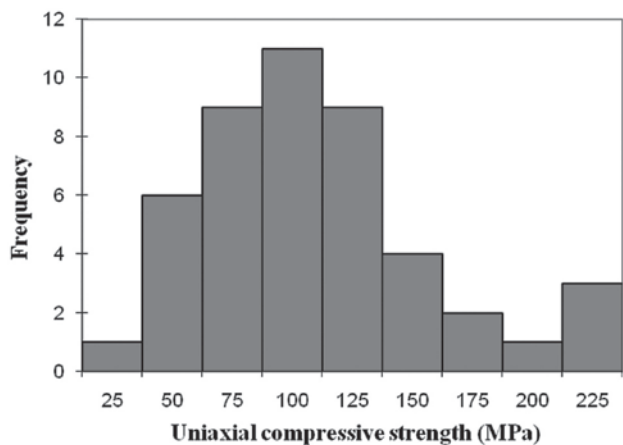


Figure 7—Histogram of UCS values

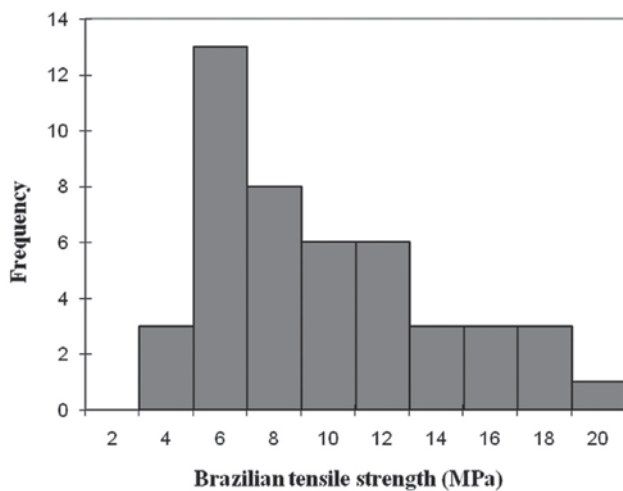


Figure 8—Histogram of BTS values

The coefficients of variation (*CoV*) were determined to evaluate the variability of the test results for each test and each rock type. The *CoV* is calculated by dividing the

standard deviation by the population mean and expressing it as a percentage. The higher the *CoV*, the more variable are the results of a given test. Figures 9, 10, and 11 show the histograms of *CoV* of *IHI*, *UCS*, and *BTS* values respectively. The histograms of *CoV* were plotted for each rock type for *IHI*, *UCS* and *BTS*, respectively and examined. It was seen

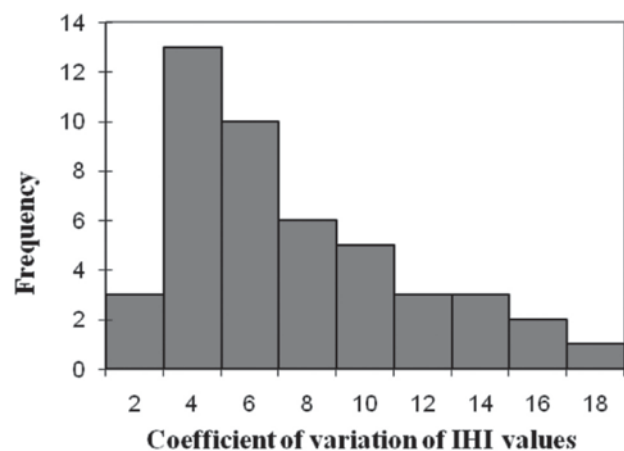


Figure 9—Histogram of coefficient of variation of IHI values

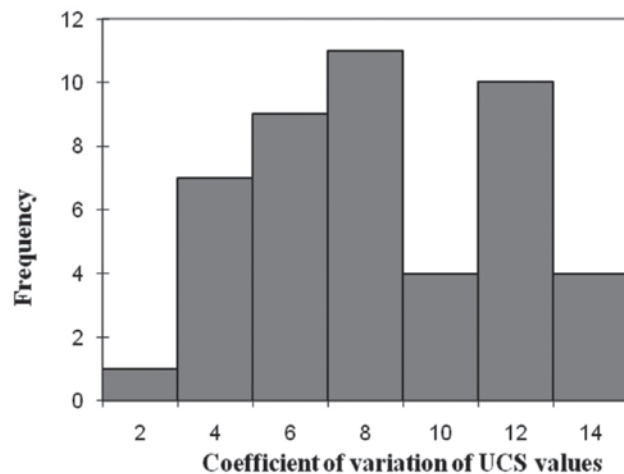


Figure 10—Histogram of coefficient of variation of UCS values

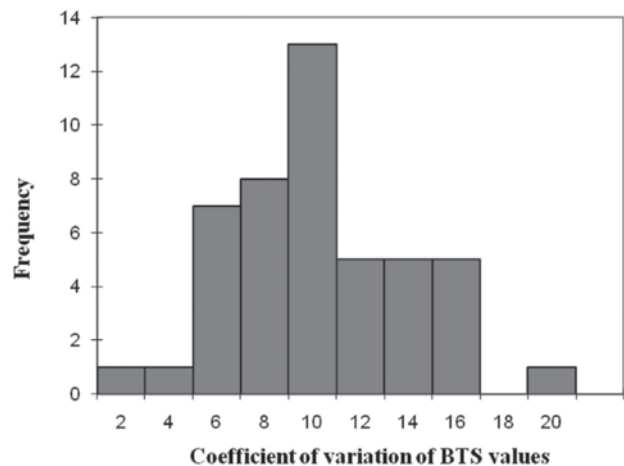


Figure 11—Histogram of coefficient of variation of BTS values

Predicting the compressive and tensile strength of rocks from indentation hardness index

that these plots reflect the plots for all rocks. The same conclusion can be drawn from the *CoV* values in Table II. For this reason, these plots were not included in this paper. The *CoV* of *IHI* values ranges from 0.7 percent for the Meke/Konya volcanic bomb to 16.8 percent for the Porrino/Spain granite, with an overall average of 6.4 percent. The *CoV* of *UCS* values ranges from 1.2 percent for the Iscehisar/Afyon marble to 13.9 percent for the Godene/Konya travertine, with an overall average of 7.5 percent. The *CoV* of *BTS* values ranges from 2.0 percent for the Kavlakepe/Nigde sandstone to 18.8 percent for the Uckapili/Nigde metagabro, with an overall average of 9.4 percent. The variability of each test is within the acceptable limits for most engineering purposes.

Most of rocks have a compressive strength that is approximately 10 times greater than the tensile strength²⁰. The data was evaluated to check whether the *UCS* is correlated to the *BTS*. As shown in Figure 12, there is a fairly good correlation between the *UCS* and the *BTS*, although the data is slightly scattered. The ratio between the *UCS* and the *BTS* is consistent with the literature.

Evaluation of the results

The test results given in Table II were analysed using the method of least squares regression. Linear, logarithmic, exponential, and power curve fitting approximations were executed and the best approximation equation with highest correlation coefficient was determined for each regression.

Uniaxial compressive strength—indentation hardness index correlation

A good linear correlation between the *IHI* and the *UCS* was found for all data (Figure 13). The equation of the line is:

$$UCS = 0.97IHI + 28.28 \quad R^2 = 0.76 \quad [2]$$

where *UCS* is the uniaxial compressive strength (MPa) and *IHI* is the indentation hardness index (kN/mm).

Figure 14 shows the difference between Equations [1] and [2]. The difference is probably due to the fact that the rock types tested are different in the two studies. Equation [1] was derived from the study carried out on ultramafic and basaltic rocks.

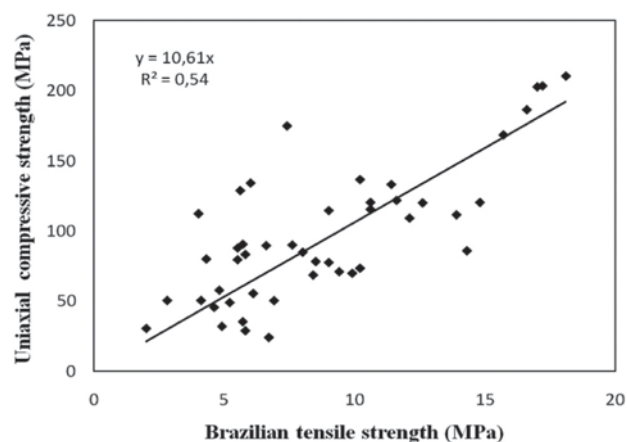


Figure 12—Correlation between the uniaxial compressive strength and Brazilian tensile strength

The data points in Figure 13 are scattered at high strength. To see how the correlation varies with the rock class, separate regression analyses were performed for igneous rocks, metamorphic rocks, and sedimentary rocks. As shown in Figures 15–17, the correlation coefficients are generally higher than that of Figure 13. The equations of the curves are given in Table III.

Tensile strength—indentation hardness index correlation

A linear correlation between the *IHI* and the *BTS* was found for all data (Figure 18). The equation of the line is:

$$BTS = 0.07IHI + 3.79 \quad R^2 = 0.58 \quad [3]$$

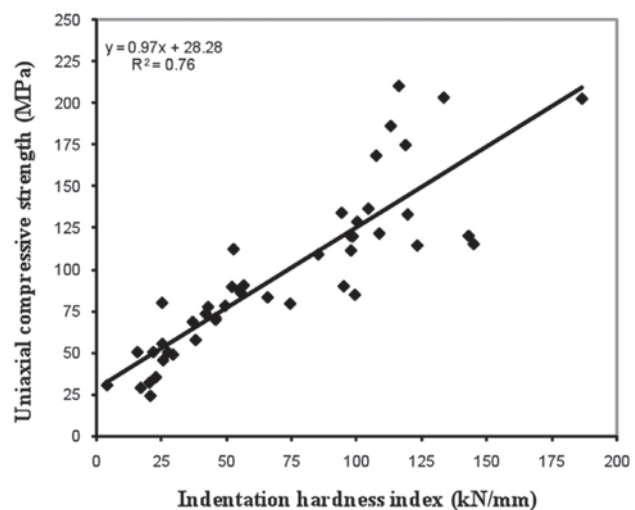


Figure 13—Correlation between uniaxial compressive strength and indentation hardness index for all tested rocks

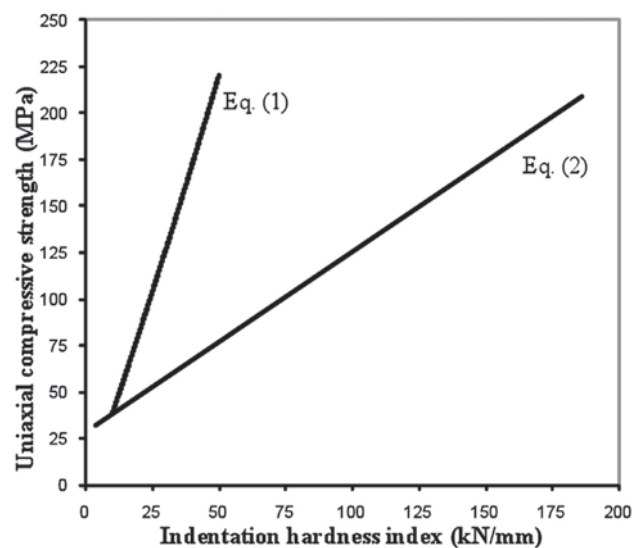


Figure 14—Comparison between Equation (1) derived by Szwedzicki¹⁹ and Equation (2) derived in this study

Predicting the compressive and tensile strength of rocks from indentation hardness index

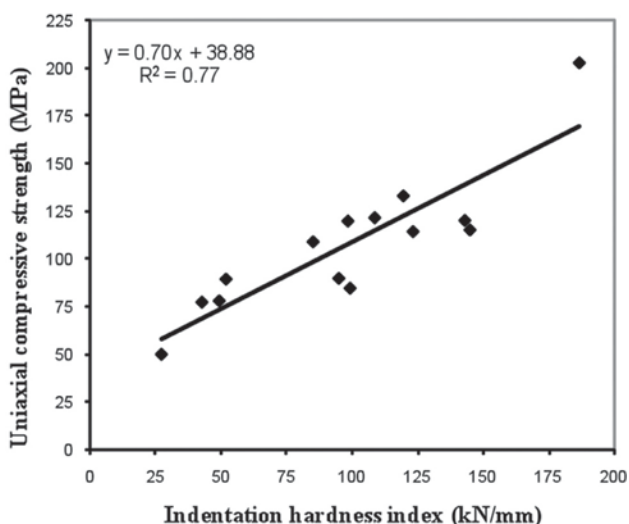


Figure 15—Correlation between uniaxial compressive strength and indentation hardness index for igneous rocks

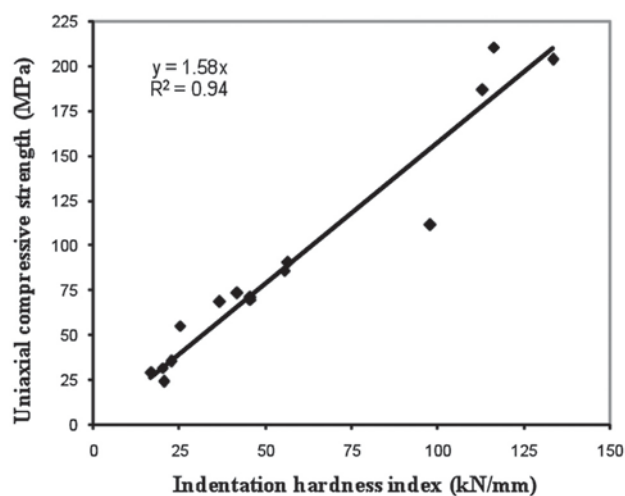


Figure 16—Correlation between uniaxial compressive strength and indentation hardness index for metamorphic rocks

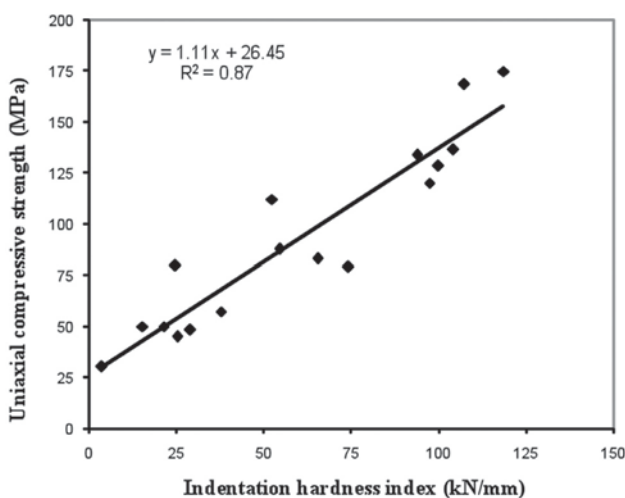


Figure 17—Correlation between uniaxial compressive strength and indentation hardness index for sedimentary rocks

where *BTS* is the Brazilian tensile strength (MPa) and *IHI* is the indentation hardness index (kN/mm).

The data points in Figure 18 are relatively scattered comparing to Figure 13, indicating the relationship between the *IHI* and the *UCS*. The scattering of data is probably due to the fact that the average *CoV* value (9.4 percent) of the *BTS* values is higher than the the average *CoV* value (7.5 percent) of the *UCS* values.

To see how the correlation varies with the rock class, separate regression analyses were performed for igneous rocks, metamorphic rocks, and sedimentary rocks, respectively. As shown in Figures 19–21, the correlation coefficients are generally higher than that of Figure 18. The equations of the curves are given in Table IV.

Validation of the derived models

As shown above, the correlation coefficients of all the equations are good, but they do not necessarily show the validity of the model. Validation of the equations was checked by the *t*- and *F*-tests.

The significance of R^2 values can be determined by the *t*-test, assuming that both variables (dependent and independent variables) are normally distributed and the observations are chosen randomly. The test compares the computed *t*-value with the tabulated *t*-value using the null hypothesis. In this test, a 95 percent level of confidence was chosen. If the computed *t*-value is greater than the tabulated

Table III
The relations between the *UCS* and *IHI* for igneous rocks, metamorphic rocks and sedimentary rocks, respectively

Rock type	<i>UCS</i> equation	Correlation coefficient (R^2)	Equation number
Igneous	$UCS = 0.70 IHI + 38.88$	0.77	[3]
Metamorphic	$UCS = 1.58 IHI$	0.94	[4]
Sedimentary	$UCS = 1.11 IHI + 26.45$	0.87	[5]

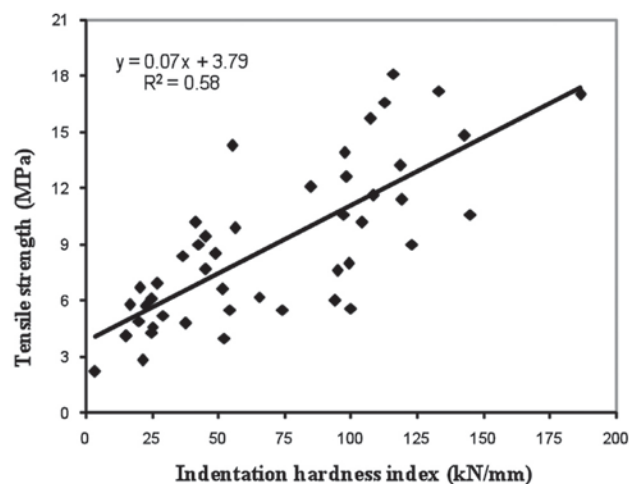


Figure 18—The correlation between tensile strength and indentation hardness index for all tested rocks

Predicting the compressive and tensile strength of rocks from indentation hardness index

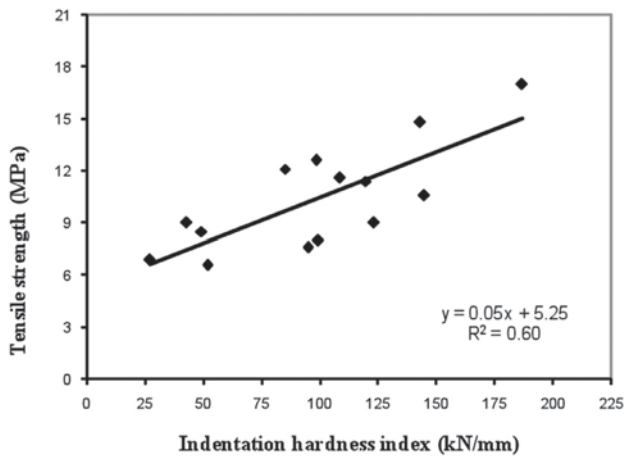


Figure 19—Correlation between tensile strength and indentation hardness index for igneous rocks

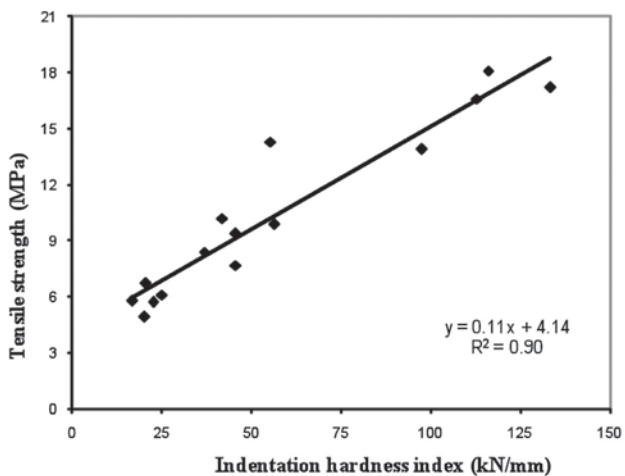


Figure 20—Correlation between tensile strength and indentation hardness index for metamorphic rocks

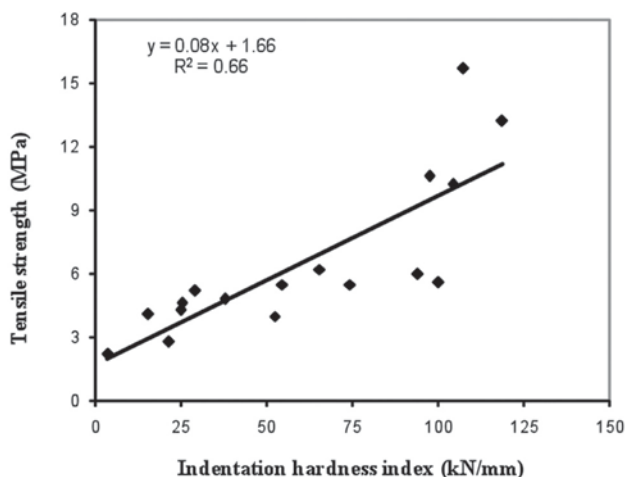


Figure 21—Correlation between tensile strength and indentation hardness index for sedimentary rocks

t -value, the null hypothesis is rejected. This means that R^2 is significant. If the computed t -value is less than the tabulated t -value, the null hypothesis is not rejected. In this case, R^2 is not significant. As seen in Table V, the computed t -values are

greater than tabulated t -values for the all equations except Equation [3]. All models except Equation [3] are valid, and there is some doubt about Equation [3].

The significance of the regressions was determined by analysis of variance. In this test, a 95 percent level of confidence was chosen. If the computed F -value is greater than tabulated F -value, the null hypothesis that there is a real relation between dependent (UCS and BTS) and independent variables (IHI) is rejected. Since the computed F -values are greater than tabulated F -values for the all equations except Equations [3] and [4], the null hypothesis is rejected (Table V). Therefore, it is concluded that all models except Equations [3] and [4] are valid, although there are some doubt about Equations [3] and [4].

Since there are some doubt about Equations [3] and [4], the estimation capabilities of these equations were investigated using the scatter diagrams of the observed and estimated values. Ideally, on a plot of observed versus estimated values the points should be scattered around the 1:1 diagonal straight line. A point lying on the line indicates an exact estimation. A systematic deviation from this line may indicate, for example, that larger errors tend to accompany larger estimations, suggesting non-linearity in one or more variables. As shown in Figures 22 and 23, the points in the plots of estimated versus observed values for Equations [3] and [4] are scattered uniformly about the diagonal line, suggesting that the models are reasonable.

Table IV

The relationships between the BTS and IHI for igneous rocks, metamorphic rocks, and sedimentary rocks

Rock type	BTS equation	Correlation coefficient (R^2)	Equation number
Igneous	$BTS = 0.05 IHI + 5.25$	0.60	[7]
Metamorphic	$BTS = 0.11 IHI + 4.14$	0.90	[8]
Sedimentary	$BTS = 0.08 IHI + 1.66$	0.66	[9]

Table V

t - and F -test results

Equation no	t -tabulated	t -test	F -tabulated	F -test
2	± 1.68	-7.45	3.59	7.36
3	± 1.77	-1.66	4.22	0.39
4	± 1.76	-4.96	4.19	3.08
5	± 1.75	-8.33	4.15	5.47
6	± 1.68	10.30	3.95	91.48
7	± 1.77	7.73	4.23	53.52
8	± 1.76	5.11	4.20	20.50
9	± 1.75	6.35	4.15	35.07

Conclusions

The prediction of rock properties from indirect tests is useful and economical particularly for preliminary investigations. The predictability of the UCS and BTS of rocks from IHI tests carried out using the point load apparatus was investigated in this study. Forty-six different rock types including igneous,

Predicting the compressive and tensile strength of rocks from indentation hardness index

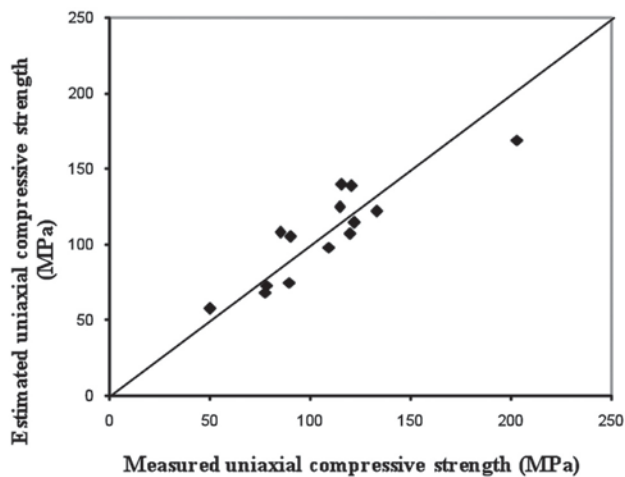


Figure 22—Measured versus estimated uniaxial compressive strength for Equation [3] indicating the relation between the UCS and *IHI* for igneous rocks

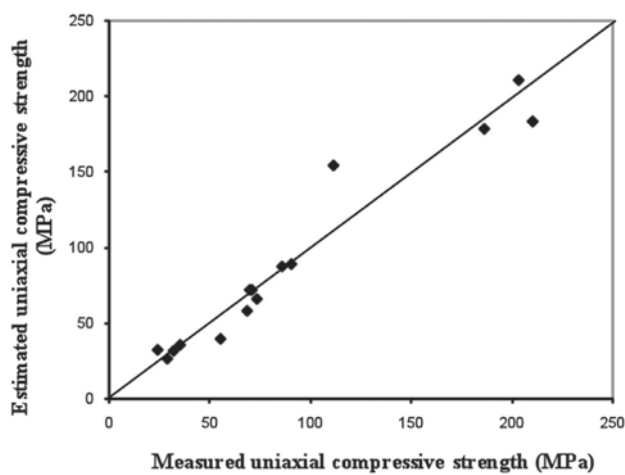


Figure 23—Measured versus estimated uniaxial compressive strength for Equation [4] indicating the relation between the UCS and *IHI* for metamorphic rocks

metamorphic, and sedimentary rocks, were collected from the field and tested in the laboratory. The test results were statistically analysed and the *UCS* and *BTS* values were correlated with the corresponding *IHI* values. The data were evaluated for all rock types and for rock classes separately. A strong correlation ($R^2 = 0.76$) between *UCS* and *IHI* was found for all data. The correlation between *BTS* and *IHI* is also good ($R^2 = 0.58$), but not as strong as the correlation between *UCS* and *IHI*. To see the influence of rock classes on the relations, regression analyses were repeated for igneous, metamorphic, and sedimentary rocks separately, and it was shown that the correlation coefficients were generally increased. Confirmation of the derived models was carried out by the *t*-test, and *F*-test and the scatter diagrams of the observed and estimated values, and it was concluded that the derived models were valid.

The study covers the three rock classes igneous, metamorphic, and sedimentary, and a remarkable number of samples were tested. The samples were collected from almost

all over Turkey. Therefore, it is thought that the derived relationships are expected to be stable for different geotechnical regions.

The main conclusion of this study is that the *UCS* and *BTS* can be estimated from the *IHI*. The effect of rock classes on the relationship between *IHI* and both *UCS* and *BTS* is important.

References

1. SZWEDZICKI, T. Draft ISRM suggested methods for determining the indentation hardness index of rock materials. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 35, 1998. pp. 831–835.
2. CHEATHAM, J.B. An analytical study of rock penetration by a single bit-tooth. *8th Annual Drilling and Blasting Symposium*, University of Minnesota, 1958. pp. 1–21.
3. GNIRK, P.F. and CHEATHAM, J.B. Indentation experiments on dry rocks under pressure. *Journal of Petroleum Technology*, September, 1963. pp. 1051–1059.
4. PAUL, B. and SIKARSKIE, D.L. A preliminary theory of static penetration by a rigid wedge into a brittle material. *7th Symposium on Rock Mechanics*, Pennsylvania State University, 1965. pp. 119–148.
5. CHEATHAM, J.B. and PITTMAN, R.W. Plastic limit analysis applied to a simplified drilling problem. *ISRM, Proceedings of 1st Congress*, Lisbon, vol.2, 1966. pp. 93–97.
6. HARTMAN, H.L. The effectiveness of indexing in percussion and rotary drilling. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 6, 1966. pp. 265–278.
7. GNIRK, P.F. An experimental study of indexed single bit-tooth penetration into dry rock at confining pressures of 0 to 7500psi. *ISRM, Proceedings of 1st Congress*, Lisbon, vol. 2, 1966. pp. 121–129.
8. PARISEAU, W.G. and FAIRHURST, C. The force-penetration characteristic for wedge penetration into rock. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 14, 1967. pp. 165–180.
9. MILLER, M.H. and SIKARSKIE, D.L. On the penetration of rock by three-dimensional indentors. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 5, 1968. pp. 375–398.
10. BENJUMEA, R. and SIKARSKIE, D.L. A note on the penetration of a rigid wedge into a nonisotropic brittle material. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 6, 1969. pp. 343–352.
11. MORRIS, R.I. Rock drillability related to a roller cone bit. *Society of Petroleum Engineers*, Paper No. 2389, 1969. pp. 79–83.
12. LUNDBERG, B. Penetration of rock by conical indentors. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 11, 1974. pp. 209–214.
13. PANG, S.S., GOLDSMITH, W., and HOOD, M. A force-indentation model for brittle rocks. *Rock Mechanics and Rock Engineering*, vol. 22, 1989. pp. 127–148.
14. BILGIN, N., ESKIKAYA, S., and DINCER, T. The performance analysis of large diameter blast hole rotary drills in Turkish Coal Enterprises. *2nd International Symposium on Mine Mechanization and Automation*. Rotterdam, Balkema, 1993. pp. 129–135.
15. KAHRAMAN, S., BALCI, C., YAZICI, S., and BILGIN, N. Prediction of the penetration rate of rotary blast hole drills using a new drillability index. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 37, 2000. pp. 729–743.
16. COPUR, H., BILGIN, N., TUNCDER, H., and BALCI, C. A set of indices based on indentation tests for assessment of rock cutting performance and rock properties. *Journal of The South African Institute of Mining and Metallurgy*, vol. 103, no. 9, 2003. pp. 589–600.
17. KAHRAMAN, S. and GUNAYDIN, O. Indentation hardness test to estimate the sawability prediction of carbonate rocks. *Bulletin of Engineering Geology and the Environment*, vol. 67, 2008. pp. 507–511.
18. YAGIZ, S. Assessment of brittleness using rock strength and density with punch penetration test. *Tunnelling and Underground Space Technology*, vol. 24, 2009. pp. 66–74.
19. SZWEDZICKI, T. The indentation hardness testing of rock. *International Journal of Rock Mechanics and Mining Sciences & Geomechanics Abstracts*, vol. 35, 1998. pp. 825–829.
20. SHEOREY, P.R. *Empirical Rock Failure Criteria*, Rotterdam, A.A. Balkema, 1997. 176 pp. ◆